
FED SUP CLASS
6140

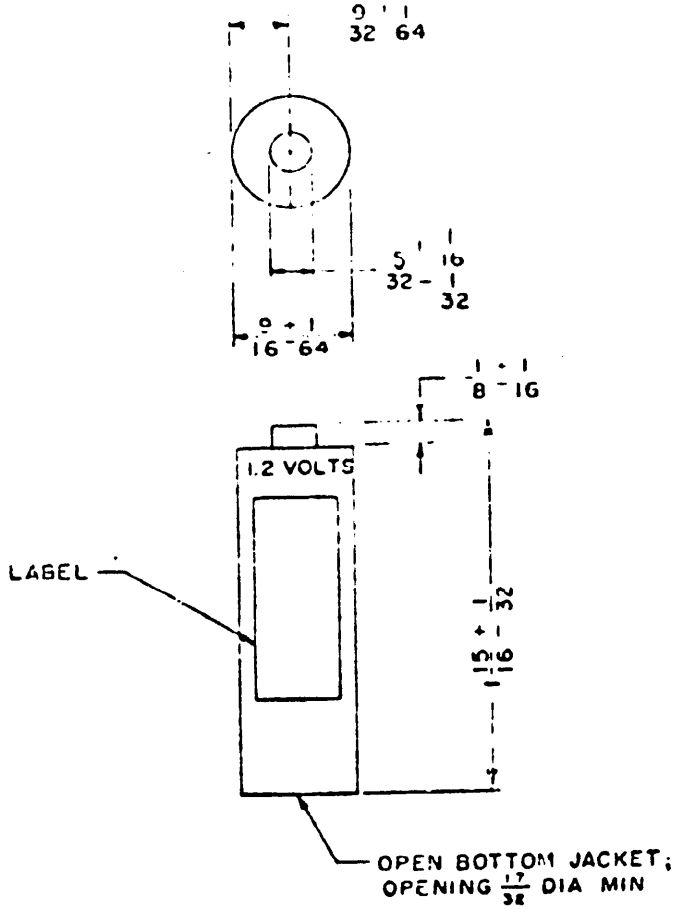

NOTES:

1. ALL DIMENSIONS IN INCHES.
2. For design feature purposes, this Standard takes precedence over procurement documents referenced herein.
3. Referenced documents shall be of the issue in effect on date of invitations for bids.

APPROVED 19 May 1961 REVISED

P.A. Sig C Other Cust	TITLE BATTERY, STORAGE BB-417( )/U	MILITARY STANDARD MS 75033 (SigC)
Procurement Specification MIL-B-55139(SigC)	SUPERSEDES	SHEET 1 OF 2

DD FORM 672 (Listed coord(nation) previous editions of this form are obsolete.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T20:27Z
Check the source to verify that this is the current version before use.

ELECTRICAL AND PHYSICAL REQUIREMENTS

FED SUP CLASS 6140

Class	Sealed Cell
Voltages	
Nominal	1.20
Final (Unless otherwise specified)	1.00
Rated Capacity (C_5)	0.450 A.H.
Charge Rate ($0.2C_5$)	0.090 Amps
Discharge Rates	
$0.2C_5$	0.090 Amps
$3\ C_5$	1.35 Amps
Terminals	Button Type
Max. Weight	1 oz
Container	Nickel-Cadmium Cold Rolled Steel, or equal
Number & Type of Cells	1 "AA" Cell

PRODUCTION SAMPLING TESTS

Tests	Test Para.	Minimum Test Value
Initial Full Capacity Discharge	4.9 .1.1	0.45 A.H.
Full Capacity Discharge	4.9 .1	0.45 A.H.
Low Temp. Discharge	4.9 .2	
Test I	4.9 .2.1	0.40 A.H.
Test II	4.9 .2.2	0.23 A.H.
High Rate Discharge	4.9 .4	
5-second voltage		1.15 volt
Minutes to 1.0 volt		15 Minutes
* Intermittent Discharge	4.9 .3	450 Minutes
Overcharge Test	4.14	0.45 A.H.
Cycle Life Test- Test I	4.12.1	400 Cycles

* Discharge through 20 ohms for 4 minutes each hour, 10 hours per day, 5 days per week to a cut-off voltage of 0.93 volt.

Retention of Charge		
Test I	4.15.1	0.34 A. H.
Test II	4.15.2	0.16 A. H.

APPROVED 19 May 1961 REVISED

Signal Corps

AMSC N/A Sig C	TITLE	MILITARY STANDARD
FSC 6140	Battery, Storage, BB-417( )/U	MS 75033 (SigC)
MIL-B-55130(SigC)	SUPERSEDES	SHEET 2 OF

DD FORM 672 (Limited coordination)

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T20:27Z
Check the source to verify that this is the current version before use.