INCH-POUND

MIL-S-13949/29A
18 May 1993
SUPERSEDING
MIL-S-13949/29
4 October 1991

MILITARY SPECIFICATION SHEET

SHEET, PRINTED WIRING BOARD, LAMINATED, BASE MATERIAL GC (WOVEN E-GLASS REINFORCEMENT, MAJORITY CYANATE ESTER RESIN, FLAME RESISTANT, METAL CLAD OR UNCLAD)

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and the issue of the following specification listed in that issue of the Department of Defense Index of Specifications and Standards (DODISS) specified in the solicitation: MIL-S-13949.

REQUIREMENTS:

Reinforcement material: G in accordance with MIL-S-13949.

Resin system: C in accordance with MIL-S-13949.

Special consideration (third letter designator): N in accordance with MIL-S-13949.

Type of metal foil: Any as specified in accordance with MIL-S-13949.

Weight of metal foil: H, 1, 2, or O in accordance with MIL-S-13949.

Solderability: Base materials clad with metal foil types A, B, C, D, G, H, J, K, L, and M shall be tested in accordance with MIL-S-13949. Solderability testing not applicable on all other metal foil types, unless otherwise specified in the ordering data.

Bow and twist: C or X in accordance with MIL-S-13949.

Grade of pits or dents: In accordance with MIL-S-13949.

Qualification inspection routine. The inspection routine shall include the glass transition temperature test in accordance with MIL-S-13949.

Conditioning of specimens prior to test: Unless otherwise specified herein, specimens shall be conditioned in accordance with the applicable test method.

Property values:

Dimensional stability (for base material thicknesses less than .020 inch (0.51 mm)).

After bake: Class A, .00075 inch/inch (0.00075 mm/mm) maximum; class B, .00050 inch/inch (0.00050 mm/mm) maximum.

After stress: Class A, .00075 inch/inch (0.00075 mm/mm) maximum; class B, .00050 inch/inch (0.00050 mm/mm) maximum.

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 202610-18T02:41Z
Check the source to verify that this is the current version before use.

Flammability.

Duration of burning time, each flame application:

Base material thicknesses greater than or equal to .020 inch (0.51 mm).

Average: 25 seconds maximum.

Single: 30 seconds maximum.

Base material thicknesses less than .020 inch (0.51 mm): 15 seconds maximum.

Burn length, average: 12 inches (305 mm) maximum.

Flexural strength (for base material thicknesses greater than or equal to .020 inch (0.51 mm)):

Crosswise: 50,000 pounds per square inch minimum.

Lengthwise: 50,000 pounds per square inch minimum.

Lengthwise at elevated temperature of 204°C: 40,000 pounds per square inch minimum.

Glass transition temperature: 230°C minimum.

Peel strength values for copper foil: See table I.

TABLE I. Peel strength values, minimum pounds per inch of width.

Test and copper foil weight	Base material thickness	
	Less than .020 inch	.020 inch and over
After thermal stress:		
½-oz/ft² (designator H)	4.0	4.0
1-oz/ft² (designator 1)	4.5	4.5
2-oz/ft² (designator 2)	5.5	5.5
At elevated temperature of 125°C:		
½-oz/ft² (designator H)	4.0	4.0
1-oz/ft² (designator 1)	4.5	4.5
2-oz/ft² (designator 2)	5.5	4.5
After exposure to processing solutions:		
½-oz/ft² (designator H)	4.0	4.0
1-oz/ft² (designator 1)	4.5	4.5
2-oz/ft² (designator 2)	5.5	5.5

Arc resistance: 120 seconds minimum.

Dielectric breakdown (for base material thicknesses greater than or equal to .020 inch (0.51 mm)): 40 kilovolts minimum.

Electric strength, average (for base material thicknesses less than .020 inch (0.51 mm)): 750 volts/mil minimum.

Loss tangent at 1 MHz: .015 maximum.

Permittivity at 1 MHz: 4.5 maximum.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:41Z
Check the source to verify that this is the current version before use.

Surface resistivity:

After moisture resistance conditioning: 10^6 megohm minimum.

After elevated temperature (204°C) conditioning (for base material thickness less than .020 inch (0.51 mm)): 10^4 megohm minimum.

After elevated temperature (204°C) conditioning (for base material thickness greater than or equal to .020 inch (0.51 mm)): 10^6 megohm minimum.

Volume resistivity:

After moisture resistance conditioning: 10^6 megohm-cm minimum.


After elevated temperature (204°C) conditioning (for base material thickness less than .020 inch (0.51 mm)): 10^4 megohm-cm minimum.

After elevated temperature (204°C) conditioning (for base material thickness greater than or equal to .020 inch (0.51 mm)): 10^6 megohm-cm minimum.

Water absorption (for base material thicknesses greater than or equal to .020 inch (0.51 mm)): 1.0 percent maximum.

Supersession information: Not applicable.

Type designation: Consists of "GC" prefix followed by coded alphas and numeric characters as shown in the following example:

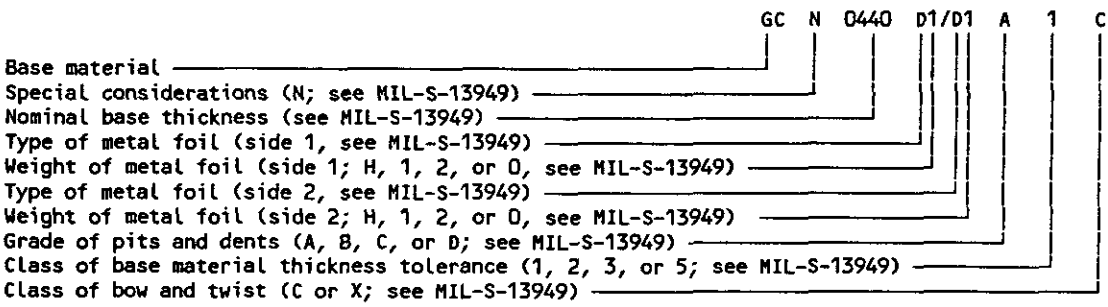

Revision letters are not used to denote changes due to the extensiveness of the changes.

CONCLUDING MATERIAL

Custodians:
Army - ER
Navy - EC
Air Force - 85

Review activities:
Army - AR, MI
Navy - AS, OS, SH
Air Force - 11, 99
NSA - NS
DLA - ES

User activities:
Army - AT, ME
Navy - MC
Air Force - 19

Preparing activity:
Army - ER

Agent:
DLA - ES

(Project 5998-0032-02)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T02:41Z
Check the source to verify that this is the current version before use.