INCH-POUND

FF-S-85F
w/AMENDMENT 3
August 6, 2024
SUPERSEDING
FF-S-85F
w/AMENDMENT 2
September 8, 2023

FEDERAL SPECIFICATION

SCREW, CAP, SLOTTED AND HEXAGON HEAD

The General Services Administration has authorized the use of this federal specification by all federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers the types and styles of slotted and hexagon head cap screws, classified in 1.2.1 (see 6.1).

1.2 Classification.

1.2.1 Types and styles. Cap screws shall be of the following types and styles (see 6.2).

Type I – Slotted head.
Style 1s – Round head (see fig. 4)
Style 2s – Flat countersunk head, 82º (see fig. 4).
Style 4s – Fillister head (see fig. 4).

Type II – Plain head.
Style 10p – Hexagon head (see fig. 4).

1.2.2 Grades. Cap screws of steel material shall be of the following grades (see 6.2).

Grade 2 – Low carbon steel.
Grade 5 – Medium carbon steel.
Grade 8 – Alloy steel.
Grade 9 – High strength alloy steel.

1.2.3 Sizes. The sizes of cap screws shall be classified by the nominal body diameter from 1/4 inch thru 3 inches as specified (see 6.2).

Comments, suggestions, or questions on this document should be addressed to DLA Aviation VEB, 6090 Strathmore Road, Richmond, VA 23237 or emailed to STDZNMGT@dla.mil. Since contact information can change, you may want to verify the accuracy of the address information using the ASSIST online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 Government publications. The following documents, of the issues in effect on the date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

FEDERAL SPECIFICATIONS

QQ-N-281	–	Nickel-Copper Alloy Bar, Rod, Plate, Sheet, Strip, Wire, Forgings, and Structural and Special Shaped Sections
QQ-N-286	–	Nickel-Copper-Aluminum Alloy, Wrought (UNS N05500)

MILITARY SPECIFICATIONS

MIL-DTL-13924	–	Coating, Inorganic, Black, for Ferrous Metals
MIL-DTL-16232	–	Phosphate Coating, Heavy, Manganese or Zinc Base
MIL-DTL-18240	–	Fastener Element, Self-Locking, Threaded Fastener, 250 °F Maximum
MIL-DTL-495	–	Finish, Chemical, Black, for Copper Alloys
MIL-PRF-8625	–	Anodic Coatings for Aluminum and Aluminum Alloy
MIL-PRF-32647	–	Zinc-Nickel Electroplating for Fasteners
MIL-STD-1916	–	DoD Preferred Methods for Acceptance of Product
MS35295	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Medium Carbon Steel, Plain Finish, UNC-2A
MS35302	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Alloy Steel, Plain Finish, UNF-2A
MS35309	–	Screw, Cap, Hexagon Head – Naval Brass, Plain Finish, UNC-2A
MS35310	–	Screw, Cap, Hexagon Head – Naval Brass, Plain Finish, UNF-2A
MS35311	–	Screw, Cap, Hexagon Head – Nickel-Copper Alloy, Plain Finish, UNC-2A
MS35312	–	Screw, Cap, Hexagon Head – Nickel-Copper Alloy, Plain Finish, UNF-2A
MS51099	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Head Drilled for Locking Wire, Steel, Corrosion-Resisting, Passivated, UNC-2A
MS51100	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Head Drilled for Locking Wire, Steel, Corrosion-Resisting, Passivated, UNF-2A
MS51107	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Shank Drilled for Cotter Pin, Alloy Steel, Grade 8, Phosphate Coated, UNC-2A
MS51108	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Shank Drilled for Cotter Pin, Alloy Steel, Grade 8, Phosphate Coated, UNF-2A

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

(Copies of military specifications and standards are available for download from the ASSIST database at https://quicksearch.dla.mil or from the Standardization Document Order Desk, 700 Robbins Ave., Building 4D, Philadelphia PA 19111-5094.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless a specific issue is identified, the issue in effect on date of invitation for bids or request for proposal shall apply.

AMERICAN SOCIETY OF MECHANICAL ENGINEERS (ASME)

ASME B1.1	–	Unified Inch Screw Threads (UN, UNR, and UNJ Thread Forms)
ASME B18.2.1	–	Square, Hex, Heavy Hex, and Askew Head Bolts and Hex, Heavy Hex, Hex Flange, Lobed Head, and Lag Screws (Inch Series)
ASME B46.1	–	Surface Texture (Surface Roughness, Waviness and Lay)

(Private sector and civilian agencies may purchase copies of these voluntary standards from https://www.asme.org.)

ASTM INTERNATIONAL

ASTM A342/A342M	–	Standard Test Methods for Permeability of Weakly Magnetic Materials
ASTM B21/B21M	–	Standard Specification for Naval Brass Rod, Bar, and Shapes
ASTM B138/B138M	–	Standard Specification for Manganese Bronze Rod, Bar, and Shapes
ASTM B139/B139M	–	Standard Specification for Phosphor Bronze Rod, Bar, and Shapes
ASTM B150/B150M	–	Standard Specification for Aluminum Bronze Rod, Bar, and Shapes
ASTM B154	–	Standard Test Method for Mercurous Nitrate Test for Copper Alloys
ASTM B633	–	Standard Specification for Electrodeposited Coatings of Zinc on Iron and Steel
ASTM D3951	–	Standard Practice for Commercial Packaging
ASTM E10	–	Standard Test Method for Brinell Hardness of Metallic Materials
ASTM E18	–	Standard Test Methods for Rockwell Hardness of Metallic Materials
ASTM E112	–	Standard Test Methods for Determining Average Grain Size
ASTM E1282	–	Standard Guide for Specifying the Chemical Compositions and Selecting Sampling Practices and Quantitative Analysis Methods for Metals, Ores, and Related Materials
ASTM E1417/E1417M	–	Standard Practice for Liquid Penetrant Testing
ASTM E1444/E1444M	–	Standard Practice for Magnetic Particle Testing for Aerospace
ASTM F468	–	Standard Specification for Nonferrous Bolts, Hex Cap Screws, Socket Head Cap Screws, and Studs for General Use
ASTM F593	–	Standard Specification for Stainless Steel Bolts, Hex Cap Screws, and Studs

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

ASTM F606/F606M	–	Standard Test Methods for Determining the Mechanical Properties of Externally and Internally Threaded Fasteners, Washers, Direct Tension Indicators, and Rivets
ASTM F788/F788M	–	Standard Specification for Surface Discontinuities of Bolts, Screws, Studs, and Rivets, Inch and Metric Series
ASTM F2328	–	Standard Test Method for Determining Decarburization and Carburization in Hardened and Tempered Threaded Steel Bolts, Screws, Studs, and Nuts

(Private sector and civilian agencies may purchase copies of these voluntary standards from https://www.astm.org)

AMERICAN SOCIETY FOR QUALITY (ASQ)

ASQ H1607	–	Zero Acceptance Number Sampling Plans – Sixth Edition
ASQ Z1.4	–	Sampling Procedures and Tables for Inspection by Attributes

(Private sector and civilian agencies may purchase copies of these voluntary standards from https://asq.org).

AEROSPACE INDUSTRIES ASSOCIATION – NATIONAL AEROSPACE STANDARDS (AIA/NAS)

AIA/NAS NASM1312-6	–	Fastener Test Methods, Method 6, Hardness
AIA/NAS NASM35307	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Steel, Corrosion Resisting, Passivated, UNC-2A
AIA/NAS NASM35308	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Steel, Corrosion Resisting, Passivated, UNF-2A
AIA/NAS NASM51095	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Head Drilled for Locking Wire, Steel, Grade 5, Cadmium Plated, UNC-2A, Plain and Self-Locking
AIA/NAS NASM51096	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Head Drilled for Locking Wire, Steel, Grade 5, Cadmium Plated, UNF-2A, Plain and Self-Locking
AIA/NAS NASM51105	–	Screw, Cap, Hexagon Head, Finished Hexagon Bolt, Shank Drilled for Cotter Pin, Steel, Grade 5, Cadmium Plated, UNC-2A
AIA/NAS NASM51106	–	Screw, Cap, Hexagon Head, Finished Hexagon Bolt, Shank Drilled for Cotter Pin, Steel, Grade 5, Plated, UNF-2A
AIA/NAS NASM51109	–	Screw, Cap, Hexagon Head, Finished Hexagon Bolt, Shank Drilled for Cotter Pin, CRES, Passivated, UNC-2A
AIA/NAS NASM51110	–	Screw, Cap, Hexagon Head, Finished Hexagon Bolt, Shank Drilled for Cotter Pin, CRES, Passivated, UNF-2A
AIA/NAS NASM90725	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Steel, Grade 5, Cadmium Plated, UNC-2A
AIA/NAS NASM90726	–	Screw, Cap, Hexagon Head (Finished Hexagon Bolt), Steel, Grade 5, Cadmium Plated, UNF-2A

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

(Private sector and civilian agencies may purchase copies of these voluntary standards from https://www.aia-aerospace.org.)

SAE INTERNATIONAL

SAE AIR4127	–	Steel: Chemical Composition and Hardenability
SAE AMS2461	–	Plating, Zinc-Nickel Alloy (12 to 16% Ni)
SAE AMS2700	–	Passivation of Corrosion Resistant Steels
SAE AMS4117	–	Aluminum Alloy, Rolled or Cold Finished, Bars, Rods, and Wire and Flash Welded Rings 1.0Mg - 0.60Si - 0.28Cu - 0.20Cr (6061; -T6, -T651) - UNS A96061
SAE AMS-QQ-A-225/6	–	Aluminum Alloy, 2024, Bar, Rod, and Wire; Rolled, Drawn, or Cold Finished - UNS A92024
SAE AMS-QQ-P-416	–	Plating, Cadmium (Electrodeposited)
SAE J429	–	Mechanical and Material Requirements for Externally Threaded Fasteners

(Private sector and civilian agencies may purchase copies of these voluntary standards from https://www.sae.org.)

3. REQUIREMENTS

3.1 Material. Unless otherwise specified in the invitation for bids, contract or order, cap screws shall be made of materials specified in 3.1.1 through 3.1.5 and Table IA (see 6.2).

3.1.1 Low carbon steel. Unless otherwise specified (see 6.2) grade 2 cap screws shall be made of low carbon steel as shown in Table I. The chemical composition shall contain a maximum of 0.28 percent carbon, a maximum of 0.04 percent phosphorus, and a maximum of 0.05 percent sulfur.

3.1.2 Medium carbon steel. Grade 5 cap screws shall be made of medium carbon steel as shown in Table I and conforming to the requirements of SAE AIR4127. The chemical composition shall contain 0.28 to 0.55 percent carbon, a maximum of 0.04 percent phosphorus and a maximum of 0.05 percent sulfur. It shall be quenched and tempered at a minimum temperature of 800 °F. Cap screws of the following standards shall be made in accordance with the specification: MS35295, AIA/NAS NASM51095, AIA/NAS NASM51096, AIA/NAS NASM51105, AIA/NAS NASM51106, AIA/NAS NASM90725, and AIA/NAS NASM90726.

3.1.3 Alloy steels.

3.1.3.1 Alloy steel, Grade 8. Grade 8 cap screws shall be made of alloy steel as shown in Table I and conforming to the requirements of SAE AIR4127. The chemical composition shall contain 0.28 to 0.55 percent carbon, a maximum of 0.04 percent phosphorus, and a maximum of 0.05 percent sulfur. Cap screws of the following standards shall be made in accordance with the specification: MS35302, MS51107, and MS51108.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

Table I. Grades and Mechanical Properties of Steel Cap Screws 0.25 thru 3 Inch Diameters

Grade Designation	Nominal Size Dia., Inch	Proof Load psi	Tensile Strength psi (min)	Hardness			
				Brinell No.		Rockwell	
				Min	Max	Min	Max
2	0.25 thru 0.75*	55,000	74,000	149	241	B80	B100
	Over 0.75 thru 1.5 **	33,000	60,000	121	241	B70	B100
5	0.25 thru 1	85,000	120,000	255	321	C25	C34
	Over 1 thru 1.5	74,000	105,000	223	285	C19	C30
	Over 1.5 thru 3	55,000	90,000	183	235	B90	C21.7
8	0.25 thru 1.5	120,000	150,000	302	352	C33	C39
	Over 1.5 thru 3	85,000	120,000	302	352	C33	C39
9 (High strength alloy)	0.25 thru 1.5	130,000	170,000	336	386	C36	C45

* 6 inches and less in length.
** All diameters if length exceeds 6 inches.

3.1.3.2 Grade 9 alloy steel. The Grade 9 alloy steel shown in Table I shall be grade 8 conforming to the requirements of SAE AIR4127 and the chemical composition of paragraph 3.1.3.1. It shall meet the mechanical properties requirements specified in Table I.

3.1.3.3 Alloy steels. Alloy steels shall be oil-quenched and tempered at a minimum temperature of 800 °F.

3.1.4 Corrosion resisting steels.

3.1.4.1 Austenitic. Austenitic corrosion resisting steel screws shall be manufactured from UNS S30000 series corrosion steel as specified in SAE AIR4127 and meet the mechanical properties specified in 3.2.2.1. Cap screws of AIA/NAS NASM35307 and AIA/NAS NASM35308 shall be made in accordance with the specification.

3.1.4.2 Ferritic and martensitic. Ferritic and martensitic corrosion resisting steel cap screws shall be manufactured from a steel composition such as steel numbers UNS S41000, UNS S41600, and UNS S43000 as specified in SAE AIR4127 and meet the mechanical properties specified in 3.2.2.2. Cap screws of MS51099, MS51100, AIA/NAS NASM51109, and AIA/NAS NASM51110 shall be made in accordance with the specification.

3.1.4.3 Galvanic corrosion. When corrosion resisting steels are used to fasten aluminum or carbon/alloy steel structures, the corrosion resisting steel fastener will cause accelerated corrosion of the structure due to galvanic effects; in this scenario it is recommended to coat corrosion resisting steel fasteners with zinc-nickel per paragraph 3.4.8 in order to protect the aluminum or steel structures.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

3.1.5 Non-ferrous material. Non-ferrous cap screws shall be manufactured from alloys specified in Table IA (see 6.2). Cap screws of MS35309, MS35310, MS35311, and MS35312 shall be made in accordance with the specification. Nickel-copper-aluminum (Ni-Cu-Al) material which has been headed or roll threaded shall not be age hardened unless it has been solution annealed subsequent to the heading and threading operations. Ni-Cu-Al fastener threads formed after the final age hardening heat treatment shall be cut or ground only.

3.1.5.1 Stress relief. Cold worked naval brass screws shall be stress relieved by heating the screws to a temperature of 600 °F and holding at that temperature for a minimum of one hour.

3.1.6 Self-locking element. Non-metallic, self-locking elements shall be in accordance with MIL-DTL-18240.

3.2 Mechanical properties.

3.2.1 Steel. Grades and mechanical properties of low carbon, medium carbon, alloy steel, and high strength alloy steel cap screws shall conform to Table I, as applicable (see 6.2).

3.2.2 Corrosion resisting steel.

3.2.2.1 Austenitic. Unless otherwise specified in the invitation for bids, contract or order, mechanical properties of austenitic corrosion-resisting steel cap screws shall conform to the following for diameters through 5/8 inch:

a.	Ultimate tensile strength	80,000 psi min
b.	Yield strength (0.2 percent offset)	30,000 psi min
c.	Rockwell Hardness	B80 min
d.	Elongation	30 percent min
e.	Reduction in area	40 percent min

For diameters over 5/8 inch, ultimate tensile strength shall be 70,000 psi min. and have a hardness of Rockwell B74 min.

3.2.2.2 Ferritic and martensitic. Unless otherwise specified in the invitation for bids, contract or order, mechanical properties of ferritic and martensitic corrosion-resisting steel cap screws shall conform to the following:

f.	Ultimate tensile strength	70,000 psi min
g.	Yield strength (0.2 percent offset)	40,000 psi min
h.	Brinell hardness	B235 max
i.	Elongation	15
j.	Reduction in area	45

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

3.2.2.3 Nickel-copper-aluminum externally threaded fasteners. Nickel-copper-aluminum material that has been headed or threaded shall not be age hardened unless it has been solution annealed subsequent to the heading and threading operations. Threads formed after the final age hardening heat treatment shall be cut or ground only.

3.2.3 Non-ferrous cap screws. Unless otherwise specified in the invitation for bids, contract or order, mechanical properties of non-ferrous cap screws shall conform to Table IA, as specified (see 6.2).

Table IA. Mechanical Properties of Screws of Non-Ferrous Materials

Material	Applicable Specifications	UNS No. or class	Temper code or condition	Tensile strength psi minimum	Yield strength at 0.2 percent offset or at extension indicated		Elongation minimum
					Minimum psi	Extension under load	
Manganese bronze	ASTM B138/B138M	C67500	O60	55,000	22,000	0.5 percent	20
Aluminum bronze	ASTM B150/B150M	C36200	TQ55 O20 O25	90,000	37,000	0.5 percent	18
Phosphor bronze	ASTM B139/B139M	C51000	H04	60,000	33,000	---	15
Silicon bronze	ASTM F468	C65100	---	60,000	40,000	0.5 percent	10
Naval brass	ASTM B21/B21M	C64200 or C46400	H04 Or O50	60,000	27,000	0.5 percent	25 2/
Aluminum alloy 2024	SAE AMS-QQ-A-225/6	---	Solution heat-treated Temper T4	62,000	40,000	0.0058 inch per inch	10 3/
Aluminum alloy 6061	SAE AMS4117	---	Age hardened temper T6	42,000	35,000	0.0055 inch per inch	10 3/
Nickel-copper alloy	QQ-N-281	Class A		80,000	40,000	0.0071 inch in 2 inches	20 1/
Nickel-copper-aluminum (Ni-Cu-Al) alloy UNS N05500 4/	QQ-N-286	Annealed	Form 2 (age hardened)	130,000	90,000 (less than 1 inch), 85,000 (1 inch and greater)	0.0109 inch in 2 inches	20 1/

1/ In 2 inches (min)
2/ In 4 times diameter or thickness (min)
3/ In 2 inches or 4 times diameter (min)
4/ See paragraph 3.1.5 for Ni-Cu-Al special processing requirements.

3.3 Dimensions and tolerances. Cap screws shall conform to the dimensions and tolerances of ASME B18.2.1 except as specified herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

3.3.1 Lengths. Unless otherwise specified (see 6.2), cap screws shall be furnished in the following length increments:

Lengths up to 1/2 inch incl – 1/16 inch increments.
Over 1/2 to 1 inches incl – 1/8 inch increments.
Over 1 to 5 inches incl – 1/4 inch increments.
Over 5 inches – 1/2 inch increments.

3.3.2 Thread series, class, lengths, and hand. Unless otherwise specified (see 6.2), cap screws shall be right – hand of the UNC (coarse thread) or UNF (fine thread) series, Class 2A, in accordance with ASME B1.1.

3.3.3 Threads protectively coated. Unless otherwise specified (see 6.2), threads protectively coated shall meet the dimensions of ASME B1.1 after the coating has been applied.

3.3.4 Bearing surface. Bearing surface of cap screw heads, except flat head, shall be at right angles to the axis of the body within a tolerance of 2 degrees and of hex head within a tolerance of 2 degrees for 1 inch size and smaller, and 1 degree for sizes larger than 1 inch. The axis of the head shall be concentric with the axis of the body (determined by one diameter length of body under head) within a tolerance equal to 3 percent (6 percent TIR) of maximum width across flats. Any mutilation of the bearing surface sufficient to prevent proper seating of the screw shall be cause for rejection.

3.4 Protective coatings.

3.4.1 Coatings. Cap screws shall be furnished uncoated, passivated, or coated as specified herein (see 6.2).

3.4.2 Passivation. Corrosion resistant steel cap screws shall be passivated in accordance with SAE AMS2700, Method 1.

3.4.3 Cadmium plating. When specified (see 6.2), cap screws shall be cadmium plated in accordance with SAE AMS-QQ-P-416, Type II, Class 2. Cadmium is an R1, R2, and D1 substance in the Aerospace and Defense Declarable Substance List. Zinc-nickel plate per paragraph 3.4.8 is the preferred alternate.

3.4.4 Zinc plating. When specified (see 6.2), cap screws shall be zinc plated as specified in ASTM B633, type II, class FE/ZN 5. Zinc plating is not recommended for high strength steels or for aerospace applications.

3.4.5 Anodizing. Unless otherwise specified, aluminum alloy cap screws shall be electrolytically treated in conformance to MIL-PRF-8625, type II, class 1, non-dyed (see 6.2).

3.4.6 Phosphate. When specified (see 6.2), cap screws shall be treated in conformance to MIL-DTL-16232, type Z, class 2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

3.4.7 Black chemical. When specified (see 6.2), brass cap screws shall be treated with a black chemical finish in accordance with MIL-DTL-495.

3.4.8 Zinc-nickel plating. When specified (see 6.2), cap screws shall be zinc-nickel plated in accordance with SAE AMS2461, Type II, Class 2 or MIL-PRF-32647, minimum thickness 0.0003 inches. Zinc-nickel plating was developed as an environmentally friendly alternative to cadmium plating and is recommended for use in lieu of cadmium plating.

3.4.9 Black oxide coating. When specified (see 6.2), steel cap screws shall be treated with a black chemical finish in accordance with MIL-DTL-13924, Class 1.

3.4.10 Hydrogen embrittlement. Alloy steel cap screws required to be electroplated or phosphate coated (see 3.4.3 thru 3.4.6) shall be subjected to a relief treatment in accordance with the methods specified in the applicable plating or coating specification, immediately after the plating or coating operation to minimize the embrittlement that results from these processes.

3.5 Metallographic requirements.

3.5.1 Decarburization. When specified (see 6.2), results shall be in accordance with the requirements of ASTM F2328.

3.5.2 Grain size of copper alloy. When specified (see 6.2), grain size of copper alloy in cap screws shall be an option of the contracting officer in accordance with the material specification.

3.6 Surface roughness. Unless otherwise specified (see 6.2), cap screws shall have a maximum arithmetical average surface roughness on the bearing surface of the head and shank of 125 microinches. Hot headed cap screws over 3/4 inch in diameter are excepted and shall have a maximum surface roughness of 250 microinches. Threads shall have a maximum surface roughness of 63 microinches. Normally, it will be sufficient to ascertain that these surfaces on screws have the equivalent of a smooth machined finish by visual comparison with known surface standards. However, then it is deemed necessary to measure these surfaces with commercially available equipment, roughness measurements shall be taken axially on the body and fillet surfaces, and circumferentially on the bearing surface in accordance with ASME B46.1.

3.7 Method of manufacture. Unless the method of manufacture is specifically stated (see 6.2), the method employed for the production of screw threads on cap screws shall be at the option of the manufacturer.

3.8 Head markings. Steel cap screws shall be permanently marked with the grade identification symbol conforming to SAE J429, and applicable documents. In addition, all cap screws shall be marked with the manufacturer's identification symbol. Markings shall be located on the top of the head, and may be either raised or depressed, at the option of the manufacturer. Grade 9 steel cap screws shall be permanently marked with the grade identification symbol FFS85_9.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

3.9 Defects and Discontinuities. Defects and discontinuities shall meet the requirements of ASTM F788/F788M.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. The contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may use his own or any other facilities suitable for the inspection requirements specified herein, unless disapproved by the Government. Inspection records of the examination and tests with itemized results shall be kept complete at the manufacturer's facility, available to the Government throughout the duration of the contract, or a minimum of two years, whichever is longer. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items shall meet all requirements of sections 3 and 5. The inspection set forth in this document shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in this document shall not relieve the contractor of the responsibility of ensuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling inspection, as part of manufacturing requirements, is an acceptable practice to certain conformance to requirements, however, this does not authorize submission of known defective material either indicated or actual, nor does it commit the Government to accept defective material.

4.1.2 Component and material inspection. Components and materials shall be inspected in accordance with all the requirements specified herein and in application referenced documents.

4.1.3 Examination of preparation for delivery. An examination shall be made to determine that the packaging, packing, and marking comply with the requirements in Section 5 of this specification.

4.2 Sampling for lot acceptance.

4.2.1 Inspection lot. A lot shall consist of cap screws of the same type, made from the same heat of material, heat treatment, protective coating, surface finish, size, length, and threads produced and manufactured at the same time by the same manufacturer's facility and offered for acceptance at the same time. Where the length of the lot of fasteners is too short to support mechanical testing of full size fasteners, the lot shall include longer length fasteners solely for the purposes of mechanical testing. The longer test fasteners shall be made from the same heat of rod, bar or wire used for the production fasteners; have the same type, style and diameter as the production fasteners; and shall be processed and heat treated with the production fasteners.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

4.2.2 Sampling for examination of cap screws. Unless otherwise specified in the contract (see 6.2), for sampling for examination of cap screws, an “accept at zero” (c=0) sampling plan such as MIL-STD-1916 or ASQ H1607 shall apply. A random sample of cap screws shall be selected from each lot in accordance with MIL-STD-1916 or ASQ H1607 using the applicable Verification Level or Index Value listed in Table II.

Table II. Classification of Defects

Categories	Defects	Inspection Method
Critical	Verification Level IV, Index Value 1.0	
1	Cracks (3.9.3)	Microscope or S.I.E.*
Major	Verification Level III, Index value = 2.5	
101	Thread size and form (3.3.1 and 3.3.2)	Thread ring gauge Go and No Go
102	Thread lengths (3.3.2)	S.I.E.*
103	Discontinuities (3.9.1)	S.I.E.*
104	Self-locking element missing, when applicable (3.1.6)	Visual
Minor	Verification Level II, Index value = 4.0	
201	Length (3.1.3)	S.I.E.*
202	Surface roughness (3.6)	Visual
203	Coated threads (when applicable)	Visual
204	Head marking (3.8)	Visual

*Standard Inspection Equipment

4.2.3 Sampling for mechanical properties and metallographic tests. Unless otherwise specified in the contract (see 6.2), for sampling for mechanical properties and metallographic tests, an “accept at zero” (c=0) sampling plan such as MIL-STD-1916 or ASQ H1607 shall apply. A random sample of cap screws shall be selected from each lot in accordance with MIL-STD-1916, verification level IV or ASQ H1607 index value 1.5.

4.2.3.1 Samples selected as specified in 4.2.3 may be used when practicable. Three quarter inch and larger test specimens processed with the lot may be used for destructive testing.

4.2.4 Chemical analysis. Chemical analysis shall be made in accordance with ASTM E1282. When a certificate covering these requirements can be furnished, it will be acceptable.

4.2.5 Sampling for packaging and packing. Sampling for inspection of packaging and packing shall be in accordance with ASTM D3951.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

4.2.6 Sampling for mercurous nitrate test. Unless otherwise specified in the contract (see 6.2), for sampling for mercurous nitrate testing, an “accept at zero” (c=0) sampling plan such as MIL-STD-1916 or ASQ H1607 shall apply. A random sample of cap screws shall be selected from each lot in accordance with MIL-STD-1916 verification level VII or ASQ H1607 index value 0.1.

4.3 Examination.

4.3.1 Visual and dimensional inspection. Each cap screw selected as specified in 4.2.2 shall be examined to verify conformance with this specification. Examination shall be conducted in accordance with Table II. Any screw having one or more defects shall be rejected and if the number of defective screws in any sample exceed the acceptance number of the sample, the lot represented by the sample shall be rejected. Retests shall be in accordance with ASQ Z1.4.

4.3.2 Inspection of packaging and packing. Inspection of packaging and packing including preservation and marking of packages and containers shall be in accordance with ASTM D3951.

4.4 Test procedure.

4.4.1 The test specified in 4.4.2 through 4.4.12 are all required. When specified (see 6.2), perform wedge tensile testing per paragraph 4.4.13.

4.4.2 Hardness. Hardness test for cap screw shall be conducted in accordance with ASTM E10 and ASTM E18 on transverse section through the threaded portion of the screw, taken one nominal diameter from the point, or when too short, halfway between the bearing surface and the point. Hardness shall be measured at a point on the section, one quarter diameter from the axis of the screw. For screws three quarter inch and larger, test may be made on a test specimen.

4.4.3 Tensile. Tensile test shall be conducted in accordance with ASTM F606/F606M. Unless otherwise specified (see 6.2), Grade 2, low carbon steel screws shall not be subjected to this test.

4.4.3.1 Full size specimens. When testing equipment is available cap screws shall be tested full size, preferably using apparatus similar to that illustrated in figure 1.

4.4.3.2 Turned shank specimens. For testing cap screws having tensile properties greater than can be measured on available test equipment, the shank or test specimen shall be turned down around the axis, to gage dimensions specified in ASTM F606/F606M. For testing cap screws or test specimens too large for full size testing, the specimen shall be turned, have its axis midway between the axis of the shank and the surface of the shank, as illustrated in figure 3.

4.4.3.3 Ductility test specimens. Test for elongation and reduction in area shall be conducted on turned shank specimens (figure 2) having dimensions to the largest practical specimens (see 4.4.3).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

4.4.3.4 Screws too short to be tensile strength tested as defined in ASTM F606/F606M shall be hardness tested in accordance with AIA/NAS NASM1312-6. If the hardness limits are not specified, screws shall meet the minimum hardness requirement of the material from which they were made.

4.4.3.5 Sampling for fasteners too long for testing. For lots of fasteners too long for testing in accordance with ASTM F606/F606M, standard length fasteners manufactured with the same lot to support mechanical testing shall be utilized to support proof, yield, axial and wedge strength testing, but shall not be used for evaluation of overall screw length, thread length or grip length.

4.4.4 Metallographic tests.

4.4.4.1 Decarburization. When required (see 6.2), tests for decarburization shall be performed in accordance with ASTM F2328.

4.4.4.2 Grain size of copper alloys. Determination of grain size of copper alloy shall be made in accordance with ASTM E112.

4.4.5 Protective coating test. Protective coating and plating tests shall be conducted in accordance with the applicable specifications shown in 3.4.3 through 3.4.7.

4.4.6 Passivation test. Passivation test shall be conducted in accordance with SAE AMS2700, Method 1.

4.4.7 Hydrogen embrittlement. The contractor shall furnish the Government certification that electroplated, or phosphate coated alloy steel screws have been subjected to the hydrogen embrittlement relief treatment specified in 3.4.10. When specified (see 6.2), electroplated or phosphate coated screws shall be subjected to the embrittlement relief test specified in the applicable plating or coating specification.

4.4.8 Magnetic permeability. Austenitic corrosion resisting steel cap screws, subjected to visual and dimensional examination, shall also be tested to determine magnetic permeability (see 3.1.4.1) in accordance with ASTM A342/A342M.

4.4.9 Discontinuities. Magnetic particle inspection performed in accordance with ASTM E1444/E1444M or liquid penetrant inspection performed in accordance with ASTM E1417/E1417M shall be used to determine the presence of cracks and discontinuities such as laps, seams, and inclusions. Magnetic particle or penetrant indications alone shall not be cause for rejection, and such screws may be sectioned, and discontinuities measured microscopically under 10X magnification to determine conformance to the requirements of 3.9. The inspection shall be performed on unfinished cap screws, free of lubrication and subsequent to any processing operation which could adversely affect the cap screws. The acceptance of these discontinuities shall be as defined in ASTM F788/F788M.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

4.4.10 Self-locking. Self-locking screws having non-metallic elements shall be tested in accordance with MIL-DTL-18240.

4.4.11 Mercurous nitrate (stress relief) test. The contractor shall furnish the government certification that cold worked naval brass screws have been subjected to the stress relief treatment specified in 3.1.5.1. When specified (see 6.2), samples taken as specified in 4.2.6 shall be subjected to a mercurous nitrate test conducted in accordance with ASTM B154. There shall be no evidence of cracks.

4.4.12 Proof load. Proof load test for cap screws shall be conducted in accordance with ASTM F606/F606M.

4.4.13 Yield strength. Yield strength test for cap screws shall be conducted in accordance with ASTM F606/F606M.

4.4.14 Wedge tensile tests. Wedge tensile tests are only required by manufacturers when required by contract. Wedge tensile strength test for steel cap screws, when required, shall be conducted in accordance with ASTM F606/F606M. Wedge tensile strength test for corrosion resisting steel cap screws, when required, shall be conducted in accordance with ASTM F606/F606M using the wedge angles of ASTM F593. Wedge tensile strength test for non-ferrous cap screws, when required, shall be conducted in accordance with ASTM F606/F606M using the wedge angles of ASTM F468. Flat countersunk head screws cannot be wedge tensile tested, even when required.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that is helpful, but is not mandatory.)

6.1 Intended use. Hexagon head and slotted head cap screws are designed primarily for use in precision machine tools and similar applications. They are commonly used in tapped holes but may be used with nuts.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

6.2 Acquisition requirements. Purchasers should select the preferred options permitted herein and include the following information in procurement documents:

(a) Title, number, and date of this specification.
(b) Type and style, grade (for carbon and alloy steel), and size or standard part number (1.2).
(c) Material and condition (3.1).
(d) Mechanical properties, if other than those specified in Tables I and IA (3.2).
(e) Length, thread series, class, and hand (3.3).
(f) Coating, if required, and whether thread shall conform to different size requirements (3.3.3 and 3.4).
(g) Decarburization test, if required (3.5.1).
(h) Copper alloy grain size, if required (3.5.2).
(i) Surface roughness, if different (3.6).
(j) Method of manufacture, if necessary (3.7).
(k) Material certification, if applicable (4.2.4).
(l) Hardness and tensile tests (4.4.2 and 4.4.3).
(m) Metallographic tests, if required (4.4.4).
(n) Selection of applicable level of packaging and packing required (5.1).
(o) Embrittlement relief test, if required (4.4.7).
(p) Sampling for examination of cap screws (4.2.2).
(q) Sampling for mechanical properties and metallographic tests (4.2.3).
(r) Mercurous nitrate test, if required (4.4.11).
(s) Sampling method for Mercurous nitrate test, if required (4.2.6).
(t) Proof load test, if required (4.4.12).
(u) Yield strength test, if required (4.4.13).
(v) Wedge test, if required (4.4.14).

6.3 Military procurement. Items procured under this specification for Military use shall be limited to the variety and materials specified on the applicable MS. Cap screws of low carbon steel are non-preferred for military use. Personnel of the Military departments are requested to refer to these documents for guidance.

6.4 Definitions.

6.4.1 Cracks. A crack is a clean crystalline break passing through the grain or grain boundary without the inclusion of foreign elements.

6.4.1.1 Quench cracks. Quench cracks are fractures occurring during heat treatment, due to excessive high thermal and transformation stresses.

6.4.1.2 Forging cracks. Forging cracks are cracks that may occur during the cut-off or forging operations.

6.4.2 Lap. A lap is a surface defect appearing as a seam, caused by the folding over of metal fins or sharp corners and then rolling or forging them into the surface, but not welding them.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

6.4.3 Seam. A seam is an unwelded fold or lap which appears as an opening in the raw material as received from the source.

6.4.4 Inclusions. Inclusions are non-metallic material in a solid metallic matrix.

6.4.5 Tool marks. Tool marks are longitudinal or circumferential grooves of shallow depth produced by the movement of manufacturing tools over the surface of the screw.

6.4.6 Void. A void is a shallow pocket or hollow on the surface of the screw due to non-filling of metal during forging or upsetting.

6.4.7 Fold. A fold is a doubling over of metal which may occur during the forging operation.

6.4.8 Burst. A burst is an open break in the metal.

6.5 Subject term (keyword) listing.

Plain head screw
Screw thread
Slotted head screw

6.6 Amendment notations. The margins of this specification are marked with vertical lines to indicate modifications generated by this amendment. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

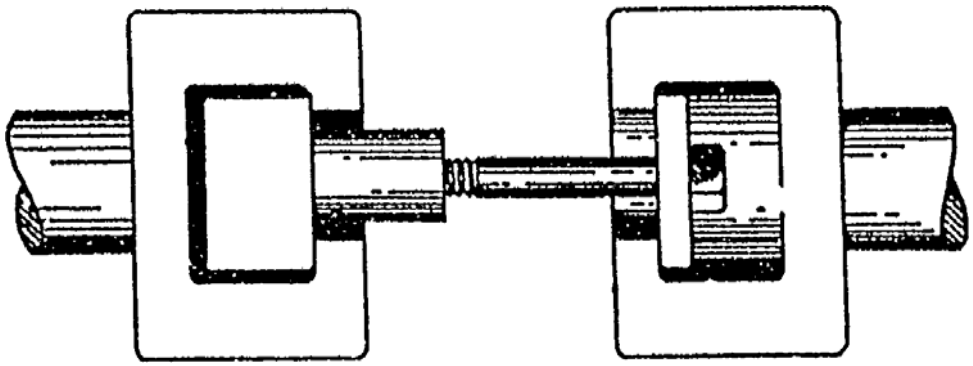


Figure 1. Tension Testing Full-Size Screw

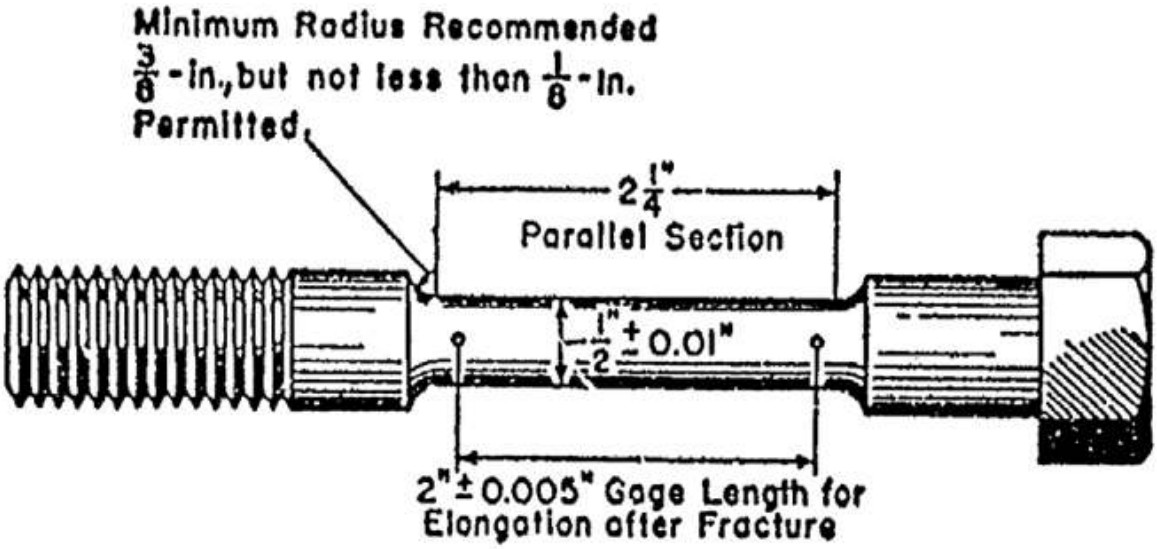


Figure 2. Tension-Test Specimen for Screw with Turned-Down Shank

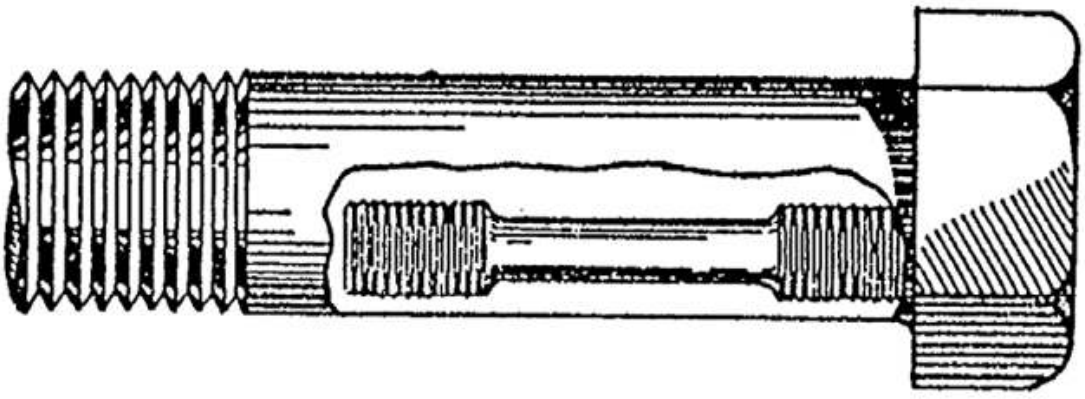


Figure 3. Location of Standard, Round, 2-inch-gage-length, Tension-Test Specimen when Turned from Large-Size Screw

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.




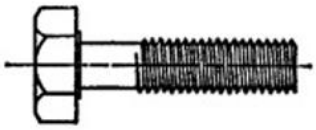
TYPE	STYLE	HEAD	DRIVE
I	1s	ROUND	
I	2s	FLAT	
I	4s	FILLISTER	
II	10P	HEXAGON	

Figure 4. Types, Heads and Styles

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.

Concluding Material:

Custodians:
Army – AR
Navy – SH
Air Force – 71
DLA – GS

Review Interests:
Army – AV
Navy – AS
Other DoD – NS

Preparing Activity:
DLA – GS6

(Project 5305-2024-004)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST database at https://assist.dla.mil/.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:44Z
Check the source to verify that this is the current version before use.