INCH-POUND

MIL-G-432G
21 November 1989
SUPERSEDING
MIL-G-432F
5 May 1986

MILITARY SPECIFICATION

GASKETS, NONMETALLIC, SYNTHETIC RUBBER

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers five types of synthetic rubber, nonmetallic gaskets.

1.2 Classification. The gaskets shall be of the following types and classes as specified (see 6.2):

Type I	- Round cross section, for 2-inch bung and 3/4-inch vent sizes (see figure 1).
Type II	- Rectangular cross section for 2-inch bung and 3/4-inch vent sizes on 55-gallon drums or steel drums (see figure 2).
Type III	- Beaded edge 2-1/4 inch ID by 3-3/8 inch OD for 5-gallon gasoline can with carrying handle (see figure 3).
Class 1	- For use at -40°F and above.
Class 2	- For use at -60°F and above.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: U.S. Army Natick Research, Development, and Engineering Center, Natick, MA 01760-5014 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 5330

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 202610-16T07:25Z
Check the source to verify that this is the current version before use.

Type VI - Rectangular cross section for 2-inch bung and 3/4-inch vent sizes for steel drums (see figure 4).

Type VII - Rectangular cross section 1-1/2 inch ID by 2-1/2 inch OD for filling tube, flexible nozzle cam type (see figure 5).

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATIONS

FEDRAL

PPP-T-45 - Tape, Gummed, Paper, Reinforced and Plain, for Sealing and Securing
PPP-B-566 - Boxes, Folding, Paperboard
PPP-B-636 - Boxes, Shipping, Fiberboard
PPP-B-676 - Boxes Setup

MILITARY

MIL-L-35078 - Loads, Unit: Preparation of Semiperishable Subsistence Items; Clothing, Personal Equipment and Equipage; General Specification For

STANDARDS

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attribute
MIL-STD-129 - Marking for Shipment and Storage
MIL-STD-147 - Palletized Unit Loads
MIL-STD-731 - Quality of Wood Members for Containers and Pallets

Source: https://assist.dla.mil -- Downloaded: 202610-16T07:25Z
Check the source to verify that this is the current version before use.

(Unless otherwise indicated, copies of federal and military specifications, standards, and handbooks are available from the Naval Publications and Forms Center, (ATTN: NPODS), 5801 Tabor Avenue, Philadelphia, PA 19120-5099.)

2.1.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues are those cited in the solicitation.

DRAWINGS

U.S. ARMY NATICK RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER

8-1-161 Pressure Jig Assembly for Gasket, Nonmetallic

(Copies of drawings are available from the U.S. Army Natick Research, Development, and Engineering Center, ATTN: STRNC-EMSS, Natick, MA 01760-5014.)

2.2 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DoD adopted are those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issues of the documents cited in the solicitation (see 6.2).

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

D 395	- Rubber Property - Compression Set
D 471	- Rubber Property - Effect of Liquids
D 1053	- Rubber Property - Stiffening at Low Temperatures: Flexible Polymers and Coated Fabrics
D 1229	- Rubber Property - Compression Set at Low Temperatures
D 2240	- Rubber Property - Durometer Hardness
D 3951	- Standard Practice for Commercial Packaging

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103-1187.)

(Non-Government standards and other publications are normally available from the organizations that prepare or distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

Source: https://assist.dla.mil -- Downloaded: 202610-16T07:25Z
Check the source to verify that this is the currentversion before use.

3. REQUIREMENTS

3.1 First article. When specified (see 6.2), a sample shall be subjected to first article inspection (see 6.3) in accordance with 4.3.

3.2 Material. Gaskets shall be made of various types of synthetic rubber that will meet the requirements of this specification. Phosphonitrilic fluoroelastomers have been found suitable for the type III, class 2 gaskets.

3.3 Design and dimensions. Design and dimensions of each type and class of gasket shall be in accordance with figures 1 to 5, as applicable, and shall be furnished in the size required (see 6.2).

3.4 Physical characteristics.

3.4.1 Hardness (Durometer). The gasket material (slabs of synthetic rubber from which the gaskets are made) shall have a Durometer hardness as shown in table I when tested as specified in 4.4.1.1.

TABLE I. Hardness

Type	Hardness (Durometer)
I, VI	60-70
II	75-85
III	65-75
VII	40-50

3.5 Performance.

3.5.1 Volume change. The slabs of synthetic rubber material from which the gaskets are made shall not swell more than 40 percent, and there shall be no shrinkage when tested as specified in 4.4.1.1.

3.5.2 Weight change. Slabs of synthetic rubber material from which types I, II, III, and VI gaskets are made shall not change more than 25 percent from the original weight when tested as specified in 4.4.1.1.

3.5.3 Immersion resistance. The gaskets shall not disintegrate, crack, nor stretch or distort more than 5 percent or show shrinkage of more than 2 percent of the original inside diameter when tested as specified in 4.4.4. In addition, after 24 hours drying time, the gasket shall not show signs of disintegration, stretching, shrinking, cracking, or distortion when compared with new untested gaskets of the same lot sample.

3.6 Low temperature compression set. The low temperature compression set shall not exceed 60 percent when tested as specified in 4.4.4.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

3.6.1 Torsional modulus ratio (type III only). The torsional modulus ratio shall not exceed 10 when tested as specified in 4.4.1.1.

3.7 Compression set. The compression set shall not exceed 40 percent of original deflection when tested as specified in 4.4.4.

3.8 Endurance (except for type VII). Gaskets shall withstand the test specified in 4.4.4.

3.9 Leakage (except for type VII). Gaskets shall withstand the test specified in 4.4.4.

3.10 Strength. Gaskets either wet or dry shall not fracture, break, nor distort beyond the periphery of the applicable gasket seat closure plug, can closure plug, or can closure when tested as specified in 4.4.4.

3.11 Replacement of defective components. During the manufacturing process, components having material defects or damages that are classified as defects in 4.4.2 and 4.4.3 shall be removed from production and replaced with nondefective and properly matched components.

3.12 Workmanship. The end items shall conform to the quality of product established by this specification. The finished gaskets shall be clean and free from defects, such as rough or scratched surfaces and edges, cuts, holes, open blisters, and lumps. Flash resulting from mold vulcanization will be acceptable within the limits shown on figure 1.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements (examinations and tests) as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in this specification where such inspections are deemed necessary to ensure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items shall meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of ensuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling inspection, as part of manufacturing operations, is an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to accept defective material.

Source: https://assist.dla.mil -- Downloaded: 202640-16T07:25Z
Check the source to verify that this is the current version before use.

4.1.2 Responsibility for dimensional requirements. Unless otherwise specified in the contract or purchase order, the contractor is responsible for ensuring that all specified dimensions have been met. When dimensions cannot be examined on the end item, inspection shall be made at any point, or at all points in the manufacturing process necessary to ensure compliance with all dimensional requirements.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.3).
b. Quality conformance inspection (see 4.4).

4.3 First article inspection. When a first article is required (see 3.1 and 6.2), it shall be examined for the defects specified in 4.4.2 and 4.4.3 and tested for the characteristics specified in 4.4.4.

4.4 Quality conformance inspection. Unless otherwise specified, sampling for inspection shall be performed in accordance with MIL-STD-105.

4.4.1 Component and material inspection. In accordance with 4.1, components and materials shall be inspected in accordance with all the requirements of referenced documents unless otherwise excluded, amended, modified, or qualified in this specification or applicable purchase document. In addition, testing shall be performed on components and materials listed in table II.

4.4.1.1 Component testing. All test reports shall contain the individual values utilized in expressing the final result. All requirements are applicable to the sample unit. The sample unit shall be one slab of the synthetic rubber, 6 inches by 6 inches. Thickness of the sample unit shall be determined by the type gasket specified, be uniform in thickness to .005 inches and shall be identical in composition and cure to the inspection lot represented. The samples selected shall be suitably marked and dated for identification with the inspection lot. Samples for testing may be selected from the stock material from which the end item is made at the time of manufacture. The stock material shall be unacceptable if one or more sample units fail to meet any test requirement specified. The sample size shall be as follows:

Lot size (yards)	Sample size (sample units)
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

TABLE II. Component testing

Material	Characteristic	Requirement paragraph	Test method
Synthetic rubber	Hardness (Durometer)	3.4.1	4.5.1
	Volume change	3.5.1	4.5.2
	Weight change	3.5.2	4.5.2 and 4.5.3
	Torsional modulus ratio (type III only):		
	Original	3.6.1	4.5.4.1
	After solvent extraction	3.6.1	4.5.4.2

4.4.2 End item visual examination. The end items shall be examined for the defects listed in table III. The lot shall be expressed in units of gaskets of the same type. The sample unit shall be one gasket of one type. The inspection level shall be I (see 6.4).

TABLE III. End item visual defects

Examine	Defect
Design	Not in accordance with specified requirements
Appearance and workmanship	Not clean
	Rough edges or rough surface
	Edges or surface nicked, scratched, or abraded
	Any cut or hole

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

TABLE III. End item visual defects (cont'd)

Examine	Defect
Appearance and workmanship (cont'd)	Any imbedded foreign matter Any open blister Any lump or closed blister

4.4.3 End item dimensional examination. The end items shall be examined for conformance to the dimensions specified in figures 1 through 5, as applicable. Any dimension not within the specified tolerance shall be classified as a defect. The lot size shall be expressed in units of gaskets, of the same type. The sample unit shall be one gasket, of one type. The inspection level shall be S-3 (see 6.4).

4.4.4 End item testing. The end items shall be tested for the characteristics listed in table IV. The lot size shall be expressed in units of gaskets, of the same type. The sample unit shall be 5 gaskets, of the same type. All test requirements shall be applicable to the sample unit. All test reports shall contain the individual values used to express the final result. The lot shall be unacceptable if one or more sample units fail to meet any test requirement specified. The sample size shall be as follows:

Lot size (gaskets)	Sample size (sample units)
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

TABLE IV. End item tests

Characteristics	Requirement paragraph	Test method	Number determinations per sample unit	Results reported as pass or fail
Immersion resistance	3.5.3	4.5.2.1	1	X

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

TABLE IV. End item tests (cont'd)

Characteristics	Requirement paragraph	Test method	Number determinations per sample unit	Results reported as pass or fail
Immersion resistance (after 24 hours)	3.5.3	4.5.2.1	1	X
Low temperature compression set. (All gaskets except type III)	3.6	4.5.4	1	X
Low temperature compression set. (For type III gasket only):				
Original	3.6	4.5.4.3	1	X
After solvent extraction	3.6	4.5.4.4	1	X
Compression set	3.7	4.5.5	1	X
Endurance	3.8	4.5.6	1	X
Leakage	3.9	4.5.7	1	X
Strength	3.10	4.5.6	1	X

4.4.5 Packaging examination. The fully packaged end items shall be examined for the defects listed below. The lot size shall be expressed in units of shipping containers. The sample unit shall be one shipping container fully packaged. The inspection level shall be S-2 (see 6.4).

Source: https://assist.dla.mil -- Downloaded: 202610-16T07:25Z
Check the source to verify that this is the current version before use.

Examine	Defect
Marking (exterior and unit packs)	Omitted; incorrect; illegible; of improper size, location, sequence, or method of application
Materials	Any component missing, damaged, or not as specified
Workmanship	Inadequate application of components, such as: incomplete sealing or closure of flap, improper taping, loose strapping or inadequate stapling Bulged or distorted container
Weight	Weight of contents exceeds requirements
Content	Number of gaskets per shipping container is more or less than required 1/

1/ For this defect, one shipping container in the sample shall be examined.

4.4.6 Palletization examination. The fully packaged and palletized end items shall be examined for the defects listed below. The lot size shall be expressed in units of palletized unit loads. The sample unit shall be one palletized unit load, fully packaged. The inspection level shall be S-1 (see 6.4).

Examine	Defect
Finished dimensions	Length, width, or height exceeds specified maximum requirement
Palletization	Load not bonded as specified
Weight	Exceeds maximum load limits
Marking	Omitted; incorrect; illegible; of improper size, location, sequence, or method of application

4.5 Methods of inspection.

4.5.1 Hardness test. The hardness shall be determined in accordance with ASTM D 2240.

4.5.2 Immersion medium test. The immersion medium for volume change and weight change shall be fuel C in accordance with ASTM D 471.

4.5.2.1 Immersion resistance test. The gaskets shall be immersed in the immersion medium specified in 4.5.2 for 46 ± 1/4 hour at 73.4° ± 3.6°F. Measurements shall be made using an inside divider and a micrometer caliper calibrated in thousands. After 24 hours of drying time at 73.4° ± 3.6°F, examination shall be made for disintegration, stretching, shrinking, cracking, or distortion.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

4.5.3 Weight change test. The weight change shall be determined by using the weights of specimen in air recorded in 4.5.2 and using the method of calculation specified in ASTM D 471 to determine the change in weight.

4.5.4 Low temperature compression set test. Low temperature compression set shall be determined in accordance with ASTM D 1229. The specimens shall be compressed 40 percent and exposure time shall be 94 ± 1/2 hour at -40°C. Readings shall be taken after the 30-minute recovery period.

4.5.4.1 Torsional modulus ratio (material for type III gaskets). The torsional modulus ratio shall be determined in accordance with ASTM D 1053. The material to be used for type III, class 1 gaskets shall be tested at -40° ± 2°F. The material to be used for type III, class 2 gaskets shall be tested at -60°F ± 2°F. The liquid coolant shall be methyl alcohol, and exposure time shall be five minutes.

4.5.4.2 Torsional modulus ratio after solvent extraction (material for type III gaskets). The gasket material shall be immersed in Reference Fuel B, ASTM D 471, for 24 ± 1/4 hours at 73° ± 5°F. The extracted sample shall then be removed from Fuel B, placed on a wire screen and dried with forced air for 24 ± 1/4 hours at 73° ± 5°F. The torsional modulus ratio shall be determined as specified in 4.5.4.1.

4.5.4.3 Low temperature compression set test (type III gaskets). The low temperature compression set shall be determined in accordance with ASTM D 1229. The type III, class 1 gasket sample shall be compressed 40 percent and exposure time shall be 94 ± 1/2 hours at -40° ± 2°F. The type III, class 2 gasket sample shall be compressed 40 percent and the exposure time shall be 94 ± 1/2 hours at -60° ± 2°F. Readings shall be taken after the 30-minute recovery period.

4.5.4.4 Low temperature compression set after solvent extraction test (type III gaskets). The gasket shall be immersed in Reference Fuel B, ASTM D 471, for 24 ± 1/4 hours at 73° ± 5°F. The sample shall then be removed from Fuel B, placed on a wire screen and dried with forced air for 24 ± 1/4 hours at 73° ± 5°F. The low temperature compression set shall be determined according to 4.5.4.3.

4.5.5 Compression set test. The compression set test shall be performed in accordance with ASTM D 395, method B, except that the sample specimen thickness shall be the actual thickness of the gasket. Spacer bars shall be the thickness required to compress the gasket 25 ± 3 percent of the original gasket thickness. The test specimen shall be held compressed for 22 hours at 158° ± 2°F.

4.5.6 Endurance test (except type VII). A closure flange shall be thoroughly wetted with the special testing fuel specified in 4.5.2, a gasket placed on it, and a plug inserted. The plug shall be tightened to the torque shown in table V with a torque wrench and loosened 30 times. An interval of 6 to 7 seconds shall be allowed between each tightening and loosening. The plug shall then be tightened once more with a torque equal to 2-1/2 times that indicated in table V.

Source: https://assist.dla.mil -- Downloaded: 202640-16T07:25Z
Check the source to verify that this is the current version before use.

TABLE V. Torque loading

Type	Size (inches)	Torque (foot-pounds)	Size (inches)	Torque (foot-(pounds)
I	2	15	3/4	7
II	2	35	3/4	20
III	2	10	--	--
VI	2	15	3/4	7

4.5.7 Leakage tests (except type VII). The leakage tests in the following paragraphs are to determine gasket failure by pressure loss. A pressure drop to 20 pounds per square inch (psi) or less reading on the gage under conditions as specified in the following test procedures shall be considered a failure to comply with the leakage requirement.

4.5.7.1 Inverted jig procedure (gasket in contact with fuel). The gasket subjected to the test specified in 4.5.7 shall be transferred to a pressure jig as shown on Drawing 8-1-161. One hundred milliliters of the special testing fuel specified in 4.5.2 shall be put in the container of the jig, and the plug with the gasket in place shall be inserted and tightened to the torque specified in table V. The jig shall be inverted so that the testing fuel is in contact with the plug. Air, or nitrogen under pressure, shall then be introduced through the air inlet until the pressure gage reads 25 psi, the pressure being maintained by closing the needle valve on the air inlet. If a pressure drop to 20 psi or less on the gage indicator is observed within 10 minutes, the test shall be considered a failure. If the gasket passes the test, proceed with the test in 4.5.7.2.

4.5.7.2 Upright jig procedure (gasket not in contact with fuel). The test shall be repeated with the same gasket in place (i.e., loosen, tighten to required torque, and introduce air again as in 4.5.7.1 with the exception that the jig shall not be inverted). If a pressure drop to 20 psi or less on the gage indicator is observed within 10 minutes, the test shall be considered a failure.

4.5.7.2.1 Room temperature. If no leakage occurs in 4.5.7.2, the pressure jig with gasket in place shall be placed in an upright position in a constant air temperature of 77° ± 2°F and accurate pressure shall be noted. The jig assembly shall remain at this temperature for 24 hours. If during the 24 hour period a pressure drop to 20 psi or less on the gage indicator is observed, the test shall be considered a failure.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

4.5.7.2.2 Water immersion. Continuing with the same assembly as specified in 4.5.7.2.1, it shall be placed under water at a controlled temperature of 140° ± 2°F and left for 24 hours. The assembly shall then be removed and allowed to remain at 77° ± 2°F for 3 hours. If a pressure drop to 20 psi or less on the gage indicator is observed, the test shall be considered a failure.

4.5.7.2.3 Cold temperature. Continuing with the same assembly, the pressure shall be observed and then the assembly shall be placed in a cold chamber at -40° ± 2°F for 2 hours. A check shall be made for leakage of the testing fuel. The pressure jig shall then be removed from the chamber and allowed to remain at 77° ± 2°F for 3 hours. If a pressure drop to 20 psi or less on the gage is observed, the test shall be considered a failure.

5. PACKAGING

5.1 Preservation. Preservation shall be level A or Commercial, as specified (see 6.2).

5.1.1 Level A preservation. One hundred gaskets, of one type, class, and size only, shall be unit packed in a kraft paper or opaque plastic film bag, or snug-fitting setup or folding paperboard box. The setup and folding boxes shall conform to PPP-B-676 and PPP-B-566, respectively, with classification optional. Each bag opening shall be secured by heat sealing, with gummed or pressure-sensitive tape, or with a mechanical tie (e.g., paper or plastic band). The box closure shall be secured with 2-inch minimum width gummed paper tape conforming to type III, grade B of PPP-T-45, applied at the center of the length opening and extending along the bottom and up the sides.

5.1.2 Commercial preservation. Gaskets shall be preserved in accordance with ASTM D 3951.

5.2 Packing. Packing shall be level A, B, or Commercial, as specified (see 6.2).

5.2.1 Level A packing. Gaskets of one type, class, and size only, preserved as specified in 5.1, shall be packed in a snug-fitting fiberboard container conforming to grade V2s, style RSC of PPP-B-636. Each shipping container shall be closed in accordance with method III, waterproofed in accordance with method V, and reinforced as specified in the appendix of PPP-B-636, except that the inspection shall be in accordance with 4.4.5. The weight of the contents of each shipping container shall not exceed 65 pounds. Shipping containers shall be arranged in unit loads in accordance with MIL-L-35078 for the type and class of load specified (see 6.2). Strapping shall be limited to nonmetallic strapping, except for type II, class F loads.

5.2.2 Level B packing. Gaskets of one type, class, and size only, preserved as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container conforming to type CF (variety SW) or SF, class domestic, grade 275, style RSC of PPP-B-636. Each shipping container shall be closed in accordance

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

with method II as specified in the appendix of PPP-B-636, except that the inspection shall be in accordance with 4.4.5. The weight of the contents of each shipping container shall not exceed 65 pounds.

5.2.2.1 Weather-resistant fiberboard containers. When specified (see 6.2), the fiberboard shipping container shall be a grade V3c, C3s, or V4s fiberboard box fabricated in accordance with PPP-B-636 and closed in accordance with method III as specified in the appendix of PPP-B-636, except that the inspection shall be in accordance with 4.4.5.

5.2.3 Commercial packing. Gaskets of one type, class, and size only, preserved as specified in 5.1, shall be packed in accordance with ASTM D 3951.

5.3 Palletization. When specified (see 6.2), gaskets, packed as specified in 5.2.2 or 5.2.3, shall be palletized on a 4-way entry pallet in accordance with load type Ia of MIL-STD-147. Pallet type shall be type I (4-way entry), type IV or type V in accordance with MIL-STD-147. Pallets shall be fabricated from wood groups I, II, III, or IV of MIL-STD-731. Each prepared load shall be bonded with primary and secondary straps in accordance with bonding means C and D or film bonding means F or G. Pallet pattern for the gasket shall be in accordance with the appendix of MIL-STD-147.

5.4 Marking. In addition to any special marking required by the contract or purchase order, unit packs, shipping containers, and palletized unit loads shall be marked in accordance with MIL-STD-129 or ASTM D 3951, as applicable.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The gaskets are intended for use with can type flexible nozzle filling tube, drums, and other containers used for transporting aromatic gasoline, or other petroleum fractions. The type III, class 1 gaskets are intended for use at -40°F and above, and type III, class 2 gaskets are intended for use at temperatures down to -60°F.

6.2 Acquisition requirements. Acquisition documents must specify the following:

a. Title, number, and date of this specification.
b. Type, class, and size required (see 1.2 and 3.3).
c. Issue of DODISS to be cited in the solicitation, and if required, the specific issue of individual documents referenced (see 2.1.1 and 2.2).
d. When a first article is required (see 3.1, 4.3, and 6.3).
e. Levels of preservation and packing (see 5.1 and 5.2).
f. Type and class of unit load required (see 5.2.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

g. When weather-resistant grade fiberboard shipping containers are required for level B packing (see 5.2.2.1).
h. When palletization is required (see 5.3).
i. Acceptance criteria required (see 6.4).

6.3 First article. When a first article is required, it shall be inspected and approved under the appropriate provisions of FAR 52.209. The first article should be a preproduction sample. The contracting officer should specify the appropriate type of first article and the number of units to be furnished. The contracting officer should also include specific instructions in acquisition documents regarding arrangements for selection, inspection, and approval of the first article.

6.4 Acceptance criteria. The acceptance criteria below are recommended for use. The acceptance criteria as specified in the contract or purchase order shall be binding. Unless otherwise specified, the following acceptance criteria are in accordance with MIL-STD-105.

6.4.1 For end item visual examination. An acceptable quality level (AQL), expressed in terms of defects per hundred units, of 2.5 is recommended.

6.4.2 For end item dimensional examination. An AQL, expressed in terms of defects per hundred units, of 4.0 is recommended.

6.4.3 For packaging examination. An AQL, expressed in terms of defects per hundred units, of 2.5 is recommended.

6.4.4 For palletization examination. An AQL, expressed in terms of defects per hundred units, of 6.5 is recommended.

6.5 Subject term (key word) listing.

55-gallon drum
Gas can
Seal

6.6 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

Custodians:
Army - GL
Navy - AS
Air Force - 99

Review activities:
Army - AT, ME, MR
Air Force - 82
DLA - IS

User activities:
Navy - CG, MC, SH

Preparing activity:
Army - GL

(Project 5330-0824)

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

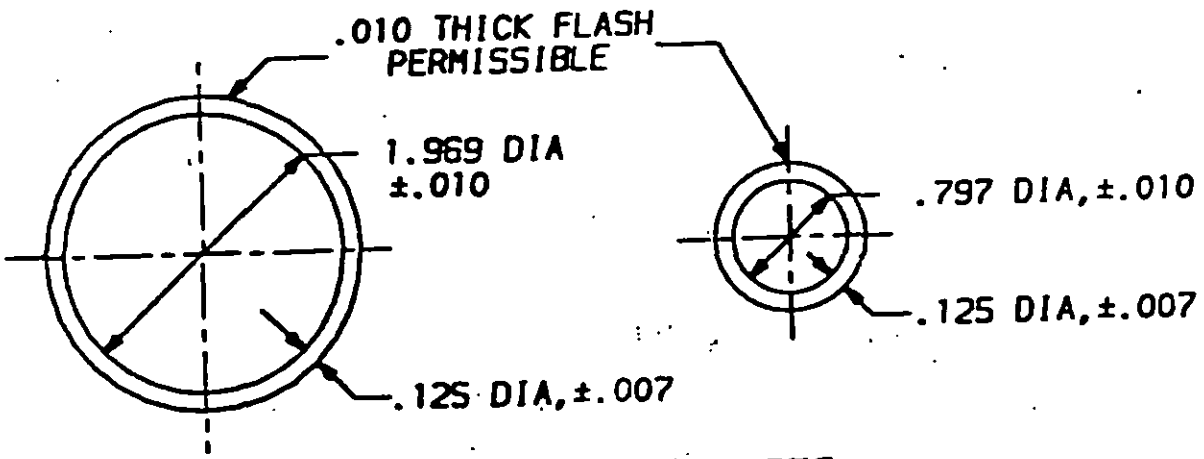


FIGURE 1. TYPE 1 GASKETS

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

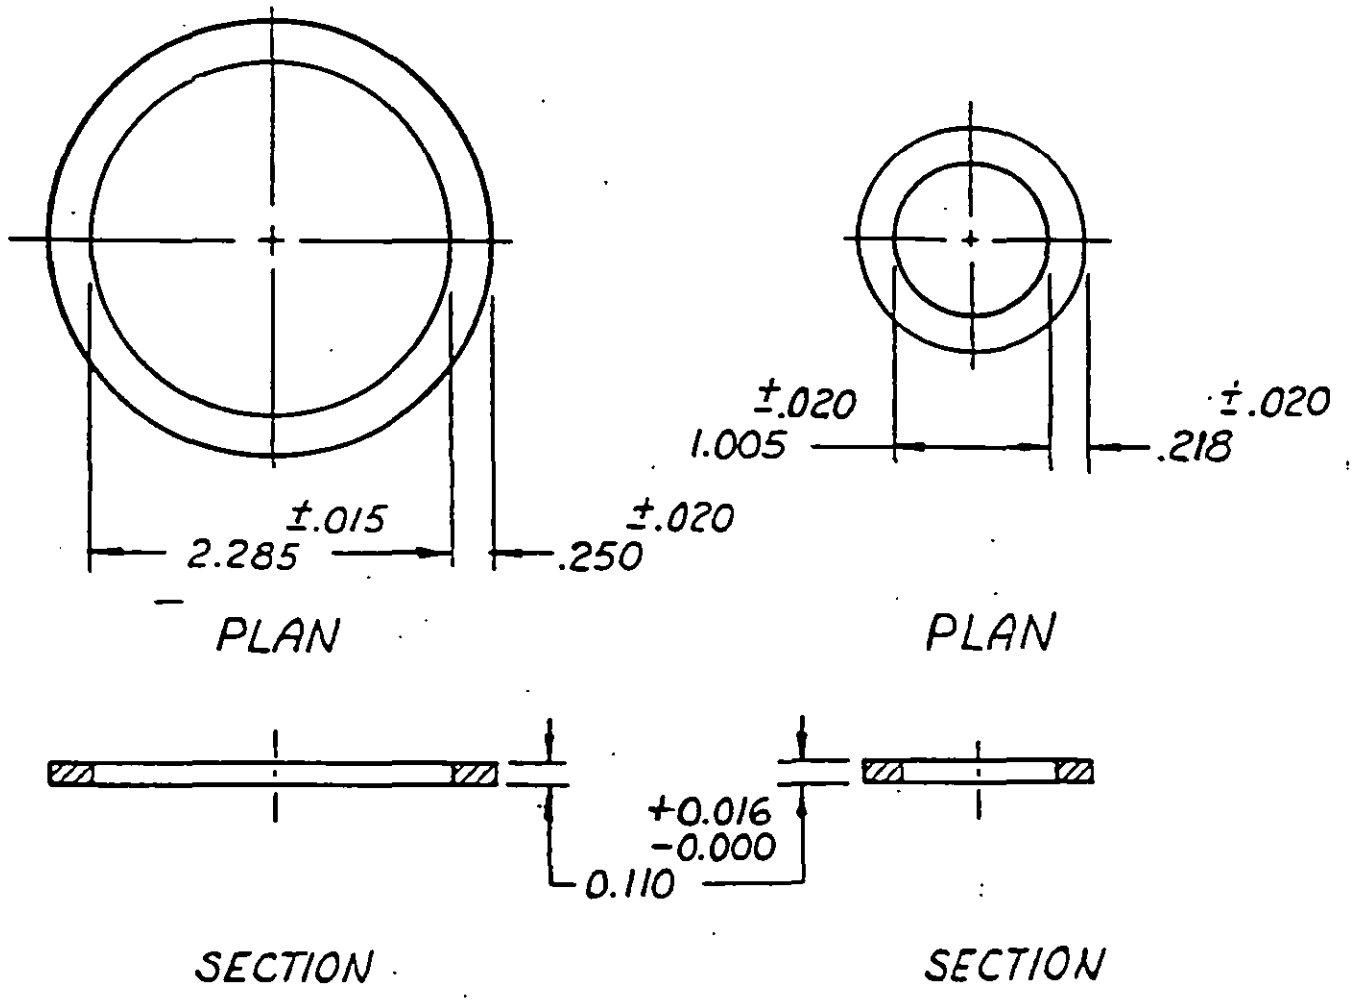


Figure 2. Type II Gaskets

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

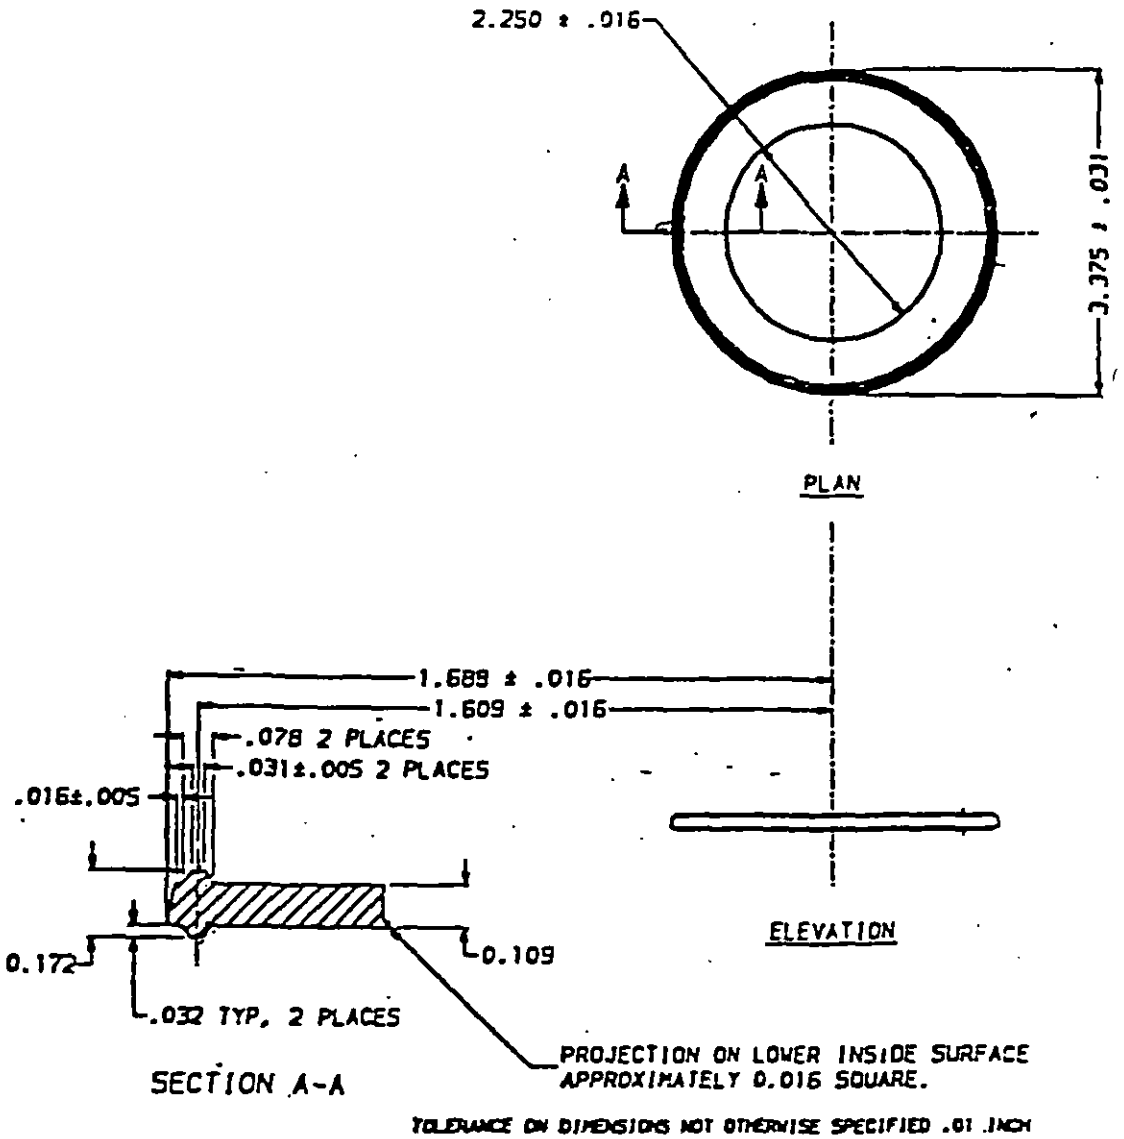
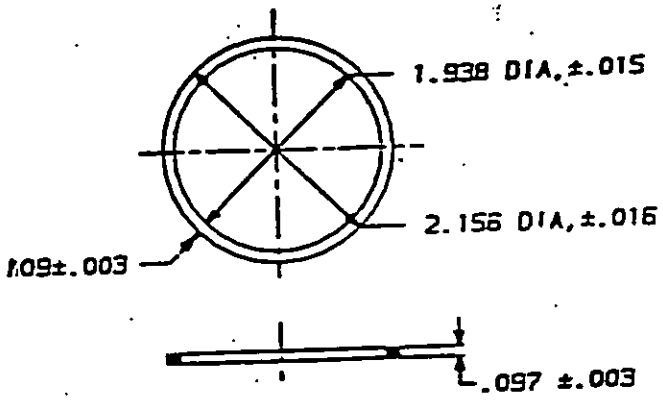


FIGURE 3. TYPE III GASKETS

Source: https://assist.dla.mil -- Downloaded: 202610-16T07:25Z
Check the source to verify that this is the current version before use.

NOTES:



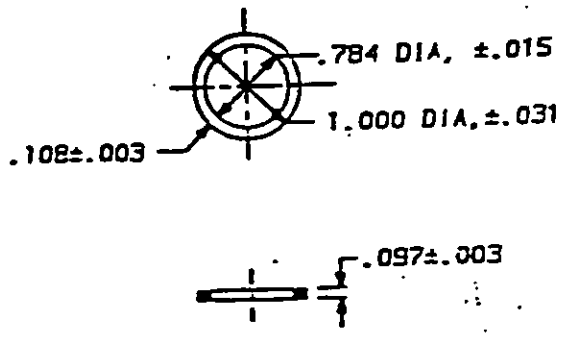


FIGURE 4. TYPE VI GASKETS

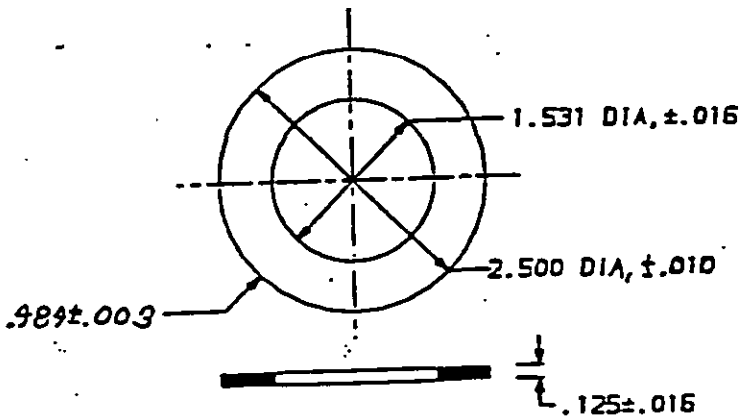


FIGURE 5. TYPE VII GASKETS

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-G-432G	Gaskets, Nonmetallic, Synthetic Rubber

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION (Mark one)
	☐ VENDOR
b. ADDRESS (Street, City, State, ZIP Code)	☐ USER
	☐ MANUFACTURER
	☐ OTHER (Specify): _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER (Last, First, MI) – Optional	b. WORK TELEPHONE NUMBER (Include Area Code) – Optional
c. MAILING ADDRESS (Street, City, State, ZIP Code) – Optional	8. DATE OF SUBMISSION (YYMMDD)

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T07:25Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY

U.S. ARMY NATICK RESEARCH, DEVELOPMENT
and ENGINEERING CENTER
ATTN: STRNC-ES
Natick, MA 01760-5014

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

NO POSTAGE
NECESSARY
IF MAILED
IN THE
UNITED STATES

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
U.S. Army Natick Research, Development
and Engineering Center
ATTN: STRNC-ES
Natick, MA 01760-5014

Source: https://assist.dla.mil -- Downloaded: 202610-16T07:25Z
Check the source to verify that this is the current version before use.