MILITARY SPECIFICATION SHEET

WIRE, ELECTRIC, FLUOROPOLYMER-INSULATED, EXTRUDED TFE, NICKEL-COATED COPPER CONDUCTOR, 1000-VOLT

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The complete requirements for procuring the wire described herein shall consist of this document and the issue in effect of Specification MIL-W-22759.

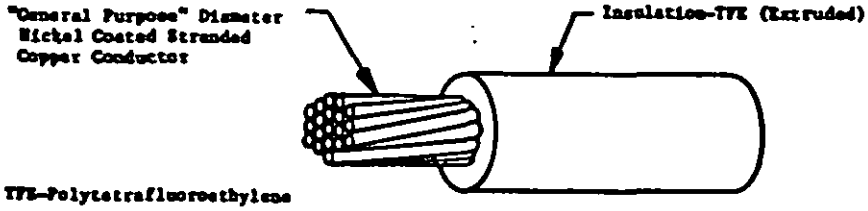


TABLE I. CONSTRUCTION DETAILS

Part No. 1/	Wire size	Stranding (Number of strands X AWG gage of strands)	Diameter of stranded conductor (inches)		Finished wire		
			(min)	(max)	Resistance at 20°C (68°F) (ohms/1000 ft) (max)	Diameter (inches)	Weight (lbs/1000 ft) (max)
M22759/10-28-*	28	7 X 36	.014	.016	67.9	.043 ±.002	1.90
M22759/10-26-*	26	19 X 38	.018	.021	42.2	.048 ±.002	2.57
M22759/10-24-*	24	19 X 36	.023	.026	25.9	.053 ±.002	3.33
M22759/10-22-*	22	19 X 34	.029	.033	16.0	.060 ±.002	4.60
M22759/10-20-*	20	19 X 32	.037	.041	9.77	.068 ±.002	6.40
M22759/10-18-*	18	19 X 30	.046	.051	6.10	.078 ±.002	9.10
M22759/10-16-*	16	19 X 29	.052	.058	4.76	.085 ±.002	11.0
M22759/10-14-*	14	19 X 27	.065	.073	3.00	.100 ±.003	16.4
M22759/10-12-*	12	(B) 19 X 25	(B) .082	(B) .092	(B) 1.89	.120 ±.004	(B) 25.3
M22759/10-10-*	10	37 X 26	.106	.114	1.24	.141 ±.004	38.2
M22759/10-8-*	8	133 X 29	.158	.173	.694	.207 ±.005	68.8

1/ PART NO.: The asterisks in the part number column, Tables I through III, shall be replaced by color code designators in accordance with MIL-STD-681. Examples: Size 20, white - M22759/10-20-9; white with orange stripe - M22759/10-20-93.

(B) denotes changes

FSC 6145

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:45Z
Check the source to verify that this is the current version before use.

TABLE II. PERFORMANCE DETAILS

Part No.	Abrasion resistance (Procedure II)				Bend testing			
					Mandrel diameter (inches) (±3%)		Test load (lbs) (±3%)	
	Resistance (inches of tape) (min) (initial condition)	Weight support bracket	Weight (lbs)	Tension load (lbs)	Life cycle (oven & bend tests) 1/	Cold bend test	Life cycle (oven & bend tests) 1/	Cold bend test
M22759/10-28-*	24	A	.50	1.0	.125	.250	.50	
M22759/10-26-*	24	A	.50	1.0	.125	.250	.50	
M22759/10-24-*	30	A	.50	1.0	.125	.250	.50	
M22759/10-22-*	30	A	.50	1.0	.250	.375	.75	
M22759/10-20-*	30	A	.50	1.0	.250	.375	.75	
M22759/10-18-*	36	B	.75	1.0	.250	.375	1.00	
M22759/10-16-*	36	B	.75	2.0	.375	.500	1.00	
M22759/10-14-*	36	B	1.25	2.0	.500	.750	2.00	
M22759/10-12-*	36	B	1.25	2.0	.500	.750	2.00	
M22759/10-10-*	48	B	1.25	2.0	.750	1.00	3.00	
M22759/10-8-*	48	C	2.00	2.0	.750	1.00	3.00	

1/ Also for bend tests after immersion.

ADDITIONAL REQUIREMENTS

TEMPERATURE RATING: 260°C (500°F) max conductor temperature
VOLTAGE RATING: 1000 volts (rms) at sea-level
SPARK TEST OF PRIMARY INSULATION: Not required
IMPULSE DIELECTRIC TEST: 9.5 kilovolts (peak), 100% test
INSULATION RESISTANCE: 50,000 megohms for 1000 ft (min)
WRAP TEST: "Wrap back" test required; no cracking
Oven temperature, 313 ±2°C (595.4 ±3.6°F)
BLOCKING: 260 ±2°C (500 ±3.6°F)
SHRINKAGE: 0.03 inch max at 290 ±2°C (554 ±3.6°F)
WICKING: No requirement
LOW TEMPERATURE (COLD BEND):
Bend temperature: -65 ±2°C (-85 ±3.6°F)
Dielectric test, 3000 volts (rms), 60Hz
THERMAL SHOCK: Oven temperature, 260 ±2°C (500 ±3.6°F)
Max change in measurement Sizes 28 through 12: 0.060 inch
Sizes 10 through 8: 0.100 inch
FLAMMABILITY: Post-flame dielectric test not required
LIFE CYCLE: Oven temperature 275 ±2°C (527 ±3.6°F)
Dielectric test, 3000 volts (rms), 60Hz
DIELECTRIC TEST AFTER IMMERSION: 3000 volts (rms), 60Hz
ABRASION RESISTANCE AFTER IMMERSION: No requirement
HUMIDITY RESISTANCE: No requirement
SURFACE RESISTANCE: 500 megohm-inches (min), initial and final readings
SMOKE: 290°C (554°F)
ACID RESISTANCE: Required
Dielectric test, 3000 volts (rms), 60Hz
COLOR: In accordance with MIL-STD-104, Class 1; white preferred

COLOR STRIPING OR BANDING DURABILITY: 250 cycles (500 strokes) (min), 500 grams weight
IDENTIFICATION DURABILITY: 125 cycles (250 strokes) (min), 500 grams weight
WIRE LENGTH REQUIREMENTS: Schedule A
SUPERSESSION DATA: The wire of this specification sheet, by part number, replaces and supersedes the wire of MS18114(AS) (canceled) in accordance with Table III.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:45Z
Check the source to verify that this is the current version before use.

TABLE III. SUPERSESSION BY PART NUMBER

Part number MS18114(AS)	Part number MIL-W-22759/10
MS18114-28-*	M22759/10-28-*
MS18114-26-*	M22759/10-26-*
MS18114-24-*	M22759/10-24-*
MS18114-22-*	M22759/10-22-*
MS18114-20-*	M22759/10-20-*
MS18114-18-*	M22759/10-18-*
MS18114-16-*	M22759/10-16-*
MS18114-14-*	M22759/10-14-*
MS18114-12-*	M22759/10-12-*
MS18114-10-*	M22759/10-10-*
MS18114-8-*	M22759/10-8*

Custodians:
Navy - AS
Army - EL
Air Force - 80

Preparing activity:
Navy - AS
(Project No. 6145-0670-8)

Review activities:
Navy - EC, OS
Army - ME, MI, MU
Air Force -
DSA - IS
NSA

User activities:
Navy - MC
Army - AT, AV
Air Force - 11

Review/user information is current as of the date of this document. For future coordination of changes to this document, draft circulation should be based on the information in the current Federal Supply Classification Listing of DOD Standardization Documents.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:45Z
Check the source to verify that this is the current version before use.