
MILITARY SPECIFICATION SHEET

WIRE, ELECTRIC, FLUOROPOLYMER-INSULATED, FEP-PVF_2, LIGHT WEIGHT, TIN-COATED COPPER CONDUCTOR, 600-VOLT

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The complete requirements for procuring the wire described herein shall consist of this document and the issue in effect of Specification MIL-W-22759.

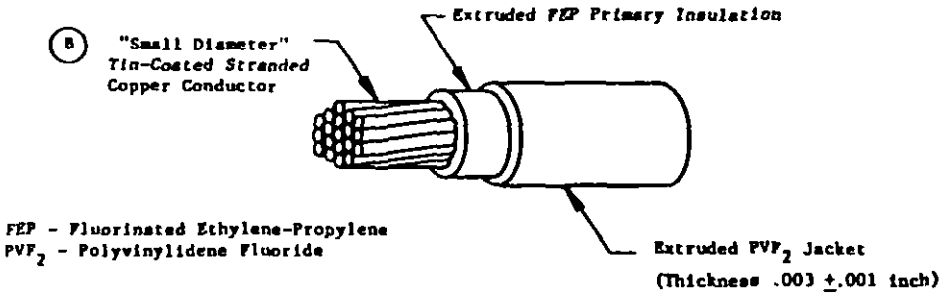

FEP - Fluorinated Ethylene-Propylene
PVF_2 - Polyvinylidene Fluoride

TABLE I. CONSTRUCTION DETAILS

Part No. 1/	Wire size	Stranding (Number of strands X AWG gage of strands)	Diameter of stranded conductor (inches) (B)		Finished wire		
			(min)	(max)	Resistance at 20°C (68°F) (ohms/1000 ft) (max) (B)	Diameter (inches)	Weight (lbs/1000 ft) (max) (B)
M22759/14-26-*	26	19 X 38	.018	.020	41.3	.037 ±.002	1.80
M22759/14-24-*	24	19 X 36	.023	.024	26.2	.042 ±.002	2.47
M22759/14-22-*	22	19 X 34	.029	.031	16.2	.048 ±.003	3.53
M22759/14-20-*	20	19 X 32	.037	.039	9.88	.056 ±.003	5.13
M22759/14-18-*	18	19 X 30	.046	.049	6.23	.066 ±.003	7.64
M22759/14-16-*	16	19 X 29	.052	.055	4.81	.071 ±.004	9.34
M22759/14-14-*	14	19 X 27	.065	.069	3.06	.087 ±.004	14.4
M22759/14-12-*	12	37 X 28	.084	.089	2.02	.107 ±.004	22.3

1/ PART NO.: The asterisks in the part number column, Tables I and II, shall be replaced by color code designators in accordance with MIL-STD-681. Examples: Size 20, white - M22759/14-20-9; white with orange stripe - M22759/14-20-93.

(B) denotes changes

FSC 6145

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:46Z
Check the source to verify that this is the current version before use.

TABLE II. PERFORMANCE DETAILS

Part No.	Abrasion resistance (Procedure II)					Bend testing				
	Resistance (inches of tape) (min) (B)		Weight support bracket	Weight (lbs)	Tension load (lbs)	Mandrel diameter (inches) (±3%)			Test load (lbs) (±3%)	
	Initial	After immersion 1/				Life cycle (oven & bend tests) 2/	Cold bend test		Life cycle (oven & bend tests) 2/	Cold bend test
M22759/14-26-*	22	15	A	.19	1.0	.50			.25	.5
M22759/14-24-*	18	13	A	.38	1.0	.50			.38	.5
M22759/14-22-*	20	14	A	.38	1.0	.75			.38	1.0
M22759/14-20-*	22	15	A	.38	1.0	.75			.38	1.0
M22759/14-18-*	18	13	A	.50	1.0	1.00			.50	1.0
M22759/14-16-*	20	14	A	.50	2.0	1.00			.50	1.0
M22759/14-14-*	24	17	A	.75	2.0	1.50			1.00	3.0
M22759/14-12-*	30	21	B	.75	2.0	2.00			1.00	3.0

1/ Qualification test only.

2/ Also for bend tests after immersion.

ADDITIONAL REQUIREMENTS

TEMPERATURE RATING: 135°C (275°F) max conductor temperature
VOLTAGE RATING: 600 volts (rms) at sea level
SPARK TEST OF PRIMARY INSULATION: 1500 volts (rms), 60Hz, 100% test
(B) IMPULSE DIELECTRIC TEST: 8.0 kilovolts (peak), 100% test
INSULATION RESISTANCE: 1000 megohms for 1000 ft (min)
WRAP TEST: "Wrap back" test required; no cracking
Oven temperature, 160 ±2°C (320 ±3.6°F)
BLOCKING: 135 ±2°C (275 ±3.6°F)
SHRINKAGE: 0.125 inch max at 150 ±2°C (302 ±3.6°F)
WICKING: No requirement
LOW TEMPERATURE (COLD BEND):
Bend temperature: -55 ±2°C (-67 ±3.6°F)
Dielectric test, 2500 volts (rms), 60Hz
THERMAL SHOCK: Oven temperature, 135 ±2°C (275 ±3.6°F)
Max change in measurement: 0.060 inch

(B) FLAMMABILITY: Post-flame dielectric test not required
LIFE CYCLE: Oven temperature 160 ±2°C (320 ±3.6°F)
Dielectric test, 2500 volts (rms) 60Hz
DIELECTRIC TEST AFTER IMMERSION: 2500 volts (rms), 60Hz
ABRASION RESISTANCE AFTER IMMERSION: Qualification test only
HUMIDITY RESISTANCE: 1000 megohms for 1000 ft, min insulation resistance after humidity exposure
SURFACE RESISTANCE: 500 megohm-inches (min), initial and final readings
SMOKE: 150°C (302°F)
ACID RESISTANCE: No requirement
(B) COLOR: In accordance with MIL-STD-104, Class 1; white preferred

COLOR STRIPING OR BANDING DURABILITY: 125 cycles (250 strokes) (min), 500 grams weight
IDENTIFICATION DURABILITY: 125 cycles (250 strokes) (min); 500 grams weight
(B) WIRE LENGTH REQUIREMENTS: Schedule A
(B) INTENDED USE: The wire of this specification sheet is intended for hookup applications in electronic chassis. It is also intended for use in bundles under a protective jacket for interconnecting applications in airframes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:46Z
Check the source to verify that this is the current version before use.

Custodians:
Navy - AS
Army - EL
Air Force - 80

Preparing activity:
Navy - AS
(Project No. 6145-0501-14)

Review activities:
Navy - EC, OS
Army - ME, MI, MU
Air Force -
DSA - IS
NSA

User activities:
Navy - MC
Army - AT, AV
Air Force - 11

Review/user information is current as of the date of this document. For future coordination of changes to this document, draft circulation should be based on the information in the current Federal Supply Classification Listing of DOD Standardization Documents.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:46Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE NAVY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12503 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE NAVY

Commanding Officer
Naval Air Engineering Center
Engineering Specifications & Standards
Department (ESSD) Code 93
Lakehurst, NJ 08733

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:46Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
	☐ USER
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ MANUFACTURER
	☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

(TO DETACH THIS FORM, CUT ALONG THIS LINE.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T13:46Z
Check the source to verify that this is the current version before use.