
FED SUP CLASS
5320

MS9403

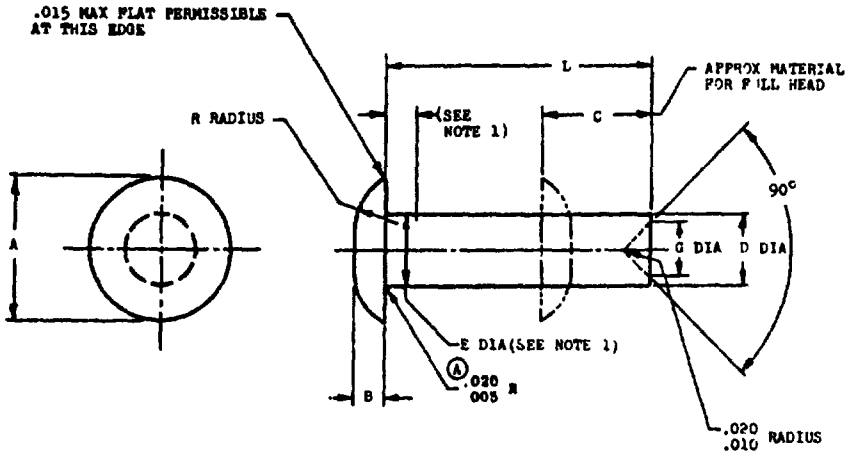

NOMINAL SIZE	A	B +.010 -.000	C	D	E	G ±.005	R	(2) S
.062	.119 - .131	.027	.094	061 - .063	.061 - .064	No Recess	.054	.010
.094	.179 - .197	.040	.141	.093 - .095	.093 - .096	No Recess	.082	.010
.125	.238 - .262	.054	.188	.123 - .126	.123 - .128	.070	.108	.010
.156	.296 .328	.067	.234	.154 157	.154 .159	.060	.135	.015
.188	.356 - .394	.080	.281	.186 - .189	.186 - .191	.100	.164	.015
.250	.475 - .525	.107	.375	.248 .252	.248 .254	125	.217	.020
.312	.594 - .656	.133	.469	.310 .314	.310 .316	.150	.272	.020
.375	.713 - .787	.161	.562	.374 .377	.373 .379	.180	.326	.020

1. DISTANCE .000 FOR LENGTHS 1/8 AND SHORTER AND .100 FOR LENGTHS LONGER THAN .1[illegible]
2. A DIA MUST BE CONCENTRIC WITH D DIA WITHIN 3 FULL INDICATOR READING
3. MATERIAL CORROSION AND HEAT RESISTANT STEEL AMS 5737 VACUUM MELT ONLY
4. SHEAR STRENGTH AT ROOM TEMPERATURE 80,000 TO 95,000 PSI AS HEAT TREATED
   90,000 PSI MINIMUM AFTER DRIVING
5. HEAT TREAT: SOLUTION TREAT AND PARTIALLY PRECIPITATION HEAT TREAT AFTER HEADING AS FOLLOWING
   SOLUTION HEAT TREAT AT 1050°F ±25° FOR 25 MINUTES - OIL QUENCH. PRECIPITATION HEAT TREAT
   AT 1250°F TO 1350°F FOR 30 TO 90 MINUTES AS NECESSARY TO MEET SHEAR REQUIREMENTS - AIR COOL
6. REMOVE BURRS AND BREAK SHARP EDGES .000 - .015
7. DIMENSIONS IN INCHES. UNLESS OTHERWISE SPECIFIED: TOLERANCES; LINEAR DIMENSIONS ±.010
   ANGULAR DIMENSIONS ±5°
8. IDENTIFICATION MARK MS9403-XXX AND MANUFACTURERS IDENTIFICATION ON CONTAINER
9. DO NOT USE UNASSIGNED PART NUMBERS

AS AND AMS ARE SAE PUBLICATIONS.

(A) FOR CHANGES SEE SHEETS 1 & 2

THIS STANDARD WAS DEVELOPED COOPERATIVELY WITH THE ENGINE AND PROPELLER UTILITY PARTS COMMITTEE OF THE SAE

P.A. USAF - 82 (A) Other Cust Army - AV Navy - AS	TITLE: RIVET, SOLID - UNIVERSAL HEAD, AMS 5737	MILITARY STANDARD MS9403
PROCUREMENT SPECIFICATION NONE	SUPERSEDES:	SHEET 1 OF 2

DD FORM 672-1 PREVIOUS EDITIONS OF THIS FORM ARE OBSOLETE 5320-0229

User activities: Army - ME, Navy - MC, Air Force - , DSA -

Review activities: Army - , Navy - , Air Force - 11, DSA -

This military standard is approved for use by all Departments and Agencies of the Department of Defense. Selection for all new engineering and design applications and for repetitive use shall be made from this document

APPROVED 9 May 62 REVISED (A) 27 Jun 74

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T13:16Z
Check the source to verify that this is the current version before use.

MS9403

FED SUP CLASS 5320

BOM SIZE	.062		.094		.125		.156		.188		.250		.312		.375	
L	PART NO.	APPROX WEIGHT LB/100	PART NO.	APPROX WEIGHT LB/100	PART NO.	APPROX WEIGHT LB/100	PART NO.	APPROX WEIGHT LB/100	PART NO.	APPROX WEIGHT LB/100	PART NO.	APPROX WEIGHT LB/100	PART NO.	APPROX WEIGHT LB/100	PART NO.	APPROX WEIGHT LB/100
.125	MS9403-002	.02	MS9403-065	.06	MS9403-126	.13	MS9403-189	.24	MS9403-250	.38					MS9403-449	4.00
.156	MS9403-003	.02	MS9403-066	.07	MS9403-127	.16	MS9403-190	.26	MS9403-251	.41	MS9403-313	.89			MS9403-450	4.11
.188	MS9403-004	.02			MS9403-128	.15	MS9403-191	.28	MS9403-252	.44	MS9403-314	.94			MS9403-451	4.22
.219	MS9403-005	.03	MS9403-067	.08	MS9403-129	.16	MS9403-192	.30	MS9403-253	.47					MS9403-452	4.33
.250	MS9403-006	.03	MS9403-068	.08	MS9403-130	.17										
.281	MS9403-007	.03	MS9403-069	.09	MS9403-131	.19										
.312	MS9403-008	.04	MS9403-070	.10												
.344	MS9403-009	.04														
.375	MS9403-010	.04	MS9403-071	.10	MS9403-132	.20	MS9403-193	.32	MS9403-254	.50	MS9403-315	.99			MS9403-453	4.45
.406	MS9403-011	.04	MS9403-072	.11	MS9403-133	.21	MS9403-194	.34	MS9403-255	.53	MS9403-316	1.04			MS9403-454	4.56
.438	MS9403-012	.05	MS9403-073	.12	MS9403-134	.22	MS9403-195	.36	MS9403-256	.54	MS9403-317	1.09			MS9403-455	4.68
.469	MS9403-013	.05	MS9403-074	.12	MS9403-135	.24	MS9403-196	.38	MS9403-257	.56	MS9403-318	1.14			MS9403-456	4.78
.500 ④	MS9403-014	.05	MS9403-075	.13	MS9403-136	.25	MS9403-197	.40	MS9403-258	.61	MS9403-319	1.19			MS9403-457	4.90
.531	MS9403-015	.06	MS9403-076	.14	MS9403-137	.26	MS9403-198	.42	MS9403-259	.64	MS9403-320	1.24			MS9403-461	5.35
.562	MS9403-016	.06	MS9403-077	.14	MS9403-138	.27	MS9403-199	.44	MS9403-260	.67	MS9403-321	1.29	MS9403-382	2.15	MS9403-465	5.80
.594	MS9403-017	.06	MS9403-078	.15	MS9403-139	.29	MS9403-200	.46	MS9403-261	.69	MS9403-322	1.34	MS9403-383	2.23	MS9403-466	6.25
.625	MS9403-018	.07	MS9403-079	.16	MS9403-140	.30	MS9403-201	.48	MS9403-262	.72	MS9403-323	1.39	MS9403-384	2.31	MS9403-473	6.70
.656			MS9403-080	.17	MS9403-141	.31	MS9403-202	.50	MS9403-263	.75	MS9403-324	1.44	MS9403-385	2.39	MS9403-474	7.15
.688			MS9403-081	.17	MS9403-142	.32	MS9403-203	.52	MS9403-264	.78	MS9403-325	1.49	MS9403-386	2.47	MS9403-481	7.60
.719			MS9403-082	.18	MS9403-143	.34	MS9403-204	.53	MS9403-265	.81	MS9403-326	1.54	MS9403-387	2.54	MS9403-482	8.05
.750			MS9403-083	.19	MS9403-144	.35	MS9403-205	.55	MS9403-266	.83	MS9403-327	1.59	MS9403-388	2.62	MS9403-489	8.50
.781			MS9403-084	.19	MS9403-145	.36	MS9403-206	.57	MS9403-267	.86	MS9403-328	1.64	MS9403-389	2.70		
.812			MS9403-085	.20	MS9403-146	.37	MS9403-207	.59	MS9403-268	.89	MS9403-329	1.69	MS9403-390	2.77		
.844			MS9403-086	.21	MS9403-147	.38	MS9403-208	.61	MS9403-269	.92	MS9403-330	1.74	MS9403-391	2.86		
.875			MS9403-087	.21	MS9403-148	.40	MS9403-209	.63	MS9403-270	.95	MS9403-331	1.79	MS9403-392	2.93	MS9403-453	4.45
.906			MS9403-088	.22	MS9403-149	.41	MS9403-210	.64	MS9403-271	.98	MS9403-332	1.84	MS9403-393	3.00	MS9403-454	4.56
.938			MS9403-089	.23	MS9403-150	.42	MS9403-211	.67	MS9403-272	1.00	MS9403-333	1.89	MS9403-394	3.09	MS9403-455	4.68
.969			MS9403-090	.23	MS9403-151	.44	MS9403-212	.68	MS9403-273	1.03	MS9403-334	1.94	MS9403-395	3.17	MS9403-456	4.78
1.000			MS9403-091	.24	MS9403-152	.45	MS9403-213	.71	MS9403-274	1.06	MS9403-335	1.99	MS9403-396	3.25	MS9403-457	4.90
1.125					MS9403-156	.50	MS9403-217	.79	MS9403-278	1.17	MS9403-339	2.19	MS9403-400	3.57	MS9403-461	5.35
1.250					MS9403-160	.55	MS9403-221	.86	MS9403-282	1.28	MS9403-343	2.39	MS9403-404	3.87	MS9403-465	5.80
1.375					MS9403-164	.60	MS9403 225	.94	MS9403-286	1.39	MS9403-347	2.59	MS9403-408	4.19	MS9403-466	6.25
1.500					MS9403-168	.65	MS9403-229	1.02	MS9403-290	1.51	MS9403-351	2.79	MS9403-412	4.50	MS9403-473	6.70
1.625					MS9403-172	.70	MS9403-233	1.10	MS9403-294	1.62	MS9403-355	2.99	MS9403-416	4.81	MS9403-474	7.15
1.750					MS9403-176	.75	MS9403-237	1.17	MS9403-298	1.73	MS9403-359	3.19	MS9403-420	5.12	MS9403-481	7.60
1.875					MS9403-180	.80	MS9403-241	1.25	MS9403-302	1.85	MS9403-363	3.39	MS9403-424	5.45	MS9403-482	8.05
2.000					MS9403-184	.85	MS9403-245	1.33	MS9403-306	1.96	MS9403-367	3.59	MS9403-428	5.75	MS9403-489	8.50

④ MS9403-014 WAS MS9403-104

Review activities:
Army –
Navy –
Air Force – 11
DSA – 15

User activities:
Army – ME
Navy – MC
Air Force –
DSA –

This military standard is approved for use by all Departments and Agencies of the Department of Defense. Selection for all new engineering and design applications and for repetitive use shall be made from this document.

AS A D AS ARE SAE PUBLICATIONS.
THIS STANDARD WAS DEVELOPED COOPERATIVELY WITH THE ENGINE AND PROPELLER UTILITY PARTS COMMITTEE OF THE SAE

APPROVED 9 May 82 REVISED Ⓐ FOR CHANGES SEE SHEETS 1 & 2

P.A. USAF - 82 Ⓐ
Other Cust
Army - AV
Navy - AS

TITLE: RIVET, SOLID - UNIVERSAL HEAD, AMS 5737

MILITARY STANDARD
MS9403

PROCUREMENT SPECIFICATION NONE

SUPERSEDES:

SHEET 2 OF 2

DD FORM 672-1

5320-0229

☆U S GOVERNMENT PRINTING OFFICE 1981 — 703 023/7849

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T13:16Z
Check the source to verify that this is the current version before use.