

## Electronic supplementary information

# INFLUENCE OF DIVALENT METAL PROMOTERS ON THE Pt DISPERSION AND PERFORMANCE OF THE Pt/MFI PROPANE DEHYDROGENATION CATALYSTS

A. B. Ponomaryov,<sup>\*a</sup> A. V. Smirnov,<sup>b</sup> M. V. Shostakovsky,<sup>a</sup>  
M. A. Kashkina,<sup>a,b</sup> and E. V. Pisarenko<sup>c</sup>

<sup>a</sup> Nesmeyanov Institute of Organoelement Compounds, Russian Academy of Sciences,  
ul. Vavilova 28, str. 1, Moscow, 119334 Russia

<sup>b</sup> Department of Chemistry, Lomonosov Moscow State University,  
Leninskie Gory 1, str. 3, Moscow, 119991 Russia

<sup>c</sup> Department of Cybernetics of Chemical Technological Processes,  
Mendeleev University of Chemical Technology of Russia,  
Miusskaya pl. 9, Moscow, 125047 Russia

## Tables of contents

<b>Experimental section</b>	S2
<b>Table S1.</b> Chemical compositions of the catalyst samples derived from MFI-80 zeolite	S4
<b>Figure S1.</b> XRD patterns of 0.5Pt-based samples derived from MFI-80 zeolite with and without Na, Mg, Cu	S5
<b>Figure S2.</b> Effect of divalent promoters on the propylene yield and selectivity to propylene in PDH reaction	S5
<b>Table S2.</b> Catalytic performance of some MPt catalysts for propane dehydrogenation reported to date in comparison with the catalysts prepared in the present study	S6
<b>References</b>	S7

## Experimental section

### Reagents and catalysts

MFI-type zeolite with the nominal SiO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> molar ratio of 80 (Zeolyst Int.) was used in the H-form after calcination at 600 °C. AR-grade NaCl, CaCl<sub>2</sub>·6H<sub>2</sub>O, MgCl<sub>2</sub>·6H<sub>2</sub>O, ZnCl<sub>2</sub>, MnCl<sub>2</sub>·4H<sub>2</sub>O, CoCl<sub>2</sub>·6H<sub>2</sub>O, CuCl<sub>2</sub>·2H<sub>2</sub>O, NiCl<sub>2</sub>·6H<sub>2</sub>O, SnCl<sub>2</sub>·2H<sub>2</sub>O, and H<sub>2</sub>PtCl<sub>6</sub>·6H<sub>2</sub>O were used for the catalyst preparation. Propane (99.92%) was purchased from BK Group, Russia. The physicochemical properties of the initial zeolites are described in Ref. [1].

### Preparation of the catalysts

All catalysts were prepared with the promoter/Pt atomic ratio of about 3 (Table S1).

**Example of the (3Na)400w150(0.4Mn0.5Pt) catalyst preparation procedure (atomic ratio Mn/Pt = 2.8).** An impregnating solution was prepared by dissolving 0.38 g of NaCl in 3 mL of distilled water. The resulting solution and 5 g of a zeolite powder were preheated separately in a water bath to 70 °C. The solution and zeolite were then mixed and held for 1 h under periodical stirring at 70 °C. The mixture was dried at 150 °C for 1 h and calcined in air in a muffle furnace at 400 °C. The powder obtained was mixed with 25 mL of distilled water using a magnetic stirrer at 80 °C for 0.5 h. The product was filtered off without additional washing and dried at 150 °C for 1 h. The sample (1.0 g) was further impregnated with a mixture of 0.015 g of MnCl<sub>2</sub>·4H<sub>2</sub>O, 0.32 g of H<sub>2</sub>PtCl<sub>6</sub> solution (13.2 g Pt/L), and 0.28 g of water. After drying at 150 °C for 1 h, the sample was calcined again at 500 °C. The calcination involved heating at a rate of 10 °C/min to 500 °C and keeping at this temperature for 1 h.

### Characterization of the catalysts

The quantitative elemental analysis was performed by energy dispersive X-ray fluorescence spectroscopy (ED-XRF) using a ThermoScientific ARL Perform'x instrument.

The phase composition of the samples was identified by powder X-ray diffraction analysis (XRD) on a TongDaTD-3700 diffractometer equipped with CuK $\alpha$  irradiation.

The Pt dispersion was measured by CO pulse chemisorption using a USGA-101 analyzer. About 200 mg of the sample was placed in a quartz microreactor 4 mm in inner diameter (ID). The sample was heated to 200 °C at a rate of 10 °C/min in a helium flow (10 mL/min) and held at 200 °C for 0.5 h. The gas flow was switched from He to H<sub>2</sub>, and the sample was heated in H<sub>2</sub> at 10 °C/min to 540 °C, followed by keeping at this temperature for another 30 min. The reactor was cooled in H<sub>2</sub> to 200 °C, purged with He at 200 °C for 0.5 h, and finally cooled to room temperature in a continuous He flow. For the chemisorption analysis, 0.25 mL pulses of carbon monoxide (CO) diluted to 9.7% in He were injected into a helium flow at 3-min intervals. This was continued until the chemisorption sites reached saturation. The CO concentration at the reactor outlet was monitored by a thermal conductivity detector (TCD). The amount of chemisorbed CO was derived from the TCD signal areas. The Pt dispersion was calculated by the equation:

$$D = \frac{V \cdot AW \cdot SF}{W \cdot 24400} \cdot 100\%,$$

where  $V$  is the volume of the adsorbed CO (mL);  $AW$  is the atomic weight of Pt (g/mol);  $SF$  is the stoichiometric factor (assumed to be equal to 1); and  $W$  is the Pt weight in the sample (g).

**The catalytic tests** were carried out in a 4-mm ID tubular quartz reactor at 540 °C, 0.1 MPa. The catalyst sample (0.05 g) was loaded into the reactor, heated in nitrogen to 300 °C at 15 mL/min, then in H<sub>2</sub> to 540 °C at 10 mL/min, and held at 540 °C for 0.5 h. The flow was then switched from H<sub>2</sub> to propane with a flow rate of 13 mL/min (WHSV=28 h<sup>-1</sup>).

The PDH reaction was conducted using pure propane without hydrogen or an inert gas. The reaction products were analyzed online on a *Chromatec Crystal 5000* gas chromatograph equipped with a 25-m KCl-Al<sub>2</sub>O<sub>3</sub> capillary column and a flame ionization detector (FID).

The propane conversion, reaction product selectivity, and product yields were determined as follows.

Propane conversion:

$$X = \frac{\text{mass of propane in the feed} - \text{mass of propane in the product}}{\text{mass of propane in the feed}} \cdot 100\%;$$

Product selectivity:

$$S_i = \frac{\text{mass of product } i}{\text{mass of all products}} \cdot 100\%;$$

Product yield:

$$Y_i = S_i \cdot X / 100$$

The specific activity was defined as moles of propylene produced by 1 mol of Pt atoms per second.

The deactivation constants  $K_d$  were calculated using the following equation:

$$K_d * t = \ln\left(\frac{(1-X_f)/X_f}{(1-X_{in})/X_{in}}\right),$$

where  $t$  is the time on stream,  $X_{in}$  is the propane conversion after 1 h on stream,  $X_f$  is the propane conversion at the end of the experiment.

A higher deactivation constant indicates a faster loss of the catalyst activity.


The catalyst index of productivity ( $IP$ ) was used as a benchmark for comparison [2], which was calculated using the following equation:

$$IP = \frac{SA}{K_d},$$


where  $SA$  is the specific activity expressed in  $s^{-1}$ ,  $K_d$  is the deactivation constant expressed in  $h^{-1}$ .

**Table S1.** Chemical compositions of the catalyst samples derived from MFI-80 zeolite

Sample		Element content, wt % (XRFI)				M:Pt atomic ratio
Promoter M	Name	Na	M	Pt	Cl	
no	(3Na)400w150(0.5Pt)	0.73	—	0.51	0.18	—
Ca	(3Na)400w150(0.3Ca0.5Pt)	0.68	0.29	0.55	0.42	2.60
Mg	(3Na)400w150(0.2Mg0.5Pt)	0.74	0.17	0.57	0.29	2.43
Mn	(3Na)400w150(0.4Mn0.5Pt)	0.65	0.42	0.53	0.26	2.82
Zn	(3Na)400w150(0.5Zn0.5Pt)	0.87	0.52	0.43	0.35	3.37
Co	(3Na)400w150(0.5Co0.5Pt)	0.94	0.52	0.51	0.28	3.37
Cu	(3Na)400w150(0.50Cu0.5Pt)	0.88	0.51	0.51	0.29	3.06
Ni	(3Na)400w150(0.5Ni0.5Pt)	0.81	0.43	0.52	0.32	2.70
Sn	(3Na)400w150(0.9Sn0.5Pt)	0.81	0.87	0.47	0.24	3.06

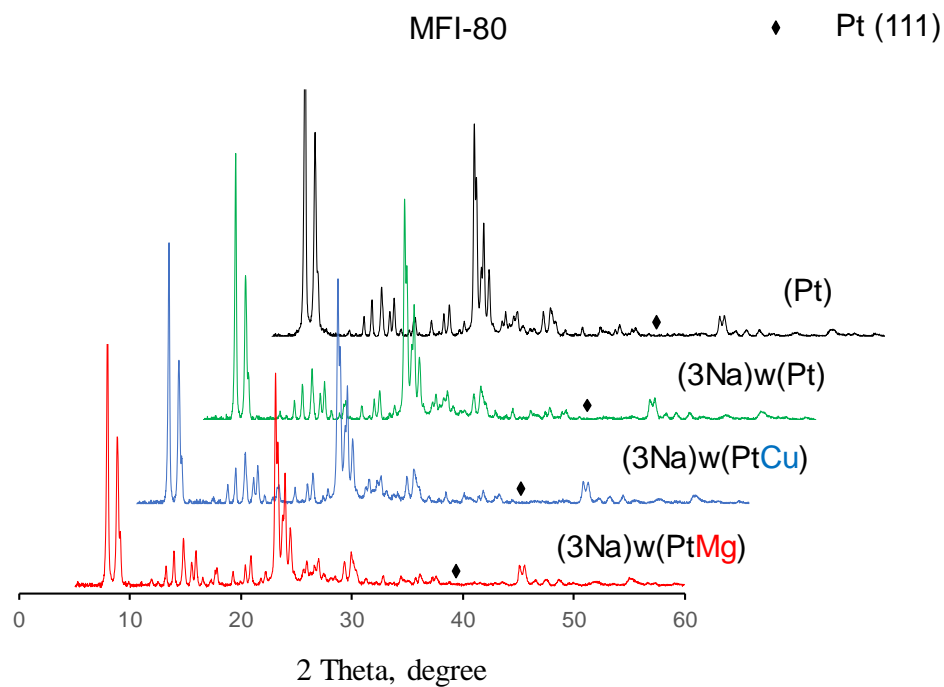

**Figure S1.** XRD patterns of 0.5Pt-based samples derived from MFI-80 zeolite with and without Na, Mg, Cu.

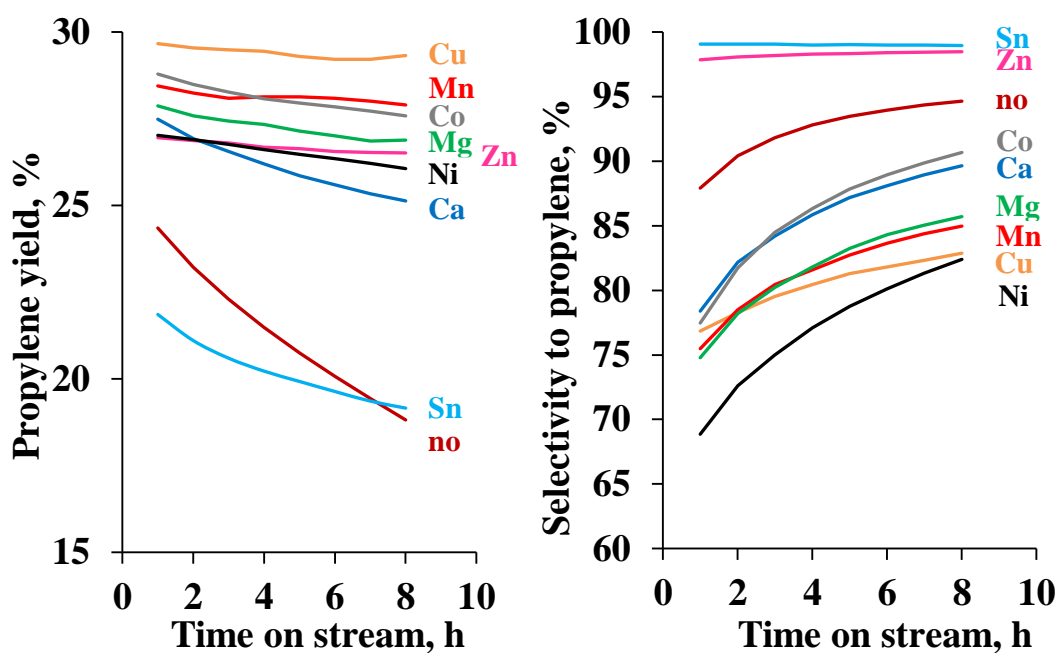

**Figure S2.** Effect of divalent promoters on the propylene yield and selectivity to propylene in PDH reaction. The reaction conditions: WHSV = 28 h<sup>-1</sup>, 540 °C, 0.1 MPa.

**Table S2.** Catalytic performance of some MPt catalysts for propane dehydrogenation reported to date in comparison with the catalysts prepared in the present study

Catalyst	WHSV, h <sup>-1</sup>	T, °C	C <sub>3</sub> H <sub>6</sub> yield, %	Feed composition	Pt, %	Time on stream, h	Specific activity, s <sup>-1a</sup>	Deactivation constant, h <sup>-1</sup>	IP <sup>b</sup>	Ref.
Pt <sup>0</sup> Zn <sup>δ+</sup> /SiO <sub>2</sub>	75	550	30	C <sub>3</sub> H <sub>8</sub> /Ar = 1/4	3.05	30	0.96	0.027	35	[3]
K-PtSn@MFI-H2	27	600	68	C <sub>3</sub> H <sub>8</sub> / N <sub>2</sub> = 1/3.3	0.40	25	3.31	0.022	150	[4]
0.1Pt0.4CuK@S-1	5.4	550	40	C <sub>3</sub> H <sub>8</sub> /N <sub>2</sub> = 1/3	0.16	73	1.73	0.005	355	[5]
(3Na0.5Sn)w(0.25Pt)	28	570	35	pure C <sub>3</sub> H <sub>8</sub>	0.24	8	5.30	0.013	404	[6]
(3Na)400w150(0.5Zn0.5Pt)			27		0.43		2.26	0.004	514	
(3Na)400w150(0.50Cu0.5Pt)			30		0.51		2.10	0.020	106	
(3Na)400w150(0.9Sn0.5Pt)			22		0.47		1.68	0.024	71	
(3Na)400w150(0.4Mn0.5Pt)			28		0.53		1.94	0.031	64	
(3Na)400w150(0.5Co0.5Pt)	28	540	29	pure C <sub>3</sub> H <sub>8</sub>	0.51	8	2.04	0.043	47	This work
(3Na)400w150(0.2Mg0.5Pt)			28		0.57		1.77	0.038	47	
(3Na)400w150(0.5Ni0.5Pt)			27		0.52		2.08	0.048	44	
(3Na)400w150(0.3Ca0.5Pt)			28		0.55		1.84	0.047	39	
(3Na)400w150(0.5Pt)			24		0.51		1.72	0.062	28	

<sup>a</sup> specific activity is defined as the moles of C<sub>3</sub>H<sub>6</sub> formation per Pt g-atom per second;

<sup>b</sup> IP (index of productivity) is the specific activity/deactivation constant [7].

## References

1. A. B. Ponomaryov, A. V. Smirnov, E. V. Pisarenko, M. V. Shostakovsky, *Microporous Mesoporous Mater.*, **2022**, 339, 112010. DOI: 10.1016/j.micromeso.2022.112010
2. A. B. Ponomaryov, A. V. Smirnov, E. V. Pisarenko, M. V. Shostakovsky, *Appl. Catal., A*, **2024**, 673, 119588. DOI: 10.1016/j.apcata.2024.119588
3. L. Rochlitz, K. Searles, J. Alfke, D. Zemlyanov, O.V. Safonova, C. Copéret, *Chem. Sci.*, **2020**, 11, 1549–1555. DOI: 10.1039/C9SC05599A
4. L. Liu, M. Lopez-Haro, C. W. Lopes, S. Rojas-Buzo, P. Concepcion, R. Manzorro, L. Simonelli, A. Sattler, P. Serna, J. J. Calvino, A. Corma, *Nat. Catal.*, **2020**, 3, 628–638. DOI: 10.1038/s41929-020-0472-7
5. J. Zhou, Y. Zhang, H. Liu, C. Xiong, P. Hu, H. Wang, S. Chen, H. Ji, *Nano Res.*, **2023**, 16, 6537–6543. DOI: 10.1007/s12274-022-5317-z
6. A. B. Ponomaryov, A. V. Smirnov, M. V. Shostakovsky, E. V. Pisarenko, A. G. Popov, M. A. Kashkina, *Pet. Chem.*, **2024**, 64, 1147–1158. DOI: 10.1134/S096554412404008X
7. A. B. Ponomaryov, A. V. Smirnov, E. V. Pisarenko, M. V. Shostakovsky, *Appl. Catal., A*, **2024**, 673, 119588. DOI: 10.1016/j.apcata.2024.119588