




APPAREL TESTING MANUAL

September 2025
Version 32

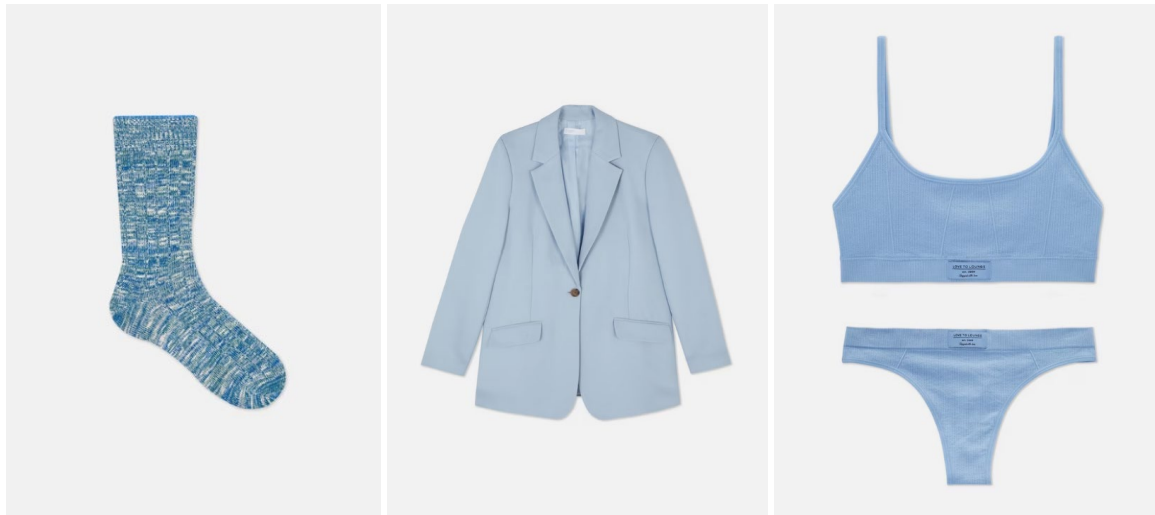

Contents

INTRODUCTION	5
PRIMARK'S MINIMUM REQUIREMENTS	5
GLOBAL LAB SUPPORT	6
PRODUCT COMPOSITION CLAIMS	7
PTC01 – ADULTS WOVEN TOPS, BOTTOMS AND DRESSES (EXCEPT DENIM)	8
PTC02 – CHILDREN'S WOVEN TOPS, BOTTOMS AND DRESSES (EXCEPT DENIM)	10
PTC03 – ADULTS DENIM WEAR.....	14
PTC04 – CHILDREN'S DENIM WEAR.....	17
PTC05 – ADULTS OUTERWEAR – WOVEN & KNITTED.....	20
PTC06 – CHILDREN'S OUTERWEAR – WOVEN & KNITTED.....	25
PTC07 – ADULTS JERSEYWEAR E.G. SINGLE JERSEY, RIBS, INTERLOCK, PIQUE, POINTELLE.....	29
PTC08 – CHILDREN'S JERSEYWEAR E.G. SINGLE JERSEY, RIBS, INTERLOCK, PIQUE, POINTELLE.....	32
PTC09 – ADULTS KNITTED LEISUREWEAR, FLEECE, LOOP-BACK, BRUSH-BACK & POLAR FLEECE.....	35
PTC10 – CHILDREN'S KNITTED LEISUREWEAR, FLEECE, LOOP-BACK, BRUSH-BACK & POLAR FLEECE.....	37
PTC11 – ADULTS KNITWEAR E.G. CARDIGANS, JUMPERS.....	41
PTC12 – CHILDREN'S KNITWEAR E.G. CARDIGANS, JUMPERS.....	43
PTC13 – ADULTS SWIMWEAR & BEACHWEAR – WOVEN & KNITTED	45
PTC14 – CHILDREN'S SWIMWEAR & BEACHWEAR – WOVEN & KNITTED	49
PTC15 – ADULTS PERFORMANCE WEAR – WOVEN & KNITTED	53
PTC15A – CHILDREN'S PERFORMANCE WEAR – WOVEN & KNITTED.....	56
PTC16 – ADULTS NIGHTWEAR AND LOUNGEWEAR – WOVEN & KNITTED	60
PTC17 – CHILDREN'S NIGHTWEAR – WOVEN AND KNITTED	65
PTC18A – ADULTS UNDERWEAR E.G., BRIEFS, TRUNKS, UNDERWEAR VESTS AND CAMI'S, UNDERWEAR LEGGINGS	71

PTC18B – ADULTS LINGERIE -ALL BRAS, BRA ACCESSORIES, UNDERWIRED, CUPPED STYLES INCLUDING BODY SUITS, CORSETS, AND SUSPENDER BELTS.	76
PTC19 – CHILDREN’S UNDERWEAR	80
PTC20A – ADULTS SOCKS.....	85
PTC20B – ADULTS HOSIERY	88
PTC21A – CHILDREN’S SOCKS	91
PTC21B – CHILDREN’S HOSIERY	95
PTC22 – ADULTS COATED PRODUCTS E.G., PU, PVC.....	97
PTC23 – CHILDREN’S COATED PRODUCTS E.G., PU, PVC.....	100
PTC24 – ADULTS WOVEN & KNITTED LININGS, POCKETINGS & INTERLININGS.....	103
PTC25 – CHILDREN’S WOVEN & KNITTED LININGS, POCKETINGS & INTERLININGS.....	105
PTC25 – CHILDREN’S WOVEN & KNITTED LININGS, POCKETINGS & INTERLININGS.....	105
PTC26 – ADULTS TRIMS, FASTENING & ZIPPER	107
PTC27 – CHILDREN’S TRIMS, FASTENING & ZIPPER	108
PTC28 – LEATHER & SUEDE PRODUCTS.....	110
PTC29 – BABY BIBS, MUSLINS, BABY BLANKETS, BABY MITTENS	111
PTT07 – DISGUISE COSTUMES, DRESS UP	115
PTC31 – ADULT TIES.....	117
PTC34 – CHILDREN’S LIGHT UP JUMPERS (EU AND UK MARKETS ONLY)	118
PTC35 – ADULTS FAUX SUEDE PRODUCTS.....	119
PTC36 – CHILDRENS FAUX SUEDE PRODUCTS	122
PTC37 – SKI WEAR	126
IN HOUSE TEST METHODS	130
PM01- PRODUCT APPEARANCE AFTER EXTENDED WASH & APPEARANCE AFTER WASH BS EN ISO 6330: 2012	131
PM01 APPEARANCE AFTER EXTENDED WASH - WASH ASSESSMENT TABLE.....	132

TABLE A (PART I) A-Q ONLY (ASSESSMENT CRITERIA FOR PM01 AND APPEARANCE AFTER WASH 1 & 5 WASHES).....	132
TABLE A – PART II – ADDITIONAL ASSESSMENT CRITERIA FOR PM01 ONLY.....	133
TABLE A – PART III – ADDITIONAL ASSESSMENT CRITERIA FOR PM01 ONLY (ADDITIONAL PRODUCT CATEGORY SPECIFIC CRITERIA FOR REVIEW IN ALL EXTENDED WASH INCREMENTS)	134
PM02 - PRINT / MOTIF / FLOCK DURABILITY.....	135
PM03 – NAP STABILITY	136
PM04 – DIMENSIONAL AND BRA WIRE CASING STABILITY.....	137
PM05 – FIBRE SHEDDING / PILE LOSS	137
PM06 – CHENILLE PILE LOSS.....	140
PM07 – BACK POCKET APPLICATION STRENGTH.....	142
PM08 – BELT LOOP APPLICATION STRENGTH.....	144
PM22 – HEAT CONDUCTIVITY ON METAL TRIMS.....	145
PM23 – ELASTIC EXTENSION AND MODULUS TEST	148
PM26 – PUNCTURE RESISTANCE OF BRA WIRE CASING	150
TABLE OF CHANGE	153

Introduction

It is the Supplier's responsibility to ensure that they are fully aware of the content and requirements of this manual. Products sold in Primark stores must at all times be safe, legal, fit for purpose, and consistently meet the quality and compliance standards of this manual. All products, including their associated packaging, supplied to Primark must fully comply with all current and relevant United Kingdom, European Union and United States legislation, regulations, standards, including, where applicable, recognised industry Codes of Conduct. Primark regularly updates documents placed on the Primark Interlink Testing Portal; therefore, it is essential that all Suppliers frequently check the information and ensure that they are familiar and up-to-date with all relevant Primark policies, Primark's compliance Code of Conduct and all Primark quality and compliance requirements.

Primark's minimum requirements:

1. **For Adult's Apparel** FULL TEST PACKAGE testing is mandatory on the first test request form (TRF) submission for at least for one colour option per style. COLOURFASTNESS TESTS and PM01 (or APPERANCE AFTER WASH) are mandatory for every single colour per style. Linking of the COLOURFASTNESS TESTS to the FULL TEST PACKAGE test report via a new TRF is only possible for products of different colours within the same style.
For Children's Apparel FULL TEST PACKAGE testing is mandatory for every single colour per style. Linking is not allowed. PM01 (or APPERANCE AFTER WASH) are mandatory for every single colour per style.
For Adult's Home Textiles FULL TEST PACKAGE testing is mandatory on the first test request form (TRF) submission for at least for one colour option per style. COLOURFASTNESS TESTS and PM01 are required for every single colour per style. Linking of the COLOURFASTNESS TESTS to the FULL TEST PACKAGE test report via a new TRF is only possible for products of different colours within the same style.
For Footwear (Children's and Adult's) FULL TEST PACKAGE testing is mandatory for every single colour per style. Linking is not allowed.
Other Adult's and Children's products FULL TEST PACKAGE testing is mandatory for every single colour per style. Linking is not allowed.
2. All product testing must be completed by one of Primark's approved Labs: TÜV SÜD, TUV Rheinland, Bureau Veritas, UL, Intertek, SGS, and Hohenstein. Suppliers are free to choose any of the above-mentioned Labs to carry out testing, however, every Lab has different capabilities. It will remain the Suppliers' responsibility to check with their preferred Lab regarding the capabilities/capacity to test a specific product category prior to submitting the TRF/sending the product sample for testing to the Lab. Testing for the same style must not be divided between different Labs, except for products with a formulated component (refer to "Requirements for Formulated Product").
3. Suppliers must complete full package testing through Primark Interlink Testing Portal. CPCs and PCCs will only be issued once the sample has passed all Primark's compliance requirements for all markets.
4. Suppliers must always select the correct test package applicable to the product. If no applicable test package is available on the TRF, please seek guidance from one of Primark's approved Labs to verify what tests are required.
5. Product submitted for testing must be a true representation of production samples including product packaging and the Gold Sealed sample by Primark.
6. Supplier must liaise with the Lab to confirm the correct number of samples to be sent for testing, which will depend on the product to be tested.
7. Critical path management is imperative. It is the Supplier's responsibility to ensure enough time has been allowed for testing and possible retests prior to the handover date.
8. Suppliers must ensure they submit the accurate information and attach all relevant supplementary documents and product pictures when submitting the TRF.
9. If technical support or Primark Interlink Testing Portal assistance is required, Suppliers should contact interlinksupport@intertek.com

10. Primark products made of wood and wood-derived fibres must comply with the PRIMARK WOOD AND WOOD-DERIVED FIBRE POLICY available on the Primark Interlink Testing Portal.
11. Risk Assessment must be completed by the supplier based on Primark template and must submit to Primark technologist for approval before black seal review.
12. A Safety Data Sheet (SDS) and toxicological risk assessment (TRA) are required for formulated/liquid products (that aren't classed as cosmetics) such as liquid filled articles, toy slimes/modelling clay etc. The Safety data sheet (SDS) and toxicological risk assessment (TRA) must be submitted by the Supplier along with the TRF to one of Primark's nominated Labs. If Supplier does not have a Safety Data Sheet (SDS) and toxicological risk assessment (TRA) in hand, these must be requested via TRF to the Primark nominated Labs.
13. For (1) stationary with a formulated component, (2) products made of gel or semi-solid material, and (3) products filled with formulated, liquid, gel, semi-solid fillings that are not classed as cosmetics, the Supplier is required to submit to the Exponent lab via a separate TRF the following: Formulation, Final Product List of Components and Materials, Final Product Design/Artwork, Raw Material Data, Product Labelling, Product Safety Report (PSR) (or TRA), Challenge Test (if product is water based), Total Viable Count (TVC), Colours / Pigments (where used), Heavy Metal Test, Safety Data Sheet, GMP, and REACH Data. The details of the process are stated in the "Primark data requirement manual for formulated toys and non-cosmetic products with international or likely skin contact". The Primark approved Lab is required to perform a full product testing (including compliance tests) as per relevant test package and must upload a test report to the Primark Datalink Testing Portal. No PCC / CPC is required, as this will be issued by the Exponent Lab after the formulated component document review.
14. For electrical products, toys, PPE and sunglasses Supplier must always submit Labelling and Artwork to the Lab along with the Product sample.

Global Lab Support

Account manager	Contacts	Website
Sean Lawler	Email: Sean.Lawler@uk.tuv.com	www.tuv.com
Gurdeep Singh Kudhail	Phone: 07585 067268 Email: Gurdeep.Kudhail@tuvsud.com	www.tuvsud.com
Katy Claypole	Phone: +44 (0)116 2846780/ Email: Katy.Claypole@sgs.com	www.sgs.com/en
Tricia Zourmand/ Jasmine To	Phone: +49 7143 271 535 Email: t.zourmand@hohenstein.com Phone +49 7143 271 13 Email: jasmine.to@hohenstein.com	hohenstein.com
Elise Cheng/ Sharen Ching	Phone: +44 7530 366076 Email: elise.cheng@bureauveritas.com Email: sharen.ching@bureauveritas.com	www.bureauveritas.co.uk/cps
Megan Smith	Email: megan.smith@intertek.com	www.intertek.com
Tomasz Potempa/ Anita Bambrych	Email: Tomasz.potempa@ul.com Phone: +44 (0)7769 264757 Email: Anita.Bambrych@ul.com	www.ul.com

Product composition Claims

PRODUCT COMPOSITION CLAIM	TEST STANDARD	LABEL CLAIM	REQUIREMENT	COMMENTS
ALL FIBRES (EXCEPT WOOL) PURE, RICH, BLENDED, MIX, CONTAINS (ANY BRANDED FIBRES NEED TO BE AGREED WITH LISCENSOR)	EU 1007/2011	PURE	MUST BE MADE FROM 100% OF CLAIMED FIBRE	* 100% MADE FROM ONE YARN FIBRE
		RICH	MUST BE MADE FROM A MINIMUM OF 60% OF CLAIMED FIBRE	* 60% MUST BE MADE FROM ONE YARN FIBRE, OTHER 40% CAN BE MADE UP OF ALL OTHER FIBRES
		BLEND	MUST BE MADE FROM A MINIMUM OF 30% OF CLAIMED FIBRE	* 30% MUST BE MADE FROM ONE YARN FIBRE, OTHER 70% CAN BE MADE UP OF ALL OTHER FIBRES
		MIX	MUST BE MADE FROM A MINIMUM OF 25% OF CLAIMED FIBRE	* 25% MUST BE MADE FROM ONE YARN FIBRE, OTHER 70% CAN BE MADE UP OF ALL OTHER FIBRES
		CONTAINS	MUST BE MADE FROM A MINIMUM OF 10% OF CLAIMED FIBRE	* 10% MUST BE MADE FROM ONE YARN FIBRE
WOOL: PURE, RICH, BLENDED, MIX, CONTAINS	EU 1007/2011	PURE	MUST BE MADE FROM 100% WOOL	* 100% WOOL YARN - WOOL YARN CANNOT BE BLENDED OR MIXED
		RICH	MUST BE MADE FROM A MINIMUM OF 60% WOOL	* 60% WOOL YARN CANNOT BE BLENDED OR MIXED - OTHER 40% CAN BE MADE UP OF ALL OTHER FIBRES
		BLEND	MUST BE MADE FROM A MINIMUM OF 50% WOOL	* 50% WOOL YARN CAN ONLY BE BLENDED WITH 1 OTHER ANIMAL FIBRE - OTHER 50% CAN BE MADE FROM OTHER FIBRES
		MIX	MUST BE MADE FROM A MINIMUM OF 25% OF CLAIMED FIBRE	* 25% WOOL YARN CAN BE MIXED WITH OTHER ANIMAL FIBRES - OTHER 75% CAN BE MADE FROM ALL OTHER FIBRES
		CONTAINS	MUST BE MADE FROM A MINIMUM OF 10% WOOL	* 10% WOOL YARN CANNOT BE BLENDED OR MIXED. OTHER 90% CAN BE FROM OTHER FIBRES
NEW WOOL (FROM FLEECE ONLY): PURE, RICH, BLENDED, *WOOL MARK LISCENCE	EU 1007/2011	PURE	MUST BE MADE FROM 100% PURE NEW WOOL	* 100% VIRGINAL WOOL YARN MUST NOT HAVE BEEN PREVIOUSLY SPUN OR USED IN ANY OTHER FINISHED PRODUCT
		RICH	MUST BE MADE FROM A MINIMUM OF 50% NEW WOOL	* 50% NEW WOOL YARN CANNOT BE BLENDED OR MIXED WITH ANY OTHER YARN - OTHER 50% CAN BE FROM ANY OTHER FIBRE
		BLEND	MUST BE MADE FROM A MINIMUM OF 30% NEW WOOL	* 30% NEW WOOL YARN CAN BE BLENDED WITH 1 OTHER ANIMAL FIBRE - OTHER 70% CAN BE FROM ANY OTHER FIBRE

PTC01 – Adults Woven Tops, Bottoms and Dresses (except Denim)

PTC01 – Adults Woven Tops, Bottoms and Dresses (except Denim)					
Test Name	Test Standard	Requirements			Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments					
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends			Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1			Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N			All attached bows, buttons, pompoms, snaps etc. Test 5 of each component type and report results individually
Mass per Unit Area	BS EN 12127	-5%/+5%			
		Lightweight ≤100gms	Medium 101-199gms	Heavyweight ≥200gms	
Tensile Strength	BS EN ISO 13934 - 2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 - 2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 - 1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 - 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites. Printed Fabrics – part of the print must be present within the tested sample.
		Shade Change @ 5000 Revs Grade 3/4 for Printed Fabrics			
Residual Elongation	BS EN 14704 -1 Method A	Max 5% Unrecovered Elongation			Fabrics containing elastane only. 40N Load on Jeans, 30N Load on all other garment types

PTC01 – Adults Woven Tops, Bottoms and Dresses (except Denim)			
Test Name	Test Standard	Requirements	Comments
			Assess after 1 and 30 minutes. Test in stretch direction only
Martindale Pilling	BS EN ISO 12945 - 2	2,000 revs Grade ¾	Test after cleansing. Assess against original. Report assessment at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles Spun synthetics, wool, acrylic and their blends only
Accelerotor	AATCC 93	Weight Loss 15% Visual Assessment ‘Negligible’	Pile fabrics only 3 mins Velvet @ 2000 R.P.M. 5 Mins Corduroy or Velour @ 2000 R.P.M.
Nap Stability	BS EN ISO 12947-4: (No weight) See PM03	b) @ 4,000 revs	Raised and pile fabrics only
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Easycare / Non-Iron	AATCC 124 or ISO 7769	Easycare Grade 3.5 Non-Iron 4.0	Only required when Easy Care or Non-Iron properties are being claimed
Crease Resistant Wrinkle Recovery	AATCC 128	Grade ¾	Only required when Crease Resistant properties are being claimed
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	0 to - 3% Wovens 0 to - 5% Woven Viscose & Viscose Blends	Wash as per Care label using the number of washes prescribed by Primark.
Spirality		3%	No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.
Colour Change and Staining		Change: Staining 5 washes: 4 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	All functional internal printing on garments to be assessed for observational changes only.
APPEARANCE AFTER WASH (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM PM01 TEST			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01	Assess dimensional stability after 1 & 5 Washes. 0 to - 3% Woven. 0 to - 5% Woven Viscose & Viscose Blends	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only.
Spirality		≤ 3%	
Colour Change and Staining	Assess at 1 & 5 washes only	Change: Staining 1 & 5 washes: 4 4 Neon/Fluorescent shades	Wash as per care label.

PTC01 – Adults Woven Tops, Bottoms and Dresses (except Denim)			
Test Name	Test Standard	Requirements	Comments
		Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label <u>No colourway linking.</u> Each colourway must have a separate result.
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Washing	BS EN ISO 105 - C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Dry Cleaning	BS EN ISO 105 - D01	Change: 4 Stain: 4	Items that are Dry Clean only N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 - E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 - X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Light	BS EN ISO 105 - B02	Grade 4 @ BWS4	SHORTS ONLY
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	N/A for Silks, Wools & Elastane fibres
Colour Fastness to Non Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	N/A for Silks, Wools & Elastane fibres

PTC02 – Children’s Woven Tops, Bottoms and Dresses (except Denim)

PTC02 – Children’s Woven Tops, Bottoms and Dresses (except Denim)			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply	

PTC02 – Children’s Woven Tops, Bottoms and Dresses (except Denim)			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonide, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard	Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds	No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.	Applies to children up to 3 years

PTC02 – Children’s Woven Tops, Bottoms and Dresses (except Denim)					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATCP § 139			Applies up to age 16 years
Residual Elongation	BS EN 14704 -1 Method A	Max 5% Unrecovered Elongation			Fabrics containing elastane only. 40N Load on Jeans, 30N Load on all other garment types Assess after 1 and 30 minutes. Test in stretch direction only
Nap Stability	BS EN ISO 12947-4: (No weight) See PM03	b) @ 4,000 revs			Raised and pile fabrics only
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable			15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Easycare / Non-Iron	AATCC 124 or ISO 7769	Easycare Grade 3.5 Non-Iron 4.0			Only required when Easy Care or Non-Iron properties are being claimed
Crease Resistant Wrinkle Recovery	AATCC 128	Grade 3-4			Only required when Crease Resistant properties are being claimed
Accelerotor	AATCC 93	Weight Loss 15% Visual Assessment ‘Negligible’			Pile fabrics only 3 mins Velvet @ 2000 R.P.M. 5 Mins Corduroy or Velour @ 2000 R.P.M.
Mass per Unit Area	BS EN 12127	-5%/+5%			
		Lightweight <100gms	Medium 101-199gms	Heavyweight >200gm	
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 - 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites
		Shade Change @ 5000 Revs Grade 4			
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4			Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4			Not applicable for Silks, Wools & Elastane fibres

PTC02 – Children’s Woven Tops, Bottoms and Dresses (except Denim)			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Light	BS EN ISO 105 -B02	Grade 4 @ BWS4 Neon: 3 Pink neon: 2-3	SHORTS ONLY
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 4 Stain:3- 4	Items that are Dry Clean only N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	0 to - 3% Wovens 0 to - 5% Woven Viscose & Viscose Blends	Wash as per Care label using the number of washes prescribed by Primark.
Spirality		≤ 3%	No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.
Colour Change and Staining		Change: 5 washes: 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label.
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01	Assess dimensional stability after 1 & 5 Washes. 0 to - 3% Woven. 0 to - 5% Woven Viscose & Viscose Blends	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only.
Spirality		≤ 3%	
Colour Change and Staining		Change: Staining 1 & 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	Wash as per Care label to 5 washes. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	No colourway linking. Each colourway must have a separate result. All functional internal printing on garments to be assessed for observational changes only

PTC03 – Adults Denim Wear

PTC03 – Adults Denim Wear			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment Buttons	BS EN 17394-2	70N	
Security of Attachment Mechanically Applied Fasteners	CEN TR 17394-3	70N	
Security of Attachment	CEN TR 17394-4	Must not detach	Applicable to rivets and non-graspable components
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonide, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Mass per Unit Area	BS EN 12127	-5%/+5%	
Unrecovered Elongation	BS EN 14704 - 1 Method A	Denim product ≤ 35% stretch, maximum unrecovered after 1 minute ≤ 7% Denim product >35% stretch, maximum unrecovered after 1 minute ≤ 10%	Only products containing elastane.

PTC03 – Adults Denim Wear										
Test Name	Test Standard	Requirements								Comments
		Denim product ≤ 35% stretch, maximum unrecovered after 30 minutes ≤ 5% Denim product >35% stretch, maximum unrecovered after 30 minutes ≤ 8%								40N Load on Jeans, 30N Load on all other garment types at 5 cycles Assess after 1 and 30 minutes. Test in stretch direction only
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable								15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
		<6 oz/yd² <200 g/m²		6-7.9 oz/yd² 201-270 g/m²		8-11.5 oz/yd² 271-390 g/m²		>11.5 oz/yd² >390 g/m²		
		war p	weft	war p	weft	war p	weft	war p	weft	
Tear Strength	BS EN 13937 – 1	12N	10N	18N	15N	24N	20N	30N	24N	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Tensile Force (Strength)	BS EN ISO 13934 -2	200 N	150 N	300 N	200 N	550 N	300 N	650 N	400N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N		140N		200N		260N		For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	90N max. 6mm		110N max. 6mm		120N max. 6mm		160N max. 6mm		For Woven Fabrics Only Test in non-stretch direction only 3mm for contrast warp & weft threads
Martindale Abrasion	BS EN ISO 12947 – 2	10,000 rubs		15,000 rubs		18,000 rubs		20,000 rubs		For Woven Fabrics Only 9kPa weight
Back pocket application strength	PM07	Lightweight <100gms 150N Medium weight 101gms to 199gms 175N Heavyweight >200gms 200N								For all products containing elastane
Belt loop application strength	PM08	Lightweight <100gms 150N Medium weight 101gms to 199gms 175N Heavyweight >200gms 200N								Only at Primark Technologist Request
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)										
Dimensional Stability	PM01 Appearance after Extended Wash	-3% to +2%								Wash as per Care label using the number of washes prescribed by Primark.
Spirality		≤ 3%								
Colour Change and Staining		Change: Staining 5 washes: 3-4 2-3 23 washes: 3-4 32 washes: 3 45 washes: 3	No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.							

PTC03 – Adults Denim Wear			
Test Name	Test Standard	Requirements	Comments
	table A (part I /II/III) assessment criteria	Stay Black/Blue Claim (after all washes): Change: 4 N/A on white & cream fabrics	Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label.
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III)) ** Includes denim assessment criteria (see table A (part II))	All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE			
Dimensional Stability	Appearance after wash	3% to +2%	Denim with surface embellishment, e.g.: sequins / diamante/foil print is to be assessed at 1 & 5 washes only.
Spirality	BS EN ISO 6330: 2012	≤ 3%	
Colour Change and Staining	and table A (part 1) in PM01 Assess at 1 & 5 washes only	Change: Staining 1 wash: 3-4 2-3 5 washes: 3-4 2-3 Stay Black/Blue Claim (after all washes): Change: 4 N/A on white & cream fabrics	Wash as per Care label to 5 washes.
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label <u>No colourway linking.</u> Each colourway must have a separate result. All functional internal printing on garments to be assessed for observational changes only
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Washing (Finished Fabric stage only – garment assessed with PM01)	BS EN ISO 105 -C06	Change 3-4 Staining 2-3 Stay Black/Blue Claim: Change:4 Staining 2-3	As received
Colour Fastness to Water	BS EN ISO 105 -E01	Change 3-4 Staining 2-3 Stay Black/Blue Claim: Change:4 Staining 2-3	As received. Required for all colour ways, except white/cream fabrics

PTC03 – Adults Denim Wear			
Test Name	Test Standard	Requirements	Comments
Colour Fastness to Rubbing	BS EN ISO 105-X12	Dry: 3-4 Wet: 2 Stay Black/Blue Claim: Dry: 3-4 Wet: 2	As received. Required for all colour ways, except white/cream fabrics. only tested on indigo finishes, on the lightest part of the garment
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non- Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres

PTC04 – Children’s Denim Wear

PTC04 – Childrens Denim Wear			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment Buttons	BS EN 17394-2	90N	
Security of Attachment Mechanically Applied Fasteners	CEN TR 17394-3	90N	
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply	
Security of Attachment	CEN TR 17394-4	Must not detach	Applicable to rivets and non-graspable components
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats

PTC04 – Childrens Denim Wear						
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)						
Test Name	Test Standard	Requirements				Comments
						4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard				Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard				Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds				No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.				Applies to children up to 3 years
Children's Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATCP § 139				Applies up to age 16 years
Mass per Unit Area	BS EN 12127	-5%/+5%				
Unrecovered Elongation	BS EN 14704 -1 Method A	Denim product ≤ 35% stretch, maximum unrecovered after 1 minute ≤ 7% Denim product >35% stretch, maximum unrecovered after 1 minute ≤ 10% Denim product ≤ 35% stretch, maximum unrecovered after 30 minutes ≤ 5% Denim product >35% stretch, maximum unrecovered after 30 minutes ≤ 8%				Only products containing elastane. 40N Load on Jeans, 30N Load on all other garment types at 5 cycles Assess after 1 and 30 minutes. Test in stretch direction only
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable				15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
		<6 oz/yd ² <200 g/m ²	6-7.9 oz/yd ² 201-270 g/m ²	8-11.5 oz/yd ² 271-390 g/m ²	>11.5 oz/yd ² >390 g/m ²	

PTC04 – Childrens Denim Wear										
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)										
Test Name	Test Standard	Requirements							Comments	
		warp	weft	warp	weft	warp	weft	warp	w e f t	
Tear Strength	BS EN 13937 – 1	12N	10N	18N	15N	24N	20N	30N	24N	For Woven Fabrics Only Test in non-stretch direction only Cellulosic & Cellulose blends
Tensile Force (Strength)	BS EN ISO 13934 -2	200N	150N	300N	200N	550N	300N	650N	400N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N		140N		200N		260N		For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	90N max. 6mm		110N max. 6mm		120N max. 6mm		160N max. 6mm		For Woven Fabrics Only Test in non-stretch direction only 3mm for contrast warp & weft threads
Martindale Abrasion	BS EN ISO 12947 – 2	10,000 rubs		15,000 rubs		18,000 rubs		20,000 rubs		For Woven Fabrics Only 9kPa weight
Back pocket application strength	PM07	Lightweight <100gms 150N Medium weight 101gms to 199gms 175N Heavyweight >200gms 200N								Only at Primark Technologist Request
Belt loop application strength	PM08	Lightweight <100gms 150N Medium weight 101gms to 199gms 175N Heavyweight >200gms 200N								Only at Primark Technologist Request 100% Cotton Only
Colour Fastness to Washing (Finished Fabric stage only – garment assessed with PM01)	BS EN ISO 105 - C06	Change 3-4 Staining 2-3 Stay Black/Blue Claim: Change:4 Staining 2-3								As received
Colour Fastness to Water	BS EN ISO 105 - E01	Change 3-4 Staining 2-3 Stay Black/Blue Claim: Change:4 Staining 2-3								As received. required for all colour ways, except white/cream fabrics
Colour Fastness to Rubbing	BS EN ISO 105 - X12	Dry: 3-4 Wet: 2 Stay Black/Blue Claim: Dry: 3-4 Wet:2								As received. required for all colour ways, except white/cream fabrics. only tested on indigo finishes, on the lightest part of the garment
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4								Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4								Not applicable for Silks, Wools & Elastane fibres
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)										
Dimensional Stability		-3% to +2%								Wash as per Care label using the number of washes prescribed by Primark.
Spirality		≤ 3%								

PTC04 – Childrens Denim Wear			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Colour Change and Staining	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Change: 5 washes: 3-4 23 washes: 3-4 32 washes: 3 45 washes: 3 Stay Black/Blue Claim (after all washes): Change: 4 N/A on white & cream fabrics	No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only
Appearance		Satisfactory **Includes assessment of Print/Flock/motif applications to garment (See table A (part III)) ** Includes denim assessment criteria (see table A (part II))	
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01	3% to +2%	Denim with surface embellishment, e.g.: sequins / diamante/foil print is to be assessed at 1 & 5 washes only. Wash as per Care label to 5 washes.
Spirality		≤ 3%	
Colour Change and Staining			Change: 1 wash: 3-4 5 washes: 3-4 Stay Black/Blue Claim (after all washes): Change: 4 N/A on white & cream fabrics
Appearance	Assess at 1 & 5 washes only	Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	

PTC05 – Adults Outerwear – Woven & Knitted

PTC05 – Adults Outerwear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets.

PTC05 – Adults Outerwear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
			For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonide, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps, etc. Test 5 of each component type. Report results individually
Martindale Pilling	BS EN ISO 12945 -2	Woven 2,000 revs. Knitted 500 revs. Grade 3-4	Test after cleansing. Assess against original. Report assessment at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles Spun synthetics, wool, acrylic and their blends only
Residual Elongation	BS EN 14704 -1 Method A	Woven Max 5% Unrecovered Elongation Knitted Max 10% Unrecovered Elongation	Fabrics containing elastane only. Woven – 30N Load. Knitted – 20N Load. Assess after 1 and 30 minutes. Test in stretch direction only
Accelerotor	AATCC 93	Weight Loss 10% Visual Assessment 'Negligible'	Pile fabrics only 3 mins Velvet @ 2000 R.P.M. 5 Mins Corduroy or Velour @ 2000 R.P.M.
Fibre Shedding	PM05	Grade 4 or above	Required on all articles that have pile or fur >3mm in length.
Surface Flash	BS 4569	No Flash Not required for testing if tested for US Clothing Flammability 16. CFR 1610	Required on all articles that have pile or fur >3mm in length
Mass per Unit Area	BS EN 12127	-5%/+5%	
Nap Stability	BS EN ISO 12947-4: (No weight) See PM03	b) @ 4,000 revs.	Raised and pile fabrics only
Fibre Proof Properties	BS 15586	No more than 6 fibres penetration	Only required on items that have synthetic wadding
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330:

PTC05 – Adults Outerwear – Woven & Knitted						
Test Name	Test Standard	Requirements			Comments	
		Slight print cracking acceptable Slight loss of flocking acceptable			2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only	
		Light weight <100gms	Medium 101g-199gms	Heavy weight >200gm		
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only	
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only	
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads	
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends	
Waterproof Claims Hydrostatic Head	EN ISO 811	Waterproof >160cm/H²O Main Fabric and Taped Seams before and one after cleanse Water Repellent >100cm/H²O Main Fabric and Taped Seams before and one after cleanse			Cleanse to Care Label Only required when Waterproof properties are being claimed	
Shower Resistant Claims Spray Rating	BS EN ISO 4920 Before & after one cleanse	Grade 4-5 as received. Grade 4 After one Cleanse			Cleanse to Care Label Only required when Shower Resistant is being claimed	
Wind Resistant Claims Air Permeability	BS EN ISO 9237	Wind Resistant <20 litres/m2/sec Windproof :<0.1 litres/m2/sec			Only required when Wind Resistant is being claimed	
Breathability Claims Moisture Vapour Permeability	BS 7209 (16 hours)	WVP Index >65%			Only required when Breathable properties are being claimed	
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value			Please refer to Product claims & Product performance claims manual for updated test method	
Performance Specifications for Down and Feather Fillings for Textile Products	ASTM D-4522: 1.1: “Requirements for fillings for industry products such as wearing apparel, sleeping bags, and comforters.” Turbidity IDFB 11 Oxygen Number IDFB 7	Oxygen Number: less than 10 Turbidity: greater than 300 mm			Only required on Down and Feather filled products	
Hygiene and Cleanliness Specification	BS EN 12935: 2001	Oxygen Index result 20 to 50 - conduct Microbiological. State EN 1884 To be conducted on untreated / undyed feathers only			<20 OI	
Feather and Down Oxygen Index Number	BS EN 1162 (method)					
Hygiene and Cleanliness Specification	BS EN 12935: 2001	Only test if OI result of BS EN 1162 is >20. Testing to be stopped and failed if >50			Impurity indicator	Limit of acceptability
	EN 1884 (method)				Mesophil aerobic bacteria count	Less than 10 ⁶ CFU/g

PTC05 – Adults Outerwear – Woven & Knitted				
Test Name	Test Standard	Requirements	Comments	
Feather and Down Determination of microbiological state (Used as filler) & Marabou – undyed. Hygiene and Cleanliness Specification (cont.)		<u>To be conducted on untreated / undyed feathers only.</u>	Faecal Streptococci count	Less than 10 ² CFU/g
			Sulphite reducing clostridium count	Less than 10 ² CFU/g
			Presence of salmonella	Absent in 20g feathers
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)				
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only	
Spirality		Woven ≤ 3% Knitted ≤ 5%		
Colour Change and Staining		Change: 5 washes: 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	Staining 4 <	

PTC05 – Adults Outerwear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
		Cross Stain: 4-5 N/A on white & cream fabrics	<u>No colourway linking.</u> Each colourway must have a separate result
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain:4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain:4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 4 Stain: 3-4	Items that are Dry Clean only N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain:4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain:4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics

PTC06 – Children’s Outerwear – Woven & Knitted

PTC06 – Children’s Outerwear – Woven & Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply	
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.

PTC06 – Children's Outerwear – Woven & Knitted					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard			Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard			Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds			No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.			Applies to children up to 3 years
Children's Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATPC § 139			Applies up to age 16 years
Martindale Pilling	BS EN ISO 12945 -2	Woven 2,000 revs. Knitted 500 revs. Grade 3-4			Test after cleansing. Assess against original. Report assessment at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles Spun synthetics, wool, acrylic and their blends only
Residual Elongation	BS EN 14704 -1 Method A	Woven Max 5% Unrecovered Elongation Knitted Max 10% Unrecovered Elongation			Fabrics containing elastane only. Woven – 30N Load. Knitted – 20N Load. Assess after 1 and 30 minutes. Test in stretch direction only
Accelerotor	AATCC 93	Weight Loss 10% Visual Assessment 'Negligible'			Pile fabrics only 3 mins Velvet @ 2000 R.P.M. 5 Mins Corduroy or Velour @ 2000 R.P.M.
		Light weight <100gms	Medium 101gms to 199gms	Heavy weight >200gm	
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends

PTC06 – Children’s Outerwear – Woven & Knitted					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
Martindale Abrasion	BS EN ISO 12947 - 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites
		Shade Change @ 5000 Revs Grade 4			
Fibre Shedding	PM05	Grade 4 or above			Required on all articles that have pile or fur >3mm in length
Surface Flash	BS 4569	No Flash. Not required for testing if tested for US Clothing Flammability 16. CFR 1610			Required on all articles that have pile or fur >3mm in length
Mass per Unit Area	BS EN 12127	-5%/+5%			
Nap Stability	BS EN ISO 12947-4: (No weight) See PM03	b) @ 4,000 revs.			Raised and pile fabrics only
Fibre Proof Properties	BS 15586	No more than 6 fibres penetration			Only required on items that have synthetic wadding
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable			15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Waterproof Claims Hydrostatic Head	EN ISO 811	Waterproof >160cm/H ² O Main Fabric and Taped Seams before and one after cleanse Water Repellent >100cm/H ² O Main Fabric and Taped Seams before and one after cleanse			Cleanse to Care Label Only required when Waterproof properties are being claimed
Shower Resistant Claims Spray Rating	BS EN ISO 4920 Before & after one cleanse	Grade 4-5 as received. Grade 4 After one Cleanse			Cleanse to Care Label Only required when Shower Resistant is being claimed
Wind Resistant Claims Air Permeability	BS EN ISO 9237	Wind Resistant <20 litres/m2/sec Windproof <0.1 litres/m2/sec			Only required when Wind Resistant is being claimed
Breathability Claims Moisture Vapour Permeability	BS 7209 (16 hours)	WVP Index >65%			Only required when Breathable properties are being claimed
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value			Please refer to Product claims & Product performance claims manual for updated test method
Performance Specifications for Down and Feather Fillings for Textile Products	ASTM D-4522: 1.1: “Requirements for fillings for industry products such as wearing apparel, sleeping bags, and comforters.” Turbidity IDFB 11 Oxygen Number IDFB 7	Oxygen Number: less than 10 Turbidity: greater than 300 mm			Only required on Down and Feather filled products
Hygiene and Cleanliness Specification Feather and Down Oxygen Index Number	BS EN 12935: 2001 BS EN 1162 (method)	Oxygen Index result 20 to 50 - conduct Microbiological. State EN 1884 To be conducted on untreated / undyed feathers only			<20 OI

PTC06 – Children’s Outerwear – Woven & Knitted				
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)				
Test Name	Test Standard	Requirements	Comments	
Hygiene and Cleanliness Specification Feather and Down Determination of microbiological state (Used as filler) & Marabou - undyed	BS EN 12935: 2001 EN 1884 (method)	Only test if OI result of BS EN 1162 is >20. Testing to be stopped and failed if >50. <u>To be conducted on untreated / undyed feathers only</u>	Impurity indicator	Limit of acceptability
			Mesophil aerobic bacteria count	Less than 10 ⁶ CFU/g
			Faecal Streptococci count	Less than 10 ² CFU/g
			Sulphite reducing clostridium count	Less than 10 ² CFU/g
			Presence of salmonella	Absent in 20g feathers
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres	
Colour Fastness to Non- Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres	
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used	
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used	
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3-4	N/A on white & cream fabrics	
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)				
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.	
Spirality		Woven ≤ 3% Knitted ≤ 5%		
Colour Change and Staining		Change: 5 washes: 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	Staining 4	Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label.
Appearance		Satisfactory Pile / Brushed fabrics assessed to criteria T in Table A -Part II **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only	
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE				
Dimensional Stability		0 to - 3% Woven.		

PTC06 – Children’s Outerwear – Woven & Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	0 to - 5% Woven Viscose & Viscose Blends Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only.
Spirality		Woven ≤ 3% Knitted ≤ 5%	Wash as per care label.
Colour Change and Staining		Change: Staining 1 & 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	No colourway linking. Each colourway must have a separate result

PTC07 – Adults Jerseywear e.g. Single Jersey, Ribs, Interlock, Pique, Pointelle.

PTC07 – Adult’s Jerseywear e.g., Single Jersey, Ribs, Interlock, Pique, Pointelle etc.			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps etc. Test 5 of each component type and report results individually
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats

PTC07 – Adult's Jerseywear e.g., Single Jersey, Ribs, Interlock, Pique, Pointelle etc.			
Test Name	Test Standard	Requirements	Comments
			4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonide, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Stability to Dry Cleaning	Commercial Process	0 to - 5% 0 to -7% for Viscose & Viscose Blends	Items that are Dry Clean only
Martindale Pilling	BS EN ISO 12945 -2	500 revs Grade 3-4	Test after cleansing. Assess against original. Report assessment for knitteds at 125 cycles, with final assessment at 500 cycles Spun synthetics, wool, acrylic, and their blends only
Residual Elongation	BS EN 14704 -1 Method A	Max 10% Unrecovered Elongation	Fabrics containing elastane only. 20N Load Assess after 1 and 30 minutes. Test in stretch direction only
Mass per Unit Area	BS EN 12127	-5%/+5%	
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Single Jersey with NO Elastane Content: 5 Washes: Length -5% / +1% Width -5% / +1% 23,32, 45 Washes: Length -7% / +1% Width -7% / +1% Single Jersey with Elastane Content, Viscose / Viscose Mix, Pique, Waffle, Ribs, Interlock: 5 Washes: Length -7% / +1% Width -7% / +1% 23,32,45 Washes: Length -7% / +1%, Width -10% / +2% Pointelle: 5 & 23 Washes: Length -10% / +2%, Width -10% / +2% 32,45 Washes: Length -12% / +2% Width -12% / +2%	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label.

PTC07 – Adult’s Jerseywear e.g., Single Jersey, Ribs, Interlock, Pique, Pointelle etc.			
Test Name	Test Standard	Requirements	Comments
Spirality		5 Washes: ≤ 5% 23,32, 45 Washes: ≤ 7% Circular knits only	All Circularity products to pass 23 washes – minimum requirement.
Colour Change and Staining		Change Staining 5 washes: 4 4 23 washes: 4 32 washes: 3-4 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross stain 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	All functional internal printing on garments to be assessed for observational changes only
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	
APPEARANCE AFTER WASH (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM PM01 TEST			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Single Jersey with NO Elastane Content: 1 & 5 Washes: Length -5% / +1% Width -5% / +1% Single Jersey with Elastane Content, Viscose / Viscose Mix, Pique, Waffle, Ribs, Interlock: 1 & 5 Washes: Length -7% / +1% Width -7% / +1% Pointelle: 1 & 5 Washes: Length -10% / +2%, Width -10% / +2%	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result
Spirality		1 & 5 Washes: ≤ 5%	
Colour Change and Staining		Change Staining 1 wash: 4 4 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross stain 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	
Appearance		Satisfactory	

PTC07 – Adult's Jerseywear e.g., Single Jersey, Ribs, Interlock, Pique, Pointelle etc.			
Test Name	Test Standard	Requirements	Comments
		**appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Washing (FINISHED Fabric stage only – garment assessed with PM01)	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW® Multifibre Strip to be used.
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Light	BS EN ISO 105 -B02	Grade 4 @ BWS4 Neon: 3 Pink neon: 2-3	SHORTS ONLY
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 4 Stain: 3-4	Items that are Dry Clean only N/A on white & cream fabrics LyoW® Multifibre Strip to be used

PTC08 – Children's Jerseywear e.g. Single Jersey, Ribs, Interlock, Pique, Pointelle

PTC08 – Children's Jerseywear e.g., Single Jersey, Ribs, Interlock, Pique, Pointelle etc.			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)

PTC08 – Children’s Jerseywear e.g., Single Jersey, Ribs, Interlock, Pique, Pointelle etc.			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
	PD CEN/TS 17394-4 Security of attachment of all other components		
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonide, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard	Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds	No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.	Applies to children up to 3 years
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply	
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATCP § 139	Applies up to age 16 years
Martindale Pilling	BS EN ISO 12945 -2	500 revs Grade 3-4	Test after cleansing. Assess against original. Spun synthetics, wool, acrylic and their blends only
Residual Elongation	BS EN 14704 -1 Method A	Max 10% Unrecovered Elongation	Fabrics containing elastane only 20N Load Assess after 1 and 30 minutes Test in stretch direction only
Mass per Unit Area	BS EN 12127	-5%/+5%	
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Slight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)			

PTC08 – Children's Jerseywear e.g., Single Jersey, Ribs, Interlock, Pique, Pointelle etc.

PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)

Test Name	Test Standard	Requirements	Comments															
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Single Jersey with NO Elastane Content: 5 Washes: Length -5% / +1% Width -5% / +1% 23,32, 45 Washes: Length -7% / +1% Width -7% / +1% Single Jersey with Elastane Content, Viscose / Viscose Mix, Pique, Waffle, Ribs, Interlock: 5 Washes: Length -7% / +1% Width -7% / +1% 23,32,45 Washes: Length -7% / +1%, Width -10% / +2% Pointelle: 5 & 23 Washes: Length -10% / +2%, Width -10% / +2% 32,45 Washes: Length -12% / +2% Width -12% / +2%	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label.															
Spirality		5 & 23 Washes: ≤ 5% 32 ,45 Washes: ≤ 7% Circular knits only	All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.															
Colour Change and Staining		<table><thead><tr><th></th><th>Change</th><th>Staining</th></tr></thead><tbody><tr><td>5 washes:</td><td>4</td><td>4</td></tr><tr><td>23 washes:</td><td>4</td><td></td></tr><tr><td>32washes:</td><td>3-4</td><td></td></tr><tr><td>45 washes:</td><td>3</td><td></td></tr></tbody></table> Neon/Fluorescent shades Change: 3 Stain: 3 Cross stain 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics		Change	Staining	5 washes:	4	4	23 washes:	4		32washes:	3-4		45 washes:	3		
		Change	Staining															
5 washes:	4	4																
23 washes:	4																	
32washes:	3-4																	
45 washes:	3																	
Appearance	Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))																	
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE																		
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Single Jersey with NO Elastane Content: 1 & 5 Washes: Length -5% / +1% Width -5% / +1% Single Jersey with Elastane Content, Viscose / Viscose Mix, Pique, Waffle, Ribs, Interlock: 1 & 5 Washes: Length -7% / +1% Width -7% / +1% Pointelle: 1 & 5 Washes: Length -10% / +2%, Width -10% / +2%	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label															
Spirality		1 & 5 Washes: ≤ 5%																
Colour Change and Staining		<table><thead><tr><th></th><th>Change</th><th>Staining</th></tr></thead><tbody><tr><td>1 wash:</td><td>4</td><td>4</td></tr><tr><td>5 washes:</td><td>4</td><td>4</td></tr></tbody></table> Neon/Fluorescent shades Change: 3 Stain: 3 Cross stain 4-5 Includes print colour change and staining.		Change	Staining	1 wash:	4	4	5 washes:	4	4	No colourway linking. Each colourway must have a separate result						
	Change	Staining																
1 wash:	4	4																
5 washes:	4	4																

PTC08 – Children’s Jerseywear e.g., Single Jersey, Ribs, Interlock, Pique, Pointelle etc.			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		Includes colour change assessment of apparel trims against main fabric.	
		N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
Mandatory colourfastness tests to complete for ALL colourways / ALL product			
Colour Fastness to Washing (FINISHED Fabric stage only – garment assessed with PM01)	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Light SHORTS ONLY	BS EN ISO 105 -B02	Grade 4 @ BWS4 Neon: 3 Pink neon: 2-3	

PTC09 – Adults Knitted Leisurewear, Fleece, Loop-back, Brush-back & Polar Fleece

PTC09 – Adults Knitted Leisurewear, Fleece, Loop-back, Brush-back & Polar Fleece			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate,

PTC09 – Adults Knitted Leisurewear, Fleece, Loop-back, Brush-back & Polar Fleece			
Test Name	Test Standard	Requirements	Comments
			viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps etc. Test 5 of each component type and report results individually.
Spirality	ISO 16322-2 Fabrics ISO 16322-3 Garments	5% max	Circular knits only Follow Dimensional Stability Procedure
Martindale Pilling	BS EN ISO 12945 -2	500 revs Grade 3-4	Test after cleansing. Assess against original. Report assessment for knitteds at 125 cycles, with final assessment at 500 cycles Applicable to all leisure fabrics except true fleece fabrications (fleece finish on both right and wrong side). For brush/fleece back - test right side only
Fibre Shedding	PM05	Grade 4 or above	Applicable for all brush-back, fleece-back and pile fabrics under 10mm including those under 3mm
Mass per Unit Area	BS EN 12127	-5%/+5%	
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	length: -5% / +2% width: -7% / +2%	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only
Spirality		≤ 5%	
Colour Change and Staining		Change: 5 washes: 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	
Appearance		Satisfactory Pile / Brushed fabrics assessed to criteria T in Table A -Part II	

PTC09 – Adults Knitted Leisurewear, Fleece, Loop-back, Brush-back & Polar Fleece			
Test Name	Test Standard	Requirements	Comments
		**INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	
APPEARANCE AFTER WASH (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM PM01 TEST			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	length: -5% / +2% width: -7% / +2%	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result
Spirality		≤ 5%	
Colour Change and Staining		Change: Staining 1& 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non- Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 4 Stain: 3-4	Items that are Dry Clean only N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Light	BS EN ISO 105 -B02	Grade 4 @ BWS4 Neon: 3 Pink neon: 2-3	SHORTS ONLY

PTC10 – Children's Knitted Leisurewear, Fleece, Loop-back, Brush-back & Polar Fleece

PTC10 – Children's Knitted Leisurewear, Fleece, Loop-back, Brush-back & Polar Fleece			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided.

PTC10 – Children’s Knitted Leisurewear, Fleece, Loop-back, Brush-back & Polar Fleece			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
			The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply	
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonide, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard	Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds.	No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the	Applies to children up to 3 years

PTC10 – Children’s Knitted Leisurewear, Fleece, Loop-back, Brush-back & Polar Fleece			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.	
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATPC § 139	Applies up to age 16 years
Martindale Pilling	BS EN ISO 12945 -2	500 revs Grade 3-4	Test after cleansing. Assess against original. Report assessment for knitteds at 125 cycles, with final assessment at 500 cycles Applicable to all leisure fabrics except true fleece fabrications (fleece finish on both right and wrong side). For brush/fleece back - test right side only
Fibre Shedding	PM05	Grade 4 or above	Applicable for all brush-back, fleece-back and pile fabrics under 10mm including those under 3mm
Mass per Unit Area	BS EN 12127	-5%/+5%	
Spirality	ISO 16322-2 Fabrics ISO 16322-3 Garments	5% max	Circular knits only Follow Dimensional Stability Procedure
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value	Please refer to Product claims & Product performance claims manual for updated test method
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics

PTC10 – Children’s Knitted Leisurewear, Fleece, Loop-back, Brush-back & Polar Fleece			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Colour Fastness to Light	BS EN ISO 105 -B02	Grade 4 @ BWS4 Neon: 3 Pink neon: 2-3	SHORTS ONLY
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	length: -5% / +2% width: -7% / +2%	Wash as per Care label using the number of washes prescribed by Primark.
Spirality		≤ 5%	
Colour Change and Staining		Change: Staining 5 washes: 4 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only
Appearance		Satisfactory Pile / Brushed fabrics assessed to criteria T in Table A -Part II **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	length: -5% / +2% width: -7% / +2%	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only.
Spirality		≤ 5%	
Colour Change and Staining		Change: Staining 1& 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	No colourway linking. Each colourway must have a separate result

PTC11 – Adults Knitwear e.g. Cardigans, Jumpers

PTC11 – Adults Knitwear e.g. Cardigans, Jumpers			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps etc. Test 5 of each component type and report results individually
Martindale Pilling	BS EN ISO 12945 -2	500 revs Grade 3-4	Test after cleansing. Assess against original. Report assessment for knitteds at 125 cycles, with final assessment at 500 cycles Spun synthetics, wool, acrylic and their blends only
Chenille Pile Loss	PM06	Grade 4 or above	
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Dimensional Stability	PM01 Appearance after Extended Wash	length: -5% / +2% width: -7% / +2%	Wash as per Care label using the number of washes prescribed by Primark.
Spirality		≤ 5%	
Colour Change and Staining		Change: Staining 5 washes: 4 4	

PTC11 – Adults Knitwear e.g. Cardigans, Jumpers			
Test Name	Test Standard	Requirements	Comments
	table A (part I /II/III) assessment criteria	23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	
<u>APPEARANCE AFTER WASH (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM PM01 TEST</u>			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	length: -5% / +2% width: -7% / +2%	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result
Spirality		≤ 5%	
Colour Change and Staining		Change: Staining 1& 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 4 Stain: 3-4	Items that are Dry Clean only N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used

PTC11 – Adults Knitwear e.g. Cardigans, Jumpers			
Test Name	Test Standard	Requirements	Comments
		Change: 3 Stain: 3 Cross Stain: 4-5	
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics

PTC12 – Children’s Knitwear e.g. Cardigans, Jumpers

PTC12 – Children’s Knitwear e.g. Cardigans, Jumpers			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply	
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate,

PTC12 – Children’s Knitwear e.g. Cardigans, Jumpers			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
			alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard	Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds	No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.	Applies to children up to 3 years
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATCP § 139	Applies up to age 16 years
Martindale Pilling	BS EN ISO 12945 -2	500 revs Grade 3-4	Test after cleansing. Assess against original. Report assessment for knitted at 125 cycles, with final assessment at 500 cycles Spun synthetics, wool, acrylic and their blends only
Chenille Pile Loss	PM06	Grade 4 or above	
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non- Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 4 Stain: 3-4	Items that are Dry Clean only N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used

PTC12 – Children’s Knitwear e.g. Cardigans, Jumpers			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	length: -5% / +2% width: -7% / +2%	Wash as per Care label using the number of washes prescribed by Primark.
Spirality		≤ 5%	No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only
Colour Change and Staining		Change: 5 washes: 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE)			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	length: -5% / +2% width: -7% / +2%	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result
Spirality		≤ 5%	
Colour Change and Staining		Change: 1& 5 washes: 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	

PTC13 – Adults Swimwear & Beachwear – Woven & Knitted

PTC13 – Adults Swimwear & Beachwear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			

PTC13 – Adults Swimwear & Beachwear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, fluoro fibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps etc. Test 5 of each component type and report results individually
Spirality	ISO 16322-2 Fabrics ISO 16322-3 Garments	5% max	Circular knits only Follow Dimensional Stability Procedure
Quick Dry	AATCC 201	≤20 minutes or ≥ 0.6mL/h	
Mass per Unit Area	BS EN 12127	-5%/+5%	
Saltwater Corrosion	EN ISO 22775 Method 2	No corrosion after 24 hours	Applicable to Metallic Trims only
Heat Conductivity	PM22	Only applicable to swimwear items with metal components in contact with skin	Applicable to Metallic Trims only
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Residual Elongation	BS EN 14704- 1: 2005 Method A	Weft knitted fabrics. 10% Max Unrecovered Elongation after 1 & 30 minutes	< 5% elastane 15N load 5% - 11% elastane 20N load >11% elastane 25N load Assess after 1 & 30 minutes. Test in stretch direction only

PTC13 – Adults Swimwear & Beachwear – Woven & Knitted					
Test Name	Test Standard	Requirements			Comments
		Warp knitted fabrics only. 5% Max Unrecovered Elongation after 1 & 30 minutes			< 5% elastane 15N load 5% - 11% elastane 20N load >11% elastane 25N load Assess after 1 & 30 minutes. Test in stretch direction only
		Woven fabrics 5% Max Unrecovered Elongation after 1 & 30 minutes			30N Load Assess after 1 & 30 minutes. Test in stretch direction only
		Light weight <100gms	Medium 101gms to 199gms	Heavy weight >200gm	
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 - 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites
		Shade Change @ 5000 Revs Grade 4			
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends			Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.
Spirality		Woven ≤ 3% Knitted ≤ 5%			Machine wash product:
Colour Change and Staining		Change: Staining 5 washes: 4 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics			- care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))			
APPEARANCE AFTER WASH (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM PM01 TEST					
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012	Woven 0 to - 3%			

PTC13 – Adults Swimwear & Beachwear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
	and table A (part 1) in PM01 Assess at 1 & 5 washes only	0 to - 5% for Viscose & Viscose Blends Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label <u>No colourway linking.</u> Each colourway must have a separate result
Spirality		Woven ≤ 3% Knitted ≤ 5%	
Colour Change and Staining		Change: 1& 5 washes: 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non- Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Light	BS EN ISO 105 -B02	Grade 4 @ BWS4 Neon: 3 Pink neon: 2-3	
Colour Fastness to Chlorinated Water	BS EN ISO 105 : E03	Change: 4 Neon/Fluorescent shades Change: 3 Pink Neon Change: 2-3	50mg/l Swimwear 20mg/l Beachwear
Colour Fastness to Sea Water	BS EN ISO 105 : E02	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Pink Neon: Change: 2-3 Stain: 2-3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Phenolic Yellowing	BS EN ISO X18	Change Grade 4	Applicable to white, pale & pastel shades Applicable to fabrics and foam cups When testing bras or cupped swimwear - test cups as a composite. If sample fails, test individual components

PTC14 – Children’s Swimwear & Beachwear – Woven & Knitted

PTC14 – Children’s Swimwear & Beachwear – Woven & Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply	
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.

PTC14 – Children’s Swimwear & Beachwear – Woven & Knitted				
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)				
Test Name	Test Standard	Requirements		
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard		
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard		
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds		
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.		
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATCP § 139		
Spirality	ISO 16322-2 Fabrics ISO 16322-3 Garments	5% max		
Mass per Unit Area	BS EN 12127	-5%/+5%		
Saltwater Corrosion	EN ISO 22775 Method 2	No corrosion after 24 hours		
Heat Conductivity	PM22	Only applicable to swimwear items with metal components in contact with skin		
Residual Elongation	BS EN 14704- 1: 2005 Method A	Weft knitted fabrics. 10% Max Unrecovered Elongation after 1 & 30 minutes		
		Warp knitted fabrics only. 5% Max Unrecovered Elongation after 1 & 30 minutes		
		Woven fabrics 5% Max Unrecovered Elongation after 1 & 30 minutes		
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable		
		Light weight <100gms	Medium 101gms to 199gms	Heavy weight >200gm

PTC14 – Children’s Swimwear & Beachwear – Woven & Knitted					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 – 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 – 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites.
		Shade Change @ 5000 Revs Grade 4			
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4			Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4			Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5			A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5			N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3			N/A on white & cream fabrics
Colour Fastness to Light	BS EN ISO 105 -B02	Grade 4 @ BWS4 Neon: 3 Pink neon: 2-3			
Colour Fastness to Chlorinated Water	BS EN ISO 105: E03	Change: 4 Neon/Fluorescent shades Change: 3 Pink Neon Change: 2-3			50mg/l Swimwear 20mg/l Beachwear
Colour Fastness to Sea Water	BS EN ISO 105: E02	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Pink Neon: Change: 2-3 Stain: 2-3 Cross Stain: 4-5			N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Phenolic Yellowing	BS EN ISO X18	Change Grade 4			Applicable to white, pale & pastel shades Applicable to fabrics and foam cups When testing bras or cupped swimwear - test cups as a composite. If sample fails, test individual components
Solar UV Protective Properties – Method of Tests for Apparel Fabrics & Classification and Marking of Apparel	EN13758-1 EN13758-2	Primark insist fabrics must show a UPF of 40 or above to be labelled with sun protection promotions			Only required when Sun Protection properties are being claimed
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)					
Dimensional Stability	PM01 Appearance after Extended Wash	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted			Wash as per Care label using the number of washes prescribed by Primark.

PTC14 – Children’s Swimwear & Beachwear – Woven & Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
	table A (part I /II/III) assessment criteria	0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.
Spirality		Woven ≤ 3% Knitted ≤ 5%	
Colour Change and Staining		Change: Staining 5 washes: 4 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE)			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only.
Spirality		Woven ≤ 3% Knitted ≤ 5%	Wash as per care label.
Colour Change and Staining		Change: Staining 1& 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label <u>No colourway linking.</u> Each colourway must have a separate result
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	

PTC15 – Adults Performance wear – Woven & Knitted

PTC15 – Adults Performance wear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps etc. Test 5 of each component type and report results individually
Spirality	ISO 16322-2 Fabrics ISO 16322-3 Garments	5% max	Circular knits only Follow Dimensional Stability Procedure
Quick Dry	AATCC 201	≤20 minutes or ≥ 0.6mL/h	
Martindale Pilling	BS EN ISO 12945 -2	Woven 2,000 revs. Knitted 500 revs. Grade 3-4	Test after cleansing. Assess against original. Report assessment for wovens at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles Report assessment for knitteds at 125 cycles, with final assessment at 500 cycles Spun synthetics, wool, acrylic and their blends only
Residual Elongation	BS EN 14704 -1 Method A	Woven Max 5% Unrecovered Elongation Knitted Max 10% Unrecovered Elongation	Fabrics containing elastane only. Woven – 30N Load. Knitted – 20N Load. Assess after 1 and 30 minutes. Test in stretch direction only

PTC15 – Adults Performance wear – Woven & Knitted					
Test Name	Test Standard	Requirements			Comments
Bursting strength	BS EN ISO 13938-2	300kPa			For Meshes only
Mass per Unit Area	BS EN 12127	-5%/+5%			
		Lightweight ≤100gms	Medium 101-199gms	Heavyweight t ≥200gms	
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 - 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites
		Shade Change @ 5000 Revs Grade 4			
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable			15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Reflectivity Test High Visibility Clothing - Test Methods and Requirements	BS EN ISO 20471	Compliance to the Standard			Applicable to products with retro reflective tape
Waterproof Claims Hydrostatic Head	EN ISO 811	Waterproof >160cm/H2O Main Fabric and Taped Seams before and one after cleanse Water Repellent >100cm/H2O Main Fabric and Taped Seams before and one after cleanse			Cleanse to Care Label Only required when Waterproof properties are being claimed
Shower Resistant Claims Spray Rating	BS EN ISO 4920 Before & after one cleanse	Grade 4-5 as received. Grade 4 After one Cleanse			Cleanse to Care Label Only required when Shower Resistant is being claimed
Wind Resistant Claims Air Permeability	BS EN ISO 9237	Wind Resistant <20 litres/m2/sec Windproof :<0.1 litres/m2/sec			Only required when Wind Resistant is being claimed
Breathability Claims Moisture Vapour Permeability	BS 7209 (16 hours)	WVP Index >65%			Only required when Breathable properties are being claimed
Water Vapor Transmission of Materials	ASTM E96-14 Procedure B - Water Method Test original state only	Greater or equal to 500 g / m ² / 24 hours			If claimed breathability or similar
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value			Please refer to Product claims & Product performance claims manual for updated test method
Vertical wicking of textiles	AATCC 197-11	Minimum 2.5 inches per 10 minutes			If Claimed "Wicks Away Moisture" or Similar
Absorbency of textiles	AATCC 79-10	Maximum 7 seconds			Moisture Management test

PTC15 – Adults Performance wear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
	Test both original and after 20 launderings		
Anti-Bacterial Claims Antibacterial Activity Assessment of Textile Materials: Parallel Streak Method	AATCC 147	No Bacterial Growth	Test Bacteria: Staphylococcus Aureus (ATCC6538) Test face side of sample as received
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.
Spirality		Woven ≤ 3% Knitted ≤ 5%	
Colour Change and Staining		Change: 5 washes: 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	
APPEARANCE AFTER WASH (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM PM01 TEST			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only.
Spirality		Woven ≤ 3% Knitted ≤ 5%	Wash as per care label.
Colour Change and Staining		Change: 1& 5 washes: 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining.	Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label

PTC15 – Adults Performance wear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
Appearance		Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	No colourway linking. Each colourway must have a separate result
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Perspiration	BS EN ISO 105 -E04	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Light	BS EN ISO 105 -B02	Grade 4 @ BWS4 Neon: 3 Pink neon: 2-3	

PTC15A – Children's Performance wear – Woven & Knitted

PTC15A – Childrens Performance wear – Woven & Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)

PTC15A – Childrens Performance wear – Woven & Knitted						
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)						
Test Name	Test Standard	Requirements			Comments	
	PD CEN/TS 17394-4 Security of attachment of all other components					
Safety of children's clothing. Cords & drawstrings on children's clothing	EN 14682	Must Comply				
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1			Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonide, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.	
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard			Applies to children up to 8 years	
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard			Applies to children up to 8 years	
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds			No Small Parts - up to 3 years. No sharp points or edges - all ages.	
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.			Applies to children up to 3 years	
Children's Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATPC § 139			Applies up to age 16 years	
Spirality	ISO 16322-2 Fabrics ISO 16322-3 Garments	5% max			Circular knits only Follow Dimensional Stability Procedure	
		Lightweig ht ≤100gms	Medium 101- 199gms	Heavywei ght ≥200gms		

PTC15A – Childrens Performance wear – Woven & Knitted					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 - 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites
		Shade Change @ 5000 Revs Grade 4			
Martindale Pilling	BS EN ISO 12945 -2	Woven 2,000 revs. Knitted 500 revs. Grade 3-4			Test after cleansing. Assess against original. Report assessment for wovens at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles Report assessment for knitteds at 125 cycles, with final assessment at 500 cycles Spun synthetics, wool, acrylic and their blends only
Residual Elongation	BS EN 14704 -1 Method A	Woven Max 5% Unrecovered Elongation Knitted Max 10% Unrecovered Elongation			Fabrics containing elastane only. Woven – 30N Load. Knitted – 20N Load. Assess after 1 and 30 minutes. Test in stretch direction only
Bursting strength	BS EN ISO 13938-2	300kPa			For Meshes only
Mass per Unit Area	BS EN 12127	-5%/+5%			
Reflectivity Test High Visibility Clothing - Test Methods and Requirements	BS EN ISO 20471	Compliance to the Standard			Applicable to products with retro reflective tape
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable			15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Waterproof Claims Hydrostatic Head	EN ISO 811	Waterproof >160cm/H2O Main Fabric and Taped Seams before and one after cleanse Water Repellent >100cm/H2O Main Fabric and Taped Seams before and one after cleanse			Cleanse to Care Label Only required when Waterproof properties are being claimed

PTC15A – Childrens Performance wear – Woven & Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Shower Resistant Claims Spray Rating	BS EN ISO 4920 Before & after one cleanse	Grade 4-5 as received. Grade 4 After one Cleanse	Cleanse to Care Label Only required when Shower Resistant is being claimed
Wind Resistant Claims Air Permeability	BS EN ISO 9237	Wind Resistant <20 litres/m2/sec Windproof :<0.1 litres/m2/sec	Only required when Wind Resistant is being claimed
Breathability Claims Moisture Vapour Permeability	BS 7209 (16 hours)	WVP Index >65%	Only required when Breathable properties are being claimed
Water Vapor Transmission of Materials	ASTM E96-14 Procedure B - Water Method Test original state only	Greater or equal to 500 g / m ² / 24 hours	If claimed breathability or similar
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value	Please refer to Product claims & Product performance claims manual for updated test method
Vertical wicking of textiles	AATCC 197-11	Minimum 2.5 inches per 10 minutes	If Claimed "Wicks Away Moisture" or Similar
Absorbency of textiles	AATCC 79-10 Test both original and after 20 launderings	Maximum 7 seconds	Moisture Management test
Anti-Bacterial Claims Antibacterial Activity Assessment of Textile Materials: Parallel Streak Method	AATCC 147	No Bacterial Growth	Test Bacteria: Staphylococcus Aureus (ATCC6538) Test face side of sample as received
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non- Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Perspiration	BS EN ISO 105 -E04	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Light	BS EN ISO 105 -B02	Grade 4 @ BWS4 Neon: 3 Pink neon: 2-3	
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.
Spirality		Woven ≤ 3% Knitted ≤ 5%	Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling).
Colour Change and Staining		Change: 5 washes: 4 23 washes: 3-4 32 washes: 3 Staining 4	

PTC15A – Childrens Performance wear – Woven & Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE)			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label.
Spirality		Woven ≤ 3% Knitted ≤ 5%	
Colour Change and Staining		Change: Staining 1& 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	

PTC16 – Adults Nightwear and Loungewear – Woven & Knitted

PTC16 – Adults Nightwear and Loungewear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets.

PTC16 – Adults Nightwear and Loungewear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
			For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps etc. Test 5 of each component type and report results individually
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Martindale Pilling	BS EN ISO 12945 -2	Woven 2,000 revs. Knitted 500 revs. Grade 3-4	Test after cleansing. Assess against original. Report assessment for wovens at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles Report assessment for knitted at 125 cycles, with final assessment at 500 cycles. Spun synthetics, wool, acrylic and their blends only
Residual Elongation	BS EN 14704 -1 Method A	Woven Max 5% Unrecovered Elongation	Fabrics containing elastane only. Woven – 30N Load.
		Knitted Max 10% Unrecovered Elongation	Knitted – 20N Load. Test in stretch direction only
		<u>Seam Free</u> 20% Max Unrecovered elongation	Extension load@ 15N Assess after 30 minutes only
		<u>Lace/Mesh</u> 5% Max Unrecovered elongation	Extension load@ 15N Assess after 30 minutes only
Mass per Unit Area	BS EN 12127	-5%/+5%	

PTC16 – Adults Nightwear and Loungewear – Woven & Knitted					
Test Name	Test Standard	Requirements			Comments
		Lightweight ≤100gms	Medium 101-199gms	Heavyweight ≥200gms	
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 – 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 – 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites Need to look at the Martindale Abrasion test on lightweight fabrics i.e. silk mix - not a realistic test, lightweight fabrics will never pass 10k revs. Spoke to UL and its not industry standard to do it on silk mixes, working on additional information
		Shade Change @ 5000 Revs Grade 4			
Fibre Shedding	PM05	Grade 4 or above			Only applicable for brushed back and pile fabrics under 10mm
Bursting strength	BS EN ISO 13938-2	Lace 175kPa			For Lace & Mesh only
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable			15 minutes @40°C Dry as per Care Label **Only required on Print/Motif/Flock product being tested to BS EN ISO 6330:2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Slip Resistance	TM 144	Coefficient of Friction – 0.3 min			Applicable to garments with a sole / foot covering. Test using Calibrated Clay Tile on Dry & Wet Surface
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Dimensional Stability		Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Follow Jersey Test Package PTC07 for all Jersey Nightwear All other Knitted fabrics 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends			Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests Each colourway must have a separate PM01 test. Multipack product testing requirements:

PTC16 – Adults Nightwear and Loungewear – Woven & Knitted																		
Test Name	Test Standard	Requirements	Comments															
Spirality	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven ≤ 3% Knitted ≤ 5%	every colourway pack/option must have a supporting PM01 test. a minimum of one product per colourway pack to be tested. A pack of Variable colour (and/or construction) = test darkest/most saturated colour option in the pack A pack of variable composition = test darkest/most saturated colour option in the pack and in addition the nightwear made from the highest variance in composition Discuss with the relevant QA on additional guidance if required. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement.															
Colour Change and Staining -		Follow Jersey Test Package PTC07 for all Jersey Nightwear For Woven fabrics and All other knitted fabrics <table><tr><td></td><td>Change</td><td>Staining</td></tr><tr><td>5 washes:</td><td>3- 4</td><td>4</td></tr><tr><td>23 washes:</td><td>3-4</td><td></td></tr><tr><td>32 washes:</td><td>3-4</td><td></td></tr><tr><td>45 washes:</td><td>3 -4</td><td></td></tr></table> Neon/Fluorescent shades Change: 3 Stain: 3 Cross stain 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric i.e., DTM elastic, binding, lace, bows etc if externally visible when worn. Does not include internal trims not visible when worn. N/A on white & cream fabrics			Change	Staining	5 washes:	3- 4	4	23 washes:	3-4		32 washes:	3-4		45 washes:	3 -4	
		Change		Staining														
5 washes:	3- 4	4																
23 washes:	3-4																	
32 washes:	3-4																	
45 washes:	3 -4																	
Appearance	Satisfactory Brushed and pile fabrics only: Pilling or fuzzing of surface fibres <table><tr><td>5, & 23 washes</td><td>3-4</td></tr><tr><td>32 & 45 washes</td><td>3</td></tr></table> Pile / Brushed fabrics assessed to criteria T in Table A -Part II **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	5, & 23 washes	3-4	32 & 45 washes	3	All functional internal printing on garments to be assessed for observational changes only												
5, & 23 washes	3-4																	
32 & 45 washes	3																	
APPEARANCE AFTER WASH (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM PM01 TEST																		
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Assess dimensional stability after 1 & 5 Washes. Woven 0 to -3% 0 to -5% for Viscose & Viscose Blends Knitted fabric: Single Jersey with NO Elastane Content: 1 & 5 Washes: Length -5% / +1% Width -5% / +1% Single Jersey with Elastane Content, Viscose / Viscose Mix, Pique, Waffle, Ribs, Interlock: 1 & 5 Washes: Length -7% / +1% Width -7% / +1% Pointelle:	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C															

PTC16 – Adults Nightwear and Loungewear – Woven & Knitted			
Test Name	Test Standard	Requirements	Comments
		1 & 5 Washes: Length -10% / +2%, Width -10% / +2%	test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result
Spirality		ALL Other Knitted fabrics: 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends Woven ≤ 3% Knitted ≤ 5%	
Colour Change and Staining		Change: Staining 1& 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
Colour Fastness to Washing All other nightwear fabrics e.g., Woven. (This test applies at FINISHED Fabric stage only . Garment assessed with PM01.)	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used.
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3-4	N/A on white & cream fabrics
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colourfastness to Perspiration	BS EN ISO 105 -E04	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics
Colourfastness to Perspiration	AATCC15 : 2013	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	At Technologist Request
Colourfastness to Hot Pressing	BS EN ISO 105-X11	Dry – Grade 4 Damp – Grade 4 Wet – Grade 4 Results reviewed at 100/150/200 degrees	Not applicable to White/Cream Fabrics. Applicable on all fabric bright/dark colourways. Applicable on all printed fabrics
Colourfastness to PVC Migration	BS EN ISO 105-X10	Dry 3-4	Applicable on all fabric bright/dark colourways. Applicable on all printed fabrics.

PTC17 – Children’s Nightwear – Woven and Knitted

PTC17 – Children’s Nightwear – Woven and Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants’ clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components 16. CFR 1610 Contains Requirements and Test Method	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. 5. Infant garment sized nine months or smaller (if meets the relevant criteria as per US Children Sleepwear Regulation). If contain Vinyl Plastic Film, then must comply to 16 CRF 1611. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose,

PTC17 – Children’s Nightwear – Woven and Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
			chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
UK Nightwear Safety Regulations	1985 SI No 2043 BS 5722: 1984 BS 5438: 1976	Compliance	Nightdresses, nightshirts and dressing gowns to be of low flammability to BS 5722 All nightwear and cotton terry bathrobes shall be properly labelled as follows: <u>Pyjamas:</u> KEEP AWAY FROM FIRE Night Dresses, Dressing Gowns Bath Robes (not cotton terry towelling) and similar garments: KEEP AWAY FROM FIRE LOW FLAMMABILITY TO BS 5722 Bath Robes made of cotton terry towelling only: KEEP AWAY FROM FIRE
Burning behaviour of children’s nightwear	BS EN 14878: 2007	Pyjamas Class B minimum Bathrobes Class A	Applicable for children’s nightwear garments not covered by BS 5722
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply	
US Children’s Sleepwear Flammability	CFR 1615 Covers US Sizes 0 to 6X The Regulation Contains the test method and requirements and dimensions regarding Tightness of Fit The US CPSC Guide for Laboratory Testing of nightwear is also a key guide	Average char length: The average char length of five specimens shall not exceed 17.8 cm. (7.0 in.) Full-specimen burn: No individual specimen shall have a char length of 25.4±0.5 cm. (10±0.2 in.). The test criteria shall be used in conjunction with fabric and garment sampling plan listed in standard. Tightness of fit is a key issue. Tight Fit across the size ranges is delineated in CFR 1615/CFR 1616. No tolerance is allowed for measurement at specified points of measurement. Refer to CPSC standards for Point of Measurements (POM). If Tight Fit various labelling requirements and CFR 1610 applies where applicable re fibre type etc. For all tight -fit stylings, no component or trim can extend more than ¼” from the point of attachment. Lettuce edging also cannot extend more than ¼” when laid flat. All types of sleepwear require mandatory labelling on the product, hang tags and on packaging based on the style sleepwear it is classifies as. Please refer to US Children Sleepwear Regulation for	Supplier must submit appropriate number of samples for each stage of testing in timely manner throughout the manufacturing process to ensure compliance to US Children Sleepwear Regulation. There are three stages of testing requirements: 1) Fabric Production Unit (FPU)- An FPU is defined as a unit of fabric up to or equivalent to 5000 linear yds of fabric for normal sampling. Test all initial FPUs in before and after 50 laundering cycles. For subsequent FPUs, test before and after 50 laundering cycles for FR treatment fabric and test only before wash for non-FR treatment fabric if the first FPU passes before and after 50 laundering cycles. 2) Prototype testing seams/trims:- In this stage, all type of seams and decorative trims used for garment should be tested according to the standard. This provides acceptance for use in the final garment. If FPU is accepted both of before and after laundering test, only perform before wash test for non-FR treatment seam and trims.

PTC17 – Children’s Nightwear – Woven and Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		clear details of labeling based on the style sleepwear.	3) Garment Production Units(GPU)- A GPU is defined as a quantity of finished garments up to 500 dozen that maintain a specific identity throughout the unit excluding differences in size, trim, findings, color, and print patterns. Testing to be performed on randomly selected finished product from the production lines for each designated GPU unit. Test Laboratories have to return tested and residue samples to the supplier. Supplier should keep "recordkeeping" samples according to the regulations.
US Children’s Sleepwear Flammability	CFR 1616 Covers US sizes 7 to 14 The Regulation Contains the test method and requirements and dimensions regarding Tightness of Fit	See the above	See the above
US Children’s Sleepwear Flammability	CFR 1615 / 1616 Laundering Test For Chemically treated items	Flammability test should be carried out on finished items (as produced or after one washing & drying) and after they have been washed and dried 50 times according to AATCC Test Method 124 - 1996 at 140°F (60°C) with 8 lb loading. Items which do not withstand 50 washes shall be tested at the end of their useful service life. Items which are not susceptible to being laundered and labelled “Dry clean only” shall be dry cleaned by a procedure acceptable by CPSC	Required legal testing overrides the Primark Extended washing up to 45 washes and must be tested to 50 washes or end of useful life
US Clothing Flammability for infant garment	16 CFR 1615.1(c)(3) 16 CFR 1610 16 CFR 1611 (if contain Vinyl film) as applicable	Meet the standard. Visible/ readable size label is required.	Infant garment means a garment which: (1) Is sized nine months or smaller. (2) If a one-piece garment, does not exceed 64.8 centimeters (25.75 inches) in length; if a two-piece garment, has no piece exceeding 40 centimeters (15.75 inches) in length. (3) Complies with all applicable requirements of the Standard for the Flammability of Clothing Textiles (16 CFR part 1610) and the Standard for the Flammability of Vinyl Plastic Film (16 CFR part 1611); and (4) Bears a label stating the size of the garment, expressed in terms of months of age.
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years

PTC17 – Children’s Nightwear – Woven and Knitted					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard			Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 – 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds			No Small Parts – up to 3 years. No sharp points or edges – all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.			Applies to children up to 3 years
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply			
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATCP § 139			Applies up to age 16 years
Martindale Pilling	BS EN ISO 12945 -2	Woven 2,000 revs. Knitted 500 revs. Grade 3-4			Test after cleansing. Assess against original. Report assessment for wovens at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles Report assessment for knitteds at 125 cycles, with final assessment at 500 cycles Spun synthetics, wool, acrylic and their blends only
Residual Elongation	BS EN 14704 -1 Method A	Woven Max 5% Unrecovered Elongation Knitted Max 10% Unrecovered Elongation			Fabrics containing elastane only. Woven – 30N Load. Knitted – 20N Load. Test in stretch direction only
		<u>Seam Free</u> 20% Max Unrecovered elongation			Extension load@ 15N Assess after 30 minutes only
		<u>Lace/Mesh</u> 5% Max Unrecovered elongation			Extension load@ 15N Assess after 30 minutes only
Mass per Unit Area	BS EN 12127	-5%/+5%			
		Lightweight ≤100gms	Medium 101-199gms	Heavyweight ≥200gms	
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 – 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 – 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites.

PTC17 – Children’s Nightwear – Woven and Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		Shade Change @ 5000 Revs Grade 4	
Fibre Shedding	PM05	Grade 4 or above	Only applicable for brushed back and pile fabrics under 10mm
Bursting strength	BS EN ISO 13938-2	Lace 175kPa	For Lace & Mesh only
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label **Only required on Print/Motif/Flock product being tested to BS EN ISO 6330:2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Slip Resistance	TM 144	Coefficient of Friction – 0.3 min	Applicable to garments with a sole / foot covering. Test using Calibrated Clay Tile on Dry & Wet Surface.
Colour Fastness to Washing (This test applies at FINISHED Fabric stage only . Garment assessed with PM01.)	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used.
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	AATCC 107	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	At Technologist Request N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3-4	N/A on white & cream fabrics
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colourfastness to Perspiration	BS EN ISO 105 -E04	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used.
Colourfastness to Perspiration	AATCC15 : 2013	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	At Technologist request LyoW ®Multifibre Strip to be used
Colourfastness to Hot Pressing	BS EN ISO 105-X11	Dry – Grade 4 Fabric and Cotton Lawn Damp – Grade 4 Wet – Grade 4 Results reviewed at 100/150/200 degrees	Not applicable to White/Cream Fabrics. Applicable on all fabric bright/dark colourways. Applicable on all printed fabrics
Colourfastness to PVC Migration	BS EN ISO 105-X10	Dry 3 - 4	Applicable on all fabric bright/dark colourways. Applicable on all printed fabrics.
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)			

PTC17 – Children’s Nightwear – Woven and Knitted																		
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)																		
Test Name	Test Standard	Requirements	Comments															
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Follow Jersey Test Package PTC08 for all Jersey Nightwear All other Knitted fabrics 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests Each colourway must have a separate PM01 test. Multipack product testing requirements: every colourway pack/option must have a supporting PM01 test. a minimum of one product per colourway pack to be tested.															
Spirality		Woven ≤ 3% Knitted ≤ 5%																
Colour Change and Staining -		Follow Jersey Test Package PTC08 for all Jersey Nightwear For Woven fabrics and All other knitted fabrics <table><tr><td></td><td>Change</td><td>Staining</td></tr><tr><td>5 washes:</td><td>3- 4</td><td>4</td></tr><tr><td>23 washes:</td><td>3-4</td><td></td></tr><tr><td>32 washes:</td><td>3-4</td><td></td></tr><tr><td>45 washes:</td><td>3 -4</td><td></td></tr></table> Neon/Fluorescent shades Change: 3 Stain: 3 Cross stain 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric i.e., DTM elastic, binding, lace, bows etc if externally visible when worn. Does not include internal trims not visible when worn. N/A on white & cream fabrics		Change	Staining	5 washes:	3- 4	4	23 washes:	3-4		32 washes:	3-4		45 washes:	3 -4		A pack of Variable colour (and/or construction) = test darkest/most saturated colour option in the pack A pack of variable composition = test darkest/most saturated colour option in the pack and in addition the nightwear made from the highest variance in composition Discuss with the relevant QA on additional guidance if required. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label.
		Change	Staining															
5 washes:	3- 4	4																
23 washes:	3-4																	
32 washes:	3-4																	
45 washes:	3 -4																	
Appearance	Satisfactory Brushed and pile fabrics only: Pilling or fuzzing of surface fibres 5, & 23 washes 3-4 32 & 45 washes 3 Pile / Brushed fabrics assessed to criteria T in Table A -Part II **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only																
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE)																		
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012	Assess dimensional stability after 1 & 5 Washes. Woven 0 to -3% 0 to -5% for Viscose & Viscose Blends Knitted fabric:	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only.															

PTC17 – Children’s Nightwear – Woven and Knitted			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
	and table A (part 1) in PM01 Assess at 1 & 5 washes only	Single Jersey with NO Elastane Content: 1 & 5 Washes: Length -5% / +1% Width -5% / +1% Single Jersey with Elastane Content, Viscose / Viscose Mix, Pique, Waffle, Ribs, Interlock: 1 & 5 Washes: Length -7% / +1% Width -7% / +1% Pointelle: 1 & 5 Washes: Length -10% / +2%, Width -10% / +2% ALL Other Knitted fabrics: 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result
Spirality		Woven ≤ 3% Knitted ≤ 5%	
Colour Change and Staining		Change: Staining 1& 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	

PTC18A – Adults Underwear e.g., briefs, trunks, underwear vests and cami’s, underwear leggings

PTC18a – Adults Underwear e.g., briefs, trunks, underwear vests and Cami’s, underwear leggings			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content.

PTC18a – Adults Underwear e.g., briefs, trunks, underwear vests and Cami's, underwear leggings			
Test Name	Test Standard	Requirements	Comments
			The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps etc. Test 5 of each component type and report results individually
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Martindale Pilling	BS EN ISO 12945 - 2	Woven 2,000 revs. Knitted 500 revs. Grade 3-4	Test after cleansing. Assess against original. Report assessment for wovens at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles Report assessment for knitteds at 125 cycles, with final assessment at 500 cycles Spun synthetics, wool, acrylic and their blends only
Residual Elongation	BS EN 14704-1 Method A OR ISO 20932-1 Method A	WEFT Knitted fabrics EXCL. SHAPEWEAR & PERFORMANCE WEAR	
		<u>Jersey Fabrics (Single jersey & Rib)</u> 10% Max Unrecovered elongation (still under review)	<u>Fabrics containing elastane only.</u> Extension load <5% elastane 15N load 5-11% elastane 20N load >11% elastane 25N load
		<u>Seam Free</u> 20% Max Unrecovered elongation	Extension load@ 15N Assess after 30 minutes only
		WARP Knitted fabrics EXCL. SHAPEWEAR & PERFORMANCE WEAR	
		<u>Lace/Mesh</u> 5% Max Unrecovered elongation	Extension load@ 15N Assess after 30 minutes only
Residual Elongation SHAPEWEAR	BS EN 14704-1 Method A OR ISO 20932-1 Method A If the control level is created using multiple fabrics	<u>SHAPEWEAR</u> <u>Light Control</u> 5% Max Unrecovered elongation 40% Modulus @150-200g <u>Medium Control</u>	Extension @36N load Extension @36N load

PTC18a – Adults Underwear e.g., briefs, trunks, underwear vests and Cami’s, underwear leggings					
Test Name	Test Standard	Requirements			Comments
	and layers, then the fabric must be tested as they are used in the garment.	5% Max Unrecovered elongation 40% Modulus @250-500g <u>Firm Control</u> 5% Max Unrecovered elongation 40% Modulus @500-750g			Extension @36N load
Mass per Unit Area	BS EN 12127	-5%/+5%			
		Lightweight ≤100gms	Medium 101-199gms	Heavyweigh t ≥200gms	
Tensile Strength	BS EN ISO 13934 - 2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 - 2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 - 1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Martindale Abrasion	BS EN ISO 12947 – 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites
		Shade Change @ 5000 Revs Grade 4			
Tear Strength	BS EN 13937 – 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Bursting strength	BS EN ISO 13938- 2	175kPa			For Lace & Mesh only
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable			15 minutes @40°C Dry as per Care Label Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value			Please refer to Product claims & Product performance claims manual for updated test method
Elastic extension and Modulus test	PM23	Woven and knitted elastics must meet the required performance outlined under the PM23 test method			
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					

PTC18a – Adults Underwear e.g., briefs, trunks, underwear vests and Cami’s, underwear leggings																
Test Name	Test Standard	Requirements	Comments													
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Follow Jersey Test Package PTC07 for all Jersey Nightwear All other Knitted fabrics 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests Each colourway must have a separate PM01 test. Multipack product testing requirements: every colourway pack/option must have a supporting PM01 test. a minimum of one product per colourway pack to be tested.													
Spirality		Woven ≤ 3% Knitted ≤ 5%	A pack of Variable colour (and/or construction) = test darkest/most saturated colour option in the pack A pack of variable composition = test darkest/most saturated colour option in the pack and in addition the nightwear made from the highest variance in composition Discuss with the relevant QA on additional guidance if required. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.													
Colour change and staining		Follow Jersey Test Package PTC07 for all Jersey Nightwear Additional standard for Rib Underwear only: Rib Underwear: 5 Washes: Length -10% / +2%, Width -10% / +2% 23,32, 45 Washes: Length -10% / +2% Width -10% / +2% For Woven fabrics and All other knitted fabrics <table><tr><td></td><td>Change</td><td>Staining</td></tr><tr><td>5 washes:</td><td>3- 4</td><td>4</td></tr><tr><td>23 washes:</td><td>3-4</td><td></td></tr><tr><td>32 washes:</td><td>3-4</td><td></td></tr><tr><td>45 washes:</td><td>3 -4</td><td></td></tr></table> Neon/Fluorescent shades Change: 3 Stain: 3 Cross stain 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric i.e., DTM elastic, binding, lace, bows etc if externally visible when worn. Does not include internal trims not visible when worn. N/A on white & cream fabrics			Change	Staining	5 washes:	3- 4	4	23 washes:	3-4		32 washes:	3-4		45 washes:
	Change	Staining														
5 washes:	3- 4	4														
23 washes:	3-4															
32 washes:	3-4															
45 washes:	3 -4															
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))														
APPEARANCE AFTER WASH (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM PM01 TEST																
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01	Assess dimensional stability after 1 & 5 Washes. Woven 0 to -3% 0 to -5% for Viscose & Viscose Blends Knitted fabric: Single Jersey with NO Elastane Content:	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only.													

PTC18a – Adults Underwear e.g., briefs, trunks, underwear vests and Cami's, underwear leggings			
Test Name	Test Standard	Requirements	Comments
	Assess at 1 & 5 washes only	1 & 5 Washes: Length -5% / +1% Width -5% / +1% Single Jersey with Elastane Content, Viscose / Viscose Mix, Pique, Waffle, Interlock: 1 & 5 Washes: Length -7% / +1% Width -7% / +1% Pointelle: 1 & 5 Washes: Length -10% / +2%, Width -10% / +2% Additional standard for Rib Underwear only: Rib Underwear: 1 & 5 Washes: Length -10% / +2%, Width -10% / +2% ALL Other Knitted fabrics: 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result
Spirality		Woven ≤ 3% Knitted ≤ 5%	
Colour Change and Staining		Change: Staining 1& 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Washing (This test applies at FINISHED Fabric stage only . Garment assessed with PM01.)	BS EN ISO 105 - C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 - E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 - X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Dye Transfer in Storage	AATCC 163	Change: 4 Stain: 4 Cross Stain: 4-5	For all multipacks of varying colours (especially those with 1 x dark colours)

PTC18a – Adults Underwear e.g., briefs, trunks, underwear vests and Cami's, underwear leggings			
Test Name	Test Standard	Requirements	Comments
Phenolic Yellowing	BS EN ISO X18	Change Grade 4	Applicable to white, pale & pastel shades Applicable to fabrics and foam cups

PTC18B – Adults Lingerie -all bras, bra accessories, underwired, cupped styles including body suits, corsets, and suspender belts.

PTC18b – Adults Lingerie -all bras, bra accessories, underwired, cupped styles including body suits, corsets, and suspender belts			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps, etc. Test 5 of each component type, and report results individually.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Martindale Pilling	BS EN ISO 12945 -2	Woven 2,000 revs. Knitted 500 revs. Grade 3-4	Test after cleansing. Assess against original. Report assessment for wovens at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles

PTC18b – Adults Lingerie -all bras, bra accessories, underwired, cupped styles including body suits, corsets, and suspender belts					
Test Name	Test Standard	Requirements			Comments
					Report assessment for knitteds at 125 cycles, with final assessment at 500 cycles Spun synthetics, wool, acrylic and their blends only
Residual Elongation	BS EN 14704-1 Method A OR ISO 20932-1 Method A	WEFT Knitted fabrics EXCL. SHAPEWEAR & PERFORMANCE WEAR			
		<u>Jersey Fabrics (Single jersey & Rib)</u> 10% Max Unrecovered elongation (still under review)			<u>Fabrics containing elastane only.</u> Extension load <5% elastane 15N load 5-11% elastane 20N load >11% elastane 25N load
		<u>Seam Free</u> 20% Max Unrecovered elongation			Extension load @ 15N. Assess after 30 minutes only
		WARP Knitted fabrics EXCL. SHAPEWEAR & PERFORMANCE WEAR			
		<u>Lace/Mesh</u> 5% Max Unrecovered elongation			Extension load @ 15N. Assess after 30 minutes only
Residual Elongation SHAPEWEAR	BS EN 14704-1 Method A OR ISO 20932-1 Method A If the control level is created using multiple fabrics and layers, then the fabric must be tested as they are used in the garment.	<u>SHAPEWEAR</u> <u>Light Control</u> 5% Max Unrecovered elongation 40% Modulus @150-200g <u>Medium Control</u> 5% Max Unrecovered elongation 40% Modulus @250-500g <u>Firm Control</u> 5% Max Unrecovered elongation 40% Modulus @500-750g			

PTC18b – Adults Lingerie -all bras, bra accessories, underwired, cupped styles including body suits, corsets, and suspender belts					
Test Name	Test Standard	Requirements			Comments
Martindale Abrasion	BS EN ISO 12947 - 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites
		Shade Change @ 5000 Revs Grade 4			
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosic & Cellulose blends
Bursting strength	BS EN ISO 13938-2	175kPa			For Lace & Mesh only
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable			15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value			Please refer to Product claims & Product performance claims manual for updated test method
Elastic extension and Modulus test	PM23	Woven and knitted elastics must meet the required performance outlined under the PM23 test method			
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)					
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Follow Jersey Test Package PTC07 for all Jersey Nightwear All other Knitted fabrics 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends			Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests Each colourway must have a separate PM01 test. Multipack product testing requirements: every colourway pack/option must have a supporting PM01 test. a minimum of one product per colourway pack to be tested.
Spirality		Woven ≤ 3% Knitted ≤ 5%			
Colour change and staining		Follow Jersey Test Package PTC07 for all Jersey Nightwear Additional standard for Rib Underwear only: Rib Underwear: 5 Washes: Length -10% / +2%, Width -10% / +2% 23,32, 45 Washes: Length -10% / +2% Width -10% / +2% For Woven fabrics and All other knitted fabrics Change Staining 5 washes: 3- 4 4			A pack of Variable colour (and/or construction) = test darkest/most saturated colour option in the pack A pack of variable composition = test darkest/most saturated colour option in the pack and in addition the nightwear made from the highest variance in composition Discuss with the relevant QA on additional guidance if required.

PTC18b – Adults Lingerie -all bras, bra accessories, underwired, cupped styles including body suits, corsets, and suspender belts			
Test Name	Test Standard	Requirements	Comments
		23 washes: 3-4 32 washes: 3-4 45 washes: 3 -4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross stain 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric i.e., DTM elastic, binding, lace, bows etc if externally visible when worn. Does not include internal trims not visible when worn. N/A on white & cream fabrics	Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	
APPEARANCE AFTER WASH (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM PM01 TEST			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Assess dimensional stability after 1 & 5 Washes. Woven 0 to -3% 0 to -5% for Viscose & Viscose Blends Knitted fabric: Single Jersey with NO Elastane Content: 1 & 5 Washes: Length -5% / +1% Width -5% / +1% Single Jersey with Elastane Content, Viscose / Viscose Mix, Pique, Waffle, Interlock: 1 & 5 Washes: Length -7% / +1% Width -7% / +1% Pointelle: 1 & 5 Washes: Length -10% / +2%, Width -10% / +2% Additional standard for Rib Underwear only: Rib Underwear: 1 & 5 Washes: Length -10% / +2%, Width -10% / +2% ALL Other Knitted fabrics: 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result
Spirality		Woven ≤ 3% Knitted ≤ 5%	

PTC18b – Adults Lingerie -all bras, bra accessories, underwired, cupped styles including body suits, corsets, and suspender belts			
Test Name	Test Standard	Requirements	Comments
Colour Change and Staining		Change: 1& 5 washes: 4 Staining 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used.
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Dye Transfer in Storage	AATCC 163	Change: 4 Stain: 4 Cross Stain: 4-5	For all bra packages
Phenolic Yellowing	BS EN ISO X18	Change Grade 4	Applicable to white, pale & pastel shades Applicable to fabrics and foam cups When testing bras or cupped swimwear - test cups as a composite. If sample fails, test individual components

PTC19 – Children’s Underwear

PTC19 – Children’s Underwear			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content.

PTC19 – Children’s Underwear			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
			The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply	
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard	Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds	No Small Parts - up to 3 years. No sharp points or edges - all ages.

PTC19 – Children’s Underwear					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.			Applies to children up to 3 years
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATCP § 139			Applies up to age 16 years
Martindale Pilling	BS EN ISO 12945 -2	Woven 2,000 revs Knitted 500 revs Grade 3-4			Test after cleansing. Assess against original. Report assessment for wovens at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles Report assessment for knitteds at 125 cycles, with final assessment at 500 cycles Spun synthetics, wool, acrylic and their blends only
Residual Elongation	BS EN 14704-1 Method A OR ISO 20932-1 Method A	WEFT Knitted fabrics EXCL. SHAPEWEAR & PERFORMANCE WEAR			
		<u>Jersey Fabrics (Single jersey & Rib)</u> 10% Max Unrecovered elongation			<u>Fabrics containing elastane only.</u> Extension load <5% elastane 15N load 5-11% elastane 20N load >11% elastane 25N load
		<u>Seam Free</u> 20% Max Unrecovered elongation			Extension load @ 15N Assess after 30 minutes only
		WARP Knitted fabrics EXCL. SHAPEWEAR & PERFORMANCE WEAR			
		<u>Lace/Mesh</u> 5% Max Unrecovered elongation			Extension load @ 15N Assess after 30 minutes only
Mass per Unit Area	BS EN 12127	-5%/+5%			
		Lightweight ≤100gms	Medium 101-199gms	Heavyweight ≥200gms	
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 - 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites
		Shade Change @ 5000 Revs Grade 4			
Elastic extension and Modulus test	PM23	Woven and knitted elastics must meet the required performance outlined under the PM23 test method			
Bursting strength	BS EN ISO 13938-2	175kPa			For Lace & Mesh only

PTC19 – Children’s Underwear			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value	Please refer to Product claims & Product performance claims manual for updated test method
Colour Fastness to Washing (This test applies at FINISHED Fabric stage only. Garment assessed with PM01.)	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	Only applicable on Childrenswear N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Phenolic Yellowing	BS EN ISO X18	Change Grade 4	Applicable to white, pale & pastel shades Applicable to fabrics and foam cups When testing bra’s or cupped swimwear - test cups as a composite. If sample fails, test individual components
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Follow Jersey Test Package PTC08 for all Jersey Nightwear All other Knitted fabrics 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests Each colourway must have a separate PM01 test. Multipack product testing requirements: every colourway pack/option must have a supporting PM01 test. a minimum of one product per colourway pack to be tested.
Spirality		Woven ≤ 3% Knitted ≤ 5%	
Colour change and staining		Follow Jersey Test Package PTC08 for all Jersey Nightwear Additional standard for Rib Underwear only:	

PTC19 – Children’s Underwear			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		Rib Underwear: 5 Washes: Length -10% / +2%, Width -10% / +2% 23,32, 45 Washes: Length -10% / +2% Width -10% / +2% For Woven fabrics and All other knitted fabrics Change Staining 5 washes: 3- 4 4 23 washes: 3-4 32 washes: 3-4 45 washes: 3 -4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric i.e., DTM elastic, binding, lace, bows etc if externally visible when worn. Does not include internal trims not visible when worn. N/A on white & cream fabrics	A pack of Variable colour (and/or construction) = test darkest/most saturated colour option in the pack A pack of variable composition = test darkest/most saturated colour option in the pack and in addition the nightwear made from the highest variance in composition Discuss with the relevant QA on additional guidance if required. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Assess dimensional stability after 1 & 5 Washes. Woven 0 to -3% 0 to -5% for Viscose & Viscose Blends Knitted fabric: Single Jersey with NO Elastane Content: 1 & 5 Washes: Length -5% / +1% Width -5% / +1% Single Jersey with Elastane Content, Viscose / Viscose Mix, Pique, Waffle, Interlock: 1 & 5 Washes: Length -7% / +1% Width -7% / +1% Pointelle: 1 & 5 Washes: Length -10% / +2%, Width -10% / +2%	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label

PTC19 – Children’s Underwear							
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)							
Test Name	Test Standard	Requirements	Comments				
		Additional standard for Rib Underwear only: Rib Underwear: 1 & 5 Washes: Length -10% / +2%, Width -10% / +2% ALL Other Knitted fabrics: 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	<u>No colourway linking.</u> Each colourway must have a separate result				
Spirality		Woven ≤ 3% Knitted ≤ 5%					
Colour Change and Staining –		<table><tr><td>Change:</td><td>Staining</td></tr><tr><td>1& 5 washes: 4</td><td>4</td></tr></table> Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 Includes print colour change and staining. Includes colour change assessment of apparel trims against main fabric. N/A on white & cream fabrics		Change:	Staining	1& 5 washes: 4	4
Change:		Staining					
1& 5 washes: 4	4						
Appearance	Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required						

PTC20A – Adults Socks

PTC20a – Adults Socks			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition – ALL SOCKS (See additional requirements below for slipper socks only)	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Fibre composition – slipper socks constructed with a separate sole panel construction only	SI 1995 No.2489 (EC Directive 94/11) The Footwear (Indication of Composition) Labelling Regulations	Must Comply with the Directive	Visual check as appropriate

PTC20a – Adults Socks			
Test Name	Test Standard	Requirements	Comments
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Security of Attachment - ALL Circular knitted Socks (with integral sole)	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps, etc. Test 5 of each component type and report results individually
Security of Attachment - ALL Cut and sew slipper socks with a <u>separate</u> sole panel construction.	SATRA TM117	70N applicable to decorative trims	ONLY For slipper socks with separate sole panel All attached bows, buttons, pompoms snaps, etc. Test 5 of each component type and report results individually
Abrasion of Knitted Footwear garments – modified Martindale	BS EN 13770	A description of the appearance and breakdown to be given with the number of rubs i.e., 'Thinning' or 'Holing' 8,000 rubs for all compositions	Test Sole Only
Fibre Shedding	PM05	Grade 4 or above	Only applicable for brushed back and pile fabrics ≥ 10mm
Slip Resistance Applicable to all styles with a rubber printed sole panel	SATRA TM 144 ISO13287	Coefficient of Friction – 0.3 min Heel and Forepart – wet and dry on all surfaces	Test using Calibrated Clay Tile on Dry & Wet Surface, Carpet, Wood, clay tile and Vinyl surfaces
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value	Please refer to Product claims & Product performance claims manual for updated test method
Anti-Bacterial/Anti-Microbial /claims		Products claiming Anti-bacterial or Anti-Microbial properties (or related wording e.g., Stay fresh for longer / Odour control)	Please refer to Product claims & Product performance claims manual for test methods (Specific to product claim) Incl. branded finishes e.g. Micro-fresh /Biome
Seam strength	BS EN ISO 17697	10N/mm Functional stress baring seams only	ONLY For slipper socks with separate sole panel
Surface flash	BS4569	No Flash	ONLY For slipper socks with separate sole panel

PTC20a – Adults Socks																		
Test Name	Test Standard	Requirements	Comments															
		Required on all articles that have a pile or fur >3mm in length																
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)																		
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	ALL SOCKS incl. slipper socks (see variable criteria below) Assess dimensional stability. Foot Length +2% to -10%	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.															
TS Board fit		For CIRCULAR KNITTED product containing ≥ 80% synthetic fibre ONLY Fit product on TS Board (see table for correct TS board to sock size) Satisfactory Product meets % change requirements AND fits correctly to TS board. Unsatisfactory All other results which are not meeting the requirements for Satisfactory result	Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. Multipack product testing requirements: every colourway pack/option must have a supporting PM01 test. a minimum of one product per colourway pack to be tested.															
Colour change and staining		<table><tr><td></td><td>Change</td><td>Staining</td></tr><tr><td>5 washes:</td><td>4</td><td>4</td></tr><tr><td>23 washes:</td><td>4</td><td></td></tr><tr><td>32 washes:</td><td>4</td><td></td></tr><tr><td>45 washes:</td><td>4</td><td></td></tr></table> cross stain 4-5 Neon/Fluorescent shades: CHANGE:3 STAINING:3 cross stain 3-4		Change	Staining	5 washes:	4	4	23 washes:	4		32 washes:	4		45 washes:	4		Solid single colour pack = test 1 sock from the pack A pack of Variable colour (and/or construction) = test darkest/most saturated colour option in the pack A pack of variable composition = test darkest/most saturated colour option in the pack and in addition the sock made from the highest variance in composition
		Change	Staining															
5 washes:	4	4																
23 washes:	4																	
32 washes:	4																	
45 washes:	4																	
Appearance	Satisfactory Includes assessment meeting criteria S1/ S2 **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	Discuss with the relevant QA on additional guidance if required. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.																
APPEARANCE AFTER WASH (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM PM01 TEST																		
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Assess dimensional stability. Foot Length +2% to -10%	Only product which is 'hand wash only' or 'dry clean only' is to be assessed at 1 & 5 washes only. Wash as per care label.															

PTC20a – Adults Socks			
Test Name	Test Standard	Requirements	Comments
TS Board fit		For CIRCULAR KNITTED product containing ≥ 80% synthetic fibre ONLY Fit product on TS Board (see table for correct TS board to sock size) Satisfactory Product meets % change requirements AND fits correctly to TS board. Unsatisfactory All other results which are not meeting the requirements for Satisfactory result	Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Multipack products – follow guidance as above for Pm01. <u>No colourway linking.</u> Each colourway must have a separate result.
Colour change and staining		Change: Staining 1 & 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colourfastness to Perspiration	BS EN ISO 105 -E04	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used ONLY required on products containing ≥ 80% synthetic fibre

PTC20B – Adults Hosiery

PTC20b – Adults Hosiery			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			

PTC20b – Adults Hosiery			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps, etc. Test 5 of each component type and report results individually.
Fibre Shedding	PM05	Grade 4 or above	Only applicable for brushed back and pile fabrics ≥ 10mm
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value	Please refer to Product claims & Product performance claims manual for updated test method
Anti-Bacterial/Anti-Microbial /claims		Products claiming Anti-bacterial or Anti-Microbial properties (or related wording e.g., Stay fresh for longer / Odour control)	Please refer to Product claims & Product performance claims manual for test methods (Specific to product claim) Incl. branded finishes e.g. Micro-fresh /Biome
Print/flock/motif durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012

PTC20b – Adults Hosiery																					
Test Name	Test Standard	Requirements	Comments																		
			Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only																		
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)																					
Dimensional stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Must fit appropriate Hoseforma or Volumetric Leg boards.	Wash as per Care label using the number of washes prescribed by Primark.																		
Colour Change and Staining		<table><tr><td>Change:</td><td>Staining</td></tr><tr><td>5 washes: 4</td><td>4</td></tr><tr><td>23 washes: 3-4</td><td></td></tr><tr><td>32 washes: 3</td><td></td></tr><tr><td>45 washes: 3</td><td></td></tr><tr><td colspan="2">Neon/Fluorescent shades</td></tr><tr><td colspan="2">Change: 3 Stain: 3</td></tr><tr><td colspan="2">Cross Stain: 4-5</td></tr><tr><td colspan="2">N/A on white & cream fabrics</td></tr></table>	Change:	Staining	5 washes: 4	4	23 washes: 3-4		32 washes: 3		45 washes: 3		Neon/Fluorescent shades		Change: 3 Stain: 3		Cross Stain: 4-5		N/A on white & cream fabrics		No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash styles All plain knit product over 20 Denier including warm handle (e.g. Velvet plush & super cosy) - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.
Change:		Staining																			
5 washes: 4	4																				
23 washes: 3-4																					
32 washes: 3																					
45 washes: 3																					
Neon/Fluorescent shades																					
Change: 3 Stain: 3																					
Cross Stain: 4-5																					
N/A on white & cream fabrics																					
Appearance	Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))																				
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE																					
Dimensional stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01	Must fit appropriate Hoseforma or Volumetric Leg boards.	ONLY Product with surface embellishment, e.g.: sequins / diamante and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label.																		
Colour Change and Staining		<table><tr><td>Change:</td><td>Staining</td></tr><tr><td>1 & 5 washes: 4</td><td>4</td></tr><tr><td colspan="2">Neon/Fluorescent shades</td></tr><tr><td colspan="2">Change: 3 Stain: 3</td></tr><tr><td colspan="2">Cross Stain: 4-5</td></tr><tr><td colspan="2">N/A on white & cream fabrics</td></tr></table>	Change:	Staining	1 & 5 washes: 4	4	Neon/Fluorescent shades		Change: 3 Stain: 3		Cross Stain: 4-5		N/A on white & cream fabrics								
Change:		Staining																			
1 & 5 washes: 4	4																				
Neon/Fluorescent shades																					
Change: 3 Stain: 3																					
Cross Stain: 4-5																					
N/A on white & cream fabrics																					
Appearance	Assess at 1 & 5 washes only Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	Handwash only styles All products up to and including 20 Denier. All deniers - embellished, jacquard, and fashion product. For products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result.																			
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)																					

PTC20b – Adults Hosiery			
Test Name	Test Standard	Requirements	Comments
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colourfastness to PVC Migration	BS EN ISO 105-X10	Dry: 4	Not applicable to White/Cream fabrics. Applicable to all tights 200 denier and above. Applicable on all coated fabrics
Colourfastness to Hot Pressing	BS EN ISO 105-X11	Dry - Grade 4 Fabric Damp – Grade 4 Wet – Grade 4 Results reviewed at 100/150/200 degrees	Not applicable to White/Cream fabrics. Applicable to all tights 200 denier and above

PTC21A – Children's Socks

PTC21a – Children's Socks			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition (See additional requirements below for slipper socks only)	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Fibre composition – slipper socks constructed with a separate sole panel only.	SI 1995 No.2489 (EC Directive 94/11) The Footwear (Indication of Composition) Labelling Regulations	Must Comply with the Directive	Visual check as appropriate
Security of Attachment – ALL Circular knitted Socks (with integral sole)	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)

PTC21a – Children’s Socks			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
	PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components		
Security of Attachment - ALL Cut and sew slipper socks with a <u>separate</u> sole panel construction.	SATRA TM117	70N applicable to decorative trims	ONLY For slipper socks with separate sole panel All attached bows, buttons, pompoms snaps’ etc. Test 5 of each component type and report results individually
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years.
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard	Applies to children up to 8 years.
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds	No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.	Applies to children up to 3 years
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATPC § 139	Applies up to age 16 years
Abrasion of Knitted Footwear garments – modified Martindale	BS EN 13770	A description of the appearance and breakdown to be given with the number of rubs i.e., ‘Thinning’ or ‘Holing’. 8,000 rubs for all compositions	Test Sole Only
Fibre Shedding	PM05	Grade 4 or above	Only applicable for brushed back and pile fabrics ≥ 10mm.
Slip Resistance Applicable to all styles with a rubber printed sole panel	SATRA TM 144 ISO13287	Coefficient of Friction – 0.3 min Heel and Forepart – wet and dry on all surfaces	Test using Calibrated Clay Tile on Dry & Wet Surface, Carpet, Wood, clay tile and Vinyl surfaces
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value	Please refer to Product claims & Product performance claims manual for updated test method

PTC21a – Children's Socks			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Anti-Bacterial/Anti-Microbial /claims		Products claiming Anti-bacterial or Anti-Microbial properties (or related wording e.g., Stay fresh for longer / Odour control)	Please refer to Product claims & Product performance claims manual for test methods (Specific to product claim) Incl. branded finishes e.g. Micro-fresh /Biome
Seam strength	BS EN ISO 17697	10N/m Functional stress baring seams only	ONLY For slipper socks with separate sole panel
Surface flash	BS4569	No Flash Required on all articles that have a pile or fur >3mm in length.	ONLY For slipper socks with separate sole panel
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colourfastness to Perspiration	BS EN ISO 105 -E04	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used. ONLY required on products containing ONLY required on products containing ≥ 80% synthetic fibre
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	ALL SOCKS incl. slipper socks (see variable criteria below) Assess dimensional stability (see extended wash assessment table) Foot Length +2% to -10%	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests.
TS Board fit		For CIRCULAR KNITTED product containing ≥ 80% synthetic fibre ONLY Fit product on TS Board (see table for correct TS board to sock size) Satisfactory Product meets % change requirements AND fits correctly to TS board.	Each colourway must have a separate PM01 test. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling).

PTC21a – Children’s Socks																					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)																					
Test Name	Test Standard	Requirements	Comments																		
		Unsatisfactory All other results which are not meeting the requirements for Satisfactory result	All product to be dried as per care label.																		
Colour change and staining		<table><tr><td></td><td>Change</td><td>Staining</td></tr><tr><td>5 washes:</td><td>4</td><td>4</td></tr><tr><td>23 washes:</td><td>4</td><td></td></tr><tr><td>32 washes:</td><td>4</td><td></td></tr><tr><td>45 washes:</td><td>4</td><td></td></tr><tr><td>cross stain 4-5</td><td></td><td></td></tr></table> Neon/Fluorescent shades: CHANGE:3 STAINING:3 cross stain 3-4		Change	Staining	5 washes:	4	4	23 washes:	4		32 washes:	4		45 washes:	4		cross stain 4-5			Multipack product testing requirements: every colourway pack/option must have a supporting PM01 test. a minimum of one product per colourway pack to be tested. Solid single colour pack = test 1 sock from the pack
		Change	Staining																		
5 washes:	4	4																			
23 washes:	4																				
32 washes:	4																				
45 washes:	4																				
cross stain 4-5																					
Appearance	Satisfactory Includes assessment meeting criteria S1/ S2 **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	A pack of Variable colour (and/or construction) = test darkest/most saturated colour option in the pack A pack of variable composition = test darkest/most saturated colour option in the pack and in addition the sock made from the highest variance in composition Discuss with the relevant QA on additional guidance if required. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.																			
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE																					
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Assess dimensional stability. Foot Length +2% to -10%	Only product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label.																		
TS Board fit		For CIRCULAR KNITTED product containing ≥ 80% synthetic fibre ONLY Fit product on TS Board (see table for correct TS board to sock size) Satisfactory Product meets % change requirements AND fits correctly to TS board. Unsatisfactory All other results which are not meeting the requirements for Satisfactory result	Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Multipack products – follow guidance as above for Pm01. No colourway linking. Each colourway must have a separate result.																		

PTC21a – Children's Socks			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Colour change and staining		Change: Staining 1 & 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	

PTC21B – Children's Hosiery

PTC21b – Children's Hosiery			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment - ALL Circular knitted product (with integral sole)	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard	Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds	No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or	Applies to children up to 3 years

PTC21b – Children’s Hosiery			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.	
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATCP § 139	Applies up to age 16 years
Fibre Shedding	PM05	Grade 4 or above	Only applicable for brushed back and pile fabrics ≥ 10mm
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value	Please refer to Product claims & Product performance claims manual for updated test method
Anti-Bacterial/Anti-Microbial /claims		Products claiming Anti-bacterial or Anti-Microbial properties (or related wording e.g., Stay fresh for longer / Odour control)	Please refer to Product claims & Product performance claims manual for test methods (Specific to product claim) Incl. branded finishes e.g. Micro-fresh /Biome
Print/flock/motif durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colourfastness to PVC Migration	BS EN ISO 105-X10	Dry: 4	Not applicable to White/Cream fabrics. Applicable to all tights 200 denier and above. Applicable on all coated fabrics
Colourfastness to Hot Pressing	BS EN ISO 105-X11	Dry - Grade 4 Fabric Damp – Grade 4 Wet – Grade 4 Results reviewed at 100/150/200 degrees	Not applicable to White/Cream fabrics. Applicable to all tights 200 denier and above
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)			

PTC21b – Children’s Hosiery			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Dimensional stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Must fit appropriate Hoseforma or Volumetric Leg boards.	Wash as per Care label using the number of washes prescribed by Primark.
Colour Change and Staining		Change:Staining 5 washes: 44 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash styles All plain knit product over 20 Denier including warm handle (e.g. Velvet plush & super cosy) - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	- care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE			
Dimensional stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Must fit appropriate Hoseforma or Volumetric Leg boards.	ONLY Product with surface embellishment, e.g.: sequins / diamante and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only.
Colour Change and Staining		Change:Staining 1 & 5 washes: 44 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	Wash as per care label.
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	Handwash only styles All products up to and including 20 Denier. All deniers - embellished, jacquard, and fashion product. For products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result

PTC22 – Adults Coated Products e.g., PU, PVC

PTC22 – Adults Coated Products e.g., PU, PVC			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets.

PTC22 – Adults Coated Products e.g., PU, PVC			
Test Name	Test Standard	Requirements	Comments
			For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
US Clothing Flammability – Vinyl Plastic Film	16. CFR 1611 Contains Requirements and Test Method	The rate of burning shall not exceed 1.2 in./sec as judged by the average of five determinations lengthwise and five determinations transverse to the direction of processing	Applicable to PVC and similar plastics
Security of Attachment	CEN/TR 16792 :2014 Annex B	70N	All attached bows, buttons, pompoms snaps, etc. Test 5 of each component type and report results individually
Crumple flex	BS EN ISO 7854	No breakdown of coating at 9,000 cycles	
Abrasion resistance (TABER)	ASTM D3884 CS10 Wheels 1000g load 100 rubs	Wear Rating 2 Shade change 3- 4 No Surface breakdown or removal of coating	
Mass per Unit Area	BS EN 12127	-5%/+5%	
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012

PTC22 – Adults Coated Products e.g., PU, PVC					
Test Name	Test Standard	Requirements			Comments
		Slight loss of flocking acceptable			Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
		Lightweight ≤100gms	Medium 101-199gms	Heavyweight ≥200gms	
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry			Wash as per Care label using the number of washes prescribed by Primark.
Spirality		3%			No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.
Colour Change and Staining		Change: Staining 5 washes: 4 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics			Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label.
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))			All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE					
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Woven 0 to - 3% Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry			ONLY Product with surface embellishment, e.g.: sequins / diamante and/or product which is 'hand wash only' or 'dry clean only' is to be assessed at 1 & 5 washes only.
Spirality		3%			
Colour Change and Staining		Change: Staining 5 washes: 4 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics			Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C

PTC22 – Adults Coated Products e.g., PU, PVC			
Test Name	Test Standard	Requirements	Comments
			test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	<u>No colourway linking.</u> Each colourway must have a separate result.
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Stability to Washing	BS EN ISO 6330:2012	Woven 0 to - 3% Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry	4N @ 40°C Dry per Care Label
Stability to Dry Cleaning	Commercial Process	Woven 0 to - 3% Knitted 0 to -5%	Items that are Dry Clean only
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 4 Stain: 3-4	Items that are Dry Clean only N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics

PTC23 – Children’s Coated Products e.g., PU, PVC

PTC23 – Children’s Coated Products e.g., PU, PVC			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)

PTC23 – Children’s Coated Products e.g., PU, PVC			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
	PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components		
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply	
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
US Clothing Flammability – Vinyl Plastic Film	16. CFR 1611 Contains Requirements and Test Method	The rate of burning shall not exceed 1.2 in./sec as judged by the average of five determinations lengthwise and five determinations transverse to the direction of processing	Applicable to PVC and similar plastics
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard	Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds	No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.	Applies to children up to 3 years

PTC23 – Children’s Coated Products e.g., PU, PVC					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATCP § 139			Applies up to age 16 years
Abrasion resistance (TABER)	ASTM D3884 CS10 Wheels 1000g load 100 rubs	Wear Rating 2 Shade change 3- 4 No Surface breakdown or removal of coating			
Crumple flex	BS EN ISO 7854	No breakdown of coating at 9,000 cycles			
Mass per Unit Area	BS EN 12127	-5%/+5%			
		Lightweig ht ≤100gms	Medium 101- 199gms	Heavywei ght ≥200gms	
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable			15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4			Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4			Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5			A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5			N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3			N/A on white & cream fabrics
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)					
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry			Wash as per Care label using the number of washes prescribed by Primark.
Spirality		3%			No colourway linking is permitted for PM01 extended wash tests.
Colour Change and Staining		Change:			

PTC23 – Children’s Coated Products e.g., PU, PVC			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	- care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label.
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Woven 0 to - 3% Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry	ONLY Product with surface embellishment, e.g.: sequins / diamante and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result.
Spirality		3%	
Colour Change and Staining		Change: Staining 1& 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	

PTC24 – Adults Woven & Knitted Linings, Pocketings & Interlinings

PTC24 – Adults Woven & Knitted Linings, Pocketings & Interlinings			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to:

PTC24 – Adults Woven & Knitted Linings, Pocketings & Interlinings					
Test Name	Test Standard	Requirements			Comments
					1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
US Clothing Flammability – Vinyl Plastic Film	16. CFR 1611 Contains Requirements and Test Method	The rate of burning shall not exceed 1.2 in./sec as judged by the average of five determinations lengthwise and five determinations transverse to the direction of processing			Applicable to PVC and similar plastics
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4			Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4			Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 4 Stain: 3-4			Items that are Dry Clean only N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5			N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3			N/A on white & cream fabrics
Stability to Washing	BS EN ISO 6330 :2012	Woven -3% / +2% length & width Knitted -6% / +2% length & width			4N @ 40°C Dry per Care Label
Stability to Dry Cleaning	Commercial Process	Woven -3% / +2% length & width Knitted -6% / +2% length & width			Items that are Dry Clean only
		Light weight <100gms	Medium 101-199gms	Heavy weight >200gms	
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only

PTC24 – Adults Woven & Knitted Linings, Pocketings & Interlinings					
Test Name	Test Standard	Requirements			Comments
					Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 - 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites
		Shade Change @ 5000 Revs Grade 4			
Mass per Unit Area	BS EN 12127	-5%/+5%			
Colour Fastness to Washing	BS EN ISO 105 -C06	Change : 4 Stain : 4 Cross Stain : 4-5 Neon/Fluorescent shades Change : 3 Stain : 3 Cross Stain : 4-5			LyoW ®Multifibre Strip to be used

PTC25 – Children’s Woven & Knitted Linings, Pocketings & Interlinings

PTC25 – Children’s Woven & Knitted Linings, Pocketings & Interlinings					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends			Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.			All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1			Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats

PTC25 – Children’s Woven & Knitted Linings, Pocketings & Interlinings					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
					4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard			Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard			Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds			No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.			Applies to children up to 3 years
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATCP § 139			Applies up to age 16 years
Stability to Washing	BS EN ISO 6330:2012	Woven -3% / +2% length & width Knitted -6% / +2% length & width			4N @ 40°C Dry per Care Label
		Lightweight ≤100gms	Medium 101-199gms	Heavyweight ≥200gms	
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 - 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight

PTC25 – Children’s Woven & Knitted Linings, Pocketings & Interlinings			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		Shade Change @ 5000 Revs Grade 4	Shade Change not required on whites
Mass per Unit Area	BS EN 12127	-5%/+5%	
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres

PTC26 – Adults Trims, Fastening & Zipper

PTC26 – Adults Trims, Fastening & Zipper			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate,

PTC26 – Adults Trims, Fastening & Zipper			
Test Name	Test Standard	Requirements	Comments
			polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps, etc. Test 5 of each component type and report results individually
Stability to Washing	BS EN ISO 6330:2012	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	4N @ 40°C Dry per Care Label
Zip Fasteners	BS EN 16732	Compliance with physical performance	as appropriate
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics Test all Textile parts of the Trim, Fastener or Zipper LyoW® Multifibre Strip to be used
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 4 Stain: 3-4	Items that are Dry Clean only N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics Test all Textile parts of the Trim, Fastener or Zipper LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics Test all Textile parts of the Trim, Fastener or Zipper

PTC27 – Children's Trims, Fastening & Zipper

PTC27 – Children's Trims, Fastening & Zipper			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Safety of children's clothing. Cords & drawstrings on children's clothing	EN 14682	Must Comply	

PTC27 – Children’s Trims, Fastening & Zipper			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard	Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds	No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.	Applies to children up to 3 years
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b)	Applies up to age 16 years

PTC27 – Children’s Trims, Fastening & Zipper			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		New York General Business Law § 391-B / Wisconsin Administrative Code ATP § 139	
Stability to Washing	BS EN ISO 6330 :2012	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry 0 to -7% for Viscose & Viscose Blends	4N @ 40°C Dry per Care Label
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Zip Fasteners	BS EN 16732	Compliance with physical performance (as appropriate)	
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics Test all Textile parts of the Trim, Fastener or Zipper LyoW® Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics Test all Textile parts of the Trim, Fastener or Zipper LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics Test all Textile parts of the Trim, Fastener or Zipper
Peel Strength Touch and close fasteners	BS EN 12242	Min 0.8 N/mm	After 5 washes Apply for Velcro Only

PTC28 – Leather & Suede Products

PTC28 – Leather & Suede Products			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, trivinyll, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.

PTC28 – Leather & Suede Products			
Test Name	Test Standard	Requirements	Comments
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps etc. Test 5 of each component type and report results individually
Stability to Dry Cleaning	Commercial Process	Woven 0 to - 3%	Items that are Dry Clean only
Peel bond	BS EN ISO 2411	35N/50mm	
Baumann tear strength	ISO 3377 - 2.	>100N	
Leather: Determination of Flex Resistance - Vamp Flex	BS EN ISO 22288	Not worse than slight damage after 500,000 flexing cycles	
Leather verification	Lab Method		
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 & Wet: 3	N/A on white & cream fabrics
Colour fastness to Water	BS EN ISO 11642	Grade 3	N/A on white & cream fabrics
Colour fastness to cycles of to-and-fro rubbing	BS EN ISO 11640	Dry: 50 cycles Grade 3 Wet: 20 cycles Grade 2-3	N/A on white & cream fabrics
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 4 Stain: 3-4	Items that are Dry Clean only N/A on white & cream fabrics LyoW® Multifibre Strip to be used

PTC29 – Baby bibs, Muslins, baby blankets, baby mittens

PTC29 – Baby bibs, Muslins, baby blankets, baby mittens			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.

PTC29 – Baby bibs, Muslins, baby blankets, baby mittens			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
Security of Attachment	CEN/TR 16792:2014 Annex C	No detachment / Negligible change	Items 3mm or less and non grippable items.
Safety of children's clothing. Cords & drawstrings on children's clothing	EN 14682	Must Comply	
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonide, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard	Applies to children up to 8 years
Torque & Tension	16 CFR 1500. 51 - 53	Torque Test 0.45 N/meters Tension: 21 lbs. force for 10 seconds	Small Parts up to 3 years.

PTC29 – Baby bibs, Muslins, baby blankets, baby mittens					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being compressed), then the item must be failed.			Applies to children up to 3 years
Children's Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATP § 139			Applies up to age 16 years
Bursting strength	BS EN ISO 13938-2	175kPa			For Lace & Mesh only
Mass per Unit Area	BS EN 12127	-5% / +5%			No underweight fabric accepted
Spirality	ISO 16322-2 Method C	5% max			Circular knits only Follow Dimensional Stability Procedure
Martindale Pilling	BS EN ISO 12945 -2german market	Woven 2,000 revs. Knitted 500 revs. Grade 3/4			Test after cleansing. Assess against original. Report assessment for wovens at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles Report assessment for knitted at 125 cycles, with final assessment at 500 cycles. Spun synthetics, wool, acrylic and their blends only
Stability to Washing	BS EN ISO 6330 :2012	0 to -3% 0 to -5% Viscose and Viscose blends			4N @ 40°C Dry per Care Label
		Lightweight <100gms	Medium 101- 199gms	Heavyweight >200gms	
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosic & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 - 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites
		Shade Change @ 5000 Revs Grade 4			

PTC29 – Baby bibs, Muslins, baby blankets, baby mittens			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4/5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable	15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4/5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4/5	A2S 40°C N/A on white & cream fabrics
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4/5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4/5	Only applicable on Childrenswear N/A on white & cream fabrics
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Saliva	DIN V 53160-1	Change Grade 4	
Phenolic Yellowing	BS EN ISO X18	Change Grade 4	Applicable to white, pale & pastel shades
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	0 to -3% 0 to -5% Viscose and Viscose blends	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.
Spirality		5%	
Colour Change and Staining		Change: Staining 5 washes: 4 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE			
Dimensional Stability	Appearance after wash	Assess dimensional stability after 1 & 5 Washes. 0 to -3% 0 to -5% Viscose and Viscose blends	ONLY Product with surface embellishment, e.g.: sequins / diamante and/or product which is

PTC29 – Baby bibs, Muslins, baby blankets, baby mittens			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Spirality	BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	5%	'hand wash only' or 'dry clean only' is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result.
Colour Change and Staining		Change: Staining 1 & 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
All silicone Bibs must be tested to the relevant Food Contact standard PTH43-50 in the Homeware Manual			
- All claims must meet the Primark performance claims manual. - All products must comply with Primark’s chemical testing manual & Primark REACH Policy			

PTT07 – Disguise Costumes, Dress Up

Attention Primark Supplier: For Disguise and Dress up costumes DOC must be requested via TRF to the Primark approved Lab.

Attention testing Lab: For Disguise and Dress up costumes DOC draft must be issued along with the product test report and uploaded to the Primark Interlink Testing Portal

If there is an electrical component test to PTT06, PTT12 or PTA01

PTT07 – Disguise Costumes, Dress Up			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Toy Safety Directive	2009/48/EC	Must Comply	
Toy Safety Assessment	Article XVIII	Must Comply	Risk assessment must be performed either by the Supplier or by the Lab and must be uploaded to Primark Portal as a supplementary document or as part of the test report
Physical & mechanical	EN 71-1	Must Comply	
Flammability	BRC Modified EN71-2 Test	Must Comply	
Flammability	EN71-2	Must Comply	
CE Mark /UKCA mark	2009/48/EC UK SI 696 2019 (schedule33)	Must Comply	
Toy Labelling	2009/48/EC	Must Comply	
Safety of children's clothing. Cords & drawstrings on children's clothing	EN 14682	Must Comply	
Physical & mechanical	ASTM F963	Must Comply	
Flammability	ASTM F963	Must Comply	
Drawstrings / Ties on children upper outerwear	16 CFR 1120	Must Comply	
CPSIA Tracking Label	CPSIA Section 103	Must comply	
Country of Origin	19 CFR 134 / Can. Customs Tariff, c. 535 / Trade Practices Act 1974	Must Comply	
Fair Packaging and Labelling Act / Uniform Packaging and Labelling Regulations	F.P. & L. Act (16 CFR 500) / NIST Uniform Laws and Regulations Handbook 130	Must comply	-Manufacturer, Packer, or Distributor's Name & Address (City, State & ZIP Code) -Product Identification -Net quantity of contents shall be expressed in terms of weight or mass, measure, numerical count, or combination so as to give accurate information to facilitate consumer comparison (U.S. and metric units).
Stuffed Toy	PA / MA / OH Stuffed Toy Law	Must Comply for PA/MA/OH	PA: Shall meet the requirements Tolerances of the Commonwealth of Pennsylvania Regulation for Stuffed Toys Shall meet the Stuffed Toy Law label requirements. MA/OH: Shall meet the Stuffed Toy Law label requirements

PTT07 – Disguise Costumes, Dress Up			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Tested before and after cleaning. Base fabric or garment can be tested. Flat Fabrics of any fibre type exempted above 88gsm. Synthetic fibres and wool exemptions not permitted.
US Clothing Flammability – Vinyl Plastic Film	16. CFR 1611 Contains Requirements and Test Method	The rate of burning shall not exceed 1.2 in./sec as judged by the average of five determinations lengthwise and five determinations transverse to the direction of processing	Applicable to PVC and similar plastics
Pile retention	PM05	4	Test on all pile over 3mm
Print durability	PM02	Change:4 Cross stain: 4/5 Sight loss of print acceptable No delamination or print cracking No loss of flocking	15 minutes @ 30°C on machine washable items ONLY Dry as per care label
pH value	ISO 3071	5.0-7.5	Any dyed textile
Migration of certain elements	EN 71-3		
EU Security of Attachment on children's clothing	Sequins were classed as non grippable so instead of trying to pull off please perform a wash test in a Durawash (twin tub type washing machine) and tested against BS 7907	90N	Sequins <u>are not</u> permitted on products 0-36 months
Allergizing Dispersed Dye	DIN 54231		
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain: 4/5	A2S 40°C N/A on white & cream fabrics
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain: 4/5	N/A on white & cream fabrics
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
Colour Fastness to Saliva and Perspiration	DIN 53160		

PTC31 – Adult ties

PTC31 – Adult ties			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content.

			The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
Stability to Dry Cleaning	Commercial Process	-3% / +2% length and width -5% / +3% length and width for viscose and blends with viscose -7% / +7% length and width viscose crepe	Items that are Dry Clean only
Colour fastness to Rubbing	BS EN ISO 105 X12	Dry: 4 Wet: 3-4	N/A on white & cream fabrics For products with Textile components only
All products which are deemed to have play value, have novelty value or child appealing must comply to The European Toy Safety Directive – EN 71 parts 1, 2 and 3 and the Standard Consumer Safety Specification for Toy Safety –ASTM F963			

PTC34 – Children’s light up jumpers (EU and UK markets only)

Children’s light up jumpers (EU and UK markets only)			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Directive 2014/30/EU Electromagnetic Compatibility	EN 55024 EN 55015 EN 55013 EN 61547 EN 61000	Must Comply	
Lighting Safety	EN62471	Must Comply	
WEEE Directive,	2002/96/EC and 2012/19/EU	Recover: 75 % Reused and recycling: 55 %	
Toys Safety Directive 2009/48/EC	EN71 series	Must Comply	
Electrical Toy Safety	EN IEC 62115	Must Comply	
Battery Standard	IEC 60086 -1 IEC 60086 – 2 IEC 60086 – 5	Must Comply	
IPXX	IEC 60529	Must Comply	If product has a relevant claim
UKCA & CE Marking	EC Regulation 765/2008 Electrical Equipment (Safety) Regulation	Must Comply	
RoHS Directive 2011/65/EU amendment (EU) 2015/863	2011/65/EU	Must comply with the limits in the directive. We do not accept the use of any exemptions	
Mercury content and labelling assessment for Battery	US Public Law 104-142	Must Comply	
Batteries Directive 2006/66/EC as amended and new Batteries Regulation (EU) 2023/1542	EN 62133 EN 60086	Must Comply	
UK Batteries and Accumulators (Placing on the Market) Regulations 2008	EN 62133 EN 60086	Must Comply	
PAS 7055:2021 Button and coin batteries – safety requirements – specification for non-toy products	PAS 7055:2021	Must comply.	This UK publicly available specification (PAS) addresses the safety issues posed by button and coin batteries in non-toy products by requiring warnings on the battery, battery packaging, and on products that contain these batteries, in addition to testing requirements for products

Children’s light up jumpers (EU and UK markets only)			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
			containing button and coin batteries.
Chlorinated organic carriers (chlorobenzene and chlorotoluene)	REACH, Annex XVII, item 72	Must Comply	
Organotin	REACH, Annex XVII, item 20	Must Comply	
Phthalates	Primark PRSL	Must Comply	
Polycyclic Aromatic Hydrocarbons	REACH, Annex XVII, item 50	Must Comply	
Functionality Test	Nominated Laboratory in-house test method	Satisfactory - Fit for use.	Whole product including all components
Garment	Test to relevant test package in the Primark Apparel Testing Manual		
Labelling and marking on Electrical Components	Follow General Labelling Regulations for Electrical Products in the Primark Electrical Testing Manual.		
Chemical Testing	Test to appropriate test package in the Primark Chemical Manual		
Primark nominated laboratory to suggest any additional testing specific to product design if applicable.			
Primark does not permit selling Children’s Light Up Apparel in the USA. Such product is for EU & UK market only.			
Electrical component should be non-accessible along with non-replaceable battery.			
Electrical component should be sealed within the garment and washable so the garment can be washed.			
Supplier must always submit Labelling, Packaging and Artworks to the Lab along with Product sample.			

PTC35 – Adults Faux Suede Products

PTC35 – Adults Faux Suede Products			
Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz.

PTC35 – Adults Faux Suede Products					
Test Name	Test Standard	Requirements			Comments
					per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonide, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Security of Attachment	CEN/TR 16792 :2014 Annex B	70N			All attached bows, buttons, pompoms snaps, etc. Test 5 of each component type and report results individually
Stability to Washing	BS EN ISO 6330:2012	Woven 0 to - 3% Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry			4N @ 40°C Dry per Care Label
Stability to Dry Cleaning	Commercial Process	Woven 0 to - 3% Knitted 0 to -5%			Items that are Dry Clean only
Abrasion resistance (TABER)	ASTM D3884 CS10 Wheels 1000g load 100 rubs	Wear Rating 2 Shade change 3- 4 No Surface breakdown or removal of coating			
Mass per Unit Area	BS EN 12127	-5%/+5%			
Nap Stability	BS EN ISO 12947-4: (No weight) See PM03	b) @ 4,000 revs.			Raised and pile fabrics only
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable			15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
		Lightweight ≤100gms	Medium 101-199gms	Heavyweight ≥200gms	
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads

PTC35 – Adults Faux Suede Products			
Test Name	Test Standard	Requirements	Comments
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry	Wash as per Care label using the number of washes prescribed by Primark.
Spirality		3%	No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.
Colour Change and Staining		Change: 5 washes: 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	Staining 4 Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label.
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Woven 0 to - 3% Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry	ONLY Product with surface embellishment, e.g.: sequins / diamante and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only.
Spirality		3%	Wash as per care label.
Colour Change and Staining		Change: 5 washes: 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	No colourway linking. Each colourway must have a separate result.
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colourfastness to Hot pressing	BS EN ISO 105-X11 1996	Grade 4	All colourways on suede product to be tested apart from white and beige
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 3-4 Stain: 3-4	Items that are Dry Clean only N/A on white & cream fabrics LyoW ®Multifibre Strip to be used

PTC35 – Adults Faux Suede Products			
Test Name	Test Standard	Requirements	Comments
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 3-4 Stain: 3-4 Cross Stain: 4-5 Heavy Shades, Fade-Outs, Prints, Coatings, Pigment, Indigo on all fibres except polyamide + polyester: Change: 3 Stain: 3 Cross Stain: 4-5 Polyamide + Polyester Fibres: Change: 2-3 Stain: 2-3 Cross Stain: 4-5	N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4, Wet: 3 Heavy Shades, Fade-Outs, Prints, Coatings, Pigment, Indigo Dry: 3, Wet: 2-3	N/A on white & cream fabrics
Colour Fastness to Washing (FINISHED Fabric stage only – garment assessed with PM01)	BS EN ISO 105 -C06	Change: 3-4 Stain: 3-4 Cross Stain: 4-5 Heavy Shades, Fade-Outs, Prints, Coatings, Pigment, Indigo on all fibres except polyamide + polyester: Change: 3 Stain: 3 Cross Stain: 4-5 Polyamide + Polyester Fibres: Change: 2-3 Stain: 2-3 Cross Stain: 4-5	A2S 40°C N/A on white & cream fabrics LyoW® Multifibre Strip to be used
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres

PTC36 – Childrens Faux Suede Products

PTC36 – Children's Faux Suede Products			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.

PTC36 – Children’s Faux Suede Products			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
Security of Attachment	EN 17394-2 Security of buttons. PD CEN/TS 17394-1 Security of attached components to infants' clothing PD CEN/TS 17394-3 Security of metal mechanically applied press fasteners PD CEN/TS 17394-4 Security of attachment of all other components	90N If the item fails after testing, it will then be tested as a small part. If it fits entirely within the EN71-1 small parts cylinder in any orientation, then the item must be failed.	All attached bows, buttons, pompoms snaps, felt additions etc. Test 5 of each component type and report results individually. Fail if small part as per EN71-1. (Non-grippable items and those under 3 mm exempt)
Safety of children’s clothing. Cords & drawstrings on children’s clothing	EN 14682	Must Comply	
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonate, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Sharp Edges Restrictions	16 CFR 1500. 49	Meets the standard	Applies to children up to 8 years
Sharp Points Restrictions	16 CFR 1500. 48	Meets the standard	Applies to children up to 8 years
Torque & Tension	EN71 part 1 16 CFR 1500. 51 - 53	Torque Test 0.45 Nm or a rotation of 180o both in a clockwise and anticlockwise direction is achieved. Tension: 90N force for 10 seconds	No Small Parts - up to 3 years. No sharp points or edges - all ages.
Small Parts Restrictions	16 CFR 1501	For all decorative and functional items intended for children 36 months (3 years) of age. If the item fails after use and abuse testing or appearance after laundering requirement, it will then be tested as a small part. If it fits entirely within the small parts cylinder in any orientation (without being	Applies to children up to 3 years

PTC36 – Children’s Faux Suede Products					
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)					
Test Name	Test Standard	Requirements			Comments
		compressed), then the item must be failed.			
Children’s Drawcords in Upper Outerwear	ASTM F 1816 – 2018	16 CFR 1120.3(b) New York General Business Law § 391-B / Wisconsin Administrative Code ATCP § 139			Applies up to age 16 years
Abrasion resistance (TABER)	ASTM D3884 CS10 Wheels 1000g load 100 rubs	Wear Rating 2 Shade change 3- 4 No Surface breakdown or removal of coating			
Mass per Unit Area	BS EN 12127	-5%/+5%			
Nap Stability	BS EN ISO 12947-4: (No weight) See PM03	b) @ 4,000 revs.			Raised and pile fabrics only
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable			15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
		Lightweight ≤100gms	Medium 101- 199gms	Heavyweight ≥200gms	
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Colourfastness to Hot pressing	BS EN ISO 105-X11 1996	Grade 4			Suede effect product only. All colourways on suede product to be tested apart from white and beige
Colour Fastness to Washing (FINISHED Fabric stage only – garment assessed with PM01)	BS EN ISO 105 -C06	Change: 3-4 Stain: 3-4 Cross Stain: 4-5 Heavy Shades, Fade-Outs, Prints, Coatings, Pigment, Indigo on all fibres except polyamide + polyester: Change: 3 Stain: 3 Cross Stain: 4-5 Polyamide + Polyester Fibres: Change: 2-3 Stain: 2-3 Cross Stain: 4-5			A2S 40°C N/A on white & cream fabrics LyoW®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 3-4 Stain: 3-4 Cross Stain: 4-5 Heavy Shades, Fade-Outs, Prints, Coatings, Pigment, Indigo on all fibres except polyamide + polyester: Change: 3 Stain: 3 Cross Stain: 4-5 Polyamide + Polyester Fibres:			N/A on white & cream fabrics LyoW®Multifibre Strip to be used

PTC36 – Children’s Faux Suede Products			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		Change: 2-3 Stain: 2-3 Cross Stain: 4-5	
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4, Wet: 3 Heavy Shades, Fade-Outs, Prints, Coatings, Pigment, Indigo Dry: 3, Wet: 2-3	N/A on white & cream fabrics
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
PM01 – Appearance after Extended wash – complete for ALL colourways / ALL product (excluding exceptions)			
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry	Wash as per Care label using the number of washes prescribed by Primark.
Spirality		3%	No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test.
Colour Change and Staining		Change:Staining 5 washes: 44 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label.
Appearance		Satisfactory **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only.
Appearance after wash (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM ABOVE			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	Woven 0 to - 3% Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry	ONLY Product with surface embellishment, e.g.: sequins / diamante and/or product which is ‘hand wash only’ or ‘dry clean only’ is to be assessed at 1 & 5 washes only.
Spirality		3%	
Colour Change and Staining		Change:Staining 1& 5 washes: 44 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label
Appearance	Satisfactory		

PTC36 – Children’s Faux Suede Products			
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Test Name	Test Standard	Requirements	Comments
		**appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	No colourway linking. Each colourway must have a separate result.

PTC37 – Ski Wear

Test Name	Test Standard	Requirements	Comments
PRIMARK MANDATORY TESTS (MUST BE COMPLETED FOR AT LEAST ONE COLOUR PER STYLE) unless specified in the comments			
Fibre Composition	1007/2011 & AATCC 20A	No tolerance for 100% composition +/- 3% on blends	Laboratory must list the labelling comments for both the EU & US markets. For Luxury Animal Fibres, evidence of full traceability throughout the manufacturing process from farm to finished goods must be provided. The fibre content on the care label shall be declared as per the test results, not the claimed fibre content. The +/- 3% on blends applies to variation in bulk production, not to declaration of fibre content on the care label.
US Clothing Flammability	16. CFR 1610 Contains Requirements and Test Method	Rated as Class 1	Applicable to: 1. Fabrics with a plain surface weighing less than 88gsm (2.6 oz. per sq. yd.) and made of non-exempt fibre(s)* 2. Fabrics with a raised surface if made of non-exempt fibre(s)* 3. Brushed back sweats 4. Fabrics with glitter, glue, mylar, foam, etc. require testing. *Non-exempt fibres: silk, cotton, kapok, hemp, linen, flax, jute, abaca, coir, ramie, acetate, alginate, cupro, modal, protein, triacetate, viscose, chlorofibre, flurofibre, polyethylene, polypropylene, polycarbonide, polyurethane, vinyl, triviny, elastodiene, elastane, glass fibre, metal fibre, metallised fibre, paper, and lyocell.
Security of Attachment	CEN/TR 16792:2014 Annex B	70N	All attached bows, buttons, pompoms snaps, etc. Test 5 of each component type. Report results individually
Martindale Pilling	BS EN ISO 12945 -2	Woven 2,000 revs. Knitted 500 revs. Grade 3-4	Test after cleansing. Assess against original. Report assessment at 125, 500 & 1,000 cycles with final assessment at 2,000 cycles Spun synthetics, wool, acrylic and their blends only
Residual Elongation	BS EN 14704 -1 Method A	Woven Max 5% Unrecovered Elongation Knitted Max 10% Unrecovered Elongation	Fabrics containing elastane only. Woven – 30N Load. Knitted – 20N Load. Assess after 1 and 30 minutes. Test in stretch direction only
Accelerator	AATCC 93	Weight Loss 10% Visual Assessment ‘Negligible’	Pile fabrics only 3 mins Velvet @ 2000 R.P.M. 5 Mins Corduroy or Velour @ 2000 R.P.M.

Test Name	Test Standard	Requirements			Comments
Fibre Shedding	PM05	Grade 4 or above			Required on all articles that have pile or fur >3mm in length.
Surface Flash	BS 4569	No Flash Not required for testing if tested for US Clothing Flammability 16. CFR 1610			Required on all articles that have pile or fur >3mm in length
Mass per Unit Area	BS EN 12127	-5%/+5%			
Nap Stability	BS EN ISO 12947-4: (No weight) See PM03	b) @ 4,000 revs.			Raised and pile fabrics only
Fibre Proof Properties	BS 15586	No more than 6 fibres penetration			Only required on items that have synthetic wadding
Print / Motif / Flock Durability	PM02	Change: 4 Cross Stain: 4-5 Sight loss of print adhesion acceptable Slight delamination of print acceptable Slight print cracking acceptable Slight loss of flocking acceptable			15 minutes @40°C Dry as per Care Label ** Only required on Print/Motif/Flock product being tested for BS EN ISO 6330: 2012 Appearance after wash (1 and 5 washes) All functional internal printing on garments to be assessed for observational changes only
		Light weight <100gms	Medium 101g-199gms	Heavy weight >200gm	
Tensile Strength	BS EN ISO 13934 -2 Grab Method	120N	160N	200N	For Woven Fabrics Only Test in non-stretch direction only
Seam Strength	BS EN ISO 13935 -2	100N	120N	140N	For Woven Fabrics Only Test in non-stretch direction only
Seam Slippage	BS EN ISO 13936 -1	80N	100N	120N	For Woven Fabrics Only Test in non-stretch direction only Seam Open 6mm 3mm for contrast warp & weft threads
Tear Strength	BS EN 13937 - 1	700cN	800cN	900cN	For Woven Fabrics Only Test in non-stretch direction only Cellulosics & Cellulose blends
Martindale Abrasion	BS EN ISO 12947 – 2	10,000 rubs	15,000 rubs	20,000 rubs	For Woven Fabrics Only 9kPa weight Shade Change not required on whites. Printed Fabrics – part of the print must be present within the tested sample.
Water resistance Claims Hydrostatic Pressure Test / Water Column test	EN ISO 811	Fabric test - Water resistance rating 10,000mm (10K) Taped seams – Water resistance rating 8,000mm(8k) Tolerance of 10%			
Shower Resistant Claims Spray Rating	BS EN ISO 4920 Before & after one cleanse	Grade 4-5 as received. Grade 4 After one Cleanse			Cleanse to Care Label Only required when Shower Resistant is being claimed
Wind Resistant Claims Air Permeability	BS EN ISO 9237	Wind Resistant <20 litres/m2/sec Windproof :<0.1 litres/m2/sec			Only required when Wind Resistant is being claimed
Water vapour resistance(m2Pa/W) Breathability Ret – only is required	ISO 11092:2014	≤ 20 Pa·m²/W: Satisfactory performance			Ret ≤ 15 m²·Pa/W: Excellent breathability - accepted Ret ≤ 20 m²·Pa/W: Good breathability - accepted
Zip Fasteners	BS EN 16732	Compliance with physical performance			as appropriate

Test Name	Test Standard	Requirements	Comments	
Thermal properties /claims	ISO 11092:2014	Products claiming thermal properties or tog value	Please refer to Product claims & Product performance claims manual for updated test method	
Performance Specifications for Down and Feather Fillings for Textile Products	ASTM D-4522: 1.1: “Requirements for fillings for industry products such as wearing apparel, sleeping bags, and comforters.” Turbidity IDFB 11 Oxygen Number IDFB 7	Oxygen Number: less than 10 Turbidity: greater than 300 mm	Only required on Down and Feather filled products	
Hygiene and Cleanliness Specification	BS EN 12935: 2001	Oxygen Index result 20 to 50 - conduct Microbiological. State EN 1884	<20 OI	
Feather and Down Oxygen Index Number	BS EN 1162 (method)	To be conducted on untreated / undyed feathers only		
Hygiene and Cleanliness Specification Feather and Down Determination of microbiological state (Used as filler) & Marabou – undyed. Hygiene and Cleanliness Specification (cont.)	BS EN 12935: 2001 EN 1884 (method)	Only test if OI result of BS EN 1162 is >20. Testing to be stopped and failed if >50 <u>To be conducted on untreated / undyed feathers only.</u>	Impurity indicator	Limit of acceptability
			Mesophil aerobic bacteria count	Less than 10 ⁶ CFU/g
			Faecal Streptococci count	Less than 10 ² CFU/g
			Sulphite reducing clostridium count	Less than 10 ² CFU/g
			Presence of salmonella	Absent in 20g feathers
PM01 – APPEARANCE AFTER EXTENDED WASH TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)				
Dimensional Stability	PM01 Appearance after Extended Wash table A (part I /II/III) assessment criteria	Woven 0 to - 3% 0 to - 5% for Viscose & Viscose Blends Knitted 0 to -5% Flat Dry 0 to -7% Tumble Dry	Wash as per Care label using the number of washes prescribed by Primark. No colourway linking is permitted for PM01 extended wash tests. Each colourway must have a separate PM01 test. Machine wash product: - care labels set at 30°C test at 3N/3M/3G as required - care labels at 40°C test at 4N/4M/4G as required (following care labelling). All product to be dried as per care label. All Circularity products to pass 23 washes – minimum requirement. All functional internal printing on garments to be assessed for observational changes only	
Spirality		Woven ≤ 3% Knitted ≤ 5%		
Colour Change and Staining		Change: 5 washes: 4 23 washes: 3-4 32 washes: 3 45 washes: 3 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics **INCLUDES assessment of Print/Flock/motif applications to garment (See table A (part III))	Staining 4 	

Test Name	Test Standard	Requirements	Comments
		to garment (See table A (part III))	
APPEARANCE AFTER WASH (1 and 5 washes) - ONLY REQUIRED FOR PRODUCT EXEMPTED FROM PM01 TEST			
Dimensional Stability	Appearance after wash BS EN ISO 6330: 2012 and table A (part 1) in PM01 Assess at 1 & 5 washes only	0 to - 3% Woven. 0 to - 5% Woven Viscose & Viscose Blends Knitted 0 to-5% Flat Dry 0 to -7% Tumble Dry	ONLY Product with surface embellishment, e.g.: sequins / diamante / foil print and/or product which is 'hand wash only' or 'dry clean only' is to be assessed at 1 & 5 washes only. Wash as per care label. Handwash only styles: products with care labels set at 30°C or 40°C test at 4H @ 40°C Dry per Care Label Machine wash styles: For products with care labels set at 30°C or 40°C test at 4N /4M /4G (follow care label) @ 40°C Dry per Care Label No colourway linking. Each colourway must have a separate result
Spirality		Woven ≤ 3% Knitted ≤ 5%	
Colour Change and Staining		Change: Staining 1 & 5 washes: 4 4 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain: 4-5 N/A on white & cream fabrics	
Appearance		Satisfactory **appearance of Print/Flock/Motif to be assessed separately by PM02 test apply as required	
COLOURFASTNESS TESTS (MUST BE COMPLETED FOR ALL COLOURS PER STYLE)			
Colour Fastness to Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Non-Chlorine Bleach	AATCC/ASTM TS-001	Grade 4	Not applicable for Silks, Wools & Elastane fibres
Colour Fastness to Washing	BS EN ISO 105 -C06	Change: 4 Stain: 4 Cross Stain:4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain:4-5	A2S 40°C N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Dry Cleaning	BS EN ISO 105 -D01	Change: 4 Stain: 3-4	Items that are Dry Clean only N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Water	BS EN ISO 105 -E01	Change: 4 Stain: 4 Cross Stain:4-5 Neon/Fluorescent shades Change: 3 Stain: 3 Cross Stain:4-5	N/A on white & cream fabrics LyoW ®Multifibre Strip to be used
Colour Fastness to Rubbing	BS EN ISO 105 -X12	Dry: 4 Wet: 3	N/A on white & cream fabrics
- All claims must meet the Primark performance claims manual. - All products must comply with Primark’s chemical testing manual & Primark REACH Policy			

In House Test Methods

In House Test Method		Accessories	Apparel	Cosmetic	Electrical	Footwear	Health & Beauty Acc.	Home	Toys	Nursery
PM01	Product Appearance after Extended Wash (1 to 45 washes) & Appearance after wash (1 & 5 washes)	x	x					x		
PM02	Print / Motif / Flock Durability	x	x					x		
PM03	Nap Stability		x							
PM04	Dimensional and Bra Wire Casing Stability		x							
PM05	Fibre Shedding / Pile loss		x			x		x		
PM06	Chenille Pile Loss		x							
PM07	Back pocket application strength – Denim jeans		x							
PM08	Belt loop application strength – Denim jeans		x							
PM10	Opening force of mechanical part	x								
PM11	Durability test (open & close for 500 cycles)	x								
PM12	Repeat manual inversion test	x								
PM13	Flexing Resistance of Band	x								
PM14	Strength of Strap / Handle attachment	x								
PM15	Telescopic Handle Loading	x								
PM16	Telescopic Handle Durability	x								
PM17	Rolling / Castor Durability	x								
PM18	Stability Test							x		
PM19	Wood / PVC Staining							x		
PM20	Tarnish Test (all coated products)	x								
PM21	Burning Evaluation of Candle Holders									
PM22	Heat Conductivity		x							
PM23	Elastic extension and Modulus		x							
PM24	Effects of hand washing									x
PM25	Effects of freezing and thawing cycle									x
PM26	Puncture Resistance of Bra Wire Casing		x							

PM01- Product Appearance after Extended Wash & Appearance After Wash BS EN ISO 6330: 2012

1. Purpose

- To assess garments for any changes after multiple washing
- Note: Minimum of two original products must be submitted in their finished state.; one for the test one for comparison*

2. Equipment:

- 2.1** A Wascator is be used in all instances unless specified by the PRIMARK. In some circumstances Primark may allow the use of a domestic washing machine for in house checks using a European Brand Miele/Bosch front loader, spin cycles of 600 & 1200 RPM required.
- 2.2** ISO 105: A002 Grey Scales
- 2.3** BS EN ISO 6330:2012 Polyester Makeweights (200 x 200 mm ± 40 mm, 50 ± 5 g)
- 2.4** Use IEC(A) Detergent, Sodium Perborate Tetrahydrate + TAED as detailed in BS EN ISO 6330:2012

Detergent	For white	ISO 6330:2012, Type 2 IEC (A*), non-phosphate, with optical brightener and with enzymes, 20g per cycle
	For colours	ISO 6330:2012, Type 3 ECE (A), non-phosphate, without optical brightener, 20g per cycle
	For machine hand wash (4H)	PERWOLL liquid (Henkel), 60ml per cycle

- 2.5** D65 artificial daylight – as per Verivide cabinet
- 2.6** Overlocking and lockstitch sewing machines

3. Method:

- 3.1 Attach a 10x4cm piece of multi-fibre strip type LyoW to the item to be washed.
- 3.2 Select appropriate programme in the Wascator.
- 3.3 Wash at care label temperature of garment /product.
- 3.4 Assess against original sample under D65 artificial daylight - as per Verivide cabinet using the below table after 5th wash (for PM01) and 1 & 5 washes (for Appearance after wash).
- 3.5 Assess dimensional stability of Product after each wash increment using wash care program listed in Performance Requirement. (See section 4 for extended wash product)
- 3.6 If the product is dry clean only, follow the above process using a commercial dry clean (ideally GreenEarth or siloxane based dry cleaning for dry clean products)
- 3.7 Minimum of two original products must be submitted in their finished state.; one is to be used as the reference sample and the other is to be tested.
- 3.8 Report only using the Primark PM01 report template.

4. Extended Wash Durability

- 4.1 For product being tested to the extended wash assessment table, washes are increased and assessed as stated.
- 4.2 Multi fibre strip is only to be used for assessment of staining for the 5th Wash (for Pm01) and 1 and 5 washes (for appearance after wash) assessments as per section 3 and removed for subsequent wash cycles and assessments.
- 4.3 Colour change assessment at all intervals must be compared against an unwashed original sample.
- 4.4 The product must achieve the increased wash cycles in line with the product testing specification table, and the extended wash table below.
- 4.5 For product being tested to PM01, assessments are to be made at the intervals shown in the table below. Stability and Appearance results are to be reported at each assessment stage.
- 4.6 ALL multi-packed product - see guidance in test package table as to testing criteria dependent on pack type / content variables. Every colourway pack will have a minimum of 1 product to be tested for PM01.

PM01 Appearance after extended wash - WASH ASSESSMENT TABLE

	Assessment wash intervals – PM01 Appearance after extended wash			
Product Category	1	2	3	4
All washable clothing	5 washes	23 washes	32 washes	45 washes
Circular product required to pass minimum 23 washes.				
For dry clean, hand wash and exempt products follow Appearance after wash test BS EN ISO 6330: 2012 (1& 5 washes only)				

- 4.7 Full PM01 assessments are to be performed at the prescribed wash intervals in the table above. For each assessment interval, the sample should be dried, otherwise continued washing is permitted. E.g., for all washable clothing, based on the above table dry and assess samples after 5, 23, 32 and 45 wash cycles.
- 4.8 If the garment **fails** at any assessment interval, **testing is to be stopped** and the results recorded at that stage.
- 4.9 Circularity product is required to pass a minimum of 23 washes – if the product subsequently fails at 32 or 45 wash increments it will still be recorded as an overall failure.

TABLE A (part I) A-Q only (Assessment criteria for PM01 and Appearance after wash 1 & 5 washes)

Ensure all components, including interlinings are assessed.

	Assessment	Satisfactory	Unsatisfactory
A	Dimensional Stability	As per product testing specification	
B	Colour change/loss using grey scale assessment (BS EN ISO 105 A02)	As per product testing specification	

	Assessment	Satisfactory	Unsatisfactory
	If OBA is present, assess sample using Fluorescent Suppressor and report Suppressed grade also.		
C	Cross staining i.e., colour transfer on to component parts and multi-fibre strip (BS EN ISO 105 A03)	As per product testing specification	
D	Fraying of fabric and trims	Not frayed	Frayed
E	Detachment of fastenings & trims	Not detached	Detached
F	Spirality/twisting of seams. Calculate spirality.	As per product testing specification	
G	Grinning/opening of seams. Measure seam opening	2mm or less	More than 2mm
H	Pilling or fuzzing of surface fibres. Assess degree of pilling/fuzzing using BS EN ISO 12945-2 grades	3-4 or better *	Less than 3-4*
I	Pile loss or flattening of pile. Assess using grey scales.	Less than 1mm ²	More than 1mm ²
		Photo required of failure	
J	Corrosion/damage/sharp edges to trim including chipping, scratching of coatings	No corrosion/damage	Corrosion/damage/sharp edges
K	Delamination of fused components	No delamination or bubbling	Delamination or bubbling
		Photo required of failure	
L	Free running and operation of zip fastener.	Slide free and operable end stops/closures	Poor function – report if the zip stops whilst closing
M	Differential shrinkage, distortion, wrinkling and twisting of fabric applications and seams.	No changes	Changes observed
		Photo required of failure	
N	Unravelling/breaks in stitching	No changes	Loose, damaged, or broken threads
		Photo required of failure	
O	Filling moved within casing	No changes	Changes observed – unfilled areas observed
P	Fibre migration	No changes	Changes observed – filling visible on outer
		Photo required of failure	
Q	Other observed changes e.g., labels, components, etc	No changes	Changes observed. List any changes observed
		Photos required for failures	

***Brushed and pile fabrics pilling = requirement of Grade 3 at 45 washes increment only**

Table A – Part II – Additional Assessment criteria for PM01 only

ADDITIONAL FOR SOCKS ONLY			
	Assessment	Satisfactory	Unsatisfactory
S1	Yarn breakdown and/or float breakdown (e.g. elastane/backing yarn) - creating holes	OBSERVED PASS – no holes recorded /list any changes observed	FAIL = HOLES RECORDED List any additional changes observed
	(Internal and external assessment of the product required)	Photo required of failure	

S2	Rib/welt change - collapsing/distortion	OBSERVATION with no change to stretch /recovery of welt or rib	OBSERVED change. change to stretch /recovery of welt or rib - change to be assessed by supplier with technologist.
		Photo of failure required	

(Additional product category specific criteria for review in all extended wash increments)

ADDITIONAL FOR PILE AND BRUSHED FABRICS ONLY (applicable to ALL relevant product)		
Assessment	Satisfactory	Unsatisfactory
T. Matting/Consolidation of Fibres (Inside / Outside of garment – see requirements)	Outside Garment 5 washes: 3-4 23 washes: 3-4 32 washes: 3-4 45 washes: 3 Inside Garment: **OBSERVED PASS **HOOD LINING = RECORD PASS/FAIL 5 washes: 3-4 23 washes: 3-4 32 washes: 3 45 washes: 3	Outside Garment 5 washes: < 3-4 23 washes: <3-4 32 washes: <3-4 45 washes: <3 Inside Garment: ** OBSERVED FAIL ** HOOD LINING = RECORD PASS/FAIL 5 washes: <3-4 23 washes: <3-4 32 washes: < 3 45 washes: <3
	Photo of failure required	
ADDITIONAL FOR DENIM ONLY		
Assessment	Satisfactory	Unsatisfactory
Y1. Broken Threads & Broken stitches	Adults: Observed change any broken thread	
	Kids: Anything below 1cm	Kids: Anything over 1cm = FAIL
Y2. Any styles with FRAY detail	Adults: Any changes to FRAY after wash = Observed change	
Y3. Any rip	Adult: Any changes over 5 washes = Observed change	Adult: Changes up to 5 washes = FAIL
Y4. Decrease in Baking/crease effect	Adults and Kids: Any changes after 5 washes would be a failure.	

Table A – Part III – Additional Assessment criteria for PM01 only (Additional product category specific criteria for review in all extended wash increments)

Print / Motif / Flock PRODUCT ONLY	
U. Report any loss of print adhesion	<u>All prints except Plastisol & Flocking.</u> All Wash Intervals Satisfactory; no change or slight Unsatisfactory; moderate, severe, complete <u>Plastisol prints & Flocking.</u> Wash Intervals 1 & 2: Satisfactory; no change or slight Unsatisfactory; moderate, severe, complete
V. Report any cracking	
W. Report any delamination	

X. Report any loss of flocking	Wash Intervals 3 & 4: Satisfactory; no change, slight or moderate Unsatisfactory; severe, complete Photograph of change/failure to be recorded in test report
**Note – Foil print assessment is excluded from extended wash	

**Any printed/flock/motif product – following the 1-5 wash (appearance after wash test method will be tested for PM02 separately)

PM02 - Print / Motif / Flock Durability

1.0 PURPOSE

To define the procedure for measuring the durability of a print on a fabric after washing.

1.1 Introduction/Principle

Printed or flock fabrics are subjected to a prolonged wash in Hoovermatic twin-tub, Durawash or Dynawash machine to determine the loss of print or flock effect. The washed piece is compared with an original and any change expressed as a shade change using grey scales.

1.2 Scope

To assess the durability of prints and flock on woven and knitted textiles.

2.0 DEFINITIONS

- 2.1 Grey Scales as defined in ISO 105: A02.
- 2.2 Makeweight, fabric pieces used to give correct wash load.
- 2.3 D65 artificial daylight - as per Verivide cabinet.

3.0 EQUIPMENT

- Hoover Twin-Tub, Roaches Durawash or Heals Dynawash.
- Polyester Makeweights (300 x 300 mm ± 30 mm, 35 ± 3 g).
- ECE detergent (phosphate type)
- Sodium perborate tetrahydrate
- Balance.
- Thermometer.
- Timer/Clock with Minutes and Seconds.
- Grey Scales ISO 105: A02.
- Verivide Cabinet with D65 Artificial Daylight.
- Overlocking and Lock Stitch Sewing Machines.

4.0 PROCEDURE

4.1 Conditioning and Testing Atmosphere

No special conditions are required.

4.2 Test Specimens

4.2.1 Woven - Cut a square containing the print of flock, a minimum of 300 x 300 mm and overlock the edges. If the sample is small e.g. Motifs or Latex type, sew onto a 300 x 300 piece of cotton fabric or Tea Towel.

4.2.2 Knitted - Cut a specimen 300 x 600 mm containing the print or flock with the long side parallel to the courses and fold in half with the fold along a wale line. Overlock the sample to form a bag with one open end, overlock the raw edges of the open end to prevent unravelling. For small prints or Latex type, support the sample by sewing onto a piece of cotton fabric minimum size 300 x 300 mm.

4.2.3 Garments - if complete garments are available wash whole.

4.3 Method

- 4.3.1 Fill the washing machine to the water line (40 litres).

- 4.3.2 Heat the water to the required temperature $\pm 2^{\circ}\text{C}$. (Check temperature with an independent thermometer).
- 4.3.3 Add 160g ECE Detergent (with phosphate) (4g/L) and 40 g Sodium Perborate (1g/L) to the water and dissolve.
- 4.3.4 Weigh the specimen or garment and make up to a total of 1 Kg with makeweights. Specimens should not exceed half the total load.
- 4.3.5 Place the load in the prepared machine and set to wash for 15 minutes.
- 4.3.6 At the end of 15 minutes, remove the specimen from the machine and rinse once in water at 40C and once in cold water to ensure removal of detergent. Spin to extract the excess water.
- 4.3.7 Dry as per care label
- 4.3.8 When dry assess **the specimens against the original piece under D65 artificial daylight using grey scales A02.**

Note: The wash solution should be changed at regular intervals due to the degradation of the Sodium Perborate or if discoloured by dye.

5.0 EXPRESSION OF RESULTS/CALCULATIONS

No special units used.

Ratings are as per ISO 105: A02.

6.0 Report using the following template.

Ensure all components, including interlinings are assessed. Include photographs of failures in the test report.

	Assessment	Satisfactory	Unsatisfactory
A	Colour change/loss using grey scale assessment (BS EN ISO 105 A02)	4 or better	Less than 4
	If OBA is present, assess sample using Fluorescent Suppressor and report Suppressed grade also.	If different print colours exhibit different degrees of shade change, quote individually	
B	Cross staining i.e. colour transfer on to component parts	4-5	Less than 4
C	Report any loss of print adhesion	Slight or No Change	Moderate or Severe
D	Report any cracking	Slight or No Change	Moderate or Severe
E	Report any delamination	Slight or No Change	Moderate or Severe
F	Report any loss of flocking	Slight or No Change	Moderate or Severe
G	Other observed changes	For record only, not pass/fail	

PM03 – Nap Stability

Additional information for Nap Stability

- Without adding any weight to the spindle, run the machine for 1,000 revolutions.
- Without removing the specimen from the holder, assess each specimen every 1,000 revolutions as follows:
 - a. No change in appearance – continue with the test for a further 1,000 revolutions.
 - b. Change in appearance **without** the base fabric visible – continue with the test for a further 1,000 revolutions.
 - c. Threadbare appearance **with** the base fabric visible (complete loss of nap) - End the test at this point and record the number of revolutions required to reach this stage.
- Continue the test, assessing the specimens at 1,000 intervals until the end point is reached at 4,000 revolutions.

PM04 – Dimensional and Bra Wire Casing Stability

1) PRINCIPLE

- 1.1 To determine the dimensional stability of under wired bras and corsets and the stability and strength of the wire casings, by giving the bra or corset a garment cleanse. The bra or corset under wire casing is then assessed for shrinkage and the bra or corset under wires are assessed for distortion.

2) APPARATUS, REAGENTS and CONSUMABLES

- 2.1 Wascator washing machine
- 2.2 Polyester Make-weights
- 2.3 IEC Detergent
- 2.4 Sodium Perborate
- 2.5 TAED
- 2.6 Drying Racks
- 2.7 Domestic Tumble Dryer

3) SPECIMENS

- 2 bra sizes should be tested. A small cup and a large cup.

4) SPECIMEN PREPARATION

- 4.1 Prepare the samples for a Dimensional Stability test according to the Marking and Measuring standard BS EN ISO: 3759.
- 4.2 Push the bra wire to one end of the casing and at the other end measure the gap between the end of the wire and the end of the casing. Record this measurement on both cups of each bra.

5 TEST PROCEDURE

- 5.1 Weigh the test specimens and make up to 2kg wash load using make-weights.
- 5.2 Select a Simulated hand wash as per BS EN ISO 6330:2012 on the Wascator washing machine. Add 38.5g of IEC detergent, 10g of Sodium perborate and 1.5g of TAED in a pre-dissolved liquor to the washing machine and run for one cycle.
- 5.3 Flat dry the specimen.

6 DIMENSIONAL CHANGE

- 6.1 After washing and drying, condition the sample and calculate from the original dimensions, the differences in dimensional change as a percentage.
- 6.2 Assess the casing for any holes punched through by the bra wires
- 6.3 If the wires have not punched through, then repeat the procedure as stated in 4.2.
- 6.4 Assess the bra wires for any distortion.

7 REPORT

- 7.1 Report the results for each bra size separately.
- 7.2 Report any dimensional changes that have occurred.
- 7.3 Report if the bra wire has punched through. If it has, it will not be necessary to report the distance from the end of the bra wire casing.
- 7.4 Report the distance in mm from the end of the bra wire to the end of the casing for each bra cup before and after washing
- 7.5 Report if the bra wires have become distorted.
- 7.6 Report any other changes that have occurred

PM05 – Fibre Shedding / Pile loss

1. Purpose:

The purpose is to determine the level of pile that is removed from the surface of a pile fabric whereby loose fibre is removed using pressure sensitive tape and a constant rate of extension (CRE) machine. Only applicable to fabric with pile or raised surface longer than 3mm.

2. Application:

This method to textile material.

3. Required equipment and accessories:

3.1 Equipment:

- CRE machine with gauge length 50mm±1mm and rate of extension 500±10mm/min.
- Clamping device full face jaws (25 mm × 40 mm minimum)
- Pressure Sensitive Tape Ref 3M.853 (25mm wide)
- 1kg cylindrical weight (30mm to 50mm wide to ensuring contact is consistent over the whole test area).
- Calibrated Steel Ruler.
- Card template measuring 210mm x 150mm with a rectangular hole cut in the centre measuring 100mm x 50mm.
- Card strips measuring 50mm x 80mm with a pen line marked 10mm in from the shorter edge. -Overlocker

4.3 Preparation of Samples

- 4.3.1 One specimen with the dimensions of a minimum of 100mm x 120mm, note that the longer length must be in the direction parallel to the lay of the pile, then overlock all sides of the sample to prevent loose pile loss.

5. Procedure

- 5.1 Condition the specimens for a minimum of four hours at 65% ± 2% relative humidity and at a temperature of 20°C ± 2°C.
- 5.2 Choose the relevant test method within the CRE machine's software with the parameters stated in 3.1 above.
- 5.3 Lay card template on the sample
- 5.4 Cut a 100mm strip of pressure sensitive tape and apply to the 10mm line on the card strip, apply the remaining tape to the pile surface through the hole in the template centrally along the specimen.
- 5.5 Press lightly into position and roll the 1kg cylindrical weight smoothly once up and down over the test area. Do not press down excessively when rolling the cylinder. (See Figure 1).




(Figure 1)

5.6 Remove the template then clamp the bottom of the fabric into the lower jaws of the tensile testing machine and clamp 60mm of the cardboard lip into the top jaws.

5.7 Set the tensile testing machine in motion at a speed of 500mm/min. The tape will begin to be removed from the fabric; continue until the tape is completely removed.

5.8 The test must then be manually stopped - ***Take care when tape has been fully peeled away from the specimen as you will have to manually stop the test and catch the card strip before it falls off the floor and potentially picks up dirt/fibres***

Note that the card strip faces downwards but needs to be pulled back on itself.. (See Figure 2)

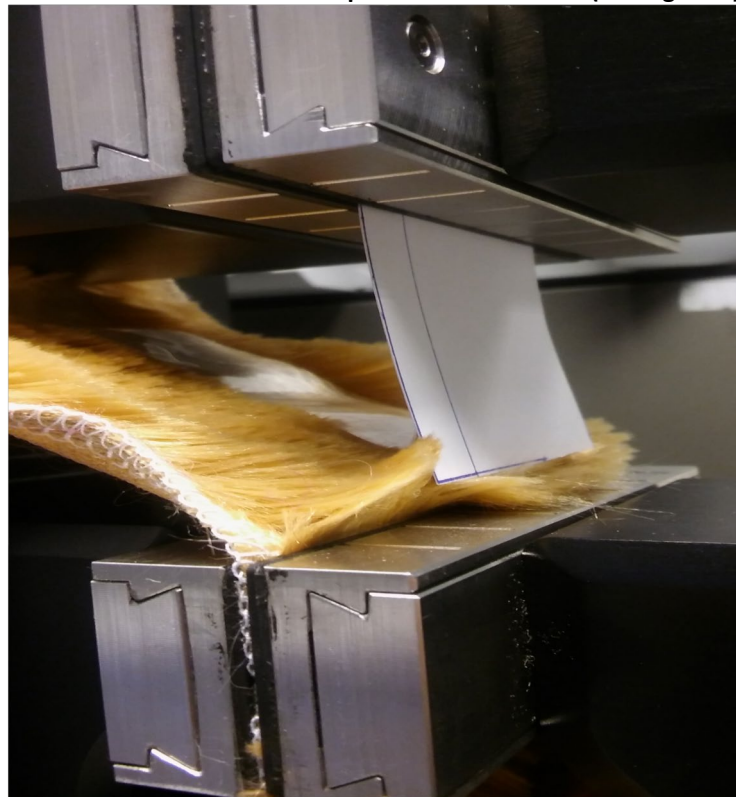

(Figure 2)

5.9 Mount the tape onto white or black card according to the colour of the pile and assess the amount of fibre stuck to the tape. (For dark coloured fabrics, use white card and vice-versa). (See Figure 3).



(Figure 3)

5.10 Repeat steps 5.4 – 5.9 a further 2 time on the same test area of the sample so you have 3 samples in total.

6. Evaluation

6.1 Visually grade using the below:

The level of fibre shedding grades	Visual reference guide for Slight, Moderate and Severe
None - Grade 5 Slight - Grade 4 Moderate - Grade 3 Significant - Grade 2 Severe – Grade 1 Pass level is Grade 4 and above	

7. Report

7.1 The test report should contain the following information:- Test Name:

Fibre shedding

- Sample Description
- Grade for all 3 samples: e.g. “Moderate Shedding”

PM06 – Chenille Pile Loss

1.0 Purpose

To assess the loss of pile and appearance of the fabric.

2.0 Apparatus

- 2.1 Martindale abrasion machine (as specified in BS EN ISO 12947-1)
- 2.2 Neoprene rubber
- 2.3 Ponep P42528 from Messmer
- 2.4 Stiff brush

3.0 Conditioning and Testing Atmosphere

After bone drying, specimens shall be tested after conditioning in the standard atmosphere for testing, i.e. a relative humidity of $65 \pm 2\%$ and a temperature of $20 \pm 2^\circ\text{C}$ for 16 hours.

4.0 Test Specimens

- 4.1 Samples are tested in original and washed conditions
- 4.2 Cut 3 specimens for each condition. The diameter of the test specimens shall be 150mm (preferably using cutting dies)
- 4.3 Overlock the edges of each specimen.
- 4.4 Dry the specimens in an oven at 105°C for 4 hours, condition in a relative humidity atmosphere of $65 \pm 4\%$ and a temperature of $20 \pm 2^\circ\text{C}$ for 16 hours.
- 4.5 Weigh the conditioned specimens (to 1g accuracy) and record the weight

5.0 Procedure

- 5.1 Mount the specimens on to the base of the Martindale test beds, over standard felt.
- 5.2 In the abrasion head, mount a piece of the rubber 38mm in diameter. Do not insert any foam behind the rubber. Place the abrasion heads over the test beds with the spindles.
- 5.3 Set the machine for 100 cycles
- 5.4 Examine the specimens for any pile loss or balding after removing any residual fluff with a soft brush. Record any visual effects observed.
- 5.5 Continue rubbing the specimens, examining at 100 cycle intervals until a total of 1000 cycles has been completed, recording any observations.
- 5.6 Bone dry the tested specimens at $105 \pm 3^\circ\text{C}$ for a minimum of 4 hours
- 5.7 After bone drying, the specimens shall be conditioned in a relative humidity atmosphere of $65 \pm 4\%$ and a temperature of $20 \pm 2^\circ\text{C}$ for 16 hours.
- 5.8 Weigh the conditioned specimens (to 1g accuracy) and record the weight

6.0 Grading Appearance and Recording

- 6.1 Determine the weight and percentage of pile loss using the weights recorded in 4.5 and 5.8
- 6.2 Determine the mass per unit area of the original fabric (this is useful in evaluating the pile loss comparatively)
- 6.3 In addition to the observations made during the test, view the samples
 - Over an illuminated table (transmitted light) to assess degree of balding
 - Using a pilling assessment unit (reflected light) to assess surface change

Using the descriptions:

- None – Grade 5
- Slight Loss – Grade 4
- Moderate Loss – Grade 3
- Significant Loss – Grade 2
- Complete/Sever Loss – Grade 1

- 6.4 Mount the specimens between two pieces of card in such a way that they can be placed over an illuminated Surface for viewing pile loss

7.0 Report

- 7.1 The pile loss in percentage & Weight (information to help validate above visual assessment)
- 7.2 Mass per unit area
- 7.3 The visual assessment for both transmitted and reflected light after 1000 cycles
- 7.4 Any significant observations made at 100 cycles examination intervals

Comment if pile loss is in localized areas or any other observations such are pile coming off in hands/clothes with general handling of product:

PM07 – Back pocket application strength

1.0 Purpose

Determine the load at which damage is caused to the back pocket area of denim jeans for assessment against specification.

2.0 Apparatus

- Constant-rate-of-extension tensile testing machine (CRE)
- Clamps/Jaws, suitable for the CRE equipment, for securing the test specimen.
- Dimensions: Front clamps/jaws 25x25mm, Back clamps/jaws 25x25mm (25x50mm maximum).
- A means of conditioning the specimens prior to test. BS EN ISO 139:2005 Textiles – Standard atmospheres for conditioning and testing:
- Standard atmosphere: 20.0°C 65%RH
- Template for specimen preparation: 50mm height x 120mm width with a central hole for location.

3.0 TEST SAMPLES

- Prepare the quantity of specimens available / required using the template described above with the central hole located over the top corner of the pocket and the long direction parallel with the weft threads of the main jean fabric.
- Mark a horizontal line 12.5mm from the pocket corner to enable consistent sample test placement.

4.0 TEST PROCEDURE

- a) Condition the specimens for a minimum of 4 hours

- b) Set the CRE on a programme to determine force & elongation. (BS 13934-1 is suitable)

Programme settings:

Gauge Length: 40mm

X Head Speed: 100mm/min (pre-set by the programme)

Load: 150N


- c) Mount the test specimen with the side edge of the top and bottom front (25 x 25mm) jaws on the marked location line, corner of pocket will be central to the test area. One jaw will secure two layers of fabric, the main jean fabric and pocket; the second jaw will secure main jean fabric only. Run CRE programme

5.0 Report

The load applied to cause damage, fabric breakdown / tear, to the test area.
Type of damage i.e. Breakdown at pocket application, jaw or 'other' location.

Fig 1

Sample preparation options:

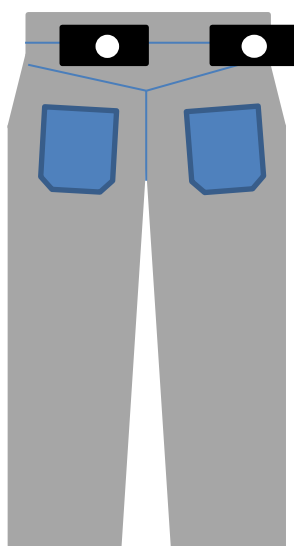


Location
line



Pocket edge:

Fig 2

Specimen Mounting.

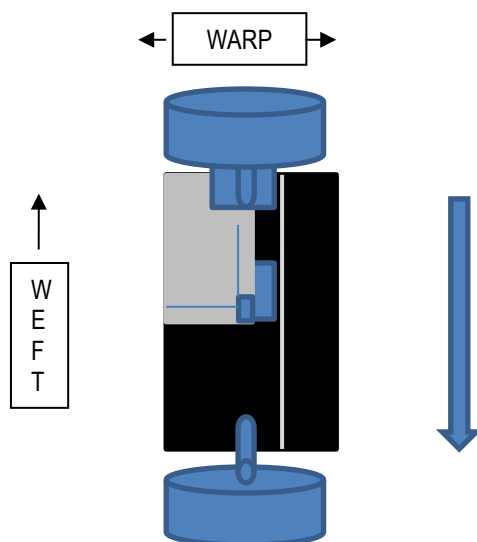



Load application

PM08 – Belt loop application strength

1.0 Purpose

Determine the load at which damage is caused to the belt loops of denim jeans for assessment against specification. The back loops are primarily subjected to stress during normal wear.

2.0 Apparatus

- Constant-rate-of-extension tensile testing machine (CRE)
- Clamps/Jaws, suitable for the CRE equipment, for securing the test specimen.
 - Dimensions: Front clamps/jaws 25x25mm, Back clamps/jaws 25x25mm (25x50mm maximum).
- A means of conditioning the specimens prior to test. BS EN ISO 139:2005 Textiles – Standard atmospheres for conditioning and testing.
 - Standard atmosphere: 20.0°C 65%RH

3.0 TEST SAMPLES

Select and prepare the quantity of specimens available / required.

Cut the belt loop close to the application point either at the top or bottom whichever is to be tested i.e. the strength of application to the waistband or to the main body of the jean.

4.0 TEST PROCEDURE


- a. Condition the specimens for a minimum of 4 hours.
- b. Set the CRE on a programme to determine force & elongation. (BS 13934-1 is suitable)
 - i. Programme settings:
 - Gauge Length: 40mm (variable due to belt loop length)
 - X Head Speed: 100mm/min (pre-set by the programme)
 - Load: 150N
- c. Mount the test specimen with the cut end of the belt loop in the top jaw and a point just below the attached belt loop in the bottom jaw. Run CRE programme

5.0 Report

The load applied to cause belt loop detachment failure, fabric breakdown / tear.

Type of damage i.e. Breakdown at belt loop attachment, surrounding fabric, or jaw.

Fig 1
Sample preparation options:

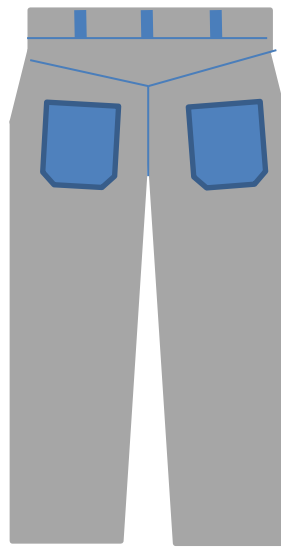

Waist
Band




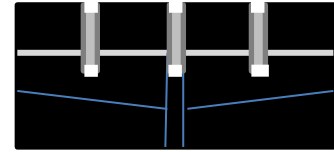


Fig 2
Specimen Mounting.
Testing bottom application

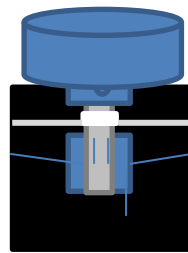

Load application

Fig 3
Specimen Mounting.
Testing waistband application

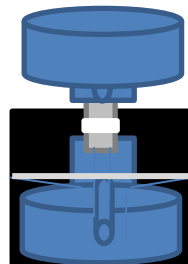

Load application

PM22 – Heat Conductivity on metal trims

Safety

Care should be taken and good laboratory practice adhered to at all times.

1.0 Definition

To record the temperature on trims used on swim wear. The test procedure may also be applied to other solid materials.

2.0 Equipment

- Infrared heat lamp
- Alcohol-in-glass thermometer
- Recording thermometer with thermocouples
- Infrared hand-held thermometer
- Air block (or other building material block to simulate natural rock surface)
- Blue or white tack
- Timer
- Marker pen
- Draught free area

3.0 Test Procedure

- 3.1 Place the air block from draughts, opening doors and windows etc.
- 3.2 Place stick thermometer held in retort stand, approximately 10mm away from block..
- 3.3 Fix test piece to air block by either balancing directly onto it or by using a tiny amount of tack to ensure it stays in place.
- 3.4 Mark on the test piece the point that the temperature will be taken
- 3.5 Switch on the lamp, and heat until the glass thermometer reaches the desired temperature. The normal specified temperature is 40°C & 65°C, but other temperatures may be specified as required by the client.
- 3.6 When the desired temperature is reached, apply the test sample to the block and start the timer. A time of 30 minutes is normally specified but other times may be used as specified by the client
- 3.7 Fix test piece securely to the breeze block as determined in 3.3 above.
- 3.8 After the specified time, shield the sample from the infrared heat lamp and record the temperature of the sample the block and the thermometer.
- 3.9 Continue to heat the sample, recording the temperature every 30 minutes up to a total of 2 hours, or the maximum duration specified by the client.

Interpretation of results

The results are for information only. There is no PASS or FAIL criteria for this test.

4.0 Results

The following results were recorded:

IR Heat source at 40°C

Time (mins)			Thermo	Block
30				
60				
90				
120				

IR Heat source at 65°C

Time (mins)			Thermo	Block
30				
60				
90				
120				

Using this arrangement the XXXXXX were exposed for a total duration of XXXX hours and XXXX minutes, with measurements taken periodically using a contact thermocouple.

END OF REPORT

PM23 – Elastic extension and Modulus test

1. Use constant rate extension tester Instron, Quick or Hounsfield
2. Cycle speed 500mm/min
3. Load using the relevant test load specified in the table.
4. Sample size cut 150 mm by 50 mm. If the lace or elastic is less than 50mm wide then use actual finished width.
5. Set Jaws to give test area 100 mm x 50 mm
6. Modulus figure to be taken at 40% stretch under second upper curve
7. Stretch to be taken at the relevant test load specified in the table.
8. Results quoted as average of three cycles

	End Use	Elastic Width (mm)	Test Load	Extension (%)	Modulus gm (@ 40% extension)
Bra Elastics	Shoulder Straps / suspender straps	8	3.6kg	60-80	400-800
		10			450-1000
		13			600-1200
		16			750-1400
		19			900-1600
		23			1600-3200
		26			1800-3400
	Under band / Underarm / top & bottom wing	8	2.5kg (Sports Bra – all widths @ 4.25kg)	125-175	100-190
		10			150-250
		12			180-290
		14			230-380
		16			280-430
		18-20			330-540
		22/24/26			350-560
Brief Elastics & Bra stabilising elastics	Fabrics WITH elastane	3-5	1.5kg	120-180	60 - 90
		6			82-112
		8			96-120
		10-12			120-150
		13			130-162
		14			140-175
		15			150-188
		16	2.5kg		160-200
		17			170-213
		18			180-225
		19			190-238
		20			200-250
		21			210-263
		23			230-288
		24			240-300
		25-29			250-313
	Fabrics WITHOUT elastane	3-5	1.5kg		56 - 86
		6			74-108
		8			84-117
		10-12			100-130
		13			104-140
		14			112-140

		15	2.5kg		120-150
		16			128-160
		17			136-170
		18			144-180
		19			152-190
		20			160-200
		21			168-210
		23			184-230
		24			192-240
		25-29			200-250
Brief Elastics	ALL fabrics Wide waist elastics	30-35	4.5kg	140-160	250-450
		36-40			300-500
		40-50			500-1050 tbc

PM26 – Puncture Resistance of Bra Wire Casing

Scope

This In-House Test Method describes the method of test in order to determine the puncture strength of bra wire casing fabric when supplied in its finished tubular form.

Principle

Test specimens are prepared and tested as specified within this test method in order to achieve a performance assessment of the product/fabric as described within the scope.

Equipment

A constant rate of traverse tensile testing instrument that meets the following requirements

Load cell with appropriate load cell capacity that would fall within 10 – 90% of the applied force

100mm per minute constant rate of traverse.

Pneumatically operated sample jaw with a pair of rubber jaw faces that give an area of contact when closed together of 75mm x 25mm.

Bra wire jaw assembly designed to hold a prong in such a way that (3.7) can be met. Standard prong (See Annex A)

Initial separation between the pneumatic jaw faces and tip of the prong of 100mm.

Metal ruler with mm graduations

Scissors

Conditioning

The sample is conditioned in the standard condition of temperature of $20 \pm 2^\circ\text{C}$ and the relative humidity $65 \pm 4\%$ for a minimum of 4 hours

Health & Safety

As recommended by your H&S officer

Preparation of test specimens/ materials

Five specimens of bra casing fabric, 300mm long.

If in tubular form, slit the reverse of the casing (One layer) down the centre to the midway point ensuring the face is not damaged.

Cut away approximately 30mm of reverse casing at this point. See Annex B for specimen diagram.

1. **NB:** Face is referring to the side of the specimen in contact with the skin.
2. **WET TEST** (if specified) soak the fabric specimens in a relaxed (open) state for 15 minutes in distilled water at 20°C . Blot off excess moisture with a paper towel and test whilst wet. Conditioning is not required if testing wet.

Test Procedure

Ensure that the testing equipment is set up exactly as described under 'Apparatus' above and calibrated according to the manufacturer's instructions.

Position the specimen so that the area on the reverse side, which has been cut away, is over the end of the prong and the prong is in contact with the back side of the face .

Secure the two ends of the specimen in the pneumatic jaw reverse sides together. The specimen should be positioned centrally and vertically ensuring that no tension is applied.

Set the machine in motion and measure the load required to penetrate through the face area of the specimen. (See Annex C)

Repeat this procedure for the remaining four specimens.

If a specimen slips through the jaws, it should be discarded, and a fresh specimen tested. This usually occurs because the specimen has been mounted incorrectly, or the jaws were incorrectly tightened.

Reporting of Results


Report the range of results.

Report the average result to the nearest 0.5kg.

Requirements/Guidelines

Minimum 26 Kg

Annex A

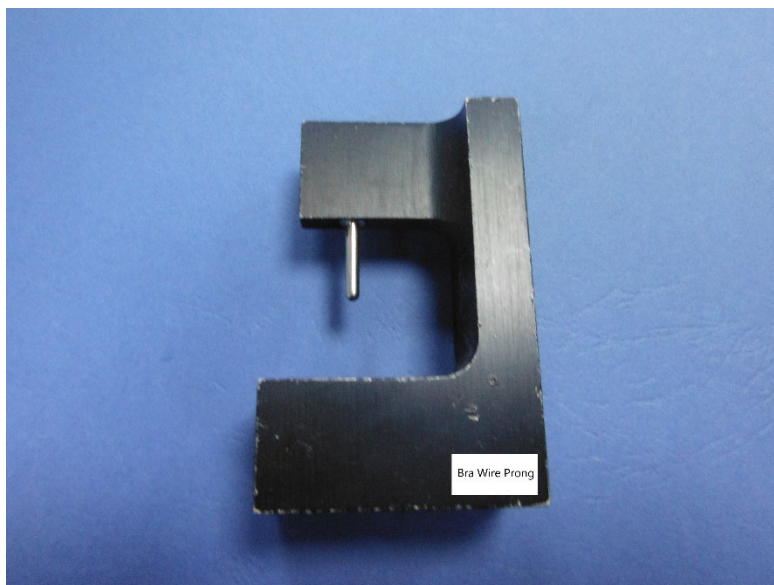

Standard Prong specification.


Diameter at point: 2.6mm

Protruding Length: 15mm

The radius of the tip and the adjacent diameter is polished to 0.1mm Ra (micrometers Roughness average).

Annex B

Diagram of specimen after preparation

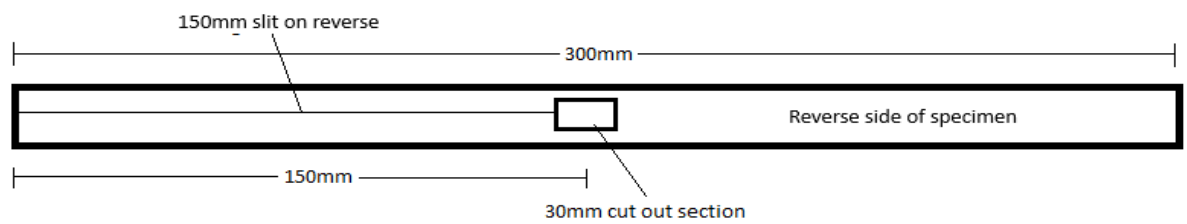

Annex C

Specimen mounted in jaws after test has been performed. The prong has penetrated through the face of the bra wire casing.



Table of Change

Version	Details of Change	Date of Change	Authorised by
1	Wash instruction for Garment Appearance after Multiple Wash PM01 test changed from Wash as per Care Label to;- For washable products;- For products with care labels set at 30°C or 40°C test at 4N @ 40°C Dry per Care Label. For products with care labels set at 50°C test at 5N ^h @ 50°C Dry per Care Label. For products with care labels set at 60°C test at 6N ^h @ 60°C Dry per Care Label	25 th Feb 2015	Janette Cox
2	Adult Lingerie Table - In Phthalates section, reference to bra gel inserts added and TRA required for any lingerie tape	29 th Jun 2015	Nicola Twist
2	PM01 - Garment Appearance after Multiple Wash - Now includes measurements after 1 st wash and name changed to Product Appearance Assessment after Multiple Wash	29 th Jun 2015	Nicola Twist
2	Extension and Modulus test removed from the manual	29 th Jun 2015	Nicola Twist
3	Residual Extension requirements and loads changed for Swimwear and Lingerie	5 th Oct 2015	Mark Pennington
3	Tear strength requirements now include cellulosic blends	5 th Oct 2015	Mark Pennington
3	Following US tests added to Performance wear Promotional Claims table Water Vapor Transmission of Materials Vertical wicking of textiles Absorbency of textiles Anti Bacterial Claims - Antibacterial Activity Assessment of Textile Materials: Parallel Streak Method	5 th Oct 2015	Mark Pennington
3	Feather and Down tests added to Outerwear Specs	5 th Oct 2015	Mark Pennington
3	Mass per Unit Area removed from True Knitwear tables	5 th Oct 2015	Mark Pennington
3	Additional information added on how to perform Security of Attachment	5 th Oct 2015	Mark Pennington
3	Seam Slippage requirements reduced by 20N each and comments added for contrast warp & weft threads	5 th Oct 2015	Mark Pennington
3	Denim – physical testing to be performed on washed panel	5 th Oct 2015	Mark Pennington
3	Tear Strength requirement reduced by 100cN each	5 th Oct 2015	Mark Pennington
3	Information added on how to report Pilling	5 th Oct 2015	Mark Pennington
3	Residual Extension – now test in direction of elastane only	5 th Oct 2015	Mark Pennington
3	Children's spec now combined	5 th Oct 2015	Mark Pennington
3	Cycles added for Crumple Flex Method	5 th Oct 2015	Mark Pennington
3	Spirality – Method C added and comments added about following Wash Procedure	5 th Oct 2015	Mark Pennington
3	Salt Water Corrosion test – requirements changed to No Corrosion after 24 hours	5 th Oct 2015	Mark Pennington
3	PM01 - for Bra's now to be tested a 4H	5 th Oct 2015	Mark Pennington
3	PM04 – now to be tested at 4H	5 th Oct 2015	Mark Pennington
3	New tables added;- Leather & Suede Products Baby Bibs, Blankets, Hats, Mittens & Muslin Cloths	5 th Oct 2015	Mark Pennington
3	PM02 – method of drying changed and assessment table changed	5 th Oct 2015	Mark Pennington
3	Residual Elongation requirements for knitted fabrics changed to 10%	5 th Oct 2015	Mark Pennington
3	PTA14 & PTA15 - Additional testing comments added to 16 CFR 1610	5 th Oct 2015	Heather Ball
3	Amendments made to Torque and Tension and Small Parts Restrictions tests	5 th Oct 2015	Heather Ball
4	PTC22 & PTC23 – Taber abrasion requirements added	18 th Feb 2016	Heather Ball
4	PTC18 – new instruction added for Residual Elongation - >11% elastane 25N load	18 th Feb 2016	Heather Ball
4	Requirements for Short Chain Chlorinated Paraffin (SCCP) Content now changed to Not Detected to match the RSL manual	18 th Feb 2016	Heather Ball
4	Information added into Introduction on Composite Testing	18 th Feb 2016	Heather Ball
4	Test name changed for Sun Protection test and method number changed to EN13758-2 – originally a typo	18 th Feb 2016	Heather Ball
4	New IHTM added for Heat Conductivity	18 th Feb 2016	Heather Ball

Version	Details of Change	Date of Change	Authorised by
4	PM02 - Print Durability – requirement in method changed to mirror that of requirements in test packages	18 th Feb 2016	Heather Ball
4	Additional comments added for testing bra cups for phenolic yellowing	3 rd Mar 2016	Heather Ball
4	Phthalate test removed from all adult test packages and requirements amended to mirror RSL manual	3 rd Mar 2016	Heather Ball
4	Fastness to Saliva requirement changed to 4	3 rd Mar 2016	Heather Ball
4	PTC09 & PTC12 - Dry Cleaning requirements added to	3 rd Mar 2016	Heather Ball
4	Formaldehyde requirements updated to mirror RSM	3 rd Mar 2016	Heather Ball
4	Print Durability requirements amended	3 rd Mar 2016	Heather Ball
4	PTC20 – Appearance assessment requirement removed from Dimensional Stability test	3 rd Mar 2016	Heather Ball
4	Spray Rating method updated	3 rd Mar 2016	Heather Ball
4	PTC41 – Adult ties – new table added to manual	3 rd Mar 2016	Hannah Williamson
4	Phthalates for REACH Annex XVII requirement amended to include 0.1% by mass	3 rd Mar 2016	Heather Ball
5	PTC30 EN71-2 BRC method replaced with EN71-2 PTC18 >11% elastane 25N load added	5 th May 2016	Hannah Williamson
5	PTC20 – Remove dimensional stability to washing from hosiery	14 th June 2016	Ashley Morgan
5	PTC28 – SCCP updated in line with new regulations	14 th June 2016	Ashley Morgan
5	EU Security of Attachment on children's clothing	5 th July 2016	Ashley Morgan
5	US Security of Attachment on children's clothing	5 th July 2016	Ashley Morgan
5	Added Moisture Regain comment to all fibre composition	28 th July 2016	Ashley Morgan
5	CE marking comment added to the manual introduction page	23 rd September	Hannah Williamson
5	Added Grade 3 for Neon/Fluorescent shades	4 th October 2016	Ashley Morgan
6	PTC 13 & PTC 14 – Updated Heat Conductivity test from 'When requested by technologist' too 'Only applicable to swimwear items with metal components in contact with skin'	20 th December 2016	Ashley Morgan
6	PTC01,02,05,06,09 and 010 include brush backed sweats in CFR 1610	7 th March 2017	Ashley Morgan/Asif Shah
6	PTC09 & PTC010 - add thermal requirement	7 th March 2017	Ashley Morgan/Asif Shah
6	PTC027 - Peel strength Touch and close fasteners	8 th March 2017	Ashley Morgan/Asif Shah
6	PM01 - Update to IEC(A) and include TAED	8 th March 2017	Ashley Morgan/Asif Shah
6	PTC028 - Chromium VI Test method updated to include ageing	8 th March 2017	Ashley Morgan/Asif Shah
6	PM23 – Method added to manual and PTC18 and PTC20	8 th March 2017	Ashley Morgan
7	PTC 17 – Clarification on tight fit and lettuce edge garments following CPSC information/interpretation.	27 March 2017	Ashley Morgan/Asif Shah
7	Added PVC Migration	04 th April 2017	Ashley Morgan
7	Remove PVC Migration	10 th July 2017	Ashley Morgan
8	PM05 - References to picture grading removed	31 st Jul 2017	Carly Macey
8	All Packages – Mass per unit area negative tolerance removed. Low weight fabrics not accepted.	3 rd Aug 2017	Eimear Hawker
9	Changed headings to US/EU Compliance and Mandatory	31 st August 2017	Mark Pennington.
9	Added Fiber composition and formaldehyde to PT10 (accidentally removed in last update)	20 th September 2017	Mark Pennington.
9	Moved Adults security of attachment from EU Compliance to Mandatory	20 th September 2017	Mark Pennington.
10	EN71-2 BRC flammability added for costumes	19Oct2017	Mark Pennington.
10	BS 7907 changed to CEN/TR 16792 for security of attachment in all relevant packages	19Oct2017	Carly Macey
10	PTC03 and PTC04 footnote added for wash panels .PM01 added	6 th Nov 2017	Carly Macey
10	Residual elongation widths clarified.	6 th Nov 2017	Carly Macey
10	PM05 typos rectified/reporting clarified with reference picture added.	6 th Nov 2017	Carly Macey

Version	Details of Change	Date of Change	Authorised by
10	Wording added to children's test packages about final product testing	6 th Nov 2017	Carly Macey
10	PM02 Print durability section added for other observations	6 th Nov 2017	Carly Macey
10	Colourway test package added to Introduction	6 th Nov 2017	Carly Macey
10	PTC18 wording clarified to remove 'children's products only' for water wash.	7 th Feb 2017	Nirosha Witana
11	Detox commitment the APEO/AP, PFCs and extra Phthalates added throughout the test packages.	9 th Feb 2018	Carly Macey/Charlotte Pumford
11	PTC29 Stability to wash shrinkage amended to 10-12%	9 th May 2018	Emily Brocklebank / Helen Colebourn
11	PTC29 Stability requirements aligned with PM01	22 nd June 2018	Emily Brocklebank / Helen Colebourn
12	PTC29 Muslin Cloths moved to Nursery Manual	18 th Sept 2018	Hannah Williamson/ Helen Colebourn
12	PCT03/PCT04 Residual Elongation and Extension updated	9 th Oct 2018	Jasmine Lauer/ Helen Colebourn
12	All tables Mass per unit area amended to -5%/+5% tolerance	9 th Oct 2018	Jasmine Lauer/ Helen Colebourn
12	PCT29 Security of attachment – labels added	29/10/18	Rachel Lindsay/Helen Colebourn
12	APs and APEOS all tables: amend to Applicable to all fabric types. Test only main material/base fabric. Trims do not need to be tested.	2/11/18	Hannah Williamson/ Katie Savage /Helen Colebourn
12	PTC03 and PTC06 Colourfastness to chlorine bleach added	2/11/18	Service Provider Partnership Notes
12	PTC07 Wet Rub requirement reduced to grade 3 to be in line with other packages	2/11/18	Service Provider Partnership Notes
12	APs and APEOS removed from composite testing at beginning of manual	2/11/18	Service Provider Partnership Notes
12	PTC07/PTC08 removed clause test leggings only	15/11/18	Helen Colebourn
12	Spirality updated to be ISO 16322-2 for fabrics and ISO 16322-3 for garments	14/1/19	Helen Colebourn following meeting notes 9/1/19
12	Residual Elongation Method updated PTC03 & PTC04	15/2/19	Eimear Hawker/Hannah Williamson
12	Antimicrobial testing when claimed added to socks	15/2/19	Notes from meeting held 12/2/19
12	Zip standard updated to BS EN 16732 throughout	15/2/19	Notes from meeting held 12/2/19
13	Chemical requirements removed and added to Chemical Manual	17/6/19	Hannah Williamson
13	New Instruction and Golden Rules Added	17/6/19	Hannah Williamson
13	PM23 Strap strength aligned to be 3.5kg and missing wide elastic requirement added to testing table	8/11/19	Alison Chance
14	PTC18 Tear Strength comments updated to match all other tables	15/6/20	SP Meeting 10/6
14	PTC05 Added Stability to Dry Cleaning	15/6/20	SP Meeting 10/6
14	PM05 added to Leisurewear, nightwear and socks tables. Only applicable for brushed back or pile fabrics under 10mm	15/6/20	SP Meeting 10/6
14	Colourfastness to Light , delete N/A white and cream for nightwear	15/6/20	SP Meeting 10/6
14	Colourfastness to Dye Transfer in Storage added to bra packages	15/6/20	SP Meeting 10/6
14	PTC16&17 Nightwear to include C/F to perspiration, extended US method for C/F to water, C/F to vinyl rubbing and C/F to hot pressing. Wet rub to be minimum 3-4.	15/6/20	SP Meeting 10/6
14	PTC05/PTC06 /PTC15 BS 20811 changed to EN ISO 811	15/6/20	SP Meeting 10/6
14	All childrenswear tables ASTM F 1816 updated to 2018 version	15/6/20	SP Meeting 10/6
14	Standardise Comments/Requirements of Residual Elongation	15/6/20	SP Meeting 10/6
14	Weights for Lightweight Medium weight and heavy weight fabrics updated	15/6/20	SP Meeting 10/6
14	PTC18 Added requirements for non-functional lace	15/6/20	SP Meeting 10/6
14	PM23 Added shapewear tables	15/6/20	SP Meeting 10/6
14	Torque and Tension aligned with Toy Manual	15/6/20	SP Meeting 10/6

Version	Details of Change	Date of Change	Authorised by
14	PTC32 and PTC33 Barrier masks added	24/6/20	Hannah Williamson/ Helen Colebourn
14	PTC01 Martindale Abrasion Shade change amended to 3/4 for printed fabrics. Comments updated for printed fabric requirements	02/09/20	Georgina Knox
14	PTC03/04 Martindale abrasion Shade change removed for 5000 revs and removal of wording to white and cream fabrics	02/09/20	Georgina Knox
14	PTC32 and PTC33 Barrier masks BFE, PFE and Differential Pressure to be tested after 5 washes	5/11/20	Emily Brocklehurst
15	PLEASE NOTE: Hong Kong's U.S. Exports to be Labelled "Made in China". Added to Introduction	2/2/21	SP Meeting 20/1/21
15	PTC16&17 CF to Hot Pressing add to requirements 'Dry - Grade 4 Fabric and Cotton Lawn'. Amend Comments to read 'Not applicable to White/Cream Fabrics. Applicable on all fabric bright/dark colourways. Applicable on all printed fabrics	2/2/21	SP Meeting 20/1/21
15	PTC16&17 CF to PVC Migration amend comments box to read 'Applicable on all fabric bright/dark colourways. Applicable on all printed fabrics.	2/2/21	SP Meeting 20/1/21
15	All Kidswear Packages- Updated methods for security of attachment	2/2/21	SP Meeting 20/1/21
15	CF to Light – removed N/A White and cream from all packages	2/2/21	SP Meeting 20/1/21
15	PTC20 - CF to PVC Migration – amend Comments to read 'Not applicable to White/Cream fabrics. Applicable to all tight 200 denier and above. Applicable on all coated fabrics	2/2/21	SP Meeting 20/1/21
15	PTC20 - Add CF to Hot Pressing requirements as PTC16 & 17. Comments to read 'Not applicable to White/Cream fabrics. Applicable to all tight 200 denier and above.	2/2/21	SP Meeting 20/1/21
15	All childrens products Security of attachment to be on all ages	13/4/21	Helen Colebourn BV
16	pH and Formaldehyde testing removed as covered in Chemicals Manual	20/4/21	SP Meeting 15/4/21
17	Spirality Standardized at 5%	8/6/21	Georgie Knox 6/6/21
17	PTC09/PTC10 Pilling statement amended	8/6/21	Georgie Knox 6/6/21
17	PTC09/PTC10 Amend wording for fibre shed	8/6/21	Georgie Knox 6/6/21
17	Luxury Animal Fibre requirement added to all applicable packages	22/6/21	Georgie Knox
18	PM01 method is updated	20/10/21	J Wilson/V Swain
18	Dimensional Stability removed on all tables as incorporated into PM01	20/10/21	J Wilson/V Swain
18	Denim wash updates added to Denim Tables PTC03 and PTC04	20/10/21	J Wilson/V Swain
18	All Colourfastness testing to specify LYOW ® multifibre strip	20/10/21	J Wilson/V Swain
19	PM23 Amended	4/2/22	Uliana Radionova
19	New PM01 added with Primark Cares Multiple Wash	25/2/22	Jonty Wilson
19	New PTC03 added with Primark Cares Multiple Wash	25/2/22	Jonty Wilson
19	New PTC04 added with Primark Cares Multiple Wash	28/2/22	Jonty Wilson
20	PTC03 and PTC04 CEN TR 17394-4 added	29/3/22	Johanna Mantynen
21	PTC18 requirements for PM23 reworded	6/5/22	Dionne Flanagan
22	PM01 requirements reverted back to V17 except for denim	9/6/22	Uliana Radionova
22	PM23 Shoulder Strap 8mm 3.6kg Modulus stop should be 350-850	9/6/22	Uliana Radionova
22	PTC29 Crumb catchers to be tested as per Nursery Manual	9/6/22	Uliana Radionova
23	SGS, Hohenstein and UL added to approved labs and Timber policy added to Golden Rules	7/7/22	Uliana Radionova
23	PM01 Polyester Makeweights amended to (200 x 200 mm ± 40 mm, 50 ± 5 g)to align with ISO 6330	9/8/22	Uliana Radionova
24	Thermal Properties to be tested to ISO 11092 for all products	1/9/22	Uliana Radionova
24	Product Composition Claims Table Added	1/9/22	Uliana Radionova
25	PTC18 and PTC19 Elongation Table Updated	23/9/22	Dionne Flanagan
26	US clothing flammability comment format updated	12/10/2022	Uliana Radionova

Version	Details of Change	Date of Change	Authorised by
27	- Primark minimum requirements amended - Labs contact details added - PM01 and PM02 updated - PM23 – Elastic extension and Modulus test renamed and updated - PTC22 and PTC23 Colourfastness to Hot pressing and Colourfastness to PVC migration tests added - Disguise costumes and dress up test pack renamed to PTT07 - Children and adult socks test packages changed to PTC20a – Adults Socks/PTC20b – Adults Hosiery/PTC21a – Children’s Socks/PTC21b – Children’s Hosiery - PTC03 /04 Denim with print has to be tested as per updated PM01 (not an exception anymore) - PTC18 – Adults Underwear & Lingerie table amended	April 2023	Added by Uliana Radionova/changes approved by Alison Chance, Dionne Flanagan, Louise Cleary
28	- PTC07 Adult’s Jerseywear e.g., Single Jersey, Ribs, Interlock, Pique, Pointelle etc test pack updated - PTC08 – Children’s Jerseywear e.g., Single Jersey, Ribs, Interlock, Pique, Pointelle etc. test pack updated - PTC16 – Adults Nightwear – Woven & Knitted test pack updated - PTC17 – Children’s Nightwear – Woven & Knitted test pack updated - PTC18a – Adults Underwear (E.g., briefs / trunks / underwear vests and cami’s / underwear leggings)-a new test pack based on the PTC18 test pack reworked and updated - PTC18b – Adults Lingerie (all bras / bra accessories / underwired / cupped styles including body suits, corsets and suspender belts)- a new test pack based on the PTC18 test pack reworked and updated - PTC19 – Children’s Underwear-test pack updated - PM01 – Product Appearance after Multiple Wash test method updated - No colourway linking is permitted for PM01 <u>extended wash tests</u> for jersey, socks and denim products.	May 2023	Added by Uliana Radionova/changes approved by Alison Chance and Mary Rowan

Version	Details of Change	Date of Change	Authorised by
29	- Dimensional stability and appearance, handwash only styles and machine wash styles updated for PTC20B – Adult Hosiery and PTC21B – Kids Hosiery - PM01- Extended wash assessment table updated - PTC18B -Phenolic yellowing and Martindale pilling requirements updated - PTC03 – Adults Denim Wear to tensile strength requirements amended - PTC16 – Adults Nightwear and Loungewear – Woven & Knitted updated - PTC17 - Children’s Nightwear and Loungewear – Woven & Knitted updated - PM01 ADDITIONAL FOR PILE AND BRUSHED FABRICS ONLY added - EXTENDED WASH ASSESSMENT TABLE updated with Warm Handle Nightwear - PTC29 - Baby bibs, Muslins, baby blankets, baby mittens updated	July 2023	Added by Uliana Radionova/changes approved by Alison Chance/Susan Yip / /Susan Daly/ Anne Marie McParland
30	- PTC04 – Children’s Denim Wear – security of attachment buttons and security of attachment mechanically applied fasteners amended from 70N to 90N - PTT07 – Disguise Costumes, Dress Up DOC required and the note added regarding if there is an electrical component test	October 2023	Added by Uliana Radionova/changes approved by Alison Chance/Susan Conneely
V30	- ALL test packages updated to 45 washes change of name of PM01 to appearance after extended wash - Revision to Appearance after wash 1-5 washes only applied as a separate test. - Fibre composition test updated in all the test packages	30 th Jan 2024	Added by Uliana Radionova and Alison Chance/ changes approved by Jonty Wilson
V30.1	- Table A – Part II – Additional Assessment criteria for PM01 only (Additional product category specific criteria for review in all extended wash increments) new requirements for denim assessment added. - Revision to Pm01 – Matting standard (inside assessment observation only (exception on hood lining) - NEW PTC34 – CHILDREN’S LIGHT UP JUMPERS (EU & UK only) test package added. - Alignment of spirality between Pm01 and main spirality testing	March 2024	Added by Uliana Radionova/changes approved by Alison Chance, Joy Laity

V31	• In PTC34, added new EU Batteries Regulation from 2023 and UK Batteries Regulation, as well, as they have diverged. • In PTC34, for product only going to EU and UK, added UK PAS 7055:2021 for safety of non-toy product containing coin and button batteries. • PTC32 – ADULT BARRIER MASKS test package removed, if you receive this product, please contact Primark compliance or quality team • PTC33 – CHILDRENS BARRIER MASKS test package removed if you receive this product please contact Primark compliance or quality team • PTC28 -updated Colour fastness to Water and Colour fastness to cycles of to-and-fro rubbing, test to the latest standard • PTC16 and PTC17 Print / Motif / Flock Durability PM02 test “(Only applicable to non-jersey nightwear e.g., woven)” wording removed. Test 15 minutes @40°C • Dry as per Care Label **Only required on Print/Motif/Flock product being tested to BS EN ISO 6330:2012 Appearance after wash (1 and 5 washes)All functional internal printing on garments to be assessed for observational changes only • Colour Fastness to Dry Cleaning BS EN ISO 105 -D01 – standards have been updated in all relevant test packages. • PTC03 test package updated. • All applicable adult test packages updated with the colour fastness tests that are moved to one block. • PTC16 updated with the Children’s Sleepwear Flammability CFR 1615 / 1616 Laundering Test for Chemically treated items • PTC22 and PTC23 – Faux Suede products have been removed from these test packages • Faux Suede products now must be tested to PTC35 and PTC36 • Colour Fastness to Light BS EN ISO 105 -B02 – removed from all test packages except for Performance, Shorts, Swim and Beachwear. For these categories, we have introduced new neon specific standards. • Colourfastness to Sea Water BS EN ISO 105: E02 – we have introduced new neon specific standards. • Colourfastness to Chlorinated Water BS EN ISO 105: E03 introduced new neon specific standards. • PM01 machine wash instructions amended in all applicable test packages • PTC34 – Children’s light up jumpers RoHS Directive 2011/65/EU amendment (EU) 2015/863 Must comply with the limits in the directive. We do not accept the use of any exemptions. Mercury content and labelling assessment for Battery US Public Law 104-142 added • Minimum requirements amended For Adult’s Apparel FULL TEST PACKAGE testing is mandatory on the first test request form (TRF) submission for	September 2024	Added by Cirrus Alpert/Uliana Radionova/changes requested by Jonty Wilson/Alison Chance
-----	--	----------------	---

Version	Details of Change	Date of Change	Authorised by
	at least for one colour option per style. COLOURFASTNESS TESTS and PM01 (or APPERANCE AFTER WASH) are mandatory for every single colour per style. Linking of the COLOURFASTNESS TESTS to the FULL TEST PACKAGE test report via a new TRF is only possible for products of different colours within the same style. For Children's Apparel FULL TEST PACKAGE testing is mandatory for every single colour per style. Linking is not allowed. PM01 (or APPERANCE AFTER WASH) are mandatory for every single colour per style. For Adult's Home Textiles FULL TEST PACKAGE testing is mandatory on the first test request form (TRF) submission for at least for one colour option per style. COLOURFASTNESS TESTS and PM01 are required for every single colour per style. Linking of the COLOURFASTNESS TESTS to the FULL TEST PACKAGE test report via a new TRF is only possible for products of different colours within the same style. For Footwear (Children's and Adult's) FULL TEST PACKAGE testing is mandatory for every single colour per style. Linking is not allowed. Other Adult's and Children's products FULL TEST PACKAGE testing is mandatory for every single colour per style. Linking is not allowed. Testing for the same style must not be divided between different Labs, except for products with a formulated component (refer to "Requirements for Formulated Product"). If technical support or Primark Interlink Testing Portal assistance is required, Suppliers should contact interlinksupport@intertek.com Requirements for formulated product chapter removed from the manual. For (1) stationary with a formulated component, (2) products made of gel or semi-solid material, and (3) products filled with formulated, liquid, gel, semi-solid fillings that are not classed as cosmetics, the Supplier is required to submit to the Exponent lab via a separate TRF the documentation. The details of the process are stated in the "Primark data requirement manual for formulated toys and non-cosmetic products with international or likely skin contact".		

Version	Details of Change	Date of Change	Authorised by
V31.1	- Added PM01- Extended wash - ADDITIONAL DENIM GUIDANCE: Decrease in Baking/crease effect – Adults and Kids: Any changes after 5 washes would be a failure. - PTC03 and PTC04: for seam slippage at heaviest fabric weight, update from 1600N (this appears to be a typo in the previous manual that is misleading the requirements) to 160N to table in both packages. - Revised Residual elongation test of PTC16 and PTC17 test packages to include the seam free and lace residual elongation requirements. - For PTC17: 1) Updated the US Clothing flammability by adding point 5 to the Comments column: 5. Infant garment sized nine months or smaller (if meets the relevant criteria as per US Children Sleepwear Regulation). If contain Vinyl Plastic Film, then must comply to 16 CRF 1611. 2) Updated US Children's Sleepwear Flammability with more details of the requirements and testing procedure to ensure compliance to US Children Sleepwear Regulation. 3) Added US Clothing Flammability for infant garment separately.	March 2025	Updated by Chirag and Andrew
V32	- Updated the testing requirement of Quick Dry for PTC13 – Adults Swimwear & Beachwear – Woven & Knitted and PTC15 – Adults Performance wear – Woven & Knitted - Test standard updated to: AATCC 201 - Requirement updated to: ≤20 minutes or ≥ 0.6mL/h - Added below comments on the testing of Fibre Composition of all applicable test packages. - The Fibre content on the care label shall be declared as per the test results, not the claimed Fibre content. - The +/- 3% on blends applies to variation in bulk production, not to declaration of Fibre content on the care label. - Created new test package of PTC37- Ski Wear - Updated PTC03 – Adults Denim Wear - the overall requirement was updated as: All mandatory tests must be completed for all colours per style. - Wording on the comment column has been changed on back pocket application strength and belt loop application strength tests, the testing of back pocket application strength is for all products containing elastane, the testing of back pocket application strength is only at Primark Technologist Request. - On the section of Primark's minimum requirements, updated the Risk Assessment requirement per GPSR: Risk Assessment must be completed by the supplier based on Primark template and must submit to Primark technologist for approval before black seal review.	September 2025	Requested by Siobhan O'Brien-Selway, Dionne Flanagan, Camilla Addis and Updated by Andrew Zhu