

UNIVERSITÉ CATHOLIQUE DE LOUVAIN

---

**Study of the stress relieve heat-treatment of  
additively manufactured AlSi10Mg alloy:**  
Influence on microstructure and mechanical properties

---

*Dissertation presented by*

David DISPAS                      *and*                      Arthur BOUILLOT

*for obtaining the Master's degree in*

Mechanical Engineering                      *and*                      Chemical and Materials  
Engineering

*at Ecole Polytechnique de Louvain (EPL)*

*Supervisor:* Aude SIMAR

*Readers:* Laurent DELANNAY, Anne MERTENS, Camille VAN DER REST

Academic year 2017-2018

*'Citation stylée.'*

Mec cool

# Acknowledgements

Gros betch à mes poules Aude Simar et Camille Van Der Rest et aux potos du labo



# Contents

<b>1</b>	<b>Introduction</b>	<b>1</b>
<b>2</b>	<b>State of the art</b>	<b>3</b>
<b>3</b>	<b>Materials and methods</b>	<b>7</b>
<b>4</b>	<b>Results</b>	<b>9</b>
<b>5</b>	<b>Discussion</b>	<b>11</b>
<b>6</b>	<b>Conclusion</b>	<b>13</b>
	<b>Bibliography</b>	<b>15</b>



# List of Figures

2.1	Parameters involved in SLM . . . . .	3
2.2	Process window for SLM of AlSi10Mg, based on the top view of single track scans . . . . .	4
2.3	Process window for SLM of AlSi10Mg, based on the depth and height of the track . . . . .	5
5.1	An Electron . . . . .	11





# List of Tables



# List of Abbreviations

**SLM** Selective Laser Melting



# Abbreviations and symbols

$D_a$	Average particle size	$[\mu m]$
$E_d$	Volumetric energy density	$[\frac{J}{mm^3}]$
$h$	Hatch space	$[\mu m]$
$P$	Laser power	$[W]$
$p_{Ar}$	Argon pressure	$[mbar]$
$t$	Layer thickness	$[\mu m]$
$v_s$	Scanning speed	$[\frac{mm}{s}]$
$\phi_{99\%}$	Laser spot size at the 99% contour	$[\mu m]$
$\rho_{rel}$	Apparent relative density	$[-]$



*Nous dédions ce travail à nos familles et amis*





## Chapter 1

# Introduction

This is, with the concluding chapter, a significant portion of memory. This should especially present the context and objectives of the work. Generally, the memory structure (content of chapters) is briefly exposed



## Chapter 2

# State of the art

Parler de l'AlSi10Mg; quel est l'intérêt de travailler avec? Difficultés? (reflectivité etc)

Microstructure homogène, diagramme de phase

The properties of parts produced through selective laser melting (SLM) stem from the coupled effects of a great deal of parameters (see figure 2.1) [1]. Results are very sensitive to their variations, which must thus be monitored thoroughly. These reasons complicate the optimisation of the process parameters, still not fully resolved for aluminium alloys.

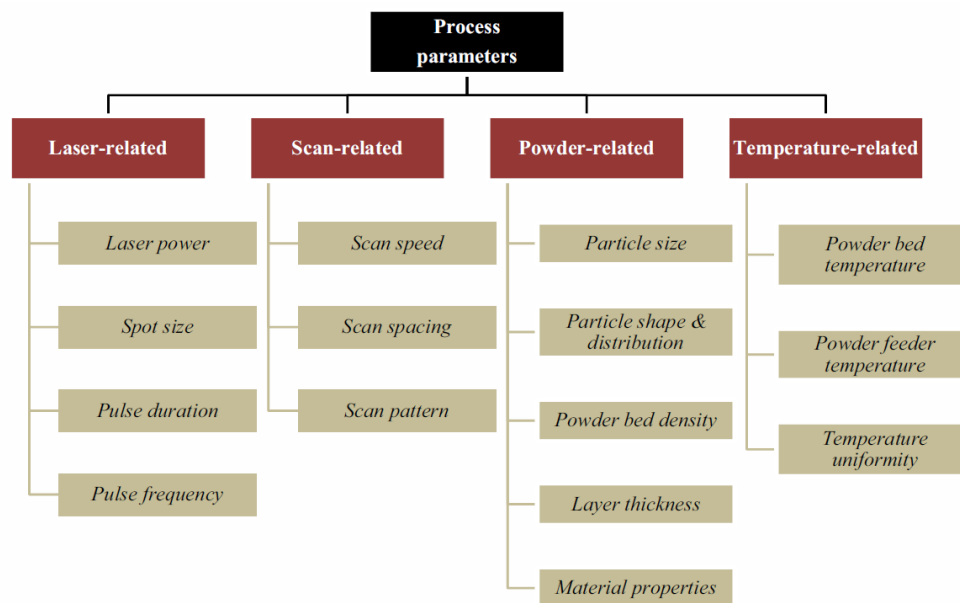


FIGURE 2.1: Parameters involved in SLM (from Aboulkhair et al, 2014)

In recent years, works aiming at meeting this challenge multiplied. The minimisation of the porosity is at the center of attention. It is indeed closely related to the quality of the mechanical properties. As porosity contributes to lowering the load-bearing surface, it reduces the apparent material strength. It was also observed to have a critical influence on the fatigue life of the produced parts. Their lifetime is especially diminished if the values of pores amount and size go beyond a certain threshold [2]. Studies investigating the effects of various parameters on the

AlSi10Mg fabrication through SLM is abundant in the literature.

The analysis of the coupled impacts of the laser power  $P$  and scan speed  $v_s$  provides a first insight. As depicted by figures 2.2 and 2.3, low  $P$  and high  $v_s$  lead to an insufficient energy input to melt the powder and re-melt the substrate, which causes the formation of droplets [3]. The opposite leads to good penetration but also to distortions and irregularities. A trend to use both high  $P$  and  $v_s$  rose in accordance with these findings. Doing so as the advantage to increase productivity. However, it also has multiple downsides including a decrease of the surface quality due to balling, excessive spatter, and an augmented gas induced porosity [5]. Therefore, a trade-off must be found.

A popular approach is to regroup multiple operating parameters into one, the volumetric energy density  $E_d$ . It is estimated through the following formula:

$$E_d = \frac{P}{v_s h t}$$

where  $t$  is the layer thickness and  $h$  is the hatch space. As a rule of thumb,  $E_d$  should be chosen in the range between 60 and 75 [ $\frac{J}{mm^3}$ ] [6]. Almost no studies were carried out to optimize  $h$  and  $t$  independently. Their values lie generally respectively in the intervals [20 ; 60] [ $\mu m$ ] and [50 ; 200] [ $\mu m$ ].

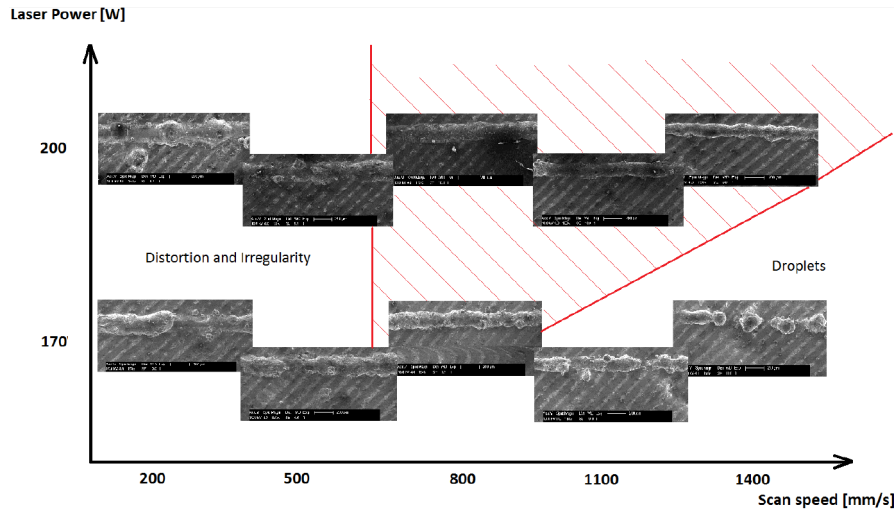


FIGURE 2.2: Process window for SLM of AlSi10Mg, based on the top view of single track scans (from Kempen et al, 2011)

The other process parameters will be covered for the sake of completeness. To begin with, the particle size  $D_a$  of the powder should be as small as possible to ensure a good flowability and allow for thin layers [3]. Typical values stretch from 15 to 60 [ $\mu m$ ]. The size distribution is more delicate to outline. On one hand, wider distributions often generate better bed density and parts with higher density and better surface finish. On the other hand, narrower ones usually provide better flowability and parts with better strength and hardness [4]. In most cases, a middle ground between the two should be sought.

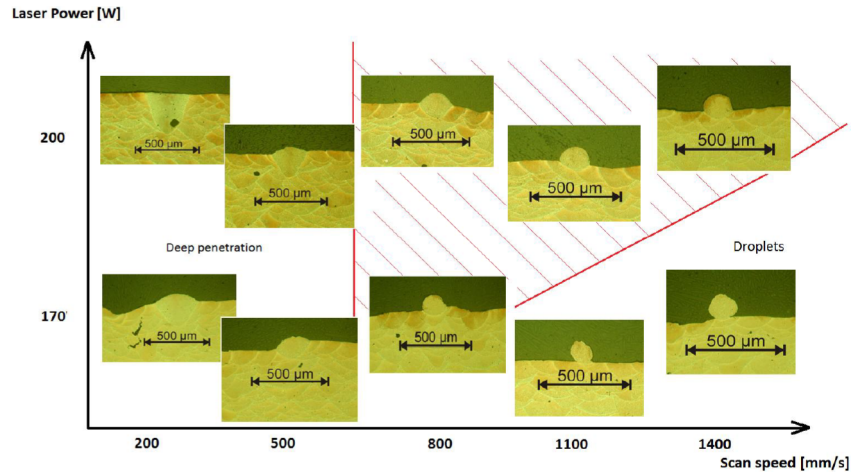


FIGURE 2.3: Process window for SLM of AlSi10Mg, based on the front view of single track scans (from Kempen et al, 2011)

Then scan pattern... Building direction...

Other laser-related parameters - the spot size and the pulse properties - can also be tuned. Only the laser spot size at the 99% contour  $\phi_{99\%}$  is frequently cited in literature. Its value lies between 100 and 200  $\mu m$ .

Finally, pressure and temperature..

Comparer les résultats avec alliage coulé/forgé

Once the porosity problem is sorted out, other matters can be addressed such as productivity and surface roughness. The latter is problematic as the surface finish obtained with SLM is typically of such poor quality that all cracks initiate near the surface for a sample with apparent relative density  $\rho_{rel} > 99\%$  [2]. Polir ou changement paramètres fab.

Post-traitements dont traitements thermiques, sur lesquels on se focalise. Expliquer



## Chapter 3

# Materials and methods

Description expériences et machines





## Chapter 4

# Results

Analyses statistiques etc...



## Chapter 5

# Discussion

Que conclure d'après les résultats? 5.1



---

FIGURE 5.1: An electron (artist's impression).



## Chapter 6

# Conclusion

They incorporate in a synthetic way the main results and compare them with the initial objectives. Generally, this final chapter also presents prospects for the continuation of the work undertaken.



# Bibliography

- [1] Nesma T. Aboulkhair et al. 'Reducing porosity in AlSi10Mg parts processed by selective laser melting'. In: *Additive Manufacturing* 1-4 (2014). Inaugural Issue, pp. 77–86. URL: <http://www.sciencedirect.com/science/article/pii/S2214860414000062>.
- [2] Erhard Brandl et al. 'Additive manufactured AlSi10Mg samples using Selective Laser Melting (SLM): Microstructure, high cycle fatigue, and fracture behavior'. In: *Materials & Design* 34 (2012), pp. 159–169. URL: <http://www.sciencedirect.com/science/article/pii/S0261306911005590>.
- [3] Karolien Kempen et al. 'Microstructural analysis and process optimization for selective laser melting of AlSi10Mg'. In: *Solid Freeform Fabrication Symposium Proceedings* (2011). Conference paper, pp. 484–495. URL: <https://sffsymposium.engr.utexas.edu/Manuscripts/2011/2011-37-Kempen.pdf>.
- [4] Bochuan Liu et al. 'Investigaztion the effect of particle size distribution on processing parameters optimisation in selective laser melting process'. In: (Jan. 2011). Conference paper, pp. 227–238.
- [5] Anne I. Mertens, Jocelyn Delahaye and Jacqueline Lecomte-Beckers. 'Fusion-Based Additive Manufacturing for Processing Aluminum Alloys: State-of-the-Art and Challenges'. In: *Advanced Engineering Materials* 19.8 (2017), p. 1700003. URL: <https://onlinelibrary.wiley.com/doi/abs/10.1002/adem.201700003>.
- [6] Noriko Read et al. 'Selective laser melting of AlSi10Mg alloy: Process optimisation and mechanical properties development'. In: *Materials & Design* (1980-2015) 65 (2015), pp. 417–424. URL: <http://www.sciencedirect.com/science/article/pii/S0261306914007468>.