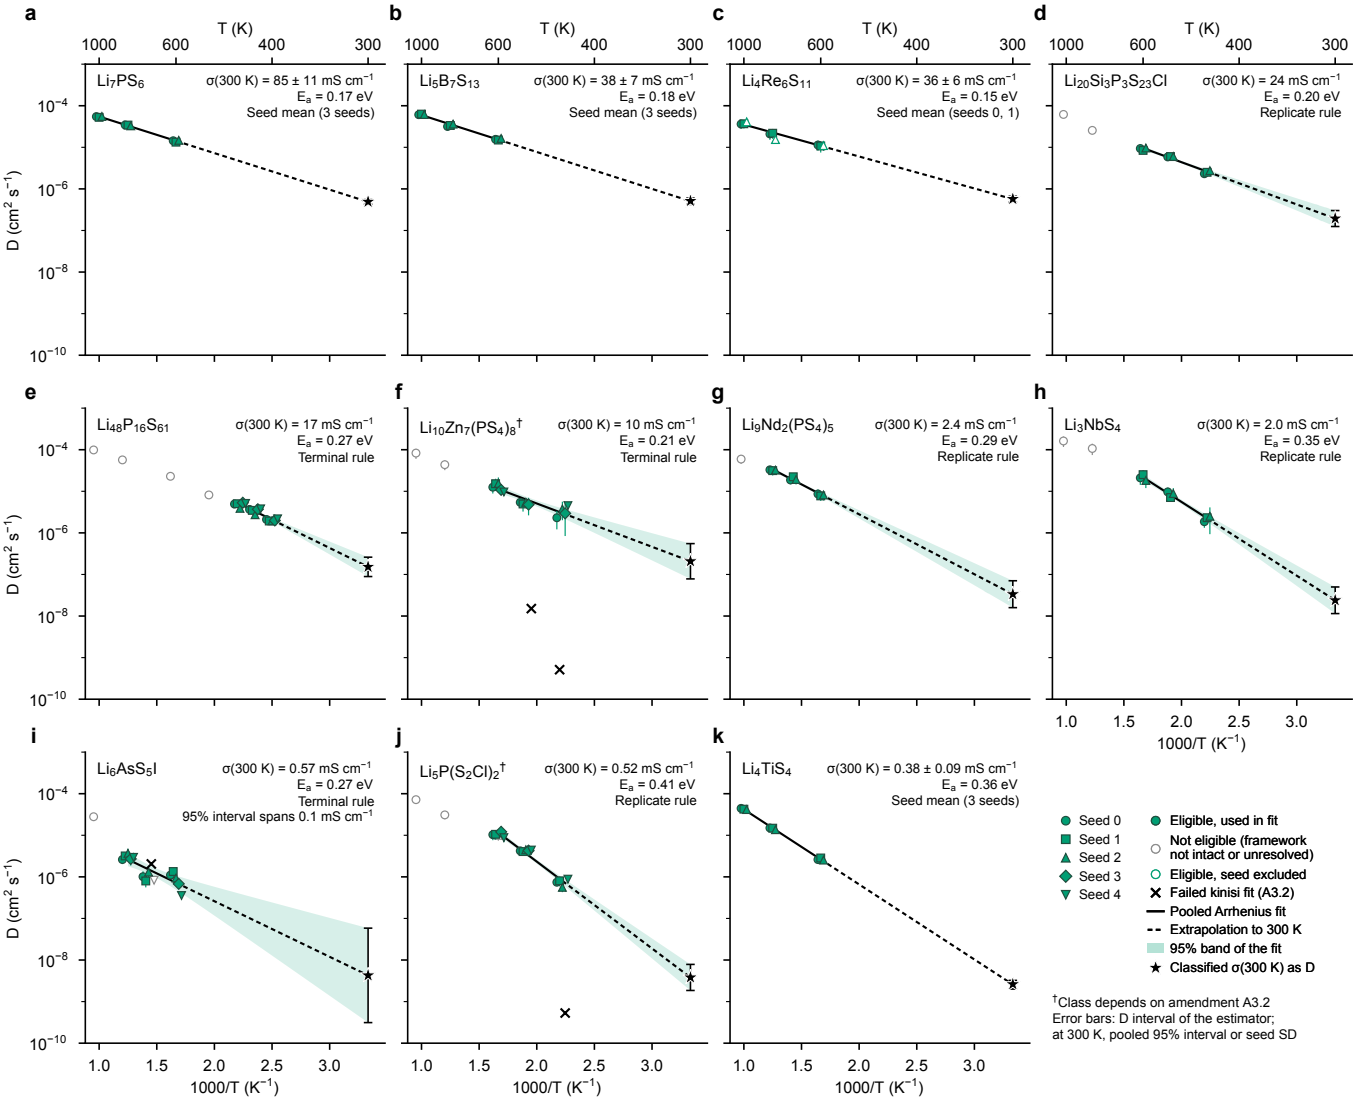

a
Li7PS6
σ(300 K) = 85 ± 11 mS cm−1
Ea = 0.17 eV
Seed mean (3 seeds)
b
Li5B7S13
σ(300 K) = 38 ± 7 mS cm−1
Ea = 0.18 eV
Seed mean (3 seeds)
c
Li4Re6S11
σ(300 K) = 36 ± 6 mS cm−1
Ea = 0.15 eV
Seed mean (seeds 0, 1)
d
Li20Si3P3S23Cl
σ(300 K) = 24 mS cm−1
Ea = 0.20 eV
Replicate rule
e
Li48P16S61
σ(300 K) = 17 mS cm−1
Ea = 0.27 eV
Terminal rule
f
Li10Zn7(PS4)8†
σ(300 K) = 10 mS cm−1
Ea = 0.21 eV
Terminal rule
g
Li9Nd2(PS4)5
σ(300 K) = 2.4 mS cm−1
Ea = 0.29 eV
Replicate rule
h
Li3NbS4
σ(300 K) = 2.0 mS cm−1
Ea = 0.35 eV
Replicate rule
i
Li6AsS5I
σ(300 K) = 0.57 mS cm−1
Ea = 0.27 eV
Terminal rule
95% interval spans 0.1 mS cm−1
j
Li5P(S2Cl)2†
σ(300 K) = 0.52 mS cm−1
Ea = 0.41 eV
Replicate rule
k
Li4TiS4
σ(300 K) = 0.38 ± 0.09 mS cm−1
Ea = 0.36 eV
Seed mean (3 seeds)
T (K)
1000
600
400
300
D (cm2 s−1)
10−4
10−6
10−8
10−10
1000/T (K−1)
1.0
1.5
2.0
2.5
3.0
Seed 0
Seed 1
Seed 2
Seed 3
Seed 4
Eligible, used in fit
Not eligible (framework not intact or unresolved)
Eligible, seed excluded
Failed kinisi fit (A3.2)
Pooled Arrhenius fit
Extrapolation to 300 K
95% band of the fit
Classified σ(300 K) as D
†Class depends on amendment A3.2
Error bars: D interval of the estimator;
at 300 K, pooled 95% interval or seed SD