

Everzol[®]

Reactive Dyes



Better Chemistry
Better Life


Everlight
Chemical

臺灣永光化學工業股份有限公司

Everlight Chemical Industrial Corporation

EVERZOL

中文版

目錄

I. 概述	A-1
1. 應用範圍介紹	A-1
2. 染料的儲藏	A-1
3. 水質與離子封鎖劑的使用	A-1
4. 染色用鹽的品質	A-2
5. 染液的製備	A-2
6. 紡織品的前處理工程	A-2
7. 染色物的後處理工程	A-4
8. 鹽和鹼的推薦用法	A-5
9. 染色方式的介紹	A-6
10. Everzol 染料的修色	A-15
II. 染色特性和堅牢度說明	A-16
1. 吸盡和固著曲線	A-16
2. 反應性	A-16
3. 親和性	A-17
4. 移染性	A-17
5. 洗淨性	A-18
6. 溶解度	A-18
7. 脫色性	A-19
8. 高溫染色安定性	A-20
9. 色恆性	A-21
10. 金屬離子的影響	A-21
11. 固色變色性	A-21
12. 樹脂加工性	A-22
13. 拔染性	A-22
14. 對溫度的依存性	A-23
15. 對鹽類的依存性	A-23
16. 對浴比的依存性	A-24
17. 對鹼類的依存性	A-24
18. 色堅牢度的試驗方法	A-25
III 染料色樣與說明	A-55
IV 染料特性資料表	A-55
V Everzol 染料組合	A-66

I 概述

1.應用範圍介紹

永光反應性染料是一種具有色澤鮮豔，溼潤堅牢度優良，實際應用於染色上方法簡便的反應性染料。它和一般染料的區別是：永光反應性染料分子中有反應基團，為水溶性的染料，其與纖維呈化學性的結合，故在水洗、日光、摩擦上，擁有優良的堅牢度。台灣永光化學公司所推薦的反應性染料為一氯均三嗪與乙烯砒型及一氯均三嗪加乙烯砒混合型反應性染料，前者染料需在高溫度和較強鹼性介質中進行反應固色，後者的反應性較高，可在中溫度下染色和固色。

永光反應性染料主要使用於棉、麻、再生纖維.....等，以及和分散性染料共同使用於混紡品的染色和印花。永光反應性染料適用於一般之染色機械的染色，如浸染、捲染、繩染、連續染色、冷壓染以及印花工藝中的輥筒印花和網版印花。

為了因應染色工業增加產量的需求，台灣永光染料的技術部門也努力提供一些新的前後處理工程和染色工程的技術，以適應更進步的新染色機械。

2.染料的儲藏

永光反應性染料在乾燥和常溫的環境條件下，具有良好的儲藏安定性。但若是在高溫多濕的地方長時間儲存，則易引起部份染料的分解，反應力有降低的傾向。因此保存的時候應注意控制濕度，避免高溫，以及使用後桶內包裝袋的密封及加蓋是必要的。

3.水質與離子封鎖劑的使用

染色用水，一般以採用接近中性的軟水為宜。少量的鈣、鎂（一般在100ppm以上）即會在加鹼劑固色時，與鹼劑結成不溶性沉澱而導致低得色量、不均染和低堅牢度。

微量之銅（2 ppm以上）或鐵（10 ppm以上）等重金屬可能影響到某些染料的色相，故應避免之。如以六偏磷酸鈉作為軟水劑而用量較多時，則需要相對的加入碳酸鈉以調整染色用水的PH值，使接近中性，以免影響染料的吸收量。

若只有硬水，則需添加金屬離子封鎖劑於染液與皂煮液中。

注意: 乙二胺四乙酸 (E.D.T.A.) 是用來封鎖重金屬離子，不能使用於含金染料。

4.染色用電解質的品質

染色用電解質 (精鹽或芒硝) 以呈中性為宜，並且要求鈣、鎂鹽含量較低，以免在加鹼固著過程中大量沉澱產生。

5.染液的製備

- (1) Everzol染料極易溶於水中。一般溶解方法為使用少量40-50°C之溫水，將染料攪拌成均勻之糊狀，然後加入80-90°C之熱水並再攪拌均勻。溶解染料的水以處理後呈中性之軟水為佳。
- (2) Everzol Turquoise Blue G則建議以60°C~80°C之熱水溶解。

6.紡織品的前處理工程

染色加工之前被染物，應進行前處理工程，以去除纖維中的雜質和紡織上的漿料等。工程次序的選擇，則視被染物的純淨程度和所染顏色的鮮明度而定。

被染物經漂白後剩餘的游離氯，經過氧化後須加以洗淨。棉製品經絲光後，吸收效果更佳。紡織品經前處理後，應具有高度吸收及濕潤性質，其PH值應接近中性，以利染色加工。

6-1· 精練方法

除淺色、極鮮明的色相外，其他所有顏色則只需施行精練工程：

典型配方如下：

精練劑 0.5-1g/l 純鹼 2g/l

沸騰處理（95-100°C）30分鐘，再以熱水和冷水清洗，以除去沉積的雜質。

6-2· 漂白方法

欲得鮮明的色相或欲除去原棉中的色素及雜質，染色前除精練以外，得再施予漂白工程，此項處理方法之典型配方如下：

過氧化物漂白法	雙氧水 (35%)	6-10	g/l
	雙氧水安定劑	1-2	g/l
	液鹼 (47°Be)	1-2	g/l
	PH	11-12.5	
90-100°C x 30-60 minutes			

染前必須以最適當方除去殘留的微量過氧化氫，再排掉漂白水，然後以熱水和冷水徹底清洗，除去沉積的雜質，然後再加醋酸中和至pH保持在6~7。

前處理配方：

材質：針織布

方法：一浴精練漂白

a. 精練劑	0.5	g/l
b. 雙氧水安定劑	0.5 - 1	g/l
c. 雙氧水 (35%)	5 - 10	g/l
d. 液鹼 (47°B'e)	1 - 2	g/l
或		
液鹼 (47°B'e)	0.5 - 1	g/l
純鹼	2 - 5	g/l
95°C x 40-60 分鐘		

材質：梭織布

方法：二浴精練漂白

(1) 退漿		
a. 精練劑	0.5	g/l
b. 退漿劑	2 - 3	g/l
95°C x 30 分鐘		
(2) 精練漂白		
與針織布相同		

7.染色物的後處理工程

永光反應性染料在印花或染色工程完畢後，須經過充分的洗滌和皂液的沸煮工程，以去除未能與纖維結合已水解的染料及鹽和鹼，方能確保優良的濕潤堅牢度品質，所以推薦的洗淨工程順序如下：

- (1) 先用大量冷水洗滌，繼用熱水或沸水充分洗滌。
- (2) 皂洗液煮沸洗滌。
- (3) 熱水洗、冷水洗、脫水、烘乾。

冷水清洗至水澄清為止，可再施以柔軟或固色工程。皂煮工程前應儘量將殘留在染色物上的鹽、鹼劑以及未固著的染料迅速以熱水沖洗，為了防止洗滌水中未固著的染料累積過多，影響白底潔白度，宜用溢流，換水洗滌。皂洗劑可以採用中性皂，陰離子性洗淨劑或非離子性合成洗淨劑.....等。

後處理工程舉例：

- | | | |
|-----------|-----|--------|
| (1) 捲染機洗滌 | 2 道 | 流動冷水洗滌 |
| | 4 道 | 皂液煮沸洗滌 |
| | 2 道 | 熱水或沸水煮 |
| | 2 道 | 流動冷水洗淨 |

(2) 繩狀染機洗滌

道數	溫度 (°C)	時間 (min)	動作
1	30-50	10-15	溢流冷水洗
2	30-50	10-15	酸中和
3	60-70	10-15	溫水洗
4	80-98	10-15	熱水洗
5	98	10-15	皂洗
6	60-70	10-15	溫水洗
7	30-50	10-15	冷水洗

8.鹽和鹼的推薦用法

永光反應性染料染色用的電解質以芒硝（元明粉）為宜，食鹽的使用除了可能會促進染料的凝集外，同時亦有腐蝕染色裝置的可能。

一般鹼劑的使用以純鹼最佳，為了確保加入鹼料之正確性，最終染液PH值應在10.8-11.2之間，可於染色工程完畢後取樣，以標準PH計測定之。

Everzol染料染色濃度及鹽和鹼的使用量


染色濃度 (% OWF)	鹽或芒硝 (g/l)		鹼 (g/l)			固著時間 (分)
	未絲光棉	絲光棉／嫘縈	純鹼 (g/l)	併用 純鹼 (g/l) + 液鹼 (ml/l)	磷酸三鈉 (g/l)	
0.5%以下	20	10	10	5 + 0.5	6	30
0.5%~1.0%	30	20	15	5 + 0.5	6	45
1.0%~2.0%	40	30	20	5 + 1.0	8	60
2.0%~3.0%	50	40	20	5 + 1.0	8	60
3.0%~4.0%	60	50	20	5 + 1.0	8	60
4.0%~5.0%	70	60	20	5 + 1.0	10	60
5.0%~6.0%	80	70	20	5 + 2.0	10	60
6.0%以上	80	70	20	5 + 2.0	10	90

- 附註： (1) 染Everzol Turquoise Blue G及Brilliant Blue R s/p及B-BRF 150%及Everzol Blue LX系列，僅建議使用芒硝染色
- (2) 染Everzol Brilliant Blue R s/p，芒硝用量請勿超過50 g/l
- (3) 液鹼濃度38°B'e (液態)


9.染色方式的介紹

9-1. Everzol染料的浸染法、棉染色


染法一：一般染法

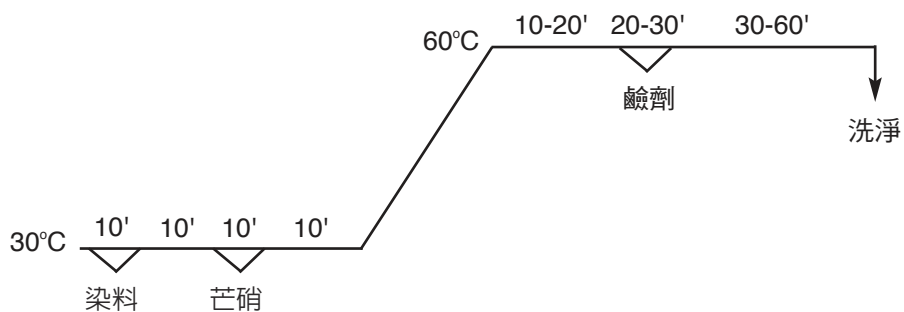


染法二：快速恆溫法（染紗及易染織物）

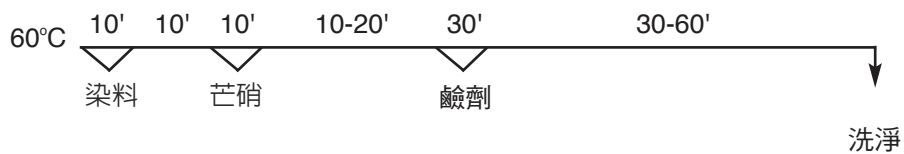


染法三：高溫移染法（厚重織物）(Viscose, Tencel, Modal, 或緻密厚重織物)

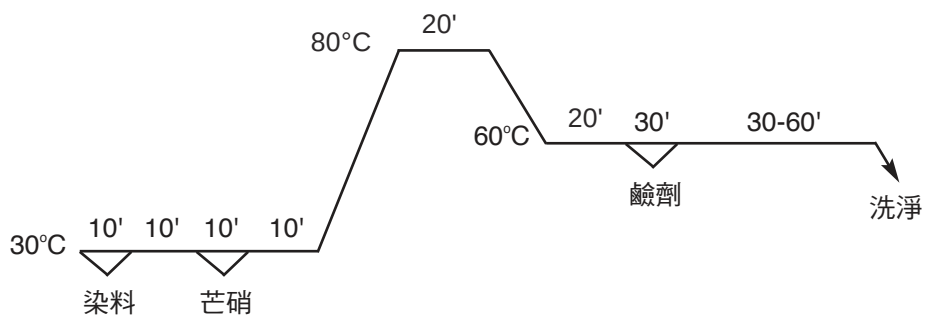


染法四：預加鹼法

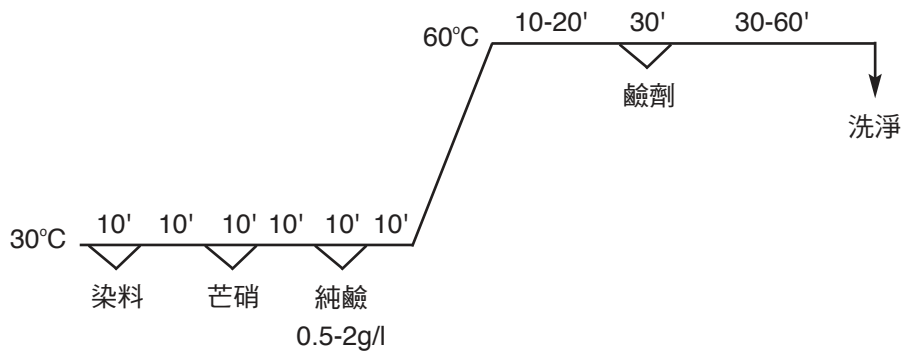

染法五：Everzol Turquoise Blue G 染法

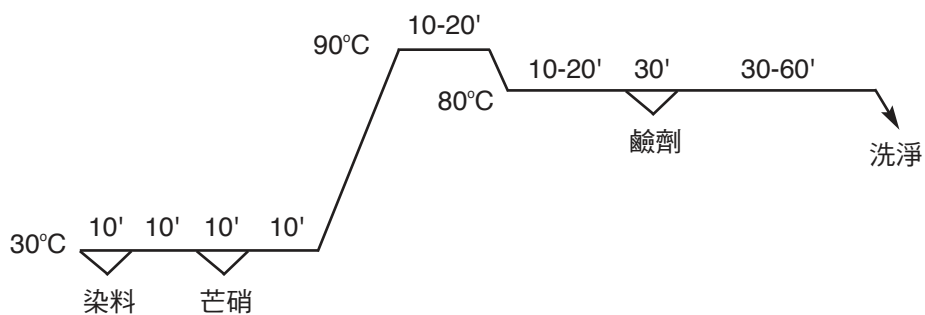


染法六：Jigger染色

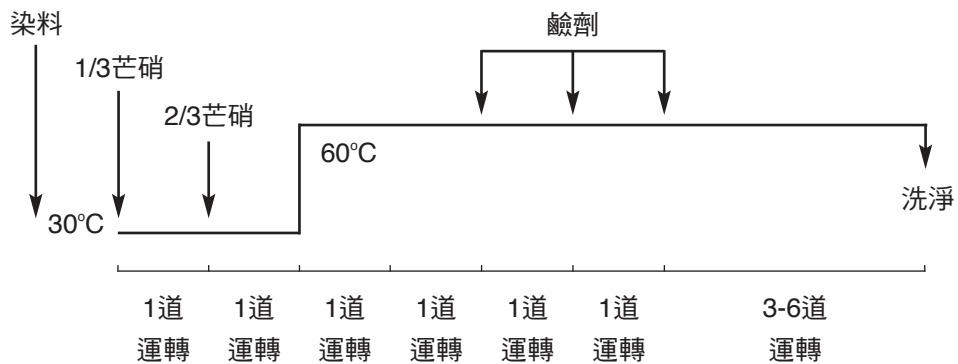

9-2.Everzol染料的連續染色法：

1.冷壓染色工程 Cold pad-batch process

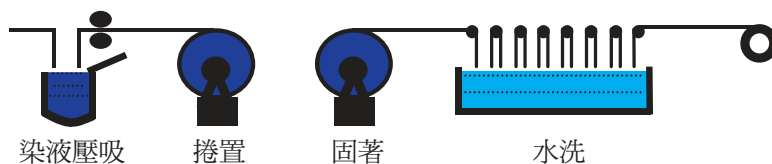

鹼劑需求：

我們推薦三種鹼劑應用於冷壓染色的工程。

A.非水玻璃法：

Everzol 染料	X g/l
液鹼 (38°B'e, 32.5%)	5+x/5 ml/l
純鹼	0~20 g/l
芒硝 (選擇使用)	0~30 g/l

B. 水玻璃法：

水玻璃			Everzol 染料使用濃度 (g/l)					
			~20	30	40	50	60	70 ↑
	g/l	ml/l	液鹼需求量NaOH 38°B'e, 32.5% (ml/l)					
37~40 °B'e	130	95	23.5	28.5	28.5	33.5	33.5	38.5
40~42 °B'e	110	75	23.5	28.5	28.5	33.5	33.5	38.5
48~50 °B'e	100	65	15	20	20	25	25	30
58~60 °B'e	90	50	6	11	11	16	16	21

C. 鹼減量法：

水玻璃			Everzol 染料使用濃度 (g/l)					
			~10	20	30	40	50	60 ↑
	g/l	ml/l	液鹼需求量NaOH 38°B'e, 32.5% (ml/l)					
37~40 °B'e	65	50	7	12	12	17	17	22
40~42 °B'e	55	40	7	12	12	17	17	22
48~50 °B'e	50	35	5	10	10	15	15	20
58~60 °B'e	45	25	3	7	7	11	11	16

助劑添加：

滲透劑的選用應注意是否適合於壓吸液，並且是非起泡性。


尿素的添加可改善提昇部份染料的溶解度。

註：

鹼劑C鹼減量法與其它鹼劑的差異為降低水玻璃與液鹼的使用量，其目的為確保在較高溫的作業環境下，仍保有壓吸液與捲置固著依存的一貫安定性，而其捲置固著時間保持16小時以上是必要的。

上述各鹼劑的應用，定量混合泵皆是必需的。

2.二浴壓染蒸處工程 Pad-dry-chemical pad-steam process

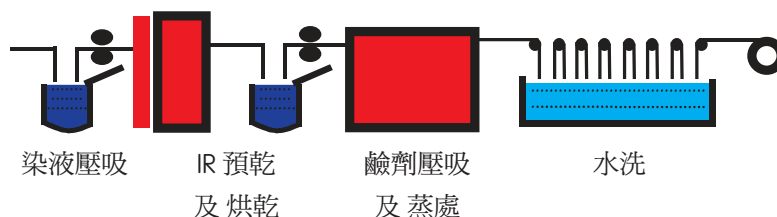

此方法為採二浴壓吸乾燥後蒸處固色的染色方法。

染色壓吸液組成：

Everzol 染料	x g/l
移行防止劑	1 g/l
還原防止劑	10 g/l
滲透劑 (選擇使用)	0~2 g/l

滲透劑的選用應注意是否適合於壓吸液，並且是非起泡性。

尿素的添加可改善提昇部份染料的溶解度。

烘乾：

紅外線IR預乾

一般乾燥到約30%左右的水含量

烘乾：110~130°C

乾燥後織物加以冷卻

中間乾燥在二浴壓吸－蒸處法中是相當重要的一環，通常使用紅外線IR預乾與熱風乾燥或錫林滾筒乾燥等組合的系統。

化學鹼液壓吸／蒸處：

在此過程中應確保壓染布在鹼液槽中有一致的吸收與呈安定的狀態。


化學鹼液需求：

A. 水玻璃 (48~50 °B'e)	60~70 %
B. 液鹼 (38°B'e, 32.5%)	14~20 ml/l
無機鹽	250 g/l
C. 液鹼 (38°B'e, 32.5%)	12~18 ml/l
純鹼	20 g/l
無機鹽	250 g/l

蒸處：

在飽和蒸汽102~105°C，採連續式固著。

3.一浴壓染熱固著工程 Pad-dry-baking process

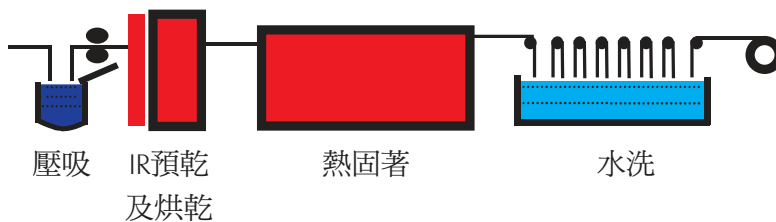

此方法在連續染色工程為採一浴乾式熱固著的染色方式。


染色壓吸液組成：

Everzol 染料	x g/l
鹼劑	見鹼劑需求表 (Page A-11)
移行防止劑	1 g/l
還原防止劑	10 g/l
尿素	50~100 g/l
滲透劑	0~2 g/l
硼砂	0~10 g/l

滲透劑的選用應注意是否適合於壓吸液中，並且是非起泡性。在本工程，尿素的添加除可增加改善部份染料的溶解度以外，更可提昇染料的得色率，但當加工條件為160°C以上時，須注意尿素熱分解的影響。硼砂的添加，可有效防止織物的黃化。

鹼劑需求：

一浴壓染熱固著工程鹼劑需求表：

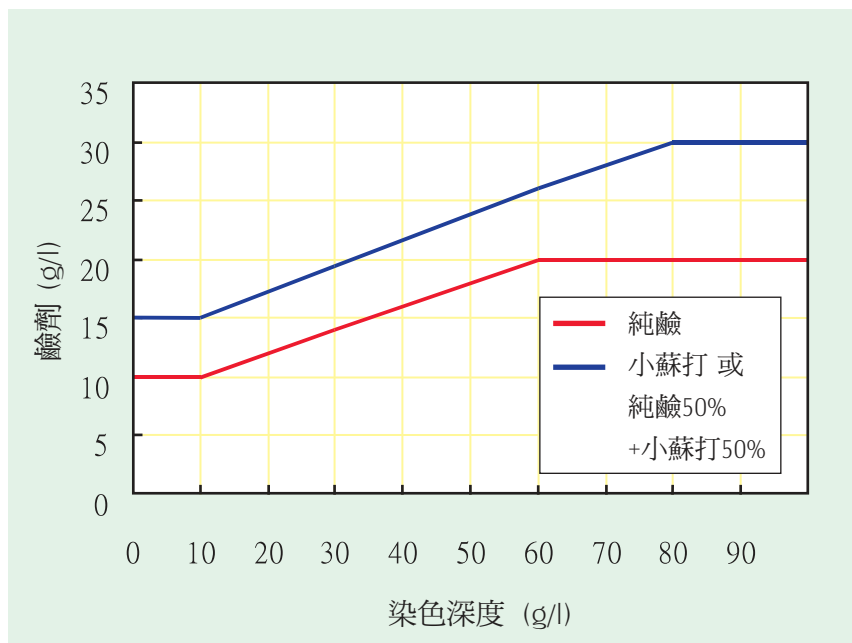

烘乾：

紅外線IR預乾。

一般乾燥到約30%左右的含水量。

烘乾：100~110℃（在有些連續染色作業上，本過程可考慮省略）

熱固著條件：

4~6	分,	at 120 °C
3~4	分,	at 140 °C
2~3	分,	at 150 °C
2~3	分,	at 160 °C
1~2	分,	at 180 °C
1	分,	at 200 °C

註：

注意織物若在高溫固著及帶鹼性的狀況下會產生黃化的現象，其織物的黃化程度，應一併考慮對配色可能的影響。

4.一浴壓染蒸處工程 Pad-steam process



此方法為採一浴溼式蒸汽固著的染色方式不需經中間乾燥，特別適合於厚重織物的染色。因為厚重織物在中間乾燥過程中是較不經濟且易產生染料移染的異常現象。

染色壓吸液組成：

Everzol 染料	x g/l
液鹼 (38°B'e, 32.5%)	見鹼劑需求表
純鹼	20 g/l
無機鹽 (選擇使用)還	0~30 g/l
原防止劑	10 g/l
滲透劑	2 g/l

壓吸液溫度 20~25°C


染料與鹼劑的混合必須使用定量混合泵。

滲透劑的選用應注意是否適合於壓吸液，並且是非起泡性。


蒸處：

飽和蒸汽102~105°C下蒸處60~100 秒。

一浴壓染蒸處工程鹼劑需求表

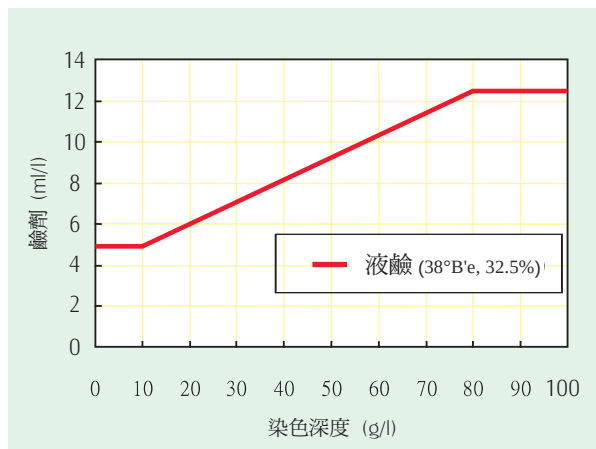

5. 一浴濕短蒸染色法 Emoistfix

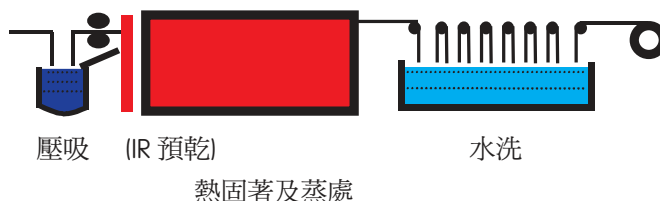

一浴濕短蒸染色是結合一個連續式的熱固著及低量蒸氣的蒸處過程。染料與鹼劑充分混合在一起，進行染色固著，染色過程簡單更經濟。

染色壓吸液組成：

染液與鹼劑必須分別調製，染色前再以定量泵混合

染液組成：

Everzol 染料	X g/l
還原防止劑	5-10 g/l
移行防止劑 (選擇使用)	0-1 g/l
滲透劑	0-2 g/l
尿素 (選擇使用)	50 g/l

滲透劑的選用應注意是否適合於壓吸液，並且是非起泡性。

尿素的添加除可增加改善部份染料的溶解度。

鹼劑需求：

Everzol 染料	Everzol 染料使用濃度 (g/l)					
	~20	20~40	40~60	60~80	80~100	100 ↑
	液鹼需求量NaOH(38°B'e, 32.5%)(ml/l)					
NaOH (38°B'e, 32.5%)	7	11	14	17	21	24
Na ₂ CO ₃	20 g/l					

定量混合泵使用是必需的

壓吸液溫度 20~25°C.

固色條件：


於120~130°C，固色2~3分鐘

蒸氣含濕控制：25%

確認染色織物乾燥完全，可獲得較一致的得色率

9-3.印花


3-1.一相飽和蒸處法

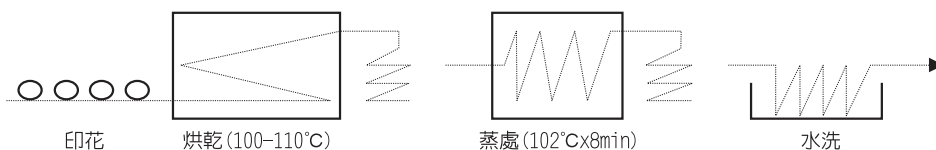

3-1-1. 色糊組成

Everzol染料	x	g
小蘇打	20	
尿素	100	
還原防止劑	10	
糊劑	y	
軟水	z	
	1000	g

3-2. 二相鹼液壓吸蒸處法

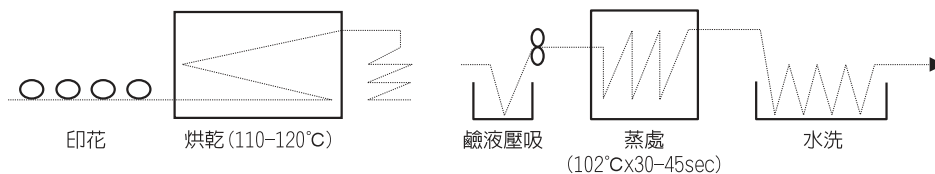

3-2-1. 色糊組成

Everzol染料	x	g
還原防止劑	10	
糊劑	y	
軟水	z	
	1000	g

3-2-2. 鹼液吸液組成

液鹼 (38°B'e)	10-15	ml/l
純鹼	150	g/l
碳酸鉀	50	g/l
中性鹽 (芒硝)	150-200	g/l

10. Everzol 染料的修色

10.1. 不排液修色法

本法推薦用於修色量為原配方的1%和1%以上。

- (a) 染液冷卻至40°C
- (b) 加入已稀釋溶解的染料
- (c) 在40°C持續染10分鐘
- (d) 升溫至60°C
- (e) 在60°C持續染30分鐘
- (f) 對色

10.2 排掉一半染液修色法

此法用於較大幅度之修色。

- (a) 排掉一半染液、注入冷水。如此可降低溫度和電解質濃度、即降低修色染料之移動力。
- (b) 加入已稀釋溶解的染料
- (c) 染10分鐘
- (d) 升溫至60°C
- (e) 在60°C持續染30分鐘
- (f) 對色

以上兩種修色的方法，均不需添加芒硝或純鹼。

II 染色特性和堅牢度說明

1.吸盡和固著曲線

染色條件：

被染物：未絲光棉布。

染料濃度：Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL,
為1%，其他Everzol與Everzol FC/ED/MX 一般色3.0%

無水芒硝：參考鹽、鹼用量表

純鹼：參考鹽、鹼用量表

溫度：60°C (Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G 80°C染色)

時間：鹼加入後60分鐘

浴比：1：10

2.反應性

為加鹼反應時最高吸收率PH值的分類基準。其反應性分類基準如下：

pH 值	<11	I 類	高反應性
	11-11.5	II 類	中反應性
	>11.5	III 類	低反應性

3.親和性

為鹼添加前染料吸收量的分類基準，其親和性分類基準如下：

吸收率	75% 以上	A 類	高親和性
	40-75%	B 類	中親和性
	未滿 40%	C 類	低親和性

4.移染性

移染性試驗按下述方法進行。將一塊已經一次吸盡染色的試驗布和同材質的一塊白布放在浴比1：10，含有60g/l的無水芒硝的處理浴中，經過30分鐘的處理後，再加入20g/l的純鹼使兩塊試驗布固色。

被 染 物：未絲光棉布

染色濃度：Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL為1%，
其他Everzol與Everzol FC/ED/MX 一般色3.0%

浴 比：1：10

助 劑：參考鹽、鹼用量表

溫 度：Everzol 60°C

(Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G 80°C染色)

時 間：鹼加入後續染60分鐘

判定：

對移染處理後的先染布樣和移染布樣（原白布）依據AATCC變褪色灰色標進行濃度判定。

5.洗淨性

將未經絲光的棉針織布，按通常的方法進行染色（3% o.w.f.）將染色物脫水到壓吸率約100%後，按下述順序進行各工程洗淨，並測定各工程的染料脫落量。（Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL為1%，其他Everzol與Everzol FC/ED/MX 一般色3.0%）

- (1) 60°C X 5分鐘 — 溫水洗
- (2) 80°C X 5分鐘 — 熱水洗
- (3) 98°C X 5分鐘 — 皂洗（皂洗劑3 g/l）
- (4) 80°C X 5分鐘 — 熱水洗
- (5) 60°C X 5分鐘 — 溫水洗

判定：

(1)和(2)兩工程的染料脫落量與整個洗淨工程全脫落量之比定為洗淨性。洗淨性優劣並按下述方法分為5級。

$$\frac{\text{(1)和(2)的染料脫落量}}{\text{全洗淨工程的脫落量}} \times 100\% = \text{洗淨性(\%)}$$

96% 以上	5 級	71%-75%	2-3 級
91%-95%	4-5 級	66%-70%	2 級
86%-90%	4 級	61%-65%	1-2 級
81%-85%	3-4 級	60% 以下	1 級
76%-80%	3 級		

6.溶解度

(A) 不添加任何助劑：

將一定量的染料以50°C的熱水溶解，然後過濾。（東洋濾紙No.1）根據過濾所得之殘渣多少，判定染料的溶解度。

(B) 加入無水芒硝50g/l：

將一定量的染料和相當於50g/l的無水芒硝，用50°C的熱水溶解，冷卻到25°C，然後過濾。（東洋濾紙No.1）根據過濾所得之殘渣多少，判定染料的溶解度。

7.脫色性

對於永光反應性染料的脫色有三種方法。

關於以濃度3.0% (o.w.f.) 染色後的棉布的脫色方法，是以下述條件進行的試驗

。(Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL為1%，其他 Everzol與Everzol FC/ED/MX 一般色3.0%)

(1) 鹼處理：

燒鹼 (38°B'e)	20ml/l
浴比	1 : 10
溫度X時間	80°CX30分鐘
溫水洗，冷水洗淨	

(2) 還原處理：

燒鹼 (38°B'e)	20ml/l
保險粉	5 g/l
浴比	1 : 10
溫度X時間	80°CX30分鐘
溫水洗，冷水洗淨	

(3) 還原處理後再氧化處理：

以上述的 (2) 的條件處理之後，再以下述的氧化浴處理。

次氯酸鈉 (有效氯12%)	8 g/l
浴比	1 : 10
溫度X時間	30°CX30分鐘
溫水洗，冷水洗淨	

(4) 氧化處理再還原處理：

以下列的條件處理之後，再以上述(2)的還原浴處理。

次氯酸鈉 (有效氯12%)	8 g/l
浴比	1 : 10
溫度X時間	30°CX30分鐘
溫水洗，冷水洗淨	

判定：根據AATCC污染灰色標比較測試樣本與白胚布之差異。

分類：(1) ×：不適合 (含2級以下)

(2) △：中等 (2-3至3級)


(3) ○：適合 (含3-4級以上)

8. 高溫染色安定性

(1) 對染色布的安定性：

依通常的染色法，以3.0% (o.w.f.) 濃度染色後的染色布作為基準，及按下述方法染色後的染色布，和基準比較，觀察濃度色相的變化，來評價對T/C混紡品的染色性。(Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL為1%，其他Everzol與Everzol FC/ED/MX 一般色3.0%)

染色方法：

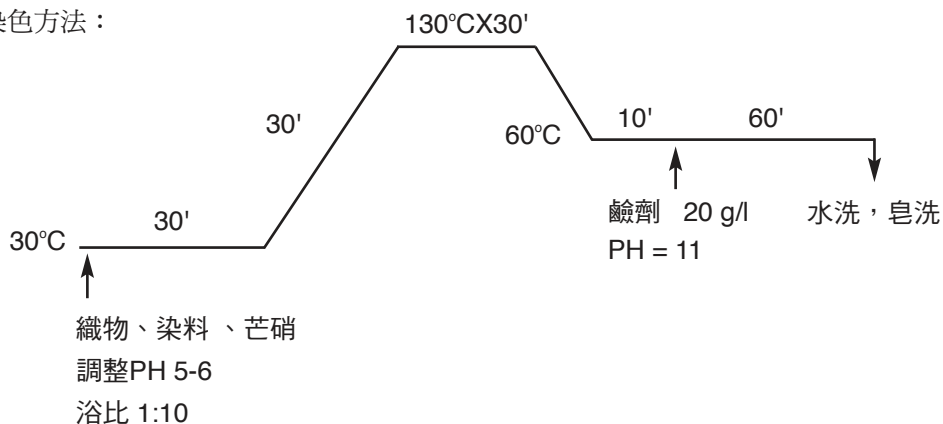


判定：

標準染色法的染色布和上述染色法的染色布，按AATCC變褪色灰色標比較，判定變色過程。

(2) 染液的安定性：

染料濃度：Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL為1%，其他Everzol與Everzol FC/ED/MX 一般色3.0%，依下方法染色後判定級數

染色方法：

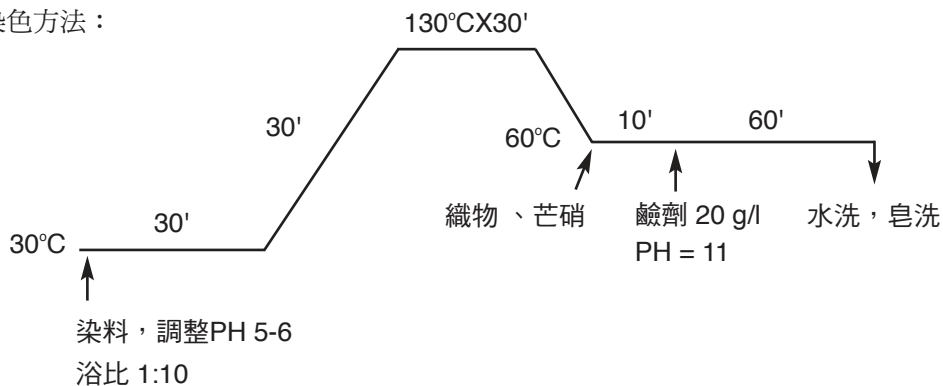

9.色恆性

以標準光源 (D65)作基準，將在鎢絲燈 (Incandescent) 和超效能日光燈 (TL-84)下的演色性依顏色變化傾向說明：

Y：黃色調 R：紅色調 B：藍色調 G：綠色調

10.金屬離子的影響

染浴中加入金屬離子而後染色，研究其對染色物色相、濃度的影響。

染色條件：

被染物：未絲光棉布

染色濃度：Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL為1%，其他Everzol與Everzol FC/ED/MX 一般色3.0%

無水芒硝：參考鹽、鹼用量表

溫度：Everzol 60°C (Yellow 4GL, Yellow 3GL, Green 6B, Turq. Blue G, Yellow ED-2G 80°C 染色)

時間：鹼加入後60分鐘

浴比：1:10

金屬離子：Fe²⁺：使用FeCl₂，20 ppm.

Cu²⁺：使用CuSO₄，20 ppm.

判定：

根據AATCC的變褪色灰色標來判定，添加金屬離子的染色色物和未加金屬離子的染色物之間色相差異程度。

11.固色變色性

(A) 聚乙烯聚胺系：2% owf 60°CX20分鐘

(B) 四級胺鹽系 ：2% owf 60°CX20分鐘

(Yel

12. 樹脂加工性

以標準染色濃度3.0% (o.w.f.) 染色的未經絲光棉布，按下述處方進行樹脂加工和未加工布比較其變退色情況。(Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL為1%，其他Everzol與Everzol FC/ED/MX 一般色3.0%)

(1) 樹脂加工處方：

(A) 三聚氰胺樹脂：

Resin M-3	40 g
Catalyst MRK	8 g
水	x g
全量	1000 g

(B) 乙二醛樹脂：

Resin GF-4000	40 g
Catalyst G	8 g
水	x g
全量	1000 g

(2) 工程：壓吸→乾燥→烘乾。

壓吸率：70%

乾燥：100°C×3分鐘

烘乾：160°C×3分鐘

判定：依據AATCC變褪色灰色標判定加工布相對於未加工布的變褪色程度。

13. 拔染性

拔染性由於底色的濃度和拔白處方的不同而效果不同。(Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL為1%，其他Everzol與Everzol FC/ED/MX 一般色3.0%) 染色後用下述二種處方進行拔染性試驗。

(1) 拔染糊處方：

	中性	鹼性
拔染劑 (Rongalit C)	200	200
純鹼	—	50
吸濕劑	X	X
糊劑	Y	Y
水	Z	Z
全量	1000 g	1000 g

(2) 工程：印花→60°C烘乾→102°C×5~8分鐘

14.對溫度的依存性

染色溫度對染料的吸盡有影響。理論上若溫度低，則需要時間長的染色，則可以獲得高固著率，然而在實際染色中由於經濟性，就必定要設定一定的染色溫度。

關於永光反應性染料對溫度依存性，按下述條件進行染色。以60°C的染物作基準，測定各個溫度的染色物的染色濃度，並圖示之。

染色條件：

被 染 物：未絲光棉布
 染料濃度：(Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL為1%，其他Everzol與Everzol FC/ED/MX 一般色3.0%)
 無水硝芒：參考鹽、鹼用量表
 純 鹼：20 g/l
 溫 度：Everzol：40°C~80°C
 Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G
 ：60~98°C
 時 間：鹼加入後60分鐘
 浴 比：1:10

15.對鹽類的依存性

反應性染料在染色時，染浴中電解質的濃度增加，染料的吸盡率也隨之增高。然而當電解質濃度超過必要濃度後，由於使染料的溶解度降低，而引起吸盡率也隨之降低，因此從經濟上考慮要加入適當量的鹽類。

關於永光反應性染料對鹽類依存性，按下列條件進行染色。以使用60g/l無水芒硝的染物作基準，將其他條件下的染色物，測定其染色濃度，並圖示之。

染色條件：

被 染 物：未絲光棉布
 染料濃度：Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL為1%，其他Everzol與Everzol FC/ED/MX 一般色3.0%
 無水硝芒：30, 40, 50, 60*, 70, 80 g/l
 純 鹼：20 g/l
 溫 度：Everzol 60°C (Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G 80°C染色)
 時 間：鹼加入後60分鐘
 浴 比：1:10

16.對浴比的依存性

一般情況下，反應性染料因為直接性低，所以它的吸盡率和固著率受浴比的影響大。其具有浴比越小固著率越高的傾向。但由於染色機的原因，浴比越小，越容易產生染斑，為此要兼顧到均染性來決定浴比。

關於永光反應性染料對浴比的依存性，按下列條件進行染色，以浴比為1：20的染物作基準，測定各個浴比的染色物的染色濃度，並圖示之。

染色條件：

被染物：未絲光棉布

染料濃度：(Everzol LX/LF/CS系列及Everzol Y C-GL, R C-3B, B-BB, BK C-RL為1%，其他Everzol與Everzol FC/ED/MX 一般色3.0%)

無水硝芒：參考鹽、鹼用量表

純鹼：參考鹽、鹼用量表

溫度：Everzol：60°C (Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G 80°C染色)

時間：鹼加入後60分鐘

浴比：1：5~120，以1：10為標準

17.對鹼類的依存性

染色條件：

被染物：未絲光棉布

染料濃度：Everzol Y C-GL, R C-3B, B-BB, BK C-RL, Everzol LX/LF系列為1%，其他Everzol, Everzol FC/ED/MX 一般色3%

無水芒硝：60 g/l

鹼類：純鹼g/l 5, 10, 15, 20*, 5, 5,
燒鹼 (38°B'e) ml/l —, —, —, —, 1, 2,

溫度：Everzol：60°C (Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G 80°C染色)

時間：鹼加入後60分鐘

浴比：1：10

18.染色堅牢度的試驗方法

1. 耐水洗	ISO 105 C10 方法 B ISO 105 C10 方法 C ISO 105 C10 方法 D ISO 105 C06-C1S ISO 105 C06-C2S Marks & Spencer C4A
2. 耐水	ISO 105 E01
3. 耐熱水	ISO 105 E08
4. 耐海水	ISO 105 E02
5. 耐後絲光	ISO 105 X04
6. 耐酸水解	1% 醋酸溶液浸泡30分鐘，進行38°C x 6小時處理。
7. 耐汗（酸，鹼）	ISO 105 E04
8. 耐氯水（20ppm）	ISO 105 E03
雙氧水漂白	ISO 105 N02
9. 耐磨擦（乾，濕）	ISO 105 X12
10. 擬溼日光	Marks & Spencer C9A
11. 耐多次水洗	ISO 105 C09
12. 耐唾液	DIN 53160
13. 耐熱壓	ISO 105 X11
14. 日光堅牢度	ISO 105 B02 & AATCC 16-3
15. 汗日光堅牢度	ISO 105 B07 & AATCC 125
16. 氣體變褪色	ISO 105-G01

臺灣永光化學工業股份有限公司

Everlight Chemical Industrial Corporation

EVERZOL

English Version

CONTENTS

1.Introduction	A-29
2.General dyeing methods for Everzol dyes	A-30
(1) Pretreatment of substrate	A-30
(2) Dissolving of dyes	A-31
(3) Dyeing methods	A-31
(4) Salt and alkali requirement of Everzol dyes	A-31
(5) Washing on winch or Jet dyeing machine	A-32
3.Exhaust dyeing	A-32
4.Continuous dyeing	A-34
5.Printing	A-41
6.Making adds	A-42
7.Test methods used to determine properties	A-43
(1) Exhaustion and fixation curves	A-43
(2) Reactivity	A-43
(3) Substantivity	A-44
(4) Migration	A-44
(5) Wash - off	A-44
(6) Solubility	A-45
(7) Stripping	A-46
(8) Suitability to high temperature one bath dyeing	A-47
(9) Color constancy	A-48
(10) Effect of metallic ions	A-48
(11) Effect of fixing agents	A-49
(12) Effect of finishing resins	A-49
(13) Dischargeability	A-50
(14) Dependency on temperature	A-50
(15) Dependency on Glauber's salt	A-51
(16) Dependency on liquor ratio	A-51
(17) Dependency on alkali	A-51
(18) Color fastness	A-52
III Dyeing Sample	A-53
IV Dyeing Properties	A-53
V Everzol dye selection	A-54

1. INTRODUCTION :

In recent years, the sales of natural cellulosic fiber have steadily increased because of its excellent fiber properties in the textile industry. Consequently, the sales of reactive dyes for cellulosic fiber have also increased every year because of their brilliant shade, excellent wet fastness properties, and wide range of applications.

With increasing demand, customer have also begun to require a higher grade of all-around fastness properties for cellulosic fibers and their blends. As a result, the Everlight Chemical Industrial Corporation research department has developed new reactive dyes with high fastness, which can meet these requirements in the market. We have marketed these new reactive dyes as "Everzol dyes".

Everzol dyes are reactive dyes, vinyl sulfone, and vinyl sulfone with monochlorotriazine based. Since the combination of these reactive dyes is stable to acid hydrolysis, the stability of the dyed substrate over time is excellent. Also, after the completion of dyeing, the substantivity of the hydrolyzed dyes is considerably low, which leads to excellent wash-off properties for unfixed dyes.

Everzol dyes have a wide range of suitable dyeing temperatures and are highly reproducible in exhaust dyeing. Also, improvement of alkali stability in continuous dyeing, cold-pad-batch dyeing, and printing, have led to highly reproducible dyeing being obtained in both continuous dyeing and printing. In addition, Everzol dyes have excellent all-round wet fastness properties, which should meet the needs of every customer.

2. GENERAL DYEING METHODS OF EVERZOL DYES :

(1) Pretreatment of substrate :

The quality of the pretreated substrate prior to dyeing will affect the result of the dyeing. Oil and sizing agents that remained on the surface of the substrate should be avoided because they can cause uneven dyeing. Residual chemicals from the pretreatment should be thoroughly removed to prevent substrate damage in the dyeing process. It is essential that pretreatments such as desizing, scouring, bleaching, mercerizing etc, be carried out as carefully as possible.

Pretreatment Recipe :

Substrate : Knitted fabric.

Method : One bath scouring & bleaching process.

a. Wetting agent	:	0.5 g/l
b. Stabilizer	:	0.5 - 1 g/l
c. Hydrogen peroxide(35%)	:	5 - 10 g/l
d. Caustic soda (47°B'e)	:	1 - 2 g/l
or		
Caustic soda (47°B'e)		0.5 - 1 g/l
Soda ash		2 - 5 g/l

Treat for 40-60 minutes at 95°C

Substrate : Woven fabric.

Method : Two bath process.

(1)Desizing process :

a.Wetting agent	:	0.5 g/l
b.Desizing agent	:	2 - 3 g/l

Treat for 30 minutes at 95°C

(2)Scouring & bleaching process :

The same method as above. (Knitted fabric)

(2) Dissolving of dyes :

Everzol dyes are highly soluble in water. To completely dissolve in water pasted the Everzol dyes are with a small amount of warm water (40-50°C) with thorough stirring. Then hot water (80-90°C) to the paste and mix thoroughly.

When a particularly higher concentration of dye solution is required, it may be necessary to add a small amount of urea into the dye solution in order to improve the solubility of the dyestuffs.

(3) Dyeing methods :

Various kinds of dyeing methods can be applied depending upon the type and form of substrate to be dyed, and the kind of dyeing machines. For example : In yarn dyeing, it is suitable to use the package, cheese, or hank dyeing machine. On the other hand, in piece dyeing, it is suitable to use winch, jet, jigger, or continuous dyeing machine.

(4) Salt and alkali requirement of Everzol dyes :

Dyestuff Depth of shade	Glauber's Salt or Common Salt (g/L)		Alkali			Fixation Time (min)
	Unmercerized Cotton	Mercerized Cotton Viscose rayon	Soda ash (g/l)	Soda ash + Caustic soda (g/l) (38°B'e ml/l)	Na ₂ PO ₄ (g/l)	
Below 0.5%	20	10	10	5 + 0.5	6	30
0.5%~1.0%	30	20	15	5 + 0.5	6	45
1.0%~2.0%	40	30	20	5 + 1.0	8	60
2.0%~3.0%	50	40	20	5 + 1.0	8	60
3.0%~4.0%	60	50	20	5 + 1.0	8	60
4.0%~5.0%	70	60	20	5 + 1.0	10	60
5.0%~6.0%	80	70	20	5 + 2.0	10	60
Above 6.0%	80	70	20	5 + 2.0	10	90

Remark : (1) When dyeing with Everzol Turquoise Blue G and Brilliant Blue R s/p, Blue BRF 150% and Blue LX, only Glauber's salt is recommended.

(2) Dyeing with Everzol Brilliant Blue R s/p, the amount of Glauber's salt should not exceed 50 g/L.


(3) Caustic soda conc. 38° B'e (liquid form)

(5) Wasing on winch or Jet dyeing machine :


Bath	Temp.(°C)	Time(min)	Function
1	30-50	10-15	cold rinsing or over-flow rinsing
2	30-50	10-15	neutralizing
3	60-70	10-15	warm rinsing
4	80-98	10-15	hot rinsing
5	98	10-15	soaping
6	60-70	10-15	warm rinsing
7	30-50	10-15	cold rinsing

3. Exhaust dyeing :


(1) General method : Temperature rise method :

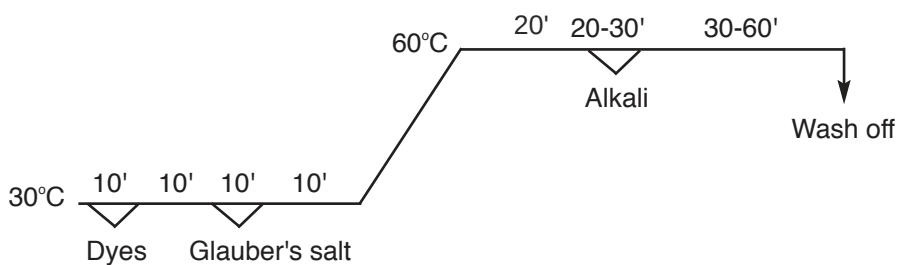


(2) Isothemol dyeing method :

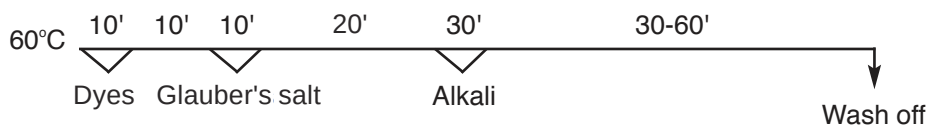


(3) Migration dyeing method : (for Viscise, Tencel, Modal, or heavy fabrics)

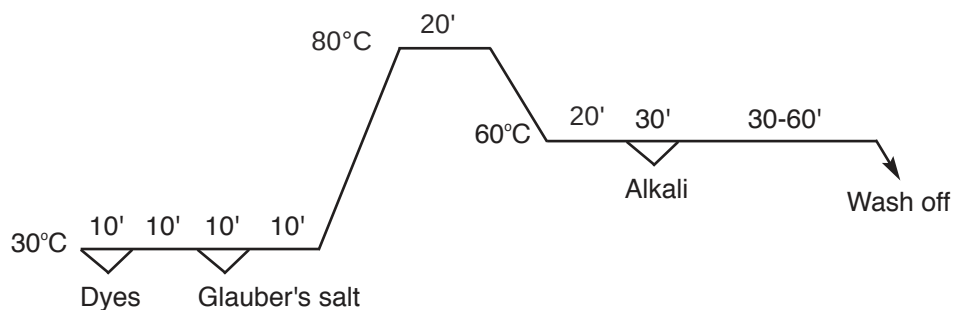


(4) Semi - All - In method :

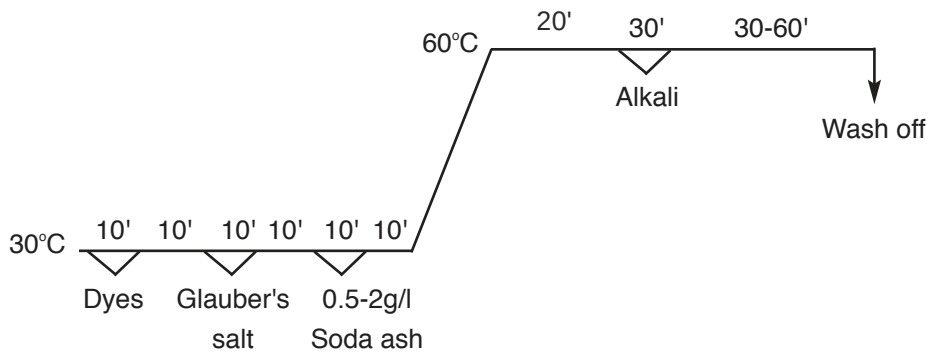

(5) Everzol Turquoise Blue G method :

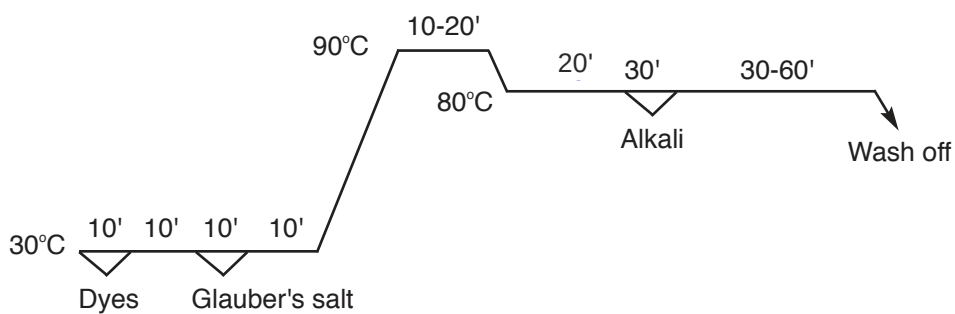


(6) Jigger method :

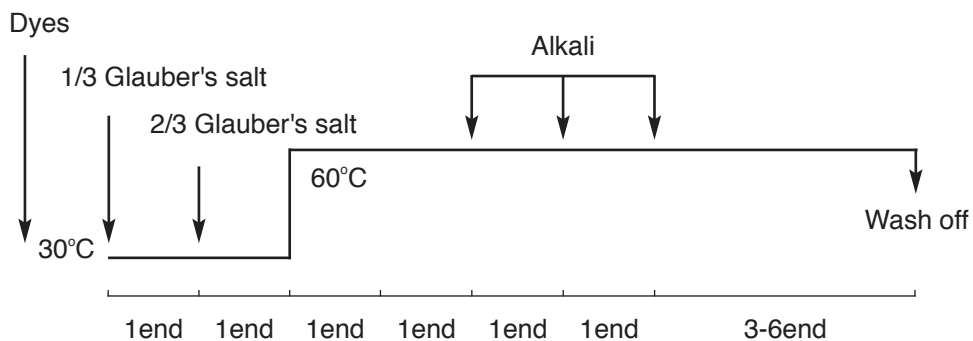

4. Continuous dyeing :

(1) Cold pad-batch process

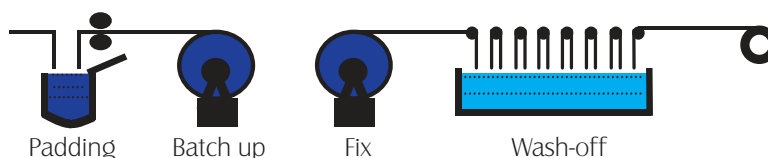

Alkali requirements :

We recommend 3 kinds of alkali for the cold pad-batch process.

A. Silicate free method : Everzol

dyes	X g/l
Caustic soda(38°B'e, 32.5%)	5+X/5 ml/l
Soda ash	0~20 g/l
Glauber's salt (option)	0~30 g/l

B. Sodium silicate method :

Sodium silicate			Amounts of Everzol dyes used (g/l)					
			~20	30	40	50	60	70 ↑
	g/l	ml/l	Amounts of caustic soda(38 °B'e, 32.5%) required (ml/l)					
37~40 °B'e	130	95	23.5	28.5	28.5	33.5	33.5	38.5
40~42 °B'e	110	75	23.5	28.5	28.5	33.5	33.5	38.5
48~50 °B'e	100	65	15	20	20	25	25	30
58~60 °B'e	90	50	6	11	11	16	16	21

C. Modified alkali method :

Sodium silicate			Amounts of Everzol dyes used (g/l)					
			~10	20	30	40	50	60 ↑
	g/l	ml/l	Amounts of caustic soda(38 °B'e, 32.5%) required (ml/l)					
37~40 °B'e	65	50	7	12	12	17	17	22
40~42 °B'e	55	40	7	12	12	17	17	22
48~50 °B'e	50	35	5	10	10	15	15	20
58~60 °B'e	45	25	3	7	7	11	11	16


Auxiliary :

The penetrating agent must also be stable in the padding liquor and be non-foaming. Urea can be added to improve the solubility of some dyes.

Notes :

The alkali C modified alkali method reduces the amount of sodium silicate and caustic soda needed. A fixation time over 16 hours or overnight is necessary. For application of all the recommended alkalis listed above, a mixing pump is required.

(2) Pad-dry-chemical pad-steam process

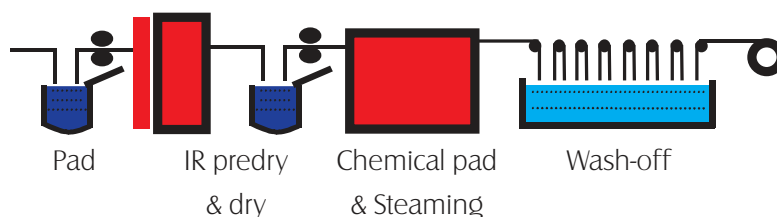

The dyes and chemical alkali are applied separately on the goods to be dyed in two batch continuous dyeing; a wide selection of dyes are available for this method.

Padding liquor condition :

Everzol dyes	x g/l
Migration inhibitor	1 g/l
Reduction inhibitor	10 g/l
Penetrating agent	0~2 g/l

The penetrating agent must also be stable in the padding liquor and be non-foaming. Reduction inhibitor can be added to prevent reduction of the reactive dyes. Urea can be added to improve the solubility of some dyes.

Drying :

- IR pre-drying
- Dry to about 30% residual moisture
- Dry at 110~130°C
- Cool goods after drying

The fabric should have adequate cooling after drying.

Intermediate drying is required in the pad-dry-pad-steam process. Usually, united infrared-heaters (pre-drying) are used with hot-flue machines or on steam heated cylinders (drying).

Chemicals padding and Steaming :

Stabilize and give uniform chemical padding across the width of the goods.


Chemicals requirement :

A. Sodium silicate (48~50°B'e)	60~70 %
B. Caustic soda (38 °B'e, 32.5%)	14~20 ml/l
Salt	250 g/l
C. Caustic soda (38 °B'e, 32.5%)	12~18 ml/l
Soda ash	20 g/l
Salt	250 g/l

Steaming :

Continuous fixation of reactive dyes in saturated steam at 102~105°C.

(3) Pad-dry-baking process

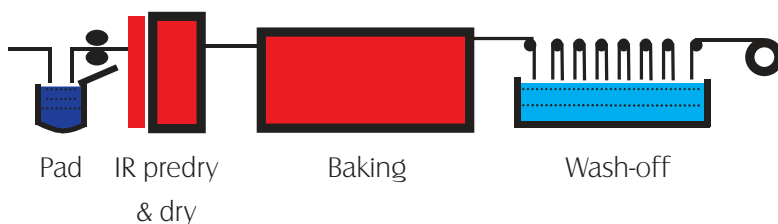

This is the one batch method continuous dyeing process.

Features :

Everzol dyes in pad-dry-baking process have :

- ☐ Even dyeing.
- ☐ Excellent stability in padding liquor.
- ☐ Excellent consistency in drying and baking.
- ☐ High productivity.


Padding liquor condition :

Everzol dyes	x g/l
Alkali	see Alkali requirements
Migration inhibitor	1 g/l
Reduction inhibitor	10 g/l
Urea	50~150 g/l
Penetrating agent	0~2 g/l
Borax	0~10 g/l

The penetrating agent must also be stable in the padding liquor and be non-foaming. Reduction inhibitor can be added to prevent reduction of the reactive dyes. Urea can be added to improve the solubility of some dyes, which will raise the color yield in this continuous process. Urea will not be necessary when the baking temperature is higher than 160 °C. Borax can be added to prevent the cotton component yellowing.

Alkali requirements :

The alkali requirements are diagrammed below :

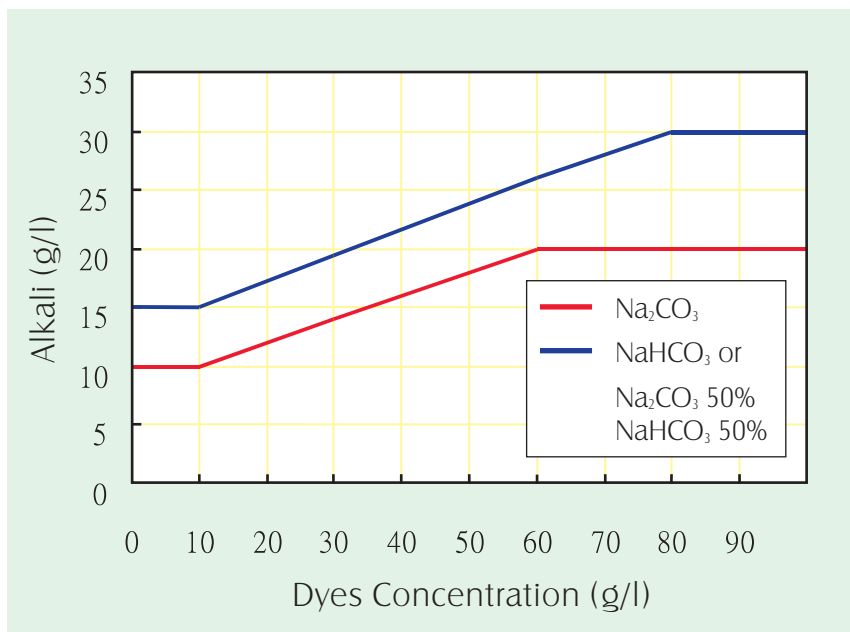

Drying :

- IR pre-drying
- Dry down to about 30% residual moisture.
- Dry at 100~110 °C


Baking :

4~6	min,	at 120 °C
3~4	min,	at 140 °C
2~3	min,	at 150 °C
2~3	min,	at 160 °C
1~2	min,	at 180 °C
1	min,	at 200 °C

Notes :

Take care about the goods yellowing at high temperature. At high temperature dyeing i.e. 180~200°C, fabric yellowing should be counted in color matching.

(4) Pad-Steam Process

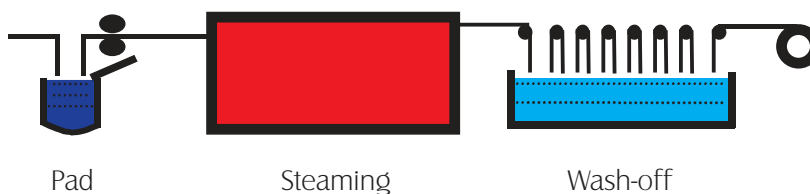

Padding liquor condition :

Everzol dyes	x g/l
Caustic soda (38 °B'e, 32.5%)	see Alkali requirements
Soda ash	20 g/l
Glauber's salt (option)	0-30 g/l
Reduction inhibitor	10 g/l
Penetrating agent	2 g/l
Padding liquor temperature at 20~25°C	

Alkali mixer is required.


The penetrating agent must also be stable in the padding liquor and be non-foaming.

Reduction inhibitor can be added to prevent reduction of the reactive dyes.


Steaming :

60~100 seconds in saturated steam at 102~105°C.

Alkali requirements :

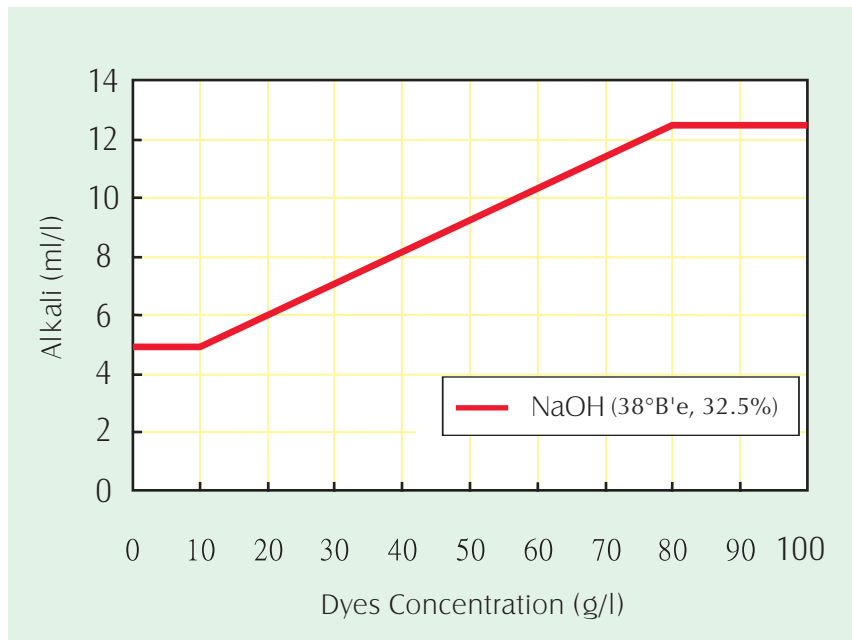

(5) Emoistfix process

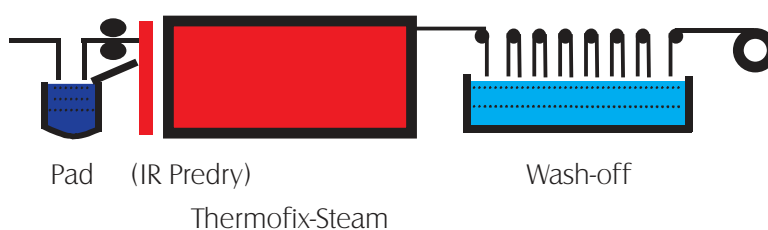

The Emoistfix process is combination of a continuous steaming and a drying process. That combines with dyestuff and alkali padding together and then drying-fixing in one batch process by continuous application to make simple and more economical.

Padding liquor condition :

It is essential to make alkali and Everzol dye solution separately.

Padding liquor:

Everzol dyes	X g/l
Reduction inhibitor	5-10 g/l
Migration inhibitor (option)	0-1 g/l
Penetrating agent in padding liquor	0-2 g/l
Urea (option)	50 g/l

The penetrating agent must also be stable in the padding liquor and be non-foaming. Reduction inhibitor can be added to prevent reduction of the reactive dyes. Urea can be added to improve the solubility of some dyes.

Alkali requirements :

Everzol dyes	Amounts of Everzol dyes used (g/l)					
	~20	20~40	40~60	60~80	80~100	100 ↑
	Amounts of caustic soda (38 °B'e, 32.5%) required (ml/l)					
NaOH (38 °B'e, 32.5%)	7	11	14	17	21	24
Na ₂ CO ₃	20 g/l					

Alkali mixer is required as same as cold pad-batch process.

Padding liquor temperature at 20-25°C.

Drying and fixation :


2-3min at 120-130°C, it depends on the substrate.

Humidity control at 25%

Make sure the dyed fabric is dry at the end of machine to achieve color yield completely.

5. Printing :


3-1 One-phase saturated steaming process

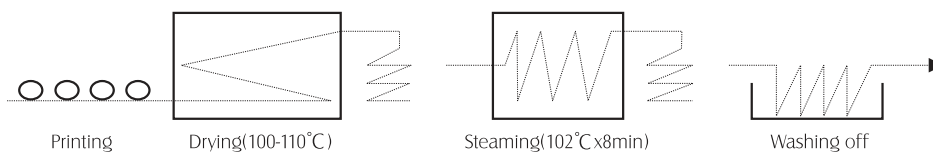

3-1-1 Printing paste

Everzol dyes	x	g
NaHCO ₃	20	
Urea	100	
Reduction inhibitor	10	
Thickener	y	
Water	z	
		1000 g

3-2. Two-phase alkali pad-steaming process

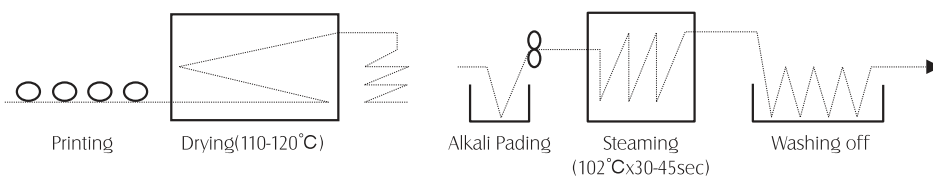

3-2-1 Printing paste

Everzol dyes	x	g
Reduction inhibitor	10	
Thickener	y	
Water	z	
		1000 g

3-2-2 Alkali bath composition

NaOH(38°B'e)	10-15 ml/l
Na ₂ CO ₃	150 g/l
K ₂ CO ₃	50 g/l
Na ₂ SO ₄	150-200 g/l

6. Making adds :

After dyeing for a predetermined period of time, a part of the dyeing substrate is sampled and dried to confirm whether or not the desired shade has been obtained. If a dyes addition is necessary, there are two kinds of adding method; as described below :

METHOD 1 :

When it is a slight difference in shade, and an add is necessary :

- * Cool the dye-bath to 40°C.
- * Add the well-diluted pre-dissolved dyes.
- * Dye for 10 minutes at 40°C.
- * Raise the temperature to 60°C.
- * Dye for 30 minutes at 60°C.
- * Check shade °

METHOD 2 :

When it is necessary to correct the shade to a large extent, the corrective addition is carried out by the following procedure :

- * Drop one-third or half of the dye-bath and refill with cold water, to lower the temperature and the electrolyte concentration and thereby slow the strike rate of the dyes addition.
- * Add the well-diluted pre-dissolved dyes.
- * Dye for 10 minutes.
- * Raise the temperature to 60°C.
- * Dye for 30 minutes at 60°C.
- * Check shade.

In either case, it is not neccessary to add any Glauber's salt or alkali into the dye-bath.

7. Test methods used to determine properties :

(1) Exhaustion and fixation curves :

The exhaustion of reactive dyes is significantly affected by various factors such as the form, preparation and crystallinity of materials to be dyed, as well as processes such as mercerization .

The degree of exhaustion and fixation of Everzol dyes, respectively, under the following conditions as shown in graphs.

Material	: Unmercerized cotton
Depth of shade	: Everzol Y C-GL, R C-3B, B-BB, Everzol LX/LF/CS, Black C-RL : 1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf
Glauber's salt	: please refer to the table of salt and alkali requirement
Soda ash	: please refer to the table of salt and alkali requirement
Liquor ratio	: 1 : 10
Dyeing temperature	: 60°C (Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G 80°C)
Dyeing time	: 60 minutes after alkali added

(2) Reactivity :

The classification was made on the basis of an amount of alkali (Soda ash) to give a maximum strength.

Assessment :

Amount of alkali required to give Reactivity Classification

pH value	Reactivity group	Classification
<11	I	High reactivity
11-11.5	II	Medium reactivity
>11.5	III	Low reactivity

(3) Substantivity :

The classification was made on the basis of a dye-uptake before the addition of alkali.

Assessment :

Dye-uptake	Substantivity group	Classification
>75%	A	High substantivity
40-75%	B	Medium substantivity
<40%	C	Low substantivity

(4) Migration property :

The migration test was carried out in the following procedure :

A test fabric was adsorbed with dyes by primary exhaustion under the following conditions and then white fabric (unadsorbed) and the test fabric (adsorbed) were treated together in a bath at a liquor ratio of 1:10 containing 60 g/l Glauber's salt at 60°C for 30 minutes, followed by fixation with an addition of 20 g/l Soda ash.

Depth of shade : Everzol Y C-GL, R C-3B, B-BB, Everzol LX/LF/CS, Black C-RL : 1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf

Glauber's salt : please refer to the table of salt and alkali requirement

Liquor ratio : 1 : 10

Dyeing temperature : 60°C (Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G : 80°C)

Dyeing time : 60 minutes after alkali added

Assessment :

A difference in depth between the test fabric originally absorbed with dyes and the fabric migrated was assessed by means of the grey scale for assessing change in color.

(5) Washing off property :

10 g unmercerized cotton knit was dyed at 3% owf by normal method and the dyed sample was washed in the sequence given below to measure the amount of unfixed dyes removed from each step. (Everzol Y C-GL, R C-3B, B BB, Everzol LX/LF/CS, BK C-RL 1% owf) ; The other Everzol & Everzol FC/ED/MX : 3% owf

- (1) 60°C, 5 min. water
- (2) 80°C, 5 min. hot water
- (3) 98°C, 5 min. soaping (neutral anionic surfactant, 3 g/l)
- (4) 80°C, 5 min. hot water
- (5) 60°C, 5 min. water

Assessment :

The washing off property was classified into five classes based on the ratio of the amount of unfixed dyes removed at steps 1 and 2 to the total amount removed.

$$\frac{\text{Amount removed at steps 1 and 2}}{\text{Total amount removed}} \times 100 = (\%)$$

Classification :

>96%	5	71 - 75%	2-3
91 - 96%	4-5	60 - 70%	2
86 - 90%	4	61 - 65%	1-2
81 - 85%	3-4	<60%	1
76 - 80%	3		

(6) Solubility :

(a) Without addition of auxiliary

A predetermined amount of dye was dissolved in warm water (50°C), and after cooling down to 25°C, the dye solution was filtered with filter paper. The solubility was measured based on the presence or absence of residue on the filter paper.

(b) With an addition of 50 g/l Glauber's salt

A predetermined amount of dye and 50 g/l Glauber's salt were dissolved in warm water (50°C), and then the solubility was measured with the same method as in (a).

(7) Stripping :

There are many methods to strip materials dyed with Everzol dyes. The stripping test was made on cotton fabrics dyed at a dyeing depth of 3.0% owf under the following conditions : (Everzol Y C-GL, R C-3B, B-BB, Everzol LX/LF/CS, Black C-RL : 1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf)

(1) Alkali treatment :

Caustic soda(38°B'e) : 20 ml/l
Liquor ratio : 1 : 10
Temperature & Time : 80°C × 30 min
Hot rinsing, neutralizing and cold rinsing.

(2) Reduction treatment :

Caustic soda(38°B'e) : 20 ml/l
Sodium hydrosulfite : 5 g/l
Liquor ratio : 1 : 10
Temperature & Time : 80°C × 30 min.
Hot rinsing, neutralizing and cold rinsing.

(3) Combined reduction and oxidation treatments :

After the treatment (2), the fabrics are treated in the following chlorine bath :
Sodium hypochlorite (available chlorine 12%) : 8 g/l
Liquor ratio : 1 : 10
Temperature & Time : 30°C × 30 min.
The treated fabrics are cold rinsed, dechlorinated with 1 g/l sodium bisulfite at 50°C, hot rinsed and cold rinsed.

(4) Combined oxidation and reduction treatments :

Sodium hypochlorite (available chlorine 12%) : 8 g/l
Liquor ratio : 1 : 10
Temperature & Time : 30°C × 30 min.
After the treatment and cold rinsing, the fabrics are further treated under the conditions (2).

Assessment :

The degree of stripping was assessed by means of the grey scale for assessing staining compared to original un-dyed fabric.


Classification :

- (1) × : unsuitable (below grade 2)
- (2) △ : moderate (between grade 2-3 to 3)
- (3) ○ : suitable (above grade 3-4)

(8) Suitability to high temperature one bath dyeing :

The suitability to high temperature one bath dyeing was examined by comparing the depth and color of the dyed fabrics obtained as follows with those of normal method.

(a) Stability to dyed fabric :

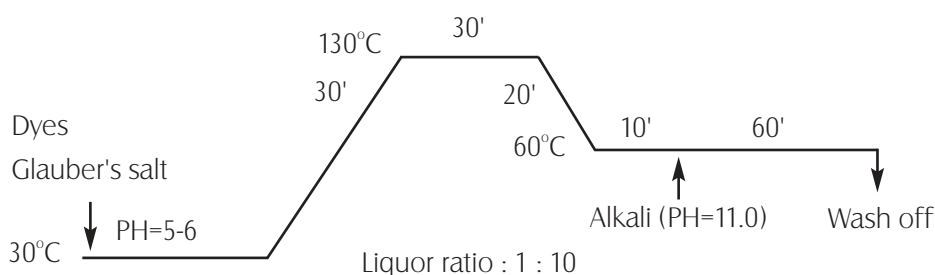

Assessment :

The shade change of the dyed fabric obtained by the above method was assessed against that obtained by the normal method by means of the grey scale for assessing the change of color.

(b) Stability to dye liquor :

Depth of shade : Everzol Y C-GL, R C-3B, B-BB, Everzol LX/LF/CS, Black C-RL :
1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf

Liquor ratio : 1 : 10

The above dye liquor was adjusted to PH 5, and without adding any fabric to be dyed, treated at 130°C for 30 minutes. After cooling down the liquor to 60°C, unmercerized cotton knits was dyed by the normal method in this dye bath.

Assessment :

The shade change of the dyed material obtained by the above method was assessed against that obtained by the normal method by means of the grey scale for assessing the change of color.

(9) Color constancy :

The shades of a sample of dyed materials under tungsten filament lamp (Inca) and daylight fluorescent lamp (TL84) were compared with that under standard light source (D65), and the degree of shade difference was measured and classified as follows :

Symbols in parentheses mean the direction of difference in shade.

Y : Yellower R : Redder B : Bluer G : Greener

(10) Effect of metallic ion :

The effect of metallic ions on the shade and depth of dyeing was examined by adding metallic ions into the dyebath.

Material	: Unmercerized cotton knits
Depth of shade	: Everzol Y C-GL, R C-3B, B-BB, Everzol LX/LF/CS, Black C-RL : 1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf
Glauber' salt	: please refer to the table of salt and alkali requirement :
Soda ash	please refer to the table of salt and alkali requiremer
Liquor ratio	: 1 : 10
Metallic ions	Fe ²⁺ ferrous chloride (20 ppm as Fe ²⁺) Cu ²⁺ copper sulfate (20 ppm as Cu ²⁺)
Dyeing temperature	: 60°C (Yellow 4GL, Yellow 3GL, Green 6B, Turq. Blue G, Yellow ED-2G 80°C)
Dyeing time	: 60 minutes after alkali added

Assessment :

The difference in shade and yield between the samples dyed with and without addition of metallic ion was judged by means of the grey scale for assessing the change in color.

(11) Effect of fixing agent :

- Fixing agent : (A) Polyethylene polyamine.
(B) Quaternary Ammonium salt.

The effect of fixing agent is measured by the following conditions :

- Depth of shade : Everzol Y C-GL, R C-3B, B-BB, Everzol LX/LF/CS, Black C-RL : 1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf
Fixing agent : 2.0% owf
Fixing temperature : 60°C
Fixing time : 20 minutes.

Assessment :

The difference in shade between the dyed samples with and without fixing was judged by means of grey scale for assessing change in color.

(12) Effect of finishing resin :

- Finishing resin : (A) Melamine resin.
(B) Glyoxal resin.

The effect of finishing agent was measured by the following conditions :

- Depth of shade : Everzol Y C-GL, R C-3B, B-BB, Everzol LX/LF/CS, Black C-RL : 1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf
Finishing agent : 40 g/l
Catalyst : 8 g/l
Finishing procedure Padding → Drying → Baking.
Padding (pick-up) : 70%
Drying : 100°C × 3 minutes.
Baking : 160°C × 3 minutes.

Assessment :

The difference in shade between the dyed samples with and without finishing was judged by means of grey scale for assessing change in color.

(13) Dischargeability :

Dischargeability varies with the depth of the ground dyeing and the recipe of the white discharge paste. The discharge test was made on cotton fabrics dyed at 3% owf (Everzol Y C-GL, R C-3B, B BB, Dark Blue LF, Everzol LX/LF/CS, Black C-RL : 1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf) by the following recipes.

(1) Recipe of discharge paste :

Composition/Method	Neutral	Alkaline
Rongalit C	200	200
Soda ash	---	50
Water	250	200
Thickener	550	550
Total	1000 parts	1000 parts

(2) Procedure :

After printing, the fabrics were dried at 60°C, steamed at 102°C for 5 to 8 minutes, followed by rinsing and soaping.

(14) Dependency on temperature :

Material	: Unmercerized cotton knits
Depth of shade	: (Everzol Y C-GL, R C-3B, B BB, Dark Blue LF, Everzol LX/LF/CS, Black C-RL : 1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf)
Glauber's salt	: please refer to the table of salt and alkali requirement
Soda ash	: please refer to the table of salt and alkali requirement
Liquor ratio	: 1 : 10
Dyeing temperature	: 40 - 80°C (Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G 60 - 98°C)
Dyeing time	: 60 minutes after alkali added

(15) Dependency on Glauber's salt :

Material	: Unmercerized cotton knits
Depth of shade	: Everzol Y C-GL, R C-3B, B BB, Dark Blue LF, Everzol LX/LF/CS, Black C-RL : 1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf
Glauber's salt	: 30, 40, 50, 60, 70, 80 g/l
Soda ash	: please refer to the table of salt and alkali requirement
Liquor ratio	: 1 : 10
Dyeing temperature	: 60°C (Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G 80°C)
Dyeing time	: 60 minutes after alkali added

(16) Dependency on liquor ratio :

Material	: Unmercerized cotton knit
Depth of shade	: Everzol Y C-GL, R C-3B, B BB, Everzol LX, Everzol LF, Black C-RL : 1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf
Glauber's salt	: please refer to the table of salt and alkali requirement
Soda ash	: please refer to the table of salt and alkali requirement
Liquor ratio	: 1 : 5~120 (1:10 as standard)
Dyeing temperature	: 60°C (Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G 80°C)
Dyeing time	: 60 minutes after alkali added

(17) Dependency on alkali :

Material	: Unmercerized cotton knit
Depth of shade	: (Everzol Y C-GL, R C-3B, B BB, Dark Blue LF, Everzol LX/LF/CS, Black C-RL : 1% owf ; The other Everzol & Everzol FC/ED/MX : 3% owf)
Glauber's salt	: please refer to the table of salt and alkali requirement
Alkali	: Soda ash g/l : 5, 10, 15, 20*, 5, 5, NaOH (38°B'e) ml/l : -, -, -, -, 1, 2,
Liquor ratio	: 1 : 10
Dyeing temperature	: 60°C (Turq. Blue G, Yellow 4GL, Yellow 3GL, Yellow ED-2G 80°C)
Dyeing time	: 60 minutes after alkali added

(18) Color fastness :

1. Fastness to washing	ISO 105 C10 Method B ISO 105 C10 Method C ISO 105 C10 Method D ISO 105 C06-C1S ISO 105 C06-C2S Marks & Spencer C4A
2. Fastness to water	ISO 105 E01
3. Fastness to hot water	ISO 105 E08
4. Fastness to sea water	ISO 105 E02
5. Fastness to post mercerizing	ISO 105 X04
6. Fastness to acid hydrolysis	1% Acetic acid solution for 30 min, 38°C X 6 hours
7. Fastness to perspiration	ISO 105 E04
8. Fastness to chlorinated water (20ppm)	ISO 105 E03
Peroxide Bleaching	ISO 105 N02
9. Fastness to rubbing (dry, wet)	ISO 105 X 12
10. Fastness to detergent light	Marks & Spencer C9A
11. Fastness to multi-laundering(M&S C10A)	ISO 105 C09
12. Fastness to saliva	DIN 53160
13. Fastness to hot-pressing	ISO 105 X 11
14. Fastness to light	ISO 105 B02 & AATCC 16-3
15. Fastness to Perspiration light	ISO 105 B07 & ATCC 125
16. Colorfastness to Nitrogen Oxides	ISO 105-G01

Everzol Dyes

頁 page	染料 dyes	1%	3%	染料特性	Characteristics
1	Brilliant Yellow 4GL			1. 可用於連續染色、印花與浸染 2. 適合艷黃色，綠色配色組合 3. 與Turq. Blue G配色染色時，染色溫度為80°C	1. Suitable for continuous dyeing, printing and exhaust dyeing 2. Suitable for brilliant yellow or green colors 3. Optimum dyeing temperature at 80°C while combined with Everzol Turq. Blue G.
3	Yellow 3GL			1. 適合艷黃色，綠色配色組合 2. 與Everzol Brill. Turq. Blue G配色染色時，染色溫度為80°C	1. Suitable for brilliant yellow or green colors 2. Optimum dyeing temperature at 80°C while combined with Everzol Turq. Blue G
5	Yellow C-GL			1. 可適用於浸染，冷壓染或拔染 2. 與Red C-3B及Blue BB 133%在極淺色組合性佳 3. 淺色耐日光及耐汗日光堅牢度佳	1. Suitable for exhaust, dischargeable dyeing and CPB 2. Excellent compatibility with Red C-3B and Blue BB 133% at very pale shade 3. Excellent light fastness and perspiration light fastness at pale shade
7	Yellow GR			1. 用途廣泛之鮮黃色 2. 可用於連續染色 3. 適合防、拔染底色	1. Versatile yellow dyes 2. Suitable for continuous dyeing 3. Suitable for resistance, discharge printing
9	Yellow CE-N			1. 無光變色性之真正金黃色染料 2. 極佳的均染性及染色再現性	1. Golden yellow dyes with non-photochromic 2. Good leveling and reproducibility properties
11	Golden Yellow RNL			1. 主要的黃色三原色 2. 適合防拔染底色染色 3. 同時適用於浸染、連續染色、冷壓染染色	1. Primary yellow dyes 2. Suitable for discharge and resist printing 3. Suitable for exhaust dyeing, CPB and continuous dyeing
13	Yellow 3RS			1. 黃色三原色，配色色域廣 2. 異二官能基成分，極佳之耐氯水牢度 3. 耐多次水洗牢度佳	1. Primary yellow, broad color range for color match 2. Bi-functional group dyes, excellent chlorinated water fastness 3. Unique UK-TO washing fastness
15	Orange 3R			1. 可用於連續染色及印花 2. 適合防、拔染底色	1. Suitable for continuous dyeing and printing 2. Suitable for resist, discharge printing
17	Scarlet 3GF			1. 鮮豔的猩紅色 2. 搭配Red BS可達極深色 3. 耐氯水牢度佳	1. Brilliant scarlet dyes 2. Compatible with Red BS for deep red or scarlet shades 3. Suitable for exhaust dyeing 4. Excellent chlorinated water fastness
19	Red C-3B			1. 可適用於浸染，冷壓染及拔染 2. 與Yellow C-GL及Blue BB 133%在極淺色組合性佳 3. 耐氯水牢度及日光牢度佳	1. Suitable for exhaust, dischargeable dyeing and CPB 2. Excellent compatibility with Yellow C-GL and Blue BB 133% at very pale shade 3. Excellent light fastness & chlorinated water fastness at pale shade
21	Brilliant Red F2B			1. 鮮豔的紅色 2. 紅色淺三原色，配色色域廣	1. Brilliant red dyes 2. Primary light red, broad color range for color match

Everzol Dyes

頁 page	染料 dyes	1%	3%	染料特性	Characteristics
23	Red BB			1. 可用於連續染色及印花 2. 適合防、拔染底色	1. Suitable for continuous dyeing and printing 2. Suitable for resist, discharge printing
25	Brilliant Red F3B			1. 三原色之鮮豔紅色，可用於浸染和 連染 2. 染深性佳 3. 可做防染和拔染	1. Brilliant trichromatic red, suitable for exhaust dyeing and continuous dyeing 2. Excellent build-up 3. Suitable for discharge printing and resist printing
27	Red 3BS			1. 紅色三原色，配色色域廣 2. 異二官能基成分，極佳之耐氯水牢 度 3. 耐多次水洗牢度佳	1. A primary red, broad color range for color match 2. Bi-function group dyes, excellent chlorinated water fastness. 3. Unique UK-TO washing fastness
29	Red BS			1. 得色率高，特別推薦施染於深紅色 系 2. 鹽依存性特佳	1. High color yield, specially recommended for deep red 2. Excellent property of dependence to salt
31	Red 6B			1. 適合於艷紅、豔紫色系 2. 染深色性佳 3. 耐氯水牢度佳	1. Important item for brilliant red, violet , purple shades 2. Excellent build-up 3. Excellent chlorinated water fastness
33	Green 6B			1. 適用於綠色系 2. 優異日光牢度 3. 均染性佳	1. Suitable for green shades 2. Unique lightfastness 3. Excellent levelness
35	Turq. Blue G			1. 適合艷綠色配色組合 2. 與Yellow 3GL, Yellow 4GL, Yellow ED-2G 配色染色時，染色溫度為80°C 3. 鹽類添加推薦使用芒硝	1. Suitable for color match of brilliant green shade 2. Optimum dyeing temperature at 80°C while combined with Everzol Yellow 3GL, 4GL and Yellow ED-2G 3. Sodium sulfate is recommended as salt
37	Brilliant Blue R s/p			1. 耐日光堅牢度佳 2. 鹽類添加推薦使用芒硝 3. 鹽類最高使用濃度不高於50g/l	1. Excellent lightfastness 2. Sodium sulfate is recommended as a salt 3. Max. salt dosage 50g/l in exhaust dyeing.
39	Royal Blue E-FR			1. 適合於寶藍、豔紫色系 2. 染深色性佳及受染因變化更穩定 3. 各項牢度及染色特性優異	1. Brilliant royal blue, violet, purple shades 2. Excellent build-up & less sensitivity to dyeing parameters 3. Overwhelming fastness & dyeing performance
41	Blue BB			1. 均染性佳之藍色淺三原色 2. 耐日光堅牢度佳 3. 適合防染底色	1. Primary light blue of trichromatic 2. Excellent lightfastness 3. Suitable for resist printing
43	Blue BRF 150%			1. 藍色三原色，配色色域廣 2. 淺色耐日光牢度佳 3. 均染性及再現性佳 4. 鹽類添加建議使用芒硝	1. Trichromatic blue, broad color range for color match 2. Unique light fastness at pale shade 3. Outstanding leveling property and reproducibility 4. Sodium sulfate is recommended as salt

Everzol Dyes

頁 page	染料 dyes	1%	3%	染料特性	Characteristics
45	Blue NXF			1. 優異耐氣體便褪色牢度 2. 優異日光牢度及氯水牢度 3. 搭配 Yellow CS/Red LF-4B 具穩定均染性	1. Unique fastness to nitrogen oxides 2. Unique fastness to light and chlorinated water 3. Excellent compatibility with Yellow CS/Red LF-4B
47	Blue RGB			1. 經濟之丈青色，可用於浸染及連續染色 2. 染深性佳 3. 中高之日光牢度	1. Economical navy dyes, suitable for exhaust dyeing and continuous dyeing 2. Excellent build-up 3. Moderate to high lightfastness
49	Navy Blue FBN			1. 藍色三原色，配色色域廣 2. 異二官能基成分，極佳之耐氯水牢度 3. 耐多次水洗牢度佳	1. A primary navy, broad color range for color match 2. Bi-functional group dyes, excellent chlorinated water fastness 3. Unique UK-TO washing fastness
51	Navy Blue GG			1. 用途廣泛之綠味藍色，適合墨綠色配色主體 2. 耐氯水牢度佳 3. 適合防、拔染底色	1. Versatile & greenish navy dye with greenish, suitable for color match of dark forest green 2. Excellent chlorinated water fastness 3. Suitable for resist, discharge printing
53	Navy Blue RGB H/C			1. 用途廣泛之綠味藍色，具經濟性 2. 耐氯水牢度佳 3. 適合防、拔染底色	1. Economical & versatile greenish navy dyes 2. Excellent chlorinated water fastness 3. Suitable for resist, discharge printing
55	Black B			1. 用途廣泛，具經濟性中、深濃度三原色 2. 最普遍應用之反應性黑色染料 3. 適合防、拔染底色	1. Economical & versatile heavy navy dyes 2. Most common used of reactive black dyes 3. Suitable for resist, discharge printing
57	Black C-RL			1. 適用於浸染、連續染色 2. 推薦於淺、中色染色 3. 淺色日光牢度優異	1. Suitable for exhaust and continuous dyeing 2. Recommended for pale to medium shade dyeing 3. Excellent light fastness at pale shade

Everzol Dyes

頁 page	染料 dyes	3%	6%	染料特性	Characteristics
59	Black GR			1. 最經濟、用途廣泛之黑色染料	1. Economical & versatile black dyes.
61	Black GRN			1. 最經濟、用途廣泛之黑色染料	1. Economical & versatile black dyes.
63	Black N			1. 用途廣泛、均染性佳之黑色染料 2. 適合防、拔染底色	1. Versatile, good leveling black dyes. 2. Suitable for resist, discharge printing
65	Black NR			1. 用途廣泛、均染性佳之黑色染料 2. 適合防、拔染底色	1. Versatile, good leveling black dyes. 2. Suitable for resist, discharge printing
67	Black GSP			1. 適合防、拔染底色 2. 耐後絲光牢度佳 3. 耐多次水洗牢度佳	1. Suitable for resist, discharge printing 2. Excellent colorfastness to post mercerizing 3. Good for UK-TO washing fastness
69	Black MWF			1. 適合防、拔染底色 2. 耐後絲光牢度佳 3. 耐多次水洗牢度佳	1. Suitable for resist, discharge printing 2. Excellent colorfastness to post mercerizing 3. Excellent for UK-TO washing fastness
71	Black DGL			1. 極佳染深力度之黑色染料 2. 偏綠味之黑色 3. 適合防、拔染色之底色 4. Cotton/Lycra染色時對Lycra污染少	1. Deep black with excellent build-up 2. Greenish black 3. Suitable for resist, discharge printing 4. Less lycra cross-dyeing for cotton/lycra dyeing
73	Black DRL			1. 極佳染深力度之黑色染料 2. 偏紅味之黑色 3. 適合防、拔染色之底色	1. Deep black with excellent build-up 2. Reddish black 3. Suitable for resist, discharge printing

Everzol LX & LF Dyes

頁 page	染料 dyes	0.3%	1%	染料特性	Characteristics
75	Yellow LX			1. 黃色三原色，配色色域廣 2. 與Red LX，Blue LX染極淺色時，均染性再現性佳 3. 淺色耐氯水牢度佳	1. Tinctorial yellow, broad color yield for color match 2. Compatible with Red LX, Blue LX at very pale shade dyeing with outstanding leveling and reproducibility 3. Excellent chlorinated water fastness
77	Red LX			1. 紅色三原色，配色色域廣 2. 與Yellow LX，Blue LX染極淺色時，均染性再現性佳	1. Tinctorial red, broad color yield for color match 2. Compatible with Yellow LX, Blue LX at very pale shade dyeing with outstanding leveling and reproducibility
79	Blue LX			1. 藍色三原色，配色色域廣 2. 與Yellow LX，Red LX染極淺色時，均染性再現性佳 3. 鹽類添加建議使用芒硝	1. Tinctorial blue, broad color yield for color match 2. Compatible with Yellow LX, Red LX at very pale shade dyeing with outstanding leveling and reproducibility 3. Glauber's salt is recommended
81	Navy LX			1. 丈青色三原色，配色色域廣 2. 異二官能基成份，極佳之耐氯水牢度 3. 耐多次水洗牢度佳 4. 均染性及再現性佳	1. Primary navy, broad color range for color match 2. Bi-functional group dyes, excellent chlorinated water fastness 3. Unique UK-TO washing fastness 4. Excellent leveling and reproducibility
83	Red LF-B			1. 用途廣泛，可用於浸染和連染 2. 極淺色具優良的耐曬與耐汗日光染色堅牢度 3. 與Everzol Yellow LX, Blue LX之組合性佳 4. 非含金染料	1. Suitable for exhaust dyeing and continuous dyeing 2. Unique light fastness and perspiration light fastness at pale shade 3. Compatible with Everzol Yellow LX, Blue LX 4. Metal-free red dyes
85	Red LF-2B			1. 適用於浸染、連續染色 2. 適用於拔染底色 3. 在極淺色有優異之日光牢度及汗日光牢度 4. 非含金染料	1. Suitable for exhaust and continuous dyeing 2. Suitable for discharge printity 3. Unique light and perspiration light fastness with Yellow LX and Blue LX at very pale shade 4. Metal-free red dyes
87	Red LF-4B			1. 優異的日光及汗日光牢度 2. 極佳的染深性 3. 中色域高日光極具經濟性	1. Excellent light and perspiration lightfastness 2. Unique build-up 3. Economical choice for high lightfastness in mid-gamut application
89	Grey LF			1. 高耐日曬以及高耐汗曬牢度 2. 絕佳的均染性以及染色再現性 3. 良好的耐氯水堅牢度	1. High light fastness & perspiration light fastness 2. Excellent levelness and reproducibility 3. Exceptional chlorinated water fastness
91	Dark Blue LF			1. 適用於浸染及連染 2. 高日光及高汗日光牢度需求 3. 推薦使用於中等濃度染色	1. Suitable for exhaust & continuous dyeing 2. Excellent lightfastness & perspiration light fastness 3. Recommend for medium shade dyeing

Everzol FC Dyes

頁 page	染料 dyes	1%	3%	染料特性	Characteristics
93	Flavine FC			1. 適合於鮮豔螢光黃及亮綠色 2. 均染性佳及優異染色再現性 3. 優異之水牢度	1. Fashionable brilliant fluorescent yellow & green shades 2. Unique levelness & Right First Time performance 3. Excellent wet fastness
95	Orange FC			1. 適合於艷橙、大紅色流行色系 2. 高彩度、高染深性 3. 高日光、高汗日光、高耐氯水牢度	1. Suitable for very brilliant orange, scarlet fashionable colors 2. High chromatic, good build-Up 3. Exceptional lightfastness, perspiration lightfastness, chlorinated water fastness
97	Scarlet FC			1. 適合於鮮豔緋紅、大紅流行色系 2. 高彩度、高染深性、洗淨性佳 3. 各項牢度優異	1. Suitable for very brilliant scarlet, red fashionable colors 2. High chromatic, good build-up, easy wash-off 3. Overwhelming fastness performance
99	Red FC			1. 高彩度之紅色染料 2. 適合於鮮豔亮紅、紫色流行色系 3. 搭配Everzol Brilliant Blue FC 於鮮豔紫色系	1. High chromatic red dyes 2. Suitable for very brilliant red & violet fashionable colors 3. Compatible with Everzol Blue FC for violet & purple shades
101	Blue FC			1. 適合於鮮豔天空藍色、紫色系 2. 均染性佳 3. 優異之日光及濕牢度	1. Extraordinary brilliant sky blue & violet & purple shades 2. Unique leveling performance 3. Excellent lightfastness & wet fastness

Everzol CS/MX Dyes

頁 page	染料 dyes	0.3%	1%	染料特性	Characteristics
103	Yellow CS			1. 敏感色穩定性佳 2. 高耐日曬以及良好的耐氯水堅牢度 3. 絕佳的均染性以及染色再現性 4. 無光變色	1. Suitable for critical colors dyeing 2. Excellent lightfastness & exceptional chlorinated water fastness 3. Excellent leveling performance & reproducibility 4. Non-photochromic
105	Orange CS			1. 敏感色穩定性佳 2. 高耐日曬以及良好的耐氯水堅牢度 3. 絕佳的均染性以及染色再現性	1. Suitable for critical colors dyeing 2. Excellent lightfastness & exceptional chlorinated water fastness 3. Excellent levelness performance & reproducibility
107	Red Brown CS			1. 敏感色穩定性佳 2. 高耐日曬以及良好的耐氯水堅牢度 3. 絕佳的均染性以及染色再現性	1. Suitable for critical colors dyeing 2. Excellent lightfastness & exceptional chlorinated water fastness 3. Excellent levelness performance & reproducibility
109	Olive CS			1. 敏感色穩定性佳 2. 高耐日曬以及良好的耐氯水堅牢度 3. 絕佳的均染性以及染色再現性	1. Suitable for critical colors dyeing 2. Excellent lightfastness & exceptional chlorinated water fastness 3. Excellent levelness performance & reproducibility
111	Grey CS			1. 敏感色穩定性佳 2. 高耐日曬以及良好的耐氯水堅牢度 3. 絕佳的均染性以及染色再現性	1. Suitable for critical colors dyeing 2. Excellent lightfastness and good chlorinated water fastness 3. Excellent levelness performance & reproducibility
113	Yellow MX			1. 敏感色系穩定性佳 2. 優異的染色再現性與均染性 3. 適合棉與人造纖維混紡一浴同色應用 4. 可搭配 Red MX 及 Navy MX	1. Unique performance for critical shades 2. Outstanding reproducibility and levelness 3. Highly suitable for cotton and regenerated cellulose blends dyeing 4. Compatible with Red MX & Navy MX
115	Red MX			1. 敏感色系穩定性佳 2. 優異的染色再現性與均染性 3. 適合棉與人造纖維混紡一浴同色應用 4. 可搭配 Yellow MX 及 Navy MX	1. Unique performance for critical shades 2. Outstanding reproducibility and levelness 3. Highly suitable for cotton and regenerated cellulose blends dyeing 4. Compatible with Yellow MX & Navy MX
117	Navy MX			1. 敏感色系穩定性佳 2. 優異的染色再現性與均染性 3. 適合棉與人造纖維混紡一浴同色應用 4. 可搭配 Yellow MX 及 Red MX	1. Unique performance for critical shades 2. Outstanding reproducibility and levelness 3. Highly suitable for cotton and regenerated cellulose blends dyeing 4. Compatible with Yellow MX & Red MX

Everzol ED Dyes

頁 page	染料 dyes	1%	3%	染料特性	Characteristics
119	Yellow ED-2G			1. 極佳的染深性 2. 與Everzol Turq. Blue G配色時，染色溫度為 80°C	1. Excellent build-up 2. Optimum dyeing temperature at 80°C while combined with Everzol Turq. Blue G
121	Yellow ED-R			1. 鮮豔且染深佳 2. 耐多次水洗牢度佳 3. 搭配Red ED-7BN及Blue L-ED適用較佳之日光牢度組合	1. Brilliant and excellent build-up 2. Unique UK-TO washing fastness 3. Combined with Red ED-7BN, Blue L-ED for good light fastness trichromatic and excellent reproducibility
123	Yellow ED			1. 極佳之染深性 2. 中、深濃度之主要三原色 3. 與Red ED、Navy ED之配色組合相容性佳	1. Excellent build-up 2. Main component for medium to deep trichromatic 3. Excellent compatibility with Red ED, Navy ED
125	Yellow ED-S			1. 染深性佳 2. 適合於浸染及連染 3. 與Red ED-S搭配適用於防染及拔染 4. 樹脂加工容易影響日光牢度及色相	1. Excellent build-up 2. Suitable for exhaust & continuous dyeing 3. Compatible with Red ED-S for resist, discharge printing 4. Precaution of lightfastness and color change after resin treatment
127	Orange ED-N			1. 極佳的染深性 2. 優異的日光牢度及汗日光牢度 3. 適合防拔染	1. Excellent build-up 2. Outstanding lightfastness and perspiration lightfastness 3. Suitable for resist, discharge printing
129	Orange ED-2R			1. 非常鮮豔之橙色染料 2. 極佳之力度與染深性 3. 極佳之耐氯水牢度	1. Very brilliant orange color 2. Excellent tinctorial strength and build-up 3. Excellent chlorinated water colorfastness
131	Orange ED-4R			1. 超經濟、超染深 2. 高日光、汗日光複合牢度 3. 優異耐氯漂牢度	1. Extremely high build-up & cost-effective 2. Excellent lightfastness & perspiration lightfastness 3. Excellent chlorinated water fastness
133	Red ED			1. 極佳之染深性（深紅色） 2. 中、深濃度之主要三原色 3. 與Yellow ED、Navy ED之配色組合相容性佳	1. Very high tinctorial strength for deep red 2. Main component for medium to deep trichromatic 3. Excellent compatibility with Yellow ED, Navy ED
135	Red ED-2B			1. 染深性極佳 2. 適用於中、深三原色	1. Very good build-up 2. For medium to heavy trichromatic
137	Red ED-3B			1. 鮮豔且染深性佳 2. 搭配Yellow ED-R及Blue L-ED適用較佳之日光牢度組合 3. 極佳之耐氯水牢度	1. Brilliant and excellent build-up 2. With Yellow ED-R, Blue L-ED for good light fastness trichromatic 3. Excellent chlorinated water colorfastness
139	Red ED-7BN			1. 染深性佳 2. 與Orange ED-4R、Blue L-ED搭配特別適用於特深色 3. 高日光牢度及耐氯水牢度優異	1. Very excellent build-up 2. Compatible with Orange ED-4R, Blue L-ED for deep shade 3. High lightfastness & Chlorinated water fastness

Everzol ED Dyes

頁 page	染料 dyes	1%	3%	染料特性	Characteristics
141	Red ED-S			1. 染深性佳 2. 適合於浸染及連染 3. 與Yellow ED-S搭配適用於防染及拔染	1. Excellent build-up 2. Suitable for exhaust and continuous dyeing 3. Compatible with Yellow ED-S for resist, discharge printing
143	Rubine ED			1. 適用於浸染、連續染色、冷壓染 2. 特別適用於明亮之酒紅色 3. 染深性佳	1. Suitable for exhaust, continuous dyeing and CPB 2. Especially for brilliant burgundy shade dyeing 3. Excellent build-up
145	Blue ED-G			1. 鮮豔偏綠的寶藍色染料 2. 極佳的日光牢度 3. 與Yellow ED-2G、Turq. B-G可配出鮮豔的翠綠色 4. N/C混紡染色，低Nylon污染	1. Brilliant greenish royal blue dyes. 2. Excellent lightfastness. 3. Compatible with Yellow ED-2G, Turq. Blue G for matching brilliant jade green shade 4. Low nylon cross-dyeing for Nylon/Cotton blends dyeing
147	Blue L-ED			1. 可用於浸染，冷壓染和連續染色工程 2. 染深性佳的藍色系染料 3. 日光堅牢度佳 4. 可做防染和拔染加工 5. 極佳的染色再現性	1. Suitable for exhaust, continuous dyeing and CPB 2. Excellent build-up 3. Good lightfastness 4. Suitable for discharge and resist printing 5. Excellent reproducibility
149	Blue ED			1. 耐日光堅牢度佳 2. 搭配Yellow ED-R及Red ED-3B適用較佳之日光牢度組合 3. 耐氯水堅牢度佳	1. Excellent lightfastness 2. With Yellow ED-R, Red ED-3B for good light fastness trichromatic 3. Good chlorinated water fastness
151	Navy ED			1. 極佳之染深性 2. 中、深濃度之主要三原色 3. 與Yellow ED、Red ED之配色組合相容性佳	1. Excellent build-up 2. Main component for medium to deep trichromatic 3. Excellent compatibility with Yellow ED, Red ED

Everzol ED Dyes

頁 page	染料 dyes	3%	6%	染料特性	Characteristics
153	Black ED			1. 染深性極佳之深黑色 2. 適合防、拔染底色 3. 耐後絲光牢度佳	1. Deep black with good build-up 2. Suitable for resist, discharge printing 3. Excellent colorfastness to post mercerizing
155	Black EDN			1. 適合於極深之黑色 2. 高染深性、洗淨性佳 3. 高水洗&濕牢度 4. 對Lycra低交互染色	1. Suitable for very deep black shades 2. High build-up, easy wash-off 3. Exceptional washing & wet fastness 4. Very less lycra cross-dyeing for cotton/lycra dyeing
157	Black ED-2R			1. 力度佳之黑深色染料 2. N/C織物染色時對尼龍交互染著低	1. Deep black with good color yield 2. Less nylon cross-dyeing when N/C blends dyeing
159	Black ED-G			1. 極佳染深力度之黑色染料 2. 偏綠味之黑色 3. 適合防、拔染色之底色 4. Cotton/Lycra染色時對Lycra污染少	1. Deep black with excellent build-up 2. Greenish black 3. Suitable for resist, discharge printing 4. Less lycra cross-dyeing for cotton/lycra dyeing
161	Black ED-R			1. 極佳染深力度之黑色染料 2. 偏紅味之黑色 3. 適合防、拔染色之底色	1. Deep black with excellent build-up 2. Reddish black 3. Suitable for resist, discharge printing
163	Black ED-3R			1. 符合Inditex 之AAA規定 2. 對酸浴整理加工色光穩定 3. 高染深 & 高水洗 & 濕牢度	1. Complies with Inditex's AAA regulations 2. More stable shade in post acidic finishing 3. Exceptional Build-Up & Washing & Wet fastness

Everzol Dyes

項目 Item	推薦組合 Recommended combinations	經濟組合 Economic combinations	輔助色 Supplementary
淺中色系 Pale-Medium Shades	Everzol Yellow LX Everzol Red LX Everzol Blue LX Everzol Yellow CE-N	Everzol Yellow 3RS Everzol Red 3BS Everzol Blue BRF 150%	Everzol Navy LX
中深色系 Medium-Dark Shades	Everzol Yellow ED Everzol Red ED-3B Everzol Red ED-7BN Everzol Blue L-ED	Everzol Yellow 3RS Everzol Red 3BS Everzol Navy Blue FBN Everzol Black B	Everzol Yellow ED-R Everzol Orange ED-N Everzol Red ED Everzol Navy ED Everzol Navy LX
極深色系 Heavy Shade	Everzol Orange ED-4R Everzol Red ED-7BN Everzol Blue L-ED	Everzol Orange ED-4R Everzol Red ED-7BN Everzol Navy ED	Everzol Yellow ED Everzol Red ED-3B Everzol Navy Blue RGB H/C Everzol Navy Blue FBN
高日光牢度 高汗日光牢度 Excellent Lightfastness & Perspiration Lightfastness	Everzol Yellow LX Everzol Red LF-B Everzol Red LF-2B Everzol Blue LX Everzol Blue FC Everzol Grey LF Everzol CS Series	Everzol Yellow C-GL Everzol Red C-3B Everzol Blue BB	Everzol Yellow 4GL Everzol Red F2B Everzol Blue BRF 150% Everzol Brilliant Blue R s/p Everzol Blue ED-G Everzol Dark Blue LF Everzol Blue L-ED Everzol Red LF-4B
淺中敏感色 高均染性 高染色再現性 Critical Color Excellent Levelness & Reproducibility	Everzol Yellow CS Everzol Orange CS Everzol Red Brown CS Everzol Olive CS Everzol Grey CS	Everzol Yellow LX Everzol Red LX Everzol Blue LX Everzol Yellow CE-N	Everzol Grey LF
高耐氯水漂牢度 Excellent Chlorinated Water Fastness	Everzol Yellow LX Everzol Red LX Everzol Navy LX Everzol CS series	Everzol Yellow 3RS Everzol Orange ED-4R Everzol Red 3BS Everzol Red ED-7BN Everzol Navy Blue FBN	Everzol Navy Blue GG Everzol Red C-3B Everzol Red 6B Everzol Red F2B Everzol Scarlet FC Everzol Orange FC Everzol Red FC

項目 Item	推薦組合 Recommended combinations	輔助色 Supplementary
淺中色無氣體變褪色 & 高日光牢度	Everzol Yellow CS Everzol Red LF-4B Everzol Blue NXF	
翠綠色 Brilliant Green Shades	Everzol Flavine FC Everzol Yellow 4GL Everzol Yellow ED-2G Everzol Turq. Blue G Everzol Blue ED-G	Everzol Yellow 3GL Everzol Brilliant Blue R s/p Everzol Royal Blue E-FR Everzol Blue BRF 150%
大紅色 Brilliant Red Shades	Everzol Orange FC Everzol Scarlet FC Everzol Orange ED-2R Everzol Red ED-3B	Everzol Yellow LX Everzol Red F2B Everzol Scarlet 3GF Everzol Red BS Everzol Red ED
深色敏感色 Dark Critical Colors	Everzol Yellow ED-R Everzol Orange ED-4R Everzol Red ED-7BN Everzol Blue L-ED	Everzol Yellow ED Everzol Red ED-3B Everzol Red ED Everzol Navy LX
寶藍色 Royal Blue Shades	Everzol Blue FC Everzol Brilliant Blue R s/p Everzol Royal Blue E-FR Everzol Blue ED-G	Everzol Red 6B Everzol Red FC
亮紫色 Brilliant Violet & purple shades	Everzol Blue FC Everzol Red FC Everzol Red 6B Everzol Brilliant Blue R s/p Everzol Royal Blue E-FR	Everzol Red 3BS Everzol Red ED-3B Everzol Rubine ED Everzol Blue ED-G
黑色 Black Shades	Everzol Black ED Everzol Black EDN Everzol Black ED-G Everzol Black ED-R Everzol Black ED-3R	Everzol Black ED-2R Everzol Black GSP Everzol Black MWF


Everzol Dyes	1
Everzol LX/LF Dyes	75
Everzol FC Dyes	93
Everzol CS/MX Dyes	103
Everzol ED Dyes	119

Everzol Yellow 4GL


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	50
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4
	Dye Liquor 染浴	3-4
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3R
	Quaternary ammonium salt 四級銨鹽	3R
Stripping 脫色性	(1)	×
	(2)	△
	(3)	△
	(4)	○
Discharge ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

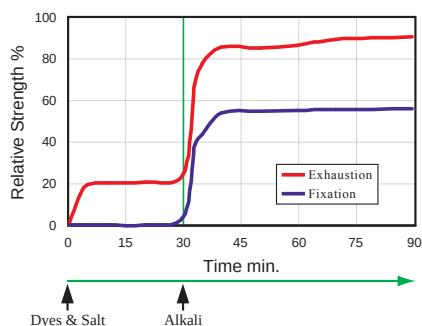

溫度依存性 Dependency on temperature

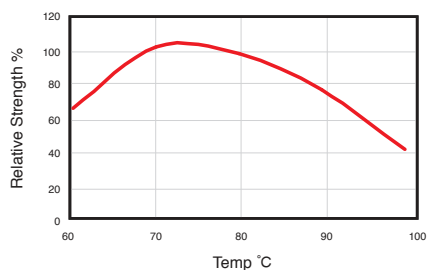

芒硝依存性 Dependency on Glauber's salt

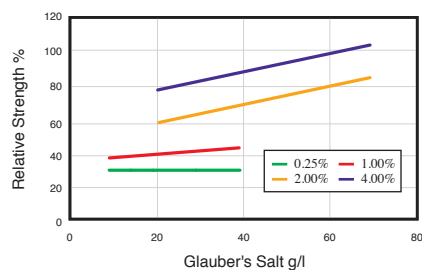

Everzol Yellow 4GL


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4	
	ISO C10 C		4-5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		4-5	5	4	4-5	5	5	3	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		4	
	ISO C06-C2S		5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	>4-5	
	M&S C4A		5	5	5	5	5	5	5			3.0%	>4-5	
Water 耐水		3.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5
Post mercerizing 後絲光		3.0%	3R		4						4 Hours after	5		
Acid hydrolysis 酸水解		3.0%	3-4	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	5	5	5	5	5	5	5		4 Hours after			4-5
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4	4-5	Perspiration Light 耐汗日光	Acid	3.0 %	4-5	6
	0.3 %	4-5	5		Alkali		4-5	5-6
	1.0 %	>4-5	>6					
	3.0 %	>4-5	>6					
	6.0 %	>4-5	>6					

浴比依存性 Dependency on Liquor ratio

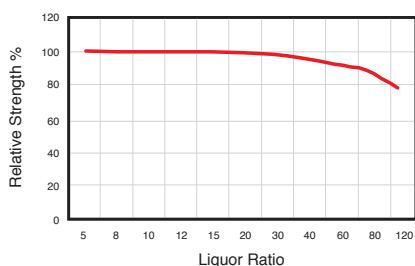

鹼依存性 Dependency on alkali

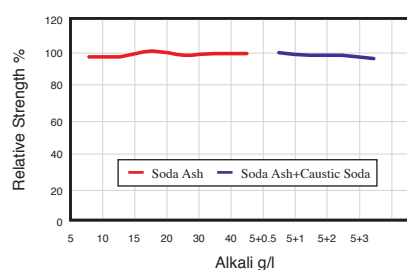


Everzol Yellow 3GL


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		4-5
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3 R
	Dye Liquor 染浴	3-4 R
Color constancy 色恆性	Tungsten Lamp	G
	TL 84 Lamp	G
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	2-3
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4 R
	Quaternary ammonium salt 四級銨鹽	4 R
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	○
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

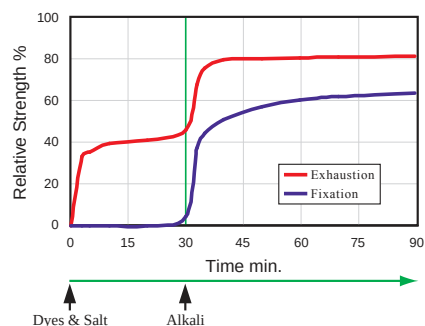

溫度依存性 Dependency on temperature

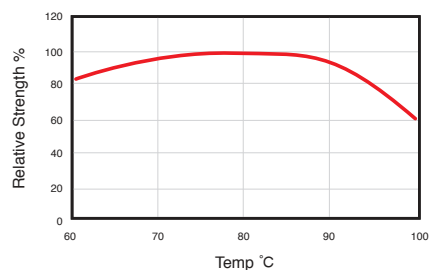

芒硝依存性 Dependency on Glauber's salt

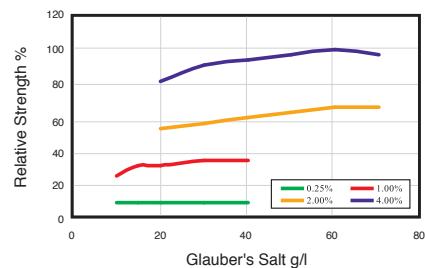

Everzol Yellow 3GL


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	3	
	ISO C10 C		5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			3	
	ISO C10 D		5	5	4	4.5	5	5	3	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		3-4	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	3	
Hot Water 耐熱水		3.0%	5	5	5	4-5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	5
Post mercerizing 後絲光		3.0%	4-5		4						4 Hours after	5		
Acid hydrolysis 酸水解		3.0%	4	5	4-5	3	5	5	3-4		Wet 濕	Immediately	3.0%	5
Perspiration 耐汗	Acid 酸	3.0%	5	5	5	5	5	5	5		4 Hours after			5
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3-4	4-5	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	5-6
	0.3 %	4	4-5		Alkali		4	3-4
	1.0 %	4	5					
	3.0 %	4-5	5-6					
	6.0 %	>4-5	>6					

浴比依存性 Dependency on Liquor ratio

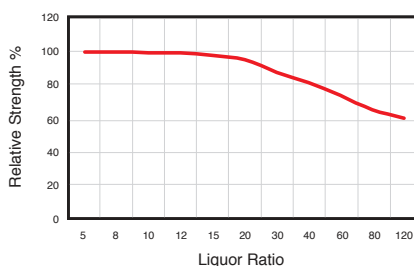

鹼依存性 Dependency on alkali

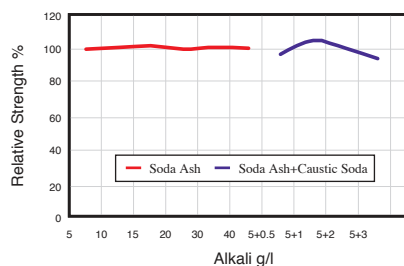


Everzol Yellow C-GL


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	3
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5 (R)
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

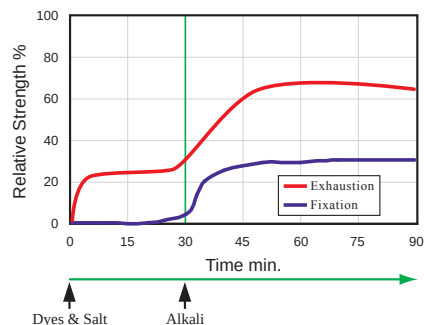

溫度依存性 Dependency on temperature

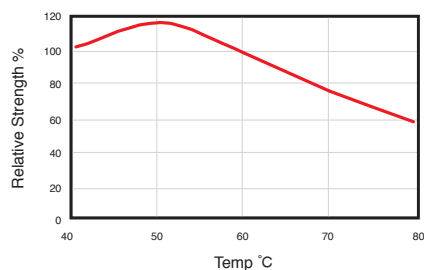

芒硝依存性 Dependency on Glauber's salt

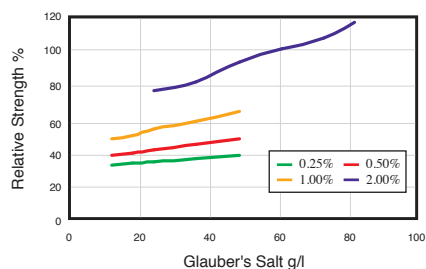

Everzol Yellow C-GL


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			1.0%	3
	ISO C10 C		5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白				4-5
	ISO C10 D		5	5	5	5	5	5	4-5	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		5	5	5	5	5	5	5		Wet 濕		4-5	
	ISO C06-C2S		5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)			0.3%	>4-5
	M&S C4A		5	5	5	5	5	5	5				1.0%	>4-5
Water 耐水		1.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗			1.0%	4-5
Hot Water 耐熱水		1.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液			1.0%	4-5
Sea Water 耐海水		1.0%	5	5	5	5	5	5	5	Hot-Pressing 耐熱壓	Dry 乾	Immediately	1.0%	4-5
Post mercerizing 後絲光		1.0%	4-5		5				4 Hours after			5		
Acid hydrolysis 酸水解		1.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	1.0%	4
Perspiration 耐汗	Acid 酸	1.0%	5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光		0.1 %	3-4	5	Perspiration Light	Acid	1.0 %	4	5-6	
		0.3 %	4	5-6	耐汗日光	Alkali		4	5-6	
		1.0 %	4-5	6						
		3.0 %	>4-5	>6						
		6.0 %	*	*						

浴比依存性 Dependency on Liquor ratio

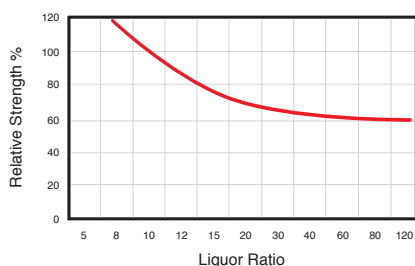

鹼依存性 Dependency on alkali

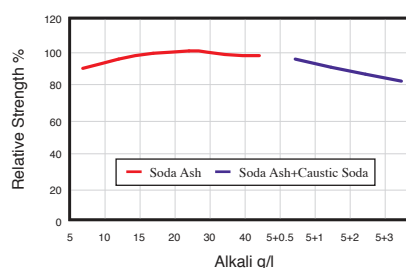


Everzol Yellow GR


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2
	Dye Liquor 染浴	4
Color constancy 色恆性	Tungsten Lamp	B (G)
	TL 84 Lamp	B (G)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	2 D
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

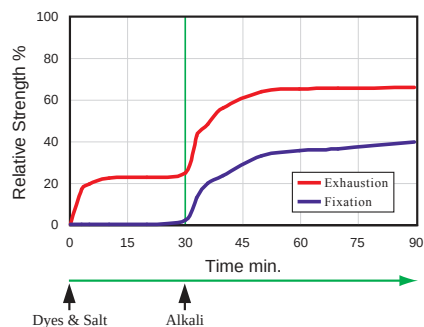

溫度依存性 Dependency on temperature

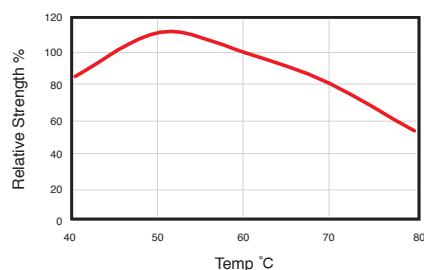

芒硝依存性 Dependency on Glauber's salt

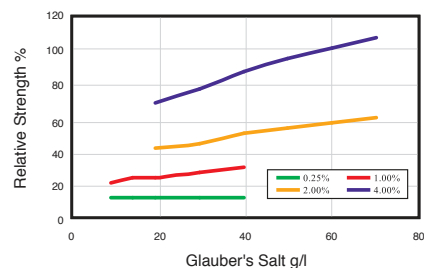

Everzol Yellow GR


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	1-2	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		4-5	5	4-5	4-5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		4-5	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	4	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	3-4	
Hot Water 耐熱水		3.0%	5	5	5	4-5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4 Y
Post mercerizing 後絲光		3.0%	2-3R		4							4 Hours after		4-5
Acid hydrolysis 酸水解		3.0%	5	5	5	3-4	5	5	4-5		Wet 濕	Immediately	3.0%	4 Y
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光		0.1 %	3	4-5	Perspiration Light 耐汗日光	Acid	3.0 %	4	5-6	
		0.3 %	3-4	4-5		Alkali		4	5	
		1.0 %	4	5-6						
		3.0 %	4-5	5-6						
		6.0 %	>4-5	>6						

浴比依存性 Dependency on Liquor ratio

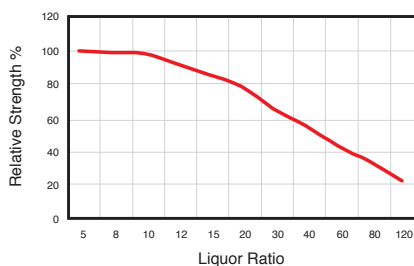

鹼依存性 Dependency on alkali

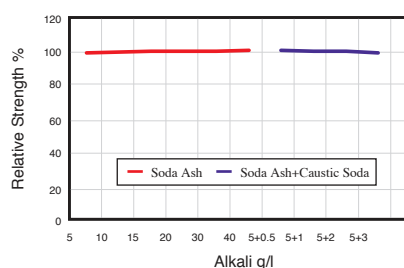


Everzol Yellow CE-N


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		3-4
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	3
Color constancy 色恆性	Tungsten Lamp	B(G)
	TL 84 Lamp	G(Y)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	3-4
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	×
	(4)	△
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	1-2


吸盡固著曲線 Exhaustion & Fixation

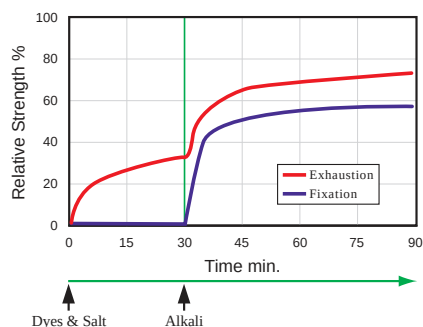

溫度依存性 Dependency on temperature

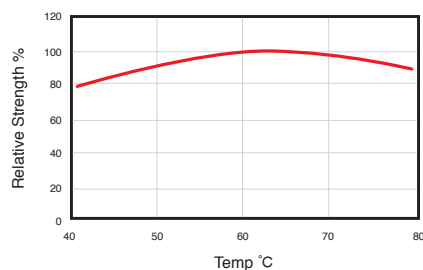

芒硝依存性 Dependency on Glauber's salt

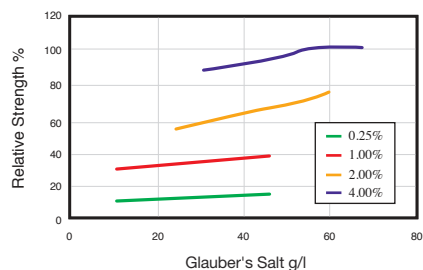

Everzol Yellow CE-N


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C02	3.0%	4-5	4-5	4	4-5	4-5	4-5	4-5	Chlorinated Water耐氯水(20ppm)			3.0%	4-5
	ISO C03		4-5	4-5	4	4-5	4-5	4-5	4-5	Peroxide Bleaching雙氧水漂白				4-5
	ISO C04		4-5	4-5	3-4	4-5	4-5	4-5	4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	4-5	3-4	4-5	4-5	4-5	4-5		Wet 濕		2-3	
	ISO C06-C2S		4-5	4-5	4	4-5	4-5	4-5	4-5	M&S C9A 擬溼日光 (detergent Light)			0.3%	4-5
	M&S C4A		4-5	4-5	4	4-5	4-5	4-5	4-5				3.0%	4-5
Water 耐水		3.0%	4-5	5	4-5	4-5	5	5	5	Multi laundering 耐多次水洗			3.0%	4-5
Hot Water 耐熱水		3.0%	4-5	5	5	4-5	5	5	5	Saliva (DIN) 耐唾液			3.0%	4-5
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	2-3		4				4 Hours after			4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	4-5	5	5	5		Wet 濕	Immediately	3.0%	3-4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			3.0%	4-5


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.1 %	4-5	5-6	Perspiration Light 耐汗日光	Acid	3.0 %	4-5	>6
		0.3 %	4-5	6		Alkali		4-5	>6
		1.0 %	4-5	>6					
		3.0 %	4-5	>6					
		6.0 %	4-5	>6					

浴比依存性 Dependency on Liquor ratio

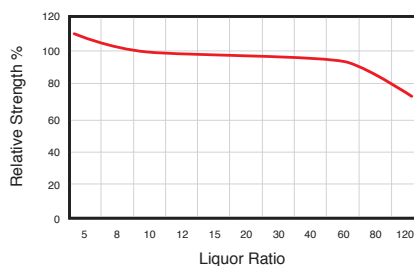

鹼依存性 Dependency on alkali

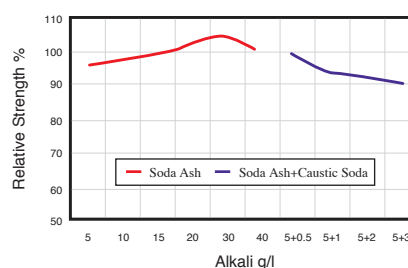


Everzol Golden Yellow RNL


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	4
Color constancy 色恆性	Tungsten Lamp	B
	TL 84 Lamp	B
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

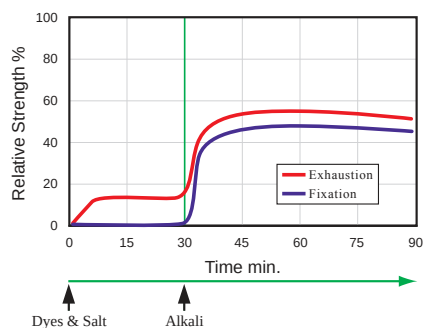

溫度依存性 Dependency on temperature

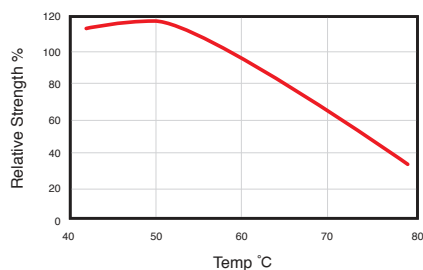

芒硝依存性 Dependency on Glauber's salt

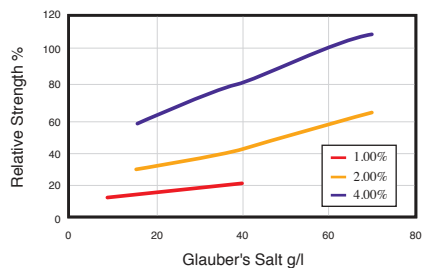

Everzol Golden Yellow RNL


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			3.0%	3
	ISO C10 C		5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白				4-5
	ISO C10 D		4-5	5	4-5	4-5	5	5	2-3	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		5	5	5	5	5	5	5		Wet 濕		4	
	ISO C06-C2S		4-5	5	5	5	5	5	3-4	M&S C9A 擬溼日光 (detergent Light)			0.3%	4-5
	M&S C4A		5	5	5	5	5	5	5				3.0%	4-5
Water 耐水		3.0%	4-5	5	5	4-5	5	5	Multi laundering 耐多次水洗			3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	4-5	5	5	4-5	5	5	Saliva (DIN) 耐唾液			3.0%	5
Sea Water 耐海水		3.0%	4-5	4-5	5	5	4-5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	3-4R		4				4 Hours after			4		
Acid hydrolysis 酸水解		3.0%	5	5	5	4	5	5	5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	5	5	5	4	5	5	5			4 Hours after		4
	Alkali 鹼		5	5	5	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			3.0%	2


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3-4	4	Perspiration Light 耐汗日光	Acid	3.0 %	4	5-6	
	0.3 %	4	4-5		Alkali		4	5-6	
	1.0 %	4-5	5						
	3.0 %	4-5	5-6						
	6.0 %	5	5-6						

浴比依存性 Dependency on Liquor ratio

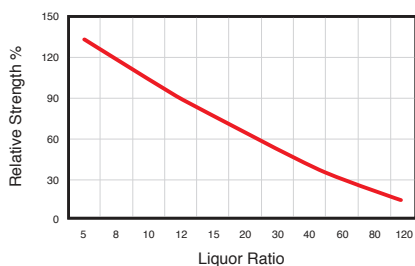

鹼依存性 Dependency on alkali

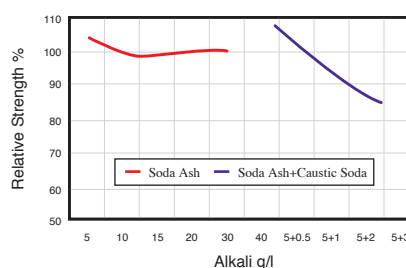


Everzol Yellow 3RS


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4-5
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2
	Dye Liquor 染浴	1-2
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4 G
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	×
	(4)	△
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	3-4


吸盡固著曲線 Exhaustion & Fixation

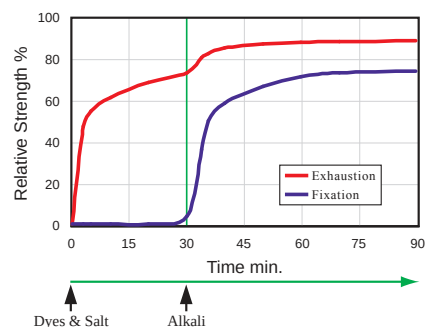

溫度依存性 Dependency on temperature

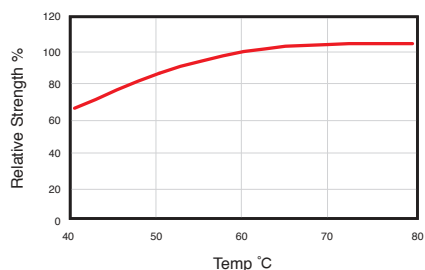

芒硝依存性 Dependency on Glauber's salt

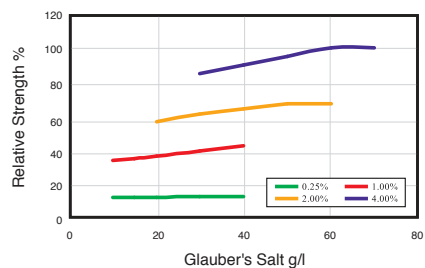

Everzol Yellow 3RS


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	5	
	ISO C10 C		5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		5	5	3	5	5	5	5	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕	4		
	ISO C06-C2S		5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	>4-5	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	>4-5	
Water 耐水		3.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	4R		4				4 Hours after			4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	5	5	5	5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO	
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4	5-6	Perspiration Light 耐汗日光	Acid	3.0 %	4-5	>6	
	0.3 %	4-5	6		Alkali		4-5	5	
	1.0 %	>4-5	>6						
	3.0 %	>4-5	>6						
	6.0 %	>4-5	>6						

浴比依存性 Dependency on Liquor ratio

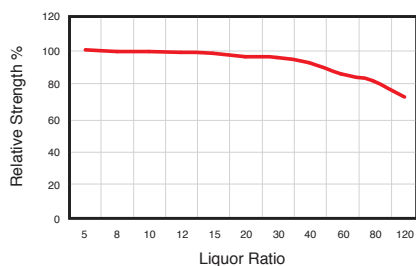

鹼依存性 Dependency on alkali

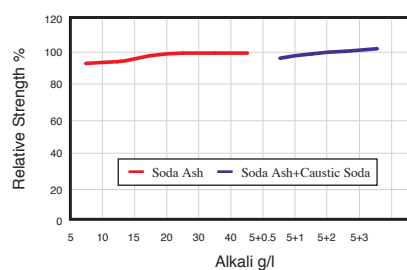


Everzol Orange 3R


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2 YD
	Dye Liquor 染浴	2-3 YD
Color constancy 色恆性	Tungsten Lamp	RD
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5 Y
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

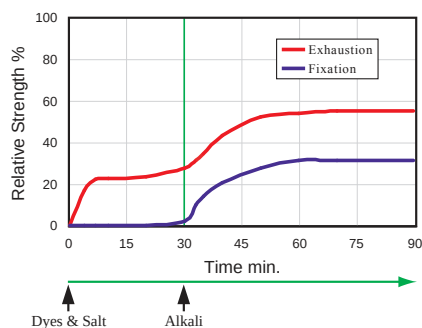

溫度依存性 Dependency on temperature

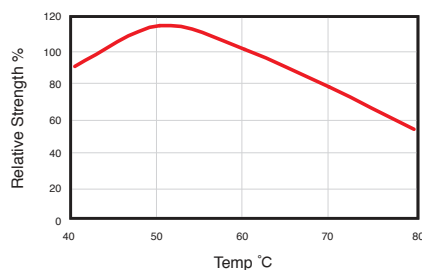

芒硝依存性 Dependency on Glauber's salt

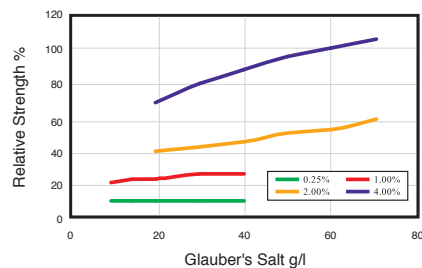

Everzol Orange 3R


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	5	5	5	4-5	Chlorinated Water耐氯水(20ppm)		3.0%	3-4	
	ISO C10 C		4-5	5	4-5	5	5	5	4-5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	3	3-4	5	5	2	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	5	5	5	5	4-5		Wet 濕		3-4	
	ISO C06-C2S		5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	5	5	5	5	4-5			3.0%	4-5	
Water 耐水		3.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	3-4	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	2-3R		4				4 Hours after			4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	4	4	5	5	4-5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	5	5	5	5	5	5	5			4 Hours after		4
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
	0.1 %	2-3	4	Perspiration Light 耐汗日光	Acid Alkali	3.0 %	3 3-4	5 4-5
Artificial Light (Xenon-Arc Lamp) 耐日光	0.3 %	3	4					
	1.0 %	3-4	5					
	3.0 %	4	5-6					
	6.0 %	4-5	>6					

浴比依存性 Dependency on Liquor ratio

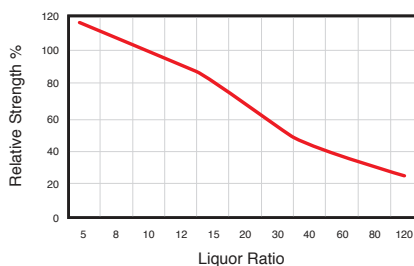

鹼依存性 Dependency on alkali

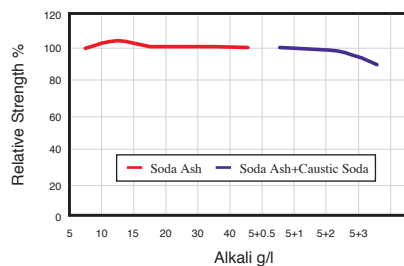


Everzol Scarlet 3GF


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		1-2
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4
	Dye Liquor 染浴	5
Color constancy 色恆性	Tungsten Lamp	R (Y)
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	1
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	×
Discharge ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	2


吸盡固著曲線 Exhaustion & Fixation

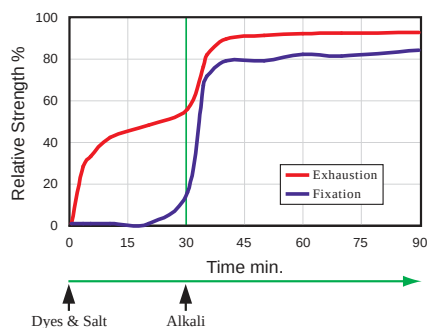

溫度依存性 Dependency on temperature

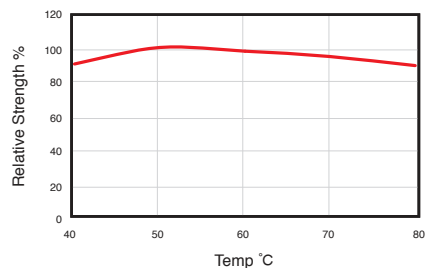

芒硝依存性 Dependency on Glauber's salt

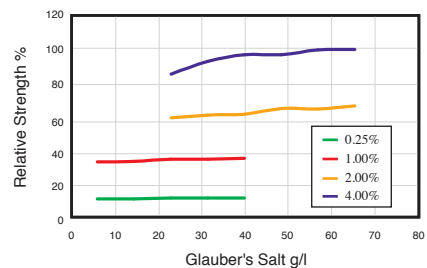

Everzol Scarlet 3GF


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	4	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C10 C		4-5	5	3-4	5	5	5	5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		4-5	3-4	2	4-5	5	5	2-3	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	2-3	5	5	5	5		Wet 濕		3	
	ISO C06-C2S		4-5	5	2-3	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4	5	5	5	5			3.0%	>4-5	
Water 耐水		3.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	5	5	4-5	4-5	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	1-2B
Post mercerizing 後絲光		3.0%	4R(Y)		4				4 Hours after			4-5		
Acid hydrolysis 酸水解		3.0%	5	5	4-5	4-5	5	5	5		Wet 濕	Immediately	3.0%	1-2B
Perspiration 耐汗	Acid 酸	3.0%	5	5	5	5	5	5	5			4 Hours after		4
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO	
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	3-4	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	5	
	0.3 %	2-3	4		Alkali		3	4-5	
	1.0 %	3	4-5						
	3.0 %	3-4	5						
	6.0 %	3-4	5						

浴比依存性 Dependency on Liquor ratio

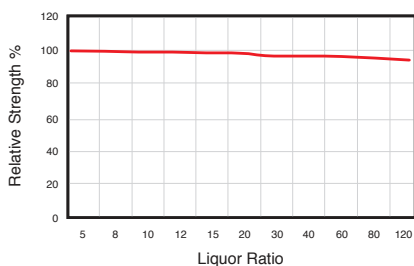

鹼依存性 Dependency on alkali

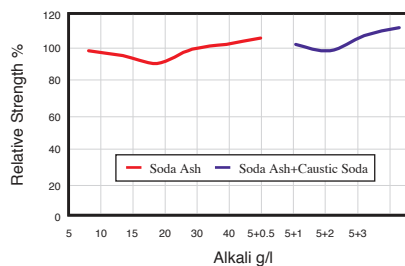


Everzol Red C-3B


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp	B
	TL 84 Lamp	B
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4 B
	Quaternary ammonium salt 四級銨鹽	4 B
Stripping 脫色性	(1)	△
	(2)	△
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

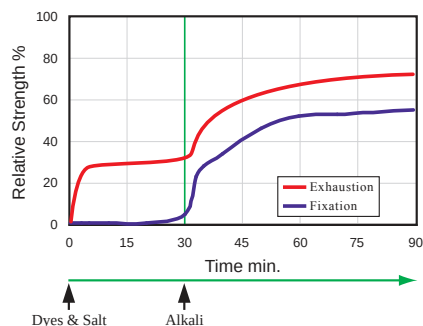

溫度依存性 Dependency on temperature

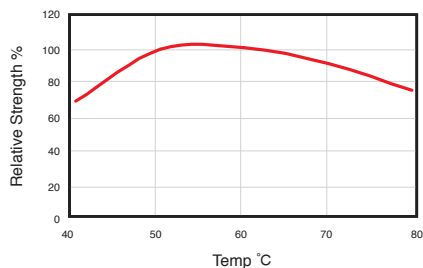

芒硝依存性 Dependency on Glauber's salt

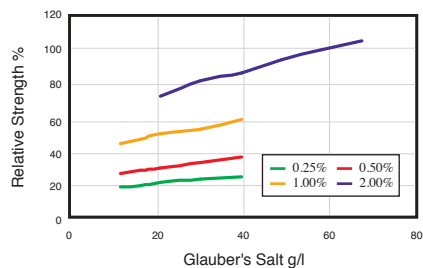

Everzol Red C-3B


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	4-5	
	ISO C10 C		4-5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			2	
	ISO C10 D		4	5	5	5	5	5	4-5	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		4-5	5	5	5	5	5	5		Wet 濕		4	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	5	5	5	5	5			1.0%	4-5	
Water 耐水		1.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	4	
Hot Water 耐熱水		1.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		1.0%	4-5	
Sea Water 耐海水		1.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	4
Post mercerizing 後絲光		1.0%	3	5					4 Hours after			5		
Acid hydrolysis 酸水解		1.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	1.0%	3-4
Perspiration 耐汗	Acid 酸	1.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4	5	Perspiration Light 耐汗日光	Acid	1.0 %	2-3	4-5	
	0.3 %	4	5-6		Alkali		3	3-4	
	1.0 %	>4-5	6						
	3.0 %	>4-5	>6						
	6.0 %	*	*						

浴比依存性 Dependency on Liquor ratio

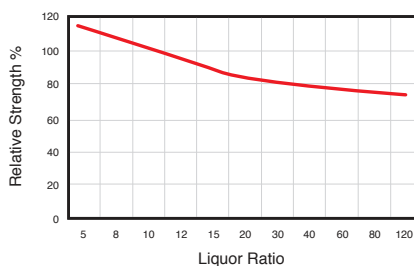

鹼依存性 Dependency on alkali

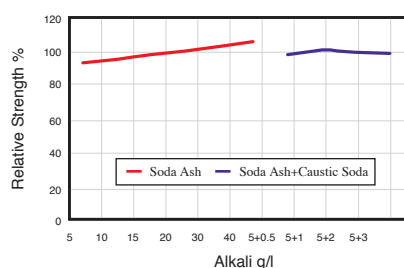


Everzol Red F2B


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		5
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	50
	50°C Water+50 g/l Salt	50
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3 B
	Dye Liquor 染浴	4 B
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	B
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	3 B
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	1-2
	Alkaline 鹼性	2


吸盡固著曲線 Exhaustion & Fixation

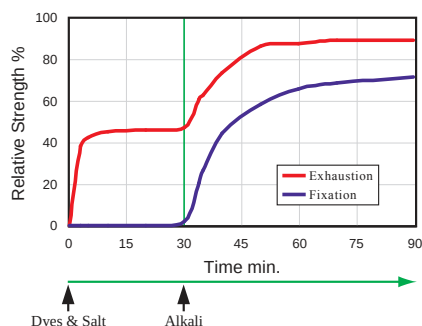

溫度依存性 Dependency on temperature

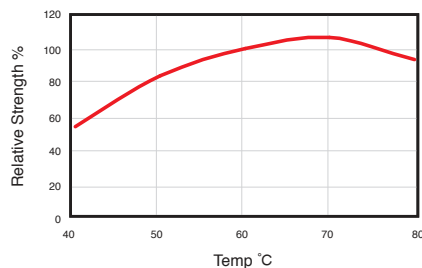

芒硝依存性 Dependency on Glauber's salt

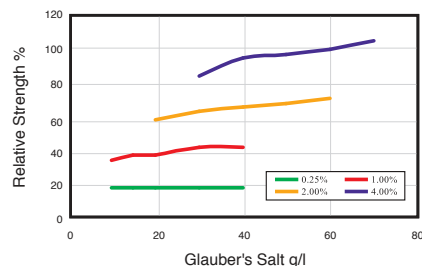

Everzol Red F2B


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C10 C		4-5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			3-4	
	ISO C10 D		5	5	3	5	5	5	3	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	>4-5	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	>4-5	
Water 耐水		3.0%	5	5	4-5	4-5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	4-5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	4-5	5	4-5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	5
Post mercerizing 後絲光		3.0%	4Y		2-3							4 Hours after		5
Acid hydrolysis 酸水解		3.0%	4-5	4-5	5	5	5	5	4-5		Wet 濕	Immediately	3.0%	4-5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		5	4-5	4-5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2-3	4	Perspiration Light 耐汗日光	Acid	3.0 %	3	5-6	
	0.3 %	3	4		Alkali		4	3-4	
	1.0 %	4	5						
	3.0 %	4-5	5-6						
	6.0 %	>4-5	6						

浴比依存性 Dependency on Liquor ratio

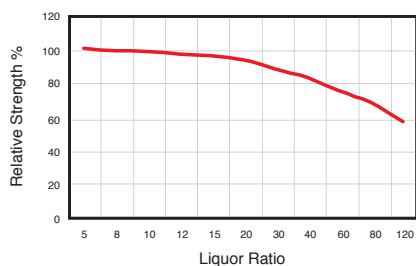

鹼依存性 Dependency on alkali

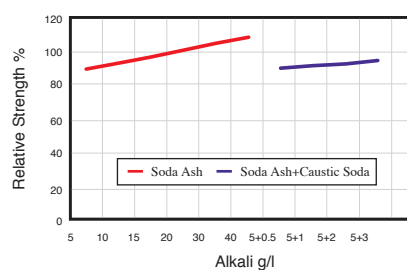


Everzol Red BB


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		4
Washing off 洗淨性		2-3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4 B
	Dye Liquor 染浴	3-4
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4 B
	Cu ²⁺ 銅	2 B
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5 B
	Glyoxal 乙二醛	4-5 B
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

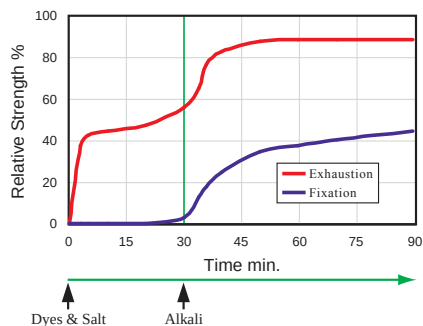

溫度依存性 Dependency on temperature

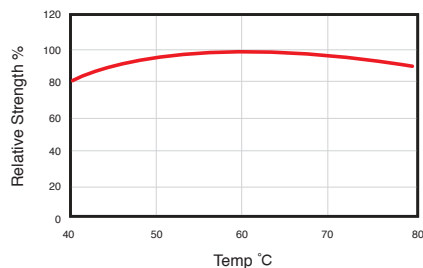

芒硝依存性 Dependency on Glauber's salt

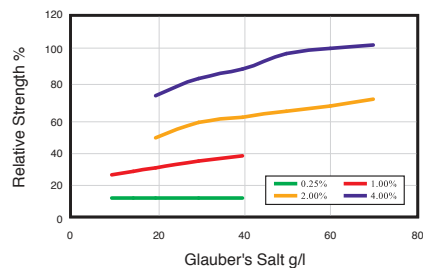

Everzol Red BB


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	1-2B	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			3B	
	ISO C10 D		4	4-5	3	4	5	5	3	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	3-4	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	3-4	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	1	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	2-3B		4						4 Hours after	4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	4	5	5	5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	4-5	5	4-5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	4-5	5	4-5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3-4	5-6	Perspiration Light 耐汗日光	Acid	3.0 %	2	5-6	
	0.3 %	3-4	5-6		Alkali		2-3	3-4	
	1.0 %	4	5-6						
	3.0 %	4	5-6						
	6.0 %	4-5	6						

浴比依存性 Dependency on Liquor ratio

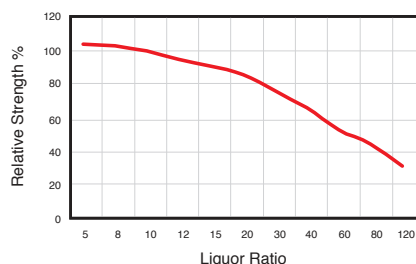

鹼依存性 Dependency on alkali

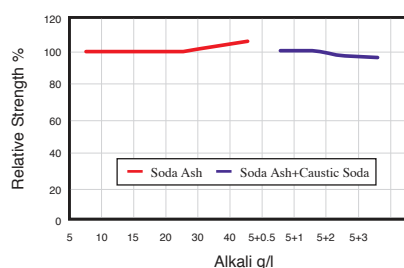


Everzol Brilliant Red F3B


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4
	Dye Liquor 染浴	5
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	1
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5 B
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

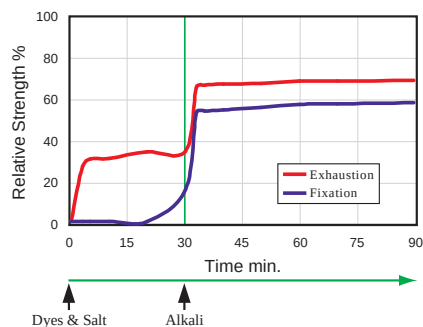

溫度依存性 Dependency on temperature

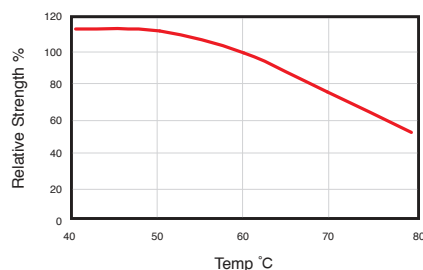

芒硝依存性 Dependency on Glauber's salt

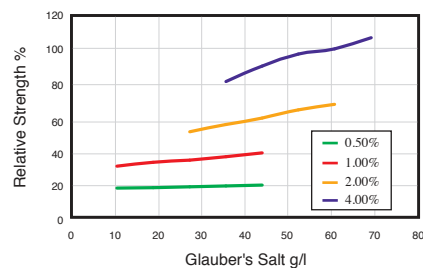

Everzol Brilliant Red F3B


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	4-5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		3-4	5	3	5	5	5	2-3	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		3	
	ISO C06-C2S		4-5	5	3	5	5	4-5	4	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	4-5	4-5	3-4	4-5	4-5	4-5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	5	5	4	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	4-5	4-5	4-5	4-5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	2B
Post mercerizing 後絲光		3.0%	4B		3						4 Hours after	4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	5	4-5	5	5	5		Wet 濕	Immediately	3.0%	2B
Perspiration 耐汗	Acid 酸	3.0%	4-5	4-5	4-5	4	4-5	4-5	4-5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	4-5	4-5	4-5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO	
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2-3	3-4	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	4	
	0.3 %	3	4		Alkali		3	3	
	1.0 %	3-4	4-5						
	3.0 %	4	5						
	6.0 %	4-5	5-6						

浴比依存性 Dependency on Liquor ratio

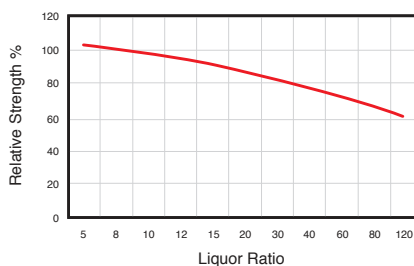

鹼依存性 Dependency on alkali

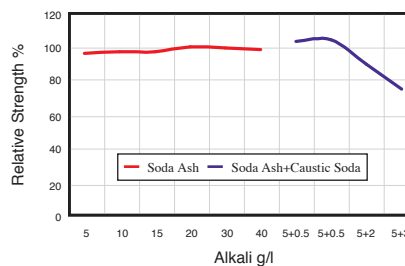


Everzol Red 3BS


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		5
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2
	Dye Liquor 染浴	1-2
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	3-4
	Cu ²⁺ 銅	2-3 B
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4 B
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	1-2
	Alkaline 鹼性	2


吸盡固著曲線 Exhaustion & Fixation

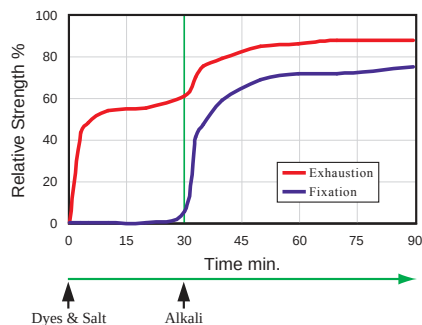

溫度依存性 Dependency on temperature

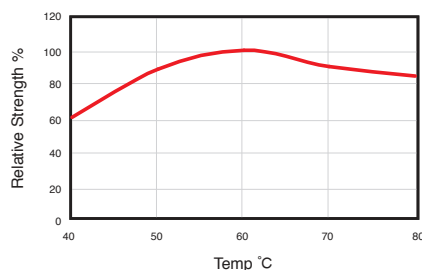

芒硝依存性 Dependency on Glauber's salt

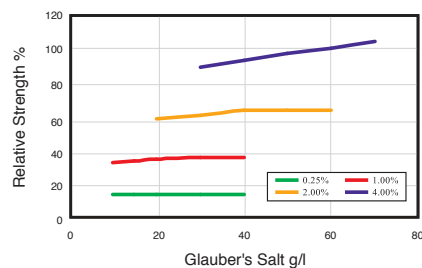

Everzol Red 3BS


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	5	
	ISO C10 C		5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		5	5	3	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		5	5	4-5	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	>4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	>4-5	
Water 耐水		3.0%	5	5	4-5	4-5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	1-2Y		3-4						4 Hours after	4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	4	4-5	5	5	4		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	4	5		4 Hours after			4-5
	Alkali 鹼		5	5	4-5	5	5	4-5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO	
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2-3	4	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	5	
	0.3 %	3	4		Alkali		3	3	
	1.0 %	4	5-6						
	3.0 %	4-5	5-6						
	6.0 %	>4-5	6						

浴比依存性 Dependency on Liquor ratio

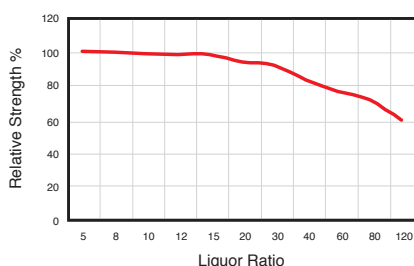

鹼依存性 Dependency on alkali

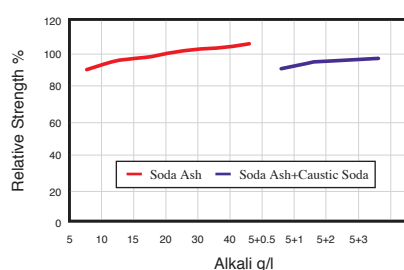


Everzol Red BS


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2 B
	Dye Liquor 染浴	1-2 B
Color constancy 色恆性	Tungsten Lamp	B
	TL 84 Lamp	B
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	5
Resin finishing 樹脂加工	Melamine 三聚氰胺	3-4 B
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	2


吸盡固著曲線 Exhaustion & Fixation

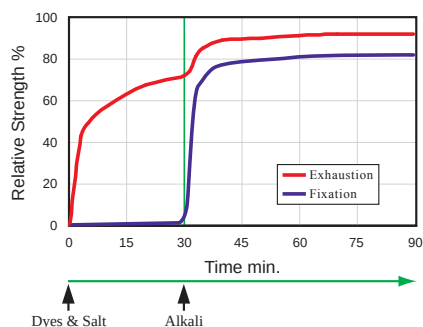

溫度依存性 Dependency on temperature

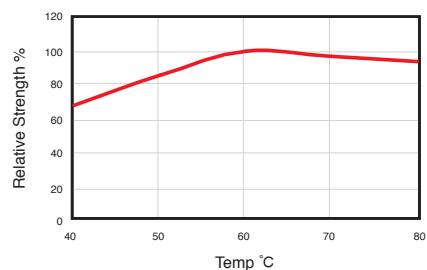

芒硝依存性 Dependency on Glauber's salt

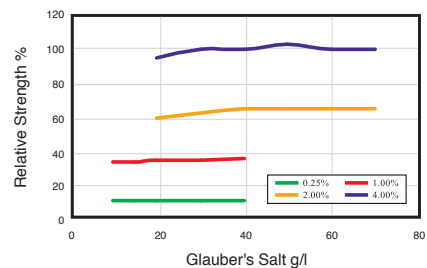

Everzol Red BS


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4	
	ISO C10 C		4-5	5	3-4	5	5	4-5	5	Peroxide Bleaching雙氧水漂白			3	
	ISO C10 D		4-5	5	2	5	5	5	3	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕	2-3		
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	2-3	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3B
Post mercerizing 後絲光		3.0%	1-2R		3-4				4 Hours after			4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	4	3	5	5	4		Wet 濕	Immediately	3.0%	2-3B
Perspiration 耐汗	Acid 酸	3.0%	5	5	5	5	5	5	5			4 Hours after		4
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	4	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	4-5
	0.3 %	2-3	4		Alkali		3	3
	1.0 %	3	4-5					
	3.0 %	3-4	5					
	6.0 %	4	5-6					

浴比依存性 Dependency on Liquor ratio

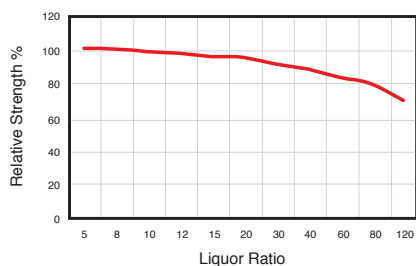

鹼依存性 Dependency on alkali

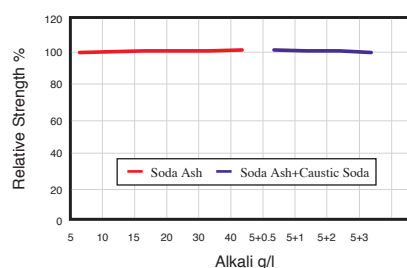


Everzol Red 6B


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		3
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	50
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4-5
	Dye Liquor 染浴	4
Color constancy 色恆性	Tungsten Lamp	Y (R)
	TL 84 Lamp	G (Y)
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	2
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	3-4


吸盡固著曲線 Exhaustion & Fixation

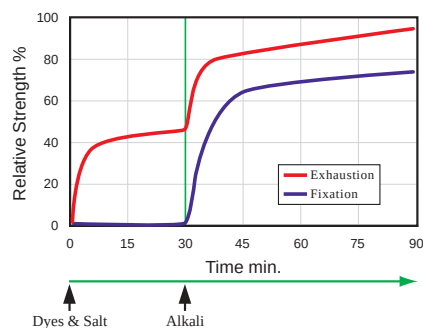

溫度依存性 Dependency on temperature

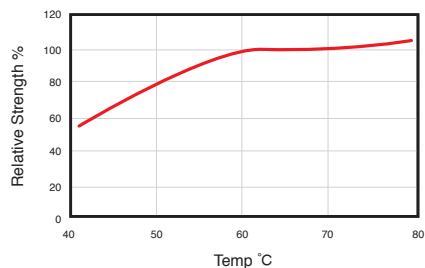

芒硝依存性 Dependency on Glauber's salt

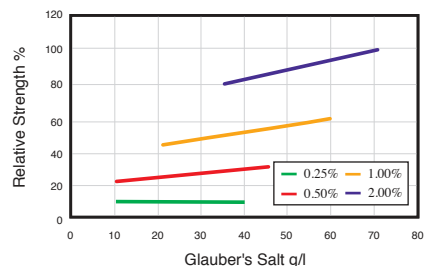

Everzol Red 6B


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	4-5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C10 C		4-5	5	4-5	5	5	4-5	4-5	Peroxide Bleaching雙氧水漂白			3-4	
	ISO C10 D		4-5	5	3-4	5	5	5	3-4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	4-5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	4-5	5	5	4-5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	5	4-5	5	5	5	Multi laundering 耐多次水洗		3.0%	4	
Hot Water 耐熱水		3.0%	4-5	5	5	3-4	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	2-3
Post mercerizing 後絲光		3.0%	4	-	3	-	-	-	-			4 Hours after		5
Acid hydrolysis 酸水解		3.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	2-3
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	3-4	Perspiration Light 耐汗日光	Acid	3.0 %	3	4-5	
	0.3 %	2-3	4		Alkali		3	4	
	1.0 %	3	4-5						
	3.0 %	3-4	5						
	6.0 %	4	5-6						

浴比依存性 Dependency on Liquor ratio

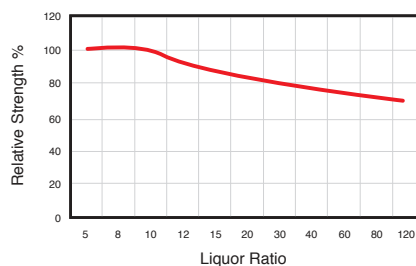

鹼依存性 Dependency on alkali

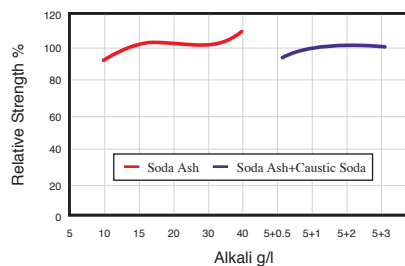


Everzol Green 6B


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		I
Substantivity 親和性		B
Migration 移染性		3-4
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	4
Color constancy 色恆性	Tungsten Lamp	B
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	3-4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	2-3
	Alkaline 鹼性	2


吸盡固著曲線 Exhaustion & Fixation

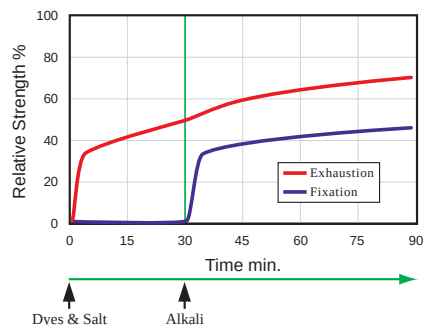

溫度依存性 Dependency on temperature

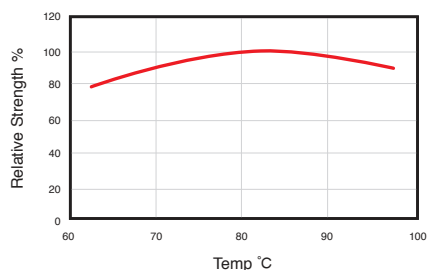

芒硝依存性 Dependency on Glauber's salt

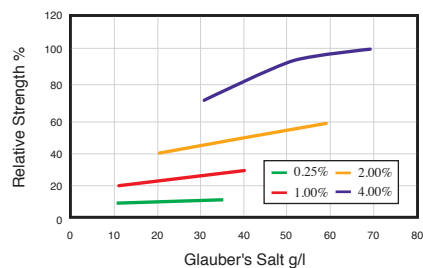

Everzol Green 6B


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	3	4-5	4-5	4-5	5	Chlorinated Water耐氯水(20ppm)		3.0%	2	
	ISO C10 C		4	5	3	5	5	5	5	Peroxide Bleaching雙氧水漂白			3-4	
	ISO C10 D		3-4	5	2-3	5	5	5	5	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		3-4	5	2-3	5	5	5	5		Wet 濕		3	
	ISO C06-C2S		4	5	2-3	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4	
	M&S C4A		3-4	5	3	5	5	5	5			3.0%	4	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	3-4	
Hot Water 耐熱水		3.0%	4-5	4-5	4-5	3-4	4-5	4-5	4-5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3-4
Post mercerizing 後絲光		3.0%	4		3-4						4 Hours after	4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	3-4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.3 %	3-4	4-5	Perspiration Light 耐汗日光	Acid	3 %	3	5
	1.0 %	4	5		Alkali		3-4	4-5
	3.0 %	4	5-6					
	6.0 %	4-5	6					
	8.0 %	4-5	6					

浴比依存性 Dependency on Liquor ratio

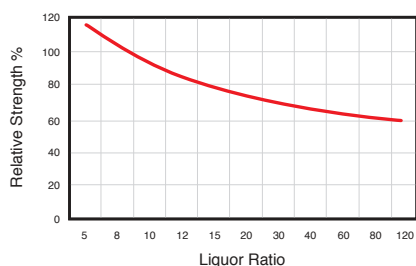

鹼依存性 Dependency on alkali

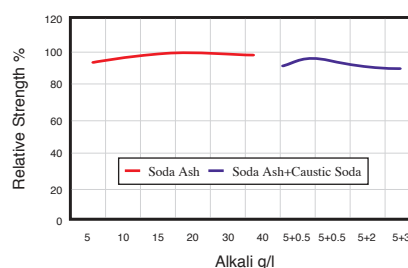


Everzol Turquoise Blue G


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		4
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4 D
	Dye Liquor 染浴	4 Y
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	5
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	4 Y
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3-4 Y
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	△
	(2)	△
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	2


吸盡固著曲線 Exhaustion & Fixation

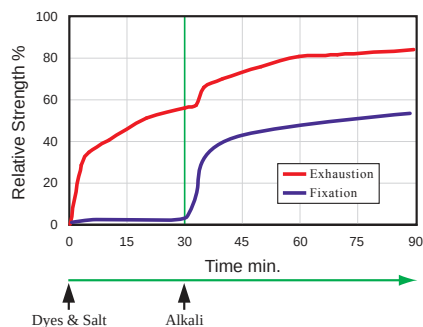

溫度依存性 Dependency on temperature

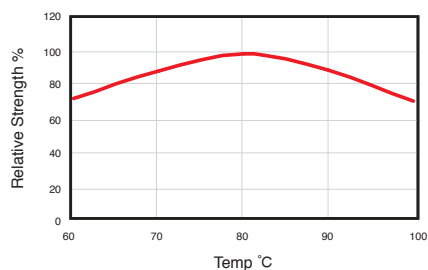

芒硝依存性 Dependency on Glauber's salt

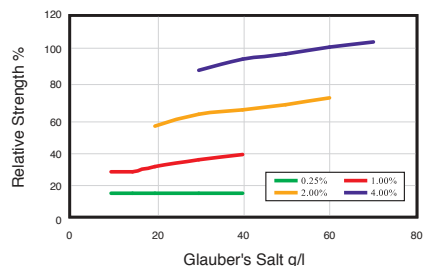

Everzol Turquoise Blue G


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	3-4	5	5	5	4-5	Chlorinated Water耐氯水(20ppm)		3.0%	3	
	ISO C10 C		4-5	5	3	4-5	5	5	4-5	Peroxide Bleaching雙氧水漂白			2	
	ISO C10 D		4-5	5	2	4-5	5	4-5	2-3	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	3	5	5	4-5	5		Wet 濕		2-3	
	ISO C06-C2S		5	5	3-4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	3	4	5	5	4-5			3.0%	4-5	
Water 耐水		3.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5
Post mercerizing 後絲光		3.0%	3G		4				4 Hours after			5		
Acid hydrolysis 酸水解		3.0%	3Y	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	4-5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3-4	5-6	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	4
	0.3 %	4	5-6		Alkali		2-3	3
	1.0 %	4	6					
	3.0 %	≧4-5	>6					
	6.0 %	≧4-5	>6					

浴比依存性 Dependency on Liquor ratio

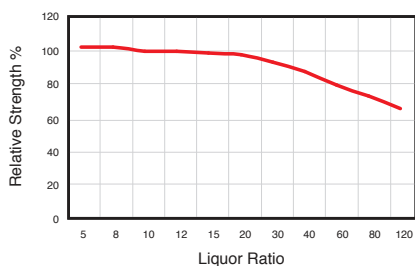

鹼依存性 Dependency on alkali

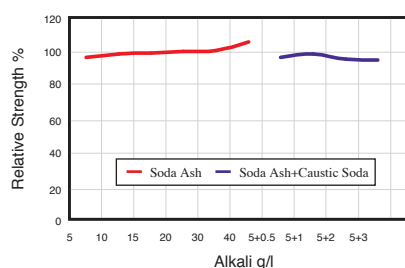


Everzol Brilliant Blue R s/p


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4 Y
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	○
	(4)	△
Discharge ability 拔染性	Neutral 中性	1
	Alkaline 鹼性	1-2


吸盡固著曲線 Exhaustion & Fixation

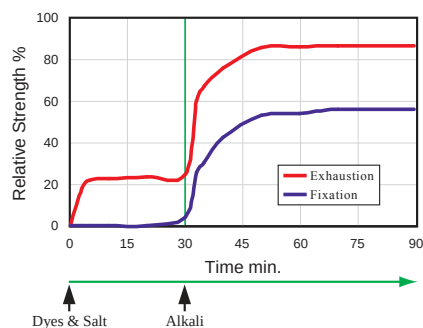

溫度依存性 Dependency on temperature

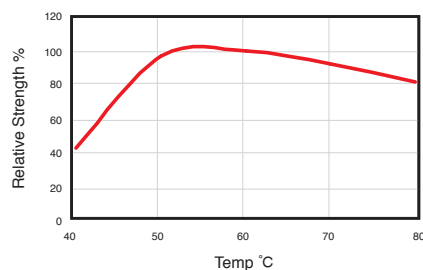

芒硝依存性 Dependency on Glauber's salt

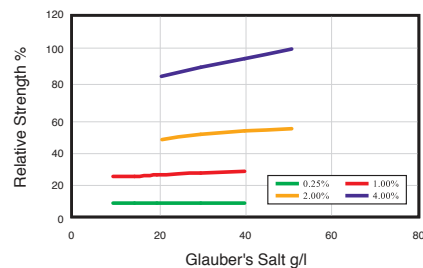

Everzol Brilliant Blue R s/p


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	4-5	5	5	4-5	Chlorinated Water耐氯水(20ppm)		3.0%	3	
	ISO C10 C		5	5	5	4	5	5	3	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		5	4	3	2	4-5	4-5	1-2	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		5	5	5	4-5	5	5	4-5		Wet 濕		2-3	
	ISO C06-C2S		5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	>4-5	
	M&S C4A		5	5	5	5	5	5	5			3.0%	>4-5	
Water 耐水		3.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	5	5	4-5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5
Post mercerizing 後絲光		3.0%	3R		2-3				4 Hours after			5		
Acid hydrolysis 酸水解		3.0%	4-5	4-5	4-5	4-5	4-5	4-5	4-5		Wet 濕	Immediately	3.0%	4-5
Perspiration 耐汗	Acid 酸	3.0%	5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	3-4	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4-5	5-6	Perspiration Light 耐汗日光	Acid	3.0 %	4	5	
	0.3 %	4-5	6		Alkali		4	4-5	
	1.0 %	>4-5	>6						
	3.0 %	>4-5	>6						
	6.0 %	>4-5	>6						

浴比依存性 Dependency on Liquor ratio

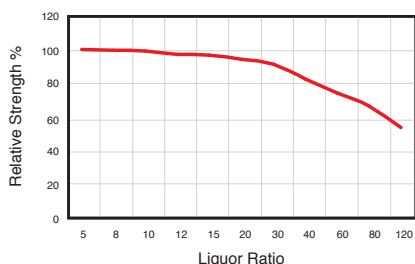

鹼依存性 Dependency on alkali

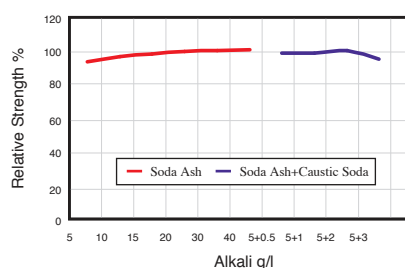


Everzol Royal Blue E-FR


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2
	Dye Liquor 染浴	3
Color constancy 色恆性	Tungsten Lamp	R (B)
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	3-4
	Glyoxal 乙二醛	4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3
	Quaternary ammonium salt 四級銨鹽	4
Stripping 脫色性	(1)	△
	(2)	△
	(3)	×
	(4)	△
Discharge ability 拔染性	Neutral 中性	1
	Alkaline 鹼性	2


吸盡固著曲線 Exhaustion & Fixation

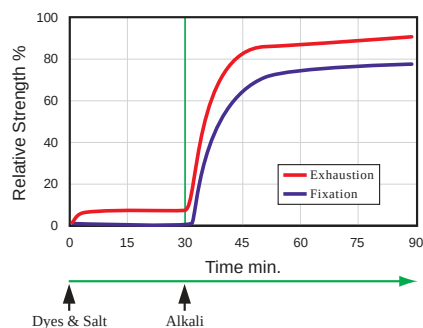

溫度依存性 Dependency on temperature

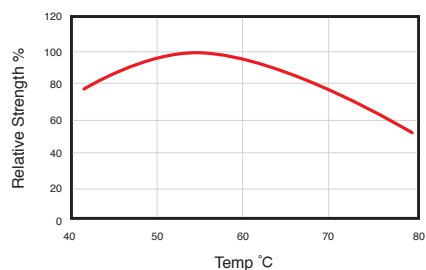

芒硝依存性 Dependency on Glauber's salt

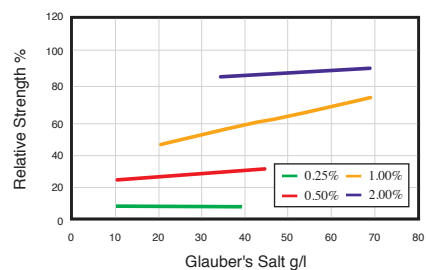

Everzol Royal Blue E-FR


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	3	
	ISO C10 C		4-5	5	4	5	5	5	5	Peroxide Bleaching雙氧水漂白		3.0%	2-3	
	ISO C10 D		4	5	3-4	5	5	5	5	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4	5	4	5	5	5	5		Wet 濕	3.0%	2-3	
	ISO C06-C2S		4	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	>4-5	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	>4-5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	3	
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3-4R
Post mercerizing 後絲光		3.0%	3-4	-	3-4	-	-	-	-		4 Hours after	3.0%	5	
Acid hydrolysis 酸水解		3.0%	5	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	3-4R
Perspiration 耐汗		3.0%	5	5	5	5	5	5	5			4 Hours after	3.0%	5
										Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	3	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4-5	5-6	Perspiration Light 耐汗日光	Acid	3.0 %	4-5	>6	
	0.3 %	4-5	5-6		Alkali		4-5	>6	
	1.0 %	>4-5	6						
	3.0 %	>4-5	>6						
	6.0 %	>4-5	>6						

浴比依存性 Dependency on Liquor ratio

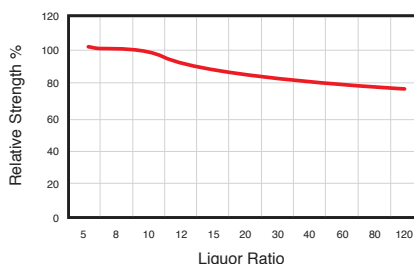

鹼依存性 Dependency on alkali

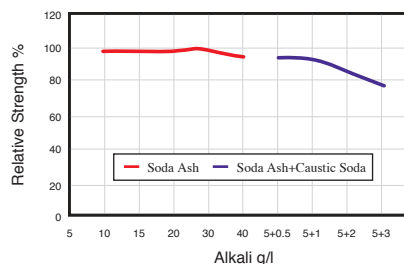


Everzol Blue BB


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4 Y
	Quaternary ammonium salt 四級銨鹽	4 Y
Stripping 脫色性	(1)	×
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

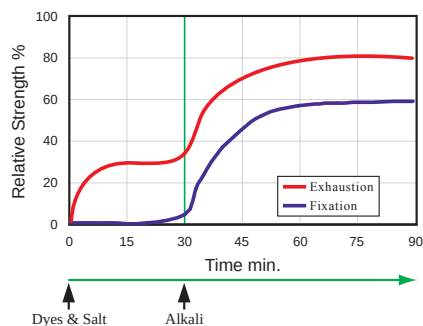

溫度依存性 Dependency on temperature

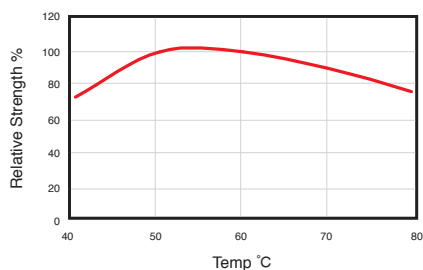

芒硝依存性 Dependency on Glauber's salt

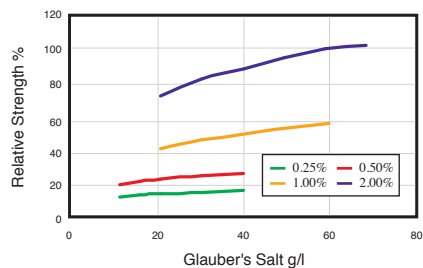

Everzol Blue BB


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	3	
	ISO C10 C		4-5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		4-5	5	4-5	5	5	5	3-4	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		5	5	5	5	5	5	5		Wet 濕		4	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	5	5	5	5	5			1.0%	4-5	
Water 耐水		1.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	4	
Hot Water 耐熱水		1.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		1.0%	4-5	
Sea Water 耐海水		1.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	4-5
Post mercerizing 後絲光		1.0%	3		5						4 Hours after	5		
Acid hydrolysis 酸水解		1.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	1.0%	4
Perspiration 耐汗	Acid 酸	1.0%	4	5	5	4-5	5	5	5		4 Hours after			4-5
	Alkali 鹼		4	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3-4	5	Perspiration Light 耐汗日光	Acid	1.0 %	2	4	
	0.3 %	4	5-6		Alkali		2-3	3-4	
	1.0 %	4-5	6						
	3.0 %	>4-5	>6						
	6.0 %	*	*						

浴比依存性 Dependency on Liquor ratio

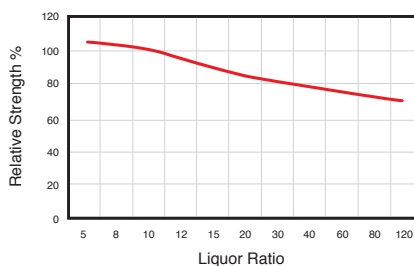

鹼依存性 Dependency on alkali

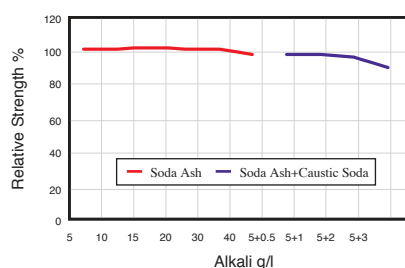


Everzol Blue BRF 150%


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		3-4
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	50
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp	G
	TL 84 Lamp	B (G)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	×
	(4)	×
Discharge ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	2-3


吸盡固著曲線 Exhaustion & Fixation

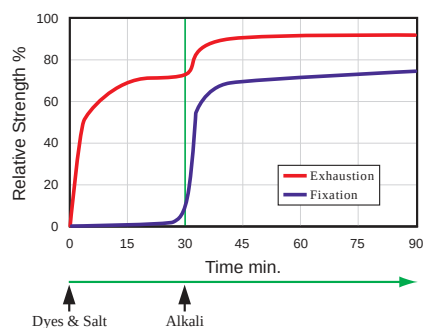

溫度依存性 Dependency on temperature

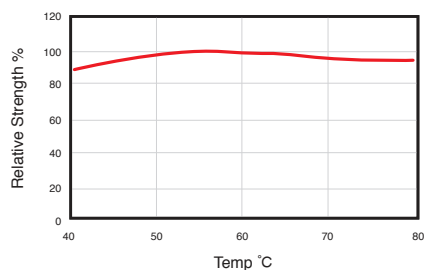

芒硝依存性 Dependency on Glauber's salt

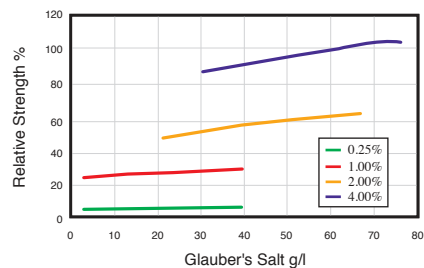

Everzol Blue BRF 150%


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	3-4	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4	
	ISO C10 C		4-5	5	3-4	5	5	5	5	Peroxide Bleaching雙氧水漂白			2-3	
	ISO C10 D		4-5	5	2-3	5	5	5	2-3	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	3-4	5	5	5	5		Wet 濕		3	
	ISO C06-C2S		4-5	5	3-4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	5	4-5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	3-4	5	3	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5
Post mercerizing 後絲光		3.0%	4		5						4 Hours after	5		
Acid hydrolysis 酸水解		3.0%	4-5	4-5	4-5	4-5	5	4-5	5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	4	5	5	5			4 Hours after		4-5
	Alkali 鹼			4-5	5	5	4	4-5	4-5	4-5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO	
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4-5	5-6	Perspiration Light 耐汗日光	Acid	3.0 %	3-4	5-6	
	0.3 %	4-5	6		Alkali		4	5	
	1.0 %	4-5	6						
	3.0 %	4-5	>6						
	6.0 %	4-5	>6						

浴比依存性 Dependency on Liquor ratio

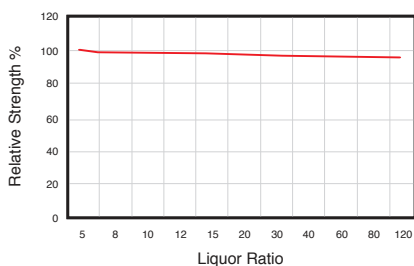

鹼依存性 Dependency on alkali

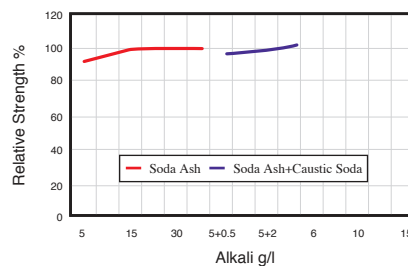


Everzol Blue NXF


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	1-2
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	3
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	3-4
Shade change after fixing treatment 固色後變色性	Polyamide 聚乙醯胺	3
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	X
	(2)	O
	(3)	O
	(4)	O
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4-5


吸盡固著曲線 Fixation & Fixation

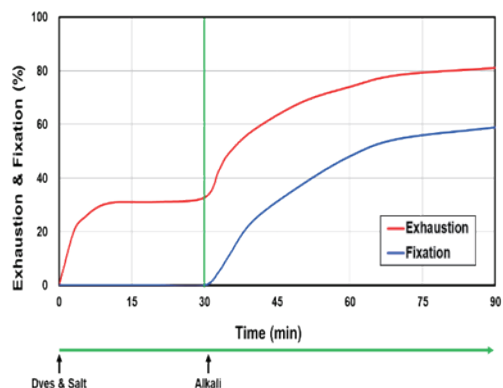

溫度依存性 Dependency on Temperature

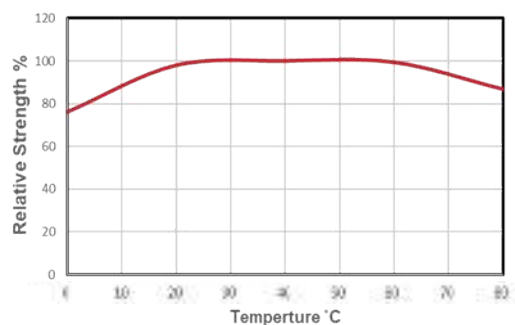

芒硝依存性 Dependency on Glauber's salt

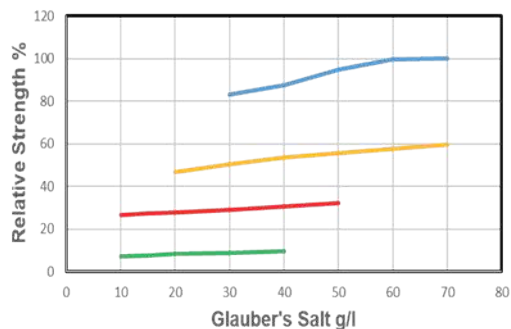

Everzol Blue NXF


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color Change 變褐色	Staing 污染						Evaluation		Depth of shade 染色濃度	Color change 變褐色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	5	5	5	5	5	Chlorinated Water 耐氯水 (20ppm)		1.0%	3	
	ISO C10 C		4-5	5	5	5	5	5	5	Peroxide Bleaching 雙氧水漂白		1.0%	4	
	ISO C10 D		4	5	5	5	5	5	3	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		4-5	5	5	5	5	5	5		Wet 濕	1.0%	4-5	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (Detergent Light)		0.1%	5	
	M&S C4A		4-5	5	5	5	5	5	5			1.0%	5	
Water 耐水		1.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	4-5	
Hot Water 耐熱水		1.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		1.0%	5	
Sea Water 耐海水		1.0%	4-5	5	5	5	5	5	5	Hot-Pressing 耐熱壓	Dry 乾	Immediately	1.0%	3-4
Post mercerizing 後絲光		1.0%	3	-	5	-	-	-	-		4 Hours after	1.0%	5	
Acid hydrolysis 酸水解		1.0%	4-5	5	5	5	5	5	5		Wet 溼	Immediately	1.0%	3-4
Perspiration 耐汗	Acid 酸	1.0%	4-5	5	5	5	5	5	5		4 Hours after	1.0%	4-5	
	Alkali 鹼	1.0%	4-5	5	5	5	5	5	5	Nitrogen Oxides 氣體變褐色		1.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing depth 染色濃度	Color Change 20AFU	Grade ISO Blue Scale	Evaluation		Dyeing depth 染色濃度	Color Change 20AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1%	4	5-6	Perspiration Light 耐汗日光	Acid	1.0%	1-2	4
	0.3%	4	5-6		Alkali		2	3-4
	1.0%	4-5	6					
	3.0%	4-5	>6					
	-	-	-					

浴比依存性 Dependency on Liquor ratio

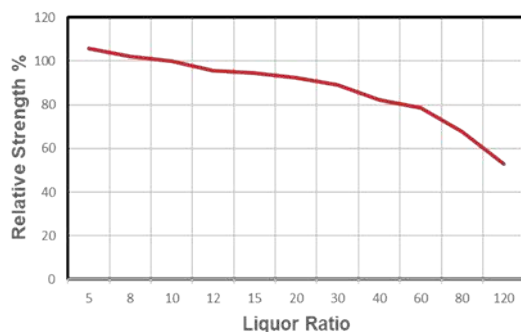

鹼依存性 Dependency on Alkali

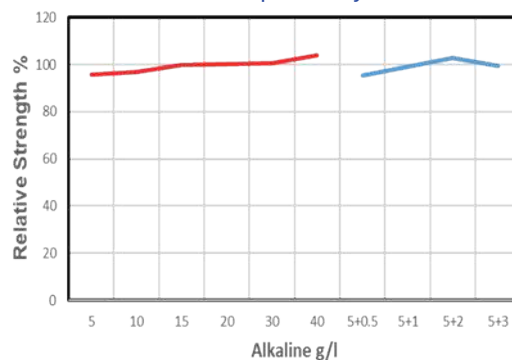


Everzol Blue RGB


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		III
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	1-2
Color constancy 色恆性	Tungsten Lamp	R (B)
	TL 84 Lamp	R (B)
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	1-2
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	×
Discharge ability 拔染性	Neutral 中性	2-3
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

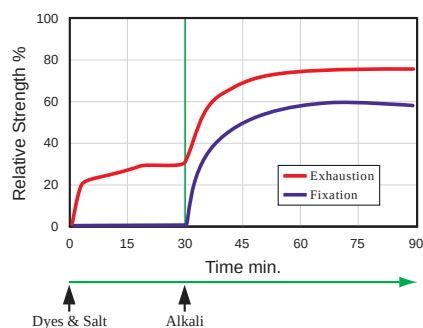

溫度依存性 Dependency on temperature

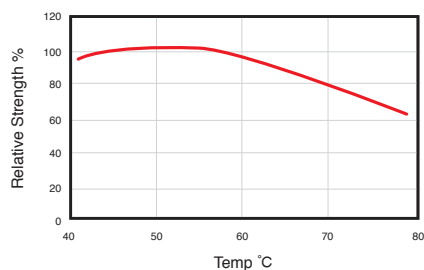

芒硝依存性 Dependency on Glauber's salt

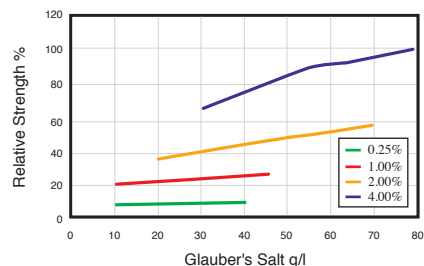

Everzol Blue RGB


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	3	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		4-5	5	4	5	5	5	3	Rubbing 耐摩擦	Dry 乾	3.0%	4	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕	3		
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	3-4	
Hot Water 耐熱水		3.0%	4-5	5	5	3	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	3-4		3						4 Hours after		4-5	
Acid hydrolysis 酸水解		3.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3	4	Perspiration Light 耐汗日光	Acid	3.0 %	2	4-5	
	0.3 %	3	4		Alkali		3	3	
	1.0 %	4	4						
	3.0 %	4	5-6						
	6.0 %	4-5	6						

浴比依存性 Dependency on Liquor ratio

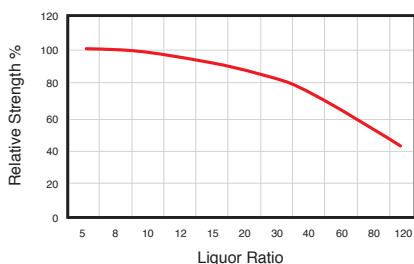

鹼依存性 Dependency on alkali

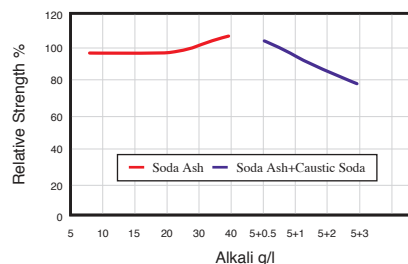


Everzol Navy Blue FBN


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4-5
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	3 G
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	×
Discharge ability 拔染性	Neutral 中性	2-3
	Alkaline 鹼性	2


吸盡固著曲線 Exhaustion & Fixation

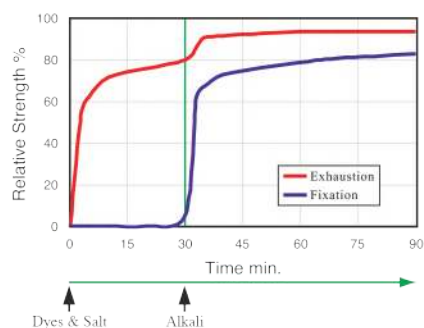

溫度依存性 Dependency on temperature

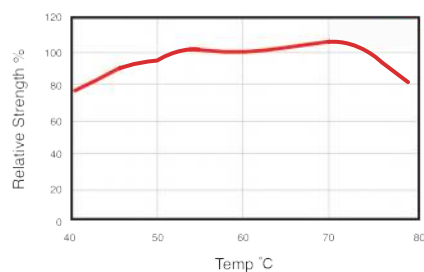

芒硝依存性 Dependency on Glauber's salt

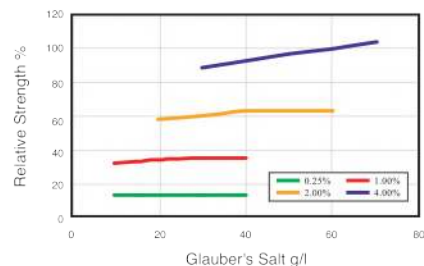

Everzol Navy Blue FBN


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		5	5	2-3	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	>4-5	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	>4-5	
Water 耐水		3.0%	5	5	4	3-4	5	4-5	4	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	5	5	4	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5
Post mercerizing 後絲光		3.0%	2-3R		3							4 Hours after		5
Acid hydrolysis 酸水解		3.0%	4-5	5	3-4	3-4	5	5	3-4		Wet 濕	Immediately	3.0%	4-5
Perspiration 耐汗	Acid 酸	3.0%	5	5	4	4-5	5	5	5			4 Hours after		4-5
	Alkali 鹼		5	5	4	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2-3	3-4	Perspiration Light 耐汗日光	Acid	3.0 %	2	4
	0.3 %	3	3-4		Alkali		2-3	3-4
	1.0 %	3-4	4					
	3.0 %	4	4-5					
	6.0 %	4-5	5					

浴比依存性 Dependency on Liquor ratio

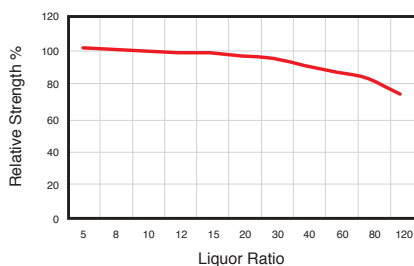

鹼依存性 Dependency on alkali

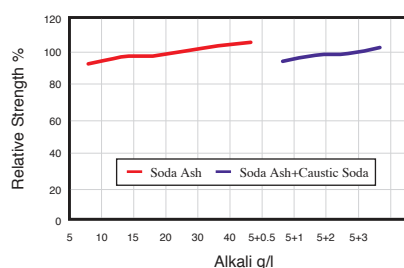


Everzol Navy Blue GG


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		5
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	3
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	3-4
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	×
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

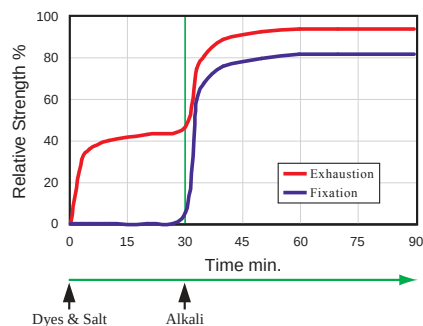

溫度依存性 Dependency on temperature

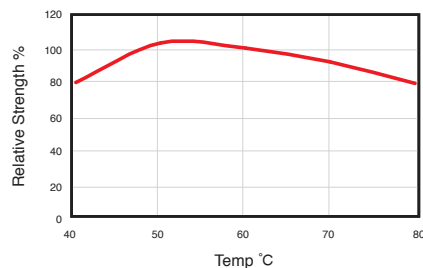

芒硝依存性 Dependency on Glauber's salt

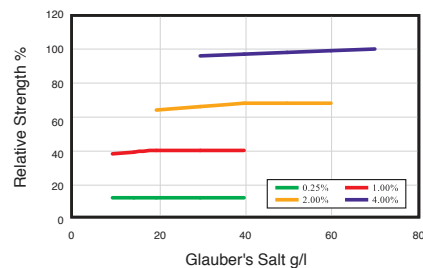

Everzol Navy Blue GG


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			3.0%	4-5
	ISO C10 C		4-5	5	4	5	5	5	5	Peroxide Bleaching雙氧水漂白				4
	ISO C10 D		4-5	5	2-3	5	5	5	2-3	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	4-5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)			0.3%	>4-5
	M&S C4A		4-5	5	5	5	5	5	5				3.0%	>4-5
Water 耐水		3.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗			3.0%	4-5
Hot Water 耐熱水		3.0%	4-5	5	4-5	5	5	5	5	Saliva (DIN) 耐唾液			3.0%	5
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5
Post mercerizing 後絲光		3.0%	2-3B		3				4 Hours after			4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	4-5	4-5	4-5	4-5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗		3.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
										Colorfastness to Nitrogen Oxides 氣體變褪色			3.0%	4-5


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3	3-4	Perspiration Light 耐汗日光	Acid	3.0 %	2	4
	0.3 %	3-4	4		Alkali		2-3	3-4
	1.0 %	3-4	5					
	3.0 %	4	5-6					
	6.0 %	4-5	5-6					

浴比依存性 Dependency on Liquor ratio

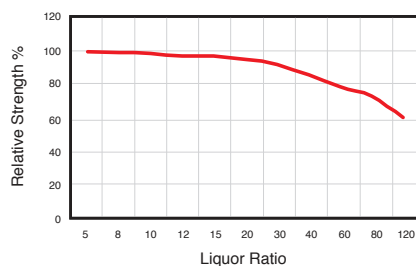

鹼依存性 Dependency on alkali

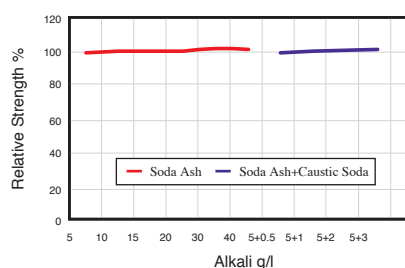


Everzol Navy Blue RGB H/C


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		2
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	G
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	2-3 R
	Cu ²⁺ 銅	3-4 R
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	×
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

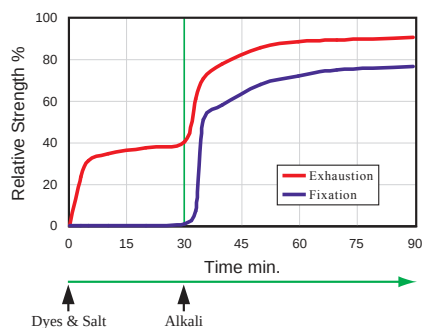

溫度依存性 Dependency on temperature

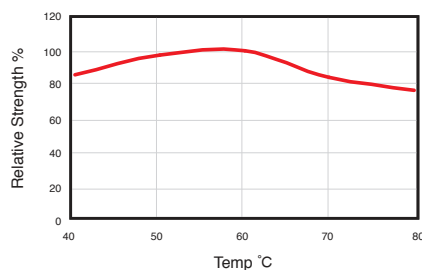

芒硝依存性 Dependency on Glauber's salt

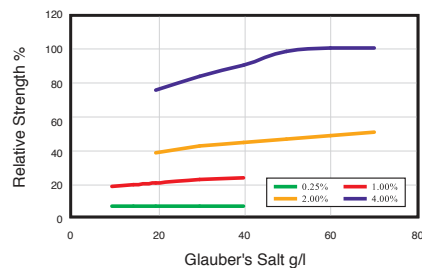

Everzol Navy Blue RGB H/C


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	3-4	
	ISO C10 C		4-5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白		4			
	ISO C10 D		3-4	5	4	4-5	5	5	3	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	5	5	5	5	5		Wet 濕	2-3		
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	>4-5	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	>4-5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3-4 R
Post mercerizing 後絲光		3.0%	2-3B		4				4 Hours after			4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	5	4-5	5	5	5		Wet 濕	Immediately	3.0%	3-4 R
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	4-5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
	0.1 %	2	3-4	Perspiration Light 耐汗日光	Acid Alkali	3.0 %	2 2-3	4 3-4
Artificial Light (Xenon-Arc Lamp) 耐日光	0.3 %	2-3	3-4					
	1.0 %	3	4					
	3.0 %	3-4	5-6					
	6.0 %	4	5-6					

浴比依存性 Dependency on Liquor ratio

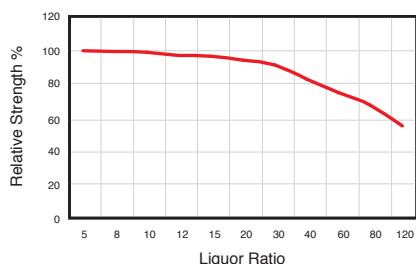

鹼依存性 Dependency on alkali

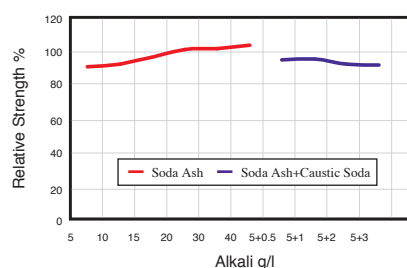


Everzol Black B


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2
	Dye Liquor 染浴	1-2
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5 Y
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

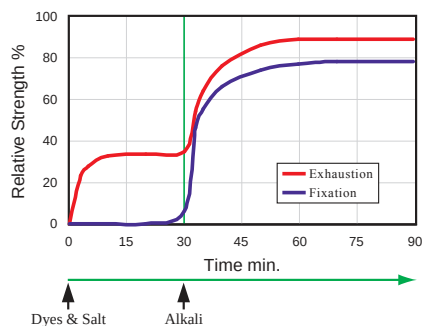

溫度依存性 Dependency on temperature

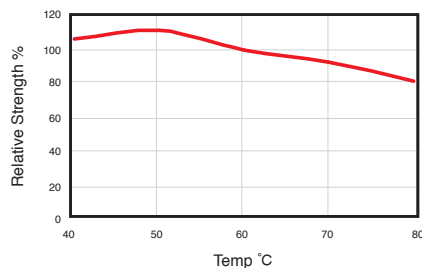

芒硝依存性 Dependency on Glauber's salt

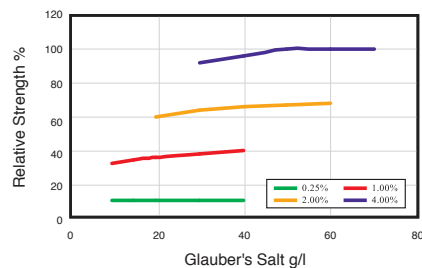

Everzol Black B


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	3	
	ISO C10 C		5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	3	5	5	3	Rubbing 耐摩擦	Dry 乾	3.0%	4-5		
	ISO C06-C1S		4-5	5	5	5	4-5	5		Wet 濕	2-3			
	ISO C06-C2S		4-5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		1.0%	3		
	M&S C4A		5	5	5	5	5	5			6.0%	4-5		
Water 耐水		3.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		6.0%	4	
Hot Water 耐熱水		3.0%	4-5	5	4-5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	2-3R		4						4 Hours after	4-5		
Acid hydrolysis 酸水解		3.0%	4	4-5	4-5	4-5	5	4-5	4-5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5		4 Hours after		4-5	
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.1 %	*	*	Perspiration Light 耐汗日光	Acid	3.0 %	2	4
		0.3 %	2-3	3-4		Alkali		2	3-4
		1.0 %	3-4	4					
		3.0 %	4	4-5					
		6.0 %	4-5	5					

浴比依存性 Dependency on Liquor ratio

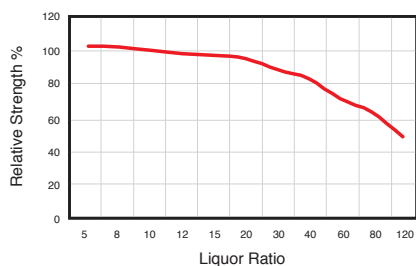

鹼依存性 Dependency on alkali

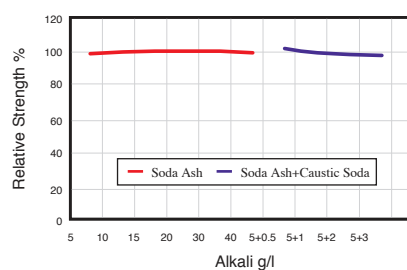


Everzol Black C-RL


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		2
Washing off 洗淨性		2-3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R (B)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

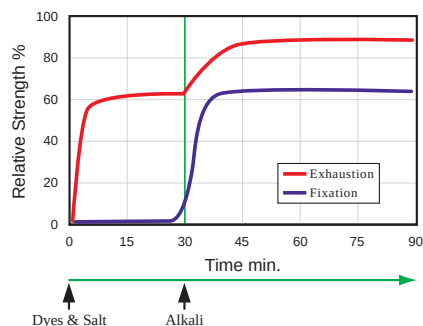

溫度依存性 Dependency on temperature

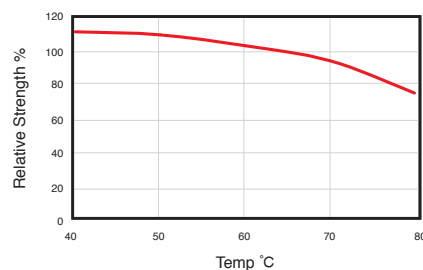

芒硝依存性 Dependency on Glauber's salt

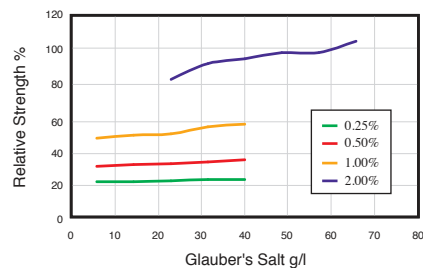

Everzol Black C-RL


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	1	
	ISO C10 C		4-5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			2-3	
	ISO C10 D		4	5	5	5	5	5	5	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		5	5	5	5	5	5	5		Wet 濕	4-5		
	ISO C06-C2S		5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.1%	>4-5	
	M&S C4A		5	5	5	5	5	5	5			1.0%	>4-5	
Water 耐水		1.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	2-3	
Hot Water 耐熱水		1.0%	5	5	4-5	5	5	5	5	Saliva (DIN) 耐唾液		1.0%	4-5	
Sea Water 耐海水		1.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	4-5Y
Post mercerizing 後絲光		1.0%	3R(Y)		4-5						4 Hours after	5		
Acid hydrolysis 酸水解		1.0%	5	5	5	4-5	5	5	5		Wet 濕	Immediately	1.0%	4Y
Perspiration 耐汗	Acid 酸	1.0%	5	5	5	5	5	5	5		4 Hours after			5
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	4-5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光		0.1 %	3-4	4-5	Perspiration Light 耐汗日光	Acid	1.0 %	3	5	
		0.3 %	3-4	5		Alkali		3-4	4	
		1.0 %	4	5-6						
		3.0 %	4-5	6						
		6.0 %	*	*						

浴比依存性 Dependency on Liquor ratio

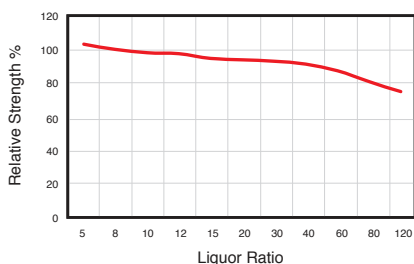

鹼依存性 Dependency on alkali

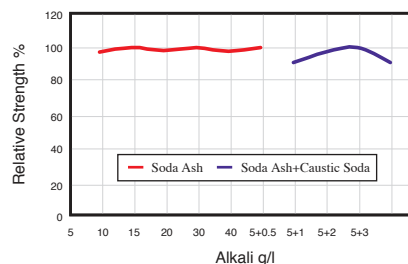


Everzol Black GR


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		I
Substantivity 親和性		C
Migration 移染性		2
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	2-3
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3-4 Y
	Quaternary ammonium salt 四級銨鹽	3-4 G
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

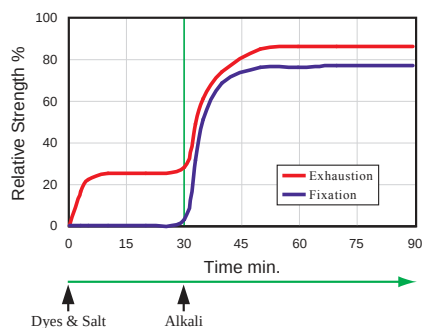

溫度依存性 Dependency on temperature

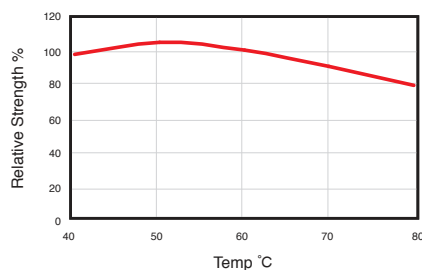

芒硝依存性 Dependency on Glauber's salt

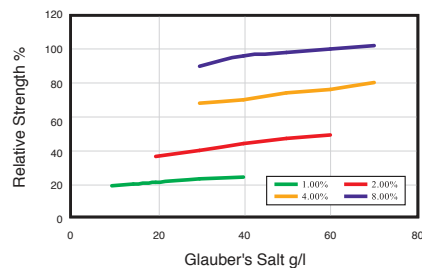

Everzol Black GR


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			6.0%	4
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白				4-5
	ISO C10 D		4-5	5	3	5	5	4-5	2	Rubbing 耐摩擦	Dry 乾	6.0%	4	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕	2-3		
	ISO C06-C2S		4-5	5	4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)			1.0%	4
	M&S C4A		4-5	5	4-5	5	5	5	5				6.0%	>4-5
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗			6.0%	4
Hot Water 耐熱水		6.0%	4-5	5	4-5	5	5	5	5	Saliva (DIN) 耐唾液			3.0%	5
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4
Post mercerizing 後絲光		6.0%	2-3R		4				4 Hours after			4-5		
Acid hydrolysis 酸水解		6.0%	4-5	4-5	5	5	5	5	5		Wet 濕	Immediately	6.0%	4
Perspiration 耐汗		6.0%	4-5	5	5	5	5	5	5			4 Hours after	4-5	
										Colorfastness to Nitrogen Oxides 氣體變褪色			6.0%	5


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.3 %	*	*	Perspiration Light	Acid	6.0 %	2-3	5
		1.0 %	2-3	3-4	耐汗日光	Alkali		3	3-4
		3.0 %	3	4-5					
		6.0 %	3-4	5-6					
		8.0 %	4	5-6					

浴比依存性 Dependency on Liquor ratio

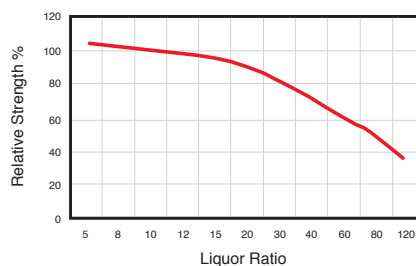

鹼依存性 Dependency on alkali

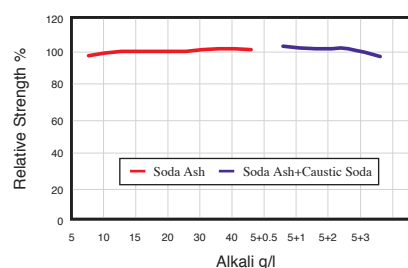


Everzol Black GRN


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		3
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	2-3
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3-4 Y
	Quaternary ammonium salt 四級銨鹽	3-4 G
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

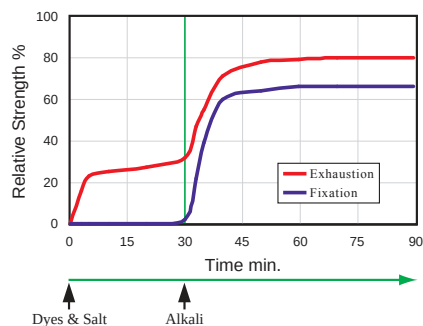

溫度依存性 Dependency on temperature

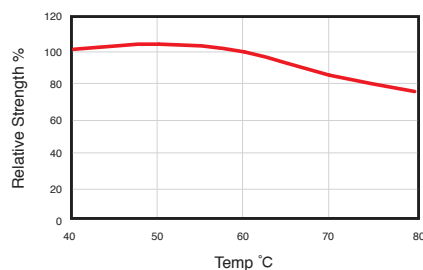

芒硝依存性 Dependency on Glauber's salt

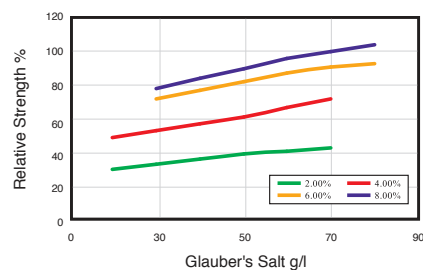

Everzol Black GRN


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			6.0%	4
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白				4-5
	ISO C10 D		4-5	5	3	5	5	4-5	2	Rubbing 耐摩擦	Dry 乾	6.0%	4	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕	2-3		
	ISO C06-C2S		4-5	5	4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)			1.0%	4
	M&S C4A		4-5	5	4-5	5	5	5	5				6.0%	>4-5
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗			6.0%	4
Hot Water 耐熱水		6.0%	4-5	5	4-5	5	5	5	5	Saliva (DIN) 耐唾液			6.0%	5
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4
Post mercerizing 後絲光		6.0%	2-3R		4-5				4 Hours after			4-5		
Acid hydrolysis 酸水解		6.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	6.0%	4
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	5	5	5	5	5			4 Hours after	4-5	
	Alkali 鹼	6.0%	4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			6.0%	5


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.3 %	*	*	Perspiration Light	Acid	6.0 %	2-3	5
	1.0 %	2-3	3-4	耐汗日光	Alkali		3	3-4
	3.0 %	3	4-5					
	6.0 %	3-4	5-6					
	8.0 %	4	5-6					

浴比依存性 Dependency on Liquor ratio

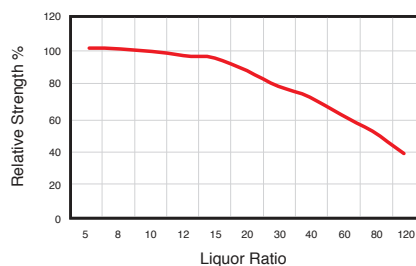

鹼依存性 Dependency on alkali

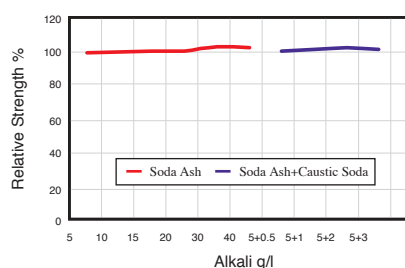


Everzol Black N


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	2
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3-4 Y
	Quaternary ammonium salt 四級銨鹽	3-4 G
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

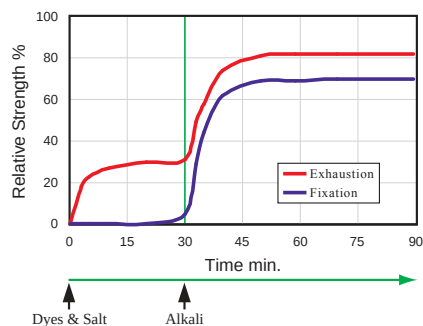

溫度依存性 Dependency on temperature

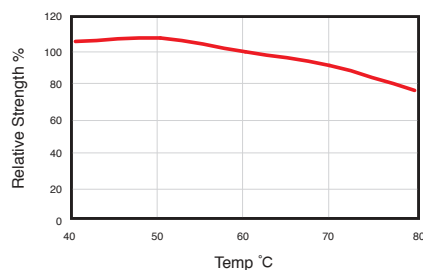

芒硝依存性 Dependency on Glauber's salt

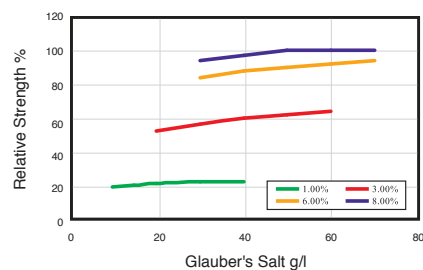

Everzol Black N


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			6.0%	4-5
	ISO C10 C		4-5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5		
	ISO C10 D		4-5	5	3-4	4	5	4-5	2	Rubbing 耐摩擦	Dry 乾	6.0%	4-5	
	ISO C06-C1S		4-5	5	5	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)			1.0%	4
	M&S C4A		4-5	5	5	4	5	5	5				6.0%	>4-5
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗			6.0%	4
Hot Water 耐熱水		6.0%	4-5	5	4-5	5	5	5	5	Saliva (DIN) 耐唾液			6.0%	5
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4
Post mercerizing 後絲光		6.0%	2-3R		4-5				4 Hours after			4-5		
Acid hydrolysis 酸水解		6.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	6.0%	4
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			6.0%	5


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.3 %	*	*	Perspiration Light 耐汗日光	Acid	6.0 %	2-3	5
	1.0 %	2-3	3-4		Alkali		3	3-4
	3.0 %	3	4-5					
	6.0 %	3-4	5-6					
	8.0 %	4	5-6					

浴比依存性 Dependency on Liquor ratio

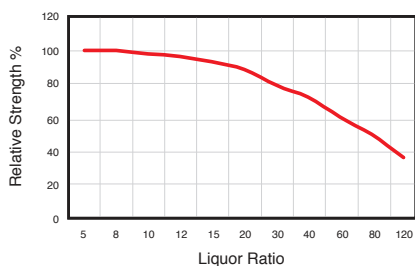

鹼依存性 Dependency on alkali

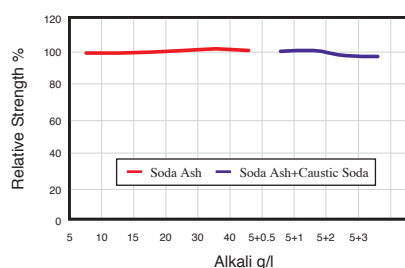


Everzol Black NR


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	2
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3-4 Y
	Quaternary ammonium salt 四級銨鹽	3-4 G
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

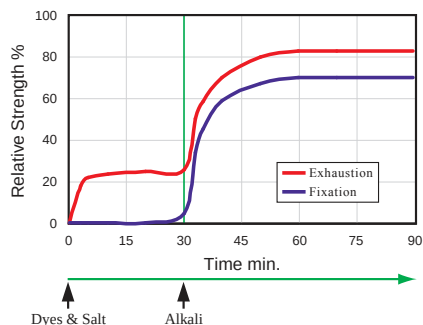

溫度依存性 Dependency on temperature

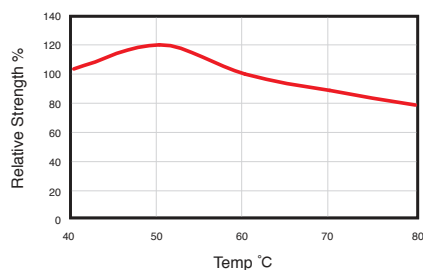

芒硝依存性 Dependency on Glauber's salt

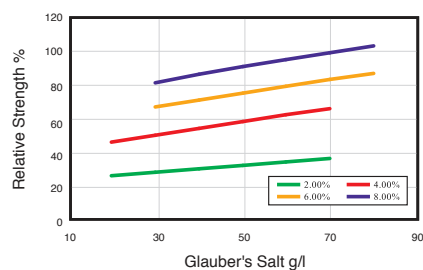

Everzol Black NR


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		6.0%	4-5	
	ISO C10 C		4-5	5	5	5	5	5	4-5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	3	4	5	4-5	2	Rubbing 耐摩擦	Dry 乾	6.0%	4	
	ISO C06-C1S		4-5	5	5	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		1.0%	4	
	M&S C4A		4-5	5	5	5	5	5	5			6.0%	>4-5	
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		6.0%	4	
Hot Water 耐熱水		6.0%	4-5	5	4-5	5	5	5	5	Saliva (DIN) 耐唾液		6.0%	5	
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4
Post mercerizing 後絲光		6.0%	2-3R		4-5				4 Hours after			4-5		
Acid hydrolysis 酸水解		6.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	6.0%	4
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		6.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光		0.3 %	*	*	Perspiration Light	Acid	6.0 %	2-3	5	
		1.0 %	2-3	3-4	耐汗日光	Alkali		3	3-4	
		3.0 %	3	4-5						
		6.0 %	3-4	5-6						
		8.0 %	4	5-6						

浴比依存性 Dependency on Liquor ratio

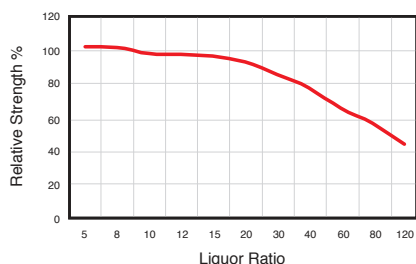

鹼依存性 Dependency on alkali

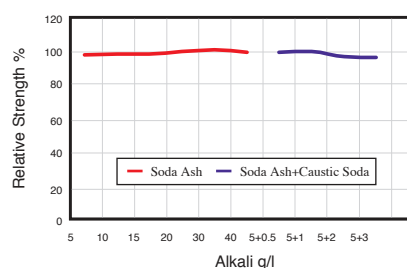


Everzol Black GSP


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

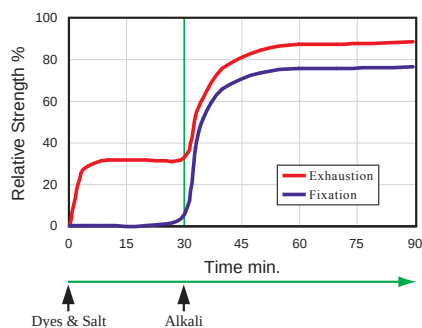

溫度依存性 Dependency on temperature

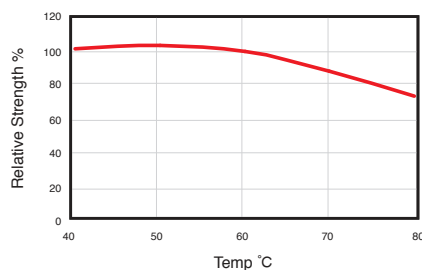

芒硝依存性 Dependency on Glauber's salt

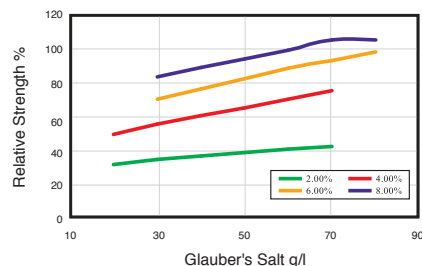

Everzol Black GSP


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	5	4-5	5	5	4-5	Chlorinated Water耐氯水(20ppm)		6.0%	4-5	
	ISO C10 C		4-5	5	5	4-5	5	5	4	Peroxide Bleaching雙氧水漂白			5	
	ISO C10 D		4-5	4-5	3	3	5	4-5	2	Rubbing 耐摩擦	Dry 乾	6.0%	4	
	ISO C06-C1S		4-5	5	5	4-5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	5	4-5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		1.0%	4	
	M&S C4A		4-5	5	5	5	5	5	5			6.0%	>4-5	
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		6.0%	4-5	
Hot Water 耐熱水		6.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		6.0%	5	
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4-5
Post mercerizing 後絲光		6.0%	2-3R		4-5				4 Hours after			4-5		
Acid hydrolysis 酸水解		6.0%	4-5	5	5	4	5	5	5		Wet 濕	Immediately	6.0%	4-5
Perspiration 耐汗		6.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
										Colorfastness to Nitrogen Oxides 氣體變褪色		6.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.3 %	*	*	Perspiration Light 耐汗日光	Acid	6.0 %	2-3	5
		1.0 %	2-3	3-4		Alkali		3	3-4
		3.0 %	3	4-5					
		6.0 %	3-4	5-6					
		8.0 %	4	5-6					

浴比依存性 Dependency on Liquor ratio

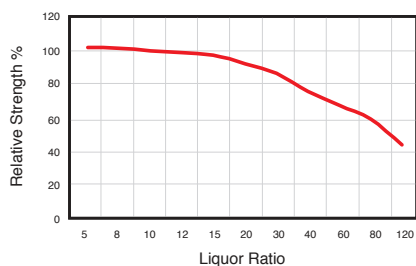

鹼依存性 Dependency on alkali

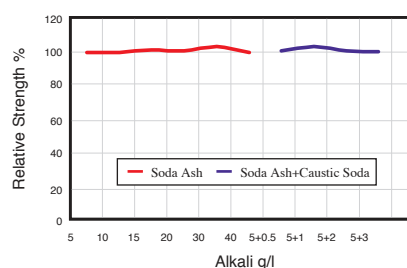


Everzol Black MWF


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	×
	(4)	×
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

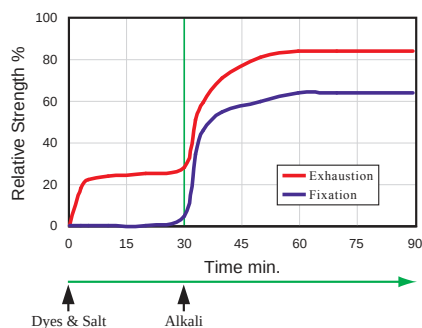

溫度依存性 Dependency on temperature

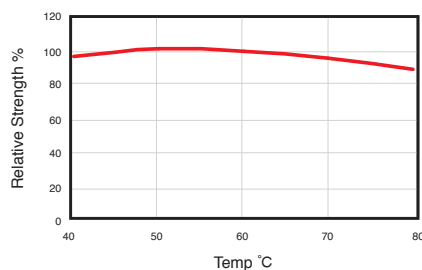

芒硝依存性 Dependency on Glauber's salt

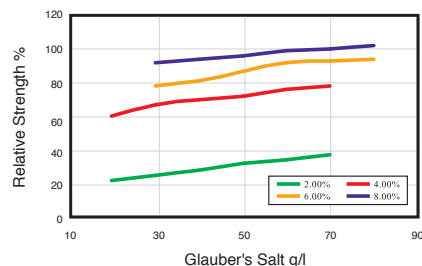

Everzol Black MWF


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	5	4-5	5	5	4-5	Chlorinated Water耐氯水(20ppm)		6.0%	4-5	
	ISO C10 C		4-5	5	4-5	5	5	5	4	Peroxide Bleaching雙氧水漂白			5	
	ISO C10 D		4-5	5	3	3	5	4-5	2	Rubbing 耐摩擦	Dry 乾	6.0%	4	
	ISO C06-C1S		4-5	5	5	4-5	5	5	4-5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	5	4-5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		1.0%	4	
	M&S C4A		4-5	5	5	5	5	5	5			6.0%	>4-5	
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		6.0%	4-5	
Hot Water 耐熱水		6.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		6.0%	5	
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4-5
Post mercerizing 後絲光		6.0%	2-3R						4 Hours after			4-5		
Acid hydrolysis 酸水解		6.0%	4-5	5	5	4-5	5	5	5		Wet 濕	Immediately	6.0%	4-5
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		6.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.3 %	*	*	Perspiration Light	Acid	6.0 %	2-3	5
		1.0 %	2-3	4	耐汗日光	Alkali		3	3-4
		3.0 %	3	4-5					
		6.0 %	3-4	5-6					
		8.0 %	4	5-6					

浴比依存性 Dependency on Liquor ratio

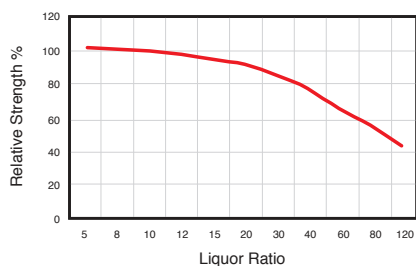

鹼依存性 Dependency on alkali

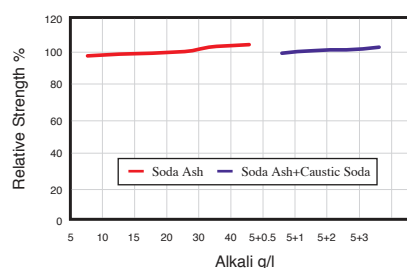


Everzol Black DGL


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	3-4
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	2-3
Resin finishing 樹脂加工	Melamine 三聚氰胺	3-4
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

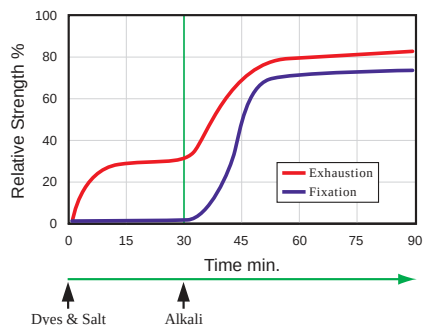

溫度依存性 Dependency on temperature

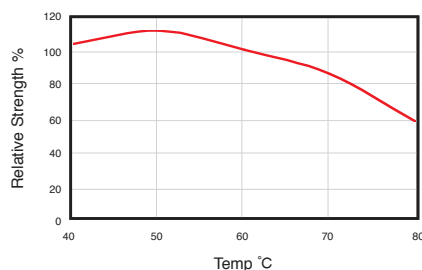

芒硝依存性 Dependency on Glauber's salt

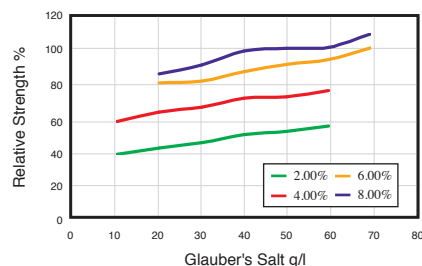

Everzol Black DGL


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		6.0%	3-4	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			5	
	ISO C10 D		4-5	5	2-3	4-5	5	4-5	2-3	Rubbing 耐摩擦	Dry 乾	6.0%	4-5	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		1.0%	4-5	
	M&S C4A		4-5	5	5	5	5	5	5			6.0%	>4-5	
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		6.0%	4-5	
Hot Water 耐熱水		6.0%	4-5	5	5	4-5	5	5	5	Saliva (DIN) 耐唾液		6.0%	5	
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4-5
Post mercerizing 後絲光		6.0%	3-4R		3-4				4 Hours after			4-5		
Acid hydrolysis 酸水解		6.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	6.0%	4-5
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		6.0%	4-5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.3 %	*	*	Perspiration Light 耐汗日光	Acid	6.0 %	2-3	5
		1.0 %	3	4		Alkali		3-4	3-4
		3.0 %	4	5					
		6.0 %	4-5	6					
		8.0 %	5	6					

浴比依存性 Dependency on Liquor ratio

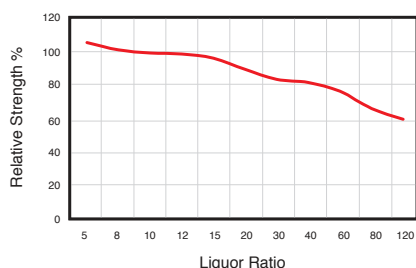

鹼依存性 Dependency on alkali

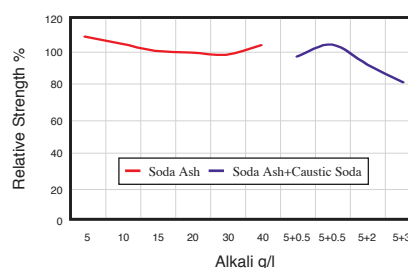


Everzol Black DRL


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	1
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	2-3
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

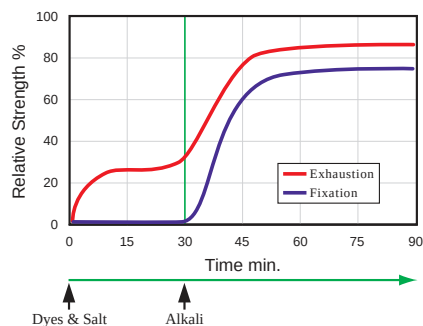

溫度依存性 Dependency on temperature

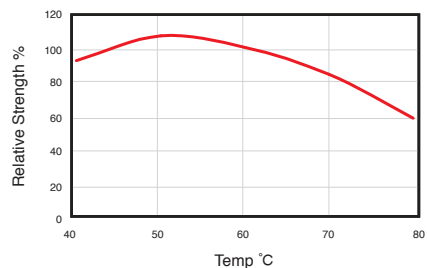

芒硝依存性 Dependency on Glauber's salt

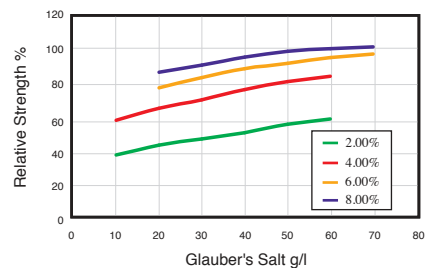

Everzol Black DRL


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			6.0%	4-5
	ISO C10 C		4-5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5		
	ISO C10 D		4-5	5	2-3	4-5	5	4-5	2-3	Rubbing 耐摩擦	Dry 乾	6.0%	4	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)			1.0%	4
	M&S C4A		4-5	5	5	5	5	5	5				6.0%	>4-5
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗			6.0%	4
Hot Water 耐熱水		6.0%	4-5	5	4-5	3-4	4-5	5	5	Saliva (DIN) 耐唾液			6.0%	5
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4-5
Post mercerizing 後絲光		6.0%	3-4R		3-4				4 Hours after			4-5		
Acid hydrolysis 酸水解		6.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	6.0%	4-5
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼			4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			6.0%


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.3 %	*	*	Perspiration Light 耐汗日光	Acid Alkali	6.0 %	2-3	5
		1.0 %	3	4				3-4	3-4
		3.0 %	3-4	5					
		6.0 %	4	5-6					
		8.0 %	4-5	6					

浴比依存性 Dependency on Liquor ratio

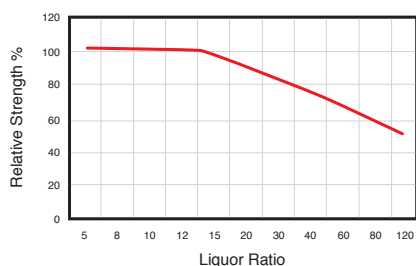

鹼依存性 Dependency on alkali

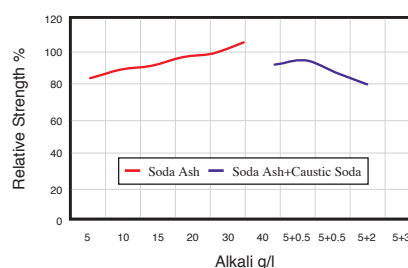


Everzol Yellow LX


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2
	Dye Liquor 染浴	1-2
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4G
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	×
	(4)	△
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

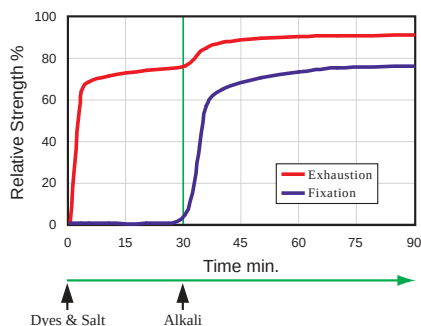

溫度依存性 Dependency on temperature

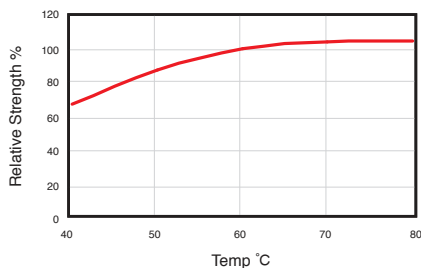

芒硝依存性 Dependency on Glauber's salt

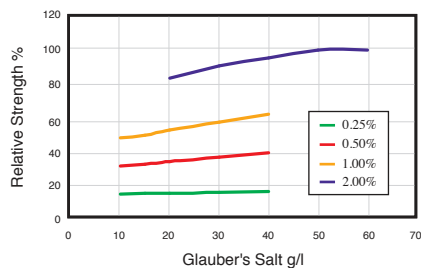

Everzol Yellow LX


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	4-5	
	ISO C10 C		5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		5	5	4	5	5	5	5	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		5	5	5	5	5	5	5		Wet 濕		4	
	ISO C06-C2S		5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.1%	>4-5	
	M&S C4A		5	5	5	5	5	5	5			1.0%	>4-5	
Water 耐水		1.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	4-5	
Hot Water 耐熱水		1.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		1.0%	5	
Sea Water 耐海水		1.0%	5	5	5	5	5	5	5	Hot-Pressing 耐熱壓	Dry 乾	Immediately	1.0%	4
Post mercerizing 後絲光		1.0%	4R		4-5							4 Hours after		4-5
Acid hydrolysis 酸水解		1.0%	4-5	5	4-5	5	5	5	5		Wet 濕	Immediately	1.0%	4
Perspiration 耐汗	Acid 酸	1.0%	5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	4-5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4-5	6	Perspiration Light 耐汗日光	Acid	1.0 %	4-5	>6	
	0.3 %	>4-5	>6		Alkali		4-5	5	
	1.0 %	>4-5	>6						
	3.0 %	>4-5	>6						
	6.0 %	*	*						

浴比依存性 Dependency on Liquor ratio

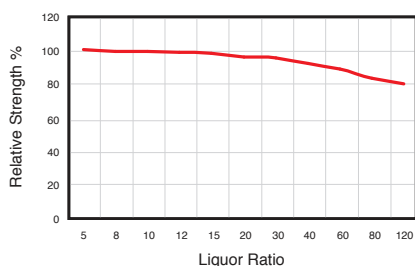

鹼依存性 Dependency on alkali

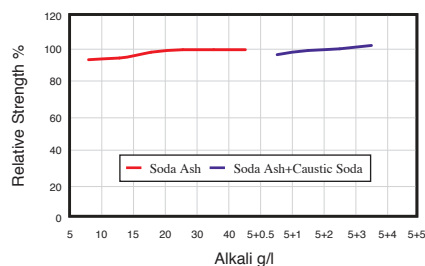


Everzol Red LX


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4
	Dye Liquor 染浴	4
Color constancy 色恆性	Tungsten Lamp	R (Y)
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	1
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

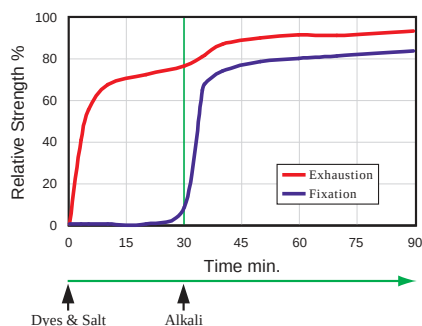

溫度依存性 Dependency on temperature

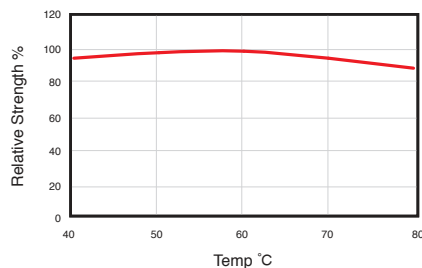

芒硝依存性 Dependency on Glauber's salt

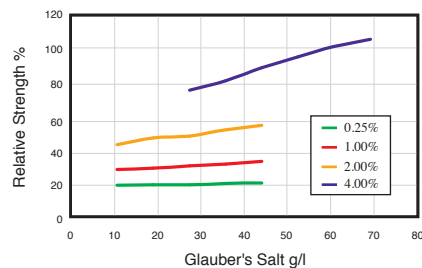

Everzol Red LX


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	4	
	ISO C10 C		5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	4	5	5	5	5	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		5	5	5	5	5	5	5		Wet 濕		4	
	ISO C06-C2S		5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.1%	4-5	
	M&S C4A		5	5	5	5	5	5	5			1.0%	4-5	
Water 耐水		1.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	5	
Hot Water 耐熱水		1.0%	5	5	4-5	4-5	5	5	5	Saliva (DIN) 耐唾液		1.0%	4-5	
Sea Water 耐海水		1.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	3B
Post mercerizing 後絲光		1.0%	2-3(B)		4-5				4 Hours after			4-5		
Acid hydrolysis 酸水解		1.0%	5	5	4-5	4	5	5	5		Wet 濕	Immediately	1.0%	3-4B
Perspiration 耐汗	Acid 酸	1.0%	5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.1 %	2-3	4	Perspiration Light 耐汗日光	Acid Alkali	1.0 %	2-3	4
		0.3 %	3	4-5				3	3-4
		1.0 %	3-4	4-5					
		3.0 %	4	5-6					
		6.0 %	*	*					

浴比依存性 Dependency on Liquor ratio

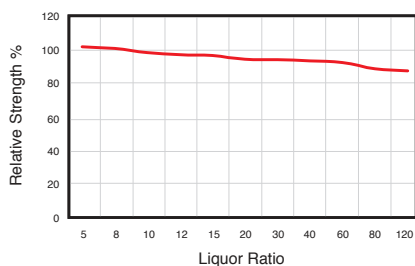

鹼依存性 Dependency on alkali

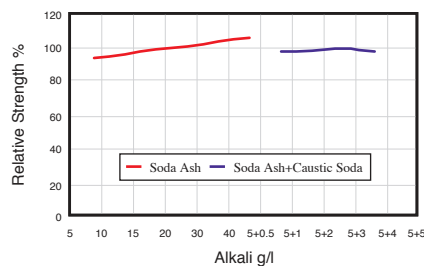


Everzol Blue LX


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	20
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp	G
	TL 84 Lamp	B (G)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	×
	(4)	×
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

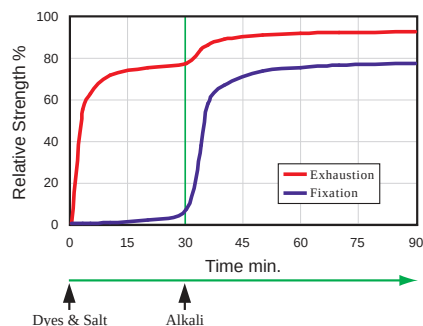

溫度依存性 Dependency on temperature

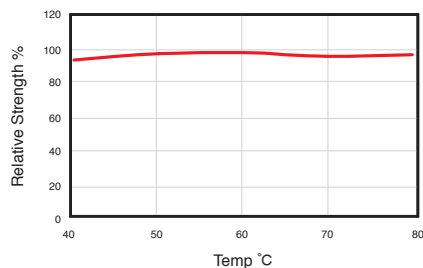

芒硝依存性 Dependency on Glauber's salt

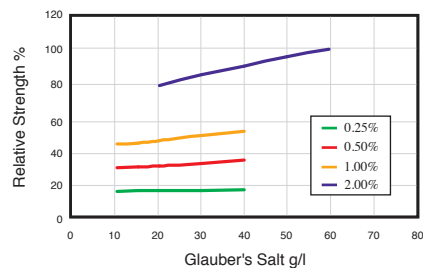

Everzol Blue LX


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	2-3	
	ISO C10 C		5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			2-3	
	ISO C10 D		4-5	5	3-4	5	5	5	4	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		3-4	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.1%	4-5	
	M&S C4A		5	5	4-5	5	5	5	5			1.0%	4-5	
Water 耐水		1.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	4-5	
Hot Water 耐熱水		1.0%	5	4-5	5	4	5	5	5	Saliva (DIN) 耐唾液		1.0%	5	
Sea Water 耐海水		1.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	4-5
Post mercerizing 後絲光		1.0%	4-5		5						4 Hours after	5		
Acid hydrolysis 酸水解		1.0%	4-5	4-5	4-5	4-5	5	5	5		Wet 濕	Immediately	1.0%	4
Perspiration 耐汗	Acid 酸	1.0%	5	5	5	4-5	5	5	5			4 Hours after		
	Alkali 鹼		5	5	5	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	4	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO	
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4-5	5-6	Perspiration Light 耐汗日光	Acid	1.0 %	3-4	5	
	0.3 %	4-5	6		Alkali		3-4	4-5	
	1.0 %	4-5	6						
	3.0 %	4-5	>6						
	6.0 %	*	*						

浴比依存性 Dependency on Liquor ratio

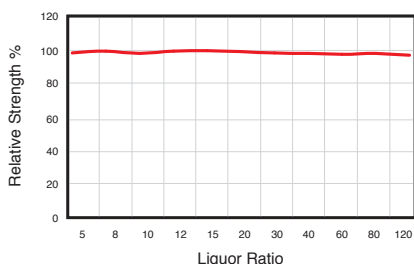

鹼依存性 Dependency on alkali

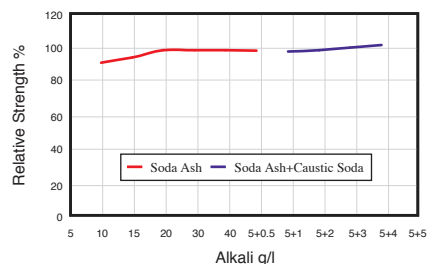


Everzol Navy LX


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4-5
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	1-2 R
	TL 84 Lamp	2 R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	3 G
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	×
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	3-4


吸盡固著曲線 Exhaustion & Fixation

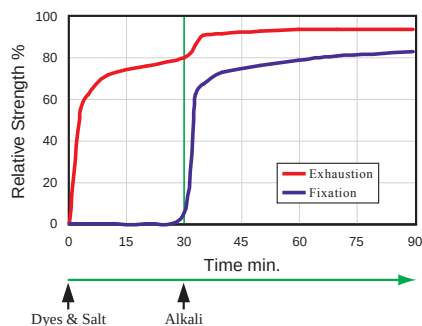

溫度依存性 Dependency on temperature

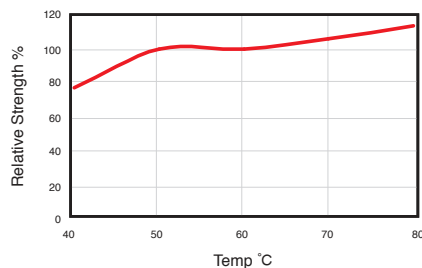

芒硝依存性 Dependency on Glauber's salt

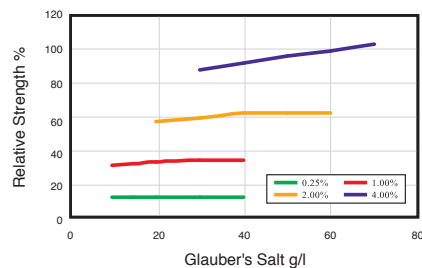

Everzol Navy LX


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		5	5	4	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	>4-5	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	>4-5	
Water 耐水		3.0%	5	5	4-5	4-5	5	5	4	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	5	5	4	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5
Post mercerizing 後絲光		3.0%	2-3R		4							4 Hours after		5
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	4-5	5	5	4-5		Wet 濕	Immediately	3.0%	4-5
Perspiration 耐汗	Acid 酸	3.0%	5	5	4-5	4-5	5	5	5			4 Hours after		4-5
	Alkali 鹼		5	5	4-5	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.1 %	2-3	3-4	Perspiration Light 耐汗日光	Acid	3.0 %	2	4
		0.3 %	3	3-4		Alkali		2-3	3-4
		1.0 %	3-4	4					
		3.0 %	4	4-5					
		6.0 %	4-5	5					

浴比依存性 Dependency on Liquor ratio

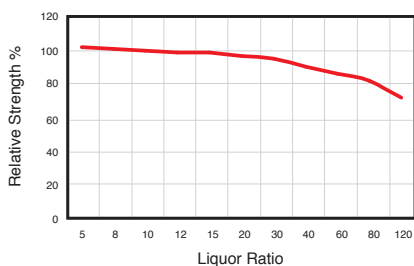

鹼依存性 Dependency on alkali

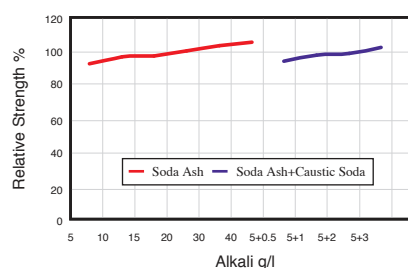


Everzol Red LF-B


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4-5
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	1
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	2-3
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	△
	(2)	△
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

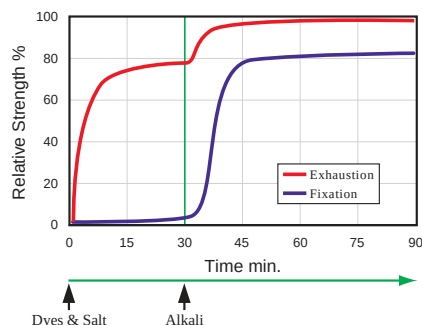

溫度依存性 Dependency on temperature

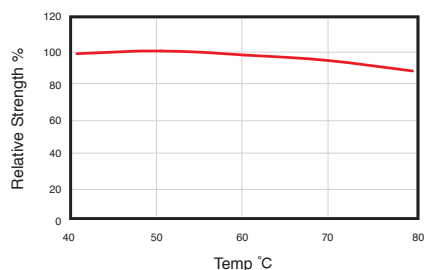

芒硝依存性 Dependency on Glauber's salt

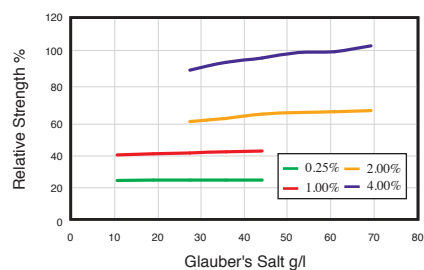

Everzol Red LF-B


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	3	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			5	
	ISO C10 D		4-5	5	3	5	5	5	3	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕		4	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.1%	>4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			1.0%	>4-5	
Water 耐水		1.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	4	
Hot Water 耐熱水		1.0%	4-5	5	5	4-5	5	5	5	Saliva (DIN) 耐唾液		1.0%	5	
Sea Water 耐海水		1.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	4-5
Post mercerizing 後絲光		1.0%	3-4		4-5						4 Hours after	4-5		
Acid hydrolysis 酸水解		1.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	1.0%	4-5
Perspiration 耐汗	Acid 酸	1.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	4	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3-4	5	Perspiration Light 耐汗日光	Acid	1.0 %	3-4	5-6
	0.3 %	4	5-6		Alkali		4	5
	1.0 %	4-5	6					
	3.0 %	4-5	6					
	6.0 %	4-5	>6					

浴比依存性 Dependency on Liquor ratio

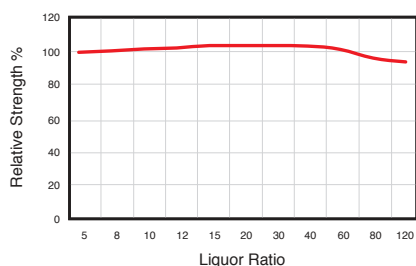

鹼依存性 Dependency on alkali

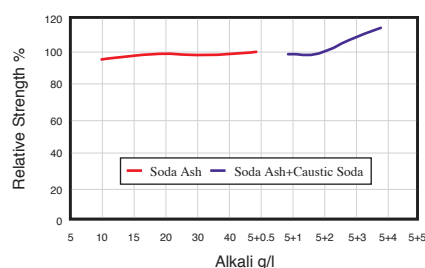


Everzol Red LF-2B


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		4
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	70
	50°C Water+50 g/l Salt	70
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	1B
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

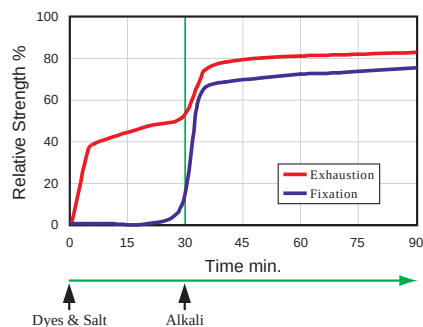

溫度依存性 Dependency on temperature

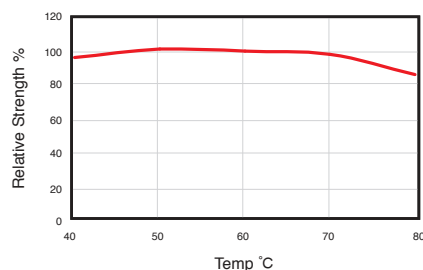

芒硝依存性 Dependency on Glauber's salt

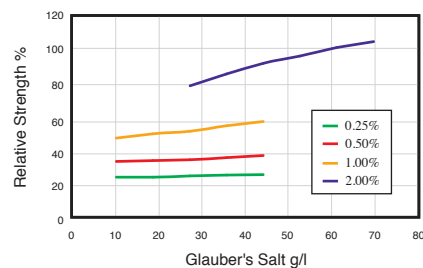

Everzol Red LF-2B


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	2-3	
	ISO C10 C		4-5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			3-4	
	ISO C10 D		4-5	5	5	5	5	5	4	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		5	5	5	5	5	5	5		Wet 濕		5	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.1%	>4-5	
	M&S C4A		4-5	5	5	5	5	5	5			1.0%	>4-5	
Water 耐水		1.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	4	
Hot Water 耐熱水		1.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		1.0%	4-5	
Sea Water 耐海水		1.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	2-3
Post mercerizing 後絲光		1.0%	3-4B		4-5							4 Hours after		4-5
Acid hydrolysis 酸水解		1.0%	5	5	5	5	5	5	5		Wet 濕	Immediately	1.0%	3
Perspiration 耐汗	Acid 酸	1.0%	5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO	
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4	5-6	Perspiration Light 耐汗日光	Acid	1.0 %	3-4	5	
	0.3 %	4	6		Alkali		4	4-5	
	1.0 %	4-5	>6						
	3.0 %	4-5	>6						
	6.0 %	*	*						

浴比依存性 Dependency on Liquor ratio

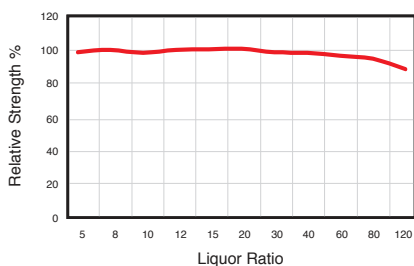

鹼依存性 Dependency on alkali

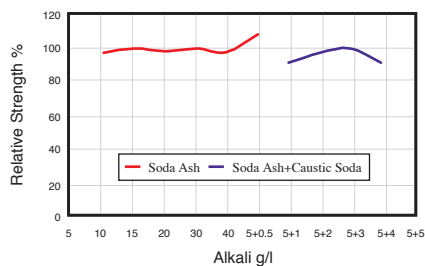


Everzol Red LF-4B


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		I
Substantivity 親和性		B
Migration 移染性		4
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	5
	Dye Liquor 染浴	5
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	2-3
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	△
	(2)	△
	(3)	△
	(4)	×
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

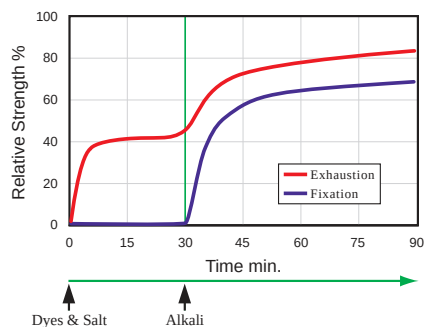

溫度依存性 Dependency on temperature

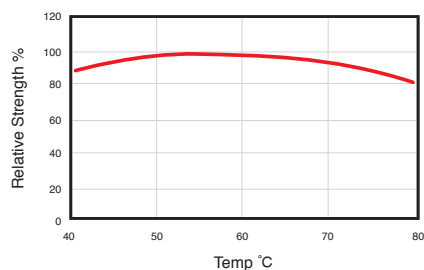

芒硝依存性 Dependency on Glauber's salt

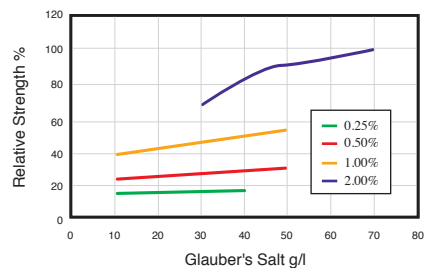

Everzol Red LF-4B


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			1.0%	3
	ISO C10 C		4-5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			5		
	ISO C10 D		4-5	5	5	5	5	4	Rubbing 耐摩擦	Dry 乾		1.0%	4-5	
	ISO C06-C1S		4-5	5	5	5	5	5		Wet 濕			3	
	ISO C06-C2S		4-5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)			0.1%	3-4	
	M&S C4A		4-5	5	5	5	5	5				1.0%	4	
Water 耐水		1.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗			1.0%	4-5
Hot Water 耐熱水		1.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液			1.0%	4-5
Sea Water 耐海水		1.0%	4-5	5	4-5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	2-3
Post mercerizing 後絲光		1.0%	3		5				4 Hours after			4-5		
Acid hydrolysis 酸水解		1.0%	4-5	5	4-5	4-5	5	5	5		Wet 濕	Immediately	1.0%	3
Perspiration 耐汗	Acid 酸	1.0%	4-5	5	4-5	4-5	5	5	4-5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	5


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3-4	5	Perspiration Light 耐汗日光	Acid	1.0 %	3-4	5-6	
	0.3 %	4	5-6		Alkali		4	4-5	
	1.0 %	4	6						
	3.0 %	4-5	>6						
	6.0 %	4-5	>6						

浴比依存性 Dependency on Liquor ratio

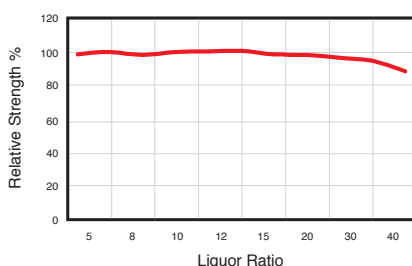

鹼依存性 Dependency on alkali

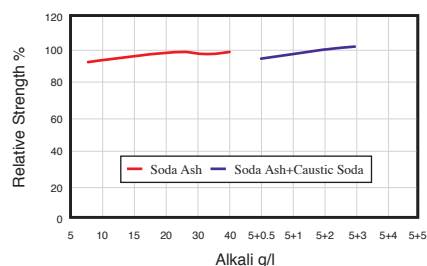


Everzol Grey LF


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		III
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	5
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	×
Discharge ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

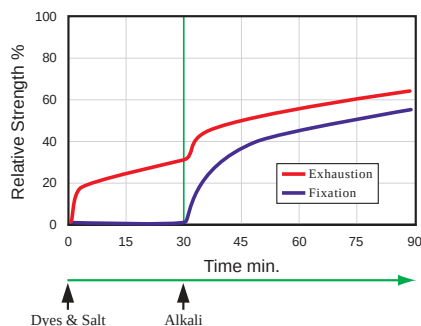

溫度依存性 Dependency on temperature

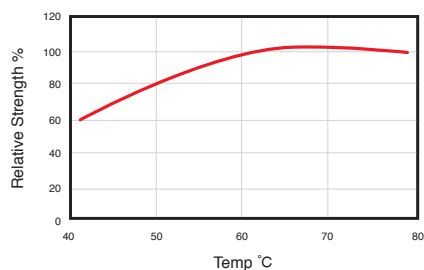

芒硝依存性 Dependency on Glauber's salt

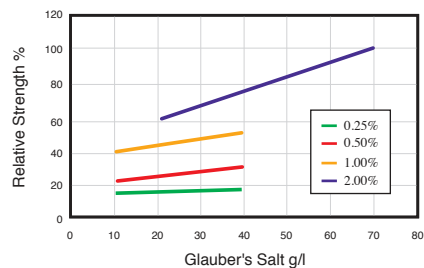

Everzol Grey LF


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛						
Fastness										Fastness					
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			1.0%	3	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白				4	
	ISO C10 D		4-5	5	5	5	5	5	5	Rubbing 耐摩擦	Dry 乾	1.0%	4-5		
	ISO C06-C1S		4-5	5	5	5	5	5	5		Wet 濕		3-4		
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)			0.1%	4-5	
	M&S C4A		4-5	5	5	5	5	5	5				1.0%	4-5	
Water 耐水		1.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗			1.0%	4-5	
Hot Water 耐熱水		1.0%	4-5	5	5	4-5	5	5	5	Saliva (DIN) 耐唾液			1.0%	4-5	
Sea Water 耐海水		1.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	3-4	
Post mercerizing 後絲光		1.0%	3-4		4-5							4 Hours after		4-5	
Acid hydrolysis 酸水解		1.0%	4-5	5	5	5	5	5	5		Wet 濕		Immediately	1.0%	3-4
Perspiration 耐汗	Acid 酸	1.0%	4-5	5	5	5	5	5	5				4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO	
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4	5	Perspiration Light 耐汗日光	Acid	1.0 %	4	5	
	0.3 %	4-5	5-6		Alkali		4-5	4	
	1.0 %	4-5	5-6						
	3.0 %	4-5	6						
	6.0 %	4-5	>6						

浴比依存性 Dependency on Liquor ratio

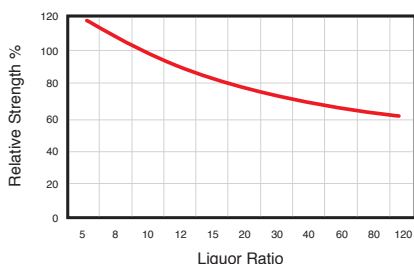

鹼依存性 Dependency on alkali

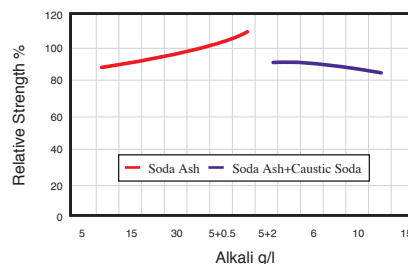


Everzol Dark Blue LF


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		2
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5G (Y)
	Cu ²⁺ 銅	4-5G (Y)
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	1
	Alkaline 鹼性	1


吸盡固著曲線 Exhaustion & Fixation

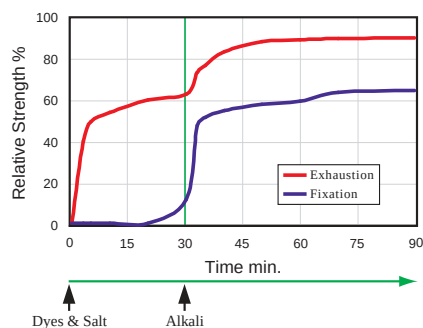

溫度依存性 Dependency on temperature

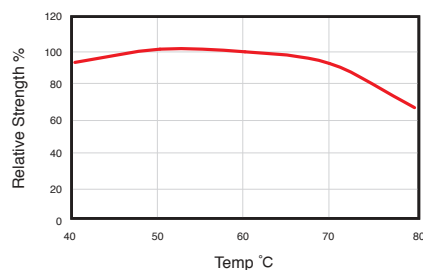

芒硝依存性 Dependency on Glauber's salt

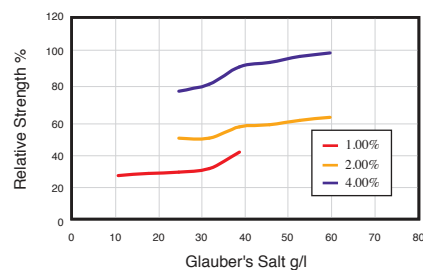

Everzol Dark Blue LF


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	1-2	
	ISO C10 C		4-5	5	4-5	5	5	5	4-5	Peroxide Bleaching雙氧水漂白			3-4	
	ISO C10 D		3	4-5	4-5	3	5	4-5	3	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	4-5		Wet 濕		3-4	
	ISO C06-C2S		4-5	4-5	4	4-5	5	4	4	M&S C9A 擬溼日光 (detergent Light)		0.1%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			1.0%	4-5	
Water 耐水		1.0%	4-5	5	5	4-5	5	5	5	Multi laundering 耐多次水洗		1.0%	3-4	
Hot Water 耐熱水		1.0%	4-5	5	3	3	4-5	5	4-5	Saliva (DIN) 耐唾液		1.0%	4-5	
Sea Water 耐海水		1.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	3-4R
Post mercerizing 後絲光		1.0%	4-5		4-5						4 Hours after	5		
Acid hydrolysis 酸水解		1.0%	4-5	5	4-5	4-5	5	5	5		Wet 濕	Immediately	1.0%	3-4R
Perspiration 耐汗	Acid 酸	1.0%	4-5	5	4-5	4-5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	3-4	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO	
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3-4	5	Perspiration Light 耐汗日光	Acid	1.0 %	2-3	5	
	0.3 %	4	5-6		Alkali		3-4	4-5	
	1.0 %	4-5	6						
	3.0 %	4-5	6						
	6.0 %	*	*						

浴比依存性 Dependency on Liquor ratio

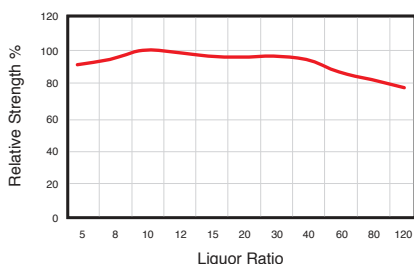

鹼依存性 Dependency on alkali

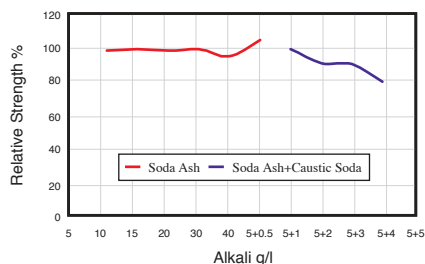


Everzol Flavine FC


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	R (B)
	TL 84 Lamp	R (Y)
Metallic ions 金屬離子	Fe ²⁺ 鐵	3-4
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	△
	(2)	△
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	1-2
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

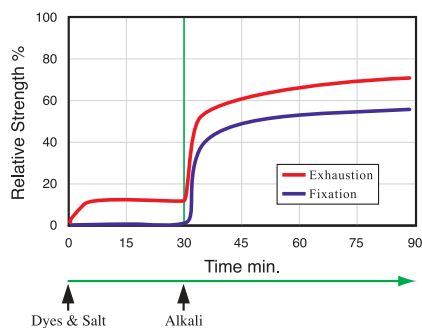

溫度依存性 Dependency on temperature

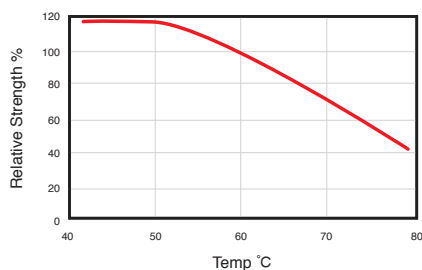

芒硝依存性 Dependency on Glauber's salt

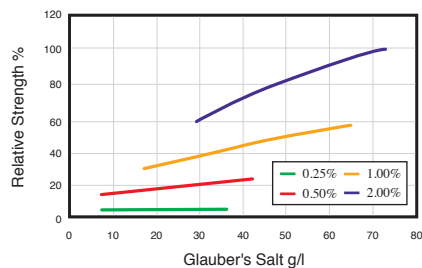

Everzol Flavine FC


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C02	3.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C03		4-5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C04		4-5	5	5	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	5	5	5	5	5		Wet 濕	4-5		
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	1	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	1	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4	
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5
Post mercerizing 後絲光		3.0%	4-5	-	4-5	-	-	-	-			4 Hours after		5
Acid hydrolysis 酸水解		3.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	4-5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4	4-5	Perspiration Light 耐汗日光	Acid	3.0 %	1-2	1	
	0.3 %	3-4	4		Alkali		1	1	
	1.0 %	3	3-4						
	3.0 %	3	3						
	6.0 %	2	2						

浴比依存性 Dependency on Liquor ratio

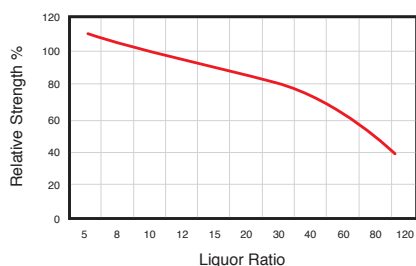

鹼依存性 Dependency on alkali

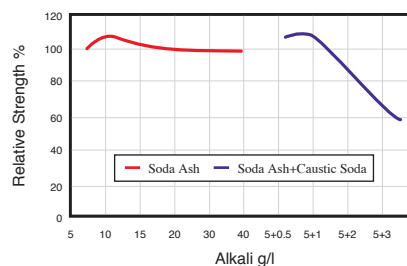


Everzol Orange FC


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4-5
	Dye Liquor 染浴	5
Color constancy 色恆性	Tungsten Lamp	Y (G)
	TL 84 Lamp	Y (G)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	2
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3-4


吸盡固著曲線 Exhaustion & Fixation

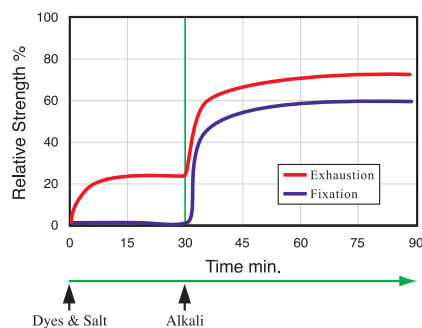

溫度依存性 Dependency on temperature

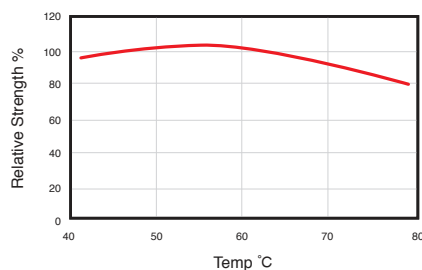

芒硝依存性 Dependency on Glauber's salt

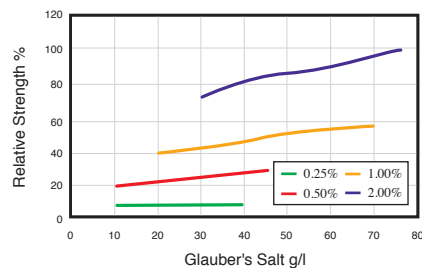

Everzol Orange FC


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			3-4	
	ISO C10 D		4-5	5	4	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		3	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	4	4	5	4	4	Multi laundering 耐多次水洗		3.0%	4	
Hot Water 耐熱水		3.0%	4-5	5	4-5	4-5	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	4-5	5	4-5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3-4
Post mercerizing 後絲光		3.0%	4	-	3-4	-	-	-	-			4 Hours after		4-5
Acid hydrolysis 酸水解		3.0%	4-5	5	3-4	3-4	5	5	4-5		Wet 濕	Immediately	3.0%	3-4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	4-5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3	4-5	Perspiration Light 耐汗日光	Acid	3.0 %	4	5-6
	0.3 %	3-4	4-5		Alkali		4	5-6
	1.0 %	4	5					
	3.0 %	4-5	5-6					
	6.0 %	4-5	6					

浴比依存性 Dependency on Liquor ratio

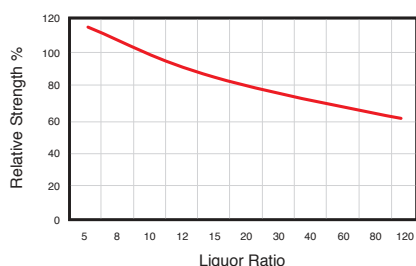

鹼依存性 Dependency on alkali

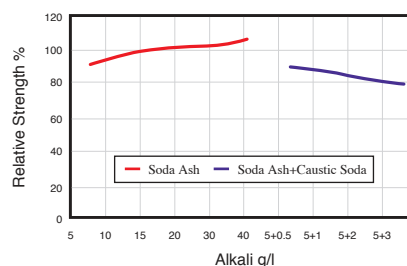


Everzol Scarlet FC


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	90
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4-5
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	Y (G)
	TL 84 Lamp	Y (G)
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	3
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	○
	(3)	○
	(4)	△
Discharge ability 拔染性	Neutral 中性	2-3
	Alkaline 鹼性	2-3


吸盡固著曲線 Exhaustion & Fixation

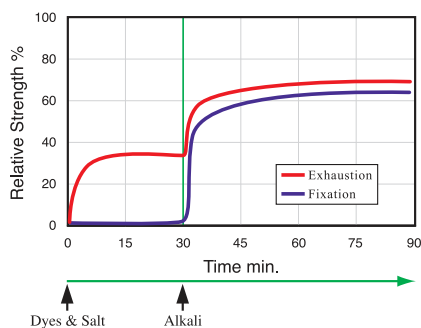

溫度依存性 Dependency on temperature

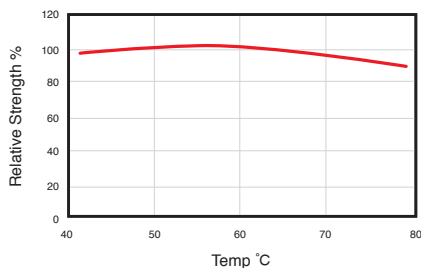

芒硝依存性 Dependency on Glauber's salt

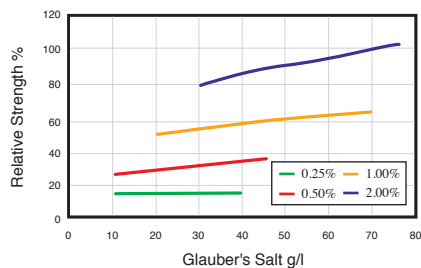

Everzol Scarlet FC


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	4-5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4	
	ISO C10 C		4-5	5	4-5	5	5	4-5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4	5	4	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	4	5	5	4-5	5		Wet 濕	2-3		
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	5	4-5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	2-3
Post mercerizing 後絲光		3.0%	4	-	3	-	-	-	-			4 Hours after		4-5
Acid hydrolysis 酸水解		3.0%	4-5	5	3-4	4-5	5	4-5	4-5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	4-5	4-5	4-5	4-5	4	4	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	3-4	Perspiration Light 耐汗日光	Acid	3.0 %	4	5	
	0.3 %	2-3	4		Alkali		4	4-5	
	1.0 %	3	4-5						
	3.0 %	3-4	5						
	6.0 %	4	5-6						

浴比依存性 Dependency on Liquor ratio

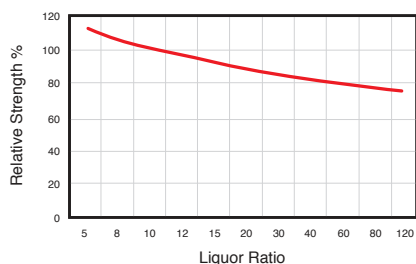

鹼依存性 Dependency on alkali

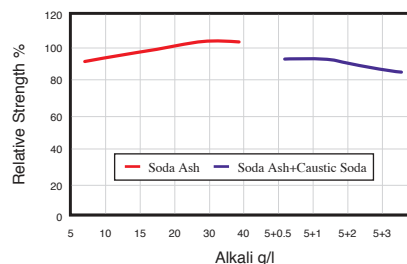


Everzol Red FC


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		3-4
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	20
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4-5
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	Y (G)
	TL 84 Lamp	G (Y)
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	1-2
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	○
	(3)	○
	(4)	△
Discharge ability 拔染性	Neutral 中性	2-3
	Alkaline 鹼性	2-3


吸盡固著曲線 Exhaustion & Fixation

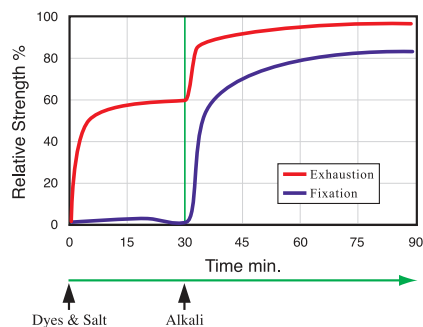

溫度依存性 Dependency on temperature

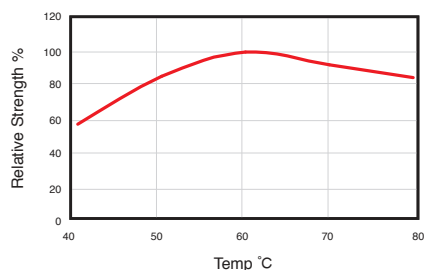

芒硝依存性 Dependency on Glauber's salt

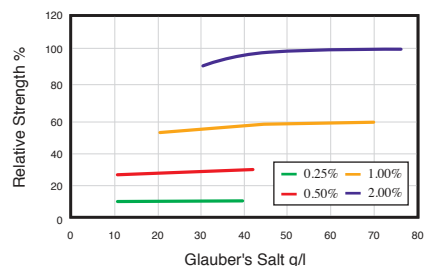

Everzol Red FC


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	4	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		3	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3
Post mercerizing 後絲光		3.0%	3	-	3-4	-	-	-	-		4 Hours after	4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	4-5	5	5	5		Wet 濕	Immediately	3.0%	3
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4	5	5	5	5		4 Hours after			4-5
	Alkali 鹼		4-5	5	4	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3	4	Perspiration Light 耐汗日光	Acid	3.0 %	3-4	4-5	
	0.3 %	3-4	4-5		Alkali		4	3-4	
	1.0 %	4	5						
	3.0 %	4-5	5-6						
	6.0 %	4-5	6						

浴比依存性 Dependency on Liquor ratio

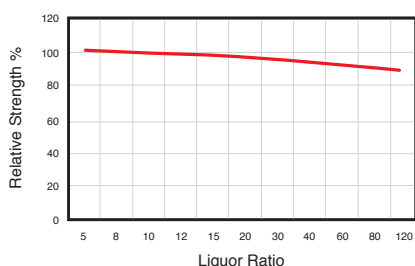

鹼依存性 Dependency on alkali

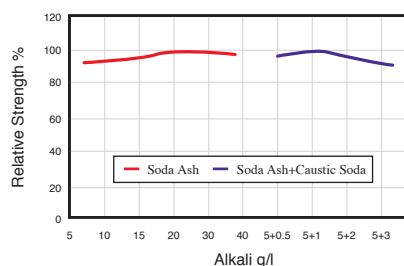


Everzol Blue FC


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	3-4
Color constancy 色恆性	Tungsten Lamp	G (B)
	TL 84 Lamp	B (G)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	×
	(4)	×
Discharge ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	1


吸盡固著曲線 Exhaustion & Fixation

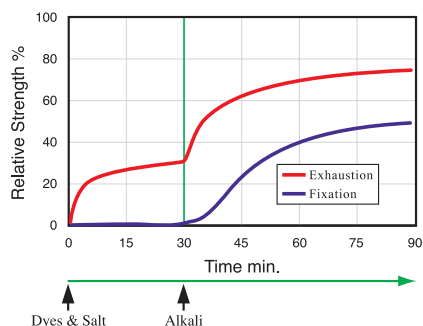

溫度依存性 Dependency on temperature

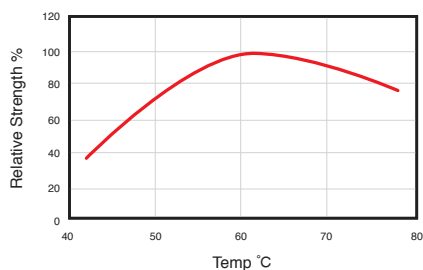

芒硝依存性 Dependency on Glauber's salt

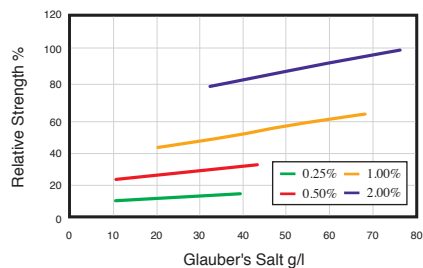

Everzol Blue FC


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C02	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	1-2	
	ISO C03		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C04		4-5	5	4-5	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		3-4	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	4-5	5	5	5	Multi laundering 耐多次水洗		3.0%	4		
Hot Water 耐熱水		3.0%	4-5	5	5	2-3	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	3	-	5	-	-	-	-			4 Hours after		4-5
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	4	5	5	5		Wet 濕	Immediately	3.0%	3-4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	1-2		


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4-5	>6	Perspiration Light 耐汗日光	Acid	3.0 %	3-4	4-5	
	0.3 %	>4-5	>6		Alkali		4	4	
	1.0 %	>4-5	>6						
	3.0 %	>4-5	>6						
	6.0 %	>4-5	>6						

浴比依存性 Dependency on Liquor ratio

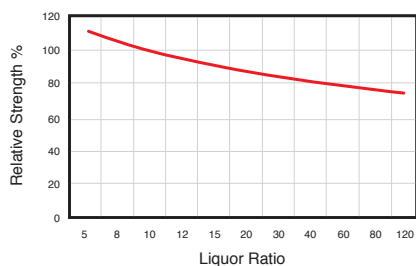

鹼依存性 Dependency on alkali

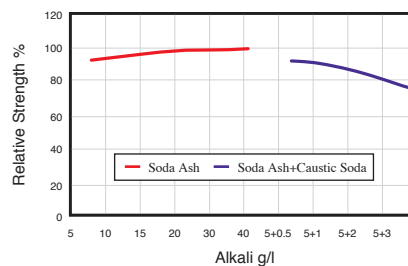


Everzol Yellow CS


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		3
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	75
	50°C Water+50 g/l Salt	75
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	G (Y)
	TL 84 Lamp	G (Y)
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	×
	(4)	×
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	2


吸盡固著曲線 Exhaustion & Fixation

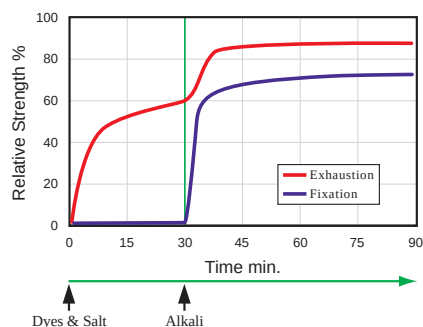

溫度依存性 Dependency on temperature

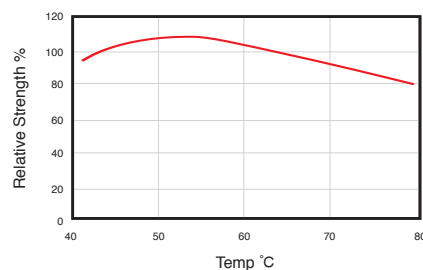

芒硝依存性 Dependency on Glauber's salt

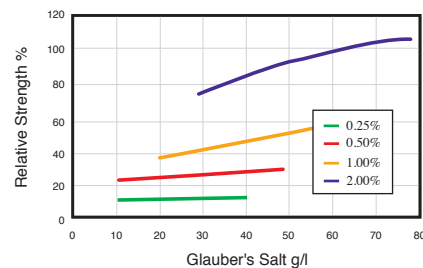

Everzol Yellow CS


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	4-5	
	ISO C10 C		4-5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	5	5	5	5	4	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		4-5	5	5	5	5	5	5		Wet 濕		4-5	
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.1%	4-5	
	M&S C4A		4-5	5	5	5	5	5	5			1.0%	5	
Water 耐水		1.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	4-5	
Hot Water 耐熱水		1.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		1.0%	5	
Sea Water 耐海水		1.0%	5	5	5	5	5	5	5	Hot-Pressing 耐熱壓	Dry 乾	Immediately	1.0%	4
Post mercerizing 後絲光		1.0%	4		4-5							4 Hours after		5
Acid hydrolysis 酸水解		1.0%	4-5	5	4-5	4	5	5	4-5		Wet 濕	Immediately	1.0%	4
Perspiration 耐汗	Acid 酸	1.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	≧4.5	6	Perspiration Light 耐汗日光	Acid	1.0 %	5	≧6
	0.3 %	≧4.5	≧6		Alkali		5	≧6
	1.0 %	≧4.5	≧6					
	3.0 %	≧4.5	≧6					
	6.0 %	≧4.5	≧6					

浴比依存性 Dependency on Liquor ratio

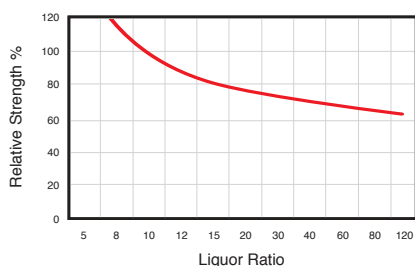

鹼依存性 Dependency on alkali

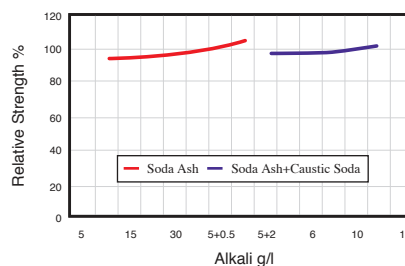


Everzol Orange CS


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		3-4
Washing off 洗淨性		2-3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2
	Dye Liquor 染浴	3
Color constancy 色恆性	Tungsten Lamp	Y (R)
	TL 84 Lamp	Y (G)
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	×
	(4)	×
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

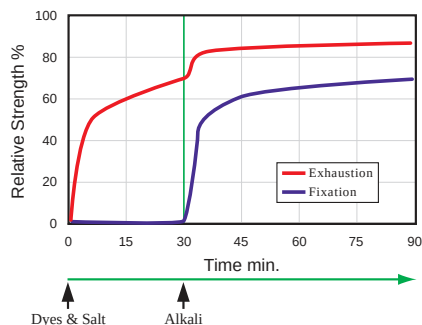

溫度依存性 Dependency on temperature

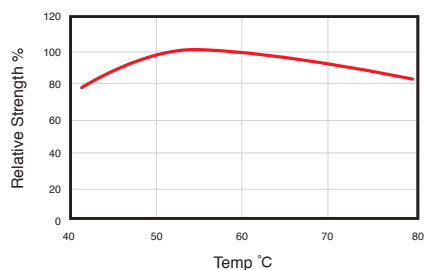

芒硝依存性 Dependency on Glauber's salt

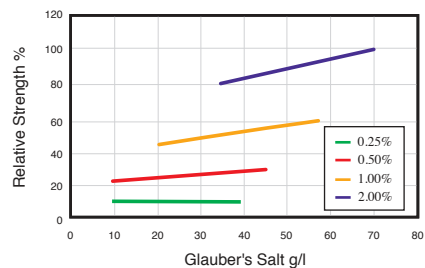


Everzol Red Brown CS


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		3
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp	R (Y)
	TL 84 Lamp	G (B)
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3
	Quaternary ammonium salt 四級銨鹽	4
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

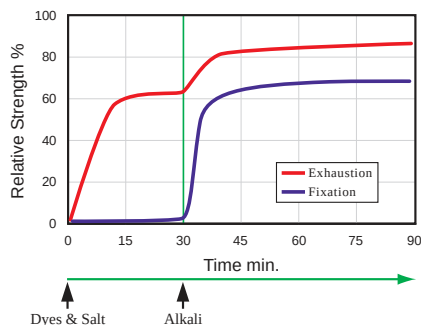

溫度依存性 Dependency on temperature

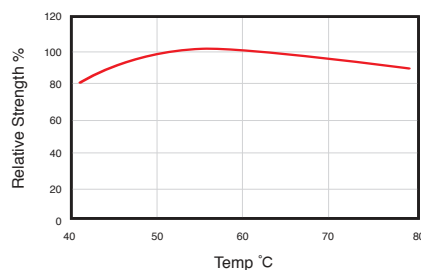

芒硝依存性 Dependency on Glauber's salt

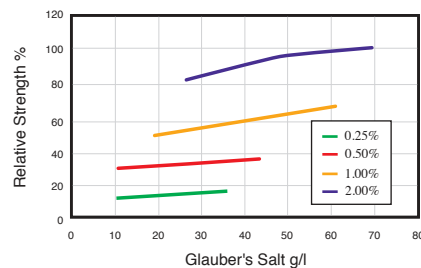

Everzol Red Brown CS


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	4	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	4-5	5	5	5	4	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕		4	
	ISO C06-C2S		4-5	5	4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.1%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			1.0%	5	
Water 耐水		1.0%	4-5	5	4	4-5	5	4-5	5	Multi laundering 耐多次水洗		1.0%	4	
Hot Water 耐熱水		1.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		1.0%	5	
Sea Water 耐海水		1.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	4
Post mercerizing 後絲光		1.0%	4		4				4 Hours after			5		
Acid hydrolysis 酸水解		1.0%	4-5	5	3-4	3	4-5	5	4		Wet 濕	Immediately	1.0%	4
Perspiration 耐汗	Acid 酸	1.0%	4-5	5	4-5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼			4-5	5	4-5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	4-5


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4-5	5-6	Perspiration Light 耐汗日光	Acid	1.0 %	3	4-5
	0.3 %	≧4-5	≧6		Alkali		4	4
	1.0 %	≧4-5	≧6					
	3.0 %	≧4-5	≧6					
	6.0 %	≧4-5	≧6					

浴比依存性 Dependency on Liquor ratio

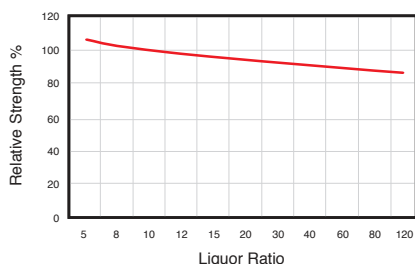

鹼依存性 Dependency on alkali

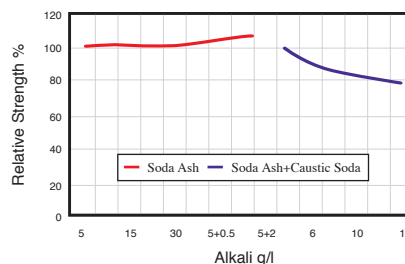


Everzol Olive CS


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		3
Washing off 洗淨性		2-3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	G
	TL 84 Lamp	G (B)
Metallic ions 金屬離子	Fe ²⁺ 鐵	5
	Cu ²⁺ 銅	5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	△
	(2)	△
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3-4


吸盡固著曲線 Exhaustion & Fixation

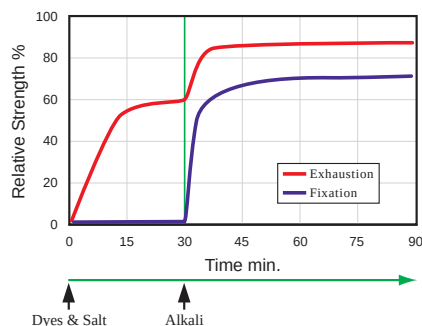

溫度依存性 Dependency on temperature

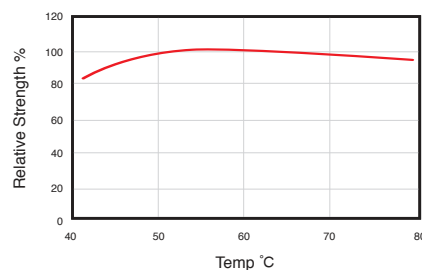

芒硝依存性 Dependency on Glauber's salt

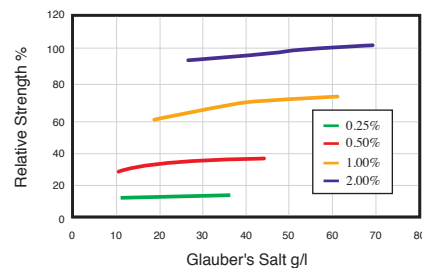

Everzol Olive CS


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	4-5	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			3	
	ISO C10 D		4-5	5	3-4	5	5	5	5	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕		3	
	ISO C06-C2S		4-5	5	4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.1%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			1.0%	4-5	
Water 耐水		1.0%	4-5	5	4-5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	4-5	
Hot Water 耐熱水		1.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		1.0%	5	
Sea Water 耐海水		1.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	3-4
Post mercerizing 後絲光		1.0%	3-4		4						4 Hours after	4-5		
Acid hydrolysis 酸水解		1.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	1.0%	3-4
Perspiration 耐汗	Acid 酸	1.0%	4-5	5	4-5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4	5-6	Perspiration Light 耐汗日光	Acid	1.0 %	2	4
	0.3 %	4-5	6		Alkali		3-4	4
	1.0 %	>4-5	>6					
	3.0 %	>4-5	>6					
	6.0 %	>4-5	>6					

浴比依存性 Dependency on Liquor ratio

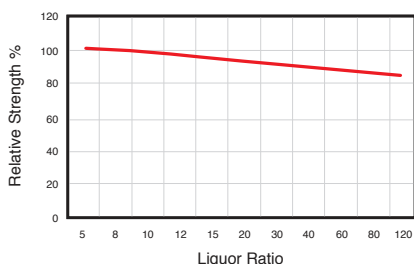

鹼依存性 Dependency on alkali

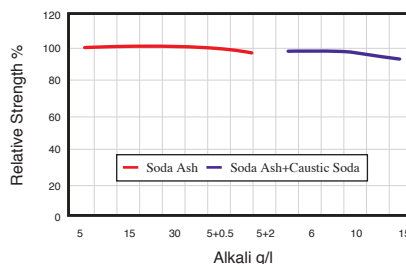


Everzol Grey CS


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		3
Washing off 洗淨性		2-3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	1
Color constancy 色恆性	Tungsten Lamp	R (Y)
	TL 84 Lamp	B
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

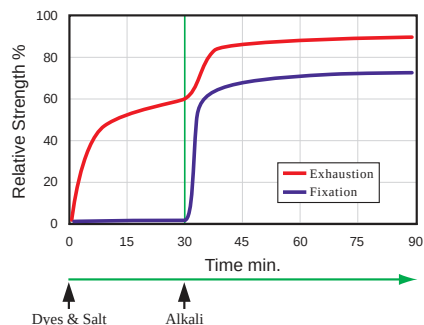

溫度依存性 Dependency on temperature

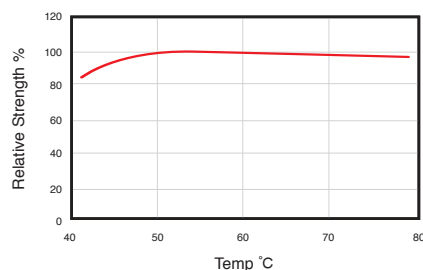

芒硝依存性 Dependency on Glauber's salt

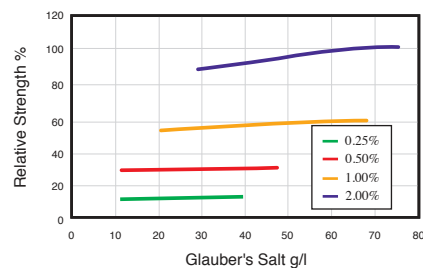

Everzol Grey CS


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	1.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		1.0%	2-3	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			3	
	ISO C10 D		4-5	5	3	5	5	5	5	Rubbing 耐摩擦	Dry 乾	1.0%	5	
	ISO C06-C1S		4-5	5	3-4	5	5	5	5		Wet 濕		4	
	ISO C06-C2S		4-5	5	4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.1%	4-5	
	M&S C4A		4-5	5	4	5	5	5	5			1.0%	4-5	
Water 耐水		1.0%	4-5	5	4-5	5	5	5	5	Multi laundering 耐多次水洗		1.0%	4	
Hot Water 耐熱水		1.0%	4-5	5	5	4-5	5	5	5	Saliva (DIN) 耐唾液		1.0%	5	
Sea Water 耐海水		1.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	1.0%	4
Post mercerizing 後絲光		1.0%	3		4-5							4 Hours after		4-5
Acid hydrolysis 酸水解		1.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	1.0%	4
Perspiration 耐汗	Acid 酸	1.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		1.0%	4	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4	5-6	Perspiration Light 耐汗日光	Acid	1.0 %	3-4	4-5	
	0.3 %	4-5	6		Alkali		4	3-4	
	1.0 %	4-5	>6						
	3.0 %	4-5	>6						
	6.0 %	4-5	>6						

浴比依存性 Dependency on Liquor ratio

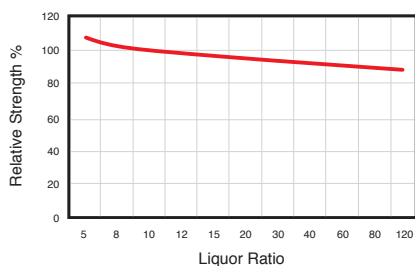

鹼依存性 Dependency on alkali

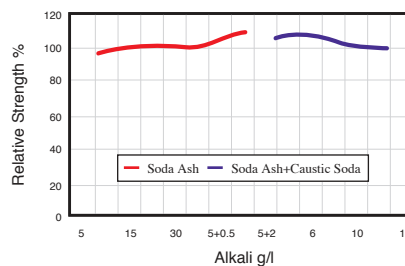


Everzol Yellow MX


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		3
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	70
	50°C Water+50g/l Salt	30 (60°C→100)
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	Y (R)
	TL 84 lamp	Y (G)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamide 聚乙醯胺	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	×
	(4)	×
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	3-4


吸盡固著曲線 Fixation & Fixation

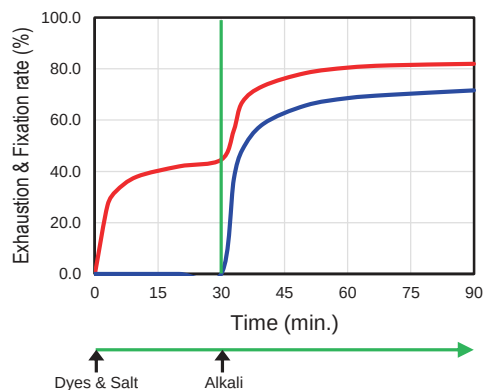

溫度依存性 Dependency on Temperature

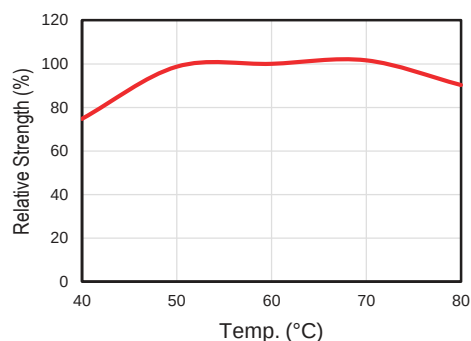

芒硝依存性 Dependency on Glauber's salt

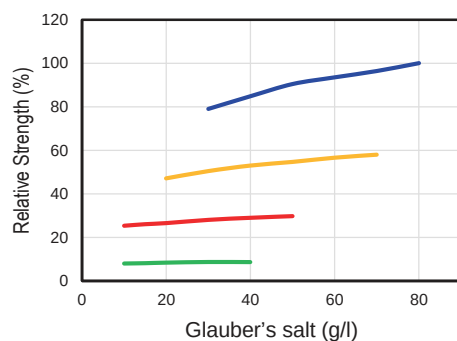

Everzol Yellow MX


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color Change 變褪色	Staing 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	5	5	5	5	5	Chlorinated Water 耐氯水 (20ppm)			3.0%	2-3
	ISO C10 C		4-5	5	5	5	5	5	5	Peroxide Bleaching 雙氧水漂白			3.0%	4-5
	ISO C10 D		4-5	5	4-5	5	5	4-5	4-5	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕	3.0%	4-5	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (Detergent Light)			0.3%	4-5
	M&S C4A		4-5	5	5	5	5	5	5				3.0%	4-5
Water 耐水		3.0%	4-5	5	4-5	4-5	5	5	5	Multi laundering 耐多次水洗			3.0%	4-5
Hot Water 耐熱水		3.0%	4-5	5	4-5	4-5	5	5	5	Saliva (DIN) 耐唾液			3.0%	4-5
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3-4
Post mercerizing 後絲光		3.0%	2-3	-	4-5	-	-	-	-			4 Hours after	3.0%	4-5
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	4	4-5	5	4		Wet 溼	Immediately	3.0%	3-4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	5	5	5	5			4 Hours after	3.0%	4-5
Alkali 鹼		3.0%	4-5	5	4-5	5	5	5	5	Nitrogen Oxides 氣體變褪色			3.0%	4-5


Light Fastness 日光堅牢度

Evaluation	Dyeing depth	Color Change	Grade	Evaluation		Dyeing depth	Color Change	Grade	
	染色濃度	20AFU	ISO			染色濃度	20AFU	ISO	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1%	4	5	Perspiration Light 耐汗日光	Acid	3.0%	4	6	
	0.3%	4-5	5-6		Alkali		4	5	
	1.0%	4-5	6						
	3.0%	4-5	>6						
	6.0%	5	>6						

浴比依存性 Dependency on Liquor ratio

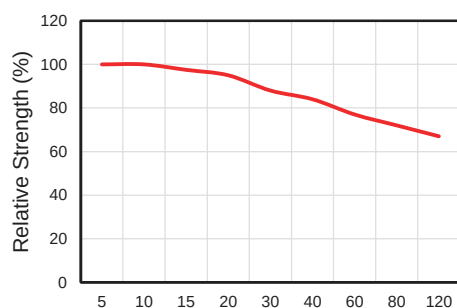

鹼依存性 Dependency on Alkali

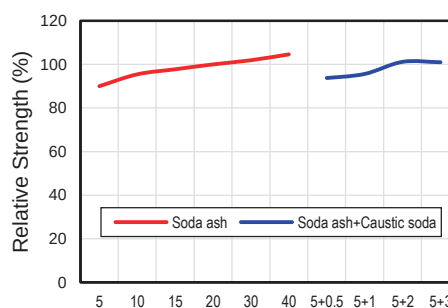


Everzol Red MX


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		2
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	Y (R)
	TL 84 lamp	G (Y)
Metallic ions 金屬離子	Fe ²⁺ 鐵	3-4
	Cu ²⁺ 銅	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4
Shade change after fixing treatment 固色後變色性	Polyamide 聚乙醯胺	3-4
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	○
	(3)	○
	(4)	△
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	3-4


吸盡固著曲線 Fixation & Fixation

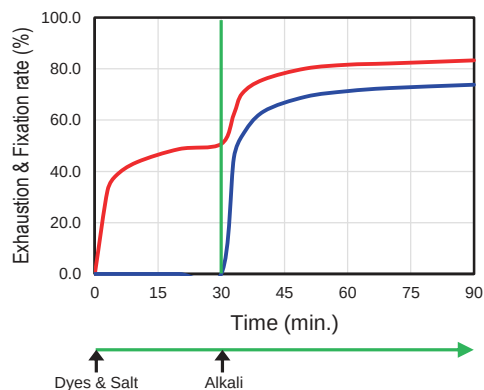

溫度依存性 Dependency on Temperature

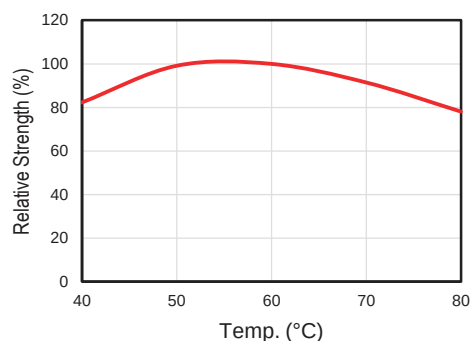

芒硝依存性 Dependency on Glauber's salt

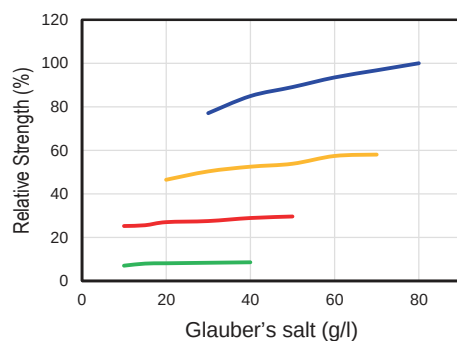

Everzol Red MX


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color Change 變褪色	Staing 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	5	5	5	5	5	Chlorinated Water 耐氯水 (20ppm)			3.0%	2
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching 雙氧水漂白			3.0%	4-5
	ISO C10 D		4-5	5	4-5	5	5	5	5	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕	3.0%	4-5	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (Detergent Light)			0.3%	4-5
	M&S C4A		4-5	5	5	5	5	5	5				3.0%	4-5
Water 耐水		3.0%	4-5	5	4-5	4-5	5	5	5	Multi laundering 耐多次水洗			3.0%	4-5
Hot Water 耐熱水		3.0%	4-5	5	4-5	5	5	5	5	Saliva (DIN) 耐唾液			3.0%	5
Sea Water 耐海水		3.0%	4-5	5	4-5	5	5	5	5	Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3
Post mercerizing 後絲光		3.0%	2	-	4-5	-	-	-	-			4 Hours after	3.0%	4-5
Acid hydrolysis 酸水解		3.0%	4-5	5	3	2-3	4-5	4-5	3-4		Wet 溼	Immediately	3.0%	2-3
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	5	5	5	5			4 Hours after	3.0%	4-5
	Alkali 鹼	3.0%	4-5	5	4-5	5	5	5	5	Nitrogen Oxides 氣體變褪色			3.0%	4-5


Light Fastness 日光堅牢度

Evaluation	Dyeing depth	Color Change	Grade	Evaluation		Dyeing depth	Color Change	Grade
	染色濃度	20AFU	ISO			染色濃度	20AFU	ISO
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1%	4	4-5	Perspiration Light 耐汗日光	Acid	3.0%	4	5
	0.3%	4	5		Alkali		4	5
	1.0%	4-5	5					
	3.0%	4-5	5-6					
	6.0%	4-5	6					

浴比依存性 Dependency on Liquor ratio

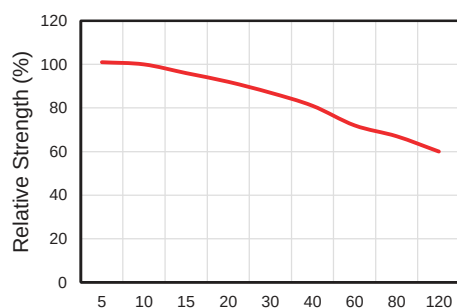

鹼依存性 Dependency on Alkali

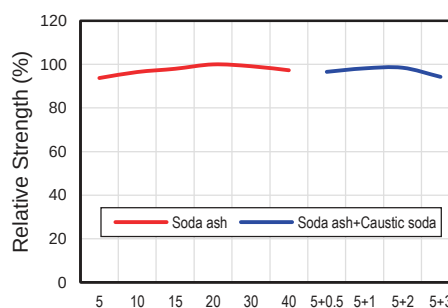


Everzol Navy MX


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		2
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	1-2
Color constancy 色恆性	Tungsten Lamp	(B)
	TL 84 lamp	(B)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	2-3
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamide 聚乙醯胺	4-5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	○
	(3)	○
	(4)	×
Discharge ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	3-4


吸盡固著曲線 Fixation & Fixation

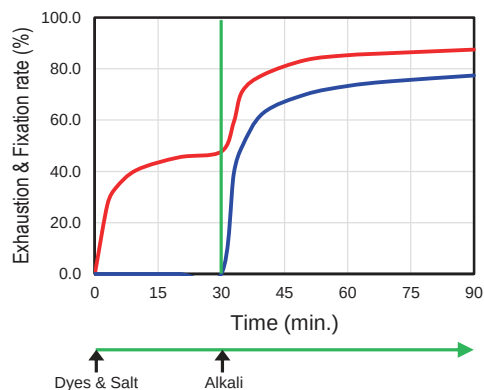

溫度依存性 Dependency on Temperature

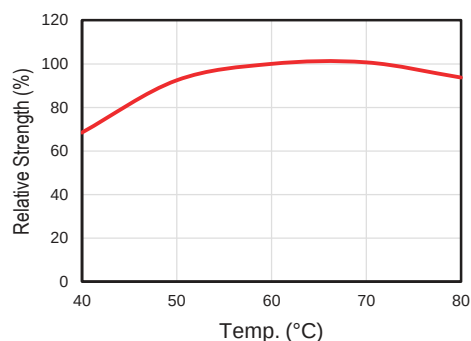

芒硝依存性 Dependency on Glauber's salt

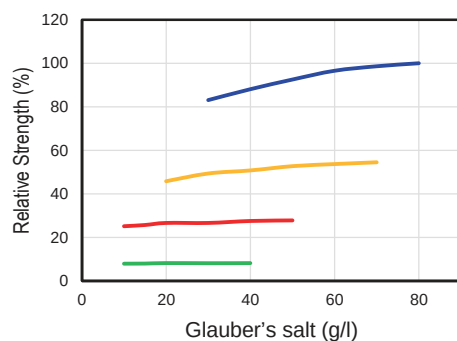

Everzol Navy MX


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color Change 變褪色	Staing 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water 耐氯水 (20ppm)			3.0%	2
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching 雙氧水漂白			3.0%	3-4
	ISO C10 D		4-5	5	3	5	5	5	3	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕	3.0%	4-5	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬渥日光 (Detergent Light)			0.3%	4
	M&S C4A		4-5	5	4-5	5	5	5	5				3.0%	4
Water 耐水		3.0%	4-5	5	4-5	5	5	5	5	Multi laundering 耐多次水洗			3.0%	4-5
Hot Water 耐熱水		3.0%	4-5	5	4-5	5	5	5	5	Saliva (DIN) 耐唾液			3.0%	4-5
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	2-3
Post mercerizing 後絲光		3.0%	2-3	-	4-5	-	-	-	-			4 Hours after	3.0%	4-5
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	4-5	5	5	5		Wet 溼	Immediately	3.0%	2-3
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	4-5	5	5	5			4 Hours after	3.0%	4-5
	Alkali 鹼	3.0%	4-5	5	4-5	4-5	5	5	5	Nitrogen Oxides 氣體變褪色			3.0%	4-5


Light Fastness 日光堅牢度

Evaluation	Dyeing depth	Color Change	Grade	Evaluation		Dyeing depth	Color Change	Grade
	染色濃度	20AFU	ISO			Blue Scale	染色濃度	20AFU
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1%	4	3-4	Perspiration Light 耐汗日光	Acid	3.0%	3	4
	0.3%	4	4		Alkali		3-4	4
	1.0%	4-5	5					
	3.0%	4-5	6					
	6.0%	5	6					

浴比依存性 Dependency on Liquor ratio

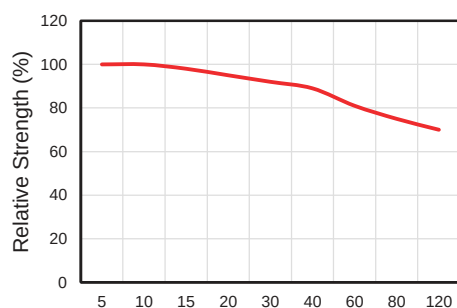

鹼依存性 Dependency on Alkali

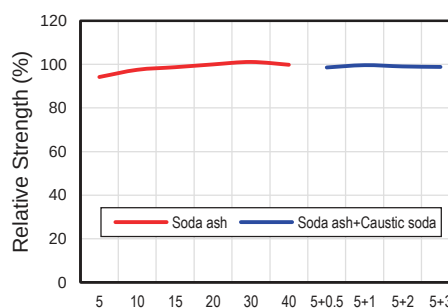


Everzol Yellow ED-2G


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		4-5
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3R
	Dye Liquor 染浴	3-4R
Color constancy 色恆性	Tungsten Lamp	G
	TL 84 Lamp	G
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	2-3
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	○
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

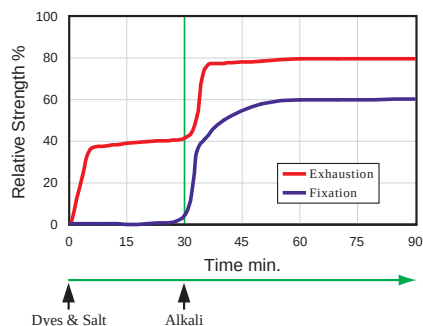

溫度依存性 Dependency on temperature

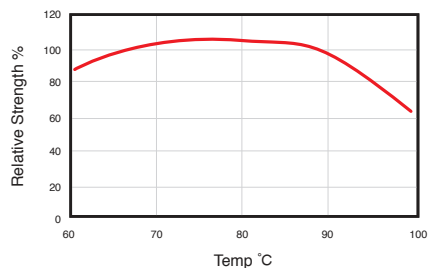

芒硝依存性 Dependency on Glauber's salt

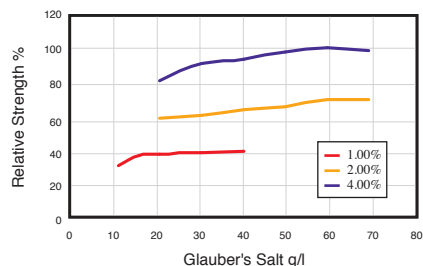

Everzol Yellow ED-2G


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	3	
	ISO C10 C		5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			2-3	
	ISO C10 D		5	5	4	5	5	5	3-4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		3-4	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	3	
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	4-5	5	5	5	5	Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	5
Post mercerizing 後絲光		3.0%	4-5		4-5				4 Hours after		5			
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	3-4	5	5	3-4		Wet 濕	Immediately	3.0%	5
Perspiration 耐汗	Acid 酸	3.0%	5	5	5	5	5	5	5		4 Hours after			5
	Alkali 鹼		5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	*	*	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	5-6	
	0.3 %	4	5		Alkali		4	3-4	
	1.0 %	4-5	6						
	3.0 %	4-5	>6						
	6.0 %	4-5	>6						

浴比依存性 Dependency on Liquor ratio

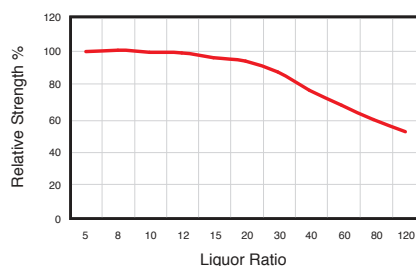

鹼依存性 Dependency on alkali

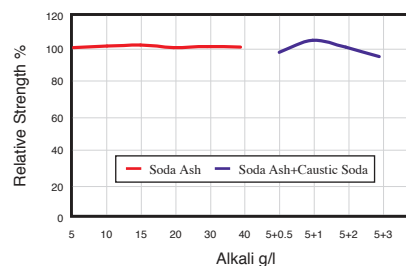


Everzol Yellow ED-R


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		2-3
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	75
	50°C Water+50 g/l Salt	75
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4
	Dye Liquor 染浴	4
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	2-3


吸盡固著曲線 Exhaustion & Fixation

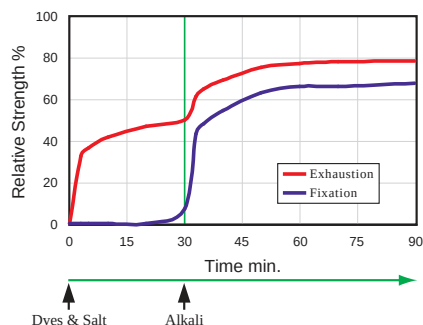

溫度依存性 Dependency on temperature

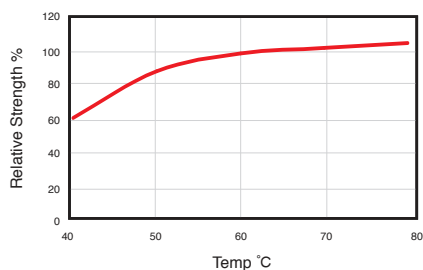

芒硝依存性 Dependency on Glauber's salt

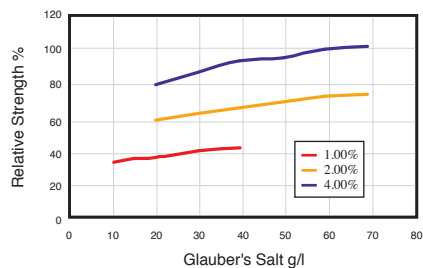

Everzol Yellow ED-R


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	2-3	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	4	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		3-4	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4	5	4-5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	5
Post mercerizing 後絲光		3.0%	4		4-5				4 Hours after			5		
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	4	5	5	4-5		Wet 濕	Immediately	3.0%	4-5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	5	5	5	5			4 Hours after		5
	Alkali 鹼		4-5	5	4-5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	*	*	Perspiration Light 耐汗日光	Acid	3.0 %	4	5-6
	0.3 %	4-5	5-6		Alkali		4	5
	1.0 %	4-5	>6					
	3.0 %	4-5	>6					
	6.0 %	4-5	>6					

浴比依存性 Dependency on Liquor ratio

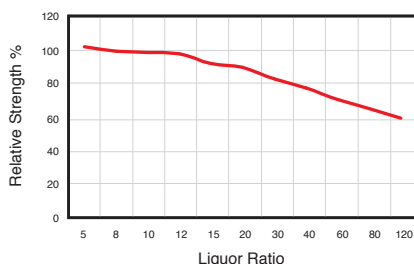

鹼依存性 Dependency on alkali

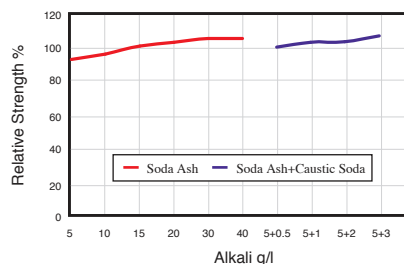


Everzol Yellow ED


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		2
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4
	Dye Liquor 染浴	4
Color constancy 色恆性	Tungsten Lamp	G
	TL 84 Lamp	G
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

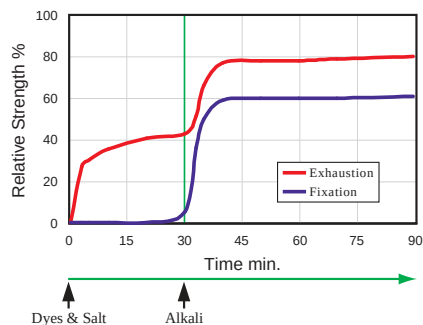

溫度依存性 Dependency on temperature

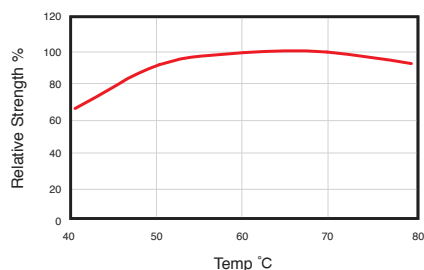

芒硝依存性 Dependency on Glauber's salt

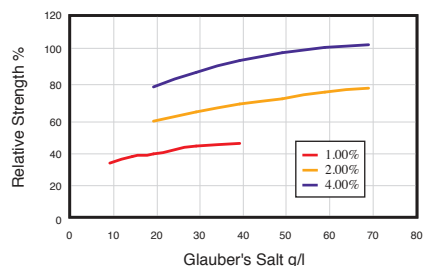

Everzol Yellow ED


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	2	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		4-5	5	4	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕		3-4	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	4-5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	5
Post mercerizing 後絲光		3.0%	3-4		4-5				4 Hours after			5		
Acid hydrolysis 酸水解		3.0%	4	5	4-5	4	5	5	4		Wet 濕	Immediately	3.0%	5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4	5	5	5	5			4 Hours after		5
	Alkali 鹼		4-5	5	4	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
	0.1 %	*	*	Perspiration Light 耐汗日光	Acid Alkali	3.0 %	4 4	5-6 5
Artificial Light (Xenon-Arc Lamp) 耐日光	0.3 %	4	5					
	1.0 %	4-5	6					
	3.0 %	4-5	>6					
	6.0 %	4-5	>6					

浴比依存性 Dependency on Liquor ratio

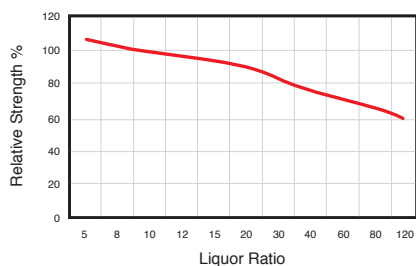

鹼依存性 Dependency on alkali

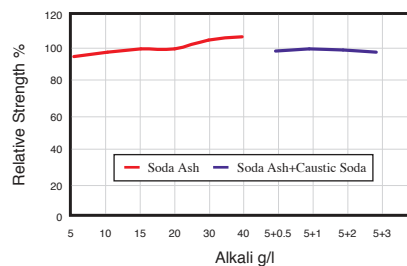


Everzol Yellow ED-S


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4G
	Dye Liquor 染浴	4G
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	2-3G
Resin finishing 樹脂加工	Melamine 三聚氰胺	2-3
	Glyoxal 乙二醛	2-3
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

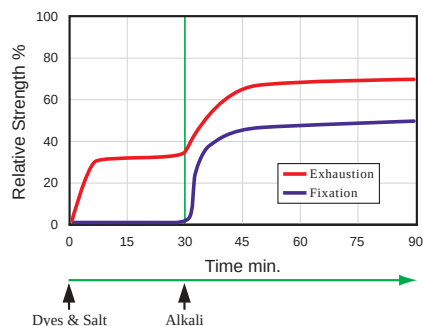

溫度依存性 Dependency on temperature

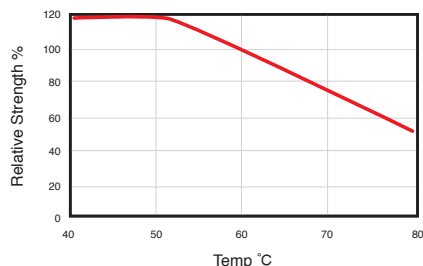

芒硝依存性 Dependency on Glauber's salt

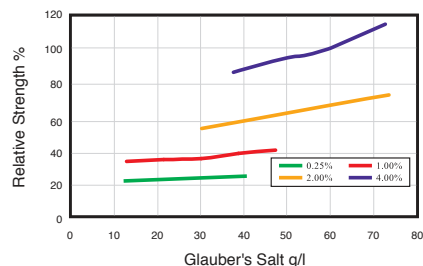

Everzol Yellow ED-S


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	5	5	5	4-5	5	Chlorinated Water耐氯水(20ppm)		3.0%	3	
	ISO C10 C		4-5	5	5	5	5	4-5	4-5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		4-5	5	4	4-5	5	5	2	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	5	5	5	4-5	5		Wet 濕	3-4		
	ISO C06-C2S		4-5	5	5	5	5	4-5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	5	5	4-5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	3-4		2				4 Hours after			4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after	4-5	
	Alkali 鹼	3.0%	4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	2	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
	0.1 %	3	4-5	Perspiration Light 耐汗日光	Acid Alkali	3.0 %	3-4 4	5-6 5
Artificial Light (Xenon-Arc Lamp) 耐日光	0.3 %	3	5					
	1.0 %	3-4	5-6					
	3.0 %	4	6					
	6.0 %	4	6					

浴比依存性 Dependency on Liquor ratio

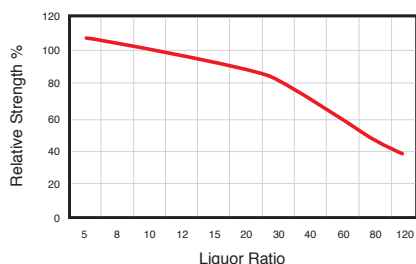

鹼依存性 Dependency on alkali

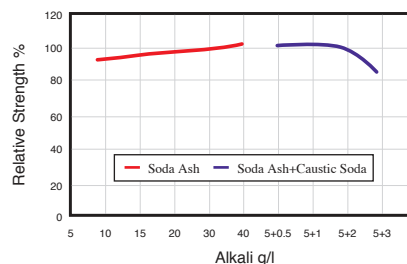


Everzol Orange ED-N


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		4
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	2-3
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	3-4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	△
	(2)	△
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	4-5
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

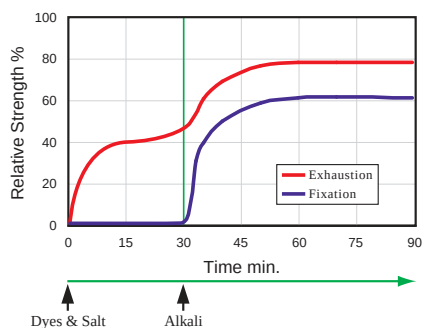

溫度依存性 Dependency on temperature

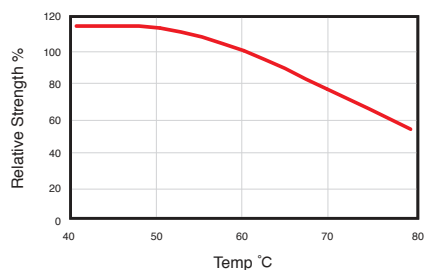

芒硝依存性 Dependency on Glauber's salt

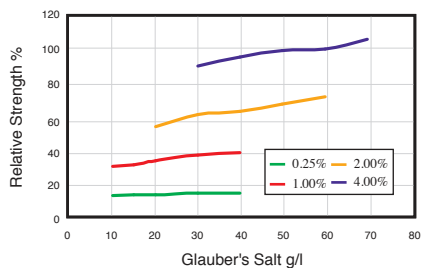

Everzol Orange ED-N


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	2-3	
	ISO C10 C		4-5	5	4	5	5	5	5	Peroxide Bleaching雙氧水漂白			3	
	ISO C10 D		4	5	3-4	4-5	5	5	2-3	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕	2-3		
	ISO C06-C2S		4-5	5	4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4	
Hot Water 耐熱水		3.0%	4-5	5	5	3	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	3-4R		3-4				4 Hours after			5		
Acid hydrolysis 酸水解		3.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		5
	Alkali 鹼		4-5	5	4-5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	*	*	Perspiration Light 耐汗日光	Acid	3.0 %	4-5	6
	0.3 %	4	5		Alkali		4-5	6
	1.0 %	4-5	5-6					
	3.0 %	4-5	6					
	6.0 %	4-5	6					

浴比依存性 Dependency on Liquor ratio

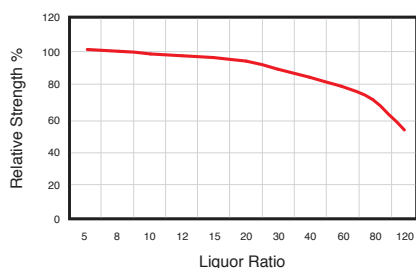

鹼依存性 Dependency on alkali

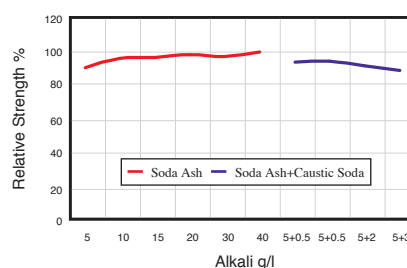


Everzol Orange ED-2R


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		1-2
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	30
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	4
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	2-3
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	2


吸盡固著曲線 Exhaustion & Fixation

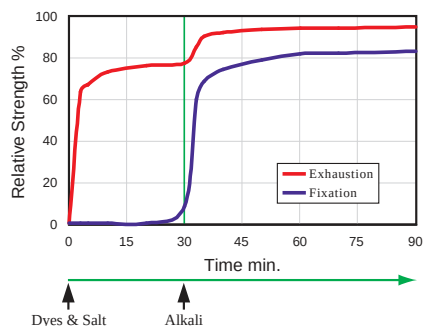

溫度依存性 Dependency on temperature

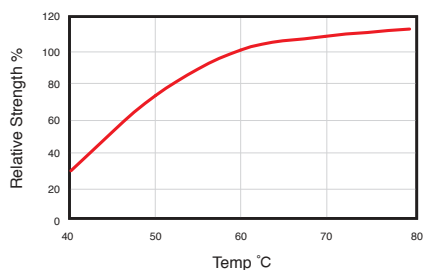

芒硝依存性 Dependency on Glauber's salt

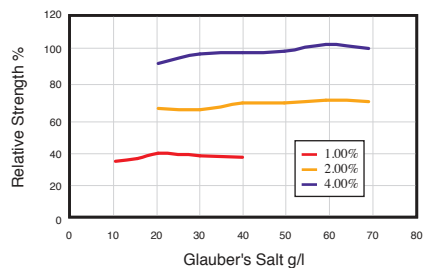

Everzol Orange ED-2R


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C10 C		4-5	5	4	5	5	5	5	Peroxide Bleaching雙氧水漂白			3-4	
	ISO C10 D		4-5	5	2-3	5	5	4-5	3-4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		3-4	5	3-4	5	5	4-5	5		Wet 濕	3		
	ISO C06-C2S		3-4	5	3-4	5	5	4-5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4	
	M&S C4A		4-5	5	4	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4	
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	3-4	5	4-5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	3-4		4-5							4 Hours after	5	
Acid hydrolysis 酸水解		3.0%	4	5	3-4	3-4	5	5	3-4		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	5	5	5	5			4 Hours after	5	
	Alkali 鹼		4-5	5	4-5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
	0.1 %	*	*	Perspiration Light 耐汗日光	Acid Alkali	3.0 %	2-3 3	4 3-4
Artificial Light (Xenon-Arc Lamp) 耐日光	0.3 %	2	3					
	1.0 %	2-3	3-4					
	3.0 %	3	4					
	6.0 %	3-4	4-5					

浴比依存性 Dependency on Liquor ratio

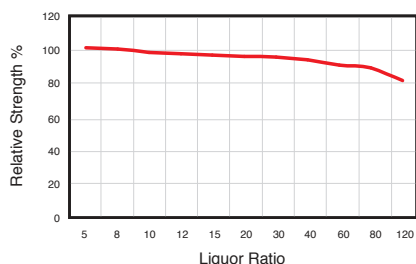

鹼依存性 Dependency on alkali

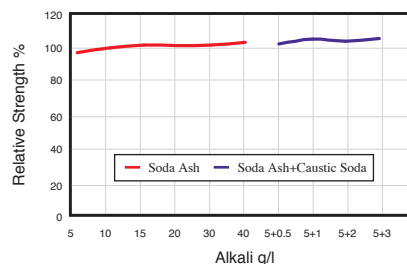


Everzol Orange ED-4R


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	Y(R)
	TL 84 Lamp	Y(G)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	1-2
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3-4


吸盡固著曲線 Exhaustion & Fixation

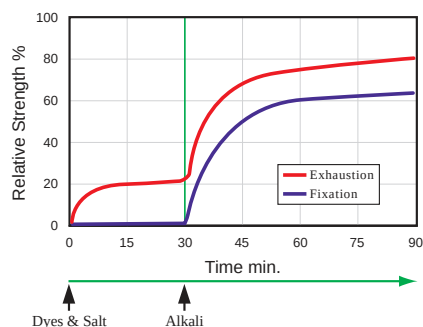

溫度依存性 Dependency on temperature

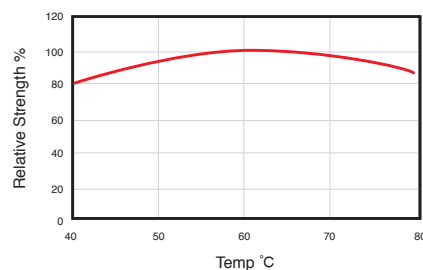

芒硝依存性 Dependency on Glauber's salt

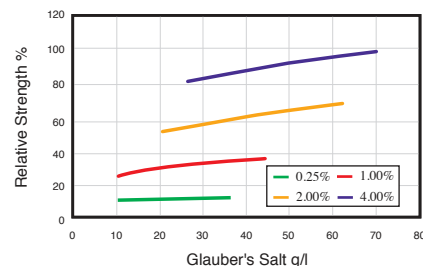

Everzol Orange ED-4R


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C02	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C03		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			3-4	
	ISO C04		4-5	5	4	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕	3		
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	4	4	5	4	4	Multi laundering 耐多次水洗		3.0%	4	
Hot Water 耐熱水		3.0%	4-5	5	4-5	4-5	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	4-5	5	4-5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3-4
Post mercerizing 後絲光		3.0%	4		3-4				4 Hours after			4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	3-4	3-4	5	5	4-5		Wet 濕	Immediately	3.0%	3-4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	4-5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.1 %	3	4-5	Perspiration Light 耐汗日光	Acid Alkali	3.0 %	4	5-6
		0.3 %	3-4	4-5				4	5-6
		1.0 %	4	5					
		3.0 %	4-5	5-6					
		6.0 %	4-5	6					

浴比依存性 Dependency on Liquor ratio

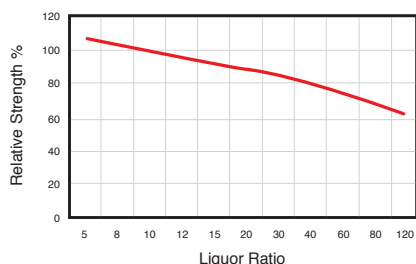

鹼依存性 Dependency on alkali

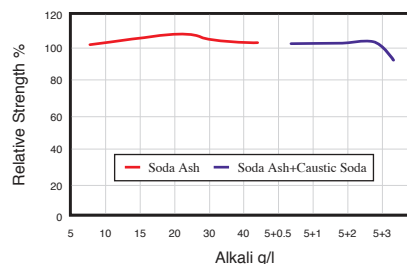


Everzol Red ED


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		2-3
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4-5
	Dye Liquor 染浴	5
Color constancy 色恆性	Tungsten Lamp	B
	TL 84 Lamp	B
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	2-3
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	4
Stripping 脫色性	(1)	×
	(2)	△
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	2-3
	Alkaline 鹼性	1-2


吸盡固著曲線 Exhaustion & Fixation

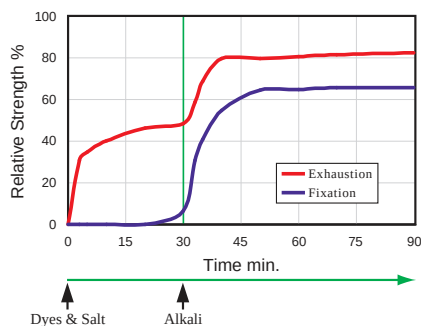

溫度依存性 Dependency on temperature

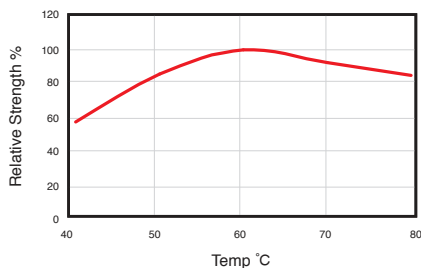

芒硝依存性 Dependency on Glauber's salt

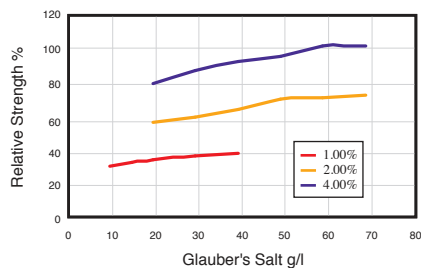

Everzol Red ED


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			3.0%	3-4
	ISO C10 C		4-5	5	4-5	5	5	5	Peroxide Bleaching雙氧水漂白			4		
	ISO C10 D		4-5	5	4	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4	5	5	4-5	5		Wet 濕		3	
	ISO C06-C2S		4-5	5	4	5	5	4-5	5	M&S C9A 擬溼日光 (detergent Light)			0.3%	4-5
	M&S C4A		4-5	5	4-5	5	5	5	5				3.0%	4
Water 耐水		3.0%	4-5	5	4-5	4-5	5	5	5	Multi laundering 耐多次水洗			3.0%	4-5
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液			3.0%	5
Sea Water 耐海水		3.0%	4-5	5	4	5	5	4	4-5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	3		4-5				4 Hours after			5		
Acid hydrolysis 酸水解		3.0%	4-5	5	2-3	2-3	5	4-5	3		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4	5	5	5	4-5			4 Hours after		5
	Alkali 鹼		4-5	5	4	5	5	5	4-5	Colorfastness to Nitrogen Oxides 氣體變褪色			3.0%	4-5


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO	
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	*	*	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	4	
	0.3 %	2	3-4		Alkali		3	3-4	
	1.0 %	2-3	4						
	3.0 %	3	4-5						
	6.0 %	3-4	5						

浴比依存性 Dependency on Liquor ratio

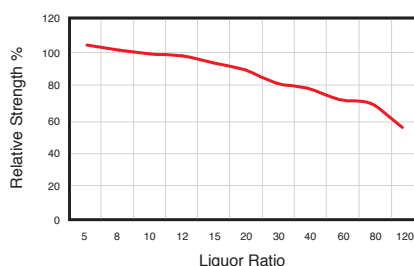

鹼依存性 Dependency on alkali

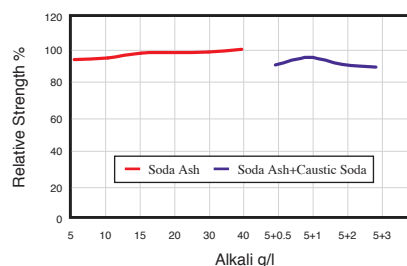


Everzol Red ED-2B


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		1
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4-5
	Dye Liquor 染浴	5
Color constancy 色恆性	Tungsten Lamp	B
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	1-2 B
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3
	Quaternary ammonium salt 四級銨鹽	3
Stripping 脫色性	(1)	×
	(2)	△
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	2-3
	Alkaline 鹼性	1-2


吸盡固著曲線 Exhaustion & Fixation

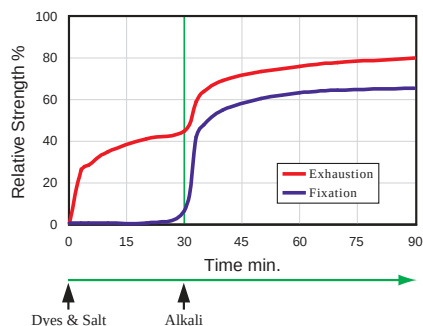

溫度依存性 Dependency on temperature

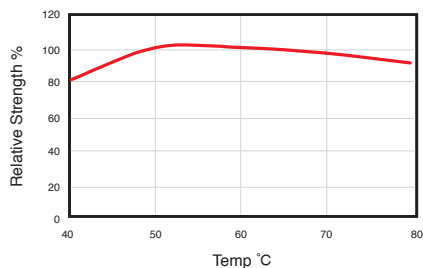

芒硝依存性 Dependency on Glauber's salt

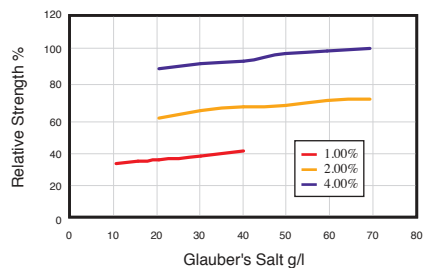

Everzol Red ED-2B


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			3.0%	3
	ISO C10 C		4-5	5	4-5	5	5	5	Peroxide Bleaching雙氧水漂白			3-4		
	ISO C10 D		4-5	5	3	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4	5	5	4-5	5		Wet 濕	2-3		
	ISO C06-C2S		4-5	5	4	5	5	4-5	5	M&S C9A 擬溼日光 (detergent Light)			0.3%	3
	M&S C4A		4-5	5	4-5	5	5	5	5				3.0%	4
Water 耐水		3.0%	4-5	5	5	4-5	5	5	5	Multi laundering 耐多次水洗			3.0%	3-4
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液			3.0%	5
Sea Water 耐海水		3.0%	4	5	4-5	5	5	4-5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	2-3		4-5				4 Hours after			5		
Acid hydrolysis 酸水解		3.0%	3-4	5	4	3	5	5	3-4		Wet 濕	Immediately	3.0%	4-5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	5	5	5	5			4 Hours after	4-5	
	Alkali 鹼		4-5	5	4	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			3.0%	5


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.1 %	*	*	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	4
		0.3 %	2-3	4		Alkali		3	4
		1.0 %	3	4-5					
		3.0 %	3-4	5					
		6.0 %	4	5-6					

浴比依存性 Dependency on Liquor ratio

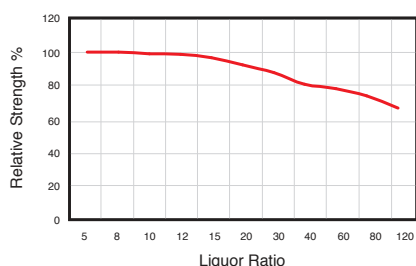

鹼依存性 Dependency on alkali

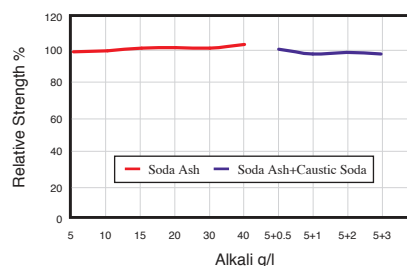


Everzol Red ED-3B


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		1-2
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4-5
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	B
	TL 84 Lamp	B
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	1-2 B
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3
	Quaternary ammonium salt 四級銨鹽	3
Stripping 脫色性	(1)	×
	(2)	△
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	2-3
	Alkaline 鹼性	1-2


吸盡固著曲線 Exhaustion & Fixation

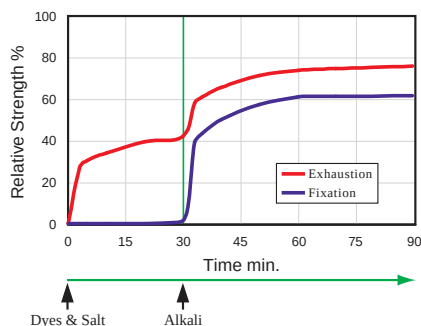

溫度依存性 Dependency on temperature

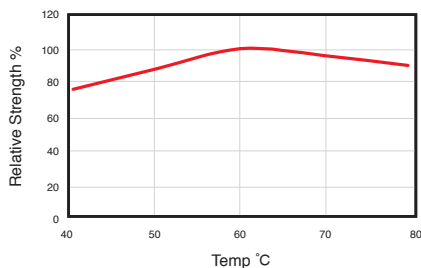

芒硝依存性 Dependency on Glauber's salt

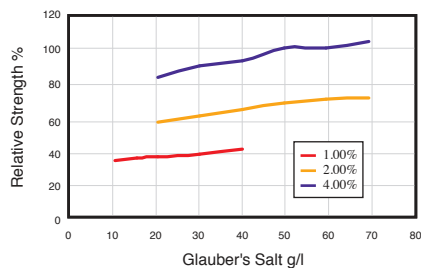

Everzol Red ED-3B


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			3-4	
	ISO C10 D		4-5	5	3-4	5	5	5	4	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		4-5	5	4	5	5	4-5	5		Wet 濕	3		
	ISO C06-C2S		4	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	3	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	3-4	
Water 耐水		3.0%	4-5	5	4-5	4-5	5	5	5	Multi laundering 耐多次水洗		3.0%	3-4	
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	3-4	5	4-5	5	5	4-5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3-4
Post mercerizing 後絲光		3.0%	2									4 Hours after		5
Acid hydrolysis 酸水解		3.0%	4-5	5	2-3	2-3	5	4-5	3		Wet 濕	Immediately	3.0%	4-5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4	5	5	4-5	4-5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4	4-5	4-5	4-5	4-5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	*	*	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	5	
	0.3 %	2-3	4		Alkali		3	3-4	
	1.0 %	3	4-5						
	3.0 %	3-4	5						
	6.0 %	4	5-6						

浴比依存性 Dependency on Liquor ratio

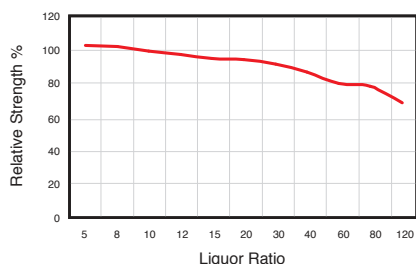

鹼依存性 Dependency on alkali

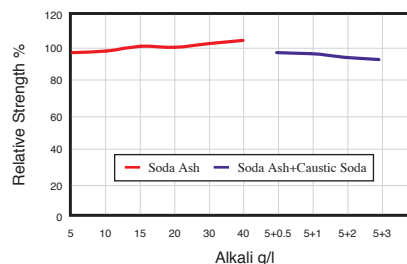


Everzol Red ED-7BN


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		3-4
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4-5
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	1
Resin finishing 樹脂加工	Melamine 三聚氰胺	3-4
	Glyoxal 乙二醛	3-4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4
Stripping 脫色性	(1)	×
	(2)	×
	(3)	×
	(4)	△
Discharge ability 拔染性	Neutral 中性	2-3
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

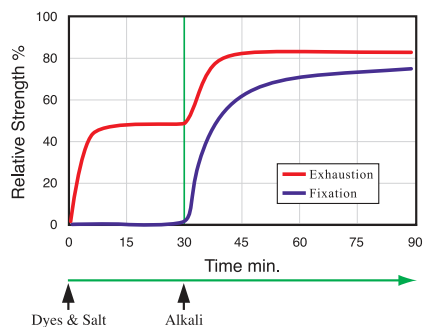

溫度依存性 Dependency on temperature

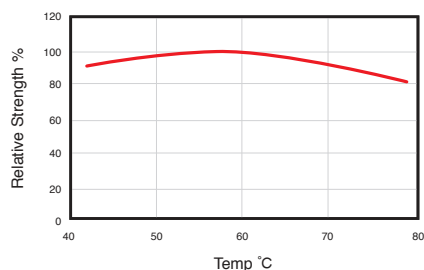

芒硝依存性 Dependency on Glauber's salt

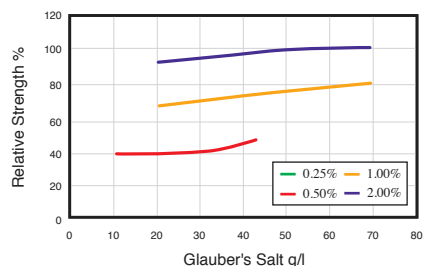

Everzol Red ED-7BN


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C10 C		4-5	5	4	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	3	4-5	5	5	3-4	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕	2-3		
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3-4
Post mercerizing 後絲光		3.0%	4B	-	2-3	-	-	-	-			4 Hours after		4
Acid hydrolysis 酸水解		3.0%	5	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	3-4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	4-5	5	4-5	5			4 Hours after		4
	Alkali 鹼		4-5	5	4	4-5	5	4-5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2-3	4	Perspiration Light 耐汗日光	Acid	3.0 %	3-4	5-6	
	0.3 %	3	4-5		Alkali		4	4	
	1.0 %	3-4	5						
	3.0 %	4	6						
	6.0 %	4-5	6						

浴比依存性 Dependency on Liquor ratio

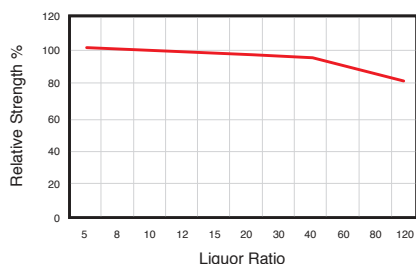

鹼依存性 Dependency on alkali

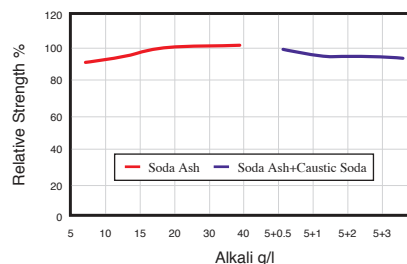


Everzol Red ED-S


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		4
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	2-3B
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4
Stripping 脫色性	(1)	×
	(2)	△
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

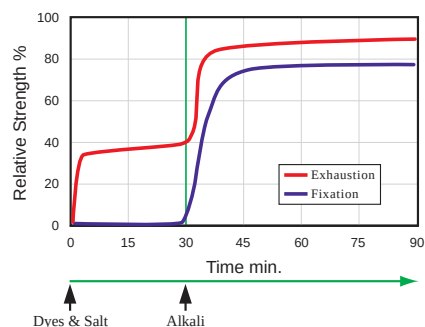

溫度依存性 Dependency on temperature

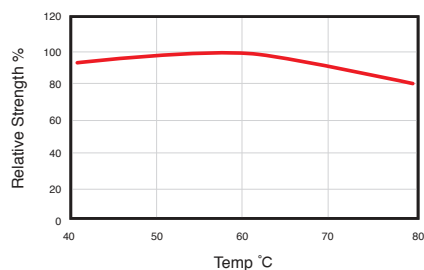

芒硝依存性 Dependency on Glauber's salt

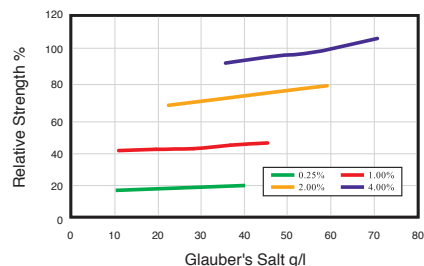

Everzol Red ED-S


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	4-5	
	ISO C10 C		4-5	5	4	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	2	4-5	5	5	3	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕		2	
	ISO C06-C2S		4-5	5	4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	5	4-5	4	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	2		2							4 Hours after		4-5
Acid hydrolysis 酸水解		3.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	2
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
	0.1 %	3	4-5	Perspiration Light 耐汗日光	Acid Alkali	3.0 %	3-4 4	6 5
Artificial Light (Xenon-Arc Lamp) 耐日光	0.3 %	3-4	5					
	1.0 %	4	5-6					
	3.0 %	4-5	6					
	6.0 %	4-5	>6					

浴比依存性 Dependency on Liquor ratio

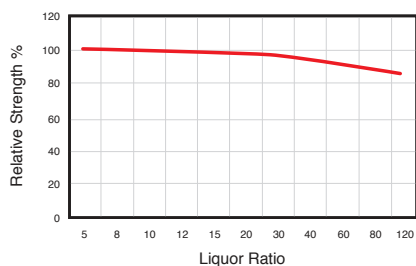

鹼依存性 Dependency on alkali

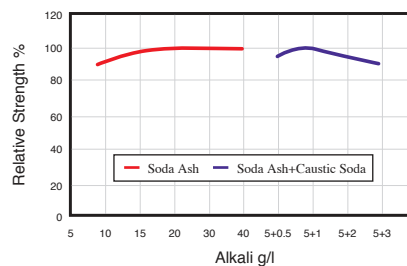


Everzol Rubine ED


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		3
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	4
Color constancy 色恆性	Tungsten Lamp	(B)
	TL 84 Lamp	(Y)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	1B
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	4
Stripping 脫色性	(1)	×
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	1
	Alkaline 鹼性	1


吸盡固著曲線 Exhaustion & Fixation

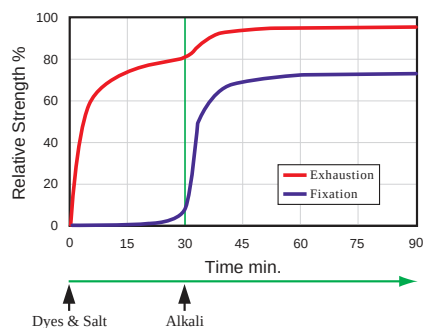

溫度依存性 Dependency on temperature

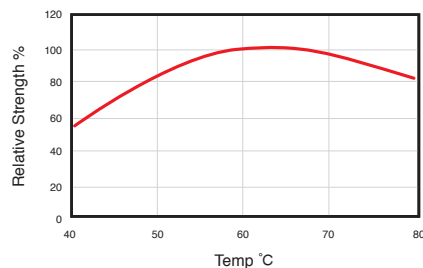

芒硝依存性 Dependency on Glauber's salt

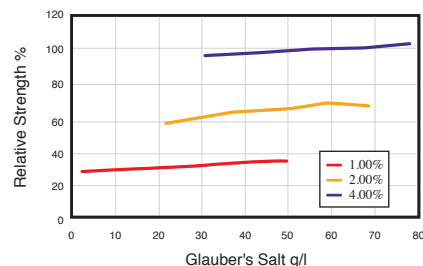

Everzol Rubine ED


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 汚染						Evaluation			Depth of shade 染色濃度	Color change 變褪色
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	3-4	5	5	4	5	Chlorinated Water耐氯水(20ppm)		3.0%	3-4(B)	
	ISO C10 C		4-5	5	3-4	5	5	4	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	2-3	4-5	5	4-5	2-3	Rubbing 耐摩擦	Dry 乾	3.0%	4	
	ISO C06-C1S		4-5	5	3-4	5	5	4	5		Wet 濕	2-3		
	ISO C06-C2S		4-5	5	3-4	5	5	4	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4	
	M&S C4A		4-5	5	4	5	5	4	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	4-5	4	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	5	4-5	3	5	5	5	Saliva (DIN) 耐唾液		3.0%	4	
Sea Water 耐海水		3.0%	4-5	5	4-5	4-5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	2(B)
Post mercerizing 後絲光		3.0%	2-3B		4						4 Hours after	4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	4	5	5	5		Wet 濕	Immediately	3.0%	2(B)
Perspiration 耐汗	Acid 酸	3.0%	4-5	4-5	3-4	3	3-4	3-4	4-5			4 Hours after		4-5
	Alkali 鹼		4-5	4-5	4	4	4-5	4-5	4-5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.1 %	*	*	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	4-5
		0.3 %	2-3	4		Alkali		2-3	4
		1.0 %	3	4-5					
		3.0 %	3-4	5					
		6.0 %	3-4	5					

浴比依存性 Dependency on Liquor ratio

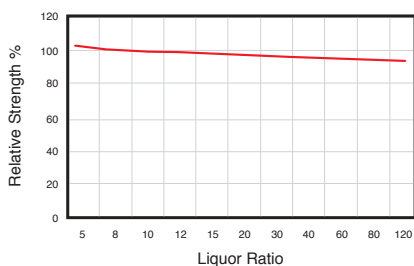

鹼依存性 Dependency on alkali

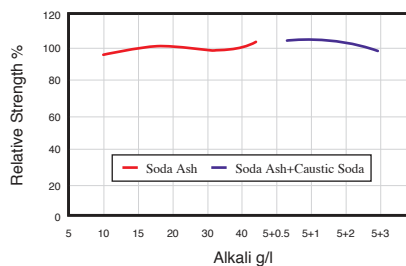


Everzol Blue ED-G


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		2-3
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	3-4
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3-4
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	1
	Alkaline 鹼性	1


吸盡固著曲線 Exhaustion & Fixation

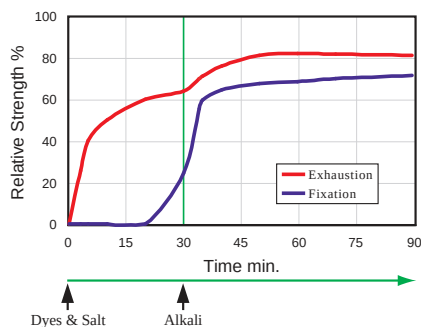

溫度依存性 Dependency on temperature

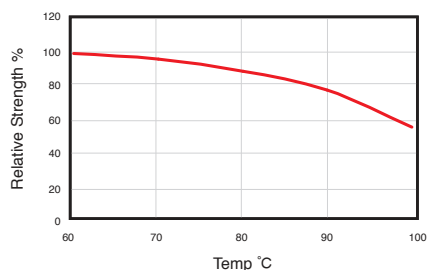

芒硝依存性 Dependency on Glauber's salt

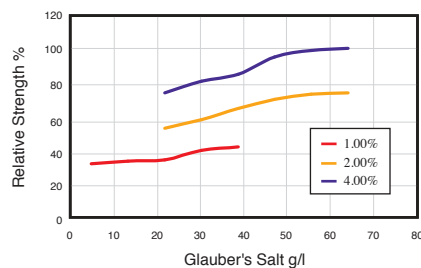

Everzol Blue ED-G


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	1	
	ISO C10 C		5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			3-4	
	ISO C10 D		5	5	4	5	5	5	5	Rubbing 耐摩擦	Dry 乾	3.0%	5	
	ISO C06-C1S		5	5	4	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		5	5	4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4-5	
	M&S C4A		5	5	5	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	5	5	4-5	4-5	5	5	5	Multi laundering 耐多次水洗		3.0%	5	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	4-5	
Sea Water 耐海水		3.0%	5	5	4-5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3-4R
Post mercerizing 後絲光		3.0%	3G(B)		4-5						4 Hours after		5	
Acid hydrolysis 酸水解		3.0%	4-5	5	3	1-2	5	5	4		Wet 濕	Immediately	3.0%	3-4R
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	4-5	5	5	5			4 Hours after		5
	Alkali 鹼		5	5	4-5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	2	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.1 %	4-5	6	Perspiration Light 耐汗日光	Acid	3.0 %	4-5	>6
		0.3 %	4-5	>6		Alkali		4-5	>6
		1.0 %	4-5	>6					
		3.0 %	4-5	>6					
		6.0 %	4-5	>6					

浴比依存性 Dependency on Liquor ratio

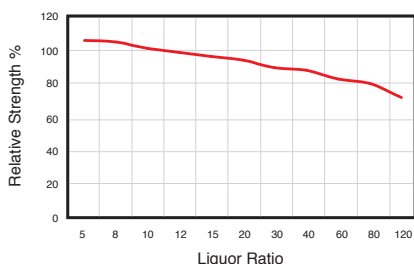

鹼依存性 Dependency on alkali

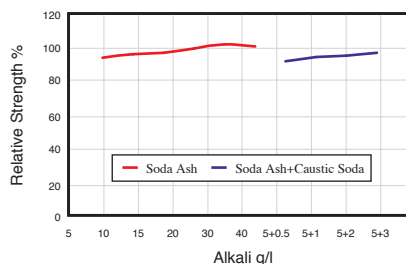


Everzol Blue L-ED


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		3-4
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	20
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	1-2
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	1-2
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	×
	(2)	×
	(3)	×
	(4)	×
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

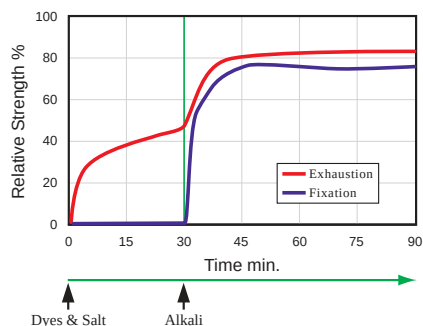

溫度依存性 Dependency on temperature

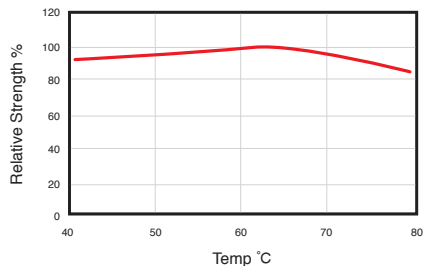

芒硝依存性 Dependency on Glauber's salt

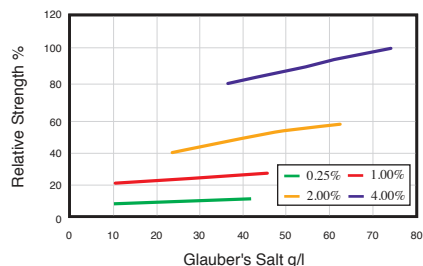

Everzol Blue L-ED


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	3	
	ISO C10 C		4-5	5	3-4	5	5	5	5	Peroxide Bleaching雙氧水漂白			3	
	ISO C10 D		4-5	5	3-4	5	5	5	2	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	3-4	5	5	5	5		Wet 濕		3	
	ISO C06-C2S		4-5	5	3-4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	2-3	
	M&S C4A		4-5	5	4	5	5	5	5			3.0%	4-5	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	4-5	5	4-5	4	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4-5	5	4-5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5
Post mercerizing 後絲光		3.0%	4		4-5							4 Hours after		5
Acid hydrolysis 酸水解		3.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO	
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale	
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2-3	3-4	Perspiration Light 耐汗日光	Acid	3.0 %	2-3	4-5	
	0.3 %	3	4		Alkali		3	4	
	1.0 %	3-4	4-5						
	3.0 %	4	5						
	6.0 %	4-5	6						

浴比依存性 Dependency on Liquor ratio

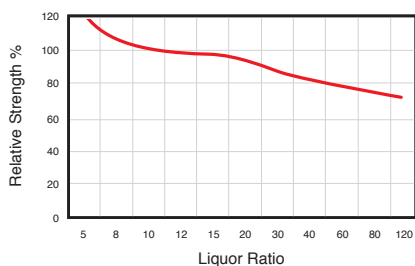

鹼依存性 Dependency on alkali

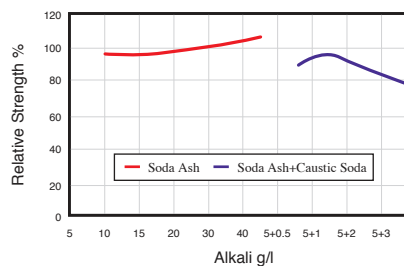


Everzol Blue ED


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		2
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2
	Dye Liquor 染浴	3
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	3-4
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	2


吸盡固著曲線 Exhaustion & Fixation

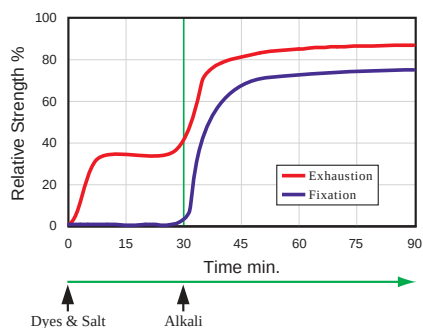

溫度依存性 Dependency on temperature

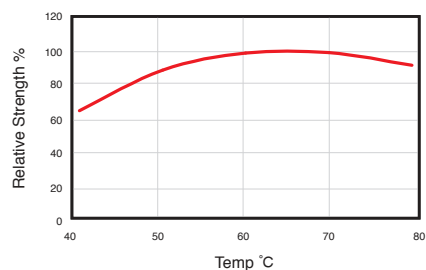

芒硝依存性 Dependency on Glauber's salt

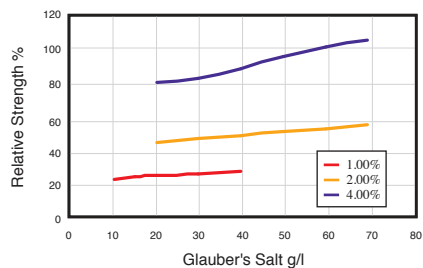

Everzol Blue ED


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	5	5	5	5	4-5	Chlorinated Water耐氯水(20ppm)		3.0%	4	
	ISO C10 C		4-5	5	5	4-5	5	5	4	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	4	3	5	5	2	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	4-5	4-5	5	4-5	4		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	4-5	5	5	5	4-5	M&S C9A 擬溼日光 (detergent Light)		0.3%	4	
	M&S C4A		4-5	5	5	5	5	5	5			3.0%	>4-5	
Water 耐水		3.0%	4-5	5	5	4	5	5	5	Multi laundering 耐多次水洗		3.0%	4-5	
Hot Water 耐熱水		3.0%	5	5	5	4-5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5
Post mercerizing 後絲光		3.0%	2-3		4-5						4 Hours after	4-5		
Acid hydrolysis 酸水解		3.0%	4-5	5	4	3-4	5	5	3-4		Wet 濕	Immediately	3.0%	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	4	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	4-5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	*	*	Perspiration Light 耐汗日光	Acid	3.0 %	3	5
	0.3 %	3-4	4		Alkali		3	4-5
	1.0 %	3-4	4-5					
	3.0 %	4	5					
	6.0 %	4-5	5-6					

浴比依存性 Dependency on Liquor ratio

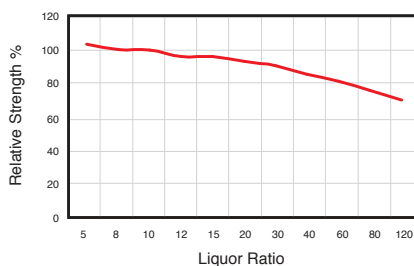

鹼依存性 Dependency on alkali

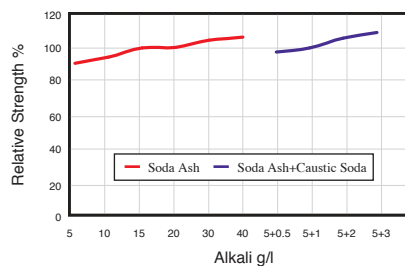


Everzol Navy ED


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		B
Migration 移染性		4
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3-4


吸盡固著曲線 Exhaustion & Fixation

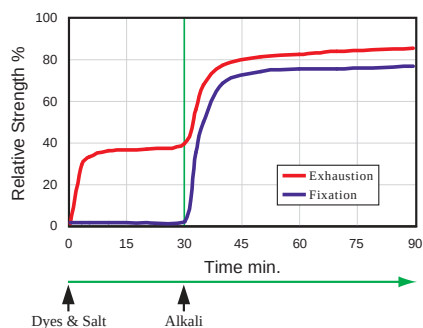

溫度依存性 Dependency on temperature

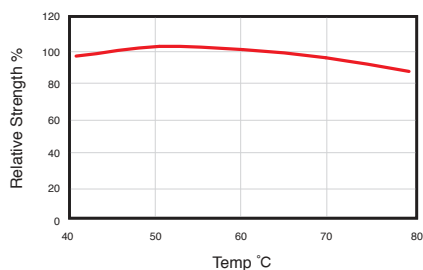

芒硝依存性 Dependency on Glauber's salt

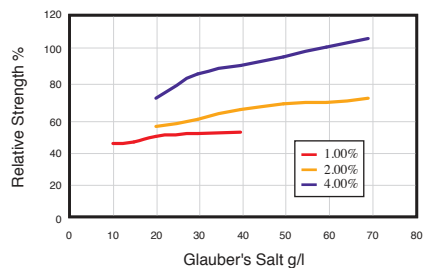

Everzol Navy ED


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		3.0%	3-4	
	ISO C10 C		4-5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4	
	ISO C10 D		4-5	5	4	5	5	5	3	Rubbing 耐摩擦	Dry 乾	3.0%	4-5	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		0.3%	3	
	M&S C4A		4-5	5	4-5	5	5	5	5			3.0%	4	
Water 耐水		3.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		3.0%	3-4	
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		3.0%	4	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
Post mercerizing 後絲光		3.0%	2-3		4				4 Hours after			4-5		
Acid hydrolysis 酸水解		3.0%	5	5	4-5	4	5	5	4		Wet 濕	Immediately	3.0%	3-4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	5	5	5	5	5			4 Hours after		4
	Alkali 鹼		4-5	5	5	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		3.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	*	*	Perspiration Light 耐汗日光	Acid	3.0 %	2	4-5	
	0.3 %	2-3	3-4		Alkali		2-3	4	
	1.0 %	3	4						
	3.0 %	3-4	4-5						
	6.0 %	4	5						

浴比依存性 Dependency on Liquor ratio

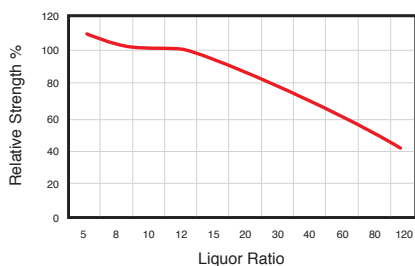

鹼依存性 Dependency on alkali

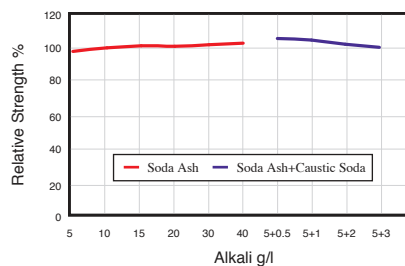


Everzol Black ED


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

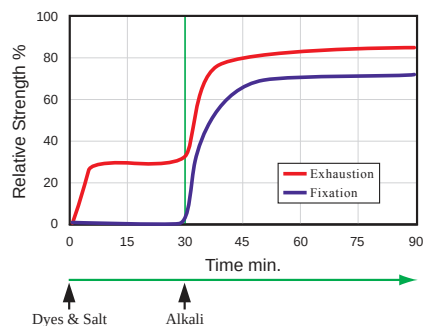

溫度依存性 Dependency on temperature

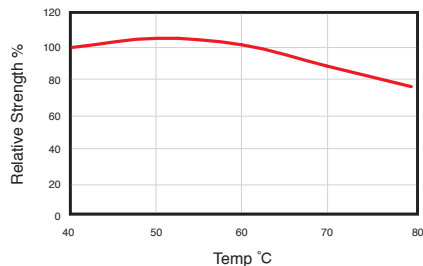

芒硝依存性 Dependency on Glauber's salt

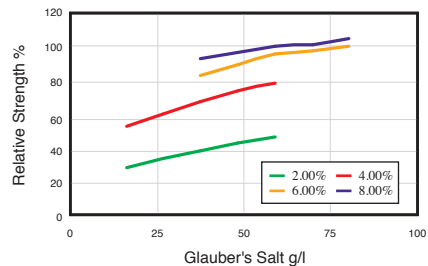

Everzol Black ED


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	5	4-5	5	5	4	Chlorinated Water耐氯水(20ppm)		6.0%	4-5	
	ISO C10 C		4-5	5	5	4-5	5	5	3-4	Peroxide Bleaching雙氧水漂白			5	
	ISO C10 D		4-5	4-5	3	3	5	4-5	2	Rubbing 耐摩擦	Dry 乾	6.0%	4	
	ISO C06-C1S		4-5	5	5	4-5	5	5	4		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	5	4-5	5	5	4-5	M&S C9A 擬溼日光 (detergent Light)		1.0%	4	
	M&S C4A		4-5	5	5	5	5	5	5			6.0%	>4-5	
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		6.0%	4-5	
Hot Water 耐熱水		6.0%	5	5	4-5	5	5	5	5	Saliva (DIN) 耐唾液		3.0%	5	
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4-5
Post mercerizing 後絲光		6.0%	3R		4-5				4 Hours after			4-5		
Acid hydrolysis 酸水解		6.0%	4	5	5	4	5	5	4-5		Wet 濕	Immediately	6.0%	4-5
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		6.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.3 %	*	*	Perspiration Light	Acid	6.0 %	2	5
		1.0 %	2-3	3-4	耐汗日光	Alkali		2-3	3-4
		3.0 %	3	4-5					
		6.0 %	3-4	5-6					
		8.0 %	4	5-6					

浴比依存性 Dependency on Liquor ratio

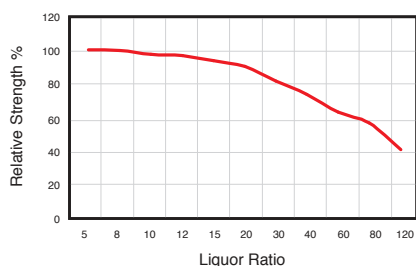

鹼依存性 Dependency on alkali

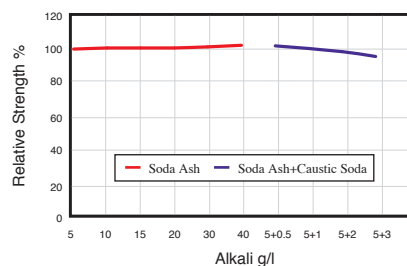


Everzol Black EDN


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		3-4
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4-5
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp	R (B)
	TL 84 Lamp	G (B)
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3-4


吸盡固著曲線 Exhaustion & Fixation

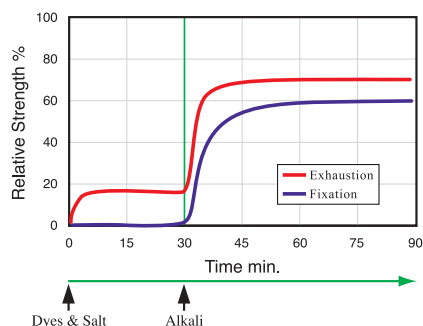

溫度依存性 Dependency on temperature

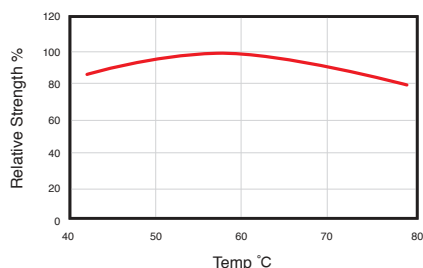

芒硝依存性 Dependency on Glauber's salt

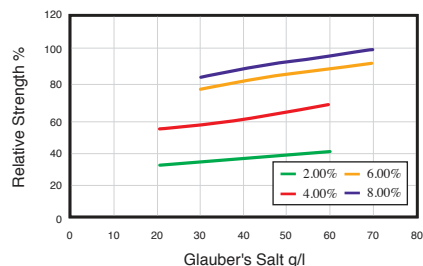

Everzol Black EDN


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		6.0%	4-5	
	ISO C10 C		4-5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白		4-5			
	ISO C10 D		4-5	5	2-3	4-5	5	4-5	3	Rubbing 耐摩擦	Dry 乾	6.0%	4-5	
	ISO C06-C1S		4-5	5	5	5	5	5	5		Wet 濕	2-3		
	ISO C06-C2S		4-5	5	5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		1.0%	4	
	M&S C4A		4-5	5	5	5	5	5	5			6.0%	4-5	
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		6.0%	4-5	
Hot Water 耐熱水		6.0%	4-5	5	5	5	5	5	5	Saliva (DIN) 耐唾液		6.0%	5	
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4-5
Post mercerizing 後絲光		6.0%	3-4	-	2	-	-	-	-			4 Hours after		4-5
Acid hydrolysis 酸水解		6.0%	4-5	5	4-5	5	5	5	5		Wet 濕	Immediately	6.0%	4-5
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		6.0%	5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.3 %	2	4	Perspiration Light 耐汗日光	Acid	6.0%	2	5
		1.0 %	3	4-5		Alkali		2-3	4
		3.0 %	3-4	5					
		6.0 %	4	5-6					
		8.0 %	4-5	6					

浴比依存性 Dependency on Liquor ratio

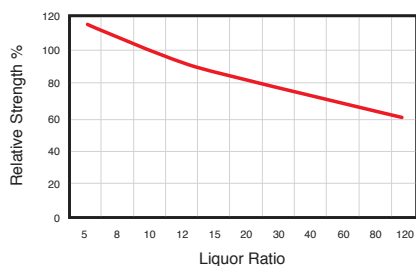

鹼依存性 Dependency on alkali

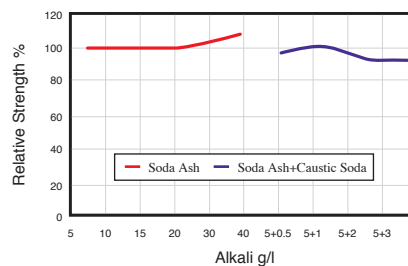


Everzol Black ED-2R


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		2
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe ²⁺ 鐵	4-5
	Cu ²⁺ 銅	3-4 R (Y)
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

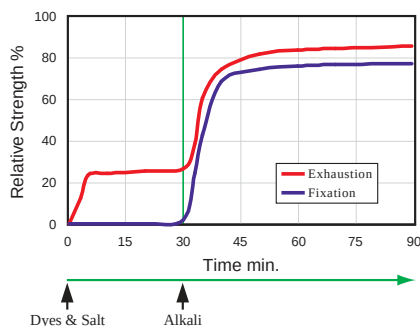

溫度依存性 Dependency on temperature

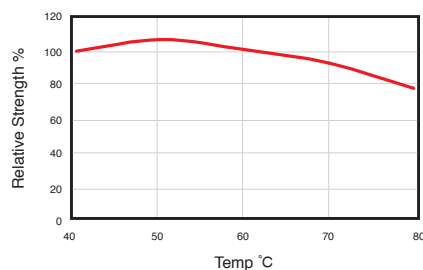

芒硝依存性 Dependency on Glauber's salt

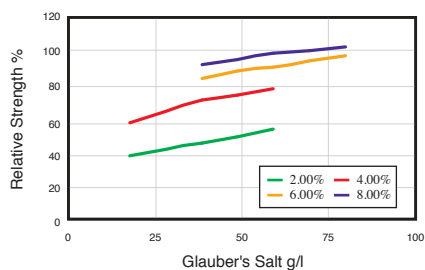

Everzol Black ED-2R


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	4	5	5	5	5	Chlorinated Water耐氯水(20ppm)		6.0%	4	
	ISO C10 C		4-5	5	4	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	3	5	5	5	2-3	Rubbing 耐摩擦	Dry 乾	6.0%	4	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕	2-3		
	ISO C06-C2S		4-5	5	4	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		1.0%	4	
	M&S C4A		4-5	5	4	5	5	5	5			6.0%	>4-5	
Water 耐水		6.0%	4-5	5	4-5	5	5	5	5	Multi laundering 耐多次水洗		6.0%	4	
Hot Water 耐熱水		6.0%	5	5	5	4-5	5	5	5	Saliva (DIN) 耐唾液		6.0%	5	
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4-5
Post mercerizing 後絲光		6.0%	3		4				4 Hours after			4-5		
Acid hydrolysis 酸水解		6.0%	4-5	5	3-4	3-4	5	5	4		Wet 濕	Immediately	6.0%	4-5
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	4-5	4-5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4-5	4-5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		6.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
	0.3 %	*	*	Perspiration Light 耐汗日光	Acid Alkali	6.0 %	2 2-3	5 3-4
Artificial Light (Xenon-Arc Lamp) 耐日光	1.0 %	2-3	3-4					
	3.0 %	3	4-5					
	6.0 %	3-4	5-6					
	8.0 %	4	5-6					

浴比依存性 Dependency on Liquor ratio

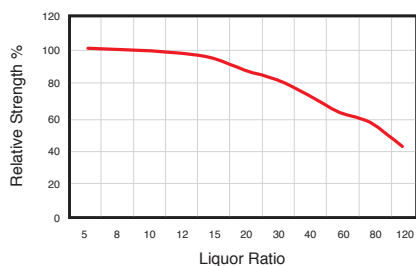

鹼依存性 Dependency on alkali

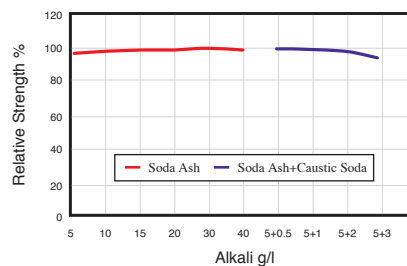


Everzol Black ED-G


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4
Washing off 洗淨性		4-5
Solubility g/l 溶解度	50°C Water	150
	50°C Water+50 g/l Salt	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	3-4
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	2-3
Resin finishing 樹脂加工	Melamine 三聚氰胺	3-4
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	4


吸盡固著曲線 Exhaustion & Fixation

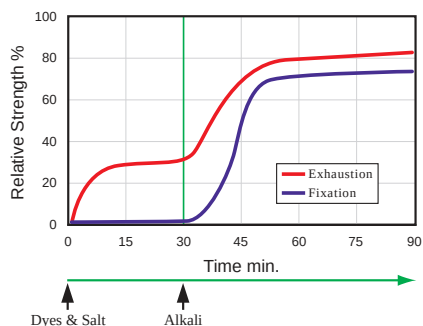

溫度依存性 Dependency on temperature

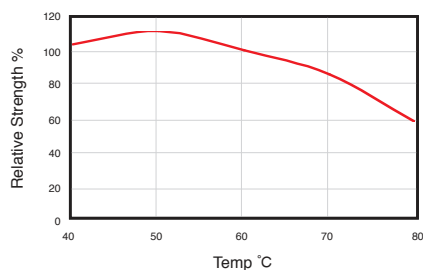

芒硝依存性 Dependency on Glauber's salt

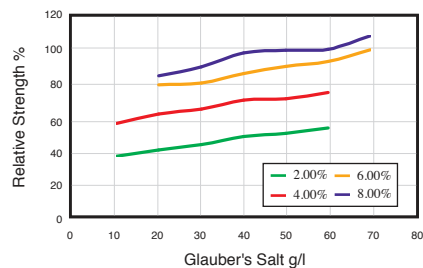

Everzol Black ED-G


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		6.0%	3-4	
	ISO C10 C		4-5	5	4-5	5	5	5	5	Peroxide Bleaching雙氧水漂白			5	
	ISO C10 D		4-5	5	2-3	4-5	5	4-5	2-3	Rubbing 耐摩擦	Dry 乾	6.0%	4-5	
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		1.0%	4-5	
	M&S C4A		4-5	5	5	5	5	5	5			6.0%	>4-5	
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		6.0%	4-5	
Hot Water 耐熱水		6.0%	4-5	5	5	4-5	5	5	5	Saliva (DIN) 耐唾液		6.0%	5	
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4-5
Post mercerizing 後絲光		6.0%	3-4R		3-4				4 Hours after		4-5			
Acid hydrolysis 酸水解		6.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	6.0%	4-5
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	5	5	5	5	5		4 Hours after	4-5		
	Alkali 鹼		4-5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		6.0%	4-5	


Light Fastness 日光堅牢度

Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale	Evaluation		Dyeing Depth 染色濃度	Color Change 20 AFU	Grade ISO Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光		0.3 %	*	*	Perspiration Light 耐汗日光	Acid Alkali	6.0 %	2-3	5
		1.0 %	3	4				3-4	3-4
		3.0 %	4	5					
		6.0 %	4-5	6					
		8.0 %	5	6					

浴比依存性 Dependency on Liquor ratio

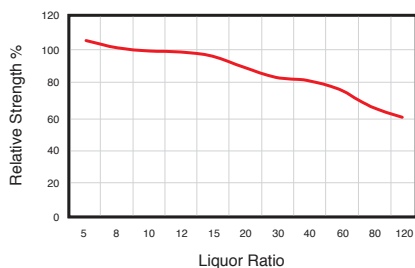

鹼依存性 Dependency on alkali

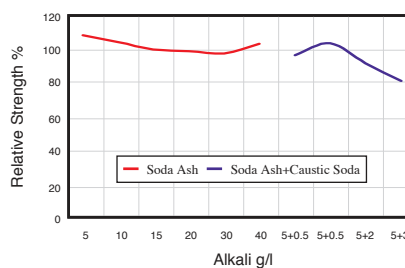


Everzol Black ED-R


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	1
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	2-3
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	△
	(2)	○
	(3)	○
	(4)	○
Discharge ability 拔染性	Neutral 中性	3-4
	Alkaline 鹼性	4-5


吸盡固著曲線 Exhaustion & Fixation

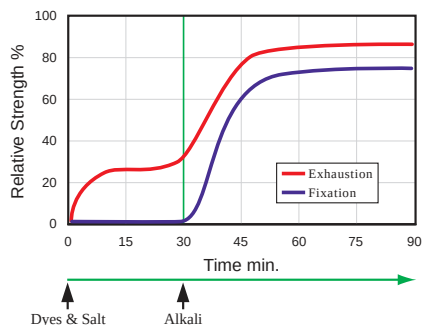

溫度依存性 Dependency on temperature

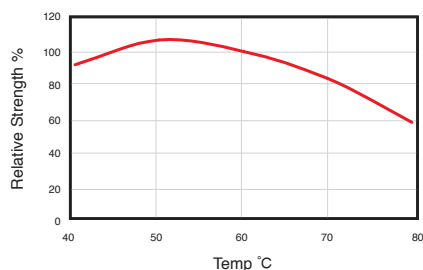

芒硝依存性 Dependency on Glauber's salt

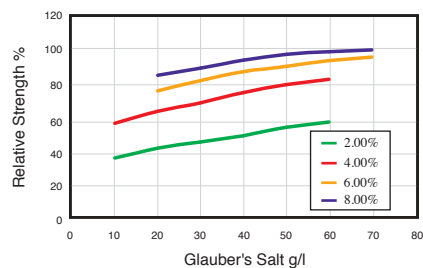

Everzol Black ED-R


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		6.0%	4-5	
	ISO C10 C		4-5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白		4-5			
	ISO C10 D		4-5	5	2-3	4-5	5	4-5	2-3	Rubbing 耐摩擦	Dry 乾	6.0%	4	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		1.0%	4	
	M&S C4A		4-5	5	5	5	5	5	5			6.0%	>4-5	
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		6.0%	4	
Hot Water 耐熱水		6.0%	4-5	5	4-5	3-4	4-5	5	5	Saliva (DIN) 耐唾液		6.0%	5	
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4-5
Post mercerizing 後絲光		6.0%	3-4R		3-4						4 Hours after	4-5		
Acid hydrolysis 酸水解		6.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	6.0%	4-5
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	5	5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		6.0%	5


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.3 %	*	*	Perspiration Light 耐汗日光	Acid	6.0 %	2-3	5
	1.0 %	3	4		Alkali		3-4	3-4
	3.0 %	3-4	5					
	6.0 %	4	5-6					
	8.0 %	4-5	6					

浴比依存性 Dependency on Liquor ratio

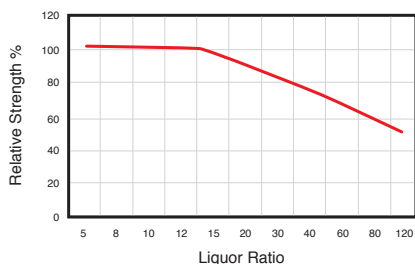

鹼依存性 Dependency on alkali

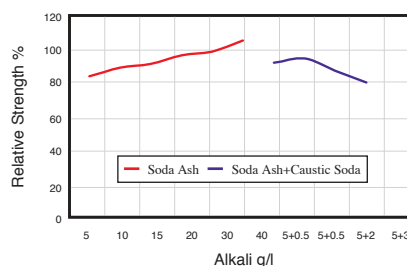


Everzol Black ED-3R


Dyeing Properties 特性

Characteristics		Evaluation
Reactivity 反應性		II
Substantivity 親和性		C
Migration 移染性		4-5
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water	100
	50°C Water+50 g/l Salt	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2-3
Color constancy 色恆性	Tungsten Lamp	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe ²⁺ 鐵	4
	Cu ²⁺ 銅	1
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	2-3
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary ammonium salt 四級銨鹽	5
Stripping 脫色性	(1)	×
	(2)	△
	(3)	△
	(4)	△
Discharge ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	3


吸盡固著曲線 Exhaustion & Fixation

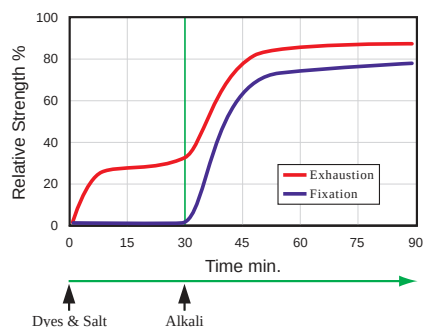

溫度依存性 Dependency on temperature

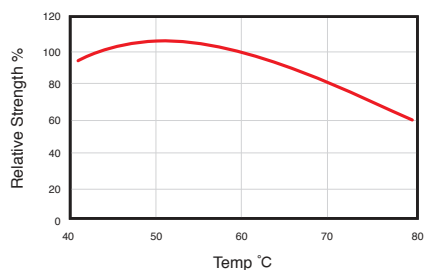

芒硝依存性 Dependency on Glauber's salt

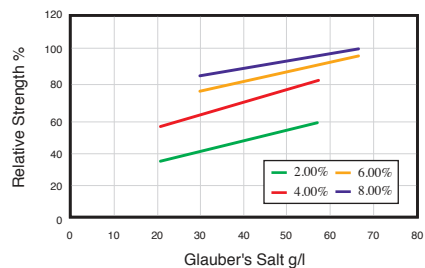

Everzol Black ED-3R


Fastness before fixing treatment 固色前牢度表

Evaluation		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation		Depth of shade 染色濃度	Color change 變褪色	
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Fastness										Fastness				
Washing 耐水洗	ISO C10 B	6.0%	4-5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)		6.0%	4	
	ISO C10 C		4-5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白			4-5	
	ISO C10 D		4-5	5	2-3	4-5	5	4-5	2-3	Rubbing 耐摩擦	Dry 乾	6.0%	3-4	
	ISO C06-C1S		4-5	5	4-5	5	5	5	5		Wet 濕		2-3	
	ISO C06-C2S		4-5	5	4-5	5	5	5	5	M&S C9A 擬溼日光 (detergent Light)		1.0%	4	
	M&S C4A		4-5	5	5	5	5	5	5			6.0%	4-5	
Water 耐水		6.0%	4-5	5	5	5	5	5	5	Multi laundering 耐多次水洗		6.0%	4	
Hot Water 耐熱水		6.0%	4-5	5	4-5	3-4	4-5	5	5	Saliva (DIN) 耐唾液		6.0%	5	
Sea Water 耐海水		6.0%	4-5	5	5	5	5	5	5	Hot- Pressing 耐熱壓	Dry 乾	Immediately	6.0%	4-5
Post mercerizing 後絲光		6.0%	3-4R		3-4						4 Hours after	4-5		
Acid hydrolysis 酸水解		6.0%	4-5	5	5	5	5	5	5		Wet 濕	Immediately	6.0%	4-5
Perspiration 耐汗	Acid 酸	6.0%	4-5	5	4-5	5	5	5	5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色		6.0%	5	


Light Fastness 日光堅牢度

Evaluation	Dyeing Depth	Color Change	Grade ISO	Evaluation		Dyeing Depth	Color Change	Grade ISO
	染色濃度	20 AFU	Blue Scale			染色濃度	20 AFU	Blue Scale
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3	3	Perspiration Light 耐汗日光	Acid	6.0 %	2-3	5
	0.3 %	3-4	4		Alkali		3-4	3-4
	1.0 %	4	5					
	3.0 %	4	5-6					
	6.0 %	4	6					

浴比依存性 Dependency on Liquor ratio

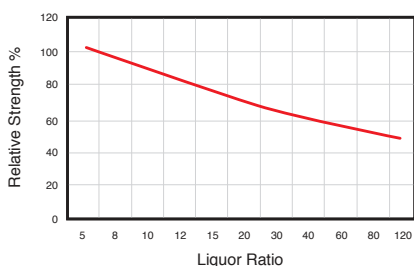

鹼依存性 Dependency on alkali

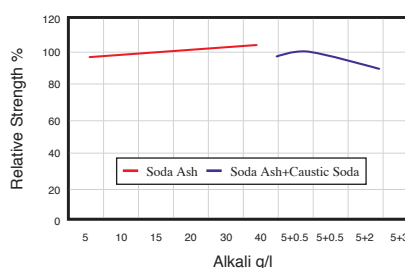

Note

Note

本資料所提供的資訊與建議是以我們最大的用心完成，但不能含括所有可能的狀況。使用相關產品或搭配其他產品時，請先自行測試。本資料並不具保證及法律效用，僅供參考使用。使用者必須自行承擔所有的風險與法律責任。

臺灣永光化學工業股份有限公司 - 技術行銷處

Warnings: The information and recommendations presented here were completed with the utmost care, but can't be extended to cover every possible case. They are intended to serve as non-binding guidelines and must be adapted to the prevailing condition. The product whether used singly or in combination with other substances, should be carried out in lab test prior to bulk production. The user needs to assume all risk and liability no matter whatsoever results are.

Issued by Everlight Chemical Industrial Corporation Tech.
Marketing & Service Div.





Everlight Chemical

Everlight Chemical Industrial Corp. (Headquarters)

臺灣永光化學工業股份有限公司

Tel: +886-2-27066006 Fax: +886-2-27081254

E-mail: sales-CCBU@ecic.com.tw

Everlight (Shanghai) Ltd.

上海德樺貿易有限公司

Tel: +86-21-62196954 Fax: +86-21-62191276

Everlight (Suzhou) Advanced Chemicals Ltd.

永光（蘇州）光電材料有限公司

Tel: +86-512-62871980 Fax: +86-512-62871217

Everlight (HongKong) Ltd.

香港永光有限公司

Tel: +852-26191095 Fax: +852-26191031

Ethical (Guangzhou) Ltd.

廣州明廣貿易有限公司

Tel: +86-20-38497030 Fax: +86-20-38497031

Qingdao Office

青島分公司

Tel: +86-532-85016051 Fax: +86-532-85016063

Tianjin Office

天津分公司

Tel: +86-22-23202016 Fax: +86-22-23202015

Everlight U.S.A.

美國永光公司

Tel: +1-704-5881004 Fax: +1-704-5880051

Everlight Europe B.V. (Netherlands)

荷蘭永光公司

Tel: +31-10-2380099 Fax: +31-10-2380090

Elite Foreign Trading Inc. (Turkey)

土耳其 Elite 公司

Tel: +90-324-2377789 Fax: +90-324-2370246

Everlight Chemicals (Vietnam) Co., Ltd.

越南永光公司

Tel: +84-28-3821-2969 Fax: +84-28-3636-8375

Technical Marketing & Service Division

技術行銷處

Tel: +886-3-483-8088 E-mail: ccbu-tms@ecic.com.tw



bluesign
SYSTEM PARTNER