Evercion®



Better Chemistry
Better Life

Everlight Chemical

臺灣永光化學工業股份有限公司

Everlight Chemical Industrial Corporation

EVERCION

中文版

Everlight
Chemical

Better Chemistry Better Life

品牌承諾

永光化學追求進步創新，以滿載的研究熱情，透過不斷的加乘與連結，
創造出許許多多的可能。永光，以化學專業給予客戶最大支持，協助客戶邁向成功，
也為美好的社會及永續的未來，做出具體貢獻。
我們相信，運用對的化學品，可以讓生活更美好！



品牌價值

永光化學相信，運用對的化學品，可以讓生活更美好！

穩健可靠
正派經營的理念、履行承諾的決心、穩定的品質與貼心的服務，奠定永光化學的品牌信賴感。

以客為尊
專注於化學本業，滿載研究熱情，永光化學追求突破與進步，讓化學對人類的貢獻，無止境地向前演進。

進步創新
關懷顧客、共創價值是永光化學的品質政策。我們以高品質產品、服務與技術支援，給予客戶支持，協助客戶邁向成功。

造福人群
提升人類生活福祉，是永光存在的意義；以不斷進步的化學專業，為更好明天與永續未來，做出具體的貢獻。

目錄

Ⅰ. 概述	A-1
1. 應用範圍介紹	A-1
2. Evercion染料一覽表	A-1
3. 水質與離子封鎖劑的使用	A-1
4. 染色用鹽的品質	A-2
5. 染液製備	A-2
6. 紡織品的前處理工程	A-2
7. 染色物的後處理工程	A-2
8. 鹽和鹼的推薦用法	A-3
9. 染色	A-4
10. Evercion 染料的修色	A-8
11. Evercion 染料的剝色	A-8
Ⅱ. 染色特性和堅牢度說明	A-9
1. 反應性	A-9
2. 親和性	A-9
3. 移染性	A-9
4. 洗淨性	A-10
5. 溶解度	A-10
6. 高溫染色安定性	A-11
7. 色恆性	A-12
8. 金屬離子的影響	A-12
9. 固色變色性	A-12
10. 樹脂加工性	A-13
11. 吸盡率和固著率曲線	A-13
12. 對鹼類的依存性	A-14
13. 對浴比的依存性	A-14
14. 對溫度的依存性	A-15
15. 對鹽類的依存性	A-15
16. 染色堅牢度的試驗法	A-16
Ⅲ. 染料特性資料表	A-38

Ⅰ. 概述

1.應用範圍介紹

Evercion反應性染料是一種具有色澤鮮豔，濕潤堅牢度優良，實際應用於染色上方法簡便的反應性染料。它的特點是：Evercion反應性染料分子中有反應基團，為水溶性的染料，其與纖維呈化學性的結合，故在水洗、日光、摩擦上，擁有優良的堅牢度。臺灣永光化學公司所推薦的反應性染料為一氯均三嗪反應性染料，需在高溫度和鹼性環境中進行反應固色。

Evercion反應性染料主要使用於棉、麻、再生纖維……等，以及和分散性染料共同使用於混紡品的染色和印花。Evercion反應性染料適用於一般之染色機械的染色，如浸染、捲染 (Jigger)、繩染 (Winch)

2.Evercion染料一覽表

(1) Evercion Yellow H-E6G
(2) Evercion Yellow H-E4G
(3) Evercion Yellow H-E4R
(4) Evercion Orange E-2G
(5) Evercion Orange H-ER
(6) Evercion Scarlet E-2G
(7) Evercion Scarlet H-E3G
(8) Evercion Red H-E3B
(9) Evercion Red H-E7B
(10) Evercion Blue H-EGN
(11) Evercion Blue H-ERD
(12) Evercion Navy Blue H-ER
(13) Evercion Turquoise H-A
(14) Evercion Green H-E4BD
(15) Evercion Yellow ESL
(16) Evercion Deep Red ESL
(17) Evercion Red ESL
(18) Evercion Crimson ESL
(19) Evercion Navy ESL

3.水質與離子封鎖劑的使用

染色用水，一般以採用接近中性的軟水為宜。少量的鈣、鎂（一般在100ppm以上）即會在加鹼劑染色時，與鹼劑結成不溶性沈澱而導致低得色量、不均染和降低堅牢度。

乙二胺四乙酸（E.D.T.A.）若用來封鎖重金屬離子，但對於含金屬染料，則不能使用，如：Evercion Blue H-ERD及Evercion Blue H-EGN。

4.染色用鹽的品質

染色用食鹽和芒硝以呈中性為宜，並且要求鈣、鎂鹽含量較低，以免在加鹼染色過程中大量沈澱產生。

如同使用硬水情況，所推薦的金屬離子封鎖劑為六偏磷酸鈉。

5.染液製備

Evercion反應性染料穩定性較高，溶解時可先以少量40~50℃熱水溶解，必要時在無鹼劑存在的情況下，可略予煮沸，使染料充分溶解。染液在使用前，應採用細篩過濾才能加料染色。

6.紡織品的前處理工程

染色加工前之被染物，應進行前處理工程，以去除纖維中的雜質和紡織上的漿料等。工程次序的選擇，則視被染物的純淨程度和所染顏色的鮮明度而定。

被染物經漂白後剩餘的游離氯或過氧化物須加以洗淨。棉製品經絲光後，吸收效果更佳。紡織品經前處理後，應具有高度吸收及濕潤性質，其pH值應接近中性，以利染色加工。

7.染色物的後處理工程

Evercion反應性染料在染色工程完畢後，須經過充分的洗滌和皂洗的沸煮工程，以去除未能與纖維結合而殘存的水解染料，如此方能確保優良的濕潤堅牢度品質，所以推薦的洗淨工程順序如下：

(1) 先用大量冷水洗滌，繼用熱水或沸水充分洗滌。
(2) 皂液沸煮洗滌，1-2g/l皂洗劑。
(3) 熱水洗。
(4) 冷水洗、脫水、烘乾。

冷水清洗至水澄清為止，可再施以柔軟或固色工程。皂煮工程前應儘量將殘留在染色物上的鹽、鹼劑以及未固著的染料迅速以熱水沖洗，為了防止洗滌水中未固著染料累積過多，影響染色品質，所以宜用溢流，換水洗滌。皂洗劑可以採用中性皂，陰離子性洗淨劑或非離子性合成洗淨劑……等。

後處理工程舉例：

(1) 捲染機洗滌 (JIG)

2道 流動冷水洗滌
4道 皂液沸煮洗滌
2道 熱水或沸水洗
2道 流動冷水洗淨

(2) 繩狀染機洗滌 (Winch)

1. 冷水清洗2~3次
2. 70~80°C熱水或沸水洗10分鐘
3. 沸騰皂煮10~20分鐘
4. 以80°C的熱水洗10分鐘
5. 流動冷水清洗至水澄清為止。

8.鹽和鹼的推薦用法

中性鹽常用作Evercion染料染色時的促染劑，反應性染料在浸染的時候，中性鹽的添加可增進染料的直接性。為了棉纖維和染料的反應結合，鹼劑的使用是必要的。Evercion染料染色用的電解質以芒硝（元明粉）為宜，食鹽的使用除了可能會促進染料的凝集外，同時在高溫高壓下亦有腐蝕染缸的可能性。

一般鹼劑的使用以純鹼最佳，若使用市面銷售之反應性染料用鹼劑，如磷酸三鈉的時候，其用量和pH值的關係應予注意檢討。純鹼的添加，若按照一般染廠的染浴直接添加方式，則部份染料容易產生快速固著反應的不均染現象，同時也會造成染浴起泡的現象。純鹼的使用，在中淺色時，應先將其以溫水充分溶解後，稀釋分次加注於染浴中是最安全可靠的。

為了確保加入鹼量之正確性，最終染液pH值應在11±0.2之間，可於染色工程完畢後取樣，以標準pH計測定之。

Evercion 染料染色濃度及鹽和鹼的使用量


染色濃度 (% o.w.f.)	鹽或芒硝 (g/l)		鹼 (g/l)		固著時間 (分)
	未絲光棉	絲光棉／嫘縈	純　鹼	併用 純鹼 + 液鹼	
0.5%以下	30	20	10	5 + 0.2	30
0.5%~1.0%	40	30	15	5 + 0.2	45
1.0%~2.0%	50	40	15	5 + 0.2	45
2.0%~3.0%	60	50	20	5 + 0.2	60
3.0%~4.0%	70	60	20	5 + 0.2	60
4.0%以上	90	65	20	5 + 0.2	60

附註：(1) 芒硝純度100%
(2) 液鹼濃度38°B'e


9.染色

9-1.Evercion H-E/H/ESL染料的浸染法、棉染色

染法1：一般染色法（General dyeing method）

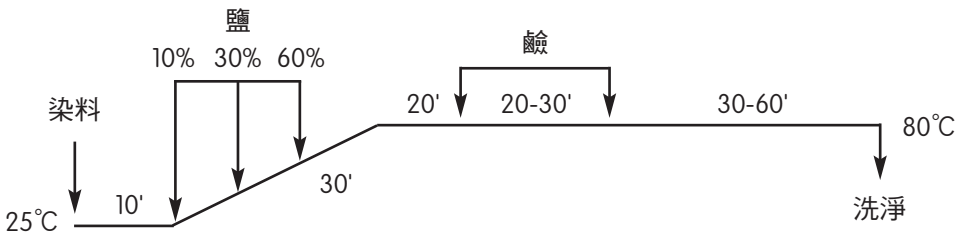


染法2：芒硝先加法（Salt at start）

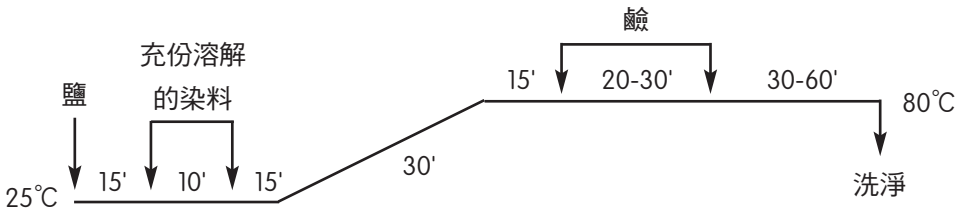


本染法適用於全自動的染色機械，如筒子紗染色機、經軸染色機、繩狀染色機、噴射染色機等。


染法3：Evercion Turquoise H-A 的特殊染色法

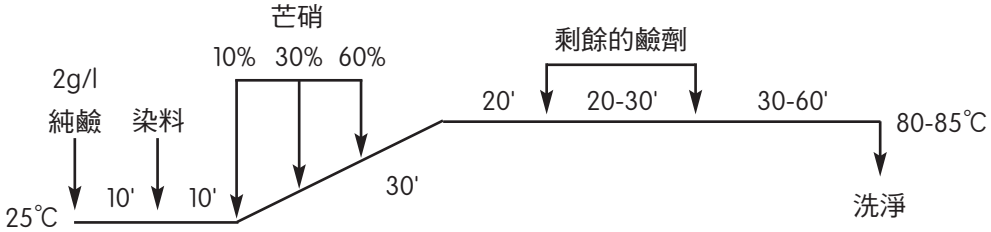


染法4：Evercion 建議染色法

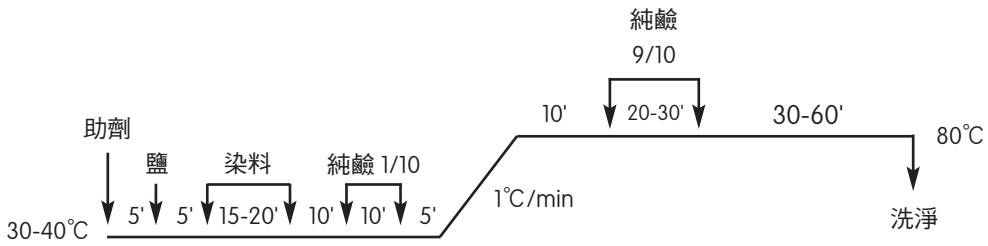

染法5：針對Cotton/Lycra、Viscose/Lycra、100%Viscose之高溫移染法
（特別是滲透困難之全棉針織布）

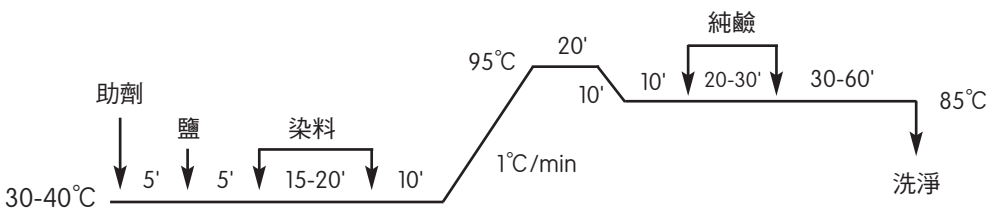

染法6：T/C 一浴二段染色法

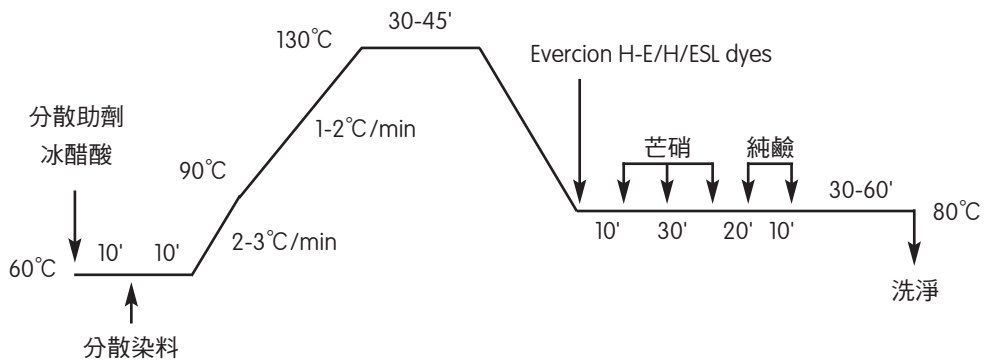

Everlight Chemical

染色優點：

1. 一浴二段方式以分散性染料及Evercion H-E/H/ESL染料施染，可以匹染、盤頭、筒紗方式染色，如此比二浴法更可節省時間及能源。
2. 適用之分散性染料必須能耐鹼以促進良好之染色再現性、染色相容性及均染性。
3. Evercion H-E/H/ESL 以一浴二段染色兼具良好均染性、再現性及牢度之優點。

染色流程：

1. 設定分散染料染浴溫度60℃，加入1g/l分散劑及pH緩衝劑以控制pH在5~5.5之間。
2. 持溫10分鐘讓染料及助劑分佈均勻，然後在45分鐘內昇溫至130℃，再持溫30~45分鐘。
3. 在25分鐘內降至80℃。
4. 加入Evercion H-E/H/ESL染料。
5. 持溫10分鐘讓染料及助劑均勻分佈，再於30分鐘內緩緩加入芒硝。
6. 持溫20分鍾，然後再於20分鐘內加入稀釋之純鹼，依染色深度施染30~60分鐘。
7. 若棉部份需要修色，先將染浴降溫至60℃，然後緩緩加入Evercion H-E/H/ESL染料，然後持溫20分鐘，繼續於20分鐘內升溫至80℃再持溫20分鐘。
8. 60℃溫水洗2~3回。每回10分鐘。
9. 沸熱皂洗（2g/l皂洗劑）。
10. 60℃溫水洗10分鐘。
11. 冷溢流洗。

* 極深色系建議多一道皂洗。

* 對大紅色系要求較高之濕牢度必須施以固色，固色劑用量依需求酌量使用，並在皂洗後固色40~50℃，20分鐘。

9-2 Evercion H-E/H/ESL 染料的搭配

1. 三原色：

   淺三原色：

   Evercion Yellow H-E4R

   Evercion Red H-E3B

   Evercion Blue H-ERD

   中、深三原色：

Evercion Yellow H-E4R	Evercion Yellow ESL
Evercion Red H-E7B	Evercion Crimson ESL
Evercion Navy Blue H-ER*	Evercion Navy ESL

   *備註：Evercion Navy Blue H-ER不建議使用於淺色色系。

2. 大紅色系：

Evercion Red H-E3B	Evercion Red H-E7B
Evercion Orange H-ER	Evercion Scarlet E-2G
Evercion Scarlet H-E3G	Evercion Deep Red ESL

3. 翠綠色系：

Evercion Yellow H-E6G	Evercion Yellow H-E4G
Evercion Turquoise H-A	Evercion Blue H-EGN

4. 湖藍色系：

   Evercion Turquoise H-A

   Evercion Blue H-EGN

5. 紫色色系：

Evercion Blue H-EGN	Evercion Crimson ESL
Evercion Red H-E7B	

6. 棗紅色系：

Evercion Yellow H-E4R	Evercion Yellow ESL
Evercion Red H-E3B	Evercion Crimson ESL
Evercion Navy Blue H-ER	Evercion Navy ESL

7. 墨綠色系：

   Evercion Green H-E4BD

   Evercion Navy Blue H-ER

   Evercion Yellow H-E4R

8. 深丈青：

Evercion Yellow H-E4R	Evercion Yellow ESL
Evercion Red H-E7B	Evercion Crimson ESL
Evercion Navy Blue H-ER	Evercion Navy ESL

10.Evercion 染料的修色

若修色量超過原配方的25%須換新染液。若修色量少於25%時，可用下述任一方法。

10.1 不排液修色法

本法推荐用於修色量原配方的1%和1%以上。

(a) 染液冷卻至60°C
(b) 加入已稀釋溶解的染料
(c) 在60°C持續染10分鐘
(d) 升溫至80°C
(e) 在80°C持續染30分鐘
(f) 對色

10.2 排掉一半染液修色法

此法用於較淺色之修色。

(a) 排掉一半染液、注入冷水。如此可降低溫度和電解質濃度，即降低修色染料之移動力。
(b) 加入已稀釋溶解的染料
(c) 染10分鍾
(d) 升溫至80°C
(e) 在80°C持續染30分鐘
(f) 對色

以下兩種修色的方法，均不需添加芒硝或純鹼。

11.Evercion 染料的剝色

Evercion染料所染的織物若需要剝色時，配方如下：

純鹼	6 g/l
保險粉	6 g/l

沸騰處理1小時，熱水清洗，冷水清洗

為達更好的剝色，常推薦在剝色後以次氯酸鈉漂之：

次氯酸鈉	10 g/l（12%有效氯）

冷溶液處理20分鐘。

再以2.5g/l亞硫酸氫鈉的冷溶液處理15分鐘，可除去殘餘的氯。重染之前，推荐先施予溫和皂煮和清洗。

Evercion Blue H-EGN不能以純鹼／保險粉或燒鹼／保險粉完全剝色。

再用次氯酸鈉漂白至一合理的程度。

II. 染色特性和堅牢度說明

1.反應性

為加鹼反應時最高吸收率pH值的分類基準。其反應性分類基準如下：

pH值	未滿11	反應性組別：Ⅰ 反應性。
pH值	11-11.5	反應性組別：Ⅱ 反應性。
pH值	11.5以上	反應性組別：Ⅲ 反應性。

2.親和性

為鹼添加前染料吸收量的分類基準，其親和性分類基準如下：

吸收率	70%以上	親和性屬：A	高親和性。
吸收率	40-75%	親和性屬：B	中親和性。
吸收率	未滿40%	親和性屬：C	低親和性。

3.移染性

移染性試驗按下述方法進行。將一塊已經一次吸盡染色的試驗布和同材質的一塊白布放在浴比1：10，含有60g/l的無水芒硝的處理浴中，經過30分鐘的處理後，再加入20g/l的純鹼使兩塊試驗布固色。

被 染 物 ： 未絲光棉布
染色濃度： 3.0%（o.w.f.）
浴　比　： 1：10
助　劑　： 無水芒硝 60g/l
溫　度　： 80℃
時　間　： 20分鐘鹼加入後續染60分鐘

判定：
對移染處理後的先染布樣和移染布樣（原白布）依據AATCC變褪色灰色標進行濃度判定。

4.洗淨性

將未經絲光的棉針織布，按通常的方法進行染色（3% o.w.f.）將染色物脫水到壓吸率約100%後，按下述順序進行各工程洗淨，並測定各工程的染料脫落量。

(1) 60℃ X 5分鐘－－溫水洗
(2) 80℃ X 5分鐘－－熱水洗
(3) 98℃ X 5分鐘－－皂　洗（皂洗劑3 g/l）
(4) 80℃ X 5分鐘－－熱水洗
(5) 60℃ X 5分鐘－－溫水洗

判定：
(1)和(2)兩工程的染料脫落量與整個洗淨工程全脫落量之比定為洗淨性。洗淨性優劣並按下述方法分為5級。

$$\frac{\text{(1)和(2)的染料脫落量}}{\text{全洗淨工程的脫落量}} \times 100\% = \text{洗淨性(\%)}$$

洗淨性為	96%以上	：5	級	洗淨性為	71%-75%	：2-3	級
洗淨性為	91%-95%	：4-5	級	洗淨性為	66%-70%	：2	級
洗淨性為	86%-90%	：4	級	洗淨性為	61%-65%	：1-2	級
洗淨性為	81%-85%	：3-4	級	洗淨性為	60%以上	：1	級
洗淨性為	76%-80%	：3	級				

5.溶解度

(A) 不添加任何助劑：
將一定量的染料以50℃的熱水溶解，冷卻到25℃，然後過濾。根據過濾所得之殘渣多少，判定染料的溶解度。


(B) 加入無水芒硝50g/l：
將一定量的染料和相當於50g/l的無水芒硝，用50℃的熱水溶解，冷卻到25℃，然後過濾。根據過濾所得之殘渣多少，判定染料的溶解度。

6.高溫染色安定性

⑴對染色布的安定性：

依通常的染色法，以3.0%（o.w.f.）濃度染色後的染色布作為基準，及按下述方法染色後的染色布，和基準比較，觀察濃度色相的變化，來評價對T/C混紡品的染色性。

染色方法：

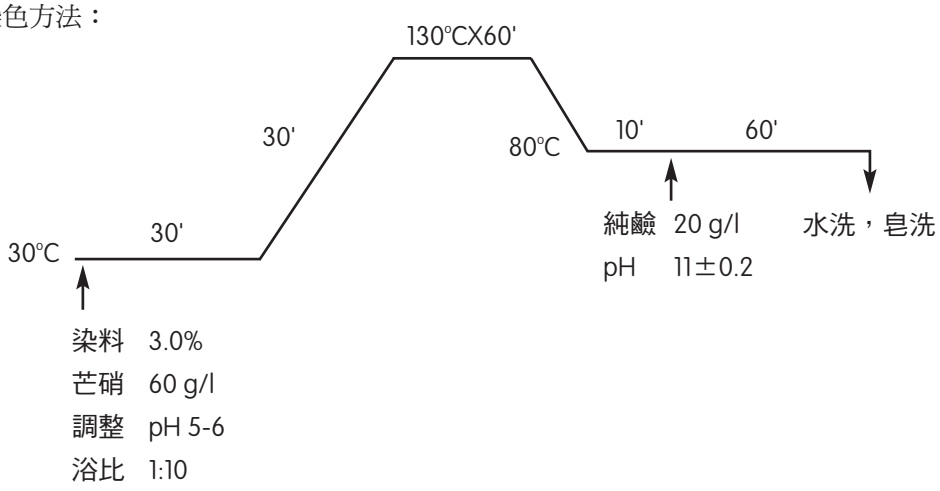

判定：

標準染色法的染色布和上述染色法的染色布，按AATCC變褪色灰色標比較，判定變色程度。

⑵染液的安定性：

染料濃度：3.0%（o.w.f.）

總液量：100ml（浴比1：10）

pH：5

溫度X時間：130°CX60分鐘

7.色恆性

以標準光源作基準，將在鎢絲燈和超效能日光燈（TL-84）下的演色性依顏色變化傾向說明表示之。

Y：黃色調　R：紅色調　B：藍色調　G：綠色調　C：鮮明　D：暗調

8.金屬離子的影響

染浴中加入金屬離子而後染色，研究其對染色物色相、濃度的影響。

染色條件：

被染物：未絲光棉布

染色濃度：3.0%（o.w.f.）

無水芒硝：60 g/l

浴比：1 : 10

溫度：80°C

時間：鹼加入後60分鐘

金屬離子：Fe^{++}：使用$FeCl_2$，20 ppm.

Cu^{++}：使用$CuSO_4$，20 ppm.

判定：

根據AATCC的變褪色灰色標來判定，添加金屬離子的染色物和未加金屬離子的染色物之間色相差異程度。

9.固色變色性

(A)　聚乙烯聚胺系：2% o.w.f.　60°C×20分鐘

(B)　四級胺鹽系　：2% o.w.f.　60°C×20分鐘

判定：

根據AATCC的變褪色灰色標來判定加工布相對於未加工布的變褪色程度。

10.樹脂加工性

以標準染色濃度3.0%（o.w.f.）染色的未經絲光棉布，按下述處方進行樹脂加工和未加工布比較其變退色情況。

⑴ 樹脂加工處方：

(A) 三聚氰胺樹脂：

Resin M-3	40	g
Catalyst MRK	8	g
水	x	g
全量	1000	g

(B) 乙二醛樹脂：

Resin GF-4000	40	g
Catalyst G	8	g
水	x	g
全量	1000	g

⑵ 工程： 壓吸→乾燥→烘乾。

壓吸率：70%±2%

乾燥：60℃×5分鐘

烘乾：160℃×3分鐘

判定：依據AATCC變褪色灰色標判定加工布相對於未加工布的變褪色程度。

11.吸盡率和固著率曲線

反應性染料的吸盡率會受到下列因素的影響：被染物的形狀、練漂程度、結晶度、絲光及被染物的支數等等。

絲光棉布和未絲光棉布的吸盡率、固著率按下述條件測定並圖示之。

染色條件：

被染物：未絲光棉布

染料濃度：3.0%(o.w.f.)

無水芒硝：60 g/l

純鹼：20 g/l

溫度：80℃

時間：鹼加入後60分鐘

浴比：1：10

Everlight Chemical

12.對鹼類的依存性

染色條件：

被 染 物：未絲光棉布
染料濃度：3.0%（o.w.f.）
無水芒硝：60 g/l
鹼　　類：純鹼g/l　5, 10, 15, 20*, 5, 5, 5,
燒鹼（38°B'e）cc/l　－, －, －, －, 0.2, 1, 2,
溫　　度：80°C
時　　間：鹼加入後60分鐘
浴　　比：1：10

13.對浴比的依存性

染色條件：

被 染 物：未絲光棉布
染料濃度：3.0%（o.w.f.）
無水芒硝：60 g/l
純　　鹼：20 g/l
溫　　度：80°C
時　　間：鹼加入後60分鐘
浴　　比：1:5~1:120，以1:10為基準

14.對溫度的依存性

染色條件：

被 染 物：未絲光棉布
染料濃度：3.0%（o.w.f.）
無水硝芒：60 g/l
純　　鹼：20 g/l
溫　　度：60℃，70℃，80℃*，90℃，98℃
時　　間：鹼加入後60分鐘
浴　　比：1:10

15.對鹽類的依存性

染色條件：

被 染 物：未絲光棉布
染料濃度：0.25%, 1%, 2%, 4%（o.w.f.）
無水芒硝：10~80 g/l
純　　鹼：20 g/l
溫　　度：80℃
時　　間：鹼加入後60分鐘
浴　　比：1：10

Everlight Chemical

16.染色堅牢度的試驗法

1. 耐水洗	ISO 105 C10 方法 B
	ISO 105 C10 方法 C
	ISO 105 C10 方法 D
	ISO 105 C06-C1S
	ISO 105 C06-C2S
	Marks & Spencer C4A
2. 耐水	ISO 105 E01
3. 耐熱水	ISO 105 E08
4. 耐海水	ISO 105 E02
5. 耐後絲光	ISO 105 X04
6. 耐酸水解	1% 醋酸溶液浸泡30分鐘，進行38°C6小時處理。
7. 耐汗（酸，鹼）	ISO 105 E04
8. 耐氯水（20ppm）	ISO 105 E03
9. 雙氧水漂白	ISO 105 N02
10. 耐磨擦（乾，濕）	ISO 105 X12
11. 擬溼日光	Marks & Spencer C9A
12. 耐多次水洗 (UK-TO)	Marks & Spencer C10A
13. 耐唾液	DIN 53160
14. 耐熱壓	ISO 105 X11
15. 日光堅牢度	ISO 105 B02 & AATCC 16-3
16. 耐汗日光堅牢度	ISO 105 B07 & AATCC 125
17. 氣體變褪色	ISO 105-G01

臺灣永光化學工業股份有限公司

Everlight Chemical Industrial Corporation

EVERCION

English Version

Everlight
Chemical

Better Chemistry Better Life

Brand Promise

Through the passionate pursuit of progress and innovation, Everlight Chemical contributes to the successes of our customers. Our work helps create a better community and ensure a sustainable future. We believe that the intelligent application of chemistry can help make the world a better place.



Brand Values

Everlight Chemical believes that the intelligent application of chemistry can help make the world a better place. Everlight Chemical has earned recognition by customers and stakeholders for the following brand values:

Reliability

Everlight Chemical's brand trustworthiness is built upon a core value of integrity, determination to deliver on promises, stable product quality, and attentive service.

Client-Centric

Customer Caring with Value Creation is Everlight Chmical's Quality Policy. Our mission is to help clients achieve success through our high-quality products, innovative solutions, and technical support.

Innovation

Focusing on our core competency-Chemistry, Everlight Chemical highly values R&D that leads to breakthroughs and progress in developing chemical products that benefit humanity.

Welfare

Contribution to the welfare of society is high among Everlight Chemical's priorities. We hope our work can contribute to a brighter future for all of mankind.

CONTENTS

I. EXHAUST DYEING OF Evercion H-E/H/ESL DYES	A-21
1. Introduction	A-21
2. List of Evercion H-E/H/ESL Dyes	A-21
3. Dyeing Quality of Water and Application of chelating agent	A-21
4. Dyeing Quality of Salt	A-22
5. Dissolving	A-22
6. Pre-treatment	A-22
7. Washing-Off Process after Dyeing	A-22
8. Recommendation of Salt and Alkali for Evercion	A-23
9. Dyeing	A-24
10. Shading for Evercion	A-28
11. Stripping for Evercion	A-28
II. DYEING PROPERTIES OF Evercion H-E/H/ESL DYES	A-29
1. Reactivity	A-29
2. Substantivity	A-29
3. Migration property	A-29
4. Washing off property	A-30
5. Solubility	A-30
6. Stability to high temperature one bath dyeing	A-31
7. Color constancy	A-32
8. Effect of metallic ion	A-32
9. Effect of fixing agent	A-33
10. Effect of flnishing resin	A-33
11. Exhaustion and fixation curves	A-34
12. Effect of alkali	A-34
13. Effect of liquor ratio	A-35
14. Effect of temperature	A-35
15. Effect of Glauber's salt	A-35
TEST METHOD OF FASTNESS PROPERTIES	A-36
III Dyed Sample	A-38
IV Dyeing Properties	A-38

Ⅰ.EXHAUST DYEING OF Evercion H-E/H/ESL DYES

1. Introduction :

Everlight Chemical Industrial Corporation manufactures a wide range of high quality reactive dyes branded : "Evercion H-E/H/ESL Dyes" .

Evercion H-E/H/ESL dyes are high exhausion reactive dyes and are highly suitable in exhaust dyeing of cellulose and its blends with synthetic fibers. The application is in either piece or yarn on all types of bathwise dyeing equipment, such as Jigger, Beam, Rapid, Jet, Hank and Package etc.

Exhaust methods are given for the dyeing of cellulose with each range of dyes.

2. List of Evercion H-E/H/ESL Dyes :

(1) Evercion Yellow H-E6G
(2) Evercion Yellow H-E4G
(3) Evercion Yellow H-E4R
(4) Evercion Orange E-2G
(5) Evercion Orange H-ER
(6) Evercion Scarlet E-2G
(7) Evercion Scarlet H-E3G
(8) Evercion Red H-E3B
(9) Evercion Red H-E7B
(10) Evercion Blue H-EGN
(11) Evercion Blue H-ERD
(12) Evercion Navy Blue H-ER
(13) Evercion Turquoise H-A
(14) Evercion Green H-E4BD
(15) Evercion Yellow ESL
(16) Evercion Deep Red ESL
(17) Evercion Red ESL
(18) Evercion Crimson ESL
(19) Evercion Navy ESL

3. Dyeing quality of water and application of chelating agent :

Neutral soft water supply is highly recommended for dyeing. Metallic ions in water, such as Ca^{2+} & Mg^{2+}, often cause uneven dyeing, poor exhaustion and fastness. E.D.T.A. can be used as chelaing agent except in the dye bath of Evercion Blue H-ERD & Evercion Blue H-EGN.

4. Dyeing quality of salt :

Neutral glauber's salt and common salt, containing less Ca^{2+} & Mg^{2++}, are prefered for cotton dyeing with reactive dyes. Corrosion on dyeing vessels by common salt must be cautious, If hard water is being used, sodium hexameta-Phosphate will be recommended as chelating agent.

5. Dissolving :

Evercion dyes are highly soluble in water. Feed the dyes steadily into dissolving tank by high speed stirring & running in water at 40°C~50°C. Proper heating will make dissolving process easier, if necessary.

6. Pre-treatment :

Cotton substrates before dyeing should be pre-scoured to remove the oil, dirts and sizes etc. The residual chlorine and peroxide after bleaching must be removed as this may cause dyeing problems. Therefore, the quality of pre-treatment such as desizing, scouring, bleaching, mercerizing etc, should be carried out as careful as possible. Initial neutral pH before dyeing will benefit dyeing quality.

7. Washing-off process after dyeing :

In order to achieve good wet fastness, the residuals of alkali and electrolyte after dyeing should be removed through proper washing and hot rinsing, soaping etc. The recommended rinsing process as below :

(1) cold rinsing, then hot rinsing, 10 min each cycle.
(2) boiled soaping with 1-2 g/l soaping agent
(3) hot rinsing 10min
(4) cold rinsing, hydro-extracting, drying.

Softening or fixing process should be done after bath is clear. Over-flow rinsing will be recommended to remove unfixed dyes for purpose of avoiding staining. For soaping effect, neutral soaps and anionic detergents or non-ionic detergents are preferred.

Examples for washing-off process：

(1) Jig dyeing

2 end over-flow rinsing

4 ends boiled soaping

2 ends hot rinsing

2 ends over-flow rinsing

(2) Piece dyeing

impact washing by cold rinsing 2-3 times

hot rinsing 10 min at 70°C~80°C

boiled soaping 10~20 min

hot rinsing at 80°C x 10min

Over-flow rinsing till bath is clear.

8.Recommendation of salt and alkali for Evercion :

Neutral salt acts as electrolyte in reactive dyes dyeing and promotes dyes substantivity. Addition of alkali bridges the chemical linkage between reactive dyes and cellulose fibers. Glauber's salt is mainly recommended as electrolyte in reactive dye dyeing. The Application of common salt (NaCl) runs the risk of causing vessel corrosion and dye aggregation. Alkali addition mainly recommends soda ash. If trisodium phosphate (Na_3PO_4) applied as alkali, pay attention to the related usage and pH.

The popular alkali addition method is feeding diluted alkali at the beginning of dyeing, but taking the risk of uneven dyeing and heavy foaming in bath by improper dissolving. The final pH of dye bath should be 11±0.2 for Evercion dyeing with assistance of pH metering device to ensure the accuracy of alkali addition.

Salt and alkali requirements for Evercion H-E/H/ESL dyes：

Dyestuff Depth of shade	Glauber's Salt or Common Salt (g/L)		Alkali (g/L)		Fixation Time (min)
	Unmercerized Cotton	Mercerized Cotton Viscose rayon	Soda ash	Soda ash + Caustic soda(38°B'e)	
Below 0.5%	30	20	10	5 + 0.2	30
0.5%～1.0%	40	30	15	5 + 0.2	45
1.0%～2.0%	50	40	15	5 + 0.2	45
2.0%～3.0%	60	50	20	5 + 0.2	60
3.0%～4.0%	70	60	20	5 + 0.2	60
Above 4.0%	90	65	20	5 + 0.2	60

Remark：(1) Glauber's salt 100%


(2) NaOH 38°B'e

Everlight Chemical

9. Dyeing :


9-1 Evercion H-E/H/ESL dyeing method

Method 1 : Portionwise addition of salt

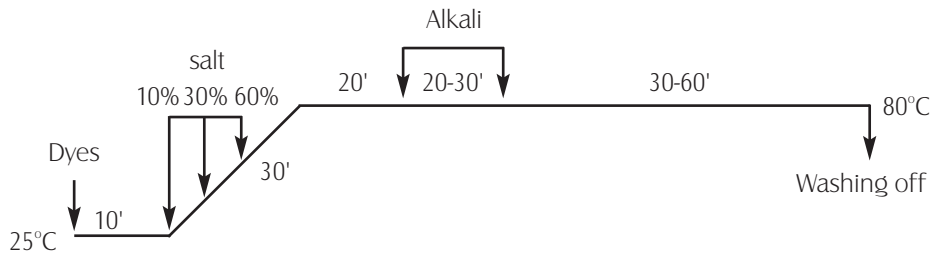


This is the general recommended method of Evercion H-E/H/ESL Dyes.

Method 2 : Salt at start

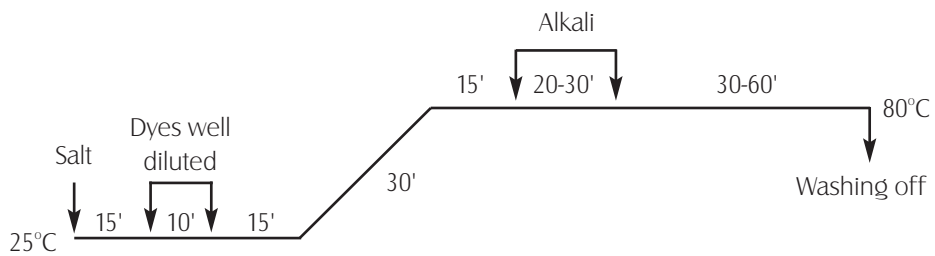


This method is recommended for fully automatic machines of Package, Beam, Winch, Jet etc.


Method 3 : Special dyeing method of Evercion Turquoise H-A

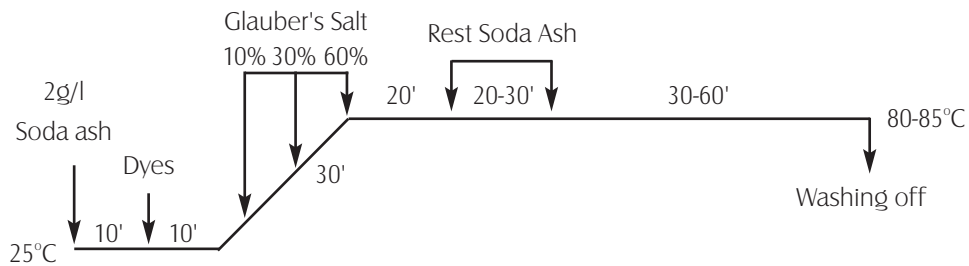


Method 4 : Evercion recommended dyeing method

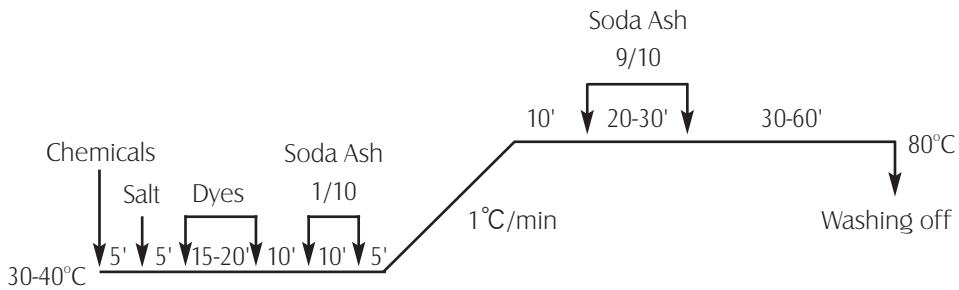

Method 5 : Migration dyeing method for Cotton/Lycra, Viscose/Lycra, 100%Viscose, especially tough penertrated cotton.

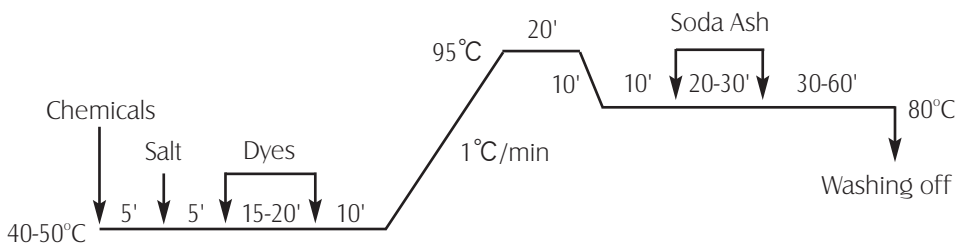

Method 6 : One-bath two-stage dyeing method of T/C blends.

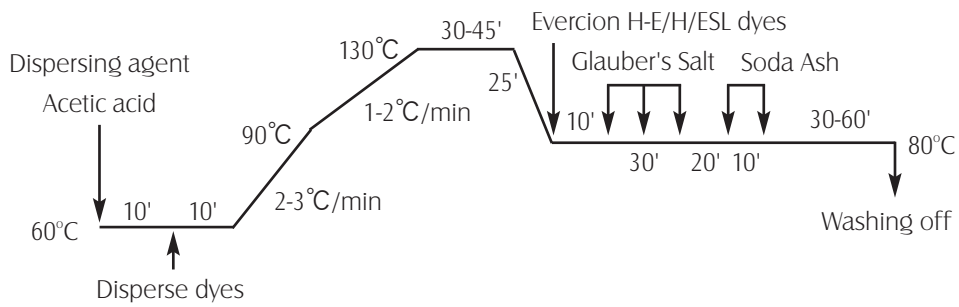

Advantages :

1. Use one-bath, two-stage method to dye disperse and Evercion H-E/H/ESL dyes on Jet, Winch, Beam or Package dyeing machine, can save more time and more enengy compared with two-bath method.
2. Selected disperse dyes will be durable in the fixation stage of Evercion H-E/H/ESL dyes with alkali and can show good reproducibility, compatibility and levelling properties.
3. Evercion H-E/H/ESL dyes can show all the advantages of one-bath, two-stage method, e.g. good levellness, reproducibility and fastness properties.

Dyeing procedure :

1. Set the bath at 60°C with disperse dyes, 1 g/l of dispersing agent and buffer solution to set the pH value between 5-5.5.
2. Allow 10 minutes for the dyes and chemicals to distribute evenly, raise the temperature over 45 minutes to 130°C and dye 30-45 minutes.
3. Cool the dyebath over 25 minutes to 80°C.
4. Add the Evercion H-E/H/ESL dyes.
5. Allow 10 minutes for the dyes and chemicals to distribute evenly, add the Glauber's salt over 30 minutes.
6. Run for 20 minutes, then add soda ash over 10 minutes and dye for 30 to 60 minutes depending on the depth of shade.
7. If shade correction of the cellulose component is necessary, the bath should be cooled down to 60°C and added slowly the required Evercion H-E/H/ESL dyes over 10 minutes. After a further 20 minutes, the temperature is raised again to 80°C over 20 minutes and continued dyeing for 20 minutes.
8. Two or three warm rinses for 10 minutes per batch at 60°C.
9. Soap 10 minutes at boiling. (Add soaping agent 2g/l)
10. Warm rinse for 10 minutes at 60°C.
11. Cold rinse with overflow.

* For very heavy shades a second soaping treatment is recommended.

* For maximun wet fastness of medium to heavy scarlet and red shades, fixing is necessary. Fixing process should be applied in the final rinsing bath after soaping. Treatrment should be for 20 minutes at 40 to 50°C.

9-2 Recommendation for dyes combination

1. Tertiary shade:
   Pale shades:
   Evercion Yellow H-E4R
   Evercion Red H-E3B
   Evercion Blue H-ERD
   Medium to heavy shades:

Evercion Yellow H-E4R	Evercion Yellow ESL
Evercion Red H-E7B	Evercion Crimson ESL
Evercion Navy Blue H-ER*	Evercion Navy ESL

   *Note:Evercion Navy Blue H-ER should not be used in pale shades.
2. Scarlet:

Evercion Red H-E3B	Evercion Red H-E7B
Evercion Orange H-ER	Evercion Scarlet E-2G
Evercion Scarlet H-E3G	Evercion Deep Red ESL

3. Jade, Grass Green:

Evercion Yellow H-E6G	Evercion Yellow H-E4G
Evercion Turquoise H-A	Evercion Blue H-EGN

4. Aqua, Turquoise:
   Evercion Turquoise H-A
   Evercion Blue H-EGN
5. Royal:

Evercion Blue H-EGN	Evercion Crimson ESL
Evercion Red H-E7B	

6. Burgundy Maroon:

Evercion Yellow H-E4R	Evercion Yellow ESL
Evercion Red H-E3B	Evercion Crimson ESL
Evercion Navy Blue H-ER	Evercion Navy ESL

7. Dark Green:
   Evercion Green H-E4BD
   Evercion Navy Blue H-ER
   Evercion Yellow H-E4R
8. Deep Navy:

Evercion Yellow H-E4R	Evercion Yellow ESL
Evercion Red H-E7B	Evercion Crimson ESL
Evercion Navy Blue H-ER	Evercion Navy ESL

10.Shading for Evercion :

If shading recipe exceeds 25% more than original one, refreshing dye bath is necessary.

If shading recipe less 25% than original one, below methods are advisable:

10.1 shading without dropping bath method:

This method is advisable for recipe more than 1%

(a) cooling bath to 60°C
(b) feeding well-diluted dyes
(c) holding 10 min at 60°C
(d) heating to 80°C
(e) holding 30 min
(f) sampling

10.2 shading with dropping half bath

This method is advisable for slight shading

(a) dropping half bath, then refilling fresh water to reduce temperature and electrolyte concentration.
(b) feeding well-diluted dyes
(c) holding 10 min
(d) heating to 80°C
(e) holding 30min at 80°C
(f) sampling

Addition of electrolyte and alkali for above methods are not necessary.

11.Stripping for Evercion :

Stripping recipe for Evercion dyes described as follows:

Soda ash	6 g/l
Sodium hydrosulphite	6 g/l

In order to achieve better stripping result, a strip with sodium hypochlorite is preferable.

NaOCL	10 g/l (active chlorine 12%)

Treat 20min at room temperature. At last, using 2.5g/l sodium bisulfate to remove the residual chlorine. It's not recommended to use soda ash/sodium hydro-sulphite or caustic/hydrosulphite to complete stripping for Evercion Blue HEGN; Nevertheless, sodium hypochlorite is preferable.

II .DYEING PROPERTIES OF Evercion H-E/H/ESL DYES

1. Reactivity :

The classification was made on the basis of an amount of alkali (Soda ash) to give a maximun strength.

Assessment :

Amount of alkali requised to give maximun strength (pH)	Reactivity group	Classification
Below 11	I	High reactivity
11.0-11.5	II	Moderate reactivity
Above 11.5	III	Low reactivity

2. Substantivity :

The classification was made on the basis of a dye-uptake before the addition of alkali.

Assessment :

Dye-uptake	Substantivity group	Classification
Above 75%	A	High substantivity
40-75%	B	Moderate substantivity
Below 40%	C	Low substantivity

3. Migration property :

The migration test was carried out in the following procedure :

A test fabric was adsorbed with dyes by primary exhaustion under the following conditions and a white fabric (unadsorbed) were treated together in a bath at a liquor ratio of 1:10 containing 60 g/l Glauber's salt at 80°C for 20 minutes, followed by fixation with an addition of 20 g/l Soda ash.

Depth of shade :	3.0% o.w.f.
Glauber's salt :	60 g/l
Liquor ratio :	1 : 10
Dyeing temperature :	80°C
Dyeing time :	60 minutes after alkali added

Assessment :

A difference in depth between the test fabric originally adsorbed with dyes and the fabric migrated was assessed by means of the grey scale for assessing change in color.

4. Washing off property :

Unmercerized cotton knit was dyed at 3% o.w.f. by normal method, the dyed sample was washed in the sequence given below to measure the amount of unfixed dyes removed from each step.

(1) 60°C, 5 min. water
(2) 80°C, 5 min. hot water
(3) 98°C, 5 min. soaping (neutral anionic surfactant, 3 g/l)
(4) 80°C, 5 min. hot water
(5) 60°C, 5 min. water

Assessment :

The washing off property was classified into five classes based on the ratio of the amount of unfixed dyes removed at steps 1 and 2 to the total amount removed.

$$\frac{\text{Amount removed at steps 1 and 2}}{\text{Total amount removed}} \times 100 = (\%)$$

Classification :

5	more than 96%	4-5	91-95%
4	86-90%	3-4	81-85%
3	76-80%	2-3	71-75%
2	66-70%	1-2	61-65%
1	60% or less		

5. Solubility :

(a) Without addition of auxiliary

A predetermined amount of dye was dissolved in warm water (50°C), and after cooling down to 25°C, the dye solution was filtered with filiter paper. The solubility was measured & based on the presence of residue on the filter paper.


(b) With an addition of 50 g/l Glauber's salt

A predetermined amount of dye and 50 g/l Glauber's salt were dissolved in warm water (50°C), and then the solubility was measured with the same method as in (a).

6. Stability to high temperature one bath dyeing :

The suitability to high temperature one bath dyeing was examined by comparing the depth and color of the dyed fabrics obtained as follows with those of normal method.

(a) Stability to dyed fabric :

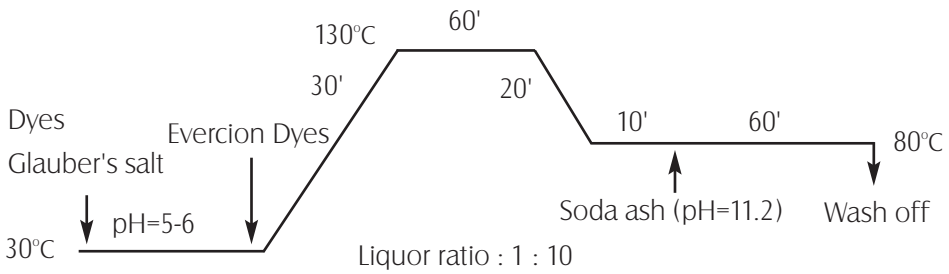

Assessment :

The shade change of the dyed fabric obtained by the above method was assessed against that obtained by the normal method by means of the grey scale for assessing the color change.

(b) Stability to dye liquor :

Depth of shade :	3.0% o.w.f.
Liquor volume :	200 ml (liquor ratio : 1 : 10)

The above dye liquor was adjusted to pH 5, and without adding any fabric to be dyed, treated at 130°C for 60 minutes. After cooling down the liquor to 60°C, unmercerized cotton knits was dyed by the normal method in this dye bath.

Assessment :

The shade change of the dyed material obained by the above method was assessed against that obtained by the normal method by means of the grey scale for assessing the color change.

7. Color Constancy :

The shades of a sample of dyed materials under tungsten filament lamp and daylight fluorescent lamp were compared with that under standard ligh source, and the degree of shade difference was measured and classified as follows.

Symbols in parentheses mean the direction of differrence in shade.
Y:Yellower R:Redder B:Bluer G:Greener C:Brighter D:Duller

8. Effect of metallic ion :

The effect of metallic ions on the shade and depth of dyeing was examined by adding metallic ions into the dyebath.

Material :	Unmercerized cotton kinit
Depth of shade :	3.0% o.w.f.
Glauber's salt :	60 g/l
Soda ash :	20 g/l
Liquor ratio :	1 : 10
Metallic ions :	Fe^{++}ferrous chloride (20 ppm as Fe^{++})
	Cu^{++} copper sulfate (20 ppm as Cu^{++})
Dyeing temperature :	80°C
Dyeing time :	60 minutes after alkali added

Assessment :

The difference in shade and yield between the samples dyed with and without addition of metallic ion was judged by means of the grey scale for assessing color change.

9. Effect of fixing agent :

Fixing agent :

(A) Polyethylene polyamine.	60°Cx20 minutes.
(B) Quaternary Ammonium salt.	60°Cx20 minutes.

The effect of fixing agent is measured by the following conditions :

Depth of shade :	3.0% o.w.f.
Fixing agent :	2.0% o.w.f.
Fixing temperature :	60°C
Fixing time :	20 minutes.

Assessment :

The difference in shade between the dyed samples with and without fixing was judged by means of grey scale for assessing color change.

10. Effect of finishing resin :

Finishing resin :

(A) Melamine resin.
(B) Glyoxal resin.

The effect of finishing agent was measured by the following conditions :

Depth of shade :	3.0% o.w.f.
Finishing agent :	40 g/l
Catalyst :	8 g/l
Finishing procedure	Padding → Drying → Baking.
Padding (pick-up) :	70%
Drying :	60°C x 5 minutes.
Baking :	160°C x 3 minutes.

Assessment :

The difference in shade between the dyed samples with and without finishing was judged by means of grey scale for assessing color change.

11. Exhaustion and fixation curves :

The degree of exhaustion of reactive dyes is considerably affected by various factors such as the form, scouring degree and crystallinity of materials to be dyed, and the degree of fibrous activity by mercerizing.

The degree of exhaustion and fixation of Evercion dyes, were measured on mercerized and unmercerzied cotton knits, respectively, under the following conditions as shown in graphs.

Material	:	Unmercerized cotton knit
Depth of shade	:	3.0% o.w.f.
Glauber's salt	:	60 g/l
Soda ash	:	20 g/l
Liquor ratio	:	1 : 10
Dyeing temperature	:	80°C
Dyeing time	:	60 minutes after alkali added

12. Effect of alkali :

Material	:	Unmercerized cotton knit
Depth of shade	:	3.0% o.w.f.
Glauber's salt	:	60 g/l
Alkali	:	Soda ash g/l : 5, 10, 15, 20*, 5, 5, 5, NaOH (38°Be') cc/l : -, -, -, -, 0.5, 1, 2,
Liquor ratio	:	1 : 10
Dyeing temperature	:	80°C
Dyeing time	:	60 minutes after alkali added

13. Effect of liquor ratio :

Material	:	Unmercerized cotton knit
Depth of shade	:	3.0% o.w.f.
Glauber's salt	:	60 g/l
Soda ash	:	20 g/l
Liquor ratio	:	1:5~1:120, 1:10 as standard
Dyeing temperature	:	80°C
Dyeing time	:	60 minutes after alkali added

14. Effect of temperature :

Material	:	Unmercerized cotton knit
Depth of shade	:	3.0% o.w.f.
Glauber's salt	:	60 g/l
Soda ash	:	20 g/l
Liquor ratio	:	1 : 10
Dyeing temperature	:	60, 70, 80*, 90, 98°C, 80°C as standard
Dyeing time	:	60 minutes after alkali added

15. Effect of Glauber's salt :




Material	:	Unmercerized cotton knit
Depth of shade	:	0.25%, 1%, 2%, 4% (o.w.f.)
Glauber's salt	:	10~80 g/l
Soda ash	:	20 g/l
Liquor ratio	:	1 : 10
Dyeing temperature	:	80°C
Dyeing time	:	60 minutes after alkali added

Everlight Chemical





TEST METHOD OF FASTNESS PROPERTIES

1. Fastness to washing	ISO 105 C10 Method B
	ISO 105 C10 Method C
	ISO 105 C10 Method D
	ISO 105 C06-C1S
	ISO 105 C06-C2S
	Marks & Spencer C4A
2. Fastness to water	ISO 105 E01
3. Fastness to hot water	ISO 105 E08
4. Fastness to sea water	ISO 105 E02
5. Fastness to post mercerizing	ISO 105 X04
6. Fastness to acid hydrolysis	1% Acteic acid solution for 30 min, 38°C
	X 6 hours
7. Fastness to perspiration	ISO 105 E04
8. Fastness to chlorinated water (20ppm)	ISO 105 E03
9. Fastness to Peroxide Bleaching	ISO 105 N02
10. Fastness to rubbing	ISO 105 X 12
11. Fastness to detergent light	Marks & Spencer C9A
12. Fastness to multi-washing (UK-TO)	Marks & Spencer C10A
13. Fastness to saliva	DIN 53160
14. Fastness to hot-pressing	ISO 105 X 11
15. Fastness to light	ISO 105 B02 & AATCC 16-3
16. Fastness to perspiration light	ISO 105 B07 & AATCC 125
17. Colorfastness to Nitrogen Oxides	ISO 105-G01

Evercion Dyes

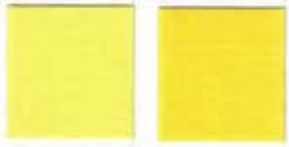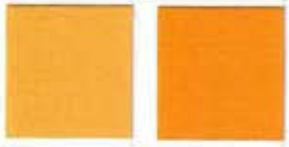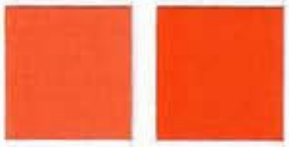頁 page	染料 dyes	1% 3%	染料特性	Characteristics
1	Yellow H-E6G		1. 耐氯水堅牢度佳 2. 耐日光堅牢度佳 3. 適合與Turq. H-A做艷綠色配色組合	1. Excellent chlorinated water fastness. 2. Unique lightfastness. 3. Suitable for color match of brilliant green with Turquoise H-A.
3	Yellow H-E4G		1. 適合與Turq. H-A配出鮮明的綠色 2. 浴比、染色溫度及鹽依存性低，有良好的染色再現性	1. Suitable for brilliant green in combination with Turquoise H-A. 2. Good reproducibility thanks for less dyeing parameters variation.
5	Yellow H-E4R		1. 黃色三原色，配色色域廣 2. 適合與Red H-E3B配成澄紅色 3. 高經濟型染料，可與Red H-E7B, Navy Blue H-ER配成棗紅色	1. Primary yellow, broad color range for color match. 2. Suitable for a component of salmon in combination with Red H-E3B. 3. Economical dye for the color match with Red H-E7B and Navy Blue H-ER of maroon.
7	Orange E-2G		1. 高得色率 2. 耐氯水堅牢度佳 3. 適合做鮮紅色或橘色，與Red H-E3B配色	1. High color yield. 2. Excellent chlorinated water fastness. 3. Suitable for color match of brilliant red and orange with Red H-E3B.
9	Orange H-ER		1. 高得色率，經濟型的艷橘色 2. 耐氯水堅牢度佳 3. 適合與Red H-E3B做配色組合	1. Economical brilliant orange with high color yield. 2. Excellent chlorinated water fastness. 3. Compatible with Red H-E3B.
11	Scarlet E-2G		1. 具有良好的色值、上色性的鮮深紅色，特別是染深色 2. 耐氯水堅牢度佳	1. High color yield, specially recommend for brilliant scalet with deep shades. 2. Excellent chlorinated water fastness.
13	Scarlet H-E3G		1. 得色率高，極佳的染深性 2. 適合與Red H-E3B或Yellow H-E4R做配色組合	1. High color yield and good build-up. 2. Compatible with Red H-E3B or Yellow H-E4R.
15	Red H-E3B		1. 得色率高，極具有經濟型的艷紅色 2. 可與Yellow H-E4R, Orange E-2G配成深紅色，亦可作為三原色中之紅色成份用	1. Economical brilliant red with high color yield. 2. Suitable for a component of red in combination with Yellow H-E4R or Orange E-2G for trichromatcic.
17	Red H-E7B		1. 紅色三原色，配色色域廣 2. 適合染鮮豔大紅色，特別是與Scarlet E-2G或Red H-E3B配色 3. 較不適合與Blue H-EGN搭配染極淺色	1. Primary red, broad color range for color match. 2. Suitable for brilliant red with good reproducibility in combination with Scarlet E-2G or Red H-E3B. 3. Not suitable for pale violet with Blue H-EGN.
19	Blue H-EGN		1. 極佳的染深色性 2. 耐日光堅牢度佳 3. 推薦使用在深寶藍色系 4. 對染極淺色較不適合	1. Excellent build-up. 2. Unique lightfastness. 3. Recommended for deep royal shades lightfastness. 4. Not suitable for pale shades.
21	Blue H-ERD		1. 色域廣之淺三原用藍色染料 2. 耐日光堅牢度佳，特別在淺色上 3. 良好的均染特性，適合淺中色染色	1. Primary light blue of trichromatic combination. 2. Excellent fastness to light, especially in pale shade. 3. Good leveling property, suitable for dyeing in pale to medium shade.

Evercion Dyes

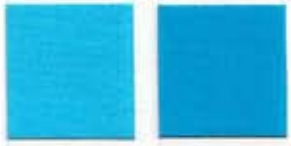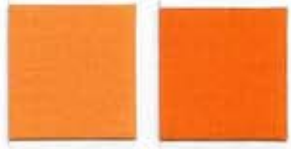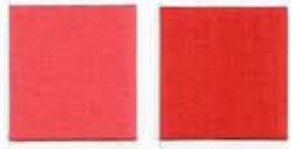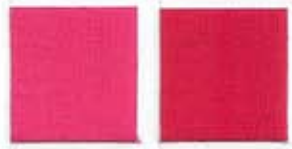頁 page	染料 dyes	1% 3%	染料特性	Characteristics
23	Navy Blue H-ER		1. 用途廣泛，具經濟性中、深濃度之紅味藍色 2. 具有良好搭配性，尤其中、深色組合與Red H-E7B或Red H-E3B和Yellow H-E4R搭配 3. 較不適合做淺色用	1. Economical & versatile heavy reddish navy. 2. Excellent combinability with Red H-E7B, Red H-E3B, Yellow H-E4R for medium to deep shade. 3. Not suitable for pale shades.
25	Turquoise H-A		1. 得色率高 2. 適合翠藍與艷綠色組合 3. 與Yellow H-E4G, H-E6G配色組合佳 4. 鹽類添加推薦使用芒硝	1. High color yield. 2. For brilliant blue, green and turq. shades. 3. Suitable for color match with Yellow H-E4G & Yellow H-E6G. 4. Sodium sulfate is recommended as a salt.
27	Green H-E4BD		1. 得色率高、極佳的染深性	1. High color yield and good build-up.
29	Yellow ESL		1. 得色率高、極佳的染深性 2. 黃色三原色，配色色域廣 3. 良好的均染性，容易溢流洗淨，適合與Red ESL和Navy ESL做組合配色 4. 耐氯水堅牢度佳	1. High color yield and good build-up. 2. Primary yellow, broad color range for color match. 3. Good leveling and easy washing off, especially compatible with Red ESL and Navy ESL for trichromatic. 4. Good in colorfastness to chlorinated water.
31	Deep Red ESL		1. 得色率高，極佳之染深性 2. 洗淨性良好	1. High color yield and good build-up. 2. Good washing off property.
33	Red ESL		1. 得色率高、極佳的染深性 2. 紅色三原色，配色色域廣 3. 良好的均染性，容易溢流洗淨，適合與Yellow ESL和Navy ESL做組合配色	1. High color yield and good build-up. 2. Primary red, broad color range for color match. 3. Good leveling and easy washing off, especially compatible with Yellow ESL and Navy ESL for trichromatic.
35	Crimson ESL		1. 得色率高、極佳之染深性 2. 紅色三原色，配色色域廣 3. 良好的均染性，容易溢流洗淨，耐氯水堅牢度佳 4. 適合與Yellow ESL和Navy ESL做中深色組合配色	1. High color yield and good build-up 2. Primary red, broad color range for color match 3. Good levelling, easy washing-off, excellent chlorinated water fastness 4. Exceptional compatibility with Yellow ESL and Navy ESL for medium to heavy shade
37	Navy ESL		1. 高得色率、極佳的染深性 2. 良好的均染性，容易溢流洗淨，適合與Yellow ESL和Red ESL做組合配色 3. 適合中深色組合用，不適合在淺色上推薦	1. High color yield and good build-up. 2. Good leveling and easy washing off, especially compatible with Yellow ESL and Red ESL for trichromatic. 3. Medium to heavy shades, suitable for not suitable in pale shades.


Everlight Chemical

Evercion Yellow H-E6G


Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		5
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water 水	70
	50°C Water 水 + 50 g/l Salt 鹽	50
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	G
	TL 84 Lamp	G
Metallic ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	4-5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5


吸盡固著曲線 Exhaustion & Fixation

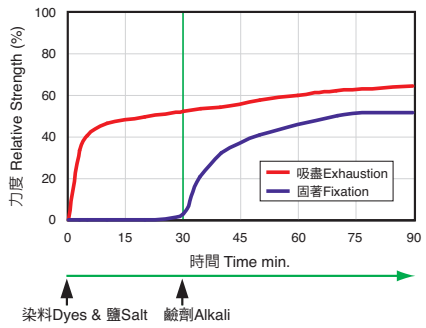

溫度依存性 Dependency on temperature

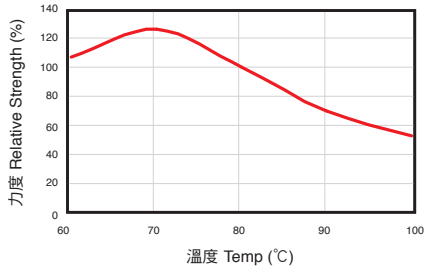

芒硝依存性 Dependency on Glauber's salt

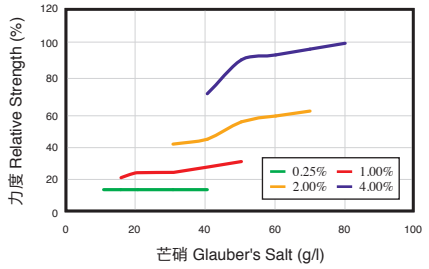

Evercion Yellow H-E6G

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		5	5	5	5	5	5	5
	ISO C06-C1S		5	5	5	5	5	5	5
	ISO C06-C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		3.0%	4-5	5	5	4-5	5	5	4-5
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	4-5
Sea Water 耐海水		3.0%	5	5	5	5	5	5	4-5
Post mercerizing 後絲光		3.0%	3-4R		4-5				
Acid hydrolysis 酸水解		3.0%	4	4-5	4	3	4-5	4-5	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	4-5	5	5	4-5
	Alkali 鹼		4-5	5	4-5	4-5	5	5	4-5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	4R
Peroxide Bleaching雙氧水漂白				3
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			4-5
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5R
		4 Hours after		4-5
	Wet 濕	Immediately	3.0%	4-5G
		4 Hours after		4
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	1	3
	0.3 %	2-3	3-4
	1.0 %	3	4-5
	3.0 %	4	5
	6.0 %	4-5	6

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	4-5	5
	Alkali鹼		4	5

浴比依存性 Dependency on Liquor ratio

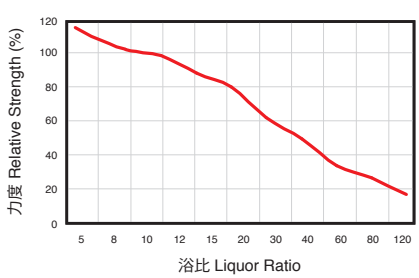

鹼依存性 Dependency on alkali

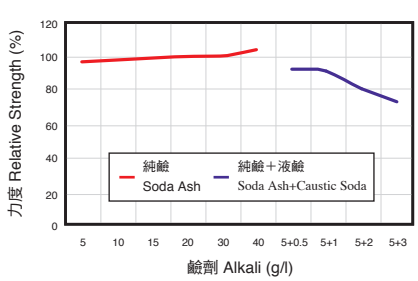


Everlight Chemical

Evercion Yellow H-E4G


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		5
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water 水	50
	50°C Water 水 + 50 g/l Salt 鹽	10 ↓
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4-5
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	B
	TL 84 Lamp	B
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5
	Cu^{2+} 銅離子	4RD
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5G
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5G
	Quaternary ammonium salt 四級銨鹽	5


吸盡固著曲線 Exhaustion & Fixation

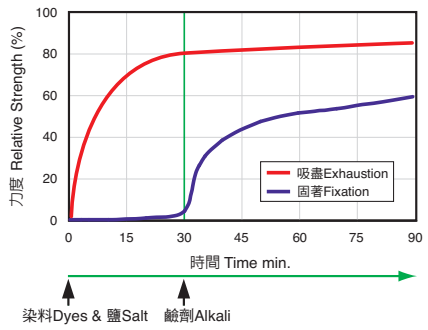

溫度依存性 Dependency on temperature

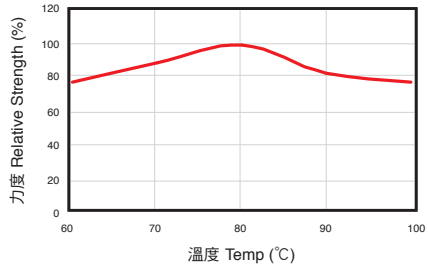

芒硝依存性 Dependency on Glauber's salt

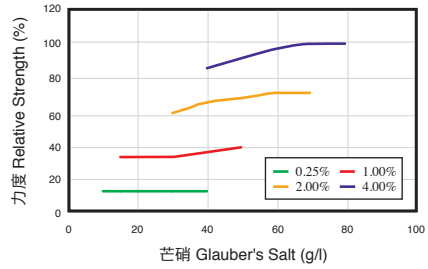

Evercion Yellow H-E4G

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		5	5	5	5	5	5	5
	ISO C06-C1S		5	5	5	5	5	5	5
	ISO C06-C2S		5	5	5	5	5	5	5
	M&S C4A		5	4-5	5	5	5	5	5
Water 耐水		3.0%	5	5	5	4-5	5	5	5
Hot Water 耐熱水		3.0%	5	4-5	5	5	5	5	5
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5
Post mercerizing 後絲光		3.0%	2-3R		4-5				
Acid hydrolysis 酸水解		3.0%	4R	4-5	4-5	5	5	5	4-5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	5	5	5	5
	Alkali 鹼		4-5	5	5	5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	3
Peroxide Bleaching雙氧水漂白				4R
Rubbing 耐摩擦	Dry 乾		3.0%	4-5
	Wet 濕			4
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	5
		4 Hours after		5
	Wet 濕	Immediately	3.0%	5
		4 Hours after		5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2-3	4
	0.3 %	3	4-5
	1.0 %	4	4-5
	3.0 %	4-5	5-6
	6.0 %	4-5	5-6

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	4-5	5-6
	Alkali鹼		3-4	5-6

浴比依存性 Dependency on Liquor ratio

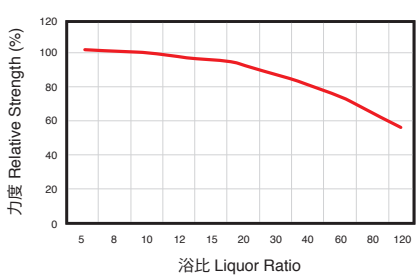

鹼依存性 Dependency on alkali

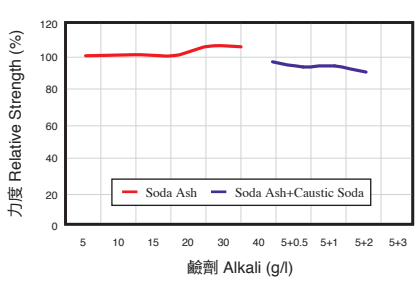


Evercion Yellow H-E4R


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4-5
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water 水	100
	50°C Water 水 + 50 g/l Salt 鹽	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2
	Dye Liquor 染浴	1
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	G
	TL 84 Lamp	G
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5D
	Cu^{2+} 銅離子	4-5G
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5R
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5R
	Quaternary ammonium salt 四級銨鹽	5


吸盡固著曲線 Exhaustion & Fixation

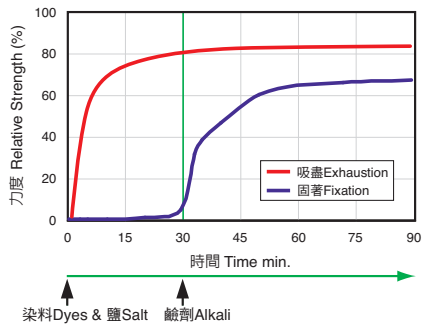

溫度依存性 Dependency on temperature

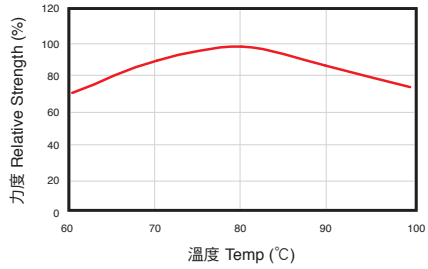

芒硝依存性 Dependency on Glauber's salt

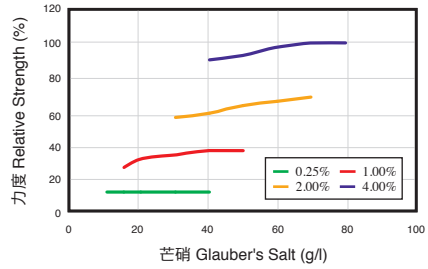

Evercion Yellow H-E4R

Everlight Chemical


Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Washing 耐水洗	ISO C10 B	3.0%	5	5	5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			3.0%	4
	ISO C10 C		5	5	5	5	5	5	5	Peroxide Bleaching雙氧水漂白				4
	ISO C10 D		5	5	5	5	5	5	5	Rubbing 耐摩擦	Dry 乾		3.0%	4-5
	ISO C06-C1S		5	5	5	5	5	5	5		Wet 濕			3-4
	ISO C06-C2S		5	5	5	5	5	5	5	M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
	M&S C4A		5	5	5	5	5	5	5				3.0%	>4-5
Water 耐水		3.0%	4-5	5	5	4	5	5	5	M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5	Saliva (DIN) 耐唾液			3.0%	4-5
Sea Water 耐海水		3.0%	4	5	4-5	5	5	5	5	Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4D
Post mercerizing 後絲光		3.0%	2-3R		4-5							4 Hours after		5
Acid hydrolysis 酸水解		3.0%	3-4	5	3	3	5	5	4		Wet 濕	Immediately	3.0%	4-5D
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4	4	5	5	5			4 Hours after		5
	Alkali 鹼		4-5	5	4	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5


Light Fastness 日光堅牢度

Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)	Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3-4	4	Perspiration Light 耐汗日光	Acid酸	3.0 %	4-5	5-6
	0.3 %	4	5		Alkali鹼		4	5-6
	1.0 %	4-5	5					
	3.0 %	>4-5	6					
	6.0 %	>4-5	6					

浴比依存性 Dependency on Liquor ratio

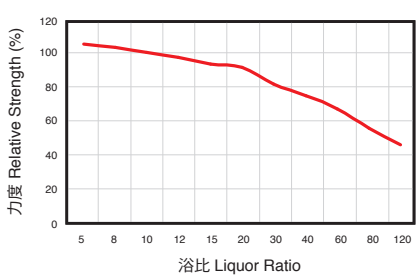

鹼依存性 Dependency on alkali

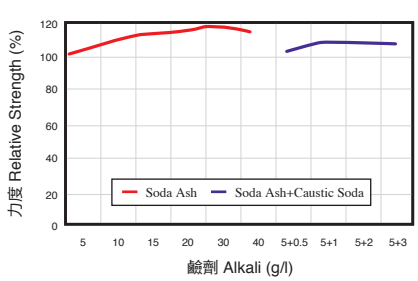


Evercion Orange E-2G


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		I
Substantivity 親和性		A
Migration 移染性		5
Washing off 洗淨性		4
Solubility g/l 溶解度	50°C Water 水	100
	50°C Water 水 + 50 g/l Salt 鹽	50
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3D
	Dye Liquor 染浴	3D
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	2-3RD
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5Y
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4Y
	Quaternary ammonium salt 四級銨鹽	4-5


吸盡固著曲線 Exhaustion & Fixation

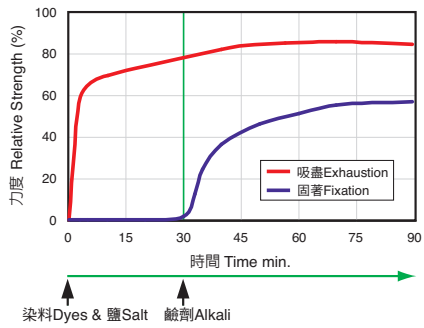

溫度依存性 Dependency on temperature

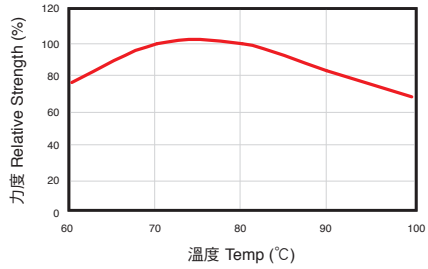

芒硝依存性 Dependency on Glauber's salt

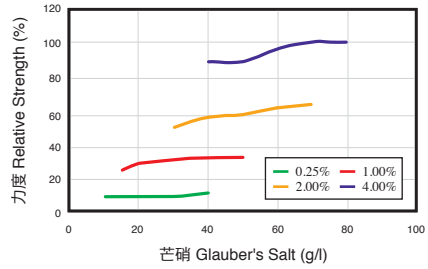

Evercion Orange E-2G

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4	5	5	5	5
	ISO C10 C		4	5	4	5	5	5	5
	ISO C10 D		4	5	3	5	5	5	5
	ISO C06-C1S		5	5	3-4	5	5	5	5
	ISO C06-C2S		5	5	3-4	5	5	5	5
	M&S C4A		5	5	3-4	5	5	5	5
Water 耐水		3.0%	4	5	4	4-5	5	5	4-5
Hot Water 耐熱水		3.0%	4-5	5	4-5	5	5	5	5
Sea Water 耐海水		3.0%	4	5	4-5	5	5	5	5
Post mercerizing 後絲光		3.0%	2Y		4-5				
Acid hydrolysis 酸水解		3.0%	4	5	4-5	4-5	5	5	4
Perspiration 耐汗	Acid 酸	3.0%	4	5	4	4	5	5	5
	Alkali 鹼		4-5	5	4	4-5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	4
Peroxide Bleaching雙氧水漂白				4
Rubbing 耐摩擦	Dry 乾		3.0%	4-5
	Wet 濕			3-4
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	2-3R
		4 Hours after		4-5
	Wet 濕	Immediately	3.0%	3R
		4 Hours after		5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	3
	0.3 %	2-3	3
	1.0 %	3	4-5
	3.0 %	4	5-6
	6.0 %	4	5-6

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	4	5-6
	Alkali鹼		4	5-6

浴比依存性 Dependency on Liquor ratio

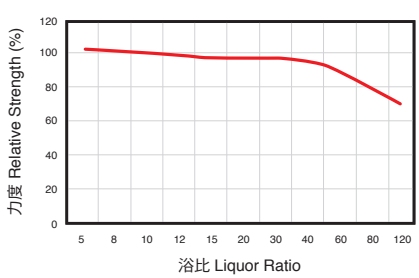

鹼依存性 Dependency on alkali

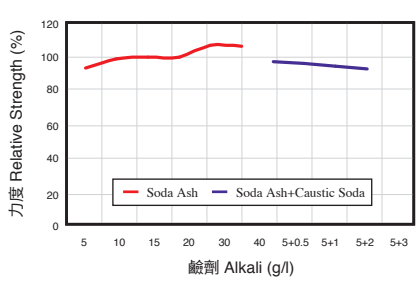


Evercion Orange H-ER


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4-5
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water 水	40
	50°C Water 水 + 50 g/l Salt 鹽	10
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3D
	Dye Liquor 染浴	2-3D
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	B
	TL 84 Lamp	G
Metallic ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	2-3RD
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5


吸盡固著曲線 Exhaustion & Fixation

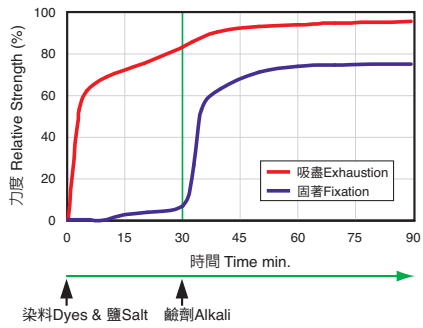

溫度依存性 Dependency on temperature

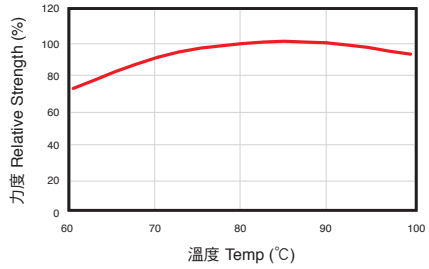

芒硝依存性 Dependency on Glauber's salt

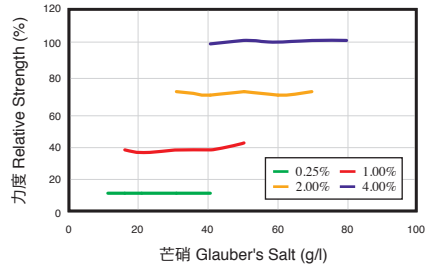

Evercion Orange H-ER

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	3-4	5	5	5	5
	ISO C10 C		4-5	4-5	4	5	5	5	5
	ISO C10 D		4-5	5	3-4	5	5	5	5
	ISO C06-C1S		4-5	5	4	5	5	5	5
	ISO C06-C2S		4-5	5	4	5	5	5	5
	M&S C4A		4-5	5	4	5	5	5	5
Water 耐水		3.0%	4-5	5	4	3	4-5	4-5	4-5
Hot Water 耐熱水		3.0%	5	5	4	5	5	5	5
Sea Water 耐海水		3.0%	4-5Y	5	4-5	5	5	5	5
Post mercerizing 後絲光		3.0%	3Y		4				
Acid hydrolysis 酸水解		3.0%	3-4R	4-5	4	3-4	5	5	3-4
Perspiration 耐汗	Acid 酸	3.0%	3-4Y	5	3-4	3-4	5	5	4-5
	Alkali 鹼		4Y	5	3-4	3-4	5	5	4-5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	4
Peroxide Bleaching雙氧水漂白				3-4
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			3
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3RD
		4 Hours after		4-5D
	Wet 濕	Immediately	3.0%	2-3D
		4 Hours after		4-5D
Colorfastness to Nitrogen Oxides 氮體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	1	2-3
	0.3 %	1-2	3
	1.0 %	2-3	3-4
	3.0 %	3-4	4
	6.0 %	3-4	4-5

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	3-4	4
	Alkali鹼		2-3	3-4

浴比依存性 Dependency on Liquor ratio

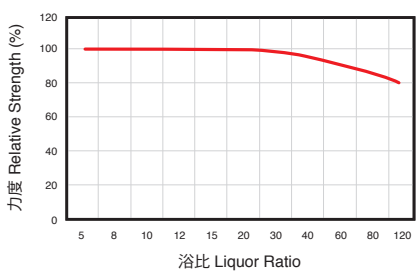

鹼依存性 Dependency on alkali

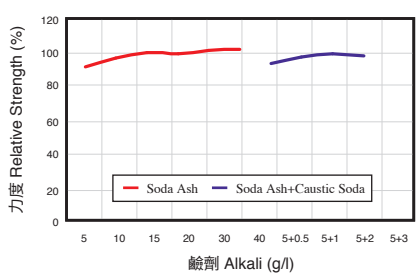


Evercion Scarlet E-2G


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		Ⅲ
Substantivity 親和性		A
Migration 移染性		4
Washing off 洗淨性		2-3
Solubility g/l 溶解度	50°C Water 水	90
	50°C Water 水 + 50 g/l Salt 鹽	10
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	3-4
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4G
	Cu^{2+} 銅離子	2-3B
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5


吸盡固著曲線 Exhaustion & Fixation

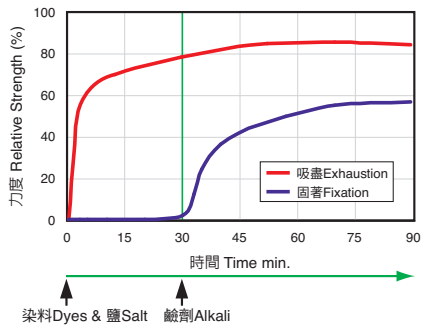

溫度依存性 Dependency on temperature

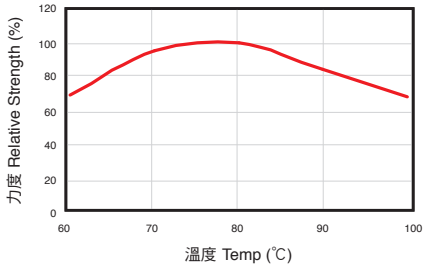

芒硝依存性 Dependency on Glauber's salt

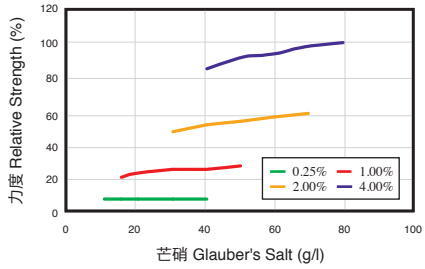

Evercion Scarlet E-2G

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4	5	5	5	5
	ISO C10 C		4	5	3-4	5	5	5	5
	ISO C10 D		4	5	3	5	5	5	3
	ISO C06-C1S		4-5	5	4	5	5	5	5
	ISO C06-C2S		4-5	5	4	5	5	5	5
	M&S C4A		4-5	5	4	5	5	5	5
Water 耐水		3.0%	4-5	5	5	4-5	5	5	4-5
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	4-5
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	4-5
Post mercerizing 後絲光		3.0%	3R		5				
Acid hydrolysis 酸水解		3.0%	4-5	5	4	5	5	4	5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4	5	5	5	5
	Alkali 鹼		4-5	4-5	4	5	5	4-5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	4-5
Peroxide Bleaching雙氧水漂白				4
Rubbing 耐摩擦	Dry 乾		3.0%	4-5
	Wet 濕			2-3
M&S C9A 濕日光 (detergent Light)			0.3%	4-5
			3.0%	4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3RD
		4 Hours after		5
	Wet 濕	Immediately	3.0%	4RD
		4 Hours after		5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	3-4
	0.3 %	2-3	3-4
	1.0 %	3-4	4-5
	3.0 %	4	5
	6.0 %	4	5-6

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	3	5
	Alkali鹼		3	5

浴比依存性 Dependency on Liquor ratio

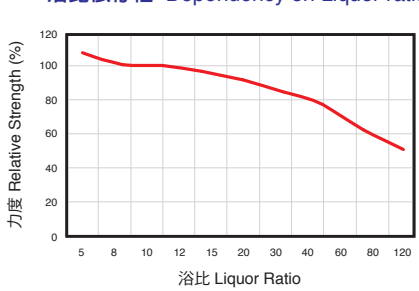

鹼依存性 Dependency on alkali

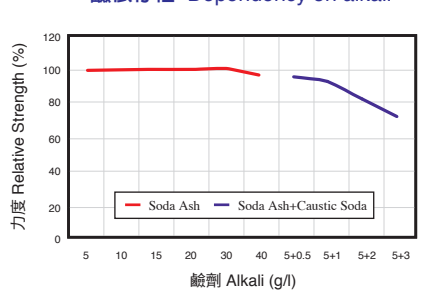


Evercion Scarlet H-E3G


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		5
Washing off 洗淨性		2-3
Solubility g/l 溶解度	50°C Water 水	100
	50°C Water 水 + 50 g/l Salt 鹽	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	B
	TL 84 Lamp	G
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5Y
	Cu^{2+} 銅離子	3-4Y
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5


吸盡固著曲線 Exhaustion & Fixation

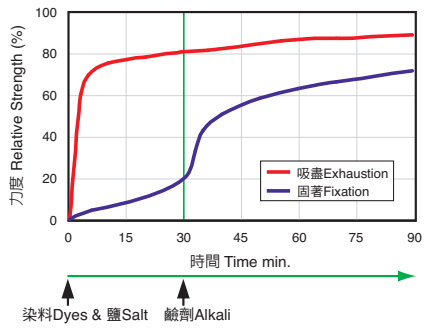

溫度依存性 Dependency on temperature

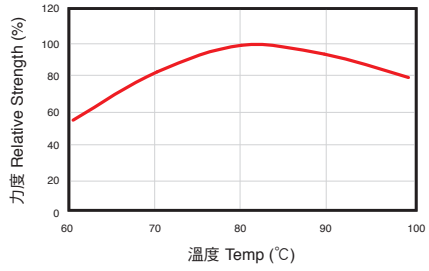

芒硝依存性 Dependency on Glauber's salt

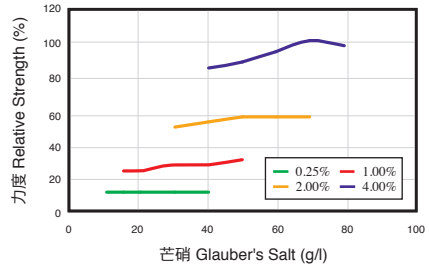

Evercion Scarlet H-E3G

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	5	5	4-5	5	5	5	5
	ISO C10 C		5	5	4-5	5	5	5	5
	ISO C10 D		5	5	4	5	5	5	5
	ISO C06-C1S		5	5	4	5	5	5	5
	ISO C06-C2S		5	5	4	5	5	5	5
	M&S C4A		5	5	4	5	5	5	5
Water 耐水		3.0%	5	5	3-4	3-4	5	5	4-5
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5
Sea Water 耐海水		3.0%	4	5	4-5	5	5	5	5
Post mercerizing 後絲光		3.0%	2-3Y		4-5				
Acid hydrolysis 酸水解		3.0%	3-4	4-5	3	3-4	5	5	3-4
Perspiration 耐汗	Acid 酸	3.0%	4-5	4-5	3-4	3-4	5	4-5	4-5
	Alkali 鹼		4-5	5	4-5	5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	3-4
Peroxide Bleaching雙氧水漂白				2
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			3
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3RD
		4 Hours after		5
	Wet 濕	Immediately	3.0%	4RD
		4 Hours after		5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	3
	0.3 %	2-3	3-4
	1.0 %	3-4	4
	3.0 %	4	4-5
	6.0 %	4	4-5

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	3	4-5
	Alkali鹼		3	4-5

浴比依存性 Dependency on Liquor ratio

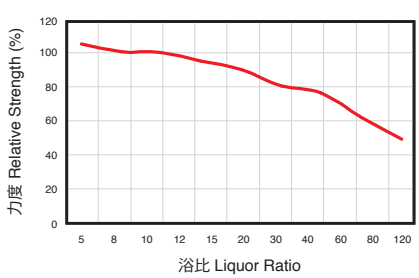

鹼依存性 Dependency on alkali

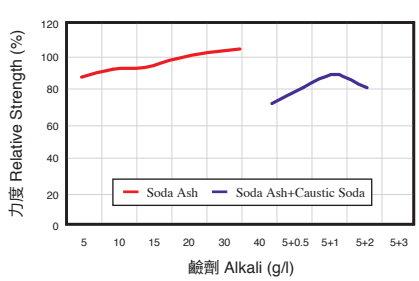


Evercion Red H-E3B


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4-5
Washing off 洗淨性		2-3
Solubility g/l 溶解度	50°C Water 水	140
	50°C Water 水 + 50 g/l Salt 鹽	140
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4
	Dye Liquor 染浴	3-4
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL 84 Lamp	Y
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5Y
	Cu^{2+} 銅離子	3-4B
Resin finishing 樹脂加工	Melamine 三聚氰胺	4BD
	Glyoxal 乙二醛	4B
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4BD
	Quaternary ammonium salt 四級銨鹽	4-5B


吸盡固著曲線 Exhaustion & Fixation

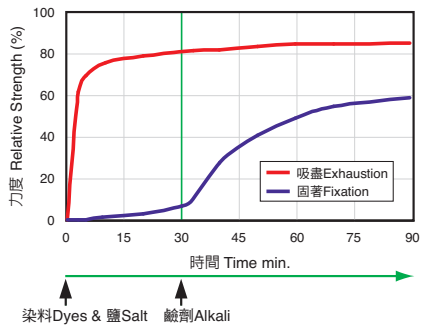

溫度依存性 Dependency on temperature

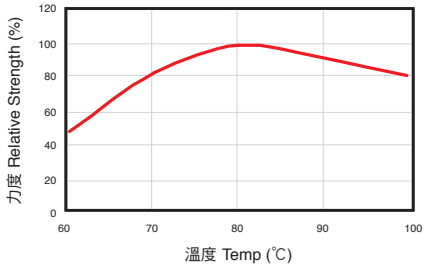

芒硝依存性 Dependency on Glauber's salt

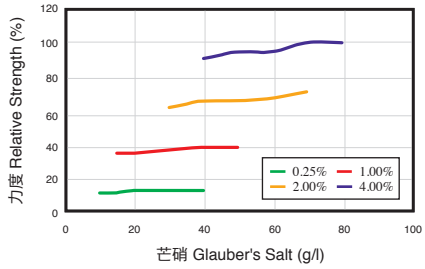

Evercion Red H-E3B

Everlight Chemical


Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5	Chlorinated Water耐氯水(20ppm)			3.0%	3B
	ISO C10 C		4-5	4	4	5	5	5	5	Peroxide Bleaching雙氧水漂白				2-3
	ISO C10 D		4-5	4-5	3	5	5	5	5	Rubbing 耐摩擦	Dry 乾		3.0%	5
	ISO C06-C1S		5	5	4-5	5	5	5	5		Wet 濕			2-3
	ISO C06-C2S		5	5	4-5	5	5	5	5	M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
	M&S C4A		5	5	4-5	5	5	5	5				3.0%	>4-5
Water 耐水		3.0%	5	5	4	3-4	5	4-5	4-5	M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Hot Water 耐熱水		3.0%	4-5	4-5	4	4-5	4-5	4-5	4-5	Saliva (DIN) 耐唾液			3.0%	4-5
Sea Water 耐海水		3.0%	3-4B	5	4-5	5	5	5	5	Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	2-3B
Post mercerizing 後絲光		3.0%	2Y		4							4 Hours after		4-5
Acid hydrolysis 酸水解		3.0%	3-4	4-5	3	3	4-5	4	3-4		Wet 濕	Immediately	3.0%	4-5
Perspiration 耐汗	Acid 酸	3.0%	4	5	4-5	4-5	5	5	5			4 Hours after		5
	Alkali 鹼		4	5	4-5	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5


Light Fastness 日光堅牢度

Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)	Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	3-4	Perspiration Light 耐汗日光	Acid酸	3.0 %	3	4-5
	0.3 %	2-3	4		Alkali鹼		3	4-5
	1.0 %	3	4-5					
	3.0 %	3-4	4-5					
	6.0 %	4	5					

浴比依存性 Dependency on Liquor ratio

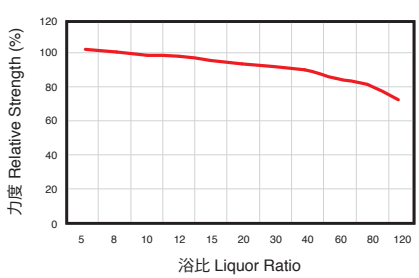

鹼依存性 Dependency on alkali

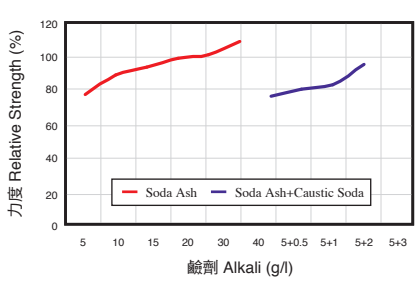


Evercion Red H-E7B


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water 水	150
	50°C Water 水 + 50 g/l Salt 鹽	150
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	3-4
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL 84 Lamp	B
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5
	Cu^{2+} 銅離子	3B
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3B
	Quaternary ammonium salt 四級銨鹽	4-5B


吸盡固著曲線 Exhaustion & Fixation

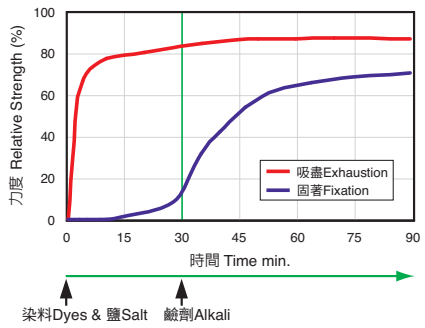

溫度依存性 Dependency on temperature

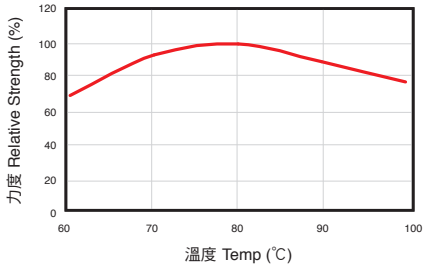

芒硝依存性 Dependency on Glauber's salt

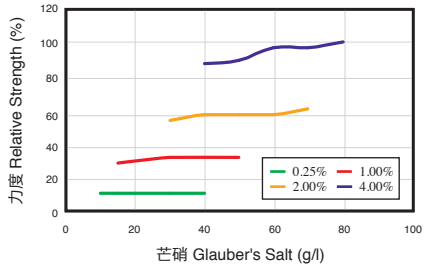

Evercion Red H-E7B

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	3-4	5	5	5	5
	ISO C10 C		4-5	4-5	3	5	5	4-5	5
	ISO C10 D		4-5	4-5	3	5	5	4-5	5
	ISO C06-C1S		5	5	4	5	5	5	5
	ISO C06-C2S		5	5	4-5	5	5	5	5
	M&S C4A		5	5	4-5	5	5	5	5
Water 耐水		3.0%	5	4-5	3	2-3	5	4-5	3-4
Hot Water 耐熱水		3.0%	5	4-5	4-5	5	5	5	5
Sea Water 耐海水		3.0%	4B	5	4-5	5	5	5	5
Post mercerizing 後絲光		3.0%	2Y		4				
Acid hydrolysis 酸水解		3.0%	4	4	3-4	3	4	4-5	3-4
Perspiration 耐汗	Acid 酸	3.0%	4B	5	3	3-4	5	4	4-5
	Alkali 鹼		4-5	5	4	5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	3-4B
Peroxide Bleaching雙氧水漂白				4
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			2-3
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	2BD
		4 Hours after		4-5
	Wet 濕	Immediately	3.0%	2-3BD
		4 Hours after		4-5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	1-2	3-4
	0.3 %	2	3-4
	1.0 %	2-3	4
	3.0 %	3-4	4-5
	6.0 %	4	5

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	3-4	4-5
	Alkali鹼		3-4	4-5

浴比依存性 Dependency on Liquor ratio

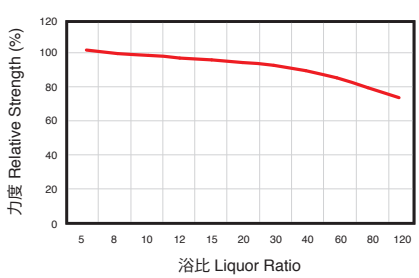

鹼依存性 Dependency on alkali

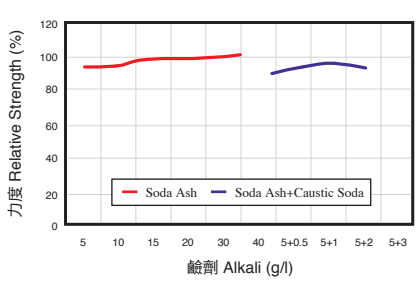


Evercion Blue H-EGN


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		5
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water 水	100
	50°C Water 水 + 50 g/l Salt 鹽	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2
	Dye Liquor 染浴	2
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5G
	Cu^{2+} 銅離子	5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5Y
	Glyoxal 乙二醛	4-5Y
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4Y
	Quaternary ammonium salt 四級銨鹽	5


吸盡固著曲線 Exhaustion & Fixation

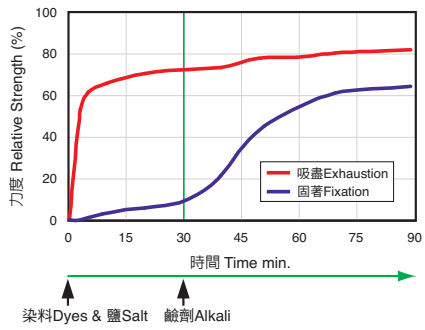

溫度依存性 Dependency on temperature

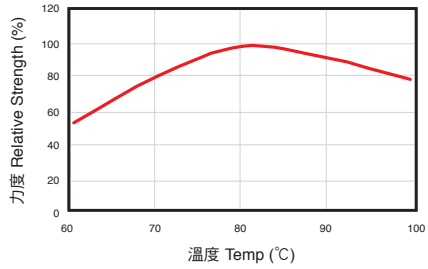

芒硝依存性 Dependency on Glauber's salt

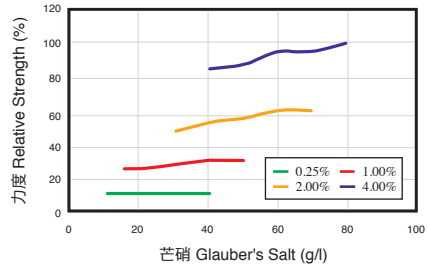

Evercion Blue H-EGN

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	5	5	4-5	5	5	5	5
	ISO C10 C		5	5	4-5	5	5	5	5
	ISO C10 D		4-5	5	3-4	5	5	5	3
	ISO C06-C1S		5	5	4	5	5	5	5
	ISO C06-C2S		5	5	4	5	5	5	5
	M&S C4A		5	5	4	5	5	5	5
Water 耐水		3.0%	5	5	3-4	3	5	5	4
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5
Post mercerizing 後絲光		3.0%	2-3R		4-5				
Acid hydrolysis 酸水解		3.0%	3	4-5	4	4	4-5	4-5	4
Perspiration 耐汗	Acid 酸	3.0%	4	5	3-4	4	5	5	4
	Alkali 鹼		4	5	3-4	4-5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	1
Peroxide Bleaching雙氧水漂白				3-4
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			3
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4D
		4 Hours after		5
	Wet 濕	Immediately	3.0%	4
		4 Hours after		5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	3

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3-4	4-5
	0.3 %	4	5-6
	1.0 %	4	5-6
	3.0 %	4-5	6
	6.0 %	4-5	>6

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	4-5	5
	Alkali鹼		4-5	5

浴比依存性 Dependency on Liquor ratio

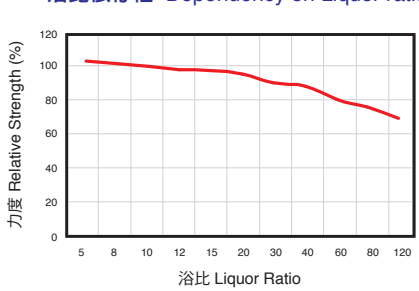

鹼依存性 Dependency on alkali

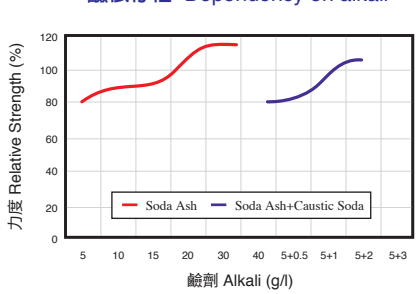


Evercion Blue H-ERD


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		5
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water 水	100
	50°C Water 水 + 50 g/l Salt 鹽	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	2-3YD
	Dye Liquor 染浴	2-3YD
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5G
	Cu^{2+} 銅離子	4-5G
Resin finishing 樹脂加工	Melamine 三聚氰胺	4Y
	Glyoxal 乙二醛	4-5G
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5Y
	Quaternary ammonium salt 四級銨鹽	4G


吸盡固著曲線 Exhaustion & Fixation

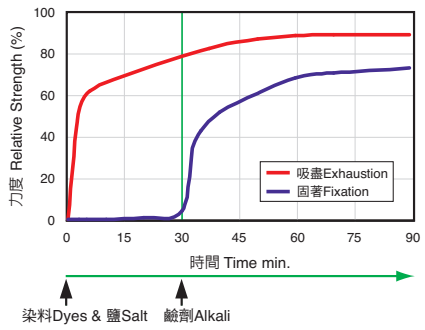

溫度依存性 Dependency on temperature

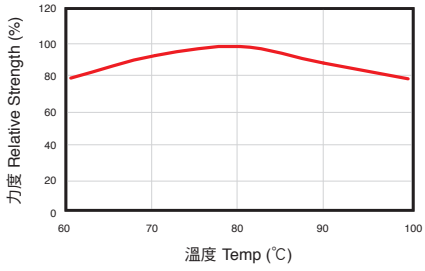

芒硝依存性 Dependency on Glauber's salt

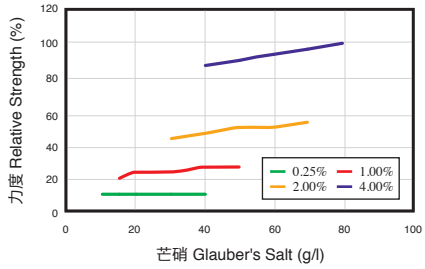

Evercion Blue H-ERD

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	5	4-5	3-4	5	5	5	5
	ISO C10 C		4-5	4-5	3-4	5	5	5	5
	ISO C10 D		4-5	4-5	3	5	5	5	5
	ISO C06-C1S		4-5	5	3-4	5	5	5	5
	ISO C06-C2S		4-5	5	4	5	5	5	5
	M&S C4A		4-5	5	4	5	5	5	5
Water 耐水		3.0%	5	5	3-4	3	5	5	5
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5
Post mercerizing 後絲光		3.0%	2-3R		4-5				
Acid hydrolysis 酸水解		3.0%	3	4-5	4	4	4-5	4-5	4
Perspiration 耐汗	Acid 酸	3.0%	4	5	3-4	4	5	5	4
	Alkali 鹼		4	5	3-4	4-5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	1
Peroxide Bleaching雙氧水漂白				3-4
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			3
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4D
		4 Hours after		5
	Wet 濕	Immediately	3.0%	4
		4 Hours after		5
Colorfastness to Nitrogen Oxides 氮體變褪色			1.0%	4

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	3	4-5
	0.3 %	3-4	5-6
	1.0 %	3-4	5-6
	3.0 %	4	6
	6.0 %	4	>6

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	3-4	5
	Alkali鹼		3	5

浴比依存性 Dependency on Liquor ratio

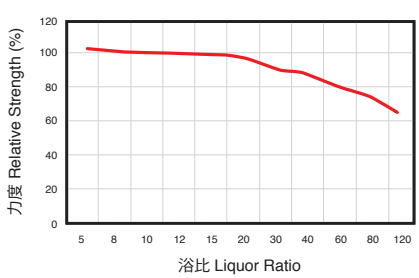

鹼依存性 Dependency on alkali

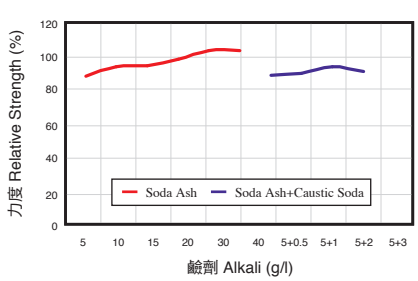


Evercion Navy Blue H-ER


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		4-5
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water 水	100
	50°C Water 水 + 50 g/l Salt 鹽	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	YD
	TL 84 Lamp	YD
Metallic ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4Y
	Glyoxal 乙二醛	4R
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4Y
	Quaternary ammonium salt 四級銨鹽	5


吸盡固著曲線 Exhaustion & Fixation

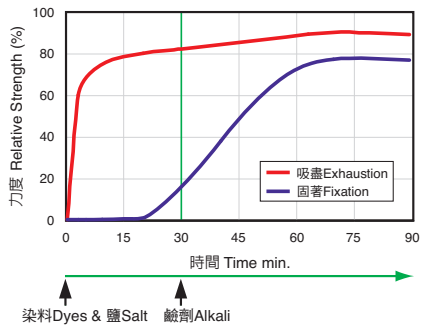

溫度依存性 Dependency on temperature

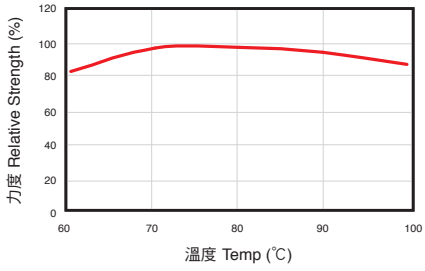

芒硝依存性 Dependency on Glauber's salt

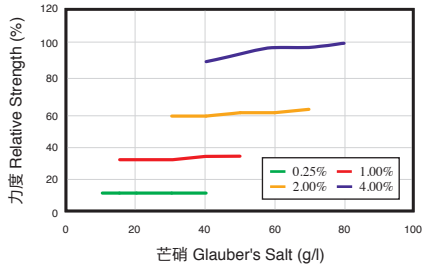

Evercion Navy Blue H-ER

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4	5	5	5	5
	ISO C10 C		4-5	5	4	5	5	5	5
	ISO C10 D		4-5	5	3-4	5	5	5	5
	ISO C06-C1S		4-5	5	4	5	5	5	5
	ISO C06-C2S		4-5	5	4	5	5	5	5
	M&S C4A		4-5	5	4	5	5	5	5
Water 耐水		3.0%	4-5	5	4	3-4	5	5	5
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5
Post mercerizing 後絲光		3.0%	2R		4-5				
Acid hydrolysis 酸水解		3.0%	4-5	5	4-5	5	5	5	4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	3-4	5	5	5
	Alkali 鹼		4-5	5	4-5	5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	4-5
Peroxide Bleaching雙氧水漂白				4-5
Rubbing 耐摩擦	Dry 乾		3.0%	4-5
	Wet 濕			2-3
M&S C9A 濕日光 (detergent Light)			0.3%	4-5
			3.0%	4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	5
		4 Hours after		5
	Wet 濕	Immediately	3.0%	5
		4 Hours after		5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	3
	0.3 %	2-3	3-4
	1.0 %	3	3-4
	3.0 %	3-4	4-5
	6.0 %	4	5-6

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	2-3	4
	Alkali鹼		2-3	4

浴比依存性 Dependency on Liquor ratio

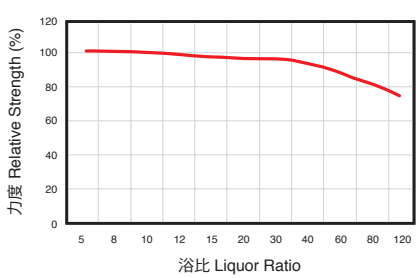

鹼依存性 Dependency on alkali

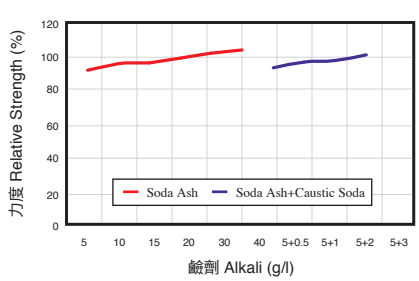


Evercion Turquoise H-A


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		5
Washing off 洗淨性		3-4
Solubility g/l 溶解度	50°C Water 水	100
	50°C Water 水 + 50 g/l Salt 鹽	10 ↓
High temp. Dyeing 高溫染色性	Dyed fabric 色布	5
	Dye Liquor 染浴	5
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	RD
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	5
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5Y
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4Y
	Quaternary ammonium salt 四級銨鹽	4-5


吸盡固著曲線 Exhaustion & Fixation

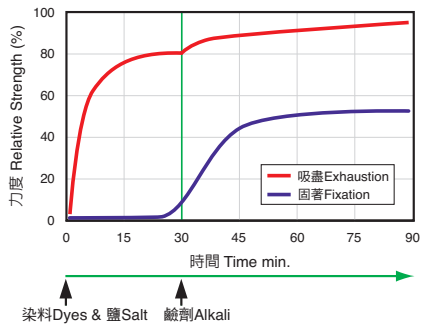

溫度依存性 Dependency on temperature

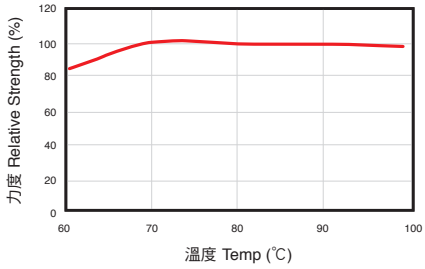

芒硝依存性 Dependency on Glauber's salt

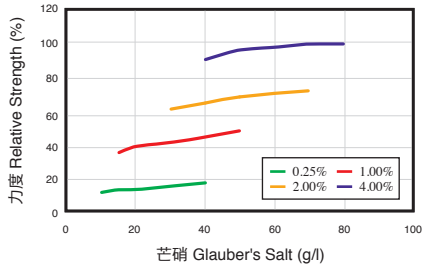

Evercion Turquoise H-A

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	5	5	3-4	5	5	4	5
	ISO C10 C		5	5	3-4	5	5	4	5
	ISO C10 D		4	5	3	5	5	4-5	5
	ISO C06-C1S		4-5	5	3-4	5	5	4	5
	ISO C06-C2S		4-5	5	3-4	5	5	4-5	5
	M&S C4A		4-5	5	3-4	5	5	4	5
Water 耐水		3.0%	5	5	4-5	3-4	4	4	4
Hot Water 耐熱水		3.0%	5	4-5	5	5	5	5	5
Sea Water 耐海水		3.0%	5	5	5	5	5	5	5
Post mercerizing 後絲光		3.0%	3-4G		3				
Acid hydrolysis 酸水解		3.0%	3	4-5	5	5	5	5	4
Perspiration 耐汗	Acid 酸	3.0%	5	5	4-5	4-5	5	5	4-5
	Alkali 鹼		4-5	5	4-5	5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	3
Peroxide Bleaching雙氧水漂白				1
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			2-3
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4-5Y
		4 Hours after		5
	Wet 濕	Immediately	3.0%	4-5Y
		4 Hours after		5
Colorfastness to Nitrogen Oxides 氮體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	3-4
	0.3 %	2-3	4-5
	1.0 %	3	4-5
	3.0 %	3-4	5
	6.0 %	4	5

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	2	4
	Alkali鹼		2	4

浴比依存性 Dependency on Liquor ratio

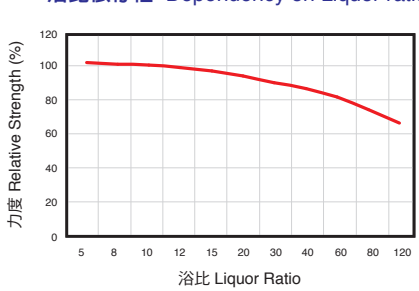

鹼依存性 Dependency on alkali

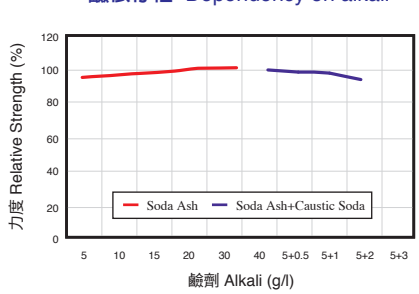


Evercion Green H-E4BD


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		3-4
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water 水	120
	50°C Water 水 + 50 g/l Salt 鹽	120
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4-5
	Dye Liquor 染浴	4
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	RD
	TL 84 Lamp	RD
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5Y
	Cu^{2+} 銅離子	4D
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5B
	Glyoxal 乙二醛	4-5B
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3-4Y
	Quaternary ammonium salt 四級銨鹽	4-5


吸盡固著曲線 Exhaustion & Fixation

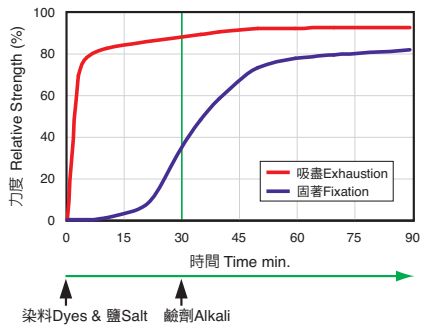

溫度依存性 Dependency on temperature

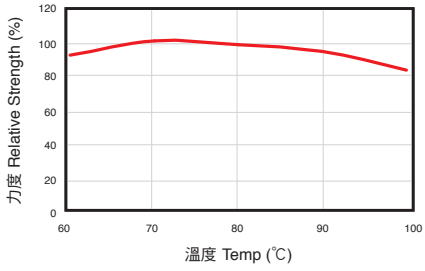

芒硝依存性 Dependency on Glauber's salt

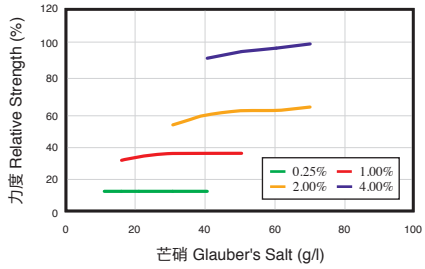

Evercion Green H-E4BD

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	5	5	4	5	5	5	5
	ISO C10 C		5	5	4	5	5	5	5
	ISO C10 D		5	5	4	5	5	5	5
	ISO C06-C1S		5	5	4	5	5	5	5
	ISO C06-C2S		5	5	4	5	5	5	5
	M&S C4A		5	5	4	5	5	5	5
Water 耐水		3.0%	4-5	5	3-4	3	5	5	3-4
Hot Water 耐熱水		3.0%	5	5	4-5	5	5	5	5
Sea Water 耐海水		3.0%	4	5	4-5	5	5	5	5
Post mercerizing 後絲光		3.0%	2-3G		4-5				
Acid hydrolysis 酸水解		3.0%	4	5	4-5	5	5	5	4-5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	2-3	3	3	5	5
	Alkali 鹼		4-5	5	3	5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	2
Peroxide Bleaching雙氧水漂白				4
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			2-3
M&S C9A 濕日光 (detergent Light)			0.3%	4
			3.0%	4
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	2-3RD
		4 Hours after		5
	Wet 濕	Immediately	3.0%	3RD
		4 Hours after		5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	1	3
	0.3 %	1-2	3
	1.0 %	2	3-4
	3.0 %	2-3	4
	6.0 %	3	4-5

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	2	4
	Alkali鹼		2	3-4

浴比依存性 Dependency on Liquor ratio

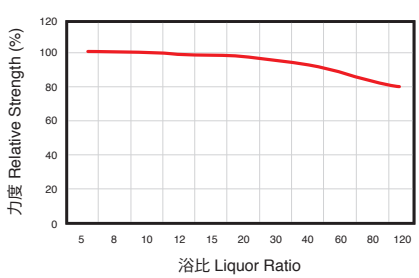

鹼依存性 Dependency on alkali

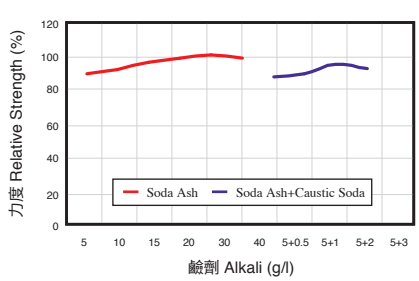


Evercion Yellow ESL


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		Ⅲ
Substantivity 親和性		A
Migration 移染性		4
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water 水	100
	50°C Water 水 + 50 g/l Salt 鹽	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	3-4
	Dye Liquor 染浴	3-4
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	G
	TL 84 Lamp	G
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5
	Cu^{2+} 銅離子	4
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	5


吸盡固著曲線 Exhaustion & Fixation

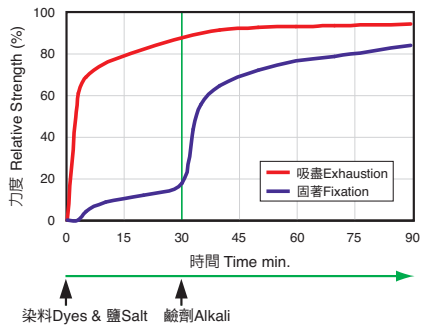

溫度依存性 Dependency on temperature

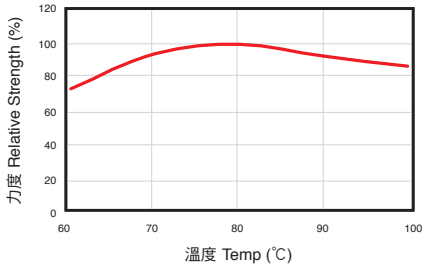

芒硝依存性 Dependency on Glauber's salt

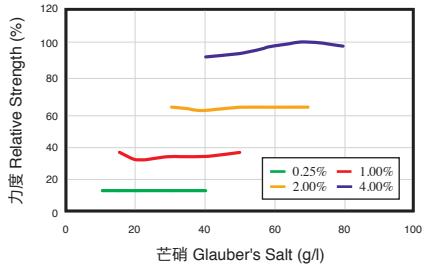

Evercion Yellow ESL

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	5	5	4-5	5	5	5	5
	ISO C10 C		5	5	4-5	5	5	5	5
	ISO C10 D		5	5	4	5	5	5	5
	ISO C06-C1S		5	5	4-5	5	5	5	5
	ISO C06-C2S		5	5	4-5	5	5	5	5
	M&S C4A		5	5	4-5	5	5	5	5
Water 耐水		3.0%	5	5	4	4	5	5	5
Hot Water 耐熱水		3.0%	5	5	4-5	5	5	5	5
Sea Water 耐海水		3.0%	5	5	4-5	5	5	5	5
Post mercerizing 後絲光		3.0%	2-3		4-5				
Acid hydrolysis 酸水解		3.0%	4-5	5	4	4-5	5	5	5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	4-5	5	5	5
	Alkali 鹼		4-5	5	4-5	5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	4Y
Peroxide Bleaching雙氧水漂白				4-5
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			3-4
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	4
		4 Hours after		5
	Wet 濕	Immediately	3.0%	4-5
		4 Hours after		5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	4	5
	0.3 %	4-5	5
	1.0 %	4-5	5
	3.0 %	4-5	5-6
	6.0 %	4-5	5-6

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	4-5	5-6
	Alkali鹼		4-5	5-6

浴比依存性 Dependency on Liquor ratio

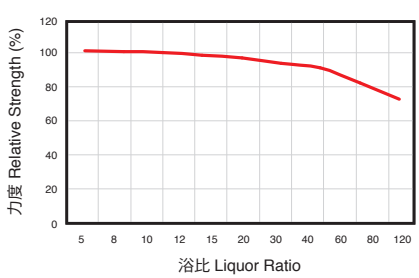

鹼依存性 Dependency on alkali

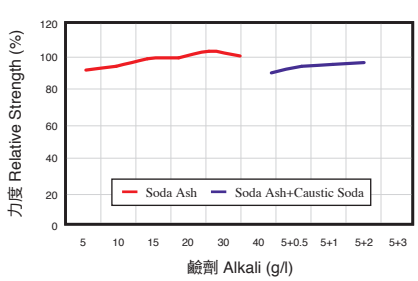


Evercion Deep Red ESL


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		II
Substantivity 親和性		A
Migration 移染性		2-3
Washing off 洗淨性		2-3
Solubility g/l 溶解度	50°C Water 水	100
	50°C Water 水 + 50 g/l Salt 鹽	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	3-4
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	B
	TL 84 Lamp	B
Metallic ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	1
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4-5
	Quaternary ammonium salt 四級銨鹽	4-5


吸盡固著曲線 Exhaustion & Fixation

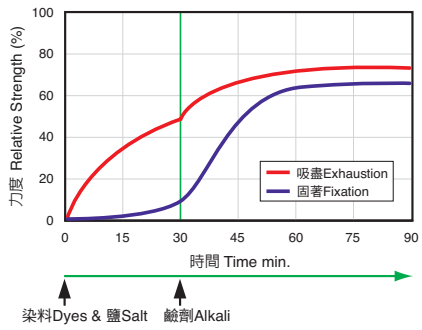

溫度依存性 Dependency on temperature

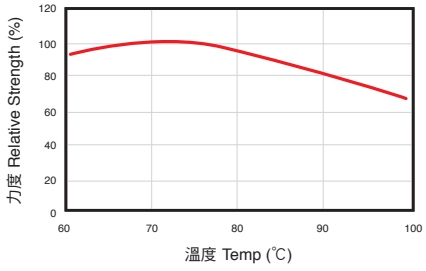

芒硝依存性 Dependency on Glauber's salt

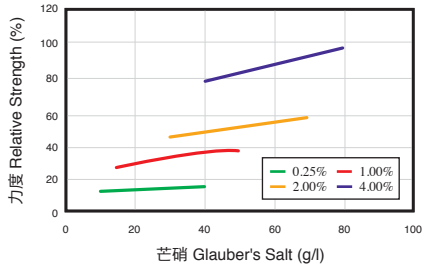

Evercion Deep Red ESL

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	5	5	4-5	5	5	5	5
	ISO C10 C		5	5	4-5	5	5	4-5	5
	ISO C10 D		5	5	5	5	5	5	5
	ISO C06-C1S		5	5	4-5	5	5	5	5
	ISO C06-C2S		5	5	4-5	5	5	4-5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		3.0%	5	5	4	4	5	4-5	5
Hot Water 耐熱水		3.0%	5	5	5	5	5	5	5
Sea Water 耐海水		3.0%	5	5	4-5	5	5	5	5
Post mercerizing 後絲光		3.0%	3-4R(Y)		4				
Acid hydrolysis 酸水解		3.0%	4-5	4-5	2	1-2	4-5	4-5	3-4
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	4-5	5	5	5
	Alkali 鹼		5	5	5	5	5	5	5


Fastness 牢度 \ Evaluation 評級			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	4(B)
Peroxide Bleaching雙氧水漂白				4
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			3
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	1-2G
		4 Hours after		4-5
	Wet 濕	Immediately	3.0%	3G
		4 Hours after		4-5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	3
	0.3 %	2	3-4
	1.0 %	3	4-5
	3.0 %	3-4	5
	6.0 %	4	5-6

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	3-4	5
	Alkali鹼		3	4-5

浴比依存性 Dependency on Liquor ratio

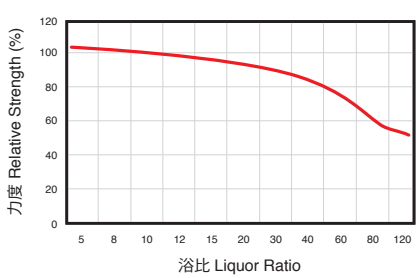

鹼依存性 Dependency on alkali

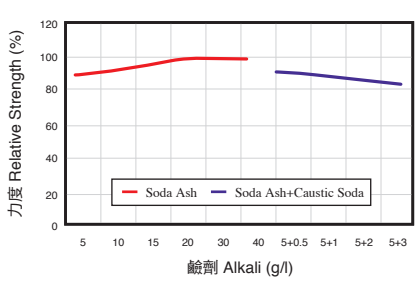


Evercion Red ESL


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		Ⅲ
Substantivity 親和性		A
Migration 移染性		4
Washing off 洗淨性		2-3
Solubility g/l 溶解度	50°C Water 水	100
	50°C Water 水 + 50 g/l Salt 鹽	80
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	4
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	B
	TL 84 Lamp	B
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5
	Cu^{2+} 銅離子	3BD
Resin finishing 樹脂加工	Melamine 三聚氰胺	4-5
	Glyoxal 乙二醛	4-5
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3B
	Quaternary ammonium salt 四級銨鹽	4-5


吸盡固著曲線 Exhaustion & Fixation

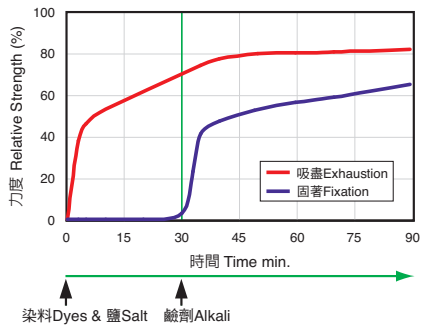

溫度依存性 Dependency on temperature

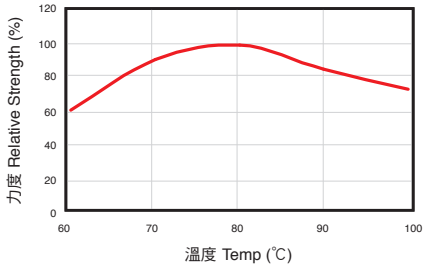

芒硝依存性 Dependency on Glauber's salt

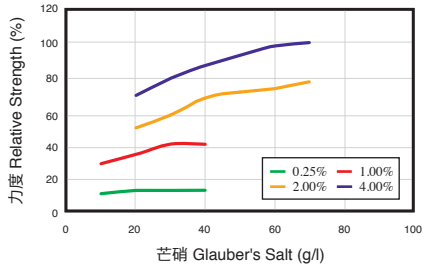

Evercion Red ESL

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	4-5	4-5	3-4	5	5	5	5
	ISO C10 C		4-5	4-5	3-4	5	5	4-5	5
	ISO C10 D		4-5	4-5	3	5	5	4-5	3
	ISO C06-C1S		5	5	4	5	5	5	5
	ISO C06-C2S		5	5	4-5	5	5	5	5
	M&S C4A		5	5	4-5	5	5	5	5
Water 耐水		3.0%	5	4-5	3-4	5	5	5	5
Hot Water 耐熱水		3.0%	5	4-5	4-5	5	5	5	5
Sea Water 耐海水		3.0%	4B	5	4-5	5	5	5	5
Post mercerizing 後絲光		3.0%	2Y		4				
Acid hydrolysis 酸水解		3.0%	4	4	3-4	3	4	3-4	3-4
Perspiration 耐汗	Acid 酸	3.0%	4B	5	3	3-4	5	4	4-5
	Alkali 鹼		4-5	5	4	5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	3-4B
Peroxide Bleaching雙氧水漂白				4
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			2-3
M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
			3.0%	>4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	4-5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3-4BD
		4 Hours after		4-5
	Wet 濕	Immediately	3.0%	3-4BD
		4 Hours after		4-5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2	3-4
	0.3 %	3	3-4
	1.0 %	3-4	4
	3.0 %	4	4-5
	6.0 %	4	4-5

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	3-4	4-5
	Alkali鹼		3	4

浴比依存性 Dependency on Liquor ratio

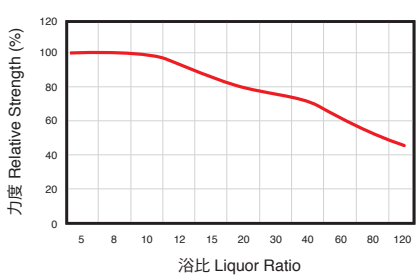

鹼依存性 Dependency on alkali

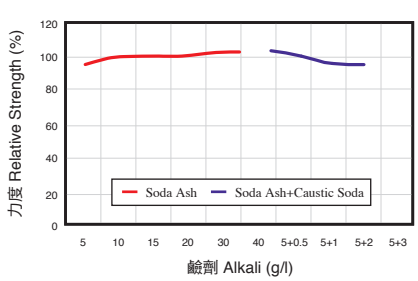


Evercion Crimson ESL


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		Ⅲ
Substantivity 親和性		A
Migration 移染性		3-4
Washing off 洗淨性		3
Solubility g/l 溶解度	50°C Water 水	100
	50°C Water 水 + 50 g/l Salt 鹽	100
High temp. Dyeing 高溫染色性	Dyed fabric 色布	4
	Dye Liquor 染浴	4-5
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL 84 Lamp	G (Y)
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5
	Cu^{2+} 銅離子	2-3(B)
Resin finishing 樹脂加工	Melamine 三聚氰胺	3
	Glyoxal 乙二醛	3-4
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	3-4
	Quaternary ammonium salt 四級銨鹽	4-5


吸盡固著曲線 Exhaustion & Fixation

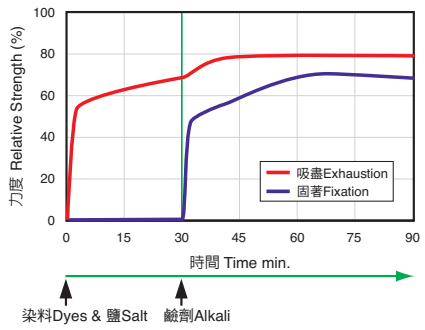

溫度依存性 Dependency on temperature

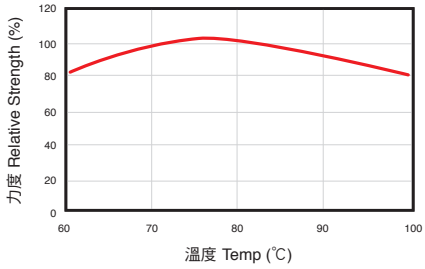

芒硝依存性 Dependency on Glauber's salt

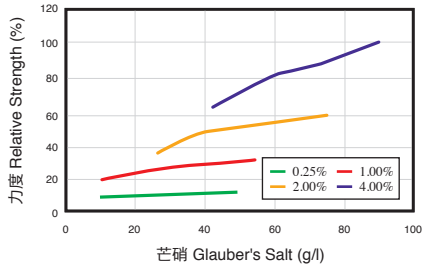

Evercion Crimson ESL

Everlight Chemical

Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	3.0%	4-5	5	4-5	5	5	5	5
	ISO C10 C		4-5	5	5	5	5	5	5
	ISO C10 D		4-5	5	4-5	5	5	5	4-5
	ISO C06-C1S		4-5	5	4-5	5	5	5	5
	ISO C06-C2S		4-5	5	4-5	5	5	5	5
	M&S C4A		4-5	5	5	5	5	5	5
Water 耐水		3.0%	4-5	5	4-5	4-5	5	5	5
Hot Water 耐熱水		3.0%	4-5	5	5	5	5	5	5
Sea Water 耐海水		3.0%	4-5	5	5	5	5	5	5
Post mercerizing 後絲光		3.0%	3*		3-4				
Acid hydrolysis 酸水解		3.0%	4-5	4-5	3	3	5	4-5	4-5
Perspiration 耐汗	Acid 酸	3.0%	4-5	5	4-5	4-5	5	5	5
	Alkali 鹼		4-5	5	4-5	5	5	5	5


Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
Chlorinated Water耐氯水(20ppm)			3.0%	4-5
Peroxide Bleaching雙氧水漂白				4-5
Rubbing 耐摩擦	Dry 乾		3.0%	5
	Wet 濕			3
M&S C9A 濕日光 (detergent Light)			0.3%	4-5
			3.0%	4-5
M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Saliva (DIN) 耐唾液			3.0%	5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3
		4 Hours after		4-5
	Wet 濕	Immediately	3.0%	3
		4 Hours after		4-5
Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4-5

Light Fastness 日光堅牢度


Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	2-3	3-4
	0.3 %	3	4
	1.0 %	3-4	4-5
	3.0 %	4	5-6
	6.0 %	4-5	6

Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Perspiration Light 耐汗日光	Acid酸	3.0 %	3	5
	Alkali鹼		3-4	4

浴比依存性 Dependency on Liquor ratio

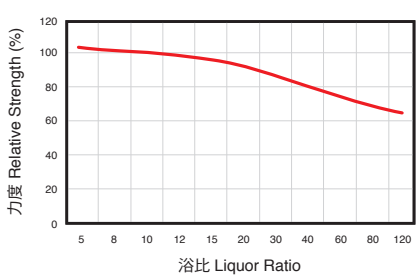

鹼依存性 Dependency on alkali

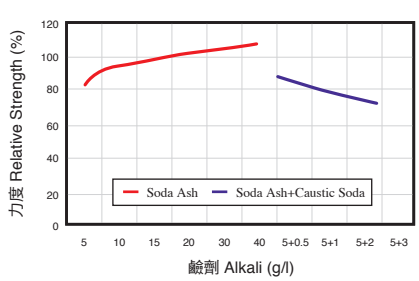


Evercion Navy ESL


Dyeing Properties 特性

Characteristics 特性		Evaluation 評級
Reactivity 反應性		Ⅲ
Substantivity 親和性		A
Migration 移染性		3-4
Washing off 洗淨性		2
Solubility g/l 溶解度	50°C Water 水	70
	50°C Water 水 + 50 g/l Salt 鹽	60
High temp. Dyeing 高溫染色性	Dyed fabric 色布	1-2R
	Dye Liquor 染浴	4G
Color constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL 84 Lamp	R
Metallic ions 金屬離子	Fe^{2+} 鐵離子	4-5
	Cu^{2+} 銅離子	3-4
Resin finishing 樹脂加工	Melamine 三聚氰胺	4Y
	Glyoxal 乙二醛	4R
Shade change after fixing treatment 固色後變色性	Polyamine 聚胺類	4Y
	Quaternary ammonium salt 四級銨鹽	5


吸盡固著曲線 Exhaustion & Fixation

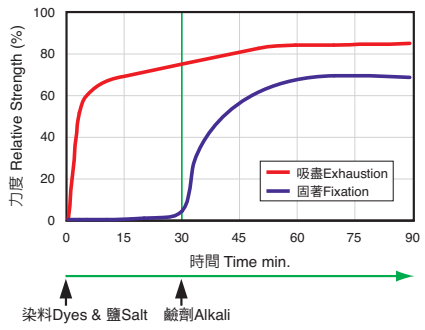

溫度依存性 Dependency on temperature

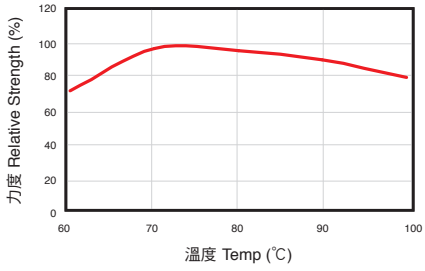

芒硝依存性 Dependency on Glauber's salt

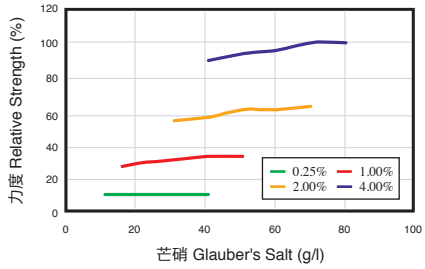

Evercion Navy ESL

Everlight Chemical


Fastness before fixing treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Depth of shade 染色濃度	Color change 變褪色	Staining 污染						Evaluation 評級 / Fastness 牢度			Depth of shade 染色濃度	Grade 級數
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛					
Washing 耐水洗	ISO C10 B	3.0%	4-5	4-5	4	5	5	5	5	Chlorinated Water耐氯水(20ppm)			3.0%	3-4B
	ISO C10 C		4-5	4-5	3-4	5	5	4-5	5	Peroxide Bleaching雙氧水漂白				4
	ISO C10 D		4-5	4-5	3-4	5	5	5	5	Rubbing 耐摩擦	Dry 乾		3.0%	5
	ISO C06-C1S		4-5	5	4	5	5	5	5		Wet 濕			2-3
	ISO C06-C2S		4-5	5	4	5	5	5	5	M&S C9A 濕日光 (detergent Light)			0.3%	>4-5
	M&S C4A		4-5	5	4	5	5	5	5				3.0%	>4-5
Water 耐水		3.0%	5	4-5	3-4	5	5	4-5	5	M&S C10A (UK-TO) 多次水洗			3.0%	4-5
Hot Water 耐熱水		3.0%	5	4-5	4-5	5	5	5	5	Saliva (DIN) 耐唾液			3.0%	4-5
Sea Water 耐海水		3.0%	4B	5	4-5	5	5	5	5	Hot-Pressing 耐熱壓	Dry 乾	Immediately	3.0%	3-4BD
Post mercerizing 後絲光		3.0%	2Y		4							4 Hours after		4-5
Acid hydrolysis 酸水解		3.0%	4	4	3-4	3	4	3-4	3-4		Wet 濕	Immediately	3.0%	3-4BD
Perspiration 耐汗	Acid 酸	3.0%	4B	5	3	3-4	5	4	4-5			4 Hours after		4-5
	Alkali 鹼		4-5	5	4	5	5	5	5	Colorfastness to Nitrogen Oxides 氣體變褪色			1.0%	4


Light Fastness 日光堅牢度

Evaluation 評級	Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)	Evaluation 評級		Dyeing Depth 染色濃度	Color Change 20 AFU 變褪色	Grade ISO Blue Scale 級數(藍色票)
Artificial Light (Xenon-Arc Lamp) 耐日光	0.1 %	1-2	3-4	Perspiration Light 耐汗日光	Acid酸	3.0 %	2-3	4-5
	0.3 %	2-3	3-4		Alkali鹼		2-3	4-5
	1.0 %	2-3	4					
	3.0 %	3	4-5					
	6.0 %	3-4	4-5					

浴比依存性 Dependency on Liquor ratio

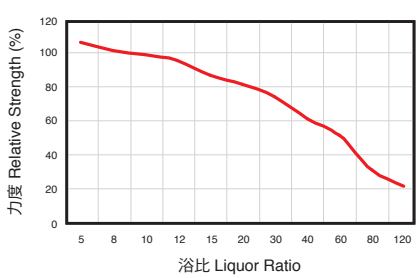

鹼依存性 Dependency on alkali

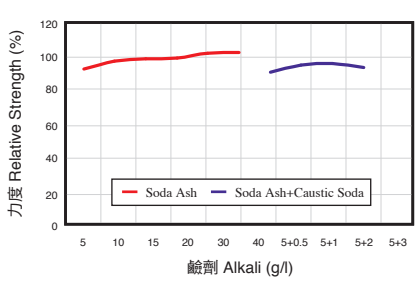

Note

Note

本資料所提供的資訊與建議是以我們最大的用心完成，但不能含括所有可能的狀況。使用相關產品或搭配其他產品時，請先自行測試。本資料並不具保證及法律效用，僅供參考使用。使用者必須自行承擔所有的風險與法律責任。

臺灣永光化學工業股份有限公司－技術行銷處

Warnings： The information and recommendations presented here were completed with the utmost care, but can't be extended to cover every possible case. They are intended to serve as non-binding guidelines and must be adapted to the prevailing condition. The product whether used singly or in combination with other substances, should be carried out in lab test prior to bulk production. The user needs to assume all risk and liability no matter whatsover results are.

Issued by Everlight Chemical Industrial Corporation-Tech. Marketing & Service Div.

Everlight Chemical