臺灣永光化學工業股份有限公司
Everlight Chemical Industrial Corporation

Everzol Dyes
冷壓染與連續染色

中文版

Everlight Chemical

Better Chemistry Better Life

品牌承諾

永光化學追求進步創新，以滿載的研究熱情，透過不斷的加乘與連結，
創造出許許多多的可能。永光，以化學專業給予客戶最大支持，協助客戶
邁向成功，也為美好的社會及永續的未來，做出具體貢獻。
我們相信，運用對的化學品，可以讓生活更美好！



品牌價值

永光化學相信，運用對的化學品，可以讓生活更美好！

穩健可靠
正派經營的理念、履行承諾的決心、穩定的品質與貼心的服務，奠定永光化學的品牌信賴感。

以客為尊
專注於化學本業，滿載研究熱情，永光化學追求突破與進步，讓化學對人類的貢獻，無止境地向前演進。

進步創新
關懷顧客、共創價值是永光化學的品質政策。我們以高品質產品、服務與技術支援，給予客戶支持，協助客戶邁向成功。

造福人群
提升人類生活福祉，是永光存在的意義；以不斷進步的化學專業，為更好明天與永續未來，做出具體的貢獻。

目錄

Everzol 染料在連續染色的應用介紹 A–1

纖維素纖維染色流程

1. 冷壓染色法 A–3
2. 二浴壓染蒸處法 A–16
3. 一浴壓染熱固著法 A–20
4. 一浴壓染蒸處法 A–23
5. 一浴濕短蒸染色法 A–25
6. 水洗工程 A–27

混紡纖維素染色流程

7. 聚醯胺（尼龍）／纖維素纖維 冷壓染 — 浸染法 A–28

Everzol 染料三原色組合推薦 A–33

Everzol 染料牢度與特性 A–76

Everzol 染料在連續染色的應用介紹

Everzol 染料可廣泛應用於冷壓染色及連續染色流程。

Everzol 染料具有：

- 產品的規劃與特性應用設計，符合冷壓染色及連續染色工程上的需求。
- 產品品質的確認，並採用冷壓染或連續染色的方式進行，使其能確保在上述各染程應用時的染色特性與染色品質。
- 增強產品於鹼浴中的染液安定性。
- 提高產品於鹼浴中的耐鹼溶解度。

Everzol 染料在連續染色的優點：

- 應用在冷壓染色及連續染色工程上，擁有產品品質的一致性。
- 在鹼浴中擁有極優異的耐鹼溶解度及染液安定性。
- 均一的染色再現性。
- 穩定於各個染程條件的變異。

Everzol 染料在連續染色的應用特性：

擁有高固著率的組合

具有低廢水和極佳的染色再現性。

中直接性

具有均一的染色結果與易水洗。

染深性佳

具高得色率，極易染得深色系。

利用冷壓染色法

當進行 N/C 混合纖維織物的染色時，若先以冷壓染流程染棉纖維，則可有效抑制染料對尼龍的污染。


色域廣

從淺三原到中深三原色，皆擁有極優異的組合性與相容性。

Everzol 染料對生產作業的效益：

- 有效降低染料耗用量。
- 優異的染色再現性。
- 短流程、高生產性、省時。
- 方便應用於多種連續染色流程。
- 省水。

1. 冷壓染色工程 Cold Pad–Batch process

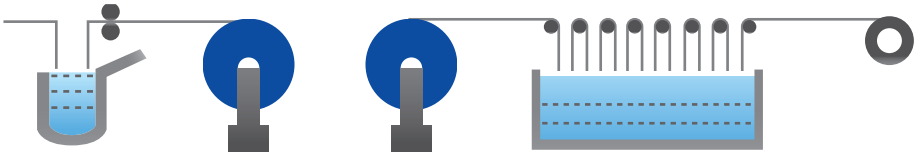

特性


Everzol 染料應用於冷壓染色擁有：

- 優異的耐鹼溶解度。
- 優異的壓吸液安定性。
- 高固著率與高染深性。
- 均一的染色再現性。
- 當進行 N/C 混合纖維織物的染色加工時，若先以冷壓染流程染棉纖維，則可有效抑制 Everzol 染料對尼龍的污染。
- 寬廣的生產應用性，適合於各類型織物，尤其像一些厚重織物，如燈芯絨、平面絨、毛巾布及磨毛桃面布等。


染液壓吸：

壓染工程為將製備好的調液與織物進行浸漬、濕潤、吸附後以壓榨輥輪壓吸一定量的染液於織物上。在冷壓染的染色工程，一般是以將預備好的染液與鹼液，經定量泵抽送固定的比例混合（一般以 4 份染液：1 份鹼液），完全充分混合之後快速流入壓吸槽進行織物浸漬、濕潤壓吸之用，其重點圖示如下。

染液與鹼液混合示意圖：

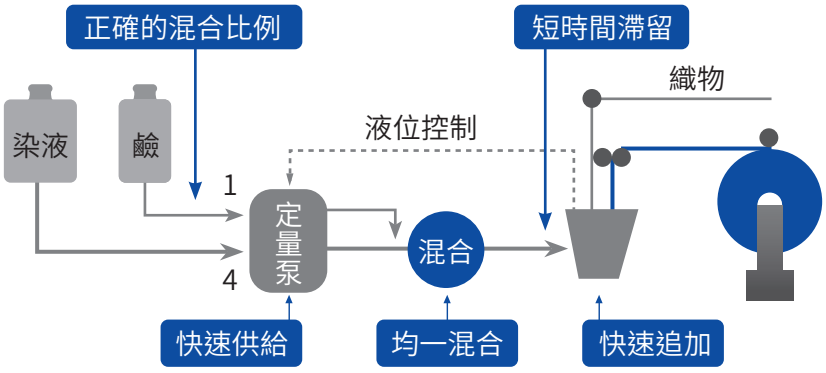

壓吸方式可依需求選擇液槽式壓吸或輥間式壓吸。液槽式壓吸可得較長的滲透與吸收時間；輥間式壓吸可提供快速的染液交換率。

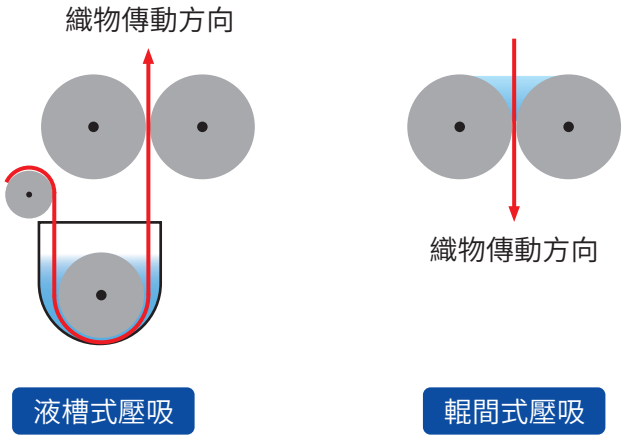

鹼劑需求：

推薦可應用於冷壓染色工程的三種鹼劑。

A. 非水玻璃法：

Everzol 染料	Everzol 染料使用濃度（g/l）						
	~10	10~20	20~40	40~60	60~80	80~100	100 ↑
純鹼（g/l）	20	20	20	20	20	20	20
液鹼 50° B'e (ml/l)	4	5	7	10	12.5	15	16.5

B. 水玻璃法：

水玻璃			Everzol 染料使用濃度（g/l）					
			~20	30	40	50	60	70 ↑
	g/l	ml/l	液鹼需求量 NaOH 50° B'e, 50%（ml/l）					
37~40° B'e	130	95	13.5	16.5	16.5	19.5	19.5	22
40~42° B'e	110	75	13.5	16.5	16.5	19.5	19.5	22
48~50° B'e	100	65	8.5	11.5	11.5	14.5	14.5	17.5
58~60° B'e	90	50	3.5	6.5	6.5	9	9	12

C. 水玻璃減量法：

水玻璃			Everzol 染料使用濃度（g/l）					
			~10	20	30	40	50	60 ↑
	g/l	ml/l	液鹼需求量 NaOH 50° B'e, 50%（ml/l）					
37~40° B'e	65	50	4	7	7	10	10	12.5
40~42° B'e	55	40	4	7	7	10	10	12.5
48~50° B'e	50	35	3	6	6	8.5	8.5	11.5
58~60° B'e	45	25	1.5	4	4	6.5	6.5	9

助劑添加：

滲透劑的選用應注意是否適合於壓吸液，並且是非起泡性。

尿素的添加可改善提昇部份染料的溶解度。

註：鹼劑 C 水玻璃減量法與其它鹼劑的差異為降低水玻璃與液鹼的使用量，其目的為確保在較高溫的作業環境下，仍保有壓吸液與捲置固著依存的一貫安定性，而其捲置固著時間保持 16 小時以上是必要的。


上述各鹼劑的應用，定量混合泵皆是必需的。


染液安定性：

染液安定性高低為依存於各鹼劑的使用上，而且隨滯留時間與染液溫度的不同而有明顯的差異變化。

對大部份的反應性染料而言其關係如下圖示：

鹼劑與染液安定性的相對關係

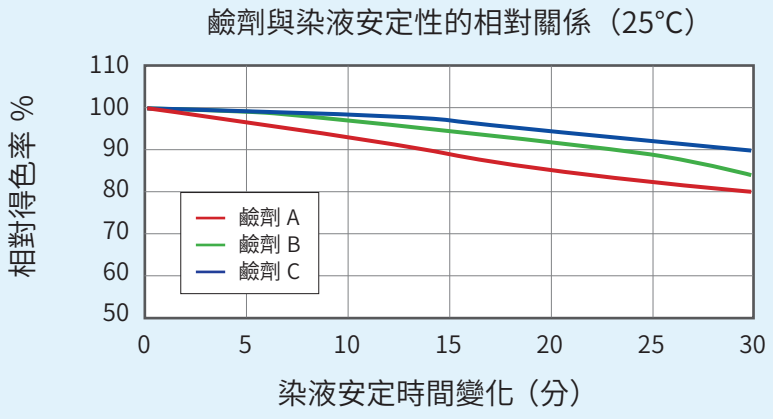

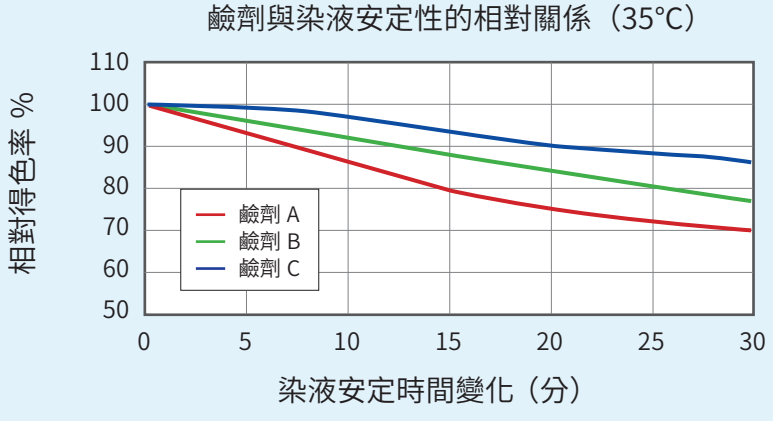


鹼劑 C 水玻璃減量法為特別設計於熱帶氣候，當染液溫度與環境的固著溫度較高時的染色場合（約 30~40°C），其目的為確保染色壓吸液與捲置固著依存擁有一貫的染色安定性。


溫度與染液安定性的相對關係

對大部份的反應性染料而言其關係如下圖示：


鹼劑 A，非水玻璃法：

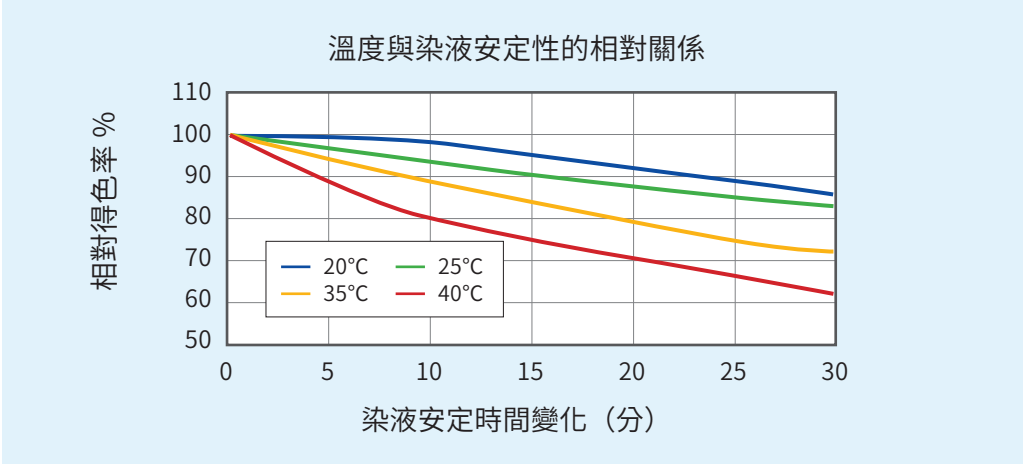

鹼劑 B，水玻璃法：

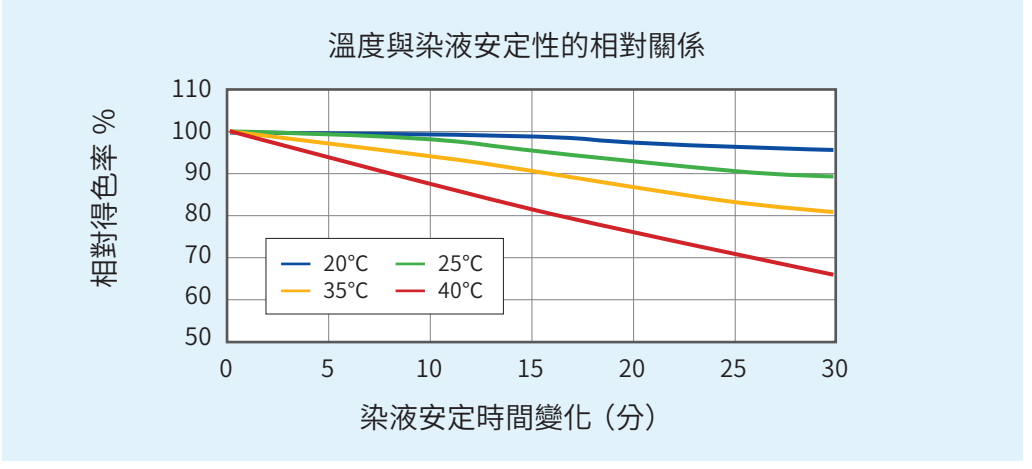

鹼劑 C，水玻璃減量法：

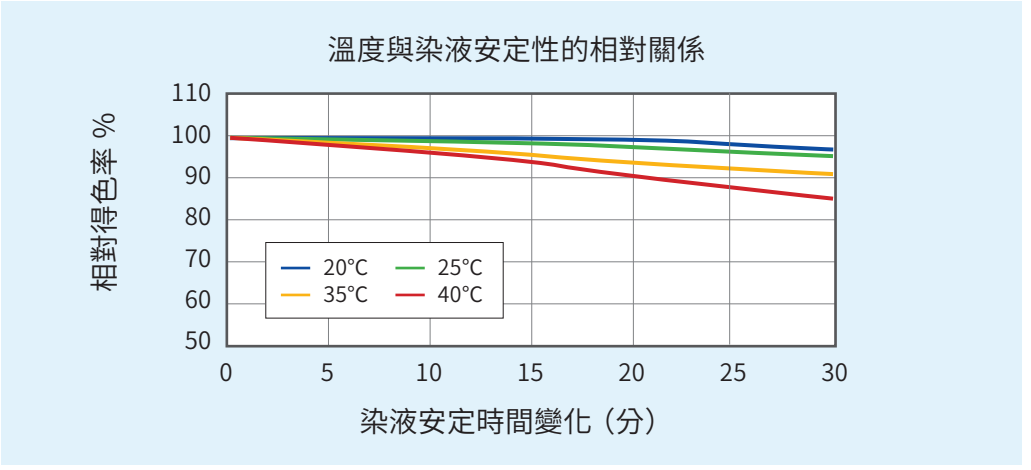

鹼劑 C 水玻璃減量法為特別設計於熱帶氣候，當染液溫度與環境的固著溫度較高時的染色場合（約 30~40°C），其目的為確保染色壓吸液與捲置固著依存擁有一貫的染色安定性。

當然，在一般的染色條件下（例如 20~25°C的染色條件），該方法仍是一個可信賴的實用方法，然而較佳的固著條件，則以長時間的隔夜捲置為需求（16 小時以上）。

固著：

在冷壓染工程，壓吸後捲取的織物，為了防止任何來自空氣中可能影響染色差異的因子，必須利用 PE 之類的不透氣膜加以包覆，並能確保完全密封，且保持布邊的捲取一致性。

除此，在捲置固著轉動過程中，要注意捲取物旋轉的速度與水平的保持。


在固著過程上，一般在一恆定的室溫下為之（通常接近於壓吸液的溫度為佳）以及最低的固著時間應能符合染料特性上的要求。

在生產作業上，對於 Everzol 染料我們一般推薦當在 25°C左右的染色條件時，最低的固著時間為 4 小時以上，如果是在長碼數或較大較多的捲置量下，適時的將捲置固著時間增加 2 小時以上，是對染著再現性有幫助的，以上為針對擬採短時間捲置作業時的建議；同時，在一般室溫下長時間的捲置固著（甚至達到 48hr）對色相的一致性是不會有影響的。

在生產作業上，如果固著溫度較一般條件為低的話，最短的固著時間必須再加以延長，乃至隔夜等。假如固著溫度高出一般室溫條件甚多的話，我們建議最長的固著時間勿超過 24 小時以上。


溫度與固著時間的相對關係

對大部份的反應性染料而言其關係如下圖示：

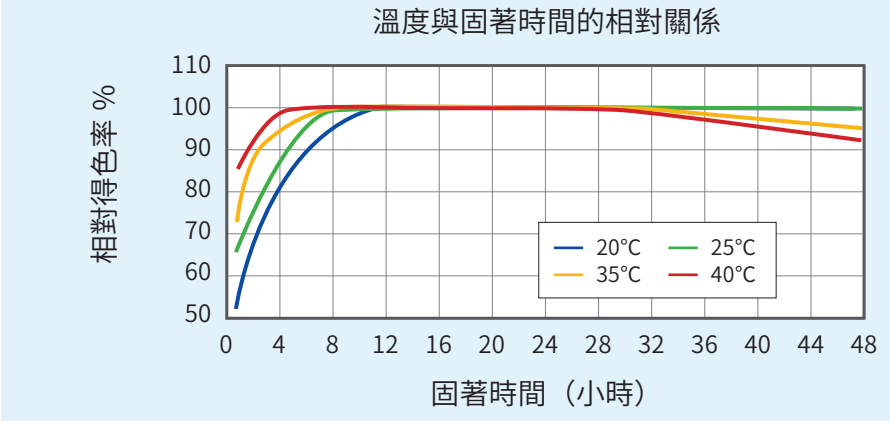

鹼劑 B，水玻璃法，絲光棉

假如固著溫度高出一般室溫條件甚多的話，我們建議最長的固著時間勿超過 24 小時以上。

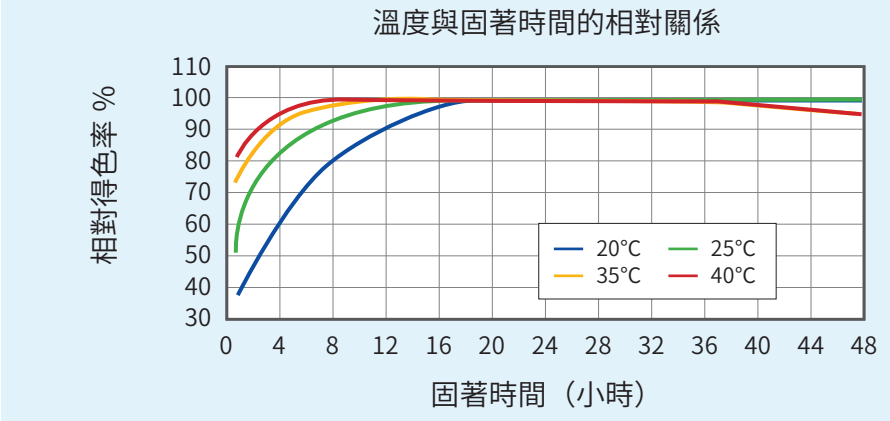


鹼劑 C，水玻璃減量法，絲光棉


鹼劑 C 水玻璃減量法為特別設計於熱帶氣候，當環境的固著溫度較高時的染色場合（約 30~40°C），其目的為保有捲置固著依存擁有一貫的染色安定與再現性。

鹼劑與固著時間的相對關係

對大部份的反應性染料而言其關係如下圖示：

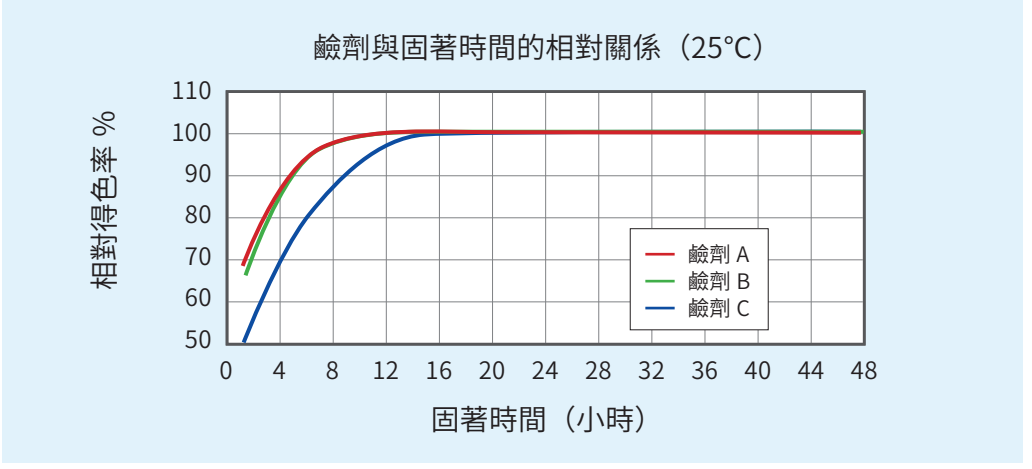

絲光棉

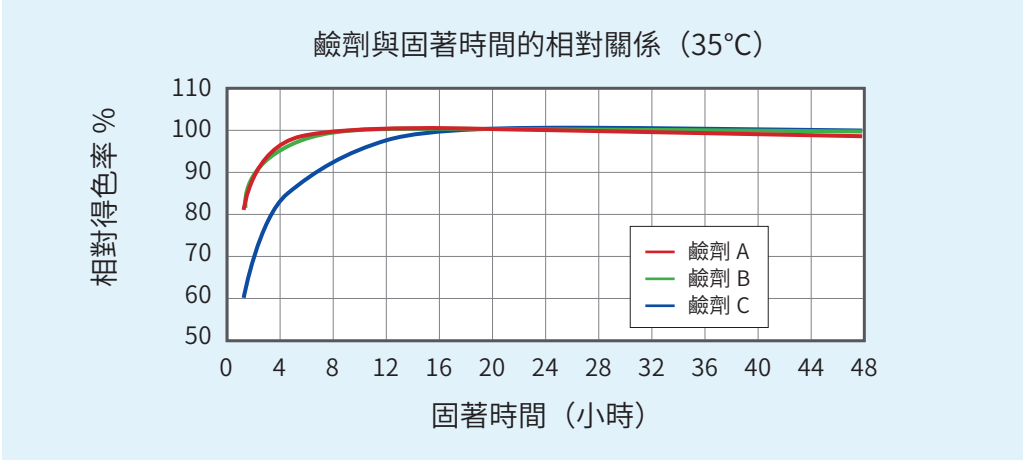

絲光棉

鹼劑 C 水玻璃減量法為特別設計於熱帶氣候，當染液溫度與環境的固著溫度較高時的染色場合（約 30~40°C），其目的除確保染色壓吸液的安定之外，亦使捲置依存擁有一貫的染色安定性。

當然，在一般的染色條件下（例如 20~25°C的染色條件），該方法仍是一個可信賴的實用方法，然而較佳的固著條件，則以長時間的捲置固著為需求（16 小時以上）。

Everlight Chemical

Everzol 染料固著時間需求表

絲光棉布

類別	I	II	III	IV
Yellow	Yellow C–GL Yellow C–GR Yellow C–RN	Orange ED–4R	Yellow CE–N Orange C–2R Yellow LX Yellow ED–R Yellow ERC	Yellow ED Yellow CS Flavine FC Orange CS Orange ED–N
Red	Red C–3B Red C–RB 133%	Red C–D Red ED–2B	Red LX Red LF–B Red LF–2B Red ED Red ED–S Red ED–3B Red ED–7BN	Red LF–4B Rubine ED Red Brown CS Orange FC Scarlet FC
Blue	Navy C–GG 133% Black C–B 133%	Blue C–R S/P Navy C–GB H/C	Blue C–BB 133% Blue L–ED Navy C–FB Navy ED Blue ERC	Turq. Blue C–G 133% Blue ED–G Blue ED Blue C–BRF Blue C–LX Blue FC
Other	Black C–RL Black ED Black ED–G Black ED–R Black ED–3R Black EDN Jet Black ERC	Dark Blue LF Black MWF Black ERC	Amber ERC Light Red ERC Cardinal ERC Bordeaux ERC Dark Blue ERC Marine ERC	Grey LF Olive CS Grey CS

固著時間	~4hrs ↑	~8hrs ↑	~12hrs ↑	~16hrs ↑

鹼劑需求：鹼劑 A：非水玻璃法
鹼劑 B：水玻璃法
材質：絲光棉
固著溫度：25°C

在配色上，當不同的染料類別組合在一起時，固著時間必須依照類別項中最長的一支染料為基礎，對於若採用鹼劑 C 水玻璃減量法時，較長的捲置固著時間是必須的（16 小時以上）。

Everzol 染料固著時間需求表

未絲光棉布

類別	I	II	III	IV
Yellow	Yellow C–GL Yellow C–GR Yellow C–RN	Orange ED–4R	Yellow CE–N Orange C–2R Yellow LX Yellow ED–R Yellow ERC	Yellow ED Yellow CS Flavine FC Orange CS Orange ED–N
Red	Red C–3B Red C–RB 133%	Red C–D Red ED–2B	Red LX Red LF–B Red LF–2B Red ED Red ED–S Red ED–3B Red ED–7BN	Red LF–4B Rubine ED Red Brown CS Orange FC Scarlet FC
Blue	Navy C–GG 133% Black C–B 133%	Blue C–R S/P Navy C–GB H/C	Blue C–BB 133% Blue L–ED Navy C–FB Navy ED Blue ERC	Turq. Blue C–G 133% Blue ED–G Blue ED Blue C–BRF Blue C–LX Blue FC
Other	Black C–RL Black ED Black ED–G Black ED–R Black ED–3R Black EDN Jet Black ERC	Dark Blue LF Black MWF Black ERC	Amber ERC Light Red ERC Cardinal ERC Bordeaux ERC Dark Blue ERC Marine ERC	Grey LF Olive CS Grey CS

固著時間	~8hrs ↑	~12hrs ↑	~16hrs ↑	~24hrs ↑

鹼劑需求：鹼劑 A：非水玻璃法
鹼劑 B：水玻璃法
材質：未絲光棉
固著溫度：25°C

在配色上，當不同的染料類別組合在一起時，固著時間必須依照類別項中最長的一支染料為基礎。對於針織物染色或採用鹼劑 C 水玻璃減量法為鹼劑時，更長的固著時間或隔夜是必需的（16 小時以上）。

Everlight Chemical


在冷壓染色中必須注意到的一些染色要因：

◆ 耐鹼溶解度



鹼劑選擇：鹼劑 C（水玻璃減量法）對大部分染料擁有更佳的耐鹼溶解度。
尿素添加：添加尿素可改善提昇部份染料的溶解度。


◆ 染液安定性

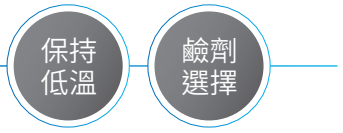

低　　溫：染色壓吸液在一般低溫下易保有其安定性，若在調液中加入尿素，一方面除助溶之外，另一面亦可有效冷卻染料溶解時的溫度，使其保持在一般常溫之下。若染液壓吸溫度在較高的情況下，由於高溫將會致使壓吸液的安定性降低，而造成得色降低、頭尾異色等異常。


鹼劑選擇：染料在鹼劑 C（水玻璃減量法）中擁有更佳的染液安定性尤其是在熱帶的環境溫度下。

◆ 溫度

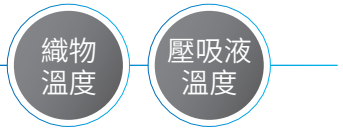


前處理完成後的待染色布，必須加以冷卻。調製好的染液在染色前亦需確認為常溫或低溫狀況，其目的為防止壓吸液在較高的溫度下影響其安定性與得色，及在非恆定的溫度壓吸作業下，易產生不均染的吸收與頭尾異色。

◆ 固著時間管理

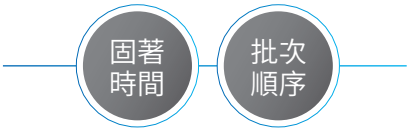

對各種染料組合，至少應有充足的固著時間；若在長碼數的染色下，可能會分成數個布捲，此時應確認其水洗先後順序。

◆ 氣候變化的影響

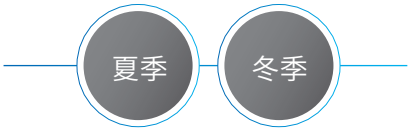

注意氣候變化對染色可能的影響，因為固著時的得色率及染色再現性常常依存於捲置的條件變化。


冷壓染實驗室小樣快速染色方法

使用烘箱法染色，再現性好，適合各種織物的快速染色。此外，提供實驗室和現場（Lab.-->Bulk）之間，驗證調液的正確性。

小樣快速染色條件

最佳條件：60°C x 30 分鐘或 70°C x 20 分鐘

2. 二浴壓染蒸處工程 Pad–Dry–Chemical Pad–Steam process

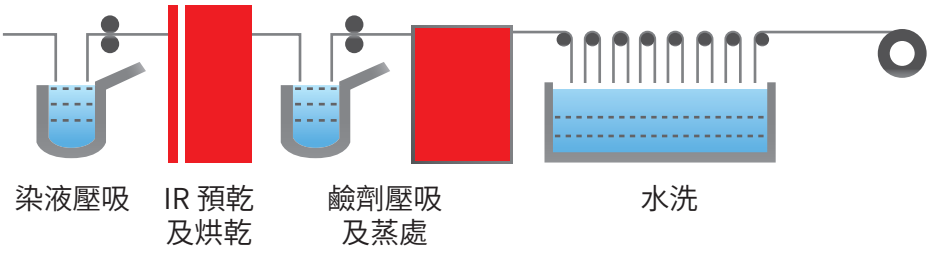

此方法為採二浴壓吸乾燥後蒸處固色的染色方法。

特性

Everzol 染料在二浴壓染 – 蒸處法上擁有：

- 均一的染色結果。
- 極佳的蒸處時間依存性。
- 高生產性。
- 高固著率。

染色壓吸液組成：

Everzol 染料	x g/l
移行防止劑	1 g/l
還原防止劑	10 g/l
滲透劑（選擇使用）	0~2 g/l

滲透劑的選用應注意是否適合於壓吸液，並且是非起泡性。
尿素的添加可改善提昇部份染料的溶解度。

壓吸：

將製備好的調液與織物於壓吸槽內進行浸漬、濕潤、吸附後以壓榨輥輪壓吸一定量的染液於織物上；此時織物在壓吸過程中有一均一的吸收是相當重要的，並應確認壓吸於一致的壓吸率下。

一個理想的壓吸結果建立在下面幾個作業因子：

壓吸液溫度：溫度太高的壓吸液，易造成頭尾異色的異常；保持在恆定一般室溫下，對染色結果是較理想的。

織物：織物在前處理之後，除確認前處理後的品質之外，必須加以冷卻，並確認是均一的乾燥程度，且維持織物在恆定的室溫與一致的含濕率。

壓吸槽：為了使壓吸槽內染液與織物吸收之間有一良好的交換率，壓吸槽的體積建議愈小愈好，尤其是輕薄織物；此外壓吸時入布的恆速，皆能有效防止頭尾異色或顏色差異的產生。

烘乾：

紅外線 IR 預乾
一般乾燥到約 30% 左右的含水量
烘乾：110~130°C
乾燥後織物加以冷卻

中間乾燥在二浴壓吸 – 蒸處法中是相當重要的一環，通常使用紅外線 IR 預乾與熱風乾燥或錫林滾筒乾燥等組合的系統。

利用紅外線 IR 預乾。其乾燥效能應能有效降低織物上的含水率到 30% 左右，其目的為利於後段的熱風或錫林乾燥工程能避免移染不均的現象發生。

假如織物在中間乾燥過程沒有使用紅外線 IR 預乾的話，此時應注意烘箱內熱風的風速，將其控制在低風速並均一的熱風對流下烘乾之，以避免移染不均的現象發生。

中間乾燥後壓染布的品質需求為均一的乾燥程度及沒有濃度差異的現象，如：內外側差（霜白）、陰陽面、左右異色、表面濃色等。

化學鹼液壓吸／蒸處：

在此過程中應確保壓染布在鹼液槽中有一致的吸收與呈安定的狀態。

化學鹼液需求：

A. 水玻璃（48~50° B'e）	60~70 %
B. 液鹼（50° B'e, 50%）	8~11.5 ml/l
無機鹽	250 g/l
C. 液鹼（50° B'e, 50%）	7~10.5 ml/l
純鹼	20 g/l
無機鹽	250 g/l


蒸處：

在飽和蒸汽 102~105°C，採連續式固著。

Everzol 在此工程中較佳的蒸處依存時間推薦如下：

30–70 secs
Everzol C Dyes : Yellow C–GL, Yellow C–GR, Yellow C–RN, Yellow CE–N Orange C–2R, Red C–3B, Red C–RB 133%, Red C–D Blue C–R S/P, Blue C–BB 133%, Blue C–BRF Navy C–GG 133%, Navy C–GB H/C, Navy C–FB Black C–B 133%, Black C–RL Black MWF **Everzol CS Dyes :** Yellow CS, Orange CS, Red Brown CS, Olive CS, Grey CS **Everzol LX/LF Dyes :** Yellow LX, Red LX, Red LF–B, Red LF–2B, Red LF–4B, Blue C–LX, Grey LF, Dark Blue LF **Everzol ED Dyes :** Yellow ED–R, Yellow ED, Orange ED–4R, Orange ED–N Red ED, Red ED–2B, Red ED–3B, Red ED–7BN, Red ED–S, Rubine ED Blue ED–G, Blue L–ED, Blue ED, Navy ED Black ED, Black ED–G, Black ED–R, Black EDN, Black ED–3R **Everzol FC Dyes :** Flavine FC, Orange FC, Scarlet FC, Blue FC **Everzol ERC Dyes :** Amber ERC, Yellow ERC, Light Red ERC, Cardinal ERC, Bordeaux ERC Blue ERC, Dark Blue ERC, Marine ERC, Black ERC, Jet Black ERC
70–100 secs
Turq. Blue C–G133%

3. 一浴壓染熱固著工程 Pad–Dry–Baking process

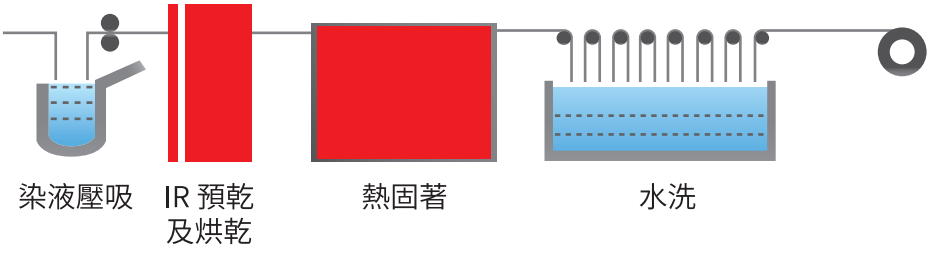

此方法在連續染色工程為採一浴乾式熱固著的染色方式。

特性

Everzol 染料在一浴壓吸熱固著工程中擁有：

- 均一的染色結果。
- 極佳的染液安定性。
- 在烘乾或熱固著工程上，擁有極佳的依存性與一致性。
- 高生產性的應用染程。

染色壓吸液組成：

Everzol 染料	x g/l
鹼劑	見 A–22 頁
移行防止劑	1 g/l
還原防止劑	10 g/l
尿素	50~150 g/l
滲透劑	0~2 g/l
硼砂	0~10 g/l

滲透劑的選用應注意是否適合於壓吸液中，並且是非起泡性。

在本工程，尿素的添加除可增加改善部份染料的溶解度以外，更可提昇染料的得色率，但當加工條件為 160°C以上時，須注意尿素熱分解的影響。

硼砂的添加，可有效防止織物的黃化。

壓吸：

織物在壓吸過程中有一均一的吸收是相當重要的，並應確認壓吸於一致的壓吸率下。

一個理想的壓吸結果建立在下面幾個作業因子：


壓吸液溫度：溫度太高的壓吸液，對染浴將呈現不安定性，易造成頭尾異色與顏色差異；保持在恆定的一般室溫下，對染色結果與再現性是較理想的。

織物：織物在前處理之後，除確認前處理後的品質之外，必須加以冷卻，並確認是均一的乾燥程度，且維持織物在恆定的室溫與一致的含濕率。

壓吸槽：為了使壓吸槽內染液與織物吸收之間有一良好的交換率，壓吸槽的體積建議愈小愈好，尤其是輕薄織物；此外壓吸時入布的恆速，皆能有效防止頭尾異色或顏色差異的產生。

鹼劑需求：

一浴壓染熱固著工程鹼劑需求表：

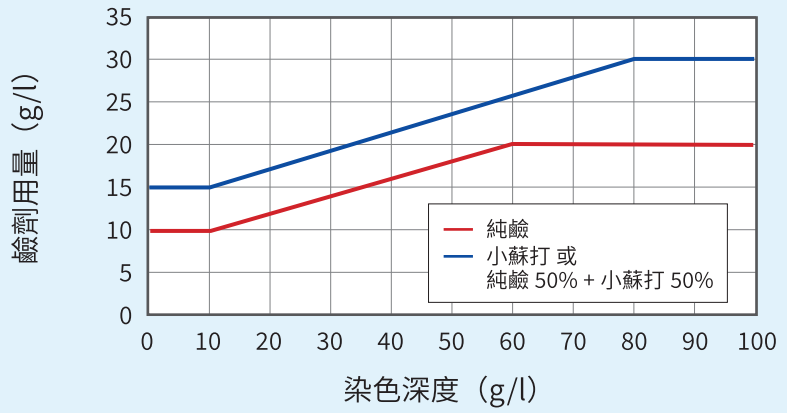

烘乾：

紅外線 IR 預乾。

一般乾燥到約 30% 左右的含水量。

烘乾：100~120°C（在有些連續染色作業上，本過程可考慮省略）

熱固著條件：

4~6 分, at 120°C

3~4 分, at 140°C

2~3 分, at 150°C


1.5~2 分, at 160°C

1~2 分, at 180°C

1 分, at 200°C

註：注意織物若在高溫固著及帶鹼性的狀況下會產生黃化的現象，其織物的黃化程度，應一併考慮對配色可能的影響。

4. 一浴壓染蒸處工程 Pad–Steam process

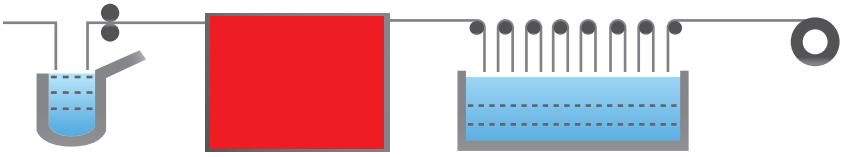

此方法為採一浴溼式蒸汽固著的染色方式不需經中間乾燥，特別適合於厚重織物的染色。因為厚重織物在中間乾燥過程中是較不經濟且易產生染料移染的異常現象。

特性

Everzol 染料在一浴壓染蒸處工程中擁有：

- 均一的染色結果。
- 高生產性的應用染程。
- 特別適合於厚重織物的染色例如燈芯絨、平面絨、毛巾布及磨毛桃皮布等。

染色壓吸液組成：

Everzol 染料	x g/l
液鹼（50° B'e, 50%）	yml/l
純鹼	20 g/l
無機鹽（選擇使用）	0~30g/l
還原防止劑	10 g/l
滲透劑	2 g/l
壓吸液溫度 20~25°C	


染料與鹼劑的混合必須使用定量混合泵。
滲透劑的選用應注意是否適合於壓吸液，並且是非起泡性。

蒸處：


飽和蒸氣 102~105°C 下蒸處 60~100 秒。

鹼劑需求：

一浴壓染蒸處工程鹼劑需求表：

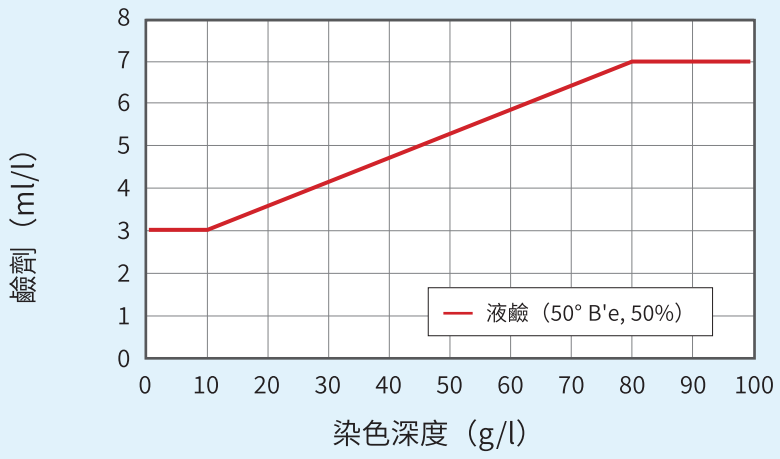

5. 一浴濕短蒸染色法 Emoistfix process

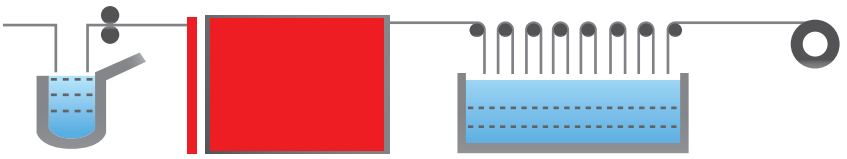

染液壓吸　(IR 預乾)　　水洗
熱固著及蒸處

一浴濕短蒸染色是結合一個連續式的熱固著及低量蒸氣的蒸處過程。染料與鹼劑充分混合在一起，進行染色固著，染色過程簡單更經濟。

特性

Everzol 使用在一浴濕短蒸工程擁有：

- 高固著率及高得色值。
- 優異的溶解度及鹼浴的染液安定性。
- 實驗室與現場間再現性及可靠性高。
- 淺～深色系色域應用範圍廣泛。

染色壓吸液組成：

染液與鹼劑必須分別調製，染色前再以定量泵混合。

染液組成：

Everzol 染料	x g/l
還原防止劑	5~10 g/l
移行防止劑 （選擇使用）	0~1 g/l
滲透劑	0~2 g/l
尿素（選擇使用）	0~50 g/l

滲透劑的選用應注意是否適合於壓吸液，並且是非起泡性。
尿素的添加可改善部份染料的溶解度。

鹼劑需求：

Everzol 染料	Everzol 染料使用濃度（g/l）					
	~20	20~40	40~60	60~80	80~100	100 ↑
液鹼 50° B'e, 50% (ml/l)	4	6.5	8	10	12	14
純鹼	20g/l					

定量混合泵使用是必需的。

壓吸液溫度 20~25°C。

壓吸：

將製備好的調液與織物進行浸漬、濕潤、吸附後以壓榨輥輪壓吸一定量的染液於織物上；此時織物在壓吸過程中有一均一的吸收是相當重要的，並應確認壓吸於一致的壓吸率下。

一個理想的壓吸結果建立在下面幾個作業因子：

壓吸液溫度：溫度太高的壓吸液，易造成頭尾異色的異常；保持在恆定一般室溫下，對染色結果是較理想的。

織物：織物在前處理之後，除確認前處理後的品質之外，必須加以冷卻，並確認是均一的乾燥程度，且維持織物在恆定的室溫與一致的含濕率。

壓吸槽：為了使壓吸槽內染液與織物吸收之間有一良好的交換率，壓吸槽的體積建議愈小愈好，尤其是輕薄織物；此外壓吸時入布的恆速，皆能有效防止頭尾異色或顏色差異的產生。

固色條件：

於 120~130°C，固色 2~3 分鐘。

蒸氣含濕控制：25%

確認染色織物乾燥完全，可獲得較一致的得色率。

6. 水洗工程



一般連續式水洗工程如下：

冷水溢流洗	1 槽	30~40°C
溫水洗	1 槽	50~60°C

（中和，鹼劑非使用水玻璃的場合；若鹼劑為使用水玻璃的話，則建議在最後一槽才進行中和。）

熱水洗	2 槽	90~95°C
皂洗	2 槽	90~95°C
溫水洗	1 槽	50~60°C
冷水洗	1 槽	30~40°C

（中和，控制 pH 值於 6~7）

對反應性染料而言，水洗工程的良莠，將對染色織物的牢度有相當大的影響，故必須在水洗工程中，將未固著的多餘染料完全的清洗掉；其最重要的一點為在水洗工程中，能有較高的熱水洗溫度及足夠的熱水洗時間，此外並應有足夠的溢洗水流，使水洗槽內被洗掉的殘留染料濃度降低，以增進洗淨效果。

為了能保有良好的皂洗或熱水洗效果，熱水洗及皂洗槽的溫度條件必須設定於 90~95°C。

7. 聚醯胺（尼龍）／纖維素纖維織物

聚醯胺（尼龍）／纖維素纖維交織物可以 Everzol 染料先用冷壓染色法染纖維素側，再利用浸染法完成聚醯胺側的染色。其目的為能有效降低反應性染料對聚醯胺側的污染而獲得良好的濕堅牢度。

纖維素纖維在冷壓染染色流程：

見冷壓染色法。（第 A–3 頁）

聚醯胺纖維在浸染的染色流程：

本公司提供一系列酸性染料產品，供您在聚醯胺側的染色。

染料特性

Everacid A 染料

- 淺濃度耐日光牢度佳。
- 淺濃度耐濕牢度佳；中深濃度則需固色後處理。
- 極佳之移染性及均染性。
- 纖維遮覆性佳。
- 配色色域廣。
- 非金屬型染料。
- 染法簡易。

Everacid N 染料

- 深色染深性佳。
- 耐日光牢度屬中等至優。
- 中等濃度耐濕牢度佳，深濃度需固色處理。
- 中等至佳之移染性。
- 遮覆性佳，搭配使用均染劑遮覆性更佳。
- 配色色域廣，色相鮮豔。
- 大多為非金屬型染料（黑色系除外）。

Everset M 染料

- 主要為 1：2 型含金複合型酸性染料。
- 對不同型態聚醯胺纖維染深性佳，如超細纖維。
- 耐日光牢度佳。
- 深濃度耐濕牢度極佳。
- 中等纖維遮覆性。
- 染料相容性佳。
- 染法簡易。

Everset PA 染料

- 染料組合性佳。
- 濕牢度優異。
- 染深性佳。
- 高耐日光牢度。
- 高耐氯漂牢度。


Everacid S 染料

- 高彩度酸性染料。
- 對不同型態尼龍染深性佳，如超細纖維。
- 深濃度耐日光牢度極佳。
- 深濃度耐濕牢度極佳。
- 染料相容性佳。
- 非含金染料
- 染法簡易。

Everacid X 染料

- 對尼龍超細纖維有極佳的染深效果。
- 深色廢水極少。
- 深濃度耐日光牢度與耐濕牢度極佳。
- 染料相容性佳。

浸染法

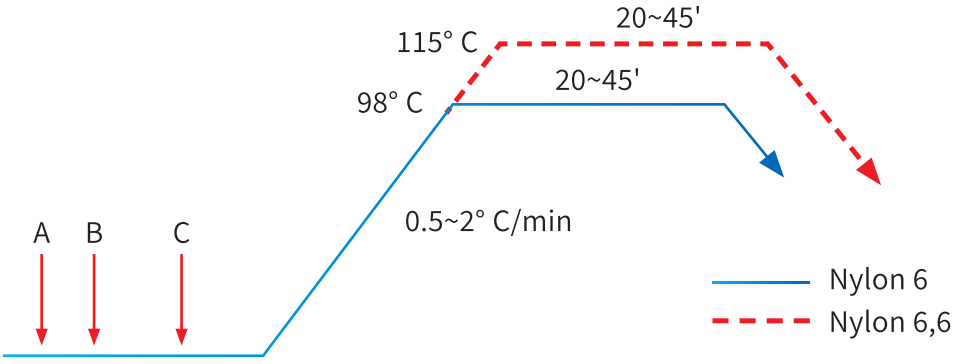


A：均染劑　　B：酸性染料　　C：硫酸銨；醋酸

染色 pH 值

染料類型	最佳 pH 值		
	淺色	中色	深色
Everacid A	5.5~6.5	5.0~6.0	—
Everacid N	5.0~6.0	4.5~5.5	4.0~5.0
Everacid S	5.0~6.0	4.5~5.5	4.0~5.0
Everacid X	—	4.5~5.5	4.0~5.5
Everset M	—	4.5~5.5	4.0~5.5
Everset PA	—	5.5~6.5	5.0~6.0

註：起始 pH 值，可使用醋酸與醋酸鈉設定。

吉革染色法

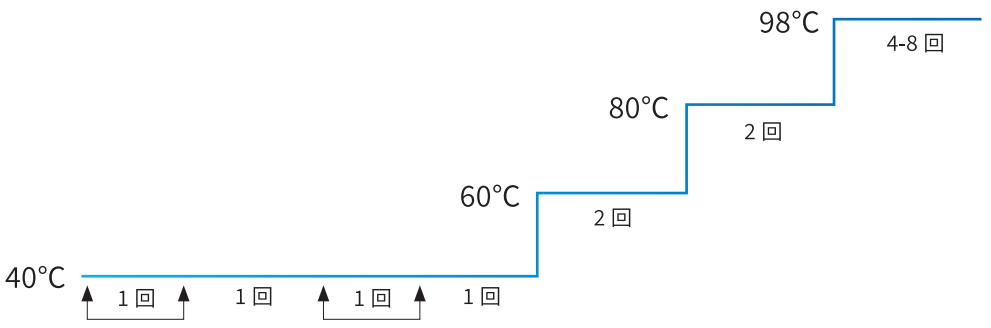

建議染法：

— 助劑以 1/2 比例分 2 回加入吉革染機：
均染劑 1–3g/l
硫酸銨搭配冰醋酸調整 pH 值
— 酸性染料以 1/2 比例分 2 回加入吉革染機
— 昇溫至 60°C，運轉 2 回
— 昇溫至 80°C，運轉 2 回
— 昇溫至 98°C，運轉 4–8 回或至少 60 分鐘

後處理

為了增進酸性染料染色濕牢度，特別是中、深濃度必須施以後處理，固色劑種類建議使用合成型之固色劑。

Everlight Chemical

Everacid ／ Everset 染料組合推薦

Everacid 三原色推薦

淺色
Everacid Yellow A-4R
Everacid Red A-2BN
Everacid Blue A-RL

中色
Everacid Yellow N-3R
Everacid Red N-2BL
Everacid Blue N-RL

深色
Everacid Orange N-GTL
Everacid Rubine N-5BL
Everacid Cyanine N-5R

Everacid S

主要應用於鮮艷色系，有別於傳統三原色的概念，建議選取主色後再搭配其他染料進行調色。

Everacid X 系列

Everacid Yellow X-BW
Everacid Red X-BW
Everacid Blue X-BW

輔助色
Everacid Bordeaux X-BW
Everacid Brown X-BW

Everset 三原色推薦

Everset M 系列

Everset Yellow M-2R
Everset Red M-G
Everset Grey M-G

輔助色
Everset Bordeaux M-B
Everset Blue M-2R

Everset PA 系列

Everset Yellow PA
Everset Red PA
Everset Blue PA

輔助色
Everset Yellow PA-2G
Everset Bordeaux PA
Everset Navy PA

Everzol 染料三原色組合推薦

淺色系

極佳的染色再現性
優異的日光堅牢度
無雙面色差
無光致變性

Everzol Yellow C–GL
Everzol Red C–3B
Everzol Blue C–BB 133%

補足色系：
Everzol Yellow LX
Everzol Red LF–B
Everzol Red LF–2B
Everzol Blue C–LX
Everzol Black C–RL

淺、中色系

優異的汗日光堅牢度
適合磨毛織物
無光致變性

Everzol Yellow CE–N
Everzol Red LF–B
Everzol Blue C–BRF

補足色系：
Everzol Yellow C–GL
Everzol Red LF–2B
Everzol Red LF–4B
Everzol Blue C–R S/P
Everzol Blue C–LX

中、深色系

極佳的染色再現性
染深性佳
高得色值
日光牢度佳

Everzol Yellow ED
Everzol Red ED–7BN
Everzol Blue L–ED

補足色系：
Everzol Yellow ED–R
Everzol Red ED–3B
Everzol Red ED–S
Everzol Blue C–BRF
Everzol Navy ED

Everlight Chemical

鮮綠色系

鮮綠的
極佳的染色再現性

Everzol Turq. Blue C–G 133%

補足色系：
Everzol Yellow 4GL
Everzol Blue ED–G
Everzol Blue C–R s/p
Everzol Navy C–GG 133%

豔色系

極佳的染色再現性

Everzol Orange FC
Everzol Scarlet FC
Everzol Blue FC

補足色系：
Everzol Orange C–2R
Everzol Flavine FC

寶藍及紫色系

鮮豔的
良好的染色再現性

極佳的耐鹼溶解度

Everzol Blue C–R s/p

補足色系：
Everzol Red 3BS H/C
Everzol Blue C–BB 133%
Everzol Blue ED–G

丈青、深藍色系

經濟性
在 CPB 工程可短時間固著
高固著率

極佳的染色再現性
優異的染深性
易水洗

Everzol Yellow C–RN
Everzol Red C–RB 133%
Everzol Navy C–GB H/C

補足色系：
Everzol Black C–B 133%
Everzol Dark Blue LF（日光牢度佳）

自然敏感色系

高耐日光牢度
優異的耐氯水牢度

高耐汗日光牢度

Everzol Yellow CS
Everzol Red Brown CS
Everzol Olive CS
Everzol Grey CS

補足色系：
Everzol Orange CS

中、深色系

極佳的染色再現性
日光牢度佳

無光致變性

Everzol Yellow CE–N
Everzol Red ED–7BN
Everzol Blue L–ED

補足色系：
Everzol Orange ED–4R
Everzol Blue C–BRF

Everlight Chemical

深黑色系

極佳的染色再現性
高固著率
Everzol Black ED–G
Everzol Black ED–R
Everzol Black ED–3R

染深性佳
良好的水洗特性

補足色系
Everzol Black MWF
Everzol Black ED
Everzol Black EDN

中、深色系

極佳的染色再現性
Everzol Yellow ERC
Everzol Cardinal ERC
Everzol Dark Blue ERC

高效能易洗淨
補足色系
Everzol Amber ERC
Everzol Bordeaux ERC
Everzol Blue ERC
Everzol Marine ERC

臺灣永光化學工業股份有限公司

Everlight Chemical Industrial Corporation

Everzol Dyes

Cold Pad–Batch and Continuous Dyeing

English Version

Better Chemistry Better Life

Brand Promise

Through the passionate pursuit of progress and innovation, Everlight Chemical contributes to the successes of our customers. Our work helps create a better community and ensure a sustainable future. We believe that the intelligent application of chemistry can help make the world a better place.





Brand Values

Everlight Chemical believes that the intelligent application of chemistry can help make the world a better place. Everlight Chemical has earned recognition by customers and stakeholders for the following brand values:

Reliability

Everlight Chemical's brand trustworthiness is built upon a core value of integrity, determination to deliver on promises, stable product quality, and attentive service.

Client-Centric

Customer Caring with Value Creation is Everlight Chemical's Quality Policy. Our mission is to help clients achieve success through our high-quality products, innovative solutions, and technical support.

Innovation

Focusing on our core competency-Chemistry, Everlight Chemical highly values R&D that leads to breakthroughs and progress in developing chemical products that benefit humanity.

Welfare

Contribution to the welfare of society is high among Everlight Chemical's priorities. We hope our work can contribute to a brighter future for all of mankind.

CONTENTS

Everzol Dyes for continuous dyeing introduction A–41

Dyeing process of cellulose

1. Cold Pad–Batch process A–42
2. Pad–Dry–Chemical Pad–Steam process A–54
3. Pad–Dry–Baking process A–58
4. Pad–Steam process A–61
5. Emoistfix process A–63
6. Wash–off process A–65

Dyeing process of blended fibres

7. Polyamide/cellulosic fibre blends A–66
   Cold Pad–Batch → Exhaust dyeing process

Recommended trichromatic combination A–71

Everzol Dyes color fastness A–76

Introduction

Everzol dyes are widely applied in Cold Pad–Batch and continuous dyeing processes.

They are :

- Designed and formulated to meet Cold Pad–Batch and continuous dyeing properties.
- Quality assurance by Cold Pad–Batch and continuous dyeing process inspections.
- Enhanced padding liquor stability.
- Enhanced solubility in alkali.

The advantages of Everzol dyes are :

- Batch to batch consistency in Cold Pad–Batch and continuous dyeing.
- Excellent stability and solubility in alkali solution.
- Uniformity of reproducibility.
- Robust to dyeing process variation.

The features of Everzol dyes

■ ***High fixation rate.***
Reduce effluent and save water.

■ ***Medium substantivity.***
Less tailing problem from dyes and good wash–off.

■ ***Good build up.***
High color yield, easy to dye heavy shades.


■ ***In Cold Pad–Batch.***
Dyeing on cotton component, less nylon side staining problem for N/C fabric.

■ ***Full range.***
Excellent compatibility for pale shades, and from medium to heavy shades.

Everzol dyes for your business have :

- Less dyestuff consumption thanks to high color yield.
- Excellent reproducibility.
- Short process, less time, high productivity, save water.
- Versatile application for continuous dyeing process.

1. Cold Pad–Batch process

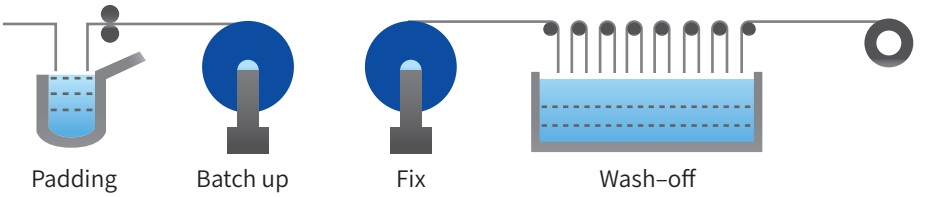

Features


Everzol dyes in Cold Pad–Batch have:

- Excellent solubility in alkali.
- Excellent padding liquor stability.
- High fixation rate and good color yield.
- Even dyeing.
- High productivity. Suitable for wide range of goods, especially for heavy fabrics, such as corduroy, velveteen, towel, emerized fabric and knitted fabrics etc.
- Less nylon staining problem for N/C fabric when dyeing the cotton component.


Padding:

In Cold Pad–Batch dyeing, the dye and alkali solutions are normally mixed at a ratio of 4 parts of the dye solution to 1 part of the alkali solution by volume. These solutions are mixed with a pump type alkali mixer before padding.

The dye and alkali solutions are mixed as follows:

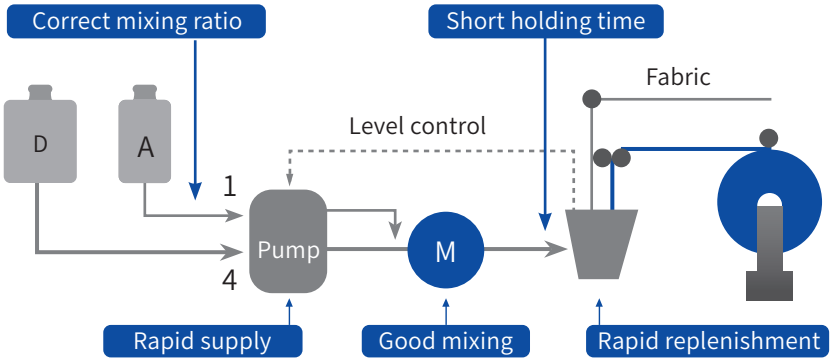

The padding method can be selected between trough padding and nip padding based on requirements. Trough padding provides longer penetration and absorption time; nip padding offers a faster dye liquor exchange.

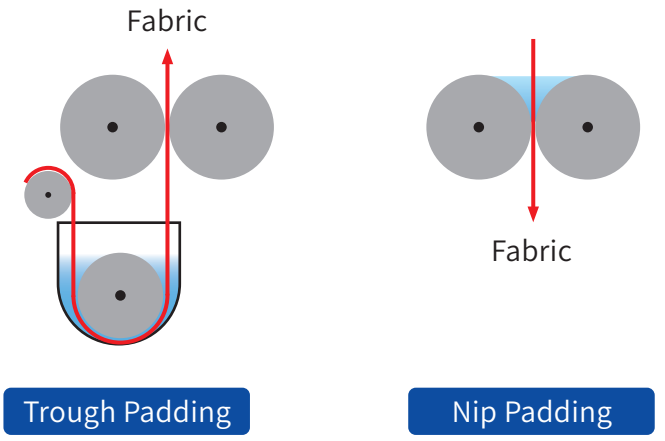

Alkali requirements:

We recommend 3 kinds of alkali for the Cold Pad–Batch process.

A. Silicate free method :

Everzol Dyes	Amounts of Everzol dyes used (g/l)						
	~10	10~20	20~40	40~60	60~80	80~100	100 ↑
Soda ash (g/l)	20	20	20	20	20	20	20
Caustic soda 50° B'e (ml/l)	4	5	7	10	12.5	15	16.5

B. Sodium silicate method :

Sodium silicate			Amounts of Everzol dyes used (g/l)					
			~20	30	40	50	60	70 ↑
	g/l	ml/l	Amounts of caustic soda 50° B'e, 50% required (ml/l)					
37~40° B'e	130	95	13.5	16.5	16.5	19.5	19.5	22
40~42° B'e	110	75	13.5	16.5	16.5	19.5	19.5	22
48~50° B'e	100	65	8.5	11.5	11.5	14.5	14.5	17.5
58~60° B'e	90	50	3.5	6.5	6.5	9	9	12

C. Modified silicate method :

Sodium silicate			Amounts of Everzol dyes used (g/l)					
			~10	20	30	40	50	60 ↑
	g/l	ml/l	Amounts of caustic soda 50° B'e, 50% required (ml/l)					
37~40° B'e	65	50	4	7	7	10	10	12.5
40~42° B'e	55	40	4	7	7	10	10	12.5
48~50° B'e	50	35	3	6	6	8.5	8.5	11.5
58~60° B'e	45	25	1.5	4	4	6.5	6.5	9

Auxiliary:

The penetrating agent must be stable in the padding liquor and non– foaming. Urea can be added to improve the solubility of some dyes.


Notes: The alkali C Modified silicate method reduces the amount of sodium silicate and caustic soda needed. A fixation time over 16 hours or overnight is necessary. For application of all the recommended alkalis listed above, a mixing pump is required.


Padding liquor stability:

The stability of padding liquor is depend on the type of alkali within the range of storage time and padding temperatures.

Example shown in the diagram. For most of reactive dyes in Cold Pad–Batch dyeing.

Relationship between alkali and stability

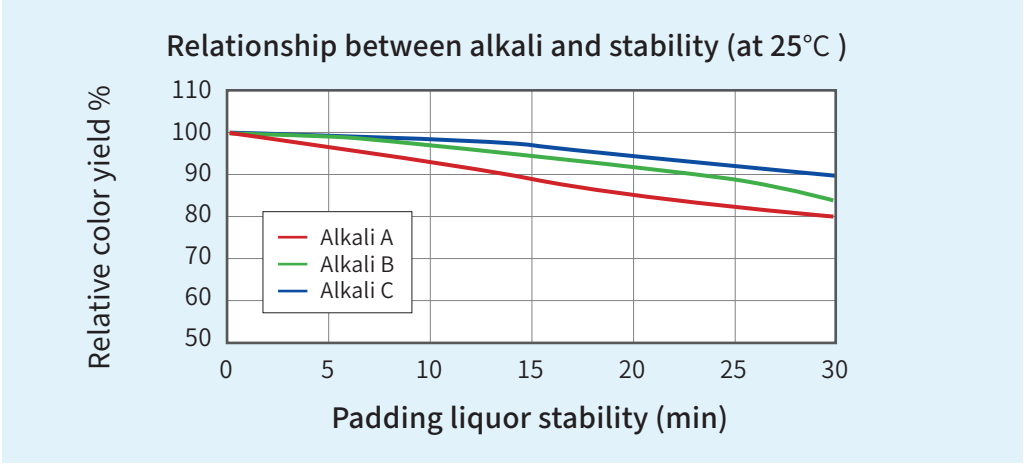

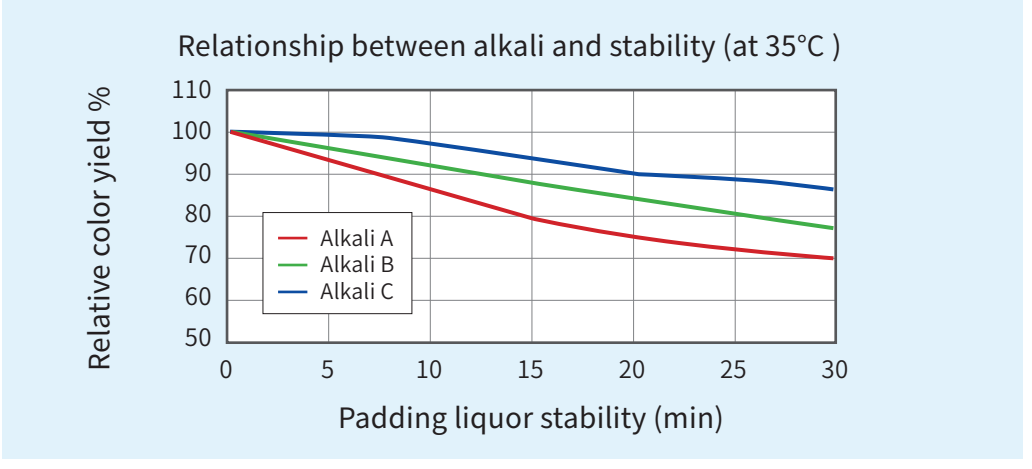


The alkali C Modified silicate method is especially designed for tropical climates when the padding liquor temperature and fixation temperature are around 30~40°C , to possess of excellent padding liquor stability.


Relationship between temperature and stability

For most of reactive dyes in Cold Pad–Batch dyeing.


In alkali A, silicate free method:

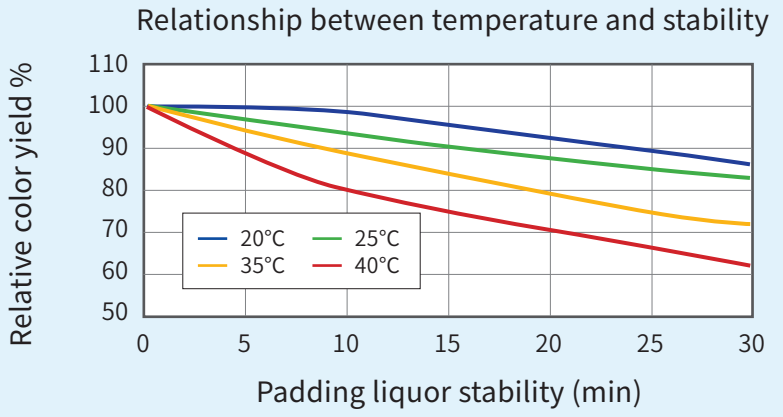

In alkali B, sodium silicate method:

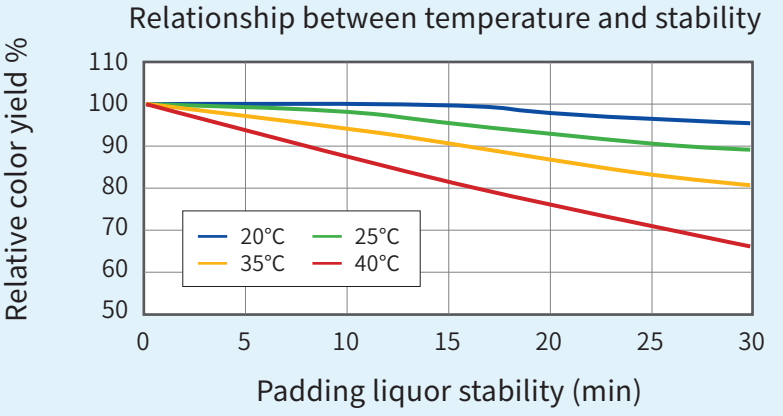

In alkali C, Modified silicate method:

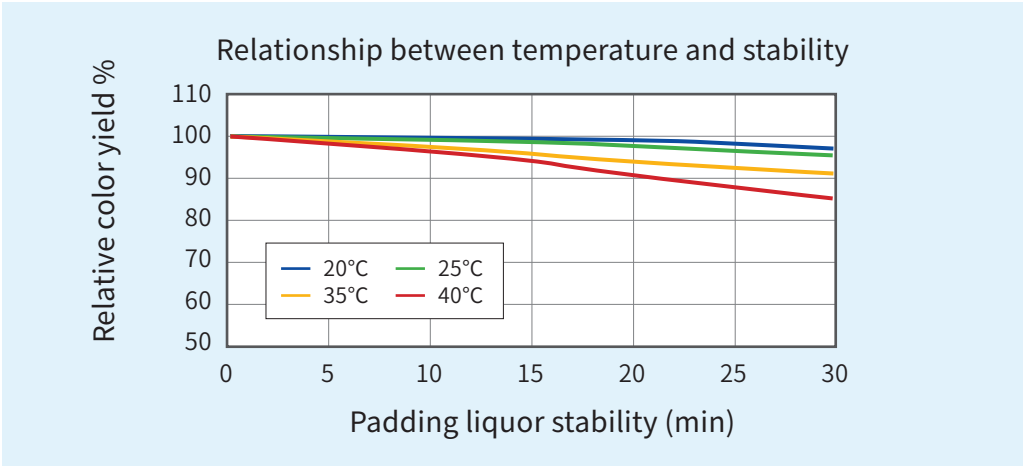

The alkali C Modified silicate method is especially designed for tropical climates when the padding liquor temperature and fixation temperature are around 30~40°C , to possess of excellent padding liquor stability. Certainly, when the padding liquor temperature and fixation temperature are normal room temperature around 20~25°C , a longer fixation time or even overnight storage is generally needed for this method of processing to be reliable.

Fixation:

The goods are batched up after padding. To avoid any effects from outside factors (air), they are wrapped in plastic film and sealed so that the roll is airtight.


The batched roll is then continuously rotated with care taken to ensure that the selvages are aligned. The rolls must be stable and rotate slowly and horizontally.

The dyes are fixed at a constant temperature (generally close to the padding liquor temperature) and for the duration of the fixation time.

In the production workshop, we generally recommend a minimum fixation time of 4 hours and at least 25°C or more after batching. If long yardages or large batched, it is better to increases 2 hours or more of the fixation time. This is recommendation to avoid tailing when customer proceed short batching time. Longer fixation times (up to 48 hours) at room temperature do not alter the shade.


If the fixation temperature is considerably lower, the minimum fixation time must be increased or overnight. If the fixation temperature is considerably higher, we suggest that the maximum fixation time does not exceed 24 hours.

Relationship between temperature and fixation time

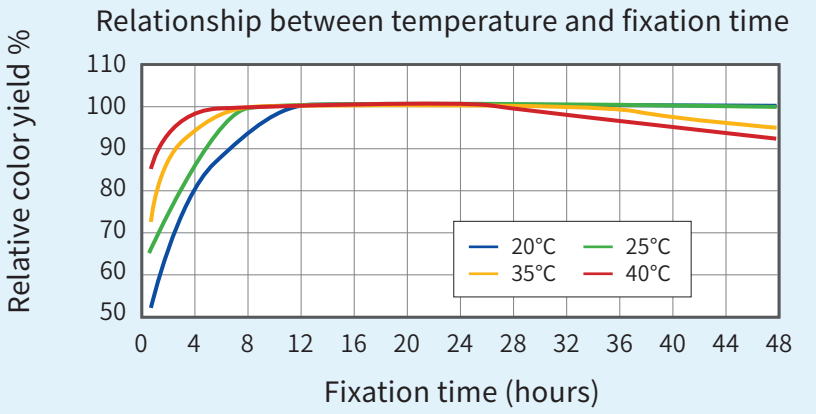

Test alkali: Alkali B: sodium silicate method,
Mercerized cotton

If the fixation temperature is considerably higher, we suggest that the maximum fixation time does not exceed 24 hours.

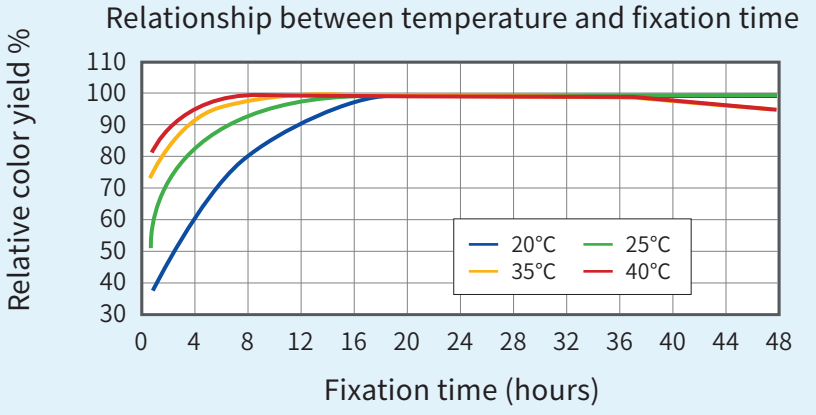


Test alkali: Alkali C: Modified silicate method
Mercerized cotton


The alkali C Modified silicate method is especially designed for tropical climates when the fixation temperature is around 30~40°C , to provide excellent batch stability and shade repeatability.

Relationship between alkali and fixation time requirement

For most of reactive dyes:

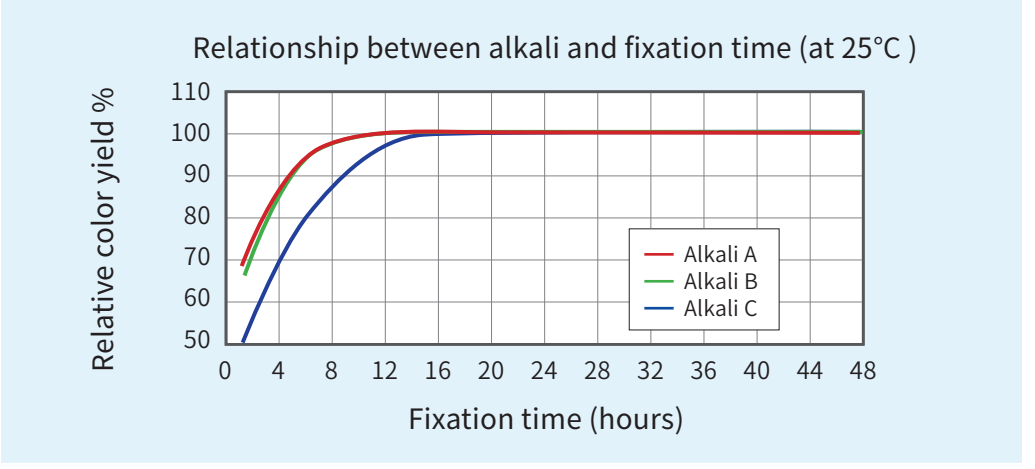

Mercerized cotton

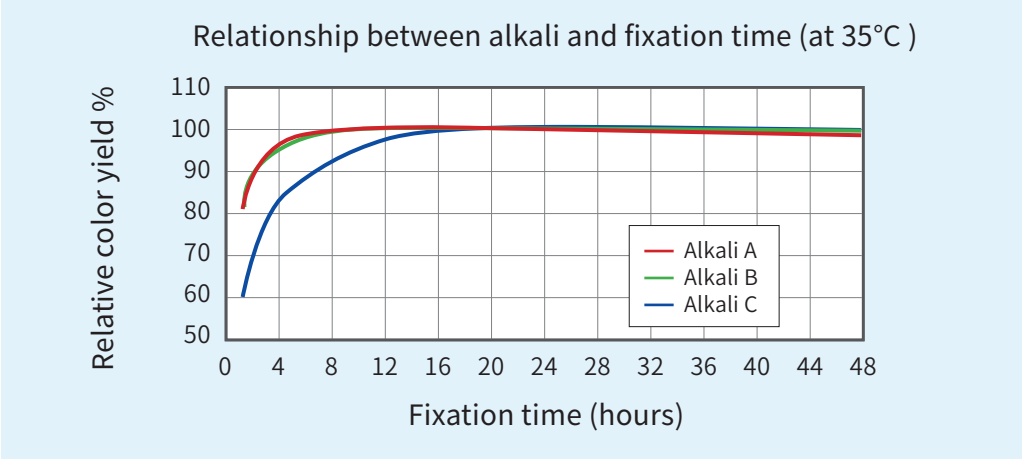

Mercerized cotton

The alkali C Modified silicate method is especially designed for tropical climates, to provide excellent batch stability and shade repeatability.

When the padding liquor temperature and fixation temperature are normal room temperature around 20~25°C , a longer fixation time or even overnight storage is generally needed for this method of processing to be reliable.

Fixation time requirements for Everzol dyes

For mercerized cotton

Series	I	II	III	IV
Yellow	Yellow C–GL Yellow C–GR Yellow C–RN	Orange ED–4R	Yellow CE–N Orange C–2R Yellow LX Yellow ED–R Yellow ERC	Yellow ED Yellow CS Flavine FC Orange CS Orange ED–N
Red	Red C–3B Red C–RB 133%	Red C–D Red ED–2B	Red LX Red LF–B Red LF–2B Red ED Red ED–S Red ED–3B Red ED–7BN	Red LF–4B Rubine ED Red Brown CS Orange FC Scarlet FC
Blue	Navy C–GG 133% Black C–B 133%	Blue C–R S/P Navy C–GB H/C	Blue C–BB 133% Blue L–ED Navy C–FB Navy ED Blue ERC	Turq. Blue C–G 133% Blue ED–G Blue ED Blue C–BRF Blue C–LX Blue FC
Other	Black C–RL Black ED Black ED–G Black ED–R Black ED–3R Black EDN Jet Black ERC	Dark Blue LF Black MWF Black ERC	Amber ERC Light Red ERC Cardinal ERC Bordeaux ERC Dark Blue ERC Marine ERC	Grey LF Olive CS Grey CS
Fixation time	~4hrs ↑	~8hrs ↑	~12hrs ↑	~16hrs ↑

Alkali requirements: Alkali A silicate free method
Alkali B sodium silicate method
Material: Mercerized cotton
Fixation temperature: 25°C

If the dyes combination involve more than one series, that means different dyes have different fixation time to be combined together, fixation time should be chosen the longest one among all the dyes in the recipe. For the alkali C Modified silicate method, a longer fixation time (above 16 hrs) or an overnight storage is necessary.

Fixation time requirements for Everzol dyes

For unmercerized cotton, the fixation time are the following:


Series	I	II	III	IV
Yellow	Yellow C–GL Yellow C–GR Yellow C–RN	Orange ED–4R	Yellow CE–N Orange C–2R Yellow LX Yellow ED–R Yellow ERC	Yellow ED Yellow CS Flavine FC Orange CS Orange ED–N
Red	Red C–3B Red C–RB 133%	Red C–D Red ED–2B	Red LX Red LF–B Red LF–2B Red ED Red ED–S Red ED–3B Red ED–7BN	Red LF–4B Rubine ED Red Brown CS Orange FC Scarlet FC
Blue	Navy C–GG 133% Black C–B 133%	Blue C–R S/P Navy C–GB H/C	Blue C–BB 133% Blue L–ED Navy C–FB Navy ED Blue ERC	Turq. Blue C–G 133% Blue ED–G Blue ED Blue C–BRF Blue C–LX Blue FC
Other	Black C–RL Black ED Black ED–G Black ED–R Black ED–3R Black EDN Jet Black ERC	Dark Blue LF Black MWF Black ERC	Amber ERC Light Red ERC Cardinal ERC Bordeaux ERC Dark Blue ERC Marine ERC	Grey LF Olive CS Grey CS
Fixation time	~8hrs ↑	~12hrs ↑	~16hrs ↑	~24hrs ↑

Alkali requirements: Alkali A silicate free method
Alkali B sodium silicate method
Material: unmercerized cotton
Fixation temperature: 25°C

If the dyes combination involve more than one series, fixation time should be the longest one. For the alkali C Modified silicate method, a longer fixation time (above 16 hrs) or overnight storage is necessary. For knitted fabric a longer fixation time (above 16 hrs) or overnight storage is necessary.

In the Cold Pad–Batch process, attention must be given to:


◆ *Solubility in alkali*

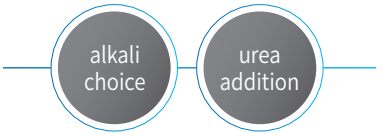

Alkali choice: In alkali C (Modified silicate method) has good solubility for some dyes.

Urea addition: Urea can be added to improve the solubility of some dyes.


◆ *Stability in padding liquor*

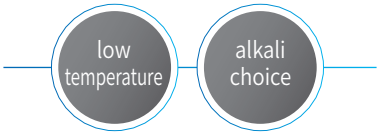

Low temperature: It is preferred to keep the padding liquor at low temperature. If urea can be added to the padding liquor, the padding liquor will cool further since urea absorbs heat as it dissolves. A higher padding temperature will reduce the padding liquor stability which may cause tailing problem and reduce the dye yield.


Alkali choice: Dyes in alkali C (Modified silicate method) has excellent padding liquor stability, especially for tropical climates.

◆ *Temperature*

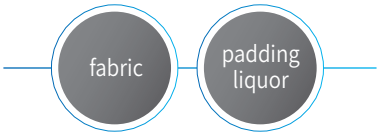


Cooling the goods after the pretreatment and cooling the padding liquor are also required. A higher temperature of the padding liquor can lower the padding liquor stability and reduce the dye yield. While higher padding temperatures reduce the padding liquor stability, non constant temperature of goods can cause uneven absorbs and tailing problem.

◆ *Fixation time management*

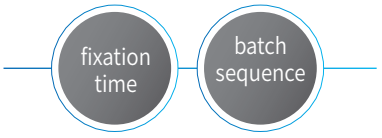

Have sufficient fixation time and wash each batch by a priority schedule to ensure shade continuity.

◆ *Condition of atmosphere change*

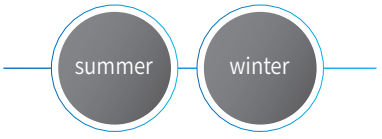


Pay attention to atmosphere change, because fixation yield and reproducibility varies with the batching condition.

Cold Pad–Batch the rapid dyeing method in the laboratory.

Dry oven method, good reproducibility to various fabrics by rapid dyeing method. Besides, it is easy to make sure right color matching between laboratory and bulk dyeing.

Optimum condition: 60°C x 30min or 70°C x 20min

2. Pad–Dry–Chemical Pad–Steam process

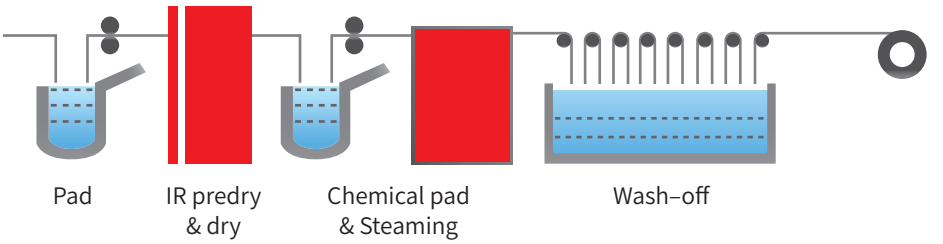

The dyes and chemical alkali are applied separately on the goods to be dyed in two batch continuous dyeing; a wide selection of dyes are available for this method.

Features

Everzol dyes in the Pad–Dry–Chemical Pad–Steam process have:

- Even dyeing.
- Good stability in steaming.
- High fixation rate.
- High productivity.

Padding liquor condition:

Everzol dyes	x g/l
Migration inhibitor	1 g/l
Reduction inhibitor	10 g/l
Penetrating agent	0~2 g/l

The penetrating agent must also be stable in the padding liquor and be non– foaming.

Reduction inhibitor can be added to prevent reduction of the reactive dyes.

Urea can be added to improve the solubility of some dyes.

Padding:

It is essential that the goods to be padded be uniformly absorbent. Make sure fabric is supported and gets uniform pick up across the width of the goods.

Optimum padding results are achieved under the following conditions:

Padding temperature: Higher padding temperatures can cause a tailing problem. Keeping the padding liquor at a constant room temperature is highly recommended.

Goods: Must be evenly dried and cool. Cool the goods after the pretreatment. Maintain at a constant room temperature and even humidity content. Ensure the quality of the pretreatment.

Padding trough: Use of a small–volume trough to ensure a rapid exchange of the padding liquor and a constant padding speed will help avoid tailing problems.

Drying:

IR pre–drying
Dry to about 30% residual moisture
Dry at 110~130°C
Cool goods after drying

The fabric should have adequate cooling after drying.

Intermediate drying is required in the Pad–Dry–Pad–Steam process. Usually, infrared–heaters (pre–drying) are used with hot–flue machines or on steam heated cylinders (drying).

The pre–drying should reduce the moisture content to about 25~30%. Under these conditions, migration is unlikely to occur during subsequent drying.

If goods are dried on ranges without a pre–drying, airflow in the hot flue must be carefully balanced and a slow fan speed used.

Goods should be dried evenly across the full width and both sides to prevent migration.

Chemicals padding and Steaming:

Stabilize and give uniform chemical padding across the width of the goods.

Chemicals requirement:

A. Sodium silicate (48~50° B'e)	60~70 %
B. Caustic soda (50° B'e, 50%)	8~11.5 ml/l
Salt	250 g/l
C. Caustic soda (50° B'e, 50%)	7~10.5 ml/l
Soda ash	20 g/l
Salt	250 g/l


Steaming:

Continuous fixation of reactive dyes in saturated steam at 102~105°C .

Recommended steaming time:

30–70 secs
Everzol C Dyes : Yellow C–GL, Yellow C–GR, Yellow C–RN, Yellow CE–N Orange C–2R, Red C–3B, Red C–RB 133%, Red C–D Blue C–R S/P, Blue C–BB 133%, Blue C–BRF Navy C–GG 133%, Navy C–GB H/C, Navy C–FB Black C–B 133%, Black C–RL Black MWF **Everzol CS Dyes :** Yellow CS, Orange CS, Red Brown CS, Olive CS, Grey CS **Everzol LX/LF Dyes :** Yellow LX, Red LX, Red LF–B, Red LF–2B, Red LF–4B, Blue C–LX, Grey LF, Dark Blue LF **Everzol ED Dyes :** Yellow ED–R, Yellow ED, Orange ED–4R, Orange ED–N Red ED, Red ED–2B, Red ED–3B, Red ED–7BN, Red ED–S, Rubine ED Blue ED–G, Blue L–ED, Blue ED, Navy ED Black ED, Black ED–G, Black ED–R, Black EDN, Black ED–3R **Everzol FC Dyes :** Flavine FC, Orange FC, Scarlet FC, Blue FC **Everzol ERC Dyes :** Amber ERC, Yellow ERC, Light Red ERC, Cardinal ERC, Bordeaux ERC Blue ERC, Dark Blue ERC, Marine ERC, Black ERC, Jet Black ERC
70–100 secs
Turq. Blue C–G133%

3. Pad–Dry–Baking process

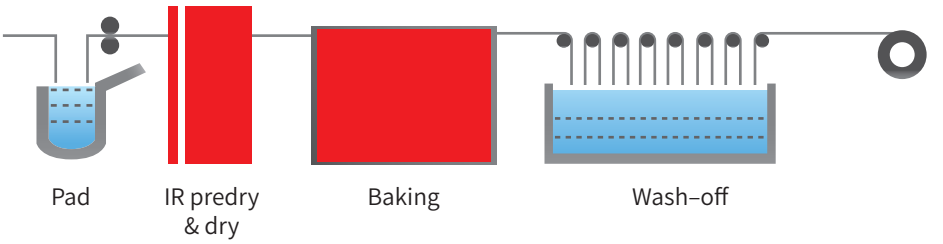

This is the one batch method continuous dyeing process.

Features

Everzol dyes in Pad–Dry–Baking process have:

- Even dyeing.
- Excellent stability in padding liquor.
- Excellent consistency in drying and baking.
- High productivity.

Padding liquor condition:

Everzol Dyes	x g/l
Alkali	see A–60
Migration inhibitor	1 g/l
Reduction inhibitor	10 g/l
Urea	50~150 g/l
Penetrating agent	0~2 g/l
Borax	0~10 g/l

The penetrating agent must also be stable in the padding liquor and be non– foaming.

Reduction inhibitor can be added to prevent reduction of the reactive dyes.

Urea can be added to improve the solubility of some dyes, which will raise the color yield in this continuous process. Urea will not be necessary when the baking temperature is higher than 160°C .

Borax can be added to prevent the cotton component yellowing.

Padding:

It is essential that the goods to be padded be uniformly absorbent. Make sure that the fabric is supported and gets uniform pick up across the width of the goods.

Optimum padding results are achieved under the following conditions:


Padding temperature: Higher padding temperatures can cause a tailing problem and reduce the dye yield. Padding liquor should be kept at a constant room temperature.

Goods: Must be evenly dried and cool. Cool the goods after the pretreatment. Maintain at a constant room temperature and even humidity content. Ensure the quality of the pretreatment is very important.

Padding trough: Use of a small–volume trough, to ensure a rapid exchange of the padding liquor and a constant padding speed will help avoid tailing problems.

Alkali requirements:

The alkali requirements are diagrammed below:

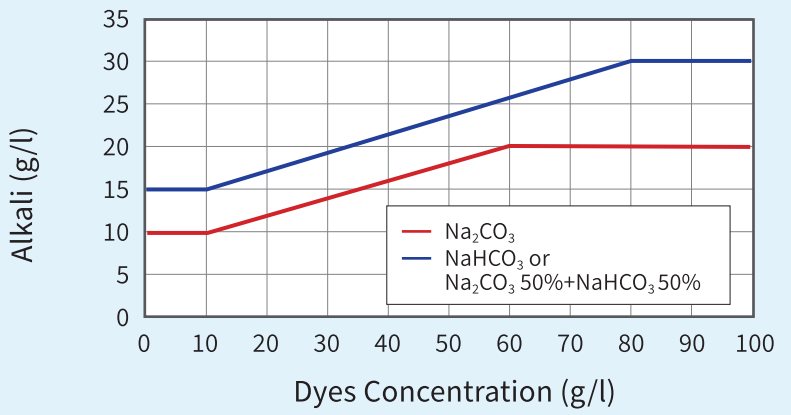

Drying:


IR pre–drying.
Dry down to about 30% residual moisture.
Dry at 100~120°C .

Baking:

4~6 min,	at 120°C
3~4 min,	at 140°C
2~3 min,	at 150°C
1.5~2 min,	at 160°C
1~2 min,	at 180°C
1 min,	at 200°C

Notes: Take care about the goods yellowing at high temperature. At high temperature dyeing i.e. 180~200°C , fabric yellowing should be counted in color matching.

4. Pad–Steam process

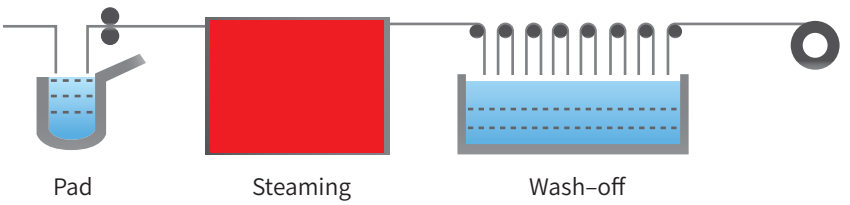

This one bath continuous dyeing process is suitable for heavy fabrics without intermediate drying, because of heavy fabrics for which intermediate drying would not be economical and that would be a risk of dyestuff migration.

Features

Everzol dyes in the Pad–Steam process have:

- Even dyeing.
- High productivity.
- Suitable for heavy fabrics such as corduroy, velveteen, towel and emerized fabric, etc.

Padding liquor condition:

Everzol dyes	x g/l
Caustic soda (50° B'e, 50%)	y ml/l
Soda ash	20 g/l
Glauber's salt (option)	0–30 g/l
Reduction inhibitor	10 g/l
Penetrating agent	2 g/l

Padding liquor temperature at 20~25°C

Alkali mixer is required.

The penetrating agent must also be stable in the padding liquor and be non– foaming.


Reduction inhibitor can be added to prevent reduction of the reactive dyes.

Steaming :


60~100 seconds in saturated steam at 102~105°C .

Alkali requirements:

The alkali requirements are diagrammed below:

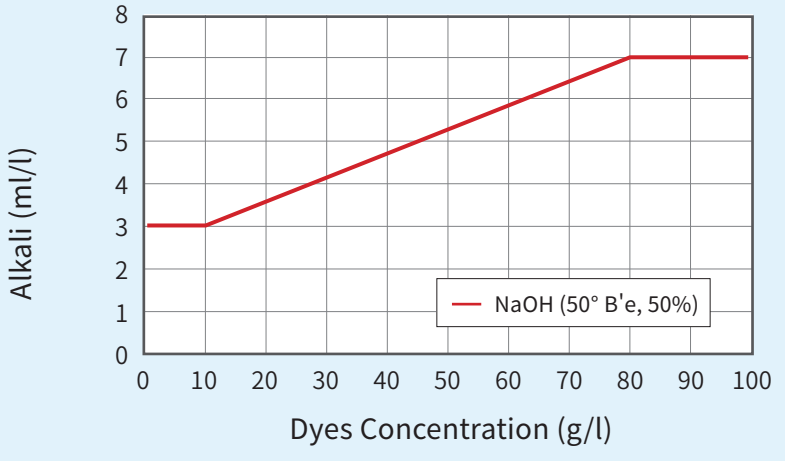

5. Emoistfix process

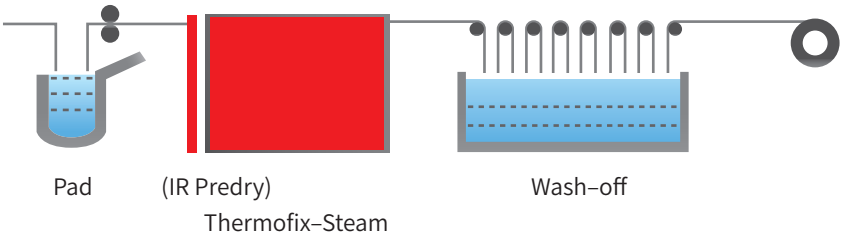

The Emoistfix process is a combination of continuous steaming and drying process. It combines dyestuff and alkalis padding together and then drying–fixing in one batch process by continuous application to make simple and more economical.

Features

Everzol dyes in the Emoistfix process have:

- High fixation rate and good color yield.
- Excellent solubility and stability in alkalis.
- High lab–to–bulk reproducibility and reliability.
- Full range of trichromatic from pale to heavy shades.

Padding liquor condition:

It is essential to make alkali and Everzol dye solution separately.

Padding liquor:

Everzol dyes	x g/l
Reduction inhibitor	5~10 g/l
Migration inhibitor (option)	0~1 g/l
Penetrating agent in padding liquor	0~2 g/l
Urea (option)	0~50 g/l

The penetrating agent must also be stable in the padding liquor and be non– foaming. Reduction inhibitor can be added to prevent reduction of the reactive dyes. Urea can be added to improve the solubility of some dyes.

Alkali requirements:

Everzol dyes	Amounts of Everzol dyes used (g/l)					
	~20	20~40	40~60	60~80	80~100	100 ↑
Caustic soda 50° B'e (ml/l)	4	6.5	8	10	12	14
Soda ash	20g/l					

An alkali mixer is required, as with the Cold Pad–Batch process. Padding liquor temperature at 20~25°C .

Padding:

It is essential that the goods to be padded be uniformly absorbent. Make sure that the fabric is supported and gets uniform pick up across the width of the goods.

Optimum padding results are achieved under the following conditions:

Padding temperature: Higher padding temperatures can cause a tailing problem and reduce the dye yield. Padding liquor should be kept at a constant room temperature.

Goods: Must be evenly dried and cool. Cool the goods after the pretreatment. Maintain at a constant room temperature and even humidity content. Ensure the quality of the pretreatment is very important.

Padding trough: Use of a small–volume trough, to ensure a rapid exchange of the padding liquor and a constant padding speed will help avoid tailing problems.

Drying and fixation:

2–3min at 120~130°C , it depends on the substrate.
Humidity control at 25%.
Make sure the dyed fabric is dry at the end of machine to achieve complete color yield.

6. Wash–off process



General wash–off process as the following:

Cold rinsing (with overflow)	1 box	at 30~40°C
Warm rinsing	1 box	at 50~60°C
(or neutralizing, when alkali without sodium silicate)		
Hot rinsing	2 box	at 90~95°C
Soaping	2 box	at 90~95°C
Warm rinsing	1 box	at 50~60°C
Cold rinsing	1 box	at 30~40°C
(neutralizing, pH value set at pH 6~7)		
(neutralize in the last rinsing bath when alkali with sodium silicate)		

The conditions used in the wash–off of reactive dyes will have a significant influence on the fastness properties of the finished fabric. It is essential that unfixed excess dye is completely removed during the wash-off process. The most important factors are achieving the highest possible temperature for the longest possible time, along with a sufficient overflow of fresh water to dilute the concentration of removed dye in the rinse baths, thereby enhancing the washing efficiency. To maintain good soaping and hot wash–off results, the temperature of the soaping and hot wash baths must be set at 90–95° C.

7. Polyamide/Cellulosic blended fabric

Polyamide/cellulosic fibre blends can be dyed with a two–bath process which provides good wet fastness and less polyamide staining than normally obtained with reactive dyes. Everzol dyes are used first in the Cold Pad–Batch process to dye the cellulosic component. Everacid dyes are then used to dye the polyamide component.

Cold Pad–Batch process:

See Cold Pad–Batch process. (page A–42)

Polyamide component in the exhaust dyeing process:

Properties

Everacid A dyes

- High light fastness, including pale shades.
- High wet fastness in pale shades; medium depths of shade need after–treatment.
- Outstanding migration and excellent leveling properties.
- Very good coverage of fibre irregularities, e.g. barre.
- Fully compatible for use in trichromatic dye combinations.
- Metal free.
- Simple dyeing method.

Everacid N dyes

- Good build–up to heavy depths of shade.
- Medium to very good light fastness properties.
- Good wet fastness up to medium depths; heavy shades require after–treatment.
- Medium to good migration.
- Good coverage of physical fabric variation when used in combination with a leveling agent.
- Compatible for use in a wide range of shades; can be used individually for bright fashion shade.

- Simple dyeing method.
- Mainly metal–free (exceptions blacks).

Everset M dyes

- Base on 1:2 metal complex dyes.
- Very good build–up on different types of polyamide (including microfibres).
- High light fastness properties.
- Medium migration.
- Moderate coverage of physical barre.
- Good compatibility.
- Simple dyeing method.

Everset PA Dyes

- Good compatibility.
- Very high wet fastness properties including heavy shade.
- Very good build–up.
- Excellent light fastness properties at all depth of shade.
- High chlorinated water fastness.


Everacid S dyes

- Brilliant acid dyes.
- Highly suitable for single dyeing.
- Very good build–up and levelness on nylon.
- Excellent light fastness properties for deep shades.
- Very high wet fastness properties in deep shades.
- Medium migration.
- Moderate coverage on barriness.
- Good compatibility.
- Simple dyeing method.

Everacid X dyes

- Excellent build-up on nylon microfibers.
- Minimal wastewater at deep shades.
- Outstanding light fastness and wet fastness at deep shades.
- Good compatibility.

Exhaust dyeing process

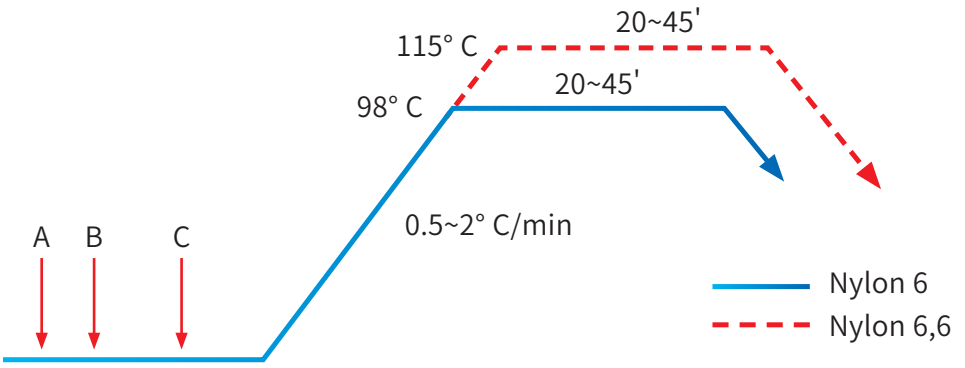


A: Levelling agent
B: Everacid / Everset Dyes
C: Ammonium Sulfate / Acetic Acid

Recommended Dyeing pH

Dyes	Optimum Dyeing pH		
	Pale Shade	Medium Shade	Dark Shade
Everacid A	5.5~6.5	5.0~6.0	—
Everacid N	5.0~6.0	4.5~5.5	4.0~5.0
Everacid S	5.0~6.0	4.5~5.5	4.0~5.0
Everacid X	—	4.5~5.5	4.0~5.5
Everset M	—	4.5~5.5	4.0~5.5
Everset PA	—	5.5~6.5	5.0~6.0

Remark: The below reference of pH setting by blending Acetic Acid & Sodium acetate.

Jig dyeing

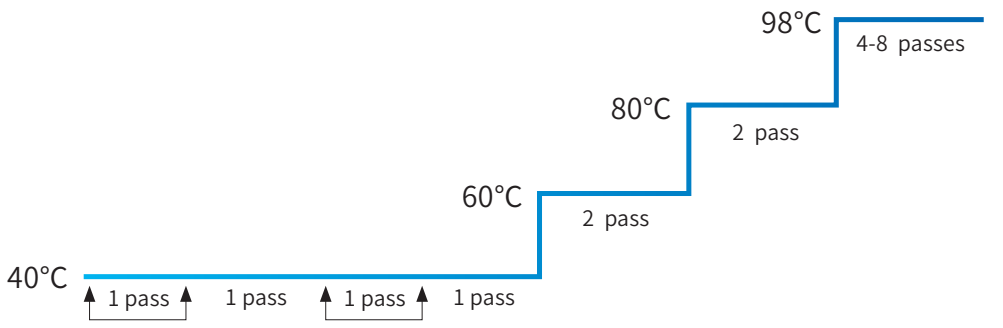

Suggestion:

- Chemicals dosing by 2 times, each half amount
  Leveling agent 1–3 g/l
  Ammonium Sulphate / Acetic Acid for pH setting
- Dyes addition by 2 times, each half amount
- Heating to 60°C . Then 2 pass
- Heating to 80°C . Then 2 pass
- Heating to 98°C . Then 4–8 pass or at least 60 min

After treatments

To improve the wet fastness, particularly at medium and deep shades, an after–treatment with a synthetic fixing agent is recommended.

Everlight Chemical

Recommended Everacid / Everset trichromatic

Everacid trichromatic

Pale shades

Everacid Yellow A-4R
Everacid Red A-2BN
Everacid Blue A-RL

Medium shades

Everacid Yellow N-3R
Everacid Red N-2BL
Everacid Blue N-RL

Deep shades

Everacid Orange N-GTL
Everacid Rubine N-5BL
Everacid Cyanine N-5R

Everacid S Range

Everacid S Range is specially designed for brilliant colors for Nylon. It is dominant as single shade dyeing. For certain shades, the shading by Everacid N, S dyes will be combined.

Everacid X Range

Everacid Yellow X-BW
Everacid Red X-BW
Everacid Blue X-BW

Supplementary

Everacid Bordeaux X-BW
Everacid Brown X-BW

Everset trichromatic

Everset M Range

Everset Yellow M-2R
Everset Red M-G
Everset Grey M-G

Supplementary

Everset Bordeaux M-B
Everset Blue M-2R

Everset PA Range

Everset Yellow PA
Everset Red PA
Everset Blue PA

Supplementary

Everset Yellow PA-2G
Everset Bordeaux PA
Everset Navy PA

Recommended Everzol dyes trichromatic

For pale shades

good reproducibility
suitable for emerized fabric
excellent lightfastness
non-photochromism

Everzol Yellow C-GL
Everzol Red C-3B
Everzol Blue C-BB 133%

Supplementary products:
Everzol Yellow LX
Everzol Red LF-B
Everzol Red LF-2B
Everzol Blue C-LX
Everzol Black C-RL

For pale-medium shades

excellent perspiration lightfastness
non-photochromism

Everzol Yellow CE-N
Everzol Red LF-B
Everzol Blue C-BRF

Supplementary products:
Everzol Yellow C-GL
Everzol Red LF-2B
Everzol Red LF-4B
Everzol Blue C-R S/P
Everzol Blue C-LX

For medium-heavy shades

good reproducibility
high build up
high color yield
good fastness to light

Everzol Yellow ED
Everzol Red ED-7BN
Everzol Blue L-ED

Supplementary products:
Everzol Yellow ED-R
Everzol Red ED-3B
Everzol Red ED-S
Everzol Blue C-BRF
Everzol Navy ED

Everlight Chemical

For brilliant turquoise and green shades

brilliant

good reproducibility

Everzol Turq. Blue C–G 133%

Supplementary products:
Everzol Yellow 4GL
Everzol Blue ED–G
Everzol Blue C–R S/P
Everzol Navy C–GG 133%

For brilliant red and scarlet shades

good reproducibility

Everzol Orange FC
Everzol Scarlet FC
Everzol Blue FC

Supplementary products:
Everzol Orange C–2R
Everzol Flavine FC

For royal blue and violet shades

brilliant

good reproducibility

excellent solubility in alkali

Everzol Blue C–R S/P

Supplementary products:
Everzol Red 3BS H/C
Everzol Blue C–BB 133%
Everzol Blue ED–G

For navy and dark blue shades

high fixation rate
short time fixation
good reproducibility
excellent build up
good wash–off

Everzol Yellow C–RN
Everzol Red C–RB 133%
Everzol Navy C–GB H/C

Supplementary products:
Everzol Black C–B 133%
Everzol Dark Blue LF
(high fastness to light)

For critical shades (Khaki, Olive, Grey)

excellent Light and Perspiration Light Fastness
good chlorinated water fastness

Everzol Yellow CS
Everzol Red Brown CS
Everzol Olive CS
Everzol Grey CS

Supplementary products:
Everzol Orange CS

For medium-heavy shades

good reproducibility
good fastness to light
non-photochromism

Everzol Yellow CE-N
Everzol Red ED-7BN
Everzol Blue L-ED

Supplementary products:
Everzol Orange ED-4R
Everzol Blue C-BRF

Everlight Chemical

For black shades

good reproducibility
high fixation rate
Everzol Black ED-G
Everzol Black ED-R
Everzol Black ED-3R

high build up
excellent wash-off property

Supplementary products:
Everzol Black MWF
Everzol Black ED
Everzol Black EDN

For medium-heavy shades

good reproducibility
Everzol Yellow ERC
Everzol Cardinal ERC
Everzol Dark Blue ERC

Eco Wash-off process
Supplementary products：
Everzol Amber ERC
Everzol Bordeaux ERC
Everzol Blue ERC
Everzol Marine ERC

Everzol C Dyes

頁 Page	染料 Dyes	10g/l	30g/l
*1	Yellow C–GL		
3	Yellow C–GR		
5	Yellow C–RN		
7	Yellow CE–N		
9	Orange C–2R		
*11	Red C–3B		
13	Red C–RB 133%		
15	Red C–D		

註 : Yellow C–GL、Red C–3B 染色濃度為 5g/l、20g/l
Notes: Yellow C–GL、Red C–3B the dyeing depth at 5g/l、20g/l

Everzol C Dyes

染料特性	Characteristics
● 優異的日光堅牢度 ● 適合防、拔染印花加工 ● 無光致變性	● Excellent in colorfastness to light. ● Suitable for resist and discharge printing. ● Non–photochromism.
● 配色色域廣 ● 適合防、拔染印花加工 ● 無光致變性	● A versatile Yellow dye. ● Suitable for resist and discharge printing. ● Non–photochromism.
● 配色色域廣、極佳的中深黃色染料 ● 適合防、拔染印花加工 ● 高得色率 ● 無光致變性	● A primary Yellow of trichromatic. ● Suitable for resist and discharge printing. ● High color yield. ● Non–photochromism.
● 全色域多功能黃色染料 ● 高耐光、耐汗日光堅牢度 ● 無光致變性	● Full gamut and primary yellow of trichromatic. ● High fastness to light and perspiration light. ● Non–photochromism.
● 高橘色以及猩紅色有廣泛的色度 ● 優異的染液安定性	● Brilliant Orange and wide range of Scarlet shade. ● Excellent solubility and stability in alkaline padding liquor.
● 優異的日光堅牢度	● Excellent in colorfastness to light.
● 配色色域廣、極佳的中深紅色染料 ● 高得色率	● A primary Red of trichromatic. ● High color yield.
● 高色值 ● 日光堅牢度佳 ● 適合防、拔染印花加工	● High color yield. ● Good color fastness to light. ● Suitable for resist and discharge printing.

Everzol C Dyes

頁 Page	染料 Dyes	10g/l	30g/l
17	Turq. Blue C–G 133%		
19	Blue C–R S/P		
*21	Blue C–BB 133%		
23	Blue C–BRF		
25	Navy C–GG 133%		
27	Navy C–GB H/C		
29	Navy C–FB		
31	Black C–B 133%		
*33	Black C–RL		
35	Black MWF		

註：Blue C–BB133%、Black C–RL 染色濃度為 5g/l、20g/l，黑色系染色濃度為 30g/l、60g/l
Notes: Blue C–BB133%、Black C–RL the dyeing depth at 5g/l、20g/l
Black shades the dyeing depth at 30g/l、60g/l

Everzol C Dyes

染料特性	Characteristics
● 極鮮艷的翠藍、翠綠色系	● Suitable for color match of brilliant green.
● 耐鹼溶解度佳 ● 耐氯水堅牢度佳 ● 適合防染印花加工 ● 優異的日光堅牢度	● Very good of solubility in alkali. ● Good in colorfastness to chlorinated water. ● Suitable for resist printing. ● Excellent color fastness to light.
● 極佳的淺色系配色用藍色染料 ● 優異的日光堅牢度 ● 適合防染印花加工	● A primary light Blue of trichromatic combination. ● Excellent color fastness to light. ● Suitable for resist printing.
● 極佳的配色用藍色染料 ● 優異的日光堅牢度	● A primary Blue of trichromatic combination. ● Excellent color fastness to light.
● 綠色系配色用丈青染料 ● 適合防拔染印花加工	● A versatile Navy dye with Green shade. ● Suitable for resist and discharge printing.
● 經濟的三原色配色用藍色染料，配色色域廣 ● 適合防、拔染印花加工	● An economical versatile navy dye with green and broad color range for color matching. ● Suitable for resist and discharge printing.
● 配色色域廣、極佳的丈青染料 ● 耐氯水堅牢度佳	● A primary Navy broad color range for color match. ● Excellent in colorfastness to chlorinated water.
● 經濟的深色染料	● An economical versatile heavy navy dye.
● 優異的日光堅牢度	● Good in color fastness to light.
● 優異的耐多次水洗牢度(M&S C10A) ● 良好的耐氯水牢度 ● 優異的耐鹼與染液安定性	● Excellent multi-laundering fastness (M&S C10A). ● High fastness to chlorinated water. ● Excellent alkali stability in CPB dyeing.

Everzol CS Dyes

頁 Page	染料 Dyes	5g/l	20g/l
37	Yellow CS		
39	Orange CS		
41	Red Brown CS		
43	Olive CS		
45	Grey CS		

Everzol FC Dyes

頁 Page	染料 Dyes	10g/l	30g/l
*47	Flavine FC		
49	Orange FC		
51	Scarlet FC		
53	Blue FC		

註 : Flavine FC 染色濃度為 5g/l、20g/l
Notes: Flavine FC the dyeing depth at 5g/l、20g/l

Everzol CS Dyes

染料特性	Characteristics
● 敏感色系穩定性佳 ● 高耐日光及良好的耐氯水堅牢度	● Suitable for critical colors dyeing. ● Excellent light–fastness & exceptional chlorinated water fastness.
● 敏感色系穩定性佳 ● 高耐日光及良好的耐氯水堅牢度	● Suitable for critical colors dyeing. ● Excellent light–fastness & exceptional chlorinated water fastness.
● 敏感色系穩定性佳 ● 高耐日光及良好的耐氯水堅牢度	● Suitable for critical colors dyeing. ● Excellent light–fastness & exceptional chlorinated water fastness.
● 敏感色系穩定性佳 ● 高耐日光及良好的耐氯水堅牢度	● Suitable for critical colors dyeing. ● Excellent light–fastness & exceptional chlorinated water fastness.
● 敏感色系穩定性佳 ● 高耐日光堅牢度	● Suitable for critical colors dyeing. ● Excellent light–fastness.

Everzol FC Dyes

染料特性	Characteristics
● 適合於鮮豔螢光黃及亮綠色 ● 優異染色再現性 ● 優異之水牢度	● Fashionable brilliant fluorescent yellow & green shades ● Right First Time performance ● Excellent wet fastness
● 適合於艷橙、大紅色流行色系 ● 高彩度、高染深性 ● 高日光、高汗日光、高耐氯水牢度	● Suitable for very brilliant orange, scarlet fashionable colors ● High chromatic, good build–up ● Exceptional lightfastness, perspiration lightfastness, chlorinated water fastness
● 適合於鮮豔緋紅、大紅流行色系 ● 高彩度、高染深性、洗淨性佳 ● 各項牢度優異	● Suitable for very brilliant scarlet, red fashionable colors ● High chromatic, good build–up, easy wash-off ● Overwhelming fastness performance
● 適合於鮮豔天空藍色、紫色系 ● 均染性佳 ● 優異之日光及濕牢度	● Extraordinary brilliant sky blue & violet & purple shades ● Unique Leveling performance ● Excellent lightfastness & wet fastness

Everzol LX & LF Dyes

頁 Page	染料 Dyes	5g/l	20g/l
55	Yellow LX		
57	Red LX		
59	Red LF–B		
61	Red LF–2B		
63	Red LF–4B		
65	Blue C–LX		
67	Grey LF		
69	Dark Blue LF		

Everzol LX & LF Dyes

染料特性	Characteristics
● 黃色三原色，配色色域廣 ● 適合與 Red LF–B、LF–2B 與 Blue C–LX 搭配	● A tinctorial Yellow, broad color yield for color match. ● Compatible with Everzol Red LF–B, LF– 2B and Blue C–LX.
● 配色色域廣，與 Yellow LX、 Blue C– LX 搭配	● Compatible with Everzol Yellow LX and Blue C–LX.
● 淺色系中有良好的日光堅牢度及耐汗日光堅牢度 ● 適合與Yellow CE-N、Blue C–LX 搭配	● Good lightfastness and perspiration lightfastness at pale shade. ● Compatible with Everzol Yellow CE-N, Blue C–LX.
● 淺色系中有優異的日光堅牢度及耐汗日光堅牢度 ● 適合與Yellow CE-N、Blue C–LX 搭配	● Excellent lightfastness and perspiration lightfastness at pale shade. ● Compatible with Everzol Yellow CE-N, Blue C–LX.
● 優異的日光及汗日光牢度 ● 極佳的染深性 ● 中色域高日光極具經濟性	● Excellent light and perspiration lightfastness ● Unique build–up ● Economical choice for high lightfastness in mid–gamut application
● 優異的日光堅牢度 ● 與 LX 和 LF 有良好的組合，適用於 CPB 或其它的連續染色方法	● Excellent color fastness to light. ● Good compatibility with Everzol LX and LF range in CPB dyeing or other continuous dyeing.
● 解決敏感灰色系的有效方案 ● 高耐日光及高耐汗光堅牢度	● Trouble–Shooting for critical color as Grey. ● High lightfastness & Perspiration light fastness.
● 優異的日光堅牢度 ● 建議使用於中等深度染色	● Excellent color fastness to light. ● Recommended for medium shade dyeing.

Everzol ED Dyes

頁 Page	染料 Dyes	10g/l	30g/l
71	Yellow ED–R		
73	Yellow ED		
75	Orange ED–N		
77	Orange ED–4R		
79	Red ED		
81	Red ED–2B		
83	Red ED–3B		
85	Red ED–7BN		
87	Red ED–S		
89	Rubine ED		

Everzol ED Dyes

染料特性	Characteristics
● 色彩明亮，且有優異的染深性 ● 優異的耐多次水洗牢度 (M&S C10A)	● Brilliant and excellent build–up. ● Excellent multi-laundering fastness (M&S C10A).
● 優異的染深性 ● 為三原色系中深色的主要組合 ● 搭配 Red ED–7BN 和 Blue L–ED 之配色組合相容性佳	● Excellent build–up. ● Main component for medium to deep trichromatic. ● Excellent compatibility with Red ED–7BN and Blue L–ED.
● 高染深性 ● 優異的日光牢度與汗日光牢度 ● 適用於防、拔染印花加工	● Excellent build–up. ● High light fastness & Perspiration light fastness. ● Suitable for resist and discharge printing.
● 全色域多功能橙色染料 ● 高染深性 ● 高耐光，耐氯水堅牢度	● Full gamut and a primary deep orange of trichromatic. ● High build up. ● High fastness to light and chlorinated water.
● 對深紅色有很高的著色率 ● 為中深濃度之主要三原色 ● 搭配 Yellow ED、Navy ED 之配色組合相容性佳	● Very high tinctorial strength for deep Red. ● Main component for medium to deep trichromatic. ● Excellent compatible with Yellow ED, Navy ED.
● 著色能力優異 ● 對於中深色系及深色系有良好的染深能力	● Tinctorially very strong. ● Very good build up for medium to heavy trichromatic.
● 色彩明亮，且有良好的著色能力 ● 優異的耐氯水堅牢度	● Brilliant and tinctorially very strong. ● Excellent in colorfastness to chlorinated water.
● 優異的染深性 ● 日光堅牢度及耐氯水堅牢度優異	● Excellent build–up. ● High lightfastness & chlorinated water fastness.
● 優異的染深性 ● 適合用於防、拔染印花加工	● Excellent build–up. ● Suitable for resist and discharge printing.
● 特別適合鮮豔的酒紅色染色	● Especially for brilliant burgundy shade dyeing.

Everzol ED Dyes

頁 Page	染料 Dyes	10g/l	30g/l
91	Blue ED–G		
93	Blue L–ED		
95	Blue ED		
*97	Navy ED		
*99	Black ED		
*101	Black ED–G		
*103	Black ED–R		
*105	Black EDN		
*107	Black ED–3R		

註 : Navy ED、黑色系 染色濃度為 30g/l、60g/l
Notes: Navy ED、Black shades the dyeing depth at 30g/l、60g/l

Everzol ED Dyes

染料特性	Characteristics
● 鮮豔偏綠的寶藍色染色 ● 可與 Yellow 4GL、Turq. Blue C–G 133% 搭配翠綠色系 ● 對 N/C 混紡織物尼龍低沾污	● Brilliant greenish royal Blue dyes. ● Compatible with Yellow 4GL, Turq. Blue C– G 133% for matching brilliant jade Green shade. ● Low nylon stain for N/C fabric.
● 為三原色基本的藍色，好的日光堅牢度 ● 適用於拔、防染印花加工 ● 與黃紅染料具優異的易搭配性與極佳的染色再現性	● Basic Blue for trichromatic, good in color fastness to light. ● Suitable for resist and discharge printing. ● Excellent compatibility with Yellow and Red color, excellent reproducibility.
● 好的日光堅牢度 ● 耐氯水堅牢度佳	● Good in colorfastness to light. ● Good in colorfastness to chlorinated water.
● 良好的染深性 ● 主要使用於中深色系及深色系 ● 使用 Yellow ED 及 Red ED 染液組合，染色效果優良	● Excellent build–up. ● Main component for medium to deep trichromatic. ● Compatible with Yellow ED, Red ED.
● 深色系有良好的染深性 ● 適合防、拔染印花加工	● Deep Black with good build up. ● Suitable for resist and discharge printing.
● 深色系有良好的染深性 ● 帶綠光的黑色染料 ● 適合防、拔染印花加工 ● 對棉及萊卡混紡染色，交叉汙染少	● Deep Black with good build up. ● Greenish black. ● Suitable for resist and discharge printing. ● Less lycra stain for cotton/lycra dyeing.
● 深色系有良好的染深性 ● 帶紅光的黑色染料 ● 適合防、拔染印花加工 ● 後絲光堅牢度佳	● Deep black with good build up. ● Reddish black. ● Suitable for resist and discharge printing. ● Good in colorfastness to post mercerizing.
● 高固著，易水洗 ● 殘液少，環境衝擊低 ● 水洗牢度佳	● High fixation, easy wash–off. ● Less effluent, less environmental impact. ● Good washing fastness.
● 對酸浴整理加工色光穩定 ● 染深性強，適合節能減排染程 ● 適用於多種染色流程 ● Inditex AAA 認可	● More stable shade in post acidic finishing. ● Unique build–up and reduce pollution. ● Versatile application for various dyeing process. ● INDITEX AAA premium accredited

Everzol ERC Dyes

頁 Page	染料 Dyes	10g/l	30g/l
109	Amber ERC		
111	Yellow ERC		
*113	Light Red ERC		
115	Cardinal ERC		
117	Bordeaux ERC		
119	Blue ERC		
121	Dark Blue ERC		
123	Marine ERC		
*125	Black ERC		
*127	Jet Black ERC		

註 : Light Red ERC 染色濃度為 5g/l、20g/l，黑色系 染色濃度為 30g/l、60g/l
Notes: Light Red ERC the dyeing depth at 5g/l、20g/l, Black shades the dyeing depth at 30g/l、60g/l

Everzol ERC Dyes

染料特性	Characteristics
● 全色域多功能黃色染料 ● 高耐光、耐汗日光堅牢度 ● 無光致變性	● Full gamut and primary yellow of trichromatic. ● High fastness to light and perspiration light. ● Non–photochromism.
● 易洗、節能、環保 ● 優異染深性 ● 優異日光牢度及耐多次水洗牢度 ● 中深色三原色	● Easy wash–off & saving energy & eco–friendly ● Unique build–up ● Unique fastness on light & multi–laundering ● Main trichromatic for medium–dark shade
● 適合於淺中色系 ● 優異日光牢度與耐氯水牢度	● Suitable for light to medium shades. ● Unique light fastness and chlorinated water fastness.
● 易洗、節能、環保 ● 色味偏黃之大紅色，優異染深性 ● 優異日光牢度及耐氯水牢度及水洗牢度 ● 適用於淺色至深色	● Easy wash–off & saving energy & eco–friendly ● Yellowish red dyes with unique build–up ● Excellent fastness on light & chlorine & washing ● Suitable for pale to dark shade
● 易洗、節能、環保 ● 色味偏藍之酒紅色，優異染深性 ● 優異日光牢度及水洗牢度 ● 深色三原色	● Easy wash–off & saving energy & eco–friendly ● Bluish red dyes with unique build–up ● Unique lightfastness & washing fastness ● Main trichromatic for deep shade
● 易洗、節能、環保 ● 藍色三原色，配色色域廣 ● 優異水洗牢度及日光牢度	● Easy wash–off & saving energy & eco–friendly ● Tinctorial blue, wide gamut for color match ● Unique fastness on washing & light
● 易洗、節能、環保 ● 優異染深性之深藍色染料 ● 優異水洗牢度及日光牢度 ● 中深色三原色	● Easy wash–off & saving energy & eco–friendly ● Outstanding fastness on washing & light ● Unique build–up for dark blue shade ● Main trichromatic for medium/deep shade
● 易洗、節能、環保 ● 優異染深性 ● 優異耐氯水及耐多次水洗牢度 ● 深色三原色	● Easy wash–off & saving energy & eco–friendly ● Unique build–up ● Unique fastness on chlorine & multi–laundering ● Main trichromatic for deep shade
● 優異的耐多次水洗牢度 (M&S C10A) ● 良好的耐氯水牢度 ● 優異的耐鹼與染液安定性	● Excellent multi-laundering fastness (M&S C10A). ● High fastness to chlorinated water. ● Excellent alkali stability in CPB dyeing.
● 適合於深黑色系 ● 泛用性廣	● Suitable for deep black shade. ● Suitable for CPB and exhaust dyeing.

Color fastness

1. Fastness to Washing	ISO 105 C10 Method B
	ISO 105 C10 Method C
	ISO 105 C10 Method D
	ISO 105 C06–C1S
	ISO 105 C06–C2S
	Marks & Spencer C4A
2. Fastness to Water	ISO 105 E01
3. Fastness to Hot Water	ISO 105 E08
4. Fastness to Sea Water	ISO 105 E02
5. Fastness to Post Mercerizing	ISO 105 X04
6. Fastness to Acid Hydrolysis	1% Acetic Acid Solution for 30 min, 38° C x 6 hours.
7. Fastness to Perspiration	ISO 105 E04
8. Fastness to Chlorinated Water (20ppm)	ISO 105 E03
9. Peroxide Bleaching	ISO 105 N02
10. Fastness to Rubbing	ISO 105 X12
11. Fastness to Detergent Light	Marks & Spencer C9A
12. Fastness to Multi–Laundering	Marks & Spencer C10A (ISO 105 C09)
13. Fastness to Saliva	DIN 53160
14. Fastness to Hot–pressing	ISO 105 X11
15. Fastness to Light	ISO 105 B02 & AATCC 16–3
16. Fastness to Perspiration Light	ISO 105 B07 & AATCC 125
17. Fastness to Nitrogen Oxides	ISO 105 G01 (1 cycle)

DYEING PROPERTIES

Everlight Chemical

Everzol Yellow C–GL

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	50
	Alkali 鹼劑 A + 100g/l Urea 尿素	70
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5(R)
	Cu^{2+} 銅離子	4–5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3–4
	Acetic Acid 醋酸	4(R)
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 10g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染			✓
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)		✓
	Emoistfix		✓
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

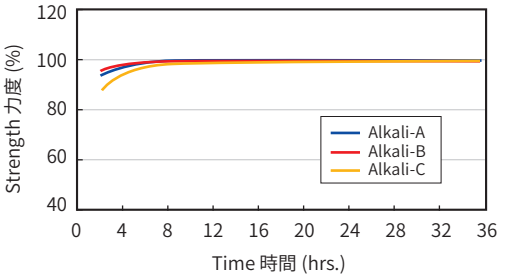


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

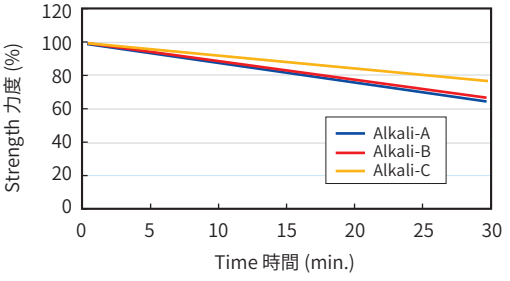


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

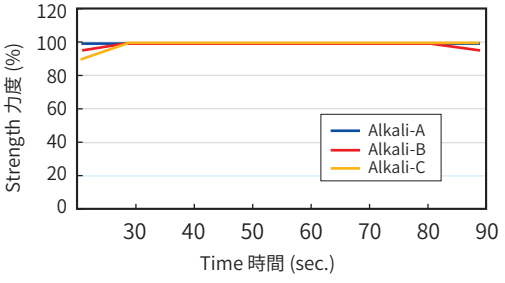

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

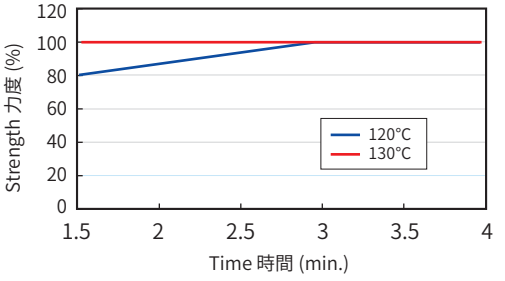

Everzol Yellow C–GL

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		4–5	5	5	5	5	5	4–5
	ISO C06–C1S		5	5	5	5	5	5	5
	ISO C06–C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		10g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	5	5	5	5	5	5	5
Sea Water 耐海水		10g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	4–5	–	4	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	5	5	5	5	5	5	5
	Alkali 鹼	10g/l	5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4–5	4–5	4–5	4
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4–5	5
		5g/l	4–5	5–6
		10g/l	5	6
		30g/l	5	>6
Perspiration Light 耐汗日光	Acid 酸	1g/l	4–5	4
		5g/l	4–5	4–5
		10g/l	4–5	5
		30g/l	4–5	5–6
	Alkali 鹼	1g/l	4–5	4
		5g/l	4–5	4–5
		10g/l	4–5	5–6
		30g/l	4–5	6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	>4–5
		30g/l	–	–

Everlight Chemical

Everzol Yellow C–GR

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	150
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	B(G)
	TL84 Lamp	B(G)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4
	Cu^{2+} 銅離子	2
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4
	Soda Ash Solution 純鹼	2
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染			✓
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25°C)

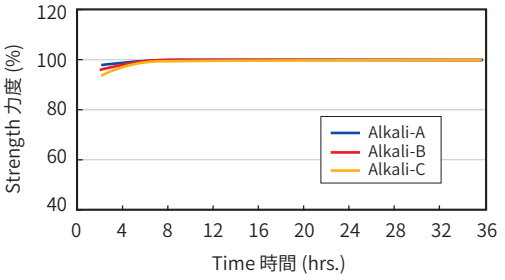


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

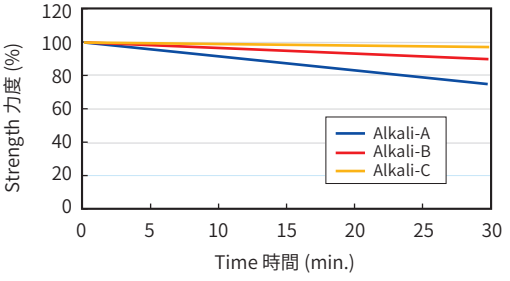

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

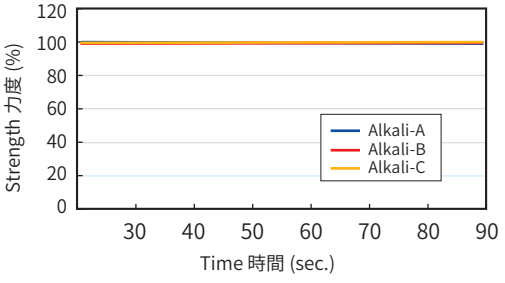

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

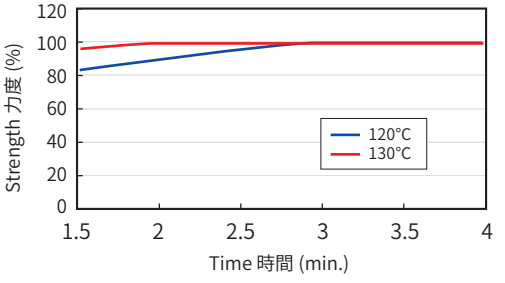

Everzol Yellow C–GR

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		4	5	4–5	5	5	5	3
	ISO C06–C1S		5	5	5	5	5	5	5
	ISO C06–C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	5	5	5	4–5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	2–3R	–	4	–			
Acid Hydrolysis 酸水解		30g/l	5	5	5	3–4	5	5	4–5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4–5	4–5	4	4
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2	–
		Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4Y	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4Y	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	3–4	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4–5	4
		10g/l	5	5
		30g/l	5	5–6
		60g/l	5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	4	4
		10g/l	4–5	4–5
		30g/l	4–5	5
		60g/l	4–5	5–6
	Alkali 鹼	5g/l	4	4
		10g/l	4–5	4–5
		30g/l	4–5	5
		60g/l	4–5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4

Everlight Chemical

Everzol Yellow C–RN

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	2
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	5
	Alkaline 鹼性	4–5


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染			✓
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

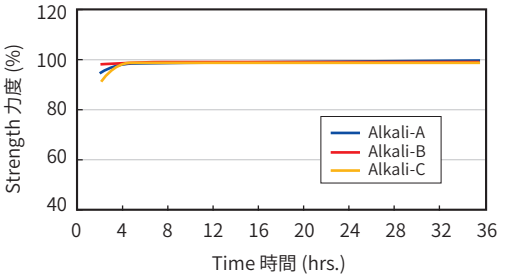


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

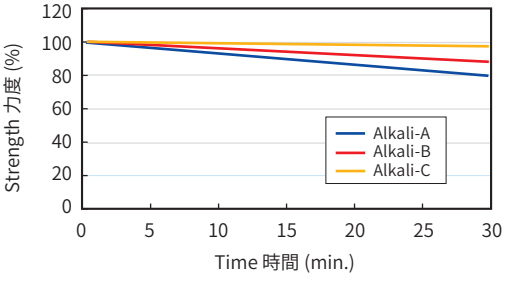


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

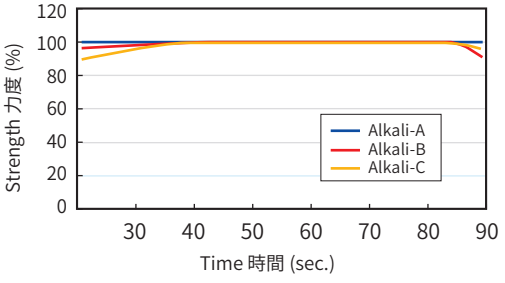

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

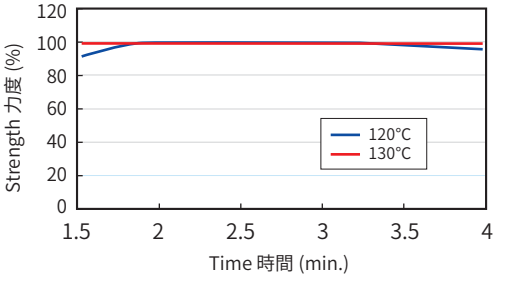

Everzol Yellow C–RN

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4–5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	5
	ISO C10 D		4	5	4–5	5	5	5	3–4
	ISO C06–C1S		5	5	5	5	5	5	5
	ISO C06–C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	4–5	–	3–4	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4–5	4–5	4	3–4
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3–4	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	3–4Y	–
		4 Hours after	–	–	5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4	4
		10g/l	4–5	4–5
		30g/l	4–5	5
		60g/l	4–5	5
Perspiration Light 耐汗日光	Acid 酸	5g/l	3	4
		10g/l	4	4–5
		30g/l	4	5
		60g/l	4	5
	Alkali 鹼	5g/l	3–4	4
		10g/l	4	4–5
		30g/l	4	5
		60g/l	4	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Yellow CE–N

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	3–4
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	5
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4–5
	Alkaline 鹼性	2–3


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

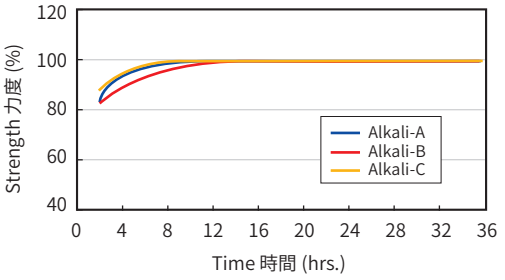


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

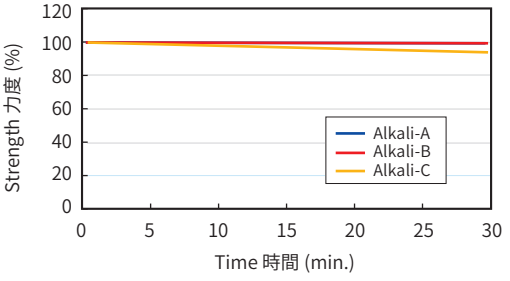


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

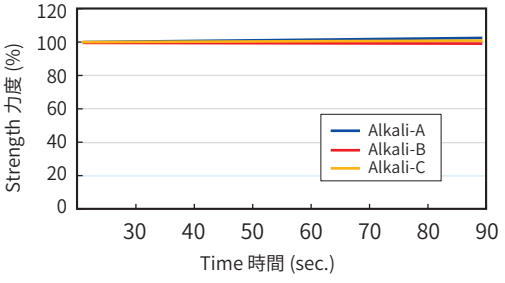

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

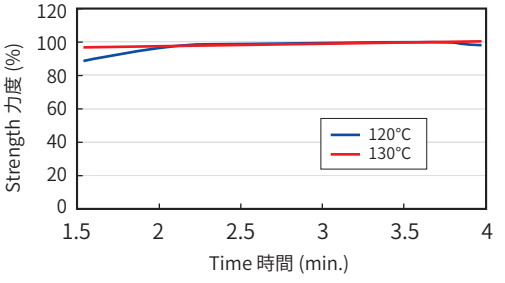

Everzol Yellow CE–N

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4–5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	5
	ISO C10 D		5	5	3–4	5	5	4–5	3–4
	ISO C06–C1S		5	5	4–5	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	4–5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	4–5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	4–5	–	4–5	–			
Acid Hydrolysis 酸水解		30g/l	5	5	4–5	4	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	5	5	4–5	5	5	5	5
	Alkali 鹼	30g/l	5	5	4–5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	4–5
		Wet 溼	4	4	3–4	3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	4	4	4	4
		Peroxide Bleaching 雙氧水漂白	–	–	5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4	–
Multi-Laundering (M&S C10A) 耐多次水洗			4–5	4–5	4–5	4
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4–5	5–6
		10g/l	5	5–6
		30g/l	5	5–6
		60g/l	5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	4–5	5–6
		10g/l	5	5–6
		30g/l	5	5–6
		60g/l	5	5–6
	Alkali 鹼	5g/l	4–5	5
		10g/l	5	5–6
		30g/l	5	5–6
		60g/l	5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	5
		30g/l	–	5

Everlight Chemical

Everzol Orange C–2R

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	70
	Alkali 鹼劑 A + 100g/l Urea 尿素	80
	Alkali 鹼劑 B	80
	Alkali 鹼劑 B + 100g/l Urea 尿素	80
	Alkali 鹼劑 C	80
	Alkali 鹼劑 C + 100g/l Urea 尿素	80
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R(Y)
	TL84 Lamp	Y(G)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	2–3
Alkali Spotting 鹼滴	Ammonia Water 氨水	3–4
	Soda Ash Solution 純鹼	5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	2–3
	Alkaline 鹼性	2–3

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)		✓
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25°C)

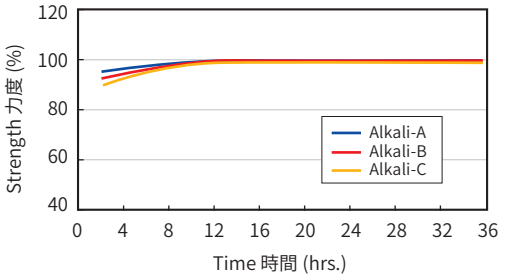


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

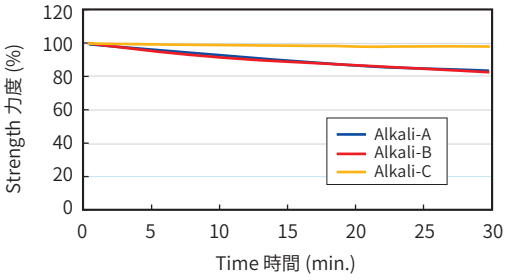

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

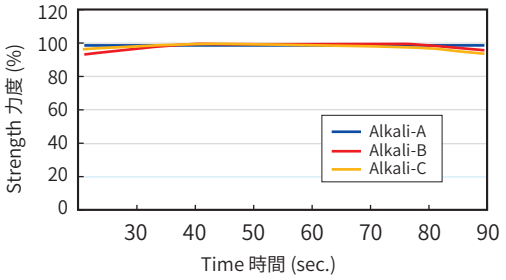

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

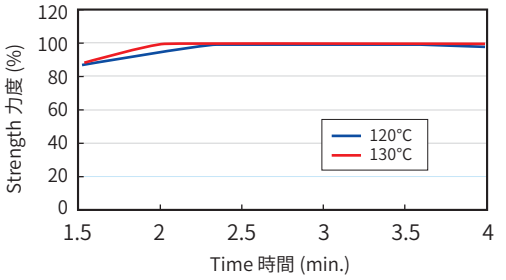

Everzol Orange C–2R

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4	5	5	5	5
	ISO C10 C		5	5	3–4	5	5	5	5
	ISO C10 D		4–5	4–5	3	5	5	5	4
	ISO C06–C1S		5	5	3–4	5	5	5	5
	ISO C06–C2S		5	5	4	5	5	5	5
	M&S C4A		5	5	4	5	5	5	5
Water 耐水		30g/l	4	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	4–5	3–4	5	5	4–5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	4–5	–	3–4	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	4–5	4–5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	4–5
		Wet 溼	4	3–4	3	3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	2(R)	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	2(R)	–
		4 Hours after	–	–	5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	3–4
		10g/l	3–4	3–4
		30g/l	4	3–4
		60g/l	4	3–4
Perspiration Light 耐汗日光	Acid 酸	5g/l	3	3
		10g/l	3–4	3–4
		30g/l	3–4	3–4
		60g/l	3–4	3–4
	Alkali 鹼	5g/l	3	3
		10g/l	3–4	3–4
		30g/l	3–4	3–4
		60g/l	3–4	3–4
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Red C–3B

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	10
	Alkali 鹼劑 A + 100g/l Urea 尿素	20
	Alkali 鹼劑 B	60
	Alkali 鹼劑 B + 100g/l Urea 尿素	60
	Alkali 鹼劑 C	80
	Alkali 鹼劑 C + 100g/l Urea 尿素	80
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	B
	TL84 Lamp	B
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4–5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4(Y)
Alkali Spotting 鹼滴	Ammonia Water 氨水	3–4(Y)
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4B
	Quaternary Ammonium Salt 四級胺鹽	4B
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4–5
	Alkaline 鹼性	4–5

X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 10g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染			✓
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)		✓
	Emoistfix		✓
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25°C)

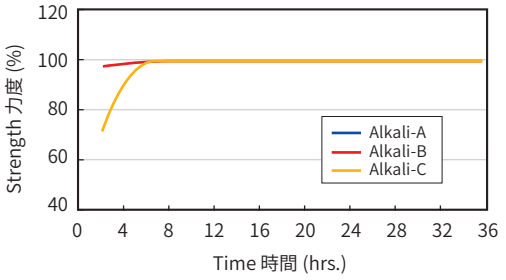


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

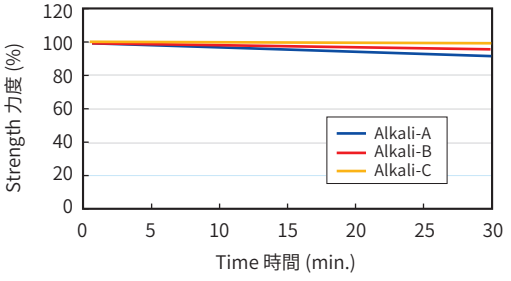

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

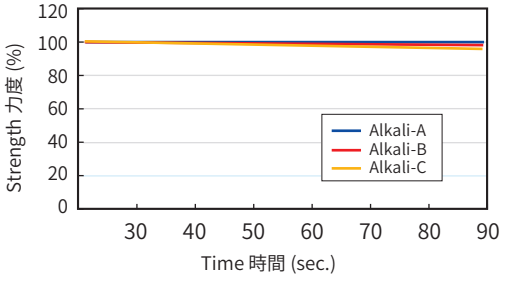

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

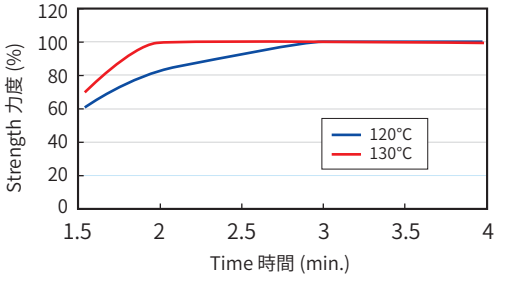

Everzol Red C–3B

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		4–5	5	5	5	5	5	4–5
	ISO C06–C1S		5	5	5	5	5	5	5
	ISO C06–C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		10g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	5	5	5	5	5	5	5
Sea Water 耐海水		10g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	3	–	5	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	10g/l	4	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4–5	4–5	4–5	3–4
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3–4	–
		Peroxide Bleaching 雙氧水漂白	–	–	2	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	3–4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4	4
		5g/l	4	4–5
		10g/l	4–5	5
		30g/l	5	6
Perspiration Light 耐汗日光	Acid 酸	1g/l	2–3	3–4
		5g/l	3	4
		10g/l	3	4–5
		30g/l	3–4	5
	Alkali 鹼	1g/l	2–3	2
		5g/l	3	2–3
		10g/l	3	3
		30g/l	3–4	4
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	–

Everlight Chemical

Everzol Red C–RB 133%

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5B
	Cu^{2+} 銅離子	4B
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	5
	Acetic Acid 醋酸	4–5Y
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5B
	Soda Ash Solution 純鹼	1B
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4B
	Quaternary Ammonium Salt 四級胺鹽	4B
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5B
	Glyoxal 乙二醛	4–5B
Discharge Ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	2


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

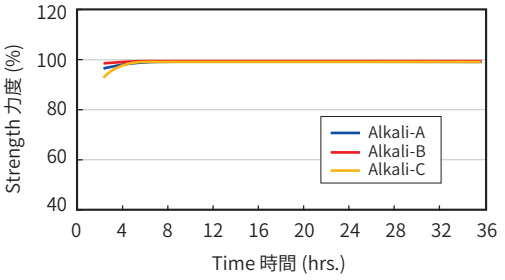


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

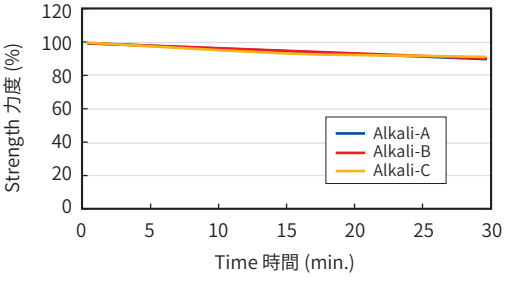


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

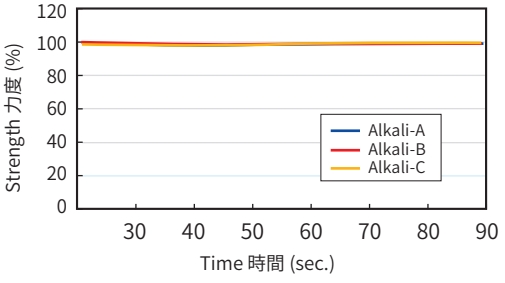

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

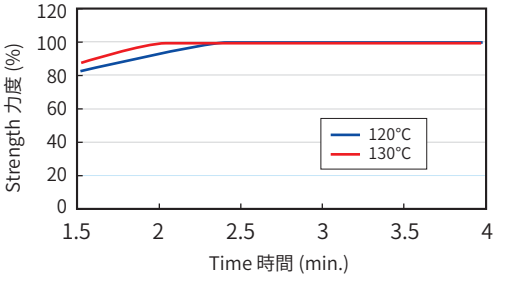

Everzol Red C–RB 133%

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	5
	ISO C10 D		5	5	4–5	5	5	5	4
	ISO C06–C1S		5	5	4–5	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	4–5	5	5	5	5
Sea Water 耐海水		30g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	1–2Y	–	3–4	–			
Acid Hydrolysis 酸水解		30g/l	4	5	5	4	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4	3–4	3	3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2–3	–
		Peroxide Bleaching 雙氧水漂白	–	–	3–4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	2–3	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3–4	4
		10g/l	4	4
		30g/l	4–5	4–5
		60g/l	4–5	5
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	3–4
		10g/l	3	4
		30g/l	3–4	4–5
		60g/l	4	5
	Alkali 鹼	5g/l	2–3	3
		10g/l	3	3–4
		30g/l	3–4	4
		60g/l	4	4–5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Red C–D

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	1B
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	1–2
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	3–4
Discharge Ability 拔染性	Neutral 中性	3–4
	Alkaline 鹼性	4


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染			✓
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

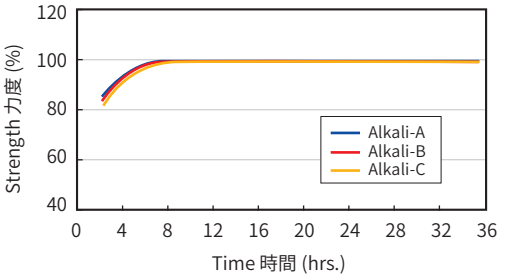


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

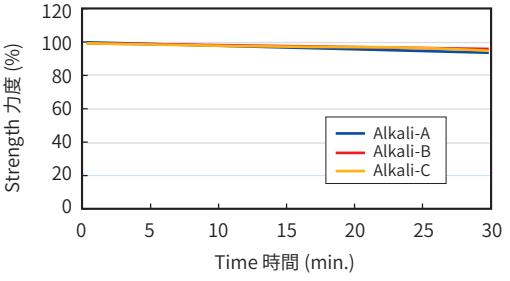


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

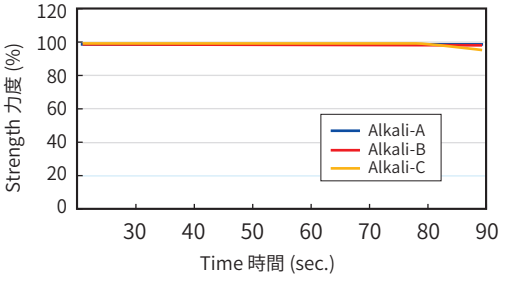

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

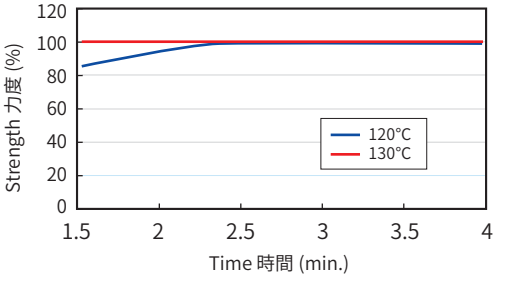

Everzol Red C–D

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	4–5	5	5	5	5
	ISO C10 C		4–5	5	3–4	5	5	5	5
	ISO C10 D		4–5	5	2–3	4–5	5	5	2–3
	ISO C06–C1S		4–5	5	3–4	5	5	4–5	5
	ISO C06–C2S		4–5	5	4	5	5	4–5	5
	M&S C4A		4–5	5	4–5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	4–5	3–4	4–5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	2	–	2	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4–5	4–5	4	3–4
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	2	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4	4–5
		10g/l	4	5
		30g/l	4–5	6
		60g/l	4–5	>6
Perspiration Light 耐汗日光	Acid 酸	5g/l	3–4	4–5
		10g/l	4	5
		30g/l	4–5	6
		60g/l	4–5	>6
	Alkali 鹼	5g/l	3–4	4
		10g/l	4	4–5
		30g/l	4–5	5–6
		60g/l	4–5	6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Turquoise Blue C–G 133%


Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	2–3Y
	Acetic Acid 醋酸	3Y
Alkali Spotting 鹼滴	Ammonia Water 氨水	3Y
	Soda Ash Solution 純鹼	2–3Y
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	3–4Y
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	4Y
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	2

X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 30g/l depth.


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

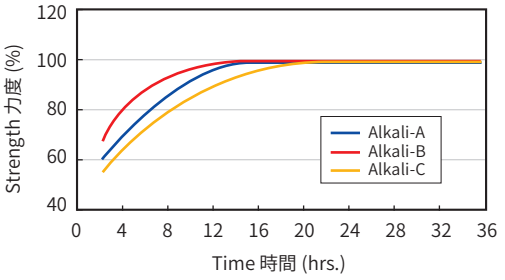


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

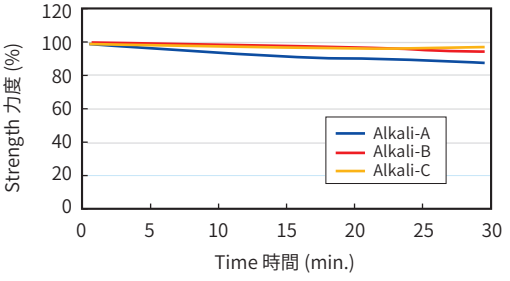

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

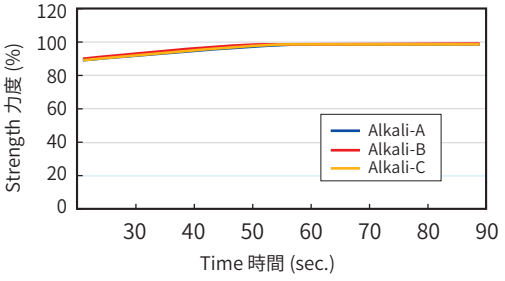

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)		✓
	Emoistfix		
Discharge Printing 拔染印花			

Everzol Turquoise Blue C–G 133%

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	3	4–5	5	5	5
	ISO C10 C		5	5	3	4–5	5	5	5
	ISO C10 D		4	4–5	2–3	4	4–5	5	2–3
	ISO C06–C1S		5	5	3	4–5	4–5	4–5	5
	ISO C06–C2S		5	5	3	4	5	5	5
	M&S C4A		5	5	3	5	5	5	5
Water 耐水		30g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	3G	–	4	–			
Acid Hydrolysis 酸水解		30g/l	3Y	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4–5	4–5	4	3–4
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2	–
		Peroxide Bleaching 雙氧水漂白	–	–	2	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	3–4
		10g/l	3–4	3–4
		30g/l	4	4
		60g/l	4–5	5
Perspiration Light 耐汗日光	Acid 酸	5g/l	3	2
		10g/l	3–4	2
		30g/l	4	3
		60g/l	4–5	3–4
	Alkali 鹼	5g/l	3	2
		10g/l	3–4	2–3
		30g/l	4	3
		60g/l	4–5	3–4
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Blue C–R S/P

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4–5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	3–4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4Y
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	1
	Alkaline 鹼性	1–2


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

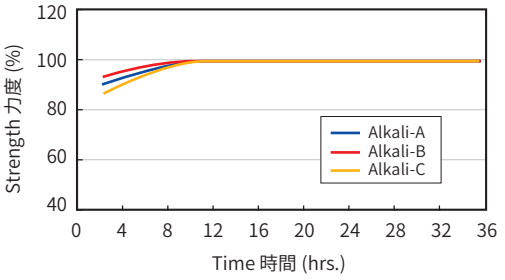


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

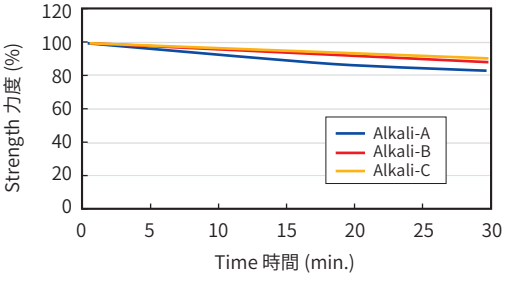


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

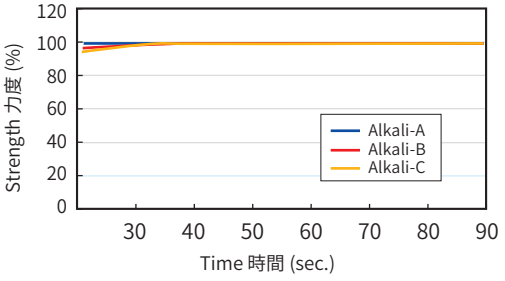

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

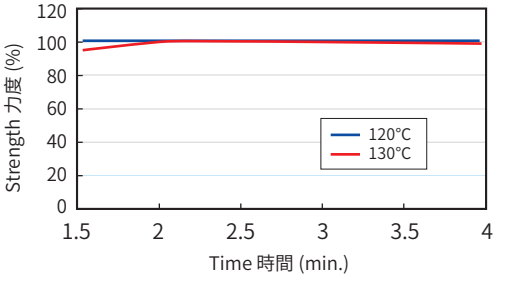

Everzol Blue C–R S/P

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	5	5	5	5	4–5
	ISO C10 C		5	5	5	4–5	5	5	4–5
	ISO C10 D		4	3–4	4	2–3	4–5	4–5	2–3
	ISO C06–C1S		5	5	4–5	4–5	5	5	4–5
	ISO C06–C2S		5	5	5	4–5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	5	5	4–5	5	5	5	5
Sea Water 耐海水		30g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	3R	–	2–3	–			
Acid Hydrolysis 酸水解		30g/l	4–5	4–5	4–5	4–5	4–5	4–5	4–5
Perspiration 耐汗	Acid 酸	30g/l	5	5	5	5	5	5	5
	Alkali 鹼	30g/l	5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4–5	4	3–4	3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3	–
		Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4	4	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4–5	4–5
		10g/l	5	5
		30g/l	5	5–6
		60g/l	5	6
Perspiration Light 耐汗日光	Acid 酸	5g/l	3–4	4–5
		10g/l	4	5
		30g/l	4–5	5–6
		60g/l	4–5	6
	Alkali 鹼	5g/l	3–4	4–5
		10g/l	4	5
		30g/l	4–5	5–6
		60g/l	4–5	6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	>4–5

Everlight Chemical

Everzol Blue C–BB 133%

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4–5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4(Y)
Alkali Spotting 鹼滴	Ammonia Water 氨水	3–4(Y)
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4(Y)
	Quaternary Ammonium Salt 四級胺鹽	4(Y)
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	2–3
	Alkaline 鹼性	3

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染			✓
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix		✓
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25°C)

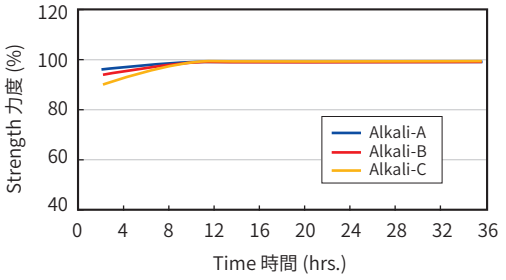


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

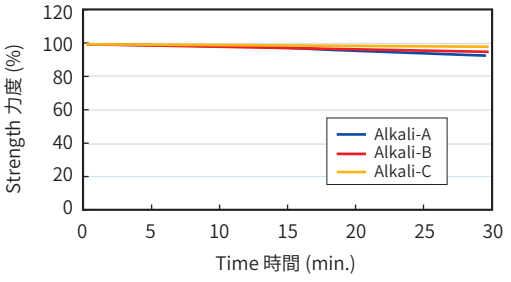

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

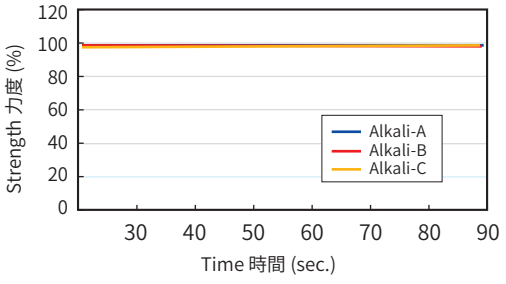

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

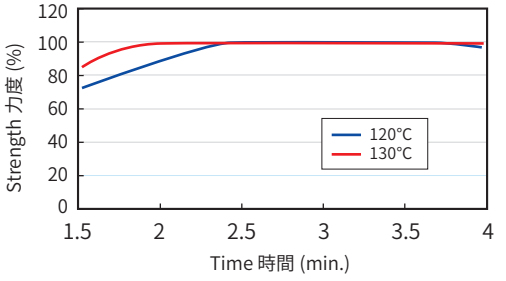

Everzol Blue C–BB 133%

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		4–5	5	4	5	5	5	3–4
	ISO C06–C1S		5	5	5	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	3	–	5	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4	5	5	4–5	5	5	5
	Alkali 鹼	30g/l	4	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4	4	3–4	3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3	–
		Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			4–5	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4–5	4
		10g/l	4–5	5
		30g/l	5	5–6
		60g/l	5	6
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	3
		10g/l	2–3	3–4
		30g/l	3	4–5
		60g/l	3–4	5
	Alkali 鹼	5g/l	2–3	3
		10g/l	2–3	3–4
		30g/l	3	4
		60g/l	3–4	4–5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	–

Everlight Chemical

Everzol Blue C–BRF

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	40
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	80
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	50
	Alkali 鹼劑 B + 100g/l Urea 尿素	70
	Alkali 鹼劑 C	50
	Alkali 鹼劑 C + 100g/l Urea 尿素	70
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	G
	TL84 Lamp	B(G)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4
	Cu^{2+} 銅離子	4–5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	1
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	2–3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	2–3


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

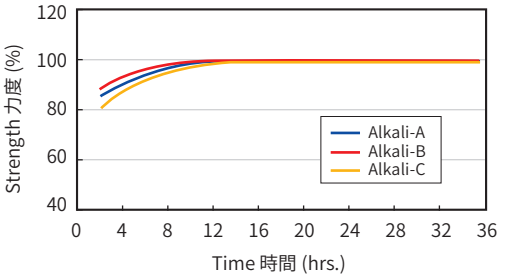


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

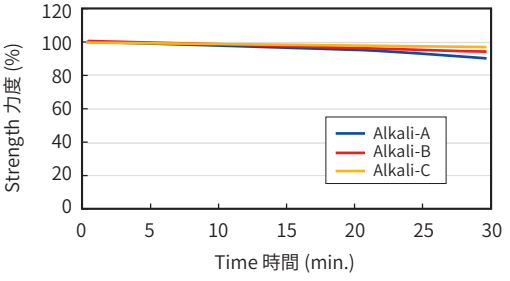


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

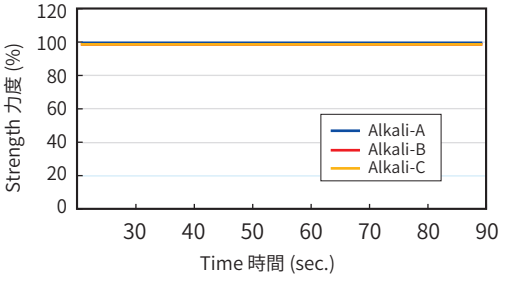

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

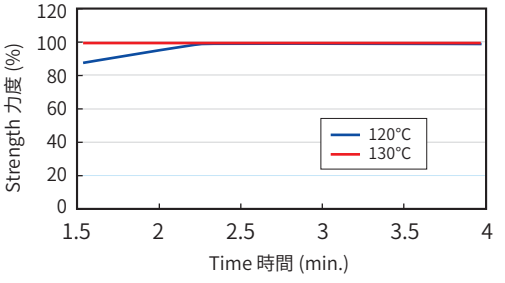

Everzol Blue C–BRF

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	3–4	5	5	5	5
	ISO C10 C		4–5	5	3–4	5	5	5	5
	ISO C10 D		4–5	5	2–3	5	5	5	2–3
	ISO C06–C1S		4–5	5	3–4	5	5	5	5
	ISO C06–C2S		4–5	5	3–4	5	5	5	5
	M&S C4A		4–5	5	4	5	5	5	5
Water 耐水		30g/l	4–5	5	5	4–5	5	5	5
Hot Water 耐熱水		30g/l	4–5	3–4	5	3	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	4	–	5	–			
Acid Hydrolysis 酸水解		30g/l	4–5	4–5	4–5	4–5	5	4–5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	4	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	4	4–5	4–5	4–5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	4–5
		Wet 溼	3–4	3–4	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2–3	–
		Peroxide Bleaching 雙氧水漂白	–	–	2	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			4	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4–5	5–6
		10g/l	4–5	5–6
		30g/l	4–5	6
		60g/l	4–5	>6
Perspiration Light 耐汗日光	Acid 酸	5g/l	4	5
		10g/l	4	5–6
		30g/l	4–5	6
		60g/l	4–5	6
	Alkali 鹼	5g/l	4	4–5
		10g/l	4	4–5
		30g/l	4–5	5
		60g/l	4–5	6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Navy C–GG 133%

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	60
	Alkali 鹼劑 A + 100g/l Urea 尿素	60
	Alkali 鹼劑 B	80
	Alkali 鹼劑 B + 100g/l Urea 尿素	80
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	1
	Cu^{2+} 銅離子	1–2
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	2–3
	Acetic Acid 醋酸	2
Alkali Spotting 鹼滴	Ammonia Water 氨水	2–3
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4–5


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

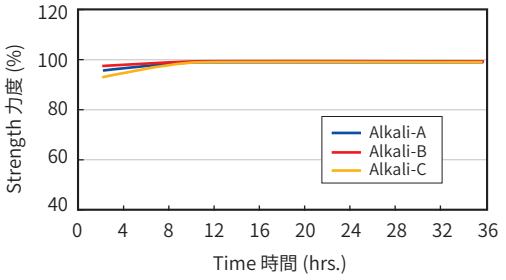


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

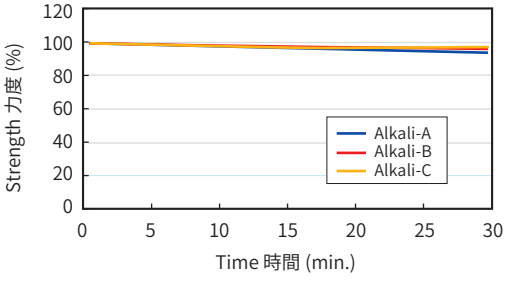


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

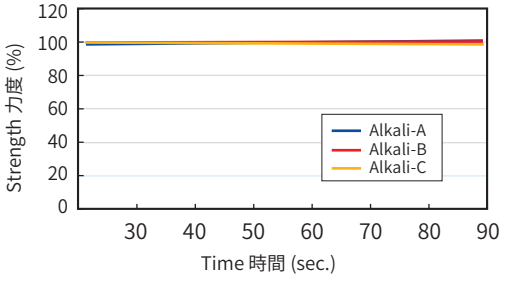

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

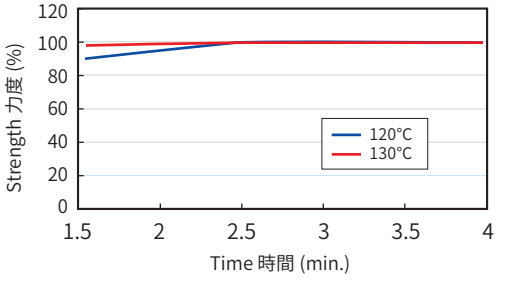

Everzol Navy C–GG 133%

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		5	4–5	3–4	5	5	5	3–4
	ISO C06–C1S		5	5	4–5	5	5	5	5
	ISO C06–C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	4–5	5	5	5	5
Sea Water 耐海水		30g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	2–3B	–	3	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	4–5	4–5	4–5	4–5	4–5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	4	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	4–5
		Wet 溼	3–4	3–4	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3–4	–
		Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	3–4
		10g/l	3	4
		30g/l	4	4–5
		60g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	3–4
		10g/l	3	4
		30g/l	3–4	4–5
		60g/l	4	5–6
	Alkali 鹼	5g/l	2–3	3–4
		10g/l	3	4
		30g/l	3–4	4–5
		60g/l	4	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	>4–5

Everlight Chemical

Everzol Navy C–GB H/C

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	80
	Alkali 鹼劑 A + 100g/l Urea 尿素	80
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	2–3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4–5


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

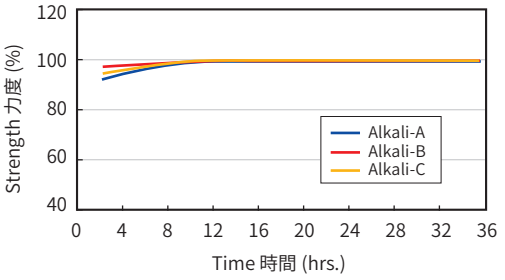


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

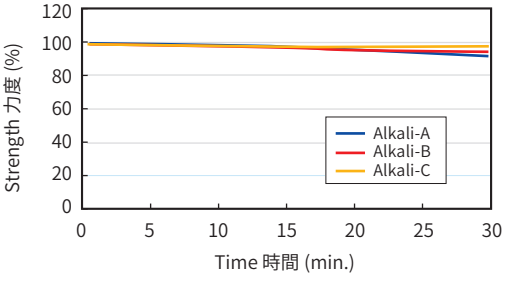


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

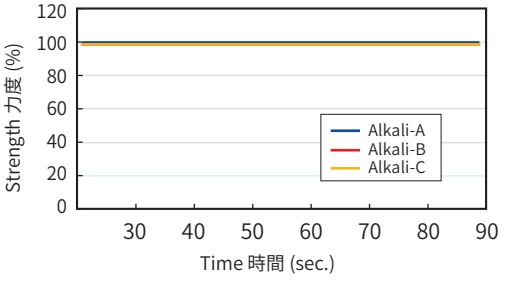

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

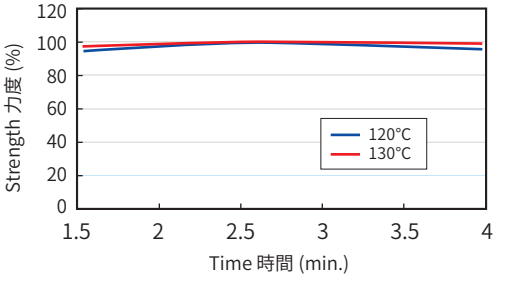

Everzol Navy C–GB H/C

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		5	5	4	5	5	5	3–4
	ISO C06–C1S		5	5	4–5	5	5	5	5
	ISO C06–C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	4–5	4–5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	4	–	5	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	4–5
		Wet 溼	3–4	3–4	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	3–4
		10g/l	3	3–4
		30g/l	4	4
		60g/l	4–5	5
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	3–4
		10g/l	3	3–4
		30g/l	3–4	4
		60g/l	4	5
	Alkali 鹼	5g/l	2–3	3–4
		10g/l	3	3–4
		30g/l	3–4	4
		60g/l	4	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Navy C–FB

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	3G
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3–4
	Acetic Acid 醋酸	5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	2–3
	Alkaline 鹼性	2


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)		✓
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

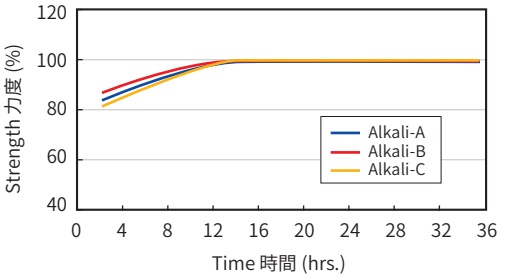


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

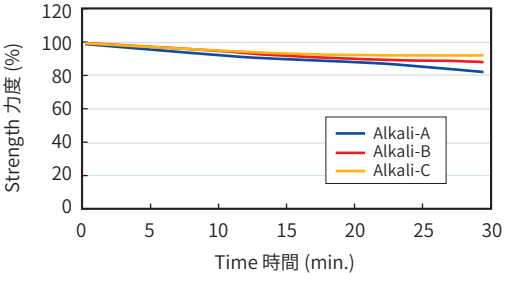


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

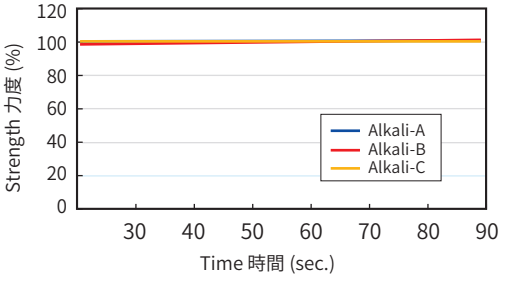

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

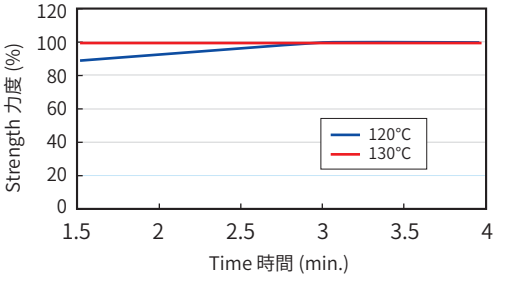

Everzol Navy C–FB

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		5	5	4	5	5	5	4
	ISO C06–C1S		5	5	4–5	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	5	5	4	3–4	5	4–5	4
Hot Water 耐熱水		30g/l	5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	5	5	4	5	5	5	5
Post Mercerizing 後絲光		30g/l	2–3R	–	3	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	3–4	3–4	5	5	3–4
Perspiration 耐汗	Acid 酸	30g/l	5	5	4	4–5	5	5	5
	Alkali 鹼	30g/l	5	5	4	4–5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	4–5	4–5
		Wet 溼	4	3–4	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4	–
		Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	2–3	3–4
		10g/l	3–4	3–4
		30g/l	4	4–5
		60g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	3
		10g/l	2–3	3–4
		30g/l	3–4	4–5
		60g/l	4	5–6
	Alkali 鹼	5g/l	2–3	4
		10g/l	2–3	4–5
		30g/l	3–4	5–6
		60g/l	4	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	>4–5

Everlight Chemical

Everzol Black C–B 133%

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	150
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	4–5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3G
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5Y
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

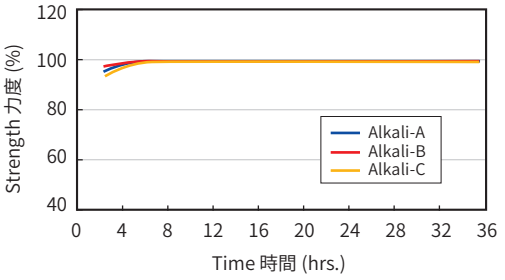


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

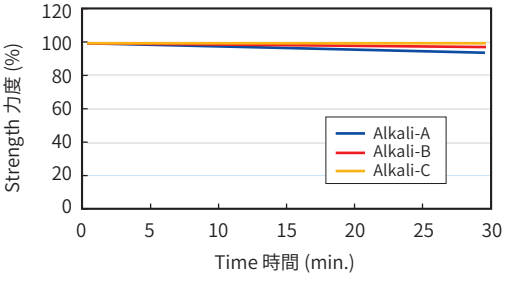


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

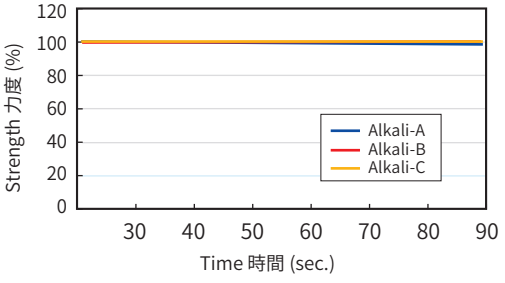

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

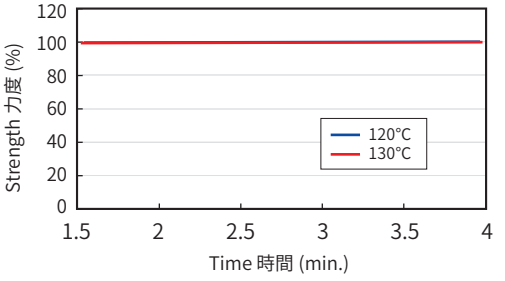

Everzol Black C–B 133%

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		5	5	4	5	5	5	3–4
	ISO C06–C1S		5	5	4–5	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	4–5	5	5	5	5
Sea Water 耐海水		30g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	2–3R	–	4	–			
Acid Hydrolysis 酸水解		30g/l	4	4–5	4–5	4–5	5	4–5	4–5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	5	5	5	5	5	5	5

Dyeing Depth 染色濃度		5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦	Dry 乾	5	5	5	4–5
	Wet 溼	4	3–4	3	2–3
		Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白	Chlorinated Water (20ppm) 耐氯水	–	–	2–3	–
	Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓 Dry 乾	Immediately	–	–	4	–
	4 Hours after	–	–	4–5	–
Hot-Pressing 耐熱壓 Wet 溼	Immediately	–	–	4	–
	4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗		–	–	3–4	–
Saliva (DIN) 耐唾液		–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色		–	–	5	5

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	2–3	3–4
		10g/l	3–4	4
		30g/l	4	4
		60g/l	4–5	5
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	2–3
		10g/l	2–3	3
		30g/l	3–4	3–4
		60g/l	4	5
	Alkali 鹼	5g/l	2–3	3
		10g/l	2–3	3–4
		30g/l	3–4	4
		60g/l	4	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Black C–RL


Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	50
	Alkali 鹼劑 A + 100g/l Urea 尿素	70
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R(B)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4–5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	2
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	1–2
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4–5

X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 10g/l depth.


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

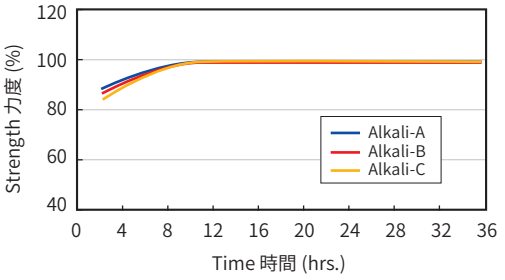


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

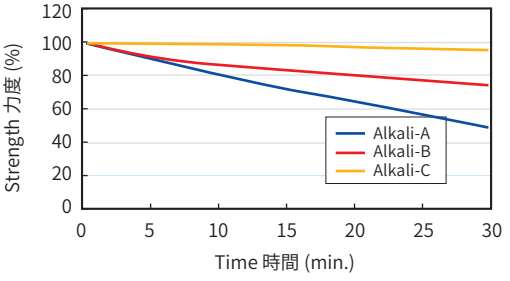

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

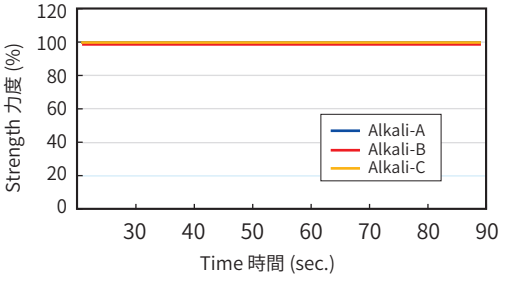

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)		✓
	Pad-Steam (PS)		✓
	Emoistfix		
Discharge Printing 拔染印花		✓	

Everzol Black C–RL

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	5	5	5	5	5
	ISO C10 D		4–5	5	4–5	5	5	5	4–5
	ISO C06–C1S		5	5	4–5	4–5	5	5	5
	ISO C06–C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		10g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	5	5	4–5	5	5	5	5
Sea Water 耐海水		10g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	3R(Y)	–	4–5	–			
Acid Hydrolysis 酸水解		10g/l	5	5	5	4–5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	5	5	5	5	5	5	5
	Alkali 鹼	10g/l	5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4–5	4–5	4–5	3–4
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	1–2	–
		Peroxide Bleaching 雙氧水漂白	–	–	2–3	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5Y	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4Y	–
		4 Hours after	–	–	5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	2–3	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4	4–5
		5g/l	4–5	5
		10g/l	4–5	5–6
		30g/l	5	5–6
Perspiration Light 耐汗日光	Acid 酸	1g/l	2–3	3–4
		5g/l	3	4
		10g/l	3–4	4–5
		30g/l	4	5
	Alkali 鹼	1g/l	2–3	3
		5g/l	3	3–4
		10g/l	3–4	4
		30g/l	4	4–5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	–

Everlight Chemical


Everzol Black MWF

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	G
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3–4
	Alkaline 鹼性	4–5

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 60g/l depth.


Dependency of Batching Time 捲置時間依存性(CPB)
(Dyeing temperature at 25°C)

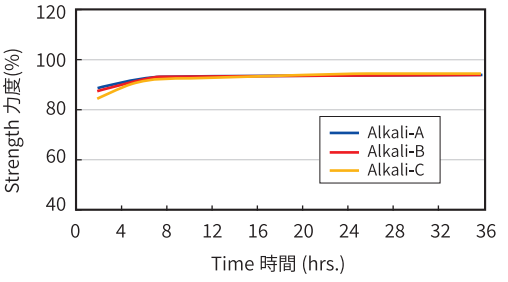

Stability of Padding Liquor 染液安定性(CPB)
(Dyeing temperature at 25°C)

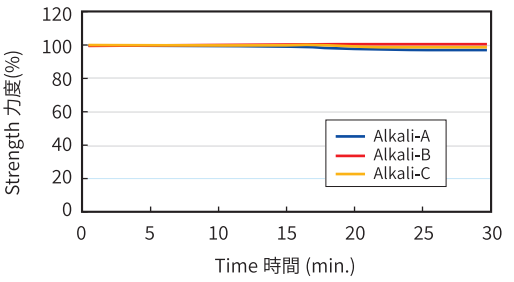


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

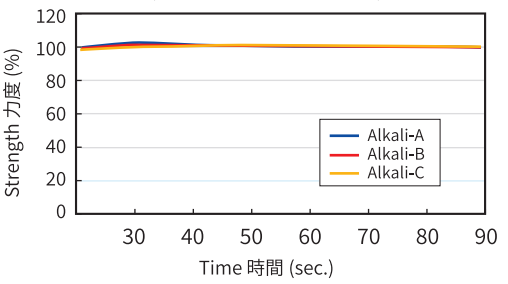

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

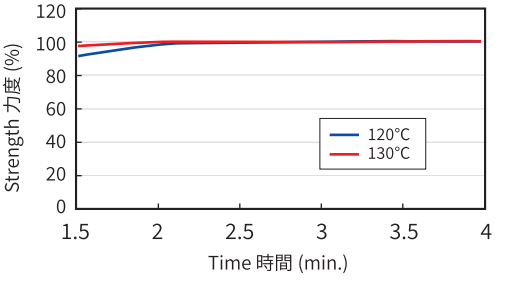

Everzol Black MWF

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	60g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	4–5	5	5	5	5
	ISO C10 D		4–5	5	3	5	5	5	2–3
	ISO C06–C1S		4–5	5	4–5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		60g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		60g/l	4–5	5	4–5	5	5	5	5
Sea Water 耐海水		60g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		60g/l	4		4				
Acid Hydrolysis 酸水解		60g/l	4–5	5	4–5	4–5	5	5	5
Perspiration 耐汗	Acid 酸	60g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	60g/l	4–5	5	4–5	5	5	5	5

Dyeing Depth 染色濃度			10g/l	30g/l	60g/l	80g/l
Rubbing 耐磨擦		Dry 乾	4–5	4–5	4–5	4–5
		Wet 溼	4	3–4	3	3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	4–5
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		10g/l	3	4
		30g/l	3–4	4–5
		60g/l	4	4–5
		80g/l	4–5	5
Perspiration Light 耐汗日光	Acid 酸	10g/l	2	3–4
		30g/l	3	4
		60g/l	3–4	4–5
		80g/l	4	5
	Alkali 鹼	10g/l	2–3	3
		30g/l	3–4	3–4
		60g/l	4	4–5
		80g/l	4–5	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4
		60g/l	–	4–5

Everlight Chemical

Everzol Yellow CS

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	80
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	80
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	G(Y)
	TL84 Lamp	G(Y)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	3–4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3–4
	Alkaline 鹼性	2

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 10g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)		✓
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)		✓
	Emoistfix		✓
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25°C)

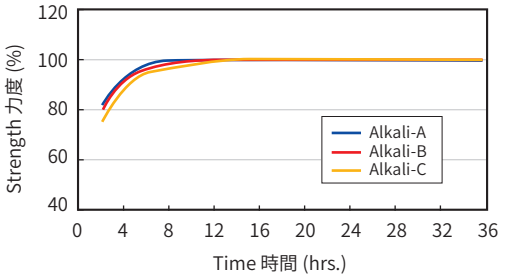


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

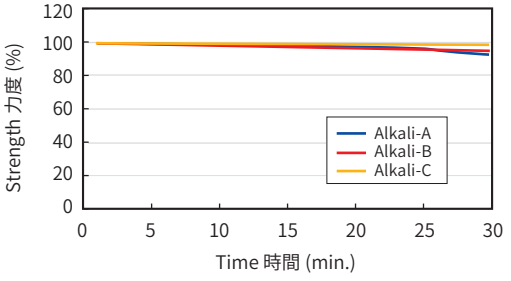

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

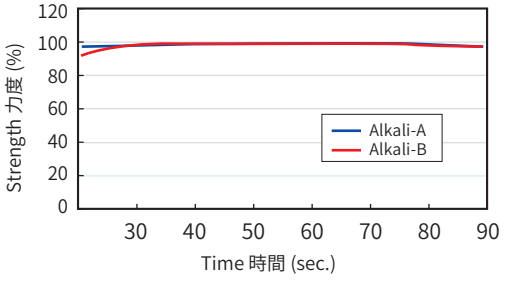

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

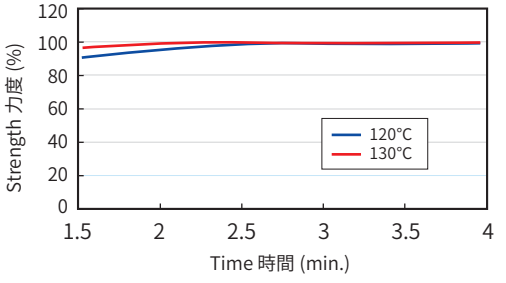

Everzol Yellow CS

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	5	5	5	5	5
	ISO C10 D		4–5	5	5	5	5	5	5
	ISO C06–C1S		4–5	5	5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		10g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		10g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	4–5	–	5	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	4–5	5	5	5	4–5
Perspiration 耐汗	Acid 酸	10g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	10g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	5	–
		Wet 溼	–	–	4–5	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4	5–6
		5g/l	4–5	6
		10g/l	4–5	6
		30g/l	5	6
Perspiration Light 耐汗日光	Acid 酸	1g/l	3–4	5–6
		5g/l	3–4	5–6
		10g/l	4	5–6
		30g/l	4–5	5–6
	Alkali 鹼	1g/l	3–4	5
		5g/l	3–4	5
		10g/l	4	5–6
		30g/l	4	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	5
		30g/l	–	4–5

Everlight Chemical

Everzol Orange CS

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	60
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	80
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	80
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	4–5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3–4
	Acetic Acid 醋酸	3–4
Alkali Spotting 鹼滴	Ammonia Water 氨水	4
	Soda Ash Solution 純鹼	4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	3R
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4–5


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 10g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)		✓
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)		✓
	Emoistfix		✓
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

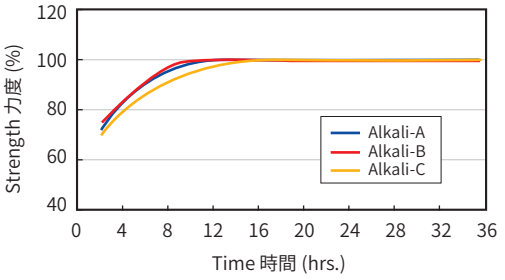


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

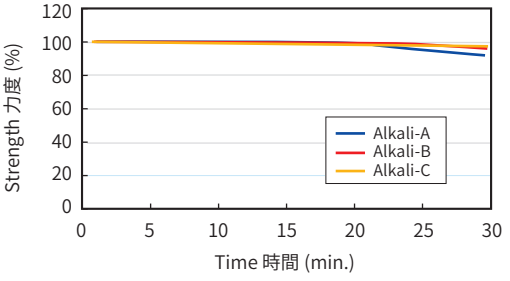


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

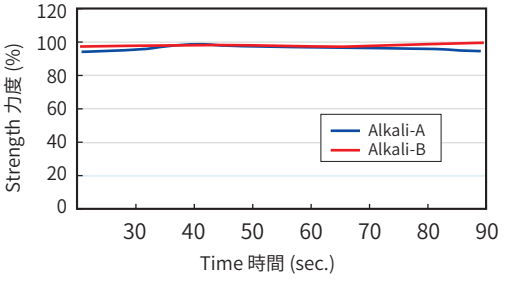

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

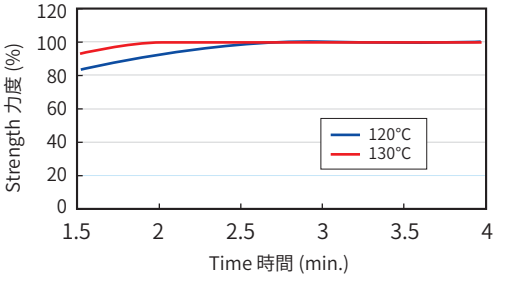

Everzol Orange CS

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		5	5	5	5	5	5	5
	ISO C06–C1S		5	5	5	5	5	5	5
	ISO C06–C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		10g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		10g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	3–4	–	4–5	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	10g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	5	–
		Wet 溼	–	–	4	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	3–4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4	4–5
		5g/l	4–5	5–6
		10g/l	4–5	5–6
		30g/l	5	6
Perspiration Light 耐汗日光	Acid 酸	1g/l	4	5
		5g/l	4	5
		10g/l	4–5	5–6
		30g/l	5	6
	Alkali 鹼	1g/l	4	4–5
		5g/l	4–5	5
		10g/l	4–5	5–6
		30g/l	5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	>4–5
		30g/l	–	>4–5

Everlight Chemical

Everzol Red Brown CS

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	80
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	80
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R(Y)
	TL84 Lamp	G(B)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4
	Soda Ash Solution 純鹼	1–2
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	3
	Quaternary Ammonium Salt 四級胺鹽	4
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3–4
	Alkaline 鹼性	3


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 10g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)		✓
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)		✓
	Emoistfix		✓
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

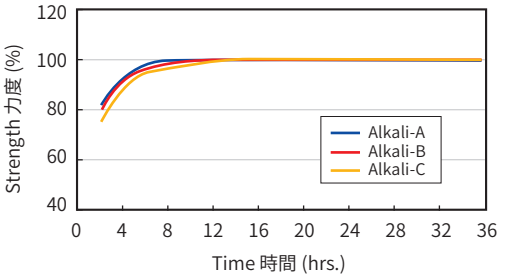


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

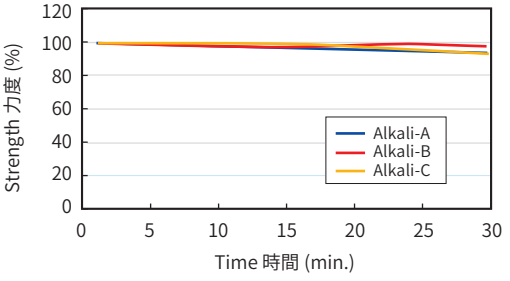


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

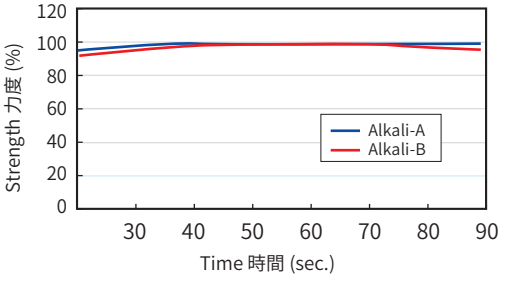

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

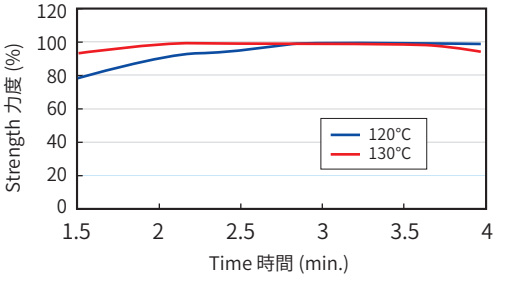

Everzol Red Brown CS

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		5	5	5	5	5	5	5
	ISO C06–C1S		5	5	5	5	5	5	5
	ISO C06–C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		10g/l	5	5	4–5	5	5	5	5
Hot Water 耐熱水		10g/l	5	5	5	5	5	5	5
Sea Water 耐海水		10g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	5	–	4	–			
Acid Hydrolysis 酸水解		10g/l	5	5	4	3–4	5	5	4–5
Perspiration 耐汗	Acid 酸	10g/l	5	5	4–5	5	5	5	5
	Alkali 鹼	10g/l	5	5	4–5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	5	–
		Wet 溼	–	–	4	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4	5
		5g/l	4–5	5–6
		10g/l	4–5	5–6
		30g/l	5	5–6
Perspiration Light 耐汗日光	Acid 酸	1g/l	3–4	4–5
		5g/l	3–4	5
		10g/l	3–4	5
		30g/l	3–4	5–6
	Alkali 鹼	1g/l	3	4
		5g/l	3–4	4–5
		10g/l	3–4	4–5
		30g/l	4	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	4–5

Everlight Chemical

Everzol Olive CS

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	50
	Alkali 鹼劑 A + 100g/l Urea 尿素	80
	Alkali 鹼劑 B	60
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	G
	TL84 Lamp	G(B)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3–4

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 10g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)		✓
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)		✓
	Emoistfix		✓
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25°C)

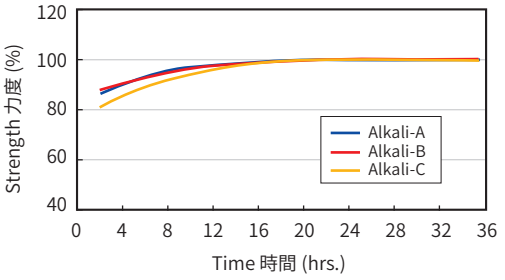


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

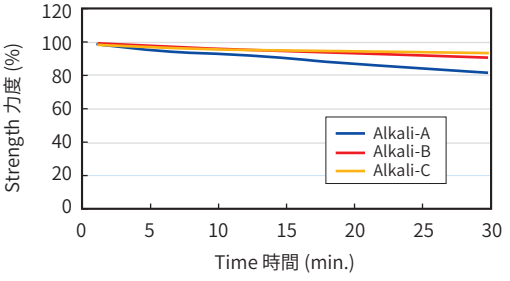

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

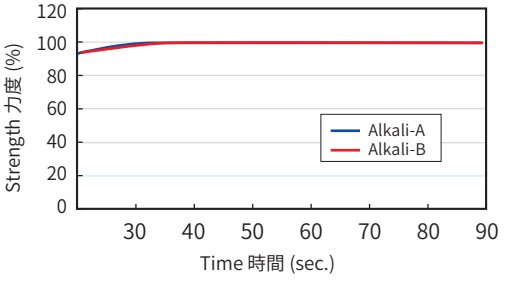

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

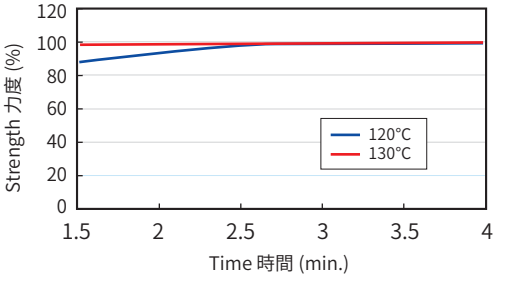

Everzol Olive CS

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4–5	5	4–5	5	5	5	5
	ISO C10 C		4–5	5	4–5	5	5	5	5
	ISO C10 D		4–5	5	4–5	5	5	5	5
	ISO C06–C1S		4–5	5	4–5	5	4–5	5	5
	ISO C06–C2S		4–5	5	4	5	4–5	5	5
	M&S C4A		4–5	5	4–5	5	5	5	5
Water 耐水		10g/l	4–5	5	4–5	5	5	5	5
Hot Water 耐熱水		10g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		10g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	3–4	–	4	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	4–5	5	4–5	5	5	5	5
	Alkali 鹼	10g/l	4–5	5	4–5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	5	–
		Wet 溼	–	–	3	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	3	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	3–4	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	3–4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4–5	5–6
		5g/l	4–5	5–6
		10g/l	4–5	6
		30g/l	5	6
Perspiration Light 耐汗日光	Acid 酸	1g/l	3	4
		5g/l	3	4
		10g/l	3	5
		30g/l	4	5
	Alkali 鹼	1g/l	3–4	3
		5g/l	3–4	3–4
		10g/l	3–4	4
		30g/l	3–4	4
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	4–5

Everlight Chemical

Everzol Grey CS

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	80
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	80
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R(Y)
	TL84 Lamp	B
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	1–2
	Acetic Acid 醋酸	2
Alkali Spotting 鹼滴	Ammonia Water 氨水	2
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 10g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)		✓
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)		✓
	Emoistfix		✓
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25°C)

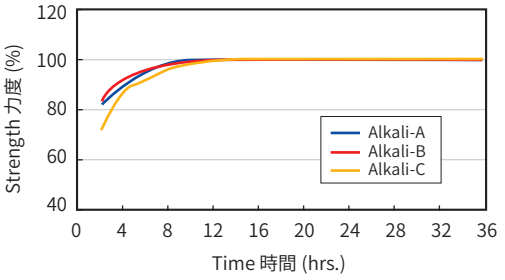


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

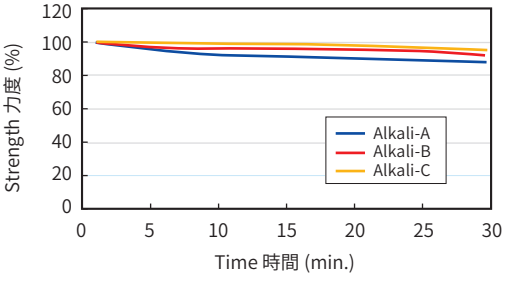

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

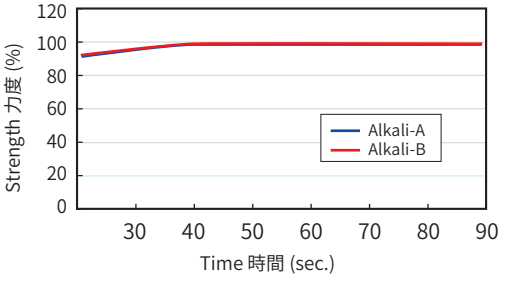

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

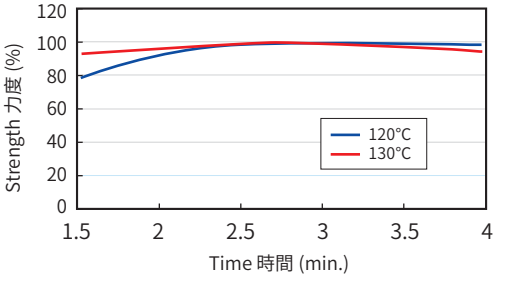

Everzol Grey CS

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4–5	5	5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	4–5	4–5
	ISO C10 D		4–5	4–5	3–4	4–5	4–5	4	3–4
	ISO C06–C1S		4–5	5	4	4–5	5	5	5
	ISO C06–C2S		4–5	5	4	4–5	5	4–5	5
	M&S C4A		4–5	5	4–5	4–5	5	4–5	5
Water 耐水		10g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	5	5	5	5	5	5	5
Sea Water 耐海水		10g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	4	–	4–5	–			
Acid Hydrolysis 酸水解		10g/l	4	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	10g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	5	–
		Wet 溼	–	–	4–5	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2–3	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4	4–5
		5g/l	4	5
		10g/l	4–5	5–6
		30g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	1g/l	2–3	4
		5g/l	3	4–5
		10g/l	3–4	5
		30g/l	4	5
	Alkali 鹼	1g/l	2–3	3–4
		5g/l	3	3–4
		10g/l	4	4
		30g/l	4–5	4
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	4–5

Everlight Chemical

Everzol Flavine FC

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	50
	Alkali 鹼劑 A + 100g/l Urea 尿素	50
	Alkali 鹼劑 B	60
	Alkali 鹼劑 B + 100g/l Urea 尿素	60
	Alkali 鹼劑 C	60
	Alkali 鹼劑 C + 100g/l Urea 尿素	60
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R(B)
	TL84 Lamp	R(Y)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	3–4
	Cu^{2+} 銅離子	4
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	3–4
	Soda Ash Solution 純鹼	1–2
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary Ammonium Salt 四級胺鹽	4
Resin Finishing 樹脂加工	Melamine 三聚氰胺	3–4
	Glyoxal 乙二醛	4
Discharge Ability 拔染性	Neutral 中性	1
	Alkaline 鹼性	2–3


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染			✓
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)		✓
	Pad-Steam (PS)		✓
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25° C)

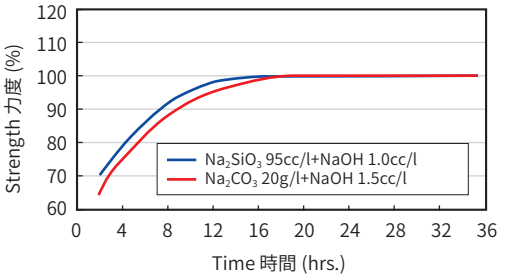


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

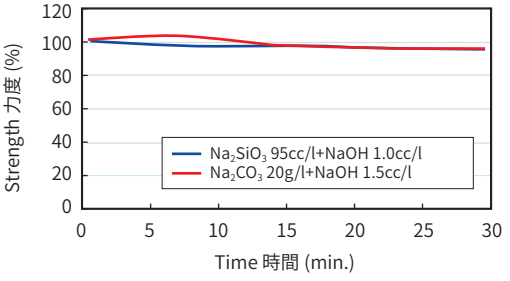


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

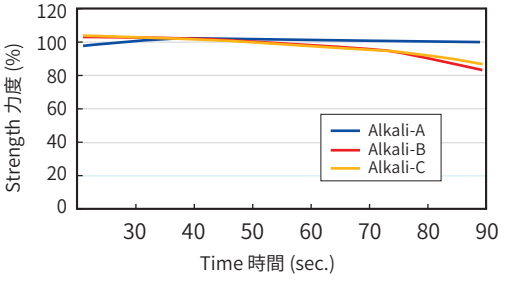

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

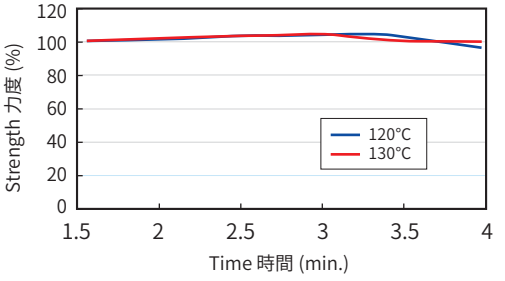

Everzol Flavine FC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4	5	5	5	5	5	5
	ISO C10 C		4–5	5	5	5	5	5	3–4
	ISO C10 D		4	5	5	5	5	5	3
	ISO C06–C1S		4–5	5	5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	3–4	–	4	–			
Acid Hydrolysis 酸水解		30g/l	4	5	5	3	5	5	3–4
Perspiration 耐汗	Acid 酸	30g/l	4	5	5	5	5	5	5
	Alkali 鹼	30g/l	4	5	5	5	5	5	5

Dyeing Depth 染色濃度		5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦	Dry 乾	5	5	5	4
	Wet 溼	5	4	3–4	3–4
		Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白	Chlorinated Water (20ppm) 耐氯水	–	–	3–4	–
	Peroxide Bleaching 雙氧水漂白	–	–	2	–
Hot-Pressing 耐熱壓 Dry 乾	Immediately	–	–	4	–
	4 Hours after	–	–	4–5	–
Hot-Pressing 耐熱壓 Wet 溼	Immediately	–	–	3–4	–
	4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗		–	–	3	–
Saliva (DIN) 耐唾液		–	–	4	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色		–	–	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3–4	3
		10g/l	3	3
		30g/l	2–3	<2
		60g/l	2	<2
Perspiration Light 耐汗日光	Acid 酸	5g/l	2	<2
		10g/l	2	<2
		30g/l	1–2	<2
		60g/l	1–2	<2
	Alkali 鹼	5g/l	2	<2
		10g/l	1–2	<2
		30g/l	1	<2
		60g/l	1	<2
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	1
		30g/l	–	1

Everlight Chemical

Everzol Orange FC

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	2–3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	2–3
	Alkaline 鹼性	2–3


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25° C)

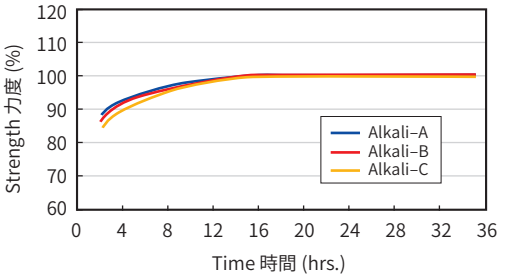


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

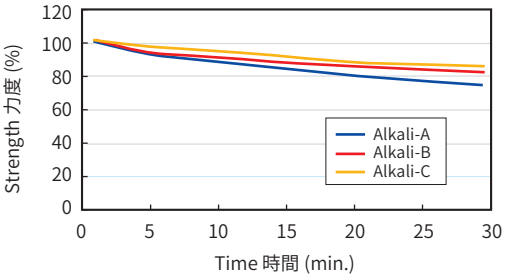


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

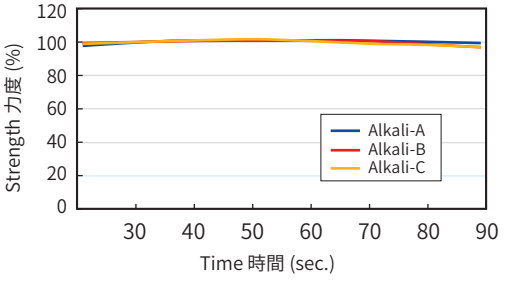

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

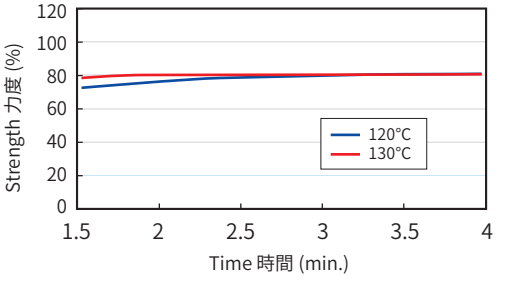

Everzol Orange FC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	5	5	5	5	5
	ISO C10 D		4–5	5	4–5	5	5	5	4–5
	ISO C06–C1S		4–5	5	5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	4–5	–	4–5	–			
Acid Hydrolysis 酸水解		30g/l	4–5	4–5	3	2–3	5	5	4
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	4–5	4–5	4–5
		Wet 溼	4	4	4	3–4
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	3–4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	2–3	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	2	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3–4	4–5
		10g/l	4	5
		30g/l	4–5	5–6
		60g/l	4–5	6
Perspiration Light 耐汗日光	Acid 酸	5g/l	3–4	4–5
		10g/l	4	4–5
		30g/l	4–5	5
		60g/l	4–5	5–6
	Alkali 鹼	5g/l	3–4	4–5
		10g/l	4	4–5
		30g/l	4–5	5
		60g/l	4–5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	4–5

Everlight Chemical

Everzol Scarlet FC

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	90
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	1–2
	Acetic Acid 醋酸	3–4
Alkali Spotting 鹼滴	Ammonia Water 氨水	4
	Soda Ash Solution 純鹼	3–4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary Ammonium Salt 四級胺鹽	3–4
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3

X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 30g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25° C)

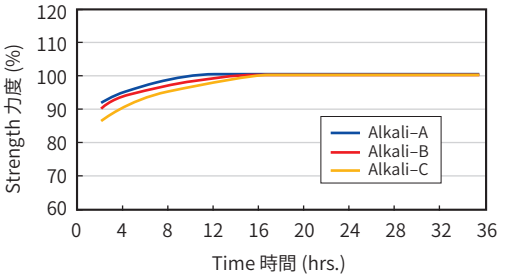


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

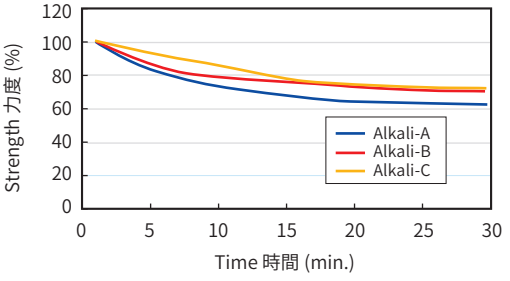

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

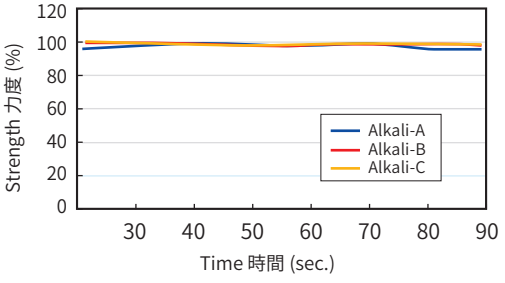

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

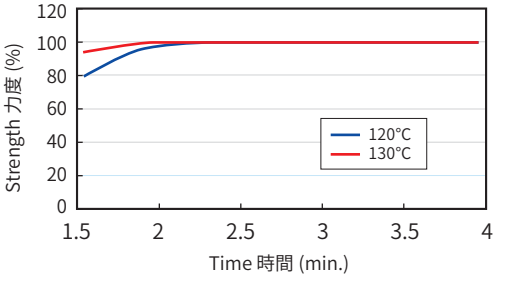

Everzol Scarlet FC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	4–5	5	5	5	5
	ISO C10 C		4	5	4–5	4–5	5	5	5
	ISO C10 D		4	5	4	5	5	5	3
	ISO C06–C1S		4	5	4	5	5	5	5
	ISO C06–C2S		4	5	4–5	5	5	5	5
	M&S C4A		4–5	5	4–5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	3–4	–	3–4	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	3	2–3	4–5	5	4–5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	4–5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	4–5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	4–5	4–5	4–5	4
		Wet 溼	3–4	3	2–3	2
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	4	4	4	4
		Peroxide Bleaching 雙氧水漂白	–	–	3	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	2–3	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	2	–
		4 Hours after	–	–	4	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	4	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	3–4
		10g/l	3–4	3–4
		30g/l	3–4	4
		60g/l	4	4–5
Perspiration Light 耐汗日光	Acid 酸	5g/l	3	4
		10g/l	3–4	4–5
		30g/l	4	5
		60g/l	4–5	5–6
	Alkali 鹼	5g/l	3	3–4
		10g/l	3–4	4
		30g/l	3–4	4–5
		60g/l	4	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	5

Everlight Chemical

Everzol Blue FC

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	30
	Alkali 鹼劑 A + 100g/l Urea 尿素	30
	Alkali 鹼劑 B	60
	Alkali 鹼劑 B + 100g/l Urea 尿素	60
	Alkali 鹼劑 C	60
	Alkali 鹼劑 C + 100g/l Urea 尿素	60
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	B(G)
	TL84 Lamp	B(G)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4
	Cu^{2+} 銅離子	4–5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	1
	Alkaline 鹼性	1

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25° C)

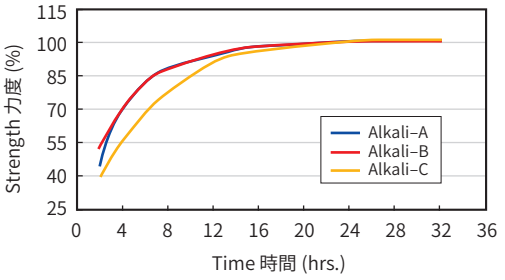


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

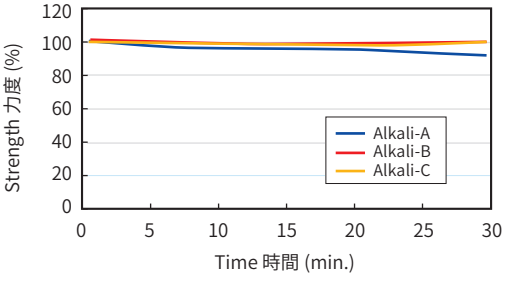

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

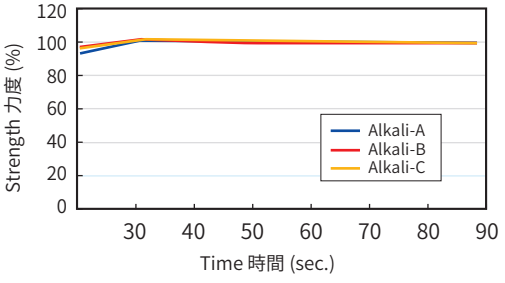

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

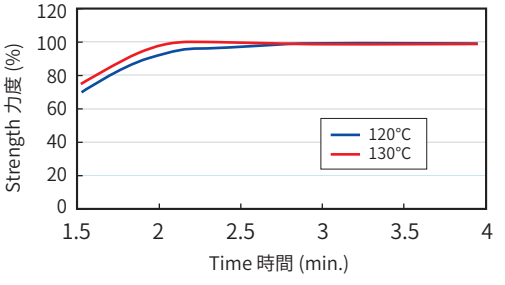

Everzol Blue FC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	4	5	5	5	5
	ISO C10 C		4–5	5	4	5	5	5	5
	ISO C10 D		4–5	5	4	5	5	5	5
	ISO C06–C1S		4–5	5	4	5	5	5	5
	ISO C06–C2S		4–5	5	4	5	5	5	5
	M&S C4A		4–5	5	4	5	5	5	5
Water 耐水		30g/l	4–5	5	4–5	4–5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	4–5	2	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	2–3	–	4–5	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	4	4	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	4–5	4	4–5	5	5
	Alkali 鹼	30g/l	4–5	5	4–5	4–5	4–5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	4–5	4
		Wet 溼	4–5	4	3–4	3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	1–2	1–2	2–3	3
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	3–4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	2	3	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4–5	5
		10g/l	5	5–6
		30g/l	5	5–6
		60g/l	5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	4	4–5
		10g/l	4–5	5
		30g/l	4–5	5
		60g/l	4–5	5
	Alkali 鹼	5g/l	4	4–5
		10g/l	4–5	4–5
		30g/l	4–5	5
		60g/l	4–5	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	5

Everlight Chemical

Everzol Yellow LX

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	120
	50°C water 水 + 50g/l Salt 鹽	120
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4G
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3–4
	Acetic Acid 醋酸	5
Alkali Spotting 鹼滴	Ammonia Water 氨水	3
	Soda Ash Solution 純鹼	5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	3


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 10g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

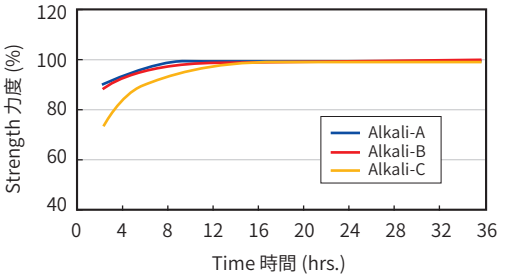


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

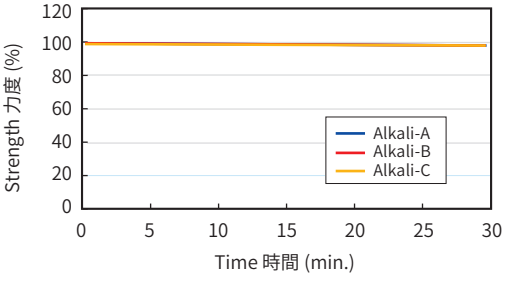


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

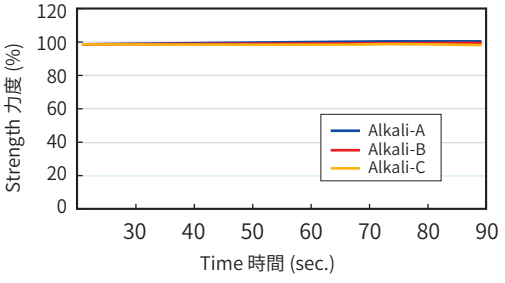

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

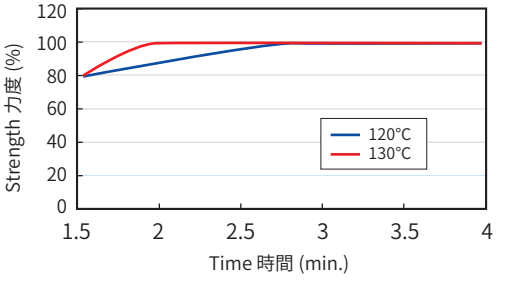

Everzol Yellow LX

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	5	5	5	5	5
	ISO C10 D		4–5	5	4–5	4–5	5	4–5	4
	ISO C06–C1S		4–5	5	5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		10g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		10g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	4R	–	4–5	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	4–5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	5	5	5	5	5	5	5
	Alkali 鹼	10g/l	5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	5	–
		Wet 溼	–	–	4	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4	–
		Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4–5	5–6
		5g/l	4–5	5–6
		10g/l	4–5	5–6
		30g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	1g/l	4–5	5–6
		5g/l	5	6
		10g/l	5	6
		30g/l	5	6
	Alkali 鹼	1g/l	4	5
		5g/l	4–5	5
		10g/l	4–5	5–6
		30g/l	4–5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	–

Everlight Chemical

Everzol Red LX

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R(Y)
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	1
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	3–4
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4–5
	Alkaline 鹼性	3


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 10g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)		✓
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

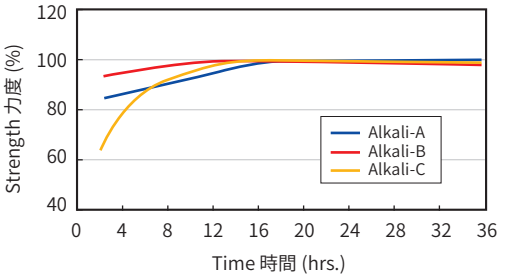


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

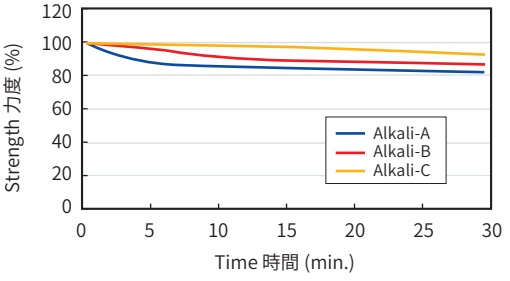


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

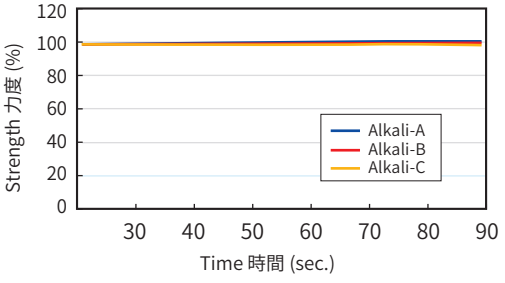

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

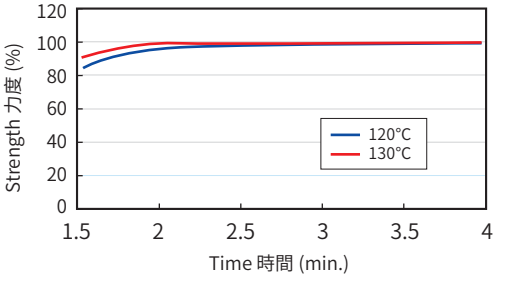

Everzol Red LX

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	5	5	5	5	5
	ISO C10 D		4–5	5	4–5	5	5	5	4–5
	ISO C06–C1S		4–5	5	4–5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		10g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	5	5	5	5	5	5	5
Sea Water 耐海水		10g/l	4	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	2	–	4–5	–			
Acid Hydrolysis 酸水解		10g/l	4	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	10g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	5	–
		Wet 溼	–	–	4	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	3–4	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	2–3	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	4	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	3–4	4
		5g/l	3–4	4
		10g/l	3–4	4–5
		30g/l	4	5–6
Perspiration Light 耐汗日光	Acid 酸	1g/l	3–4	3–4
		5g/l	3	3–4
		10g/l	3	3–4
		30g/l	4	3–4
	Alkali 鹼	1g/l	3–4	3
		5g/l	3–4	3–4
		10g/l	3–4	3–4
		30g/l	4	4
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	–

Everlight Chemical

Everzol Red LF–B

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	80
	Alkali 鹼劑 A + 100g/l Urea 尿素	80
	Alkali 鹼劑 B	80
	Alkali 鹼劑 B + 100g/l Urea 尿素	80
	Alkali 鹼劑 C	80
	Alkali 鹼劑 C + 100g/l Urea 尿素	80
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4
	Cu^{2+} 銅離子	1
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5(B)
	Acetic Acid 醋酸	5
Alkali Spotting 鹼滴	Ammonia Water 氨水	2
	Soda Ash Solution 純鹼	1
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	2–3
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 10g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

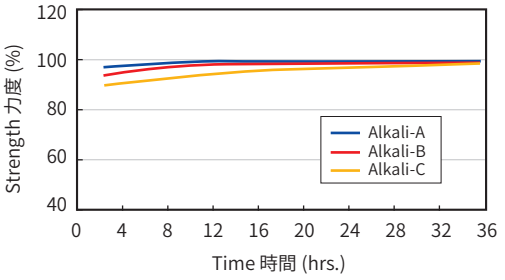


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

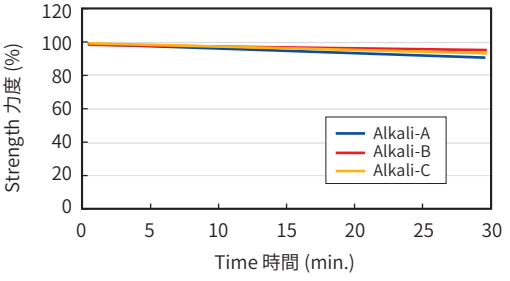


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

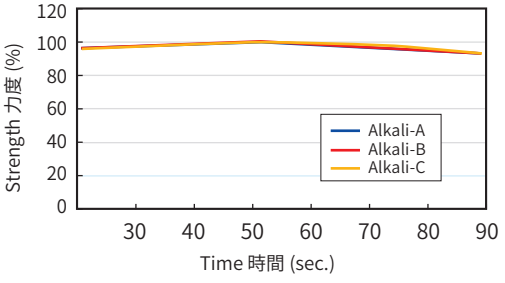

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

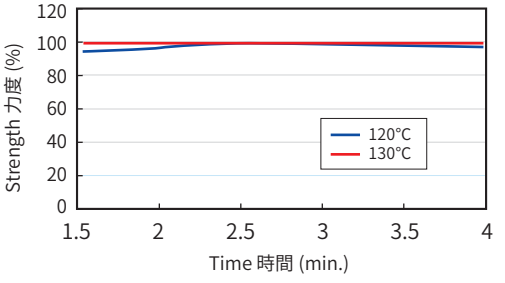

Everzol Red LF–B

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4	5	4–5	5	5	5	5
	ISO C10 C		4	5	4	5	5	5	5
	ISO C10 D		4	5	3–4	5	5	5	3–4
	ISO C06–C1S		4	5	3–4	5	5	5	5
	ISO C06–C2S		4	5	3–4	5	5	5	5
	M&S C4A		4–5	5	4–5	5	5	5	5
Water 耐水		10g/l	4–5	5	5	4–5	5	5	5
Hot Water 耐熱水		10g/l	4–5	5	4–5	5	5	5	5
Sea Water 耐海水		10g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	3–4	–	4–5	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	5	5	5	5	5	5	5
	Alkali 鹼	10g/l	5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	5	–
		Wet 溼	–	–	4	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2	–
		Peroxide Bleaching 雙氧水漂白	–	–	5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4	4–5
		5g/l	4–5	5
		10g/l	4–5	5–6
		30g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	1g/l	3	4–5
		5g/l	3–4	5
		10g/l	4	5–6
		30g/l	4–5	5–6
	Alkali 鹼	1g/l	3–4	3–4
		5g/l	4	4
		10g/l	4	4–5
		30g/l	4–5	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	–

Everlight Chemical

Everzol Red LF–2B

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	70
	Alkali 鹼劑 A + 100g/l Urea 尿素	70
	Alkali 鹼劑 B	80
	Alkali 鹼劑 B + 100g/l Urea 尿素	80
	Alkali 鹼劑 C	80
	Alkali 鹼劑 C + 100g/l Urea 尿素	80
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	1B
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	3
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4–5


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 10g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

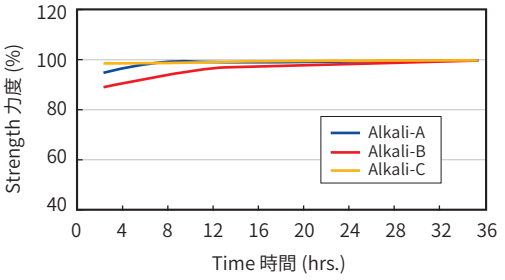


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

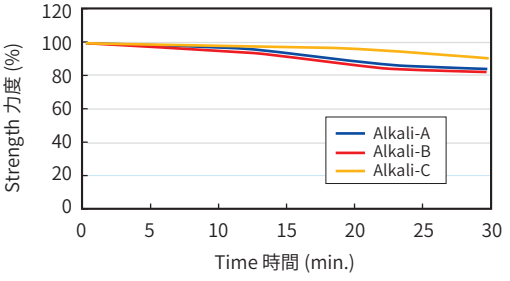


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

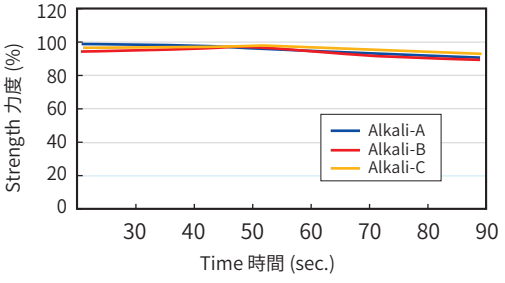

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

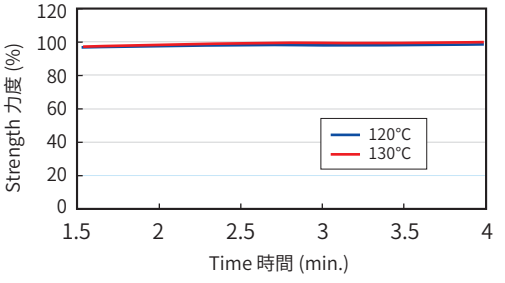

Everzol Red LF–2B

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4	5	4–5	5	5	5	5
	ISO C10 C		4	5	4–5	5	5	5	5
	ISO C10 D		4	5	4–5	4–5	5	5	3–4
	ISO C06–C1S		4	5	4–5	5	5	5	5
	ISO C06–C2S		4	5	4–5	5	5	5	5
	M&S C4A		4–5	5	4–5	5	5	5	5
Water 耐水		10g/l	4–5	5	5	4–5	5	5	5
Hot Water 耐熱水		10g/l	4–5	5	4–5	5	5	5	5
Sea Water 耐海水		10g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	3–4B	–	4–5	–			
Acid Hydrolysis 酸水解		10g/l	5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	5	5	5	5	5	5	5
	Alkali 鹼	10g/l	5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	5	–
		Wet 溼	–	–	4–5	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2	–
		Peroxide Bleaching 雙氧水漂白	–	–	3–4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	2–3	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	3	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4–5	5
		5g/l	4–5	5–6
		10g/l	4–5	5–6
		30g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	1g/l	3–4	5
		5g/l	4	5–6
		10g/l	4–5	5–6
		30g/l	4–5	5–6
	Alkali 鹼	1g/l	4	4–5
		5g/l	4	5
		10g/l	4–5	5
		30g/l	4–5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	–

Everlight Chemical

Everzol Red LF–4B

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	80
	Alkali 鹼劑 A + 100g/l Urea 尿素	80
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	2–3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3
	Acetic Acid 醋酸	3
Alkali Spotting 鹼滴	Ammonia Water 氨水	3
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4
Discharge Ability 拔染性	Neutral 中性	4–5
	Alkaline 鹼性	4–5


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 10g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

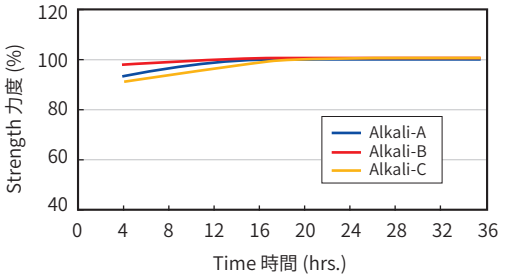


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

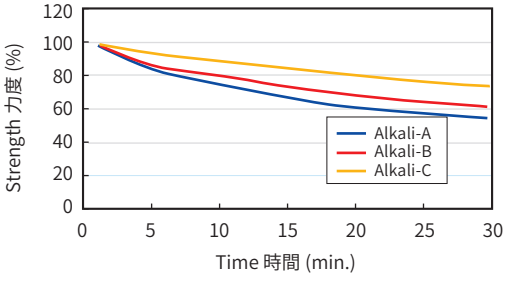


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

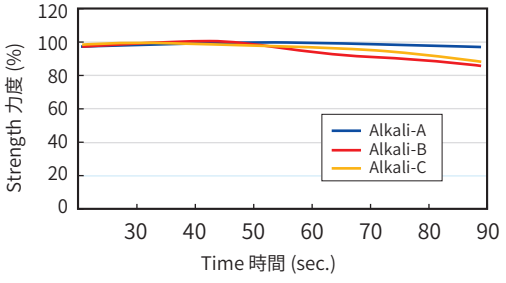

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

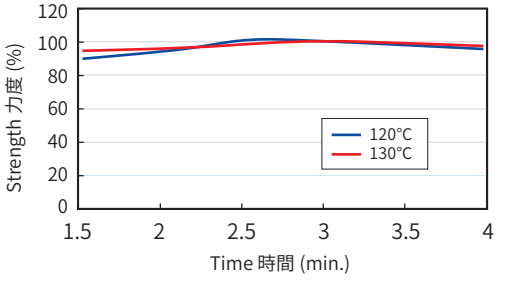

Everzol Red LF–4B

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4	5	5	5	5	5	5
	ISO C10 C		4	5	5	4–5	5	5	4–5
	ISO C10 D		4	5	5	4	5	5	5
	ISO C06–C1S		4	5	5	4–5	4–5	5	5
	ISO C06–C2S		4	5	5	4–5	5	5	4–5
	M&S C4A		4	5	5	5	5	5	4–5
Water 耐水		10g/l	4–5	5	4–5	4–5	5	5	5
Hot Water 耐熱水		10g/l	4–5	5	4–5	5	5	5	4–5
Sea Water 耐海水		10g/l	4–5	5	4–5	5	5	5	5
Post Mercerizing 後絲光		10g/l	4	–	3	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	4–5	5	5	5	4–5
Perspiration 耐汗	Acid 酸	10g/l	4–5	4–5	4–5	4–5	5	5	5
	Alkali 鹼	10g/l	4–5	5	4–5	4–5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4	3–4	3	3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3	–
		Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	4	3–4	3–4	–
		4 Hours after	5	5	5	–
	Wet 溼	Immediately	3	3	3	–
		4 Hours after	4–5	4–5	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	3–4	4
		5g/l	4	4–5
		10g/l	4	5
		30g/l	4–5	5
Perspiration Light 耐汗日光	Acid 酸	1g/l	3	4
		5g/l	3	4–5
		10g/l	3–4	5
		30g/l	4	5
	Alkali 鹼	1g/l	3	4
		5g/l	3	4
		10g/l	3–4	4–5
		30g/l	4	4–5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	5
		30g/l	–	5

Everlight Chemical

Everzol Blue C–LX

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	40
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	80
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	70
	Alkali 鹼劑 B + 100g/l Urea 尿素	80
	Alkali 鹼劑 C	70
	Alkali 鹼劑 C + 100g/l Urea 尿素	80
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	G
	TL84 Lamp	B(G)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4
	Cu^{2+} 銅離子	4–5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	1
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	2–3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	2–3


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 10g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

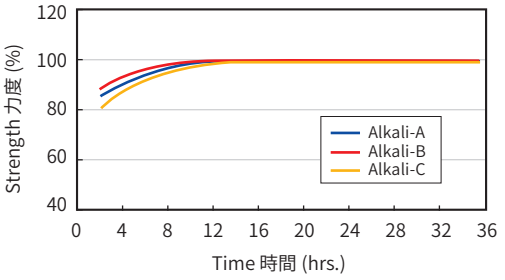


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

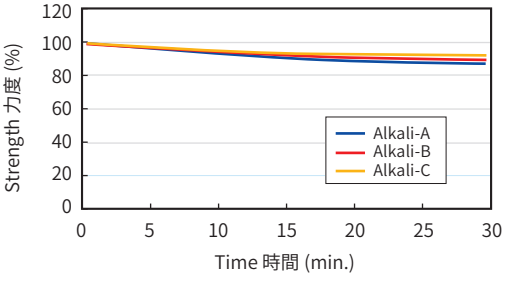


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

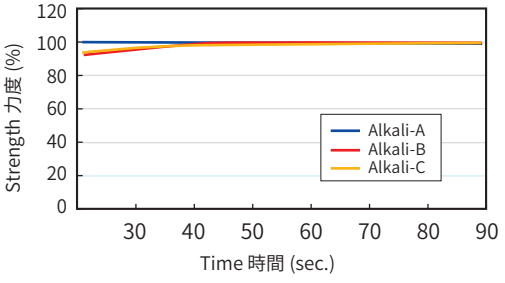

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

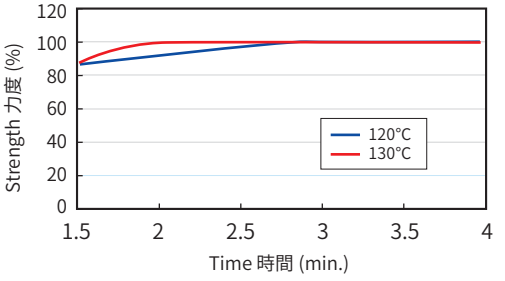

Everzol Blue C–LX

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4–5	5	4–5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	5
	ISO C10 D		4–5	5	3–4	5	5	5	4
	ISO C06–C1S		4–5	5	4–5	5	5	5	5
	ISO C06–C2S		4–5	5	4–5	5	5	5	5
	M&S C4A		5	5	4–5	5	5	5	5
Water 耐水		10g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	5	4–5	5	4	5	5	5
Sea Water 耐海水		10g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	4–5	–	5	–			
Acid Hydrolysis 酸水解		10g/l	4–5	4–5	4–5	4–5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	5	5	5	4–5	5	5	5
	Alkali 鹼	10g/l	5	5	5	4–5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	5	–
		Wet 溼	–	–	3–4	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2–3	–
		Peroxide Bleaching 雙氧水漂白	–	–	2–3	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4	4–5
		5g/l	4–5	5
		10g/l	4–5	5–6
		30g/l	4–5	6
Perspiration Light 耐汗日光	Acid 酸	1g/l	4	4
		5g/l	4	4–5
		10g/l	4–5	5
		30g/l	>4–5	5–6
	Alkali 鹼	1g/l	4	3–4
		5g/l	4	4
		10g/l	4–5	4–5
		30g/l	>4–5	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Grey LF

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	1–2
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	3–4
	Soda Ash Solution 純鹼	3–4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	3–4
	Glyoxal 乙二醛	3–4
Discharge Ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	2


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 10g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix		✓
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

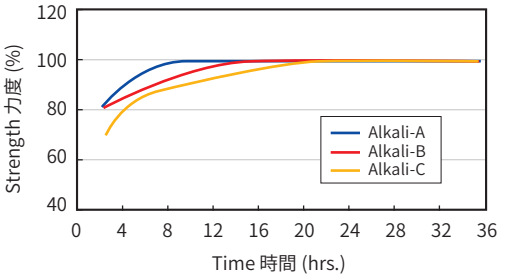


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

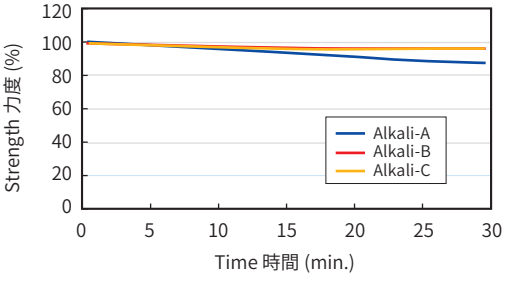


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

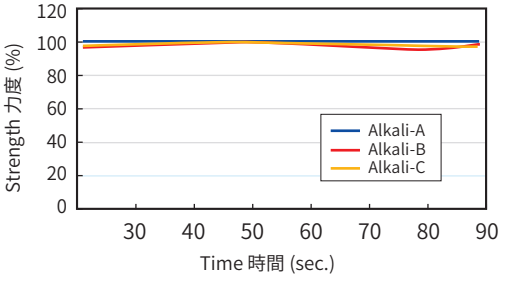

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

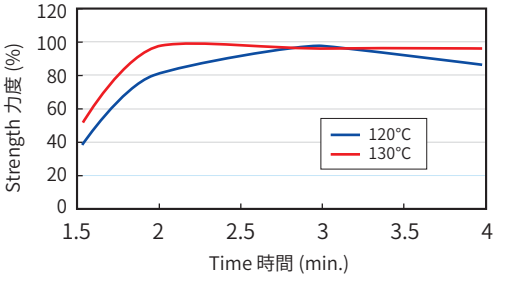

Everzol Grey LF

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	4–5	5	5	5	5
	ISO C10 D		4–5	5	5	5	5	5	5
	ISO C06–C1S		4–5	5	5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		10g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	4–5	5	5	4–5	5	5	5
Sea Water 耐海水		10g/l	4	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	4	–	4–5	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	10g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	4–5	–
		Wet 溼	–	–	4	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3	–
		Peroxide Bleaching 雙氧水漂白	–	–	3–4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4	4–5
		5g/l	4–5	5
		10g/l	4–5	5–6
		30g/l	4–5	6
Perspiration Light 耐汗日光	Acid 酸	1g/l	3–4	4
		5g/l	4	4–5
		10g/l	4	5
		30g/l	4	5–6
	Alkali 鹼	1g/l	3–4	4
		5g/l	4	4–5
		10g/l	4	5
		30g/l	4–5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4
		30g/l	–	–

Everlight Chemical

Everzol Dark Blue LF

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	60
	Alkali 鹼劑 A + 100g/l Urea 尿素	80
	Alkali 鹼劑 B	80
	Alkali 鹼劑 B + 100g/l Urea 尿素	80
	Alkali 鹼劑 C	80
	Alkali 鹼劑 C + 100g/l Urea 尿素	80
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5G(Y)
	Cu^{2+} 銅離子	4–5G(Y)
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	1
	Acetic Acid 醋酸	5
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	1
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	1
	Alkaline 鹼性	1

X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 10g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染			✓
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25°C)

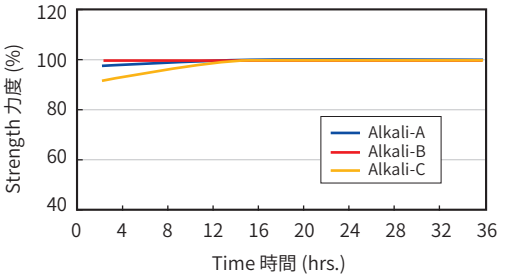


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

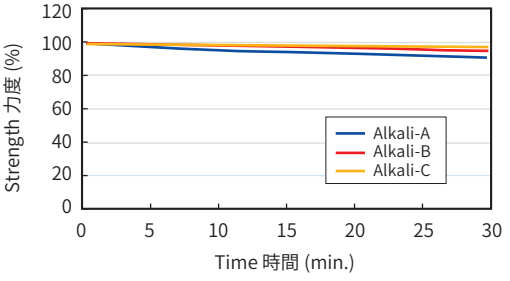

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

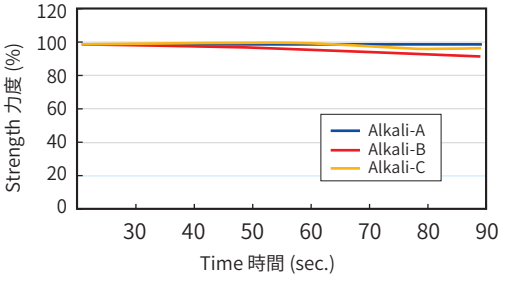

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

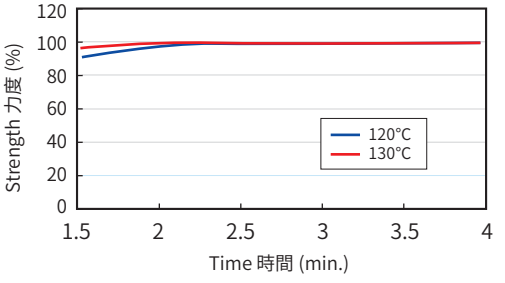

Everzol Dark Blue LF

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	4	5	5	5	4–5
	ISO C10 D		4	5	4–5	3–4	5	5	2
	ISO C06–C1S		4–5	5	4–5	5	5	5	4–5
	ISO C06–C2S		4–5	5	4–5	5	5	5	4–5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		10g/l	4–5	5	5	4–5	5	5	5
Hot Water 耐熱水		10g/l	4–5	5	5	5	5	5	4–5
Sea Water 耐海水		10g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	4–5	–	4–5	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	4–5	4–5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	4–5	5	4–5	4–5	5	5	5
	Alkali 鹼	10g/l	4–5	5	4–5	4–5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	5	–
		Wet 溼	–	–	3–4	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	1–2	–
		Peroxide Bleaching 雙氧水漂白	–	–	3–4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	3–4R	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	3–4R	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	3–4	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	3–4	4	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	3–4	4
		5g/l	4	4–5
		10g/l	4	5
		30g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	1g/l	3	4–5
		5g/l	3–4	5
		10g/l	4	5
		30g/l	4–5	5–6
	Alkali 鹼	1g/l	3	3–4
		5g/l	3–4	4
		10g/l	4	4–5
		30g/l	4–5	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	–

Everlight Chemical

Everzol Yellow ED–R

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	2–3


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

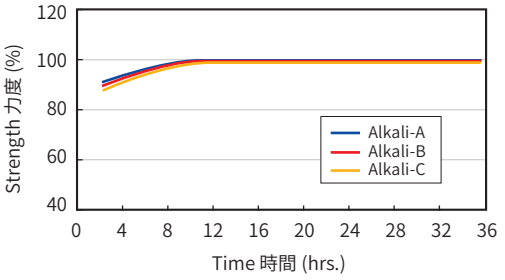


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

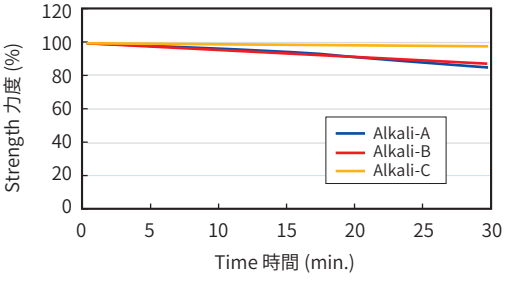


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

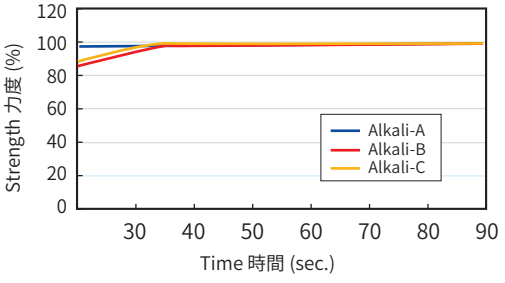

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

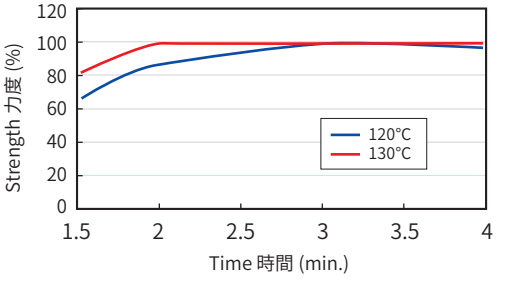

Everzol Yellow ED–R

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4–5	5	5	5	5
	ISO C10 C		5	5	4	5	5	5	5
	ISO C10 D		5	5	4–5	5	5	5	4–5
	ISO C06–C1S		5	5	4–5	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	4–5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4	5	4–5	5	5	5	5
Post Mercerizing 後絲光		30g/l	4	–	4–5	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	4–5	4	5	5	4–5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	4–5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	4–5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	4–5	4–5
		Wet 溼	4	3–4	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2–3	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4–5	5–6
		10g/l	4–5	5–6
		30g/l	4–5	5–6
		60g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	4	5–6
		10g/l	4–5	5–6
		30g/l	4–5	6
		60g/l	4–5	6
	Alkali 鹼	5g/l	4–5	5
		10g/l	4–5	5–6
		30g/l	4–5	5–6
		60g/l	4–5	6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	5

Everlight Chemical

Everzol Yellow ED

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	G
	TL84 Lamp	G
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	4–5
	Alkaline 鹼性	3


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

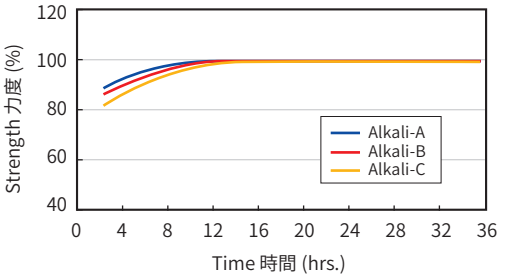


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

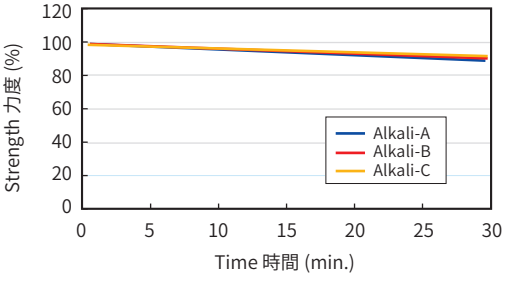


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

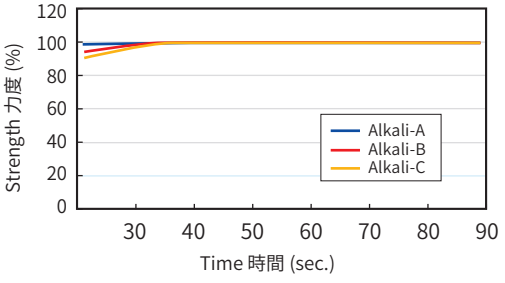

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

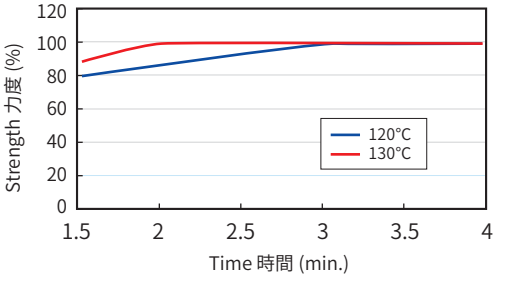

Everzol Yellow ED

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4–5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	5
	ISO C10 D		5	4–5	4	5	5	5	4–5
	ISO C06–C1S		5	5	4	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	4–5	5	5	5	5
Post Mercerizing 後絲光		30g/l	3–4	–	4–5	–			
Acid Hydrolysis 酸水解		30g/l	4	5	4–5	4	5	5	4
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	4	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	4	4–5	5	5	5

Dyeing Depth 染色濃度		5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦	Dry 乾	5	5	4–5	4–5
	Wet 溼	4	3–4	3	2–3
		Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白	Chlorinated Water (20ppm) 耐氯水	–	–	2	–
	Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓 Dry 乾	Immediately	–	–	5	–
	4 Hours after	–	–	5	–
Hot-Pressing 耐熱壓 Wet 溼	Immediately	–	–	5	–
	4 Hours after	–	–	5	–
Multi-Laundering (M&S C10A) 耐多次水洗		–	–	4–5	–
Saliva (DIN) 耐唾液		–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色		–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4–5	5
		10g/l	4–5	5
		30g/l	4–5	5–6
		60g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	4	5
		10g/l	4	5
		30g/l	4	5–6
		60g/l	4	5–6
	Alkali 鹼	5g/l	4	4–5
		10g/l	4	5
		30g/l	4	5–6
		60g/l	4	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	5

Everlight Chemical

Everzol Orange ED–N


Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	40
	Alkali 鹼劑 A + 100g/l Urea 尿素	60
	Alkali 鹼劑 B	40
	Alkali 鹼劑 B + 100g/l Urea 尿素	60
	Alkali 鹼劑 C	60
	Alkali 鹼劑 C + 100g/l Urea 尿素	60
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	2–3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	3–4
Discharge Ability 拔染性	Neutral 中性	4–5
	Alkaline 鹼性	4–5

X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 10g/l depth.


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

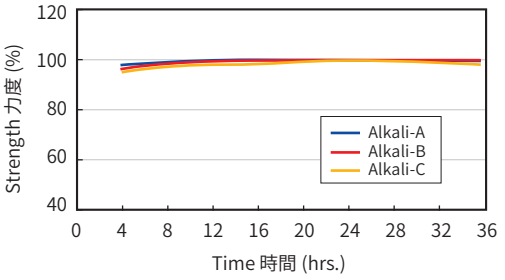


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

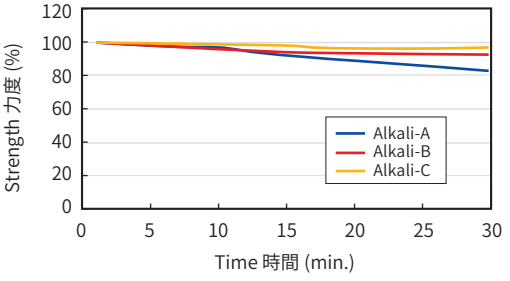

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

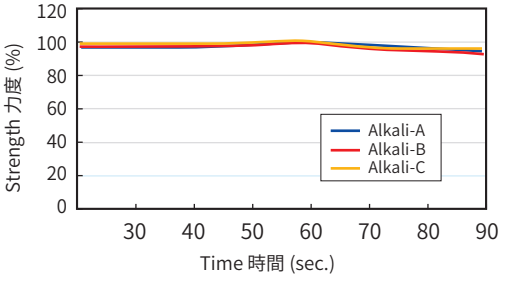


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)		✓
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix		✓
Discharge Printing 拔染印花		✓	

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

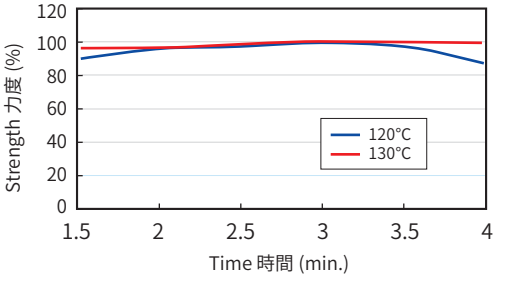

Everzol Orange ED–N

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	5	5	5	5	5
	ISO C10 D		4–5	5	5	5	5	5	4
	ISO C06–C1S		4–5	5	5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		10g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		10g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	4–5	–	4	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	10g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	4–5	–
		Wet 溼	–	–	3–4	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2–3	–
		Peroxide Bleaching 雙氧水漂白	–	–	3–4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	3–4	4–5
		5g/l	4	5
		10g/l	4–5	5
		30g/l	4–5	4–6
Perspiration Light 耐汗日光	Acid 酸	1g/l	3–4	4–5
		5g/l	4	5
		10g/l	4–5	5
		30g/l	4–5	5
	Alkali 鹼	1g/l	3	4–5
		5g/l	3	5
		10g/l	3–4	5
		30g/l	4	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	4–5

Everlight Chemical

Everzol Orange ED–4R

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	30
	Alkali 鹼劑 A + 100g/l Urea 尿素	80
	Alkali 鹼劑 B	60
	Alkali 鹼劑 B + 100g/l Urea 尿素	80
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	1–2
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	5
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	4–5
	Alkaline 鹼性	4–5


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

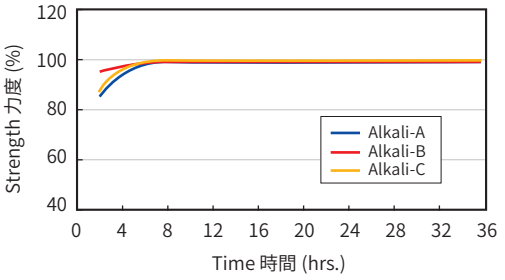


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

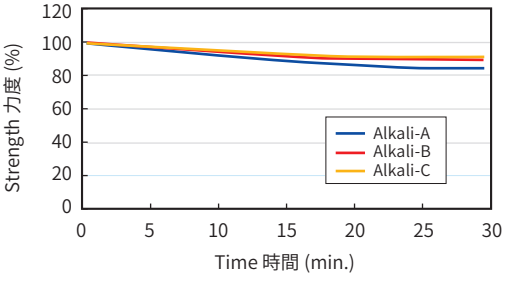


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

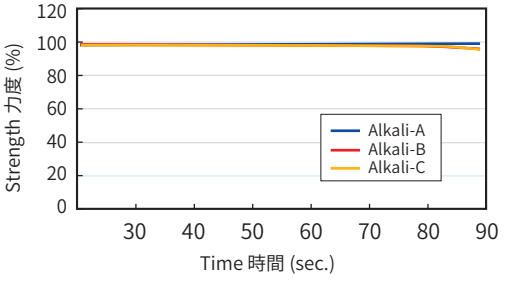

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

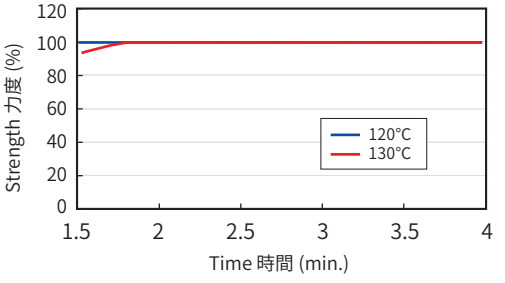

Everzol Orange ED–4R

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	4–5	5	5	5	5
	ISO C10 D		4	5	3–4	4–5	5	4–5	3–4
	ISO C06–C1S		4–5	5	4–5	5	5	5	5
	ISO C06–C2S		4–5	5	4–5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	3	–	3	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	4–5	5	5	5	4–5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	4–5	4–5
		Wet 溼	4	3–4	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	2–3	3	3–4	4
		Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	2–3	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	2–3	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3–4	4–5
		10g/l	4	4–5
		30g/l	4	5
		60g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	3–4	4–5
		10g/l	4	5
		30g/l	4	5
		60g/l	4–5	5–6
	Alkali 鹼	5g/l	3–4	4
		10g/l	4	4–5
		30g/l	4–5	5
		60g/l	4–5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	4–5

Everlight Chemical

Everzol Red ED

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	B
	TL84 Lamp	B
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4
	Cu^{2+} 銅離子	2–3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	2–3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary Ammonium Salt 四級胺鹽	4
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	2–3
	Alkaline 鹼性	1–2


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

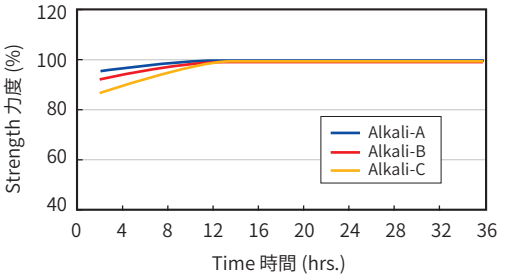


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

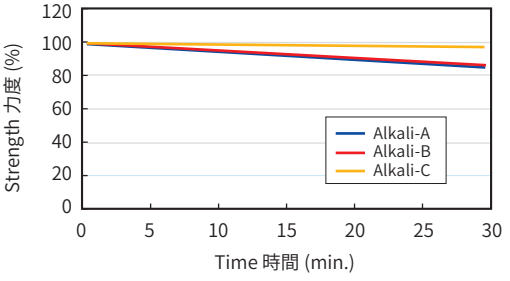


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

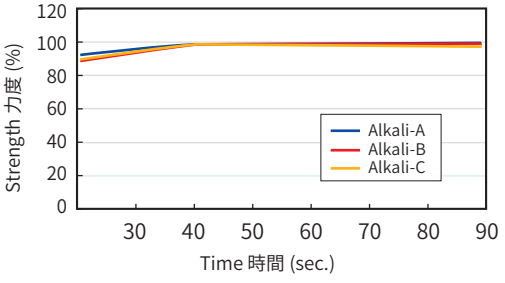

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

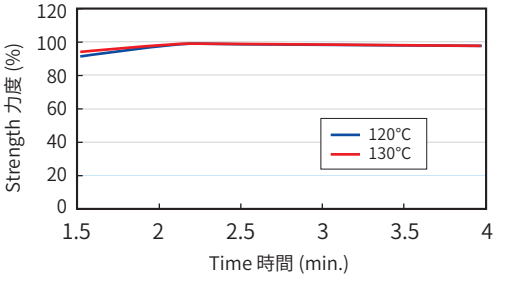

Everzol Red ED

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4–5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	5
	ISO C10 D		5	4–5	4	5	5	5	4–5
	ISO C06–C1S		5	5	4–5	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	4–5	5	5	5	5
Water 耐水		30g/l	4–5	5	4–5	4–5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	4	5	5	4	4–5
Post Mercerizing 後絲光		30g/l	3	–	4–5	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	2–3	2–3	5	4–5	3
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	4	5	5	5	4–5
	Alkali 鹼	30g/l	4–5	5	4	5	5	5	4–5

Dyeing Depth 染色濃度		5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦	Dry 乾	5	5	4–5	4–5
	Wet 溼	3–4	3	3	2–3
		Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白	Chlorinated Water (20ppm) 耐氯水	–	–	3–4	–
	Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓 Dry 乾	Immediately	–	–	4	–
	4 Hours after	–	–	5	–
Hot-Pressing 耐熱壓 Wet 溼	Immediately	–	–	4	–
	4 Hours after	–	–	5	–
Multi-Laundering (M&S C10A) 耐多次水洗		–	–	4–5	–
Saliva (DIN) 耐唾液		–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色		–	4–5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	4
		10g/l	3–4	4–5
		30g/l	4	5
		60g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	3–4
		10g/l	3	4
		30g/l	3–4	4–5
		60g/l	4	5
	Alkali 鹼	5g/l	2–3	3
		10g/l	3	3–4
		30g/l	4	4–5
		60g/l	4	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4

Everlight Chemical

Everzol Red ED–2B

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	150
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	B
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	1–2B
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	1B
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	3
	Quaternary Ammonium Salt 四級胺鹽	3
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	2–3
	Alkaline 鹼性	1–2


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

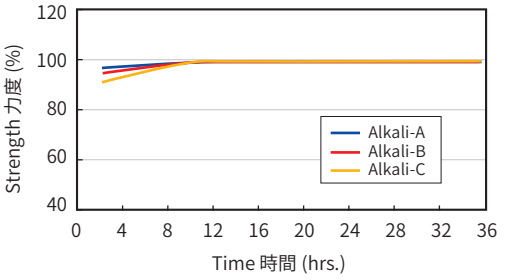


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

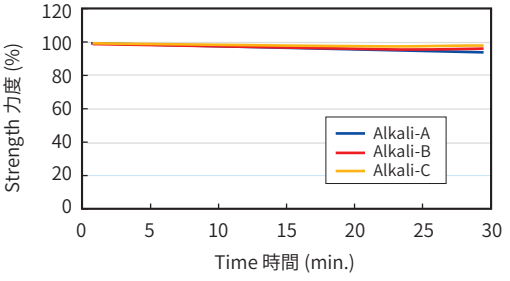


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

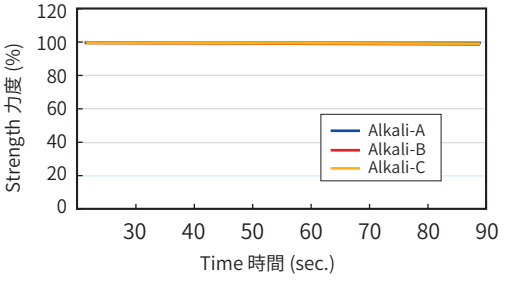

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

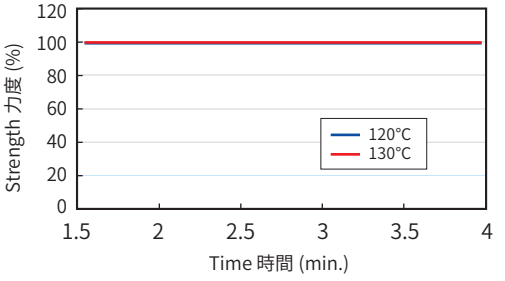

Everzol Red ED–2B

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4–5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	4–5	5
	ISO C10 D		5	5	4	5	5	5	4–5
	ISO C06–C1S		5	5	4	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	4–5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	4–5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4	5	4–5	5	5	4–5	5
Post Mercerizing 後絲光		30g/l	2–3	–	4–5	–			
Acid Hydrolysis 酸水解		30g/l	3–4	5	4	3	5	5	3–4
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	4–5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	4	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	4–5	4–5
		Wet 溼	3–4	3	2–3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3	–
		Peroxide Bleaching 雙氧水漂白	–	–	3–4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	3–4	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	4
		10g/l	3–4	4–5
		30g/l	4	5
		60g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	4
		10g/l	3	4
		30g/l	4	4–5
		60g/l	4	5
	Alkali 鹼	5g/l	2–3	3
		10g/l	3	3
		30g/l	3–4	4
		60g/l	3–4	4–5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4

Everlight Chemical

Everzol Red ED–3B

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	B
	TL84 Lamp	B
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	1–2B
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	1B
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	3
	Quaternary Ammonium Salt 四級胺鹽	3
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	2–3
	Alkaline 鹼性	1–2


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

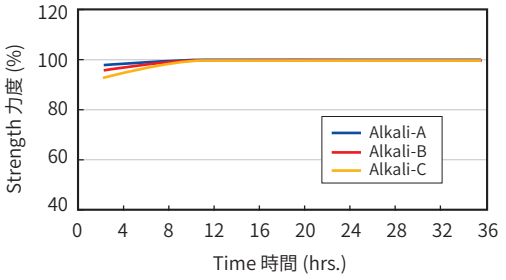


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

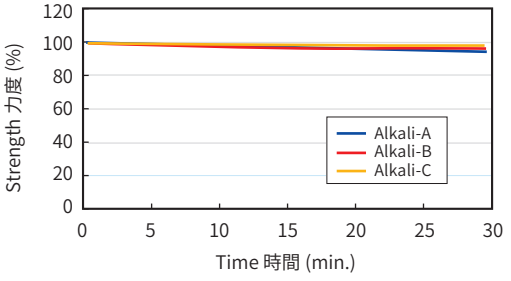


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

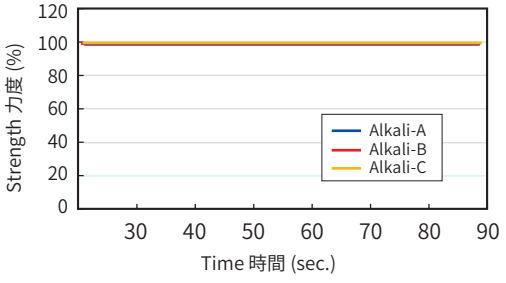

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

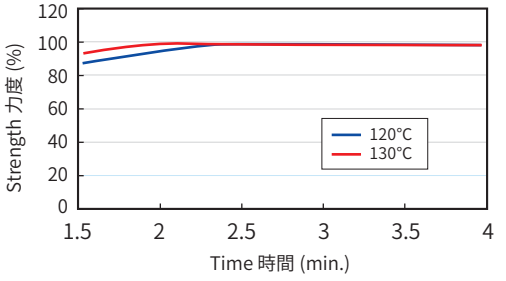

Everzol Red ED–3B

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4–5	5	5	4–5	5
	ISO C10 C		5	5	4–5	5	5	5	5
	ISO C10 D		5	5	4	5	5	5	4–5
	ISO C06–C1S		5	5	4–5	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	4–5	5	5	5	5
Water 耐水		30g/l	4–5	5	4–5	4–5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	3–4	5	4–5	5	5	4–5	5
Post Mercerizing 後絲光		30g/l	2	–	4–5	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	2–3	2–3	5	4–5	3
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	4	5	5	4–5	4–5
	Alkali 鹼	30g/l	4–5	5	4	4–5	4–5	4–5	4–5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	4–5	4–5
		Wet 溼	4	3–4	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4	–
		Peroxide Bleaching 雙氧水漂白	–	–	3–4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	3–4	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	3–4	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3–4	4–5
		10g/l	4	4–5
		30g/l	4	5
		60g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	2	3–4
		10g/l	2–3	4
		30g/l	3–4	4
		60g/l	4	5
	Alkali 鹼	5g/l	2–3	2
		10g/l	3	3
		30g/l	3–4	3–4
		60g/l	4	4–5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	3–4

Everlight Chemical

Everzol Red ED–7BN

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	1
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3–4
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	2–3B
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4
Resin Finishing 樹脂加工	Melamine 三聚氰胺	3–4
	Glyoxal 乙二醛	3–4
Discharge Ability 拔染性	Neutral 中性	2–3
	Alkaline 鹼性	3


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染			✓
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

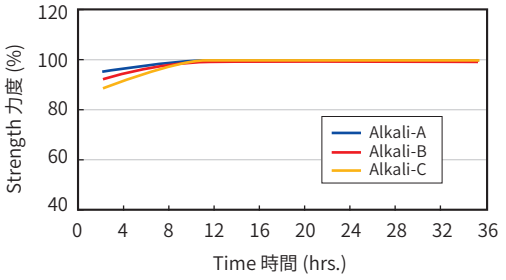


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

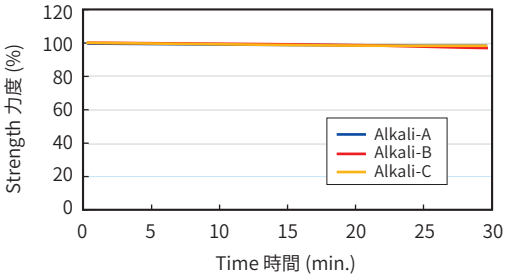


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

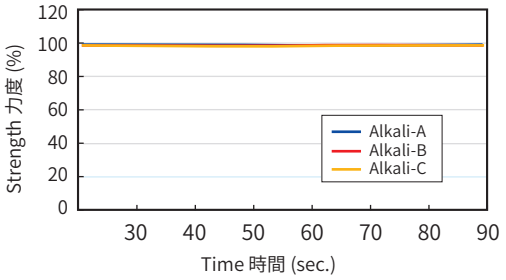

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

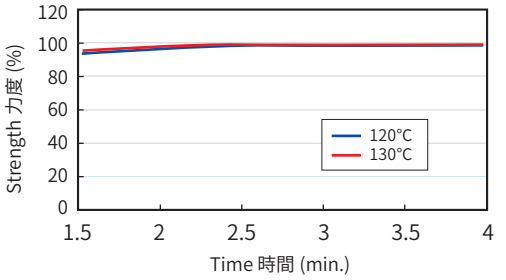

Everzol Red ED–7BN

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	4–5	5	5	5	5
	ISO C10 C		4–5	5	4	5	5	5	5
	ISO C10 D		4–5	5	3	5	5	5	3–4
	ISO C06–C1S		4–5	5	4	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		30g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	4B	–	2–3	–			
Acid Hydrolysis 酸水解		30g/l	5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	5	5	5	5	5	5	5
	Alkali 鹼	30g/l	5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	4–5	4–5
		Wet 溼	3–4	3	2–3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	3–4	–
		4 Hours after	–	–	4	–
	Wet 溼	Immediately	–	–	3–4	–
		4 Hours after	–	–	4	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	4–5
		10g/l	3–4	5
		30g/l	4	5–6
		60g/l	4–5	6
Perspiration Light 耐汗日光	Acid 酸	5g/l	3–4	4–5
		10g/l	4	5
		30g/l	4–5	5
		60g/l	>4–5	6
	Alkali 鹼	5g/l	3–4	4
		10g/l	4	4–5
		30g/l	4	5–6
		60g/l	4–5	6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Red ED–S

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	2–3B
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3–4
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	4
	Soda Ash Solution 純鹼	4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4
Discharge Ability 拔染性	Neutral 中性	3–4
	Alkaline 鹼性	4


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染			✓
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

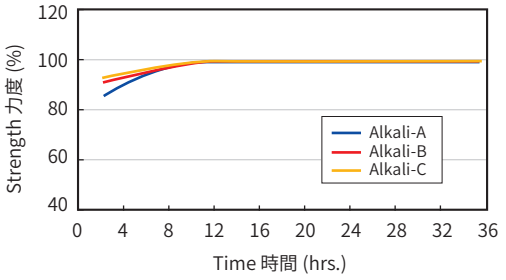


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

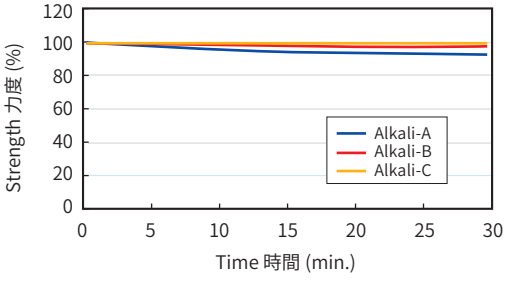


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

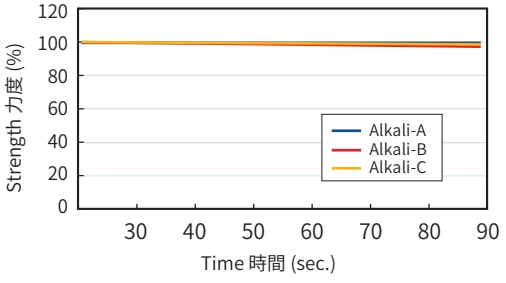

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

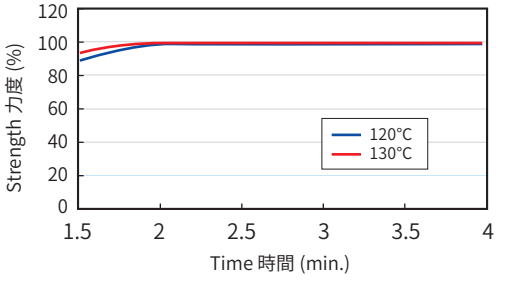

Everzol Red ED–S

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	4–5	5	5	5	5
	ISO C10 C		4–5	5	4	5	5	5	5
	ISO C10 D		4–5	5	2	4–5	5	5	3
	ISO C06–C1S		4–5	5	4	5	5	5	5
	ISO C06–C2S		4–5	5	4	5	5	5	5
	M&S C4A		4–5	5	4–5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	4–5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	2	–	2	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	4–5	4–5	4–5	4
		Wet 溼	4	3	2–3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	2	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	2–3	4
		10g/l	3	4–5
		30g/l	3–4	5
		60g/l	4	6
Perspiration Light 耐汗日光	Acid 酸	5g/l	2	3–4
		10g/l	2–3	4
		30g/l	3	5
		60g/l	4	6
	Alkali 鹼	5g/l	2	3–4
		10g/l	2–3	4
		30g/l	3–4	5
		60g/l	4	6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Rubine ED

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	80
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	B
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	1B
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary Ammonium Salt 四級胺鹽	4
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	1
	Alkaline 鹼性	1

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25°C)

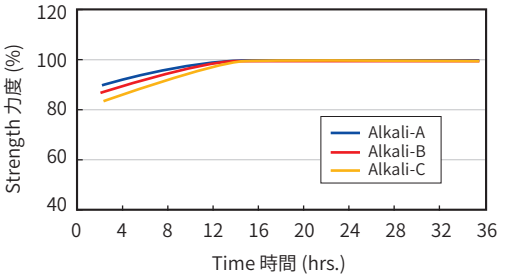


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

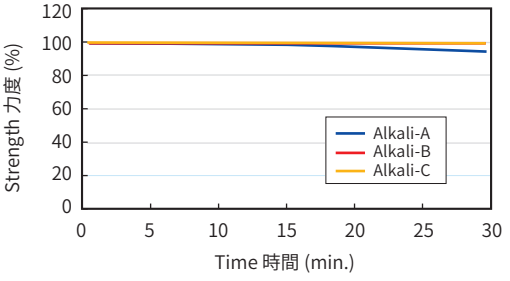

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

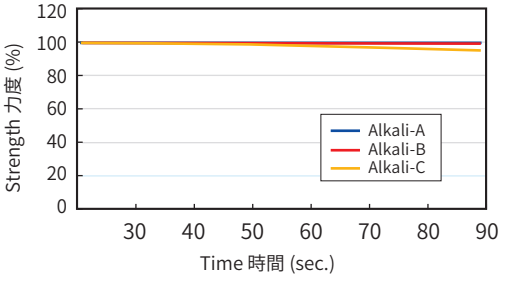

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

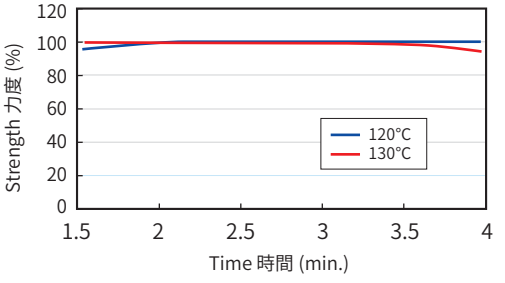

Everzol Rubine ED

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4	5	5	4–5	5
	ISO C10 C		5	5	3–4	5	5	4–5	5
	ISO C10 D		5	4	3	4–5	5	5	3
	ISO C06–C1S		5	5	3–4	4–5	5	4–5	5
	ISO C06–C2S		5	5	3–4	5	5	4	5
	M&S C4A		5	5	4	5	5	4–5	5
Water 耐水		30g/l	4–5	5	4–5	4	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	4–5	3	5	5	5
Sea Water 耐海水		30g/l	4–5	5	4–5	4–5	5	5	5
Post Mercerizing 後絲光		30g/l	2–3B	–	4	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	4–5	4	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	4–5	3–4	3	3–4	3–4	4–5
	Alkali 鹼	30g/l	4–5	4–5	4	4	4–5	4–5	4–5

Dyeing Depth 染色濃度		5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦	Dry 乾	5	5	4–5	4–5
	Wet 溼	3–4	3	2–3	2–3
		Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白	Chlorinated Water (20ppm) 耐氯水	–	–	3–4	–
	Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓 Dry 乾	Immediately	–	–	2	–
	4 Hours after	–	–	4–5	–
Hot-Pressing 耐熱壓 Wet 溼	Immediately	–	–	2	–
	4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗		–	–	4–5	–
Saliva (DIN) 耐唾液		–	–	4	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色		–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	4
		10g/l	3–4	4
		30g/l	3–4	4–5
		60g/l	4	4–5
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	3–4
		10g/l	3	3–4
		30g/l	3–4	4
		60g/l	3–4	4
	Alkali 鹼	5g/l	2–3	2–3
		10g/l	3	2–3
		30g/l	3–4	3–4
		60g/l	3–4	3–4
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Blue ED–G

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	2–3
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	1–2
	Soda Ash Solution 純鹼	2
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	3–4
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	1
	Alkaline 鹼性	1


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

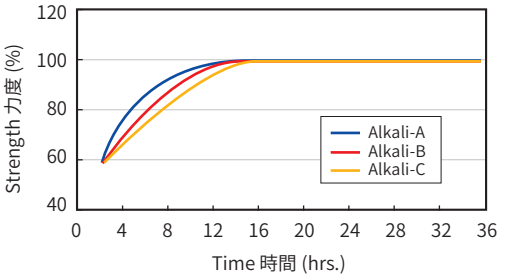


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

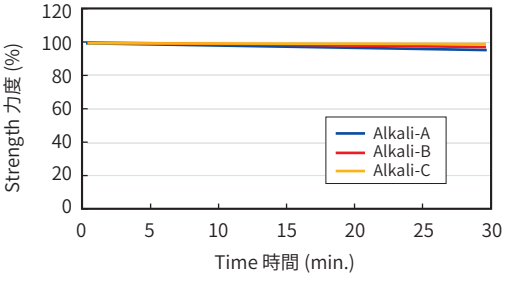


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

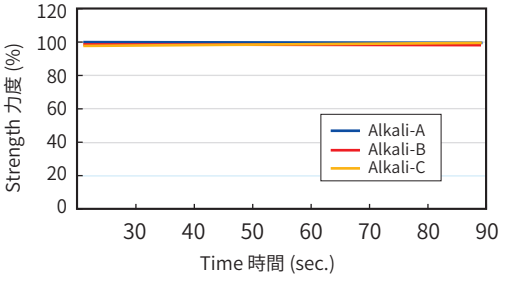

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

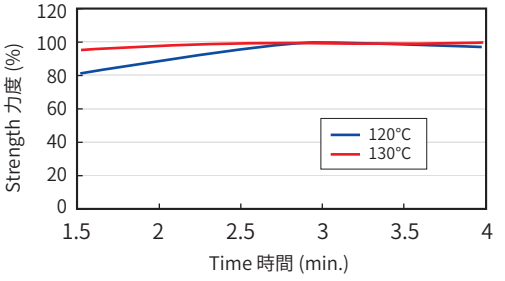

Everzol Blue ED–G

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	5
	ISO C10 D		5	5	4	5	5	5	4–5
	ISO C06–C1S		5	5	4	5	5	5	5
	ISO C06–C2S		5	5	4	5	5	5	5
	M&S C4A		5	5	4–5	5	5	5	5
Water 耐水		30g/l	5	5	4–5	4–5	5	5	5
Hot Water 耐熱水		30g/l	5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	5	5	4–5	5	5	5	5
Post Mercerizing 後絲光		30g/l	3G(B)	–	4–5	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	3	2	5	5	4
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	4–5	4–5	5	5	5
	Alkali 鹼	30g/l	5	5	4–5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	4–5
		Wet 溼	4	3–4	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	1	–
		Peroxide Bleaching 雙氧水漂白	–	–	3–4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	3–4	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	3–4	–
		4 Hours after	–	–	5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	5	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	2	3	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4	4–5
		10g/l	4–5	5–6
		30g/l	4–5	6
		60g/l	4–5	6
Perspiration Light 耐汗日光	Acid 酸	5g/l	4	4
		10g/l	4	4–5
		30g/l	4–5	5
		60g/l	4–5	5–6
	Alkali 鹼	5g/l	4–5	4
		10g/l	4–5	4–5
		30g/l	4–5	5
		60g/l	4–5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Blue L–ED

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4
	Cu^{2+} 銅離子	1–2
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	1–2
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	2–3


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

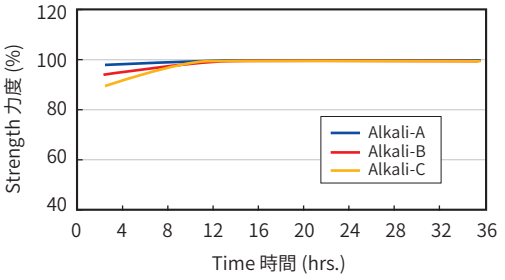


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

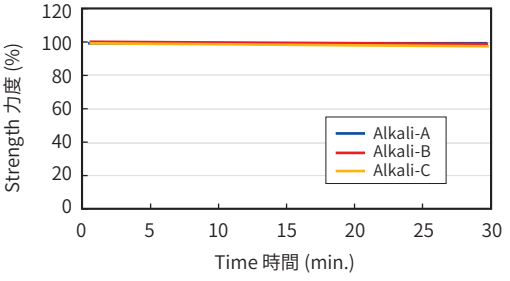


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

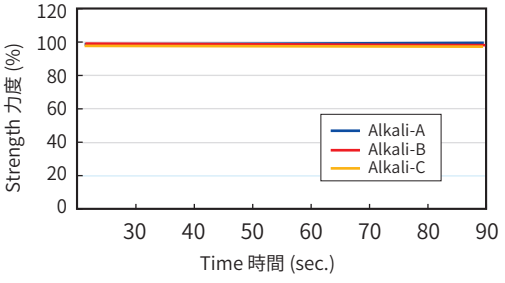

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

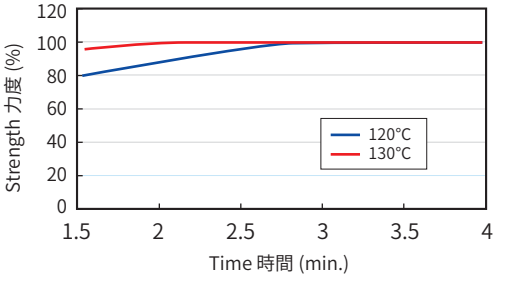

Everzol Blue L–ED

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	4–5	5	5	5	5
	ISO C10 C		4–5	5	4	5	5	5	5
	ISO C10 D		4–5	5	3	5	5	5	2–3
	ISO C06–C1S		4–5	5	4	5	5	5	5
	ISO C06–C2S		4–5	5	4	5	5	5	5
	M&S C4A		4–5	5	4–5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	4–5	4–5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	4R	–	4	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	5	4–5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	4–5	4–5	4–5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	4–5
		Wet 溼	4	3–4	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3	–
		Peroxide Bleaching 雙氧水漂白	–	–	2	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	4
		10g/l	3–4	4–5
		30g/l	4	5
		60g/l	4–5	6
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	3–4
		10g/l	3	4
		30g/l	3–4	4–5
		60g/l	4	5
	Alkali 鹼	5g/l	2–3	3
		10g/l	3	3–4
		30g/l	3–4	4
		60g/l	4–5	4–5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Blue ED

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4
	Cu^{2+} 銅離子	4
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	2–3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary Ammonium Salt 四級胺鹽	3–4
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	2
	Alkaline 鹼性	2


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

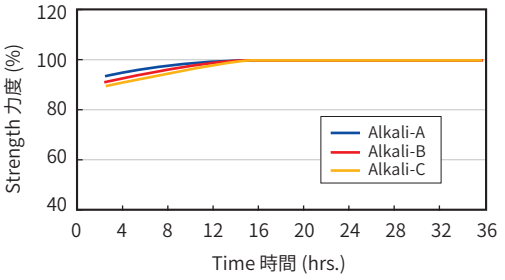


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

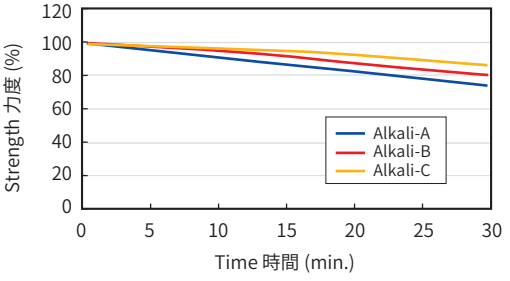


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

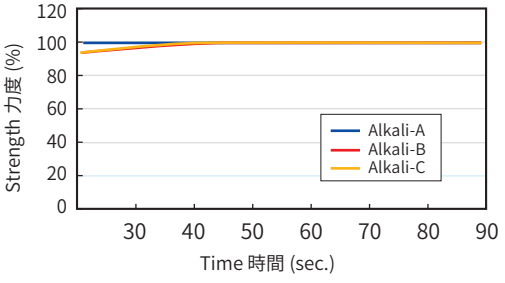

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

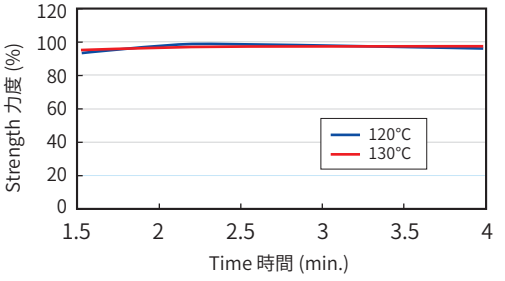

Everzol Blue ED

Fastness Before Fixing Treatment 固色前牢度表

Evaluation 評級 / Fastness 牢度		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4–5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	4–5
	ISO C10 D		5	4–5	3–4	3–4	5	5	3
	ISO C06–C1S		5	5	4–5	5	5	5	4–5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	4	5	5	5
Hot Water 耐熱水		30g/l	5	5	5	4–5	5	5	5
Sea Water 耐海水		30g/l	4	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	2–3	–	4–5	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	4	3–4	5	5	3–4
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	4–5	4	5	5	5
	Alkali 鹼	30g/l	4–5	5	4–5	4–5	5	5	5

Dyeing Depth 染色濃度		5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦	Dry 乾	5	5	4–5	4–5
	Wet 溼	4	3–4	2–3	2–3
		Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白	Chlorinated Water (20ppm) 耐氯水	–	–	4	–
	Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓 Dry 乾	Immediately	–	–	4–5	–
	4 Hours after	–	–	4–5	–
Hot-Pressing 耐熱壓 Wet 溼	Immediately	–	–	4	–
	4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗		–	–	4–5	–
Saliva (DIN) 耐唾液		–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色		–	4–5	5	–

Light Fastness 日光堅牢度表

Evaluation 評級 / Fastness 牢度		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3–4	4
		10g/l	4	4–5
		30g/l	4–5	5
		60g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	3–4
		10g/l	3	4
		30g/l	3–4	5
		60g/l	4	5
	Alkali 鹼	5g/l	2–3	3
		10g/l	3	3–4
		30g/l	3–4	4
		60g/l	4	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	5

Everlight Chemical

Everzol Navy ED

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	150
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3–4
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3–4
	Alkaline 鹼性	3–4


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

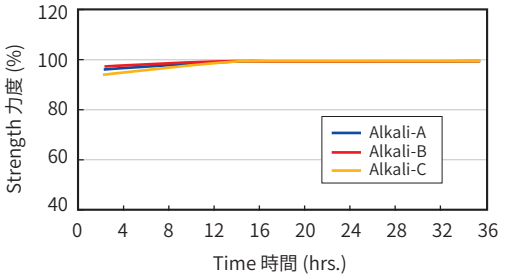


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

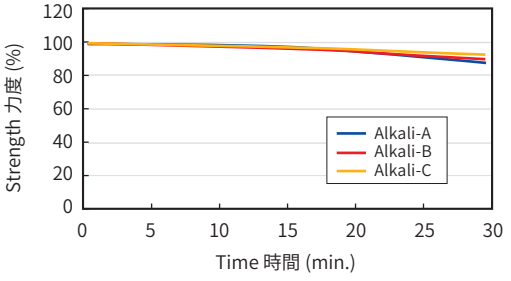


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

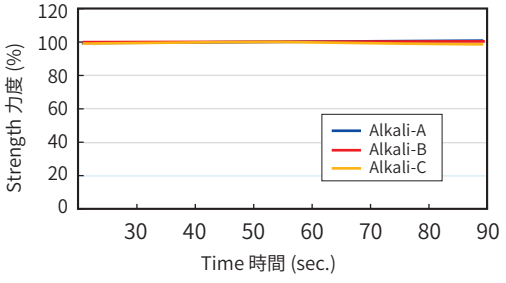

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

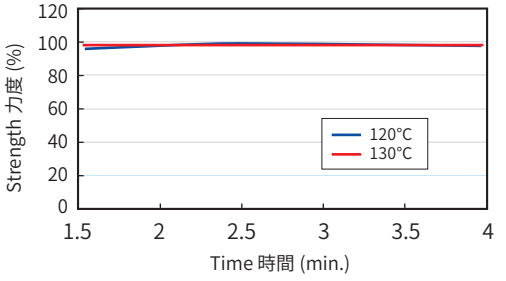

Everzol Navy ED

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	5
	ISO C10 D		5	5	4	5	5	5	3–4
	ISO C06–C1S		5	5	4–5	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	2–3	–	4	–			
Acid Hydrolysis 酸水解		30g/l	5	5	4–5	4	5	5	4
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	4–5	5	5	5

Dyeing Depth 染色濃度			10g/l	30g/l	60g/l	80g/l
Rubbing 耐磨擦		Dry 乾	5	5	4–5	4–5
		Wet 溼	3–4	3	2–3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3–4	–
		Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	2–3	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		10g/l	3	4–5
		30g/l	4	5
		60g/l	4–5	5–6
		80g/l	5	5–6
Perspiration Light 耐汗日光	Acid 酸	10g/l	2	3–4
		30g/l	3	4
		60g/l	4	5
		80g/l	4	5
	Alkali 鹼	10g/l	2–3	3
		30g/l	3–4	4
		60g/l	4	4–5
		80g/l	4	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		60g/l	–	2–3

Everlight Chemical

Everzol Black ED

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	150
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	80
	Alkali 鹼劑 A + 100g/l Urea 尿素	80
	Alkali 鹼劑 B	80
	Alkali 鹼劑 B + 100g/l Urea 尿素	80
	Alkali 鹼劑 C	80
	Alkali 鹼劑 C + 100g/l Urea 尿素	80
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	2–3
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4–5


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 60g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

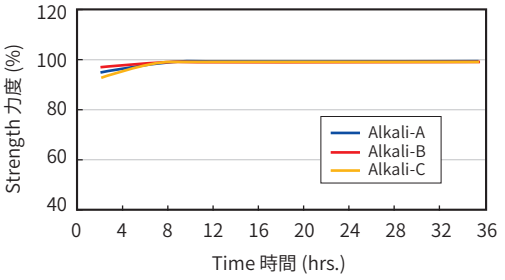


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

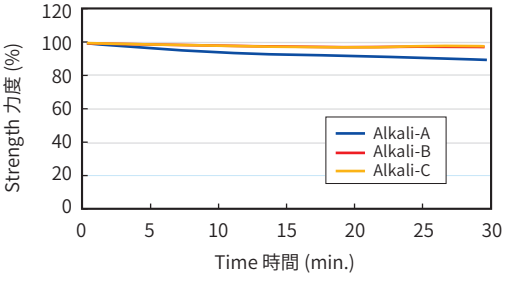


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

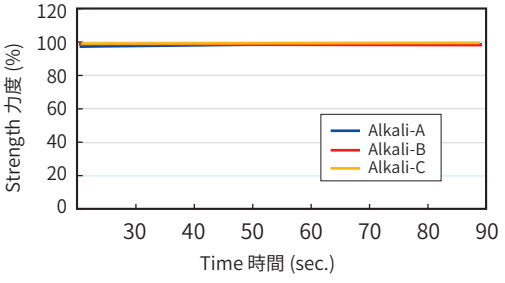

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

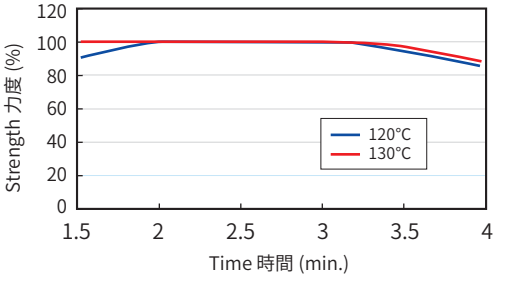

Everzol Black ED

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	60g/l	5	5	4–5	4–5	5	5	4
	ISO C10 C		5	5	4–5	5	5	5	5
	ISO C10 D		5	4–5	3–4	3	5	5	2–3
	ISO C06–C1S		5	5	4	4	5	5	4
	ISO C06–C2S		5	5	4–5	4–5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		60g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		60g/l	5	5	4–5	5	5	5	5
Sea Water 耐海水		60g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		60g/l	3R	–	4–5	–			
Acid Hydrolysis 酸水解		60g/l	4	5	5	4	5	5	4–5
Perspiration 耐汗	Acid 酸	60g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	60g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度		10g/l	30g/l	60g/l	80g/l
Rubbing 耐磨擦	Dry 乾	5	5	4–5	4–5
	Wet 溼	3–4	3	2–3	2–3
		Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白	Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
	Peroxide Bleaching 雙氧水漂白	–	–	5	–
Hot-Pressing 耐熱壓 Dry 乾	Immediately	–	–	4	–
	4 Hours after	–	–	4–5	–
Hot-Pressing 耐熱壓 Wet 溼	Immediately	–	–	4	–
	4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗		–	–	4–5	–
Saliva (DIN) 耐唾液		–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色		–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		10g/l	3	4–5
		30g/l	4	5
		60g/l	4–5	5–6
		80g/l	4–5	6
Perspiration Light 耐汗日光	Acid 酸	10g/l	1	3
		30g/l	2	4
		60g/l	3–4	5
		80g/l	4–5	5–6
	Alkali 鹼	10g/l	1–2	2
		30g/l	2–3	3–4
		60g/l	4	4–5
		80g/l	4–5	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		60g/l	–	>4–5

Everlight Chemical

Everzol Black ED–G

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	150
	50°C water 水 + 50g/l Salt 鹽	150
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4
	Cu^{2+} 銅離子	2–3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	5
	Acetic Acid 醋酸	5
Alkali Spotting 鹼滴	Ammonia Water 氨水	3–4
	Soda Ash Solution 純鹼	1–2
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	3–4
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	4


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 60g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

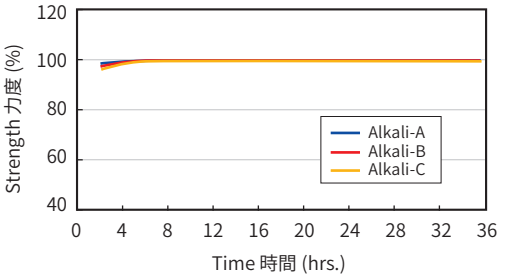


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

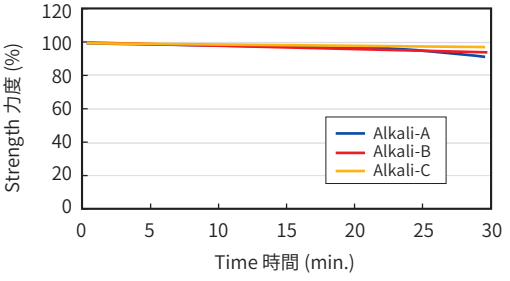


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

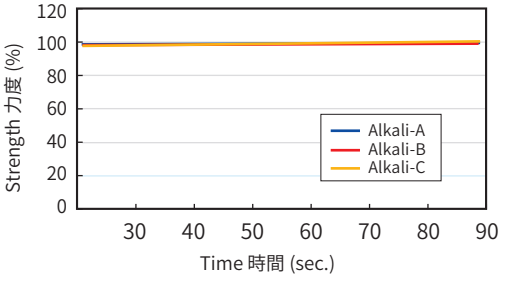

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

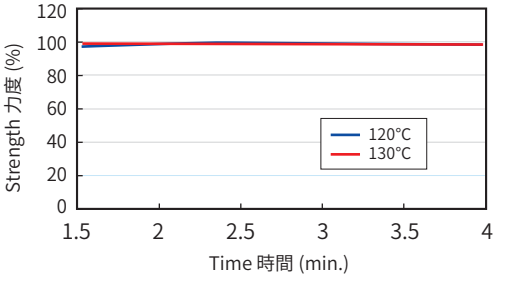

Everzol Black ED–G

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	60g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		5	5	3–4	5	5	5	3–4
	ISO C06–C1S		5	5	5	5	5	5	5
	ISO C06–C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		60g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		60g/l	4–5	5	5	4–5	5	5	5
Sea Water 耐海水		60g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		60g/l	3–4R	–	3–4	–			
Acid Hydrolysis 酸水解		60g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	60g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	60g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			10g/l	30g/l	60g/l	80g/l
Rubbing 耐磨擦		Dry 乾	5	4–5	4–5	4–5
		Wet 溼	3–4	3	2–3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3–4	–
		Peroxide Bleaching 雙氧水漂白	–	–	5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	3–4	–
		4 Hours after	–	–	4	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		10g/l	2	4
		30g/l	3	5
		60g/l	4	5–6
		80g/l	4–5	6
Perspiration Light 耐汗日光	Acid 酸	10g/l	1–2	3–4
		30g/l	2–3	4–5
		60g/l	4	5–6
		80g/l	4–5	5–6
	Alkali 鹼	10g/l	1–2	3
		30g/l	3	4–5
		60g/l	4	5–6
		80g/l	4–5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		60g/l	–	5

Everlight Chemical

Everzol Black ED–R

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4
	Cu^{2+} 銅離子	1
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	2–3
	Soda Ash Solution 純鹼	1
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	2–3
Discharge Ability 拔染性	Neutral 中性	3–4
	Alkaline 鹼性	4–5


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 60g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

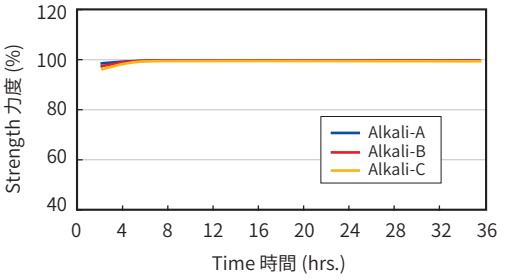


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

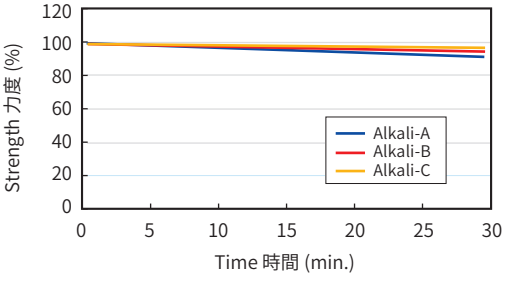


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

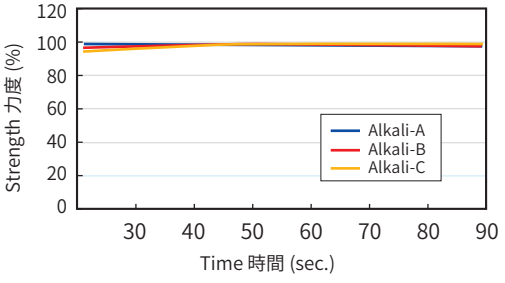

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

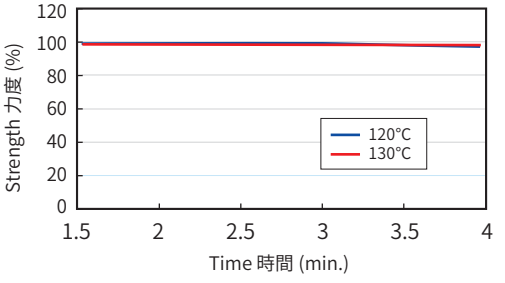

Everzol Black ED–R

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	60g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	5	5	5	5	5
	ISO C10 D		5	5	3–4	4–5	5	5	3–4
	ISO C06–C1S		5	5	5	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		60g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		60g/l	4–5	5	4–5	3–4	4–5	5	5
Sea Water 耐海水		60g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		60g/l	3–4R	–	3–4	–			
Acid Hydrolysis 酸水解		60g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	60g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	60g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			10g/l	30g/l	60g/l	80g/l
Rubbing 耐磨擦		Dry 乾	5	5	4–5	4–5
		Wet 溼	3–4	3	2–3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		10g/l	2–3	4
		30g/l	3–4	5
		60g/l	4	5–6
		80g/l	4–5	6
Perspiration Light 耐汗日光	Acid 酸	10g/l	2–3	4
		30g/l	4	5–6
		60g/l	4–5	6
		80g/l	4–5	6
	Alkali 鹼	10g/l	2–3	3
		30g/l	3–4	4
		60g/l	4–5	5–6
		80g/l	4–5	6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		60g/l	–	4–5

Everlight Chemical

Everzol Black EDN

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	90
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	G
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	3–4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4
	Alkaline 鹼性	4


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 60g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

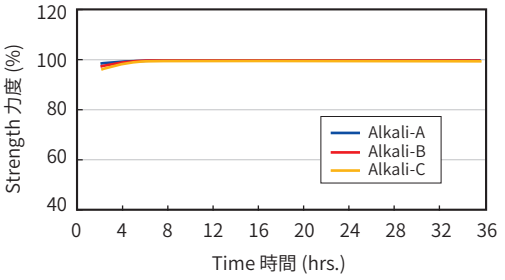


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

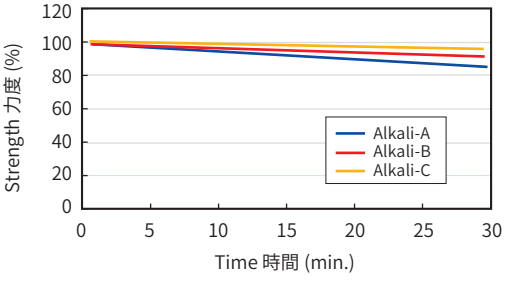


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

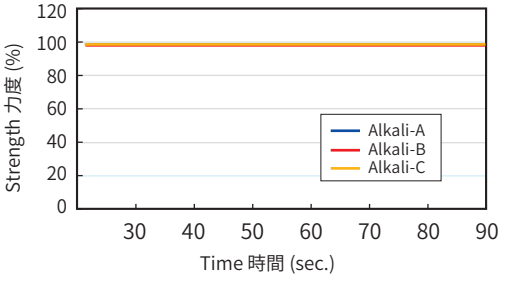

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

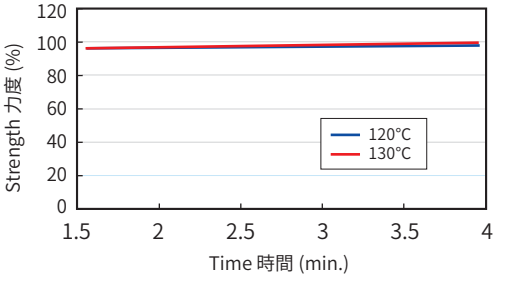

Everzol Black EDN

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	60g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	4–5
	ISO C10 D		5	5	4	5	5	5	4
	ISO C06–C1S		5	5	4–5	5	5	4–5	4
	ISO C06–C2S		4–5	5	4–5	5	5	4–5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		60g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		60g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		60g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		60g/l	4–5	–	2–3	–			
Acid Hydrolysis 酸水解		60g/l	4–5	5	4–5	4	5	5	5
Perspiration 耐汗	Acid 酸	60g/l	4–5	5	4–5	4–5	5	5	5
	Alkali 鹼	60g/l	4–5	5	4–5	4–5	5	5	5

Dyeing Depth 染色濃度			10g/l	30g/l	60g/l	80g/l
Rubbing 耐磨擦		Dry 乾	4–5	4–5	4	4
		Wet 溼	3–4	3	2	2
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		10g/l	3–4	4
		30g/l	3–4	4–5
		60g/l	4	5–6
		80g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	10g/l	1–2	3–4
		30g/l	3	4–5
		60g/l	4	5–6
		80g/l	4–5	5–6
	Alkali 鹼	10g/l	1–2	2
		30g/l	3–4	3–4
		60g/l	4–5	4–5
		80g/l	4–5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		60g/l	–	5

Everlight Chemical

Everzol Black ED–3R

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4
	Cu^{2+} 銅離子	1
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	2


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 60g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

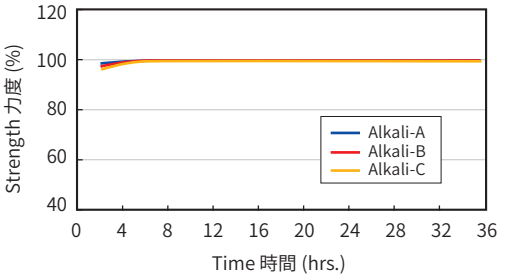


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

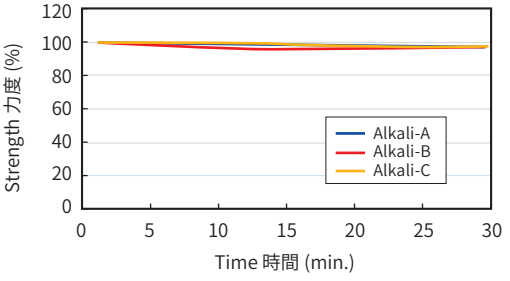


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

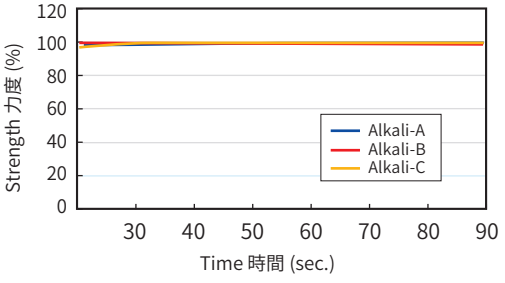

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

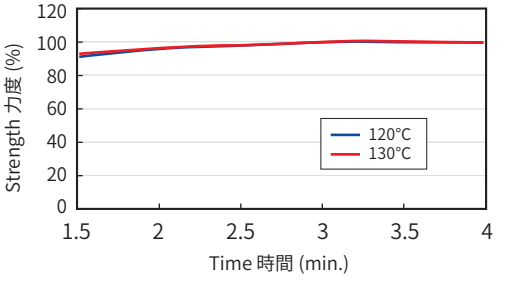

Everzol Black ED–3R

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	60g/l	5	5	4–5	5	5	5	5
	ISO C10 C		5	5	4	4–5	5	5	4
	ISO C10 D		4–5	4–5	2–3	4	5	4–5	2
	ISO C06–C1S		4–5	5	4	4–5	5	4–5	4
	ISO C06–C2S		4–5	5	4	4–5	5	4–5	4
	M&S C4A		4–5	5	4–5	4–5	5	5	4–5
Water 耐水		60g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		60g/l	5	5	5	5	5	5	4–5
Sea Water 耐海水		60g/l	5	5	5	5	5	5	4–5
Post Mercerizing 後絲光		60g/l	4–5	–	3	–			
Acid Hydrolysis 酸水解		60g/l	5	5	4	3–4	4–5	5	4
Perspiration 耐汗	Acid 酸	60g/l	4–5	5	4–5	4	4–5	5	5
	Alkali 鹼	60g/l	5	5	4–5	4–5	4–5	5	5

Dyeing Depth 染色濃度			10g/l	30g/l	60g/l	80g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4–5	3–4	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4	–
		Peroxide Bleaching 雙氧水漂白	3–4	4	4–5	5
Hot-Pressing 耐熱壓	Dry 乾	Immediately	4–5	4	4	4
		4 Hours after	5	5	5	5
	Wet 溼	Immediately	4–5	4	4	4
		4 Hours after	2–3	3	3–4	4–5
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	3–4	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		10g/l	3	3–4
		30g/l	4–5	4–5
		60g/l	5	5
		80g/l	5	5
Perspiration Light 耐汗日光	Acid 酸	10g/l	2	2–3
		30g/l	3–4	3–4
		60g/l	4–5	4–5
		80g/l	5	5
	Alkali 鹼	10g/l	2–3	2–3
		30g/l	4	3–4
		60g/l	4–5	4–5
		80g/l	5	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		60g/l	–	5

Everlight Chemical

Everzol Amber ERC

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	3–4
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	5
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	5
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4–5
	Alkaline 鹼性	2–3


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

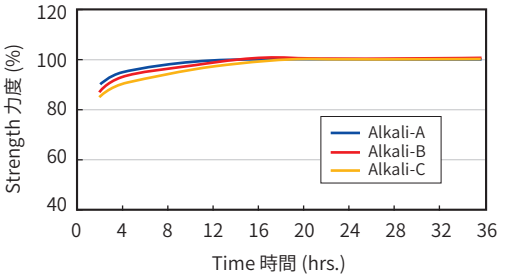


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

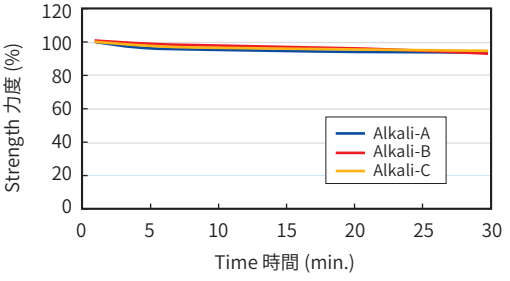


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

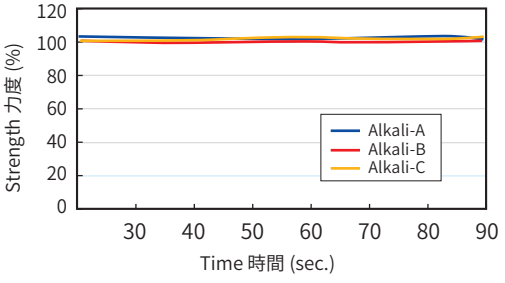

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

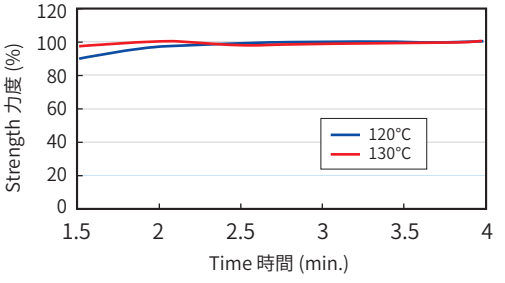

Everzol Amber ERC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4–5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	5
	ISO C10 D		5	5	3–4	4-5	5	5	3
	ISO C06–C1S		5	5	4–5	5	4-5	5	5
	ISO C06–C2S		5	5	4–5	5	4-5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	4–5	–	4–5	-			
Acid Hydrolysis 酸水解		30g/l	5	5	4–5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	5	5	4–5	5	5	5	5
	Alkali 鹼	30g/l	5	5	4–5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	4–5
		Wet 溼	4	4	3–4	3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	4	4	4	4
		Peroxide Bleaching 雙氧水漂白	–	–	5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4	–
		4 Hours after	–	–	4	–
Multi-Laundering (M&S C10A) 耐多次水洗			4–5	4–5	4–5	4
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	4–5	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4–5	5–6
		10g/l	5	5–6
		30g/l	5	5–6
		60g/l	5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	4–5	5–6
		10g/l	5	5–6
		30g/l	5	5–6
		60g/l	5	5–6
	Alkali 鹼	5g/l	4–5	5
		10g/l	5	5–6
		30g/l	5	5–6
		60g/l	5	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	5
		30g/l	–	5

Everlight Chemical

Everzol Yellow ERC

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	R
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	5
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	5
	Glyoxal 乙二醛	5
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	2–3

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25° C)

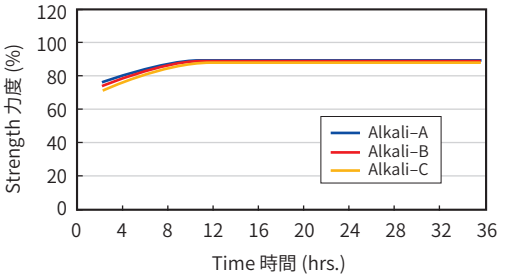


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

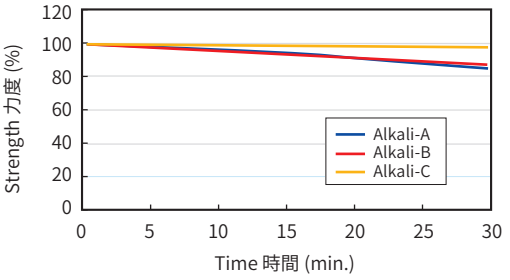

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

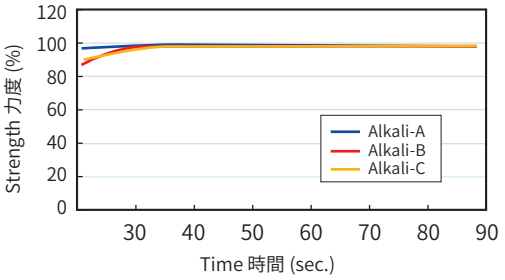

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

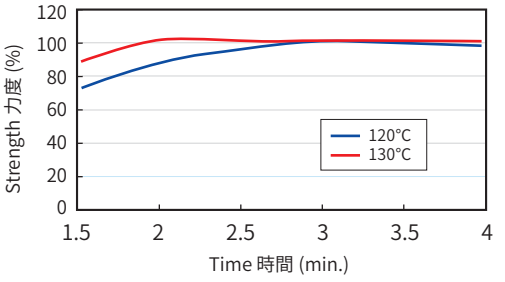

Everzol Yellow ERC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4–5	5	5	5	5
	ISO C10 C		5	5	4	5	5	5	5
	ISO C10 D		5	5	4–5	5	5	5	4–5
	ISO C06–C1S		5	5	4–5	5	5	5	5
	ISO C06–C2S		5	5	4–5	5	5	5	5
	M&S C4A		5	5	4–5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4	5	4–5	5	5	5	5
Post Mercerizing 後絲光		30g/l	4	–	4–5	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	4–5	4	5	5	4–5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	4–5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	4–5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	4–5	4–5
		Wet 溼	4	4–5	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2–3	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	5	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4–5	5–6
		10g/l	4–5	5–6
		30g/l	4–5	5–6
		60g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	4	5–6
		10g/l	4–5	5–6
		30g/l	4–5	6
		60g/l	4–5	6
	Alkali 鹼	5g/l	4–5	5
		10g/l	4–5	5–6
		30g/l	4–5	5–6
		60g/l	4–5	6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	5

Everlight Chemical

Everzol Light Red ERC

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	2–3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	4–5
	Alkaline 鹼性	4–5


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 10g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

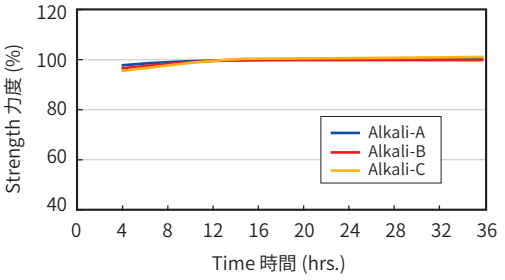


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

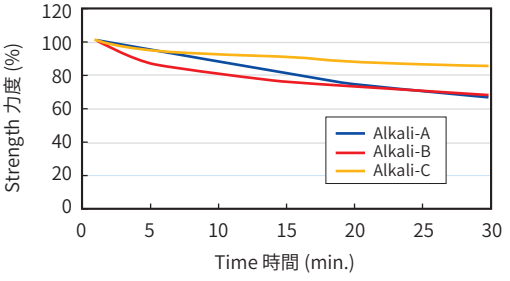


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

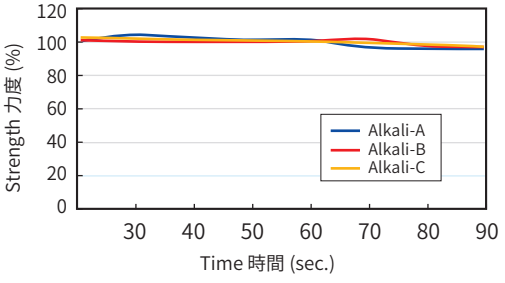

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

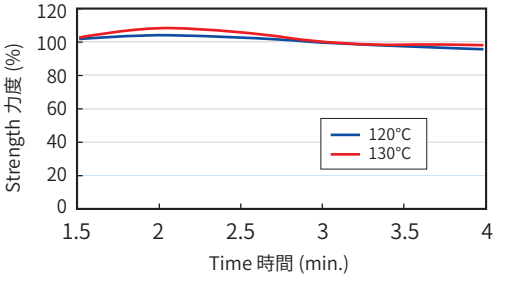

Everzol Light Red ERC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	10g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	5	5	5	5	5
	ISO C10 D		4–5	5	4–5	5	5	5	4
	ISO C06–C1S		4–5	5	5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		10g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		10g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		10g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		10g/l	3–4	–	4	–			
Acid Hydrolysis 酸水解		10g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	10g/l	5	5	5	5	5	5	5
	Alkali 鹼	10g/l	5	5	5	5	5	5	5

Dyeing Depth 染色濃度			1g/l	5g/l	10g/l	30g/l
Rubbing 耐磨擦		Dry 乾	–	–	4–5	–
		Wet 溼	–	–	2	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2–3	–
		Peroxide Bleaching 雙氧水漂白	–	–	3–4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	2–3	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	2–3	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		1g/l	4	4–5
		5g/l	4	5
		10g/l	4–5	5–6
		30g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	1g/l	3	4–5
		5g/l	3–4	4–5
		10g/l	3–4	5
		30g/l	3–4	5
	Alkali 鹼	1g/l	3	4
		5g/l	3–4	4
		10g/l	3–4	4–5
		30g/l	3–4	4–5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	4–5

Everlight Chemical

Everzol Cardinal ERC

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	Y
	TL84 Lamp	Y
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3–4
	Alkaline 鹼性	3


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 30g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

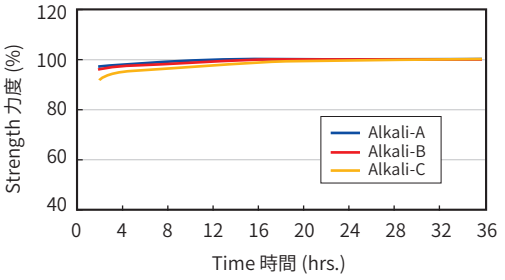


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

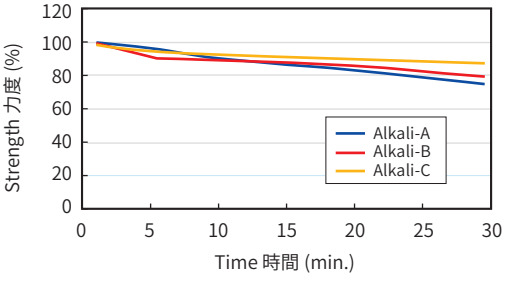


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

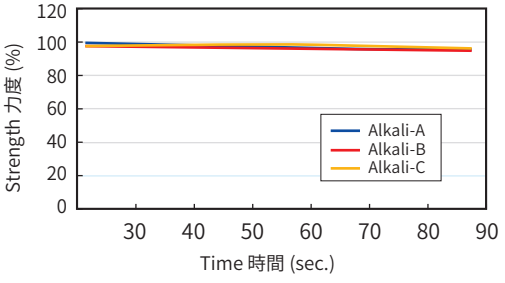

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

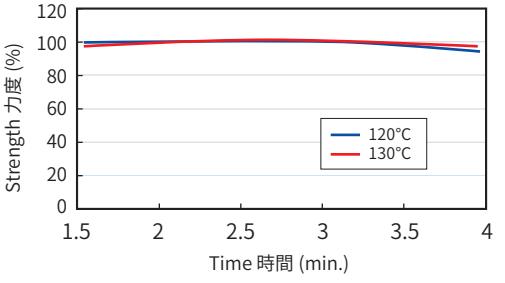

Everzol Cardinal ERC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	4–5	5	5	4–5	5
	ISO C10 C		5	5	4	5	5	4–5	4
	ISO C10 D		4	5	2–3	5	5	4–5	3
	ISO C06–C1S		4–5	5	4	5	5	5	4
	ISO C06–C2S		4–5	5	4	5	5	5	5
	M&S C4A		4–5	5	4–5	5	5	5	5
Water 耐水		30g/l	5	5	4	4–5	5	5	5
Hot Water 耐熱水		30g/l	5	5	4–5	5	5	5	4–5
Sea Water 耐海水		30g/l	5	5	4	4–5	5	5	5
Post Mercerizing 後絲光		30g/l	3–4	–	2	–			
Acid Hydrolysis 酸水解		30g/l	5	5	4	3	4–5	4–5	3–4
Perspiration 耐汗	Acid 酸	30g/l	5	5	4	5	5	4–5	4–5
	Alkali 鹼	30g/l	5	5	4	5	5	4–5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	4–5	4	3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4	–
		Peroxide Bleaching 雙氧水漂白	4–5	4–5	4	4
Hot-Pressing 耐熱壓	Dry 乾	Immediately	4	4–5	4–5	4–5
		4 Hours after	5	5	5	5
	Wet 溼	Immediately	4	3–4	3–4	3
		4 Hours after	5	5	5	5
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	4	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	5	5–6
		10g/l	5	6
		30g/l	5	6
		60g/l	5	6
Perspiration Light 耐汗日光	Acid 酸	5g/l	4	4–5
		10g/l	4–5	4–5
		30g/l	5	4–5
		60g/l	5	5
	Alkali 鹼	5g/l	4–5	4–5
		10g/l	5	4–5
		30g/l	5	4–5
		60g/l	5	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Bordeaux ERC

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	60
	Alkali 鹼劑 A + 100g/l Urea 尿素	80
	Alkali 鹼劑 B	50
	Alkali 鹼劑 B + 100g/l Urea 尿素	80
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	△
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R(Y)
	TL84 Lamp	G(Y)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	3–4
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	4
	Soda Ash Solution 純鹼	1–2
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3–4
	Alkaline 鹼性	4–5

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25° C)

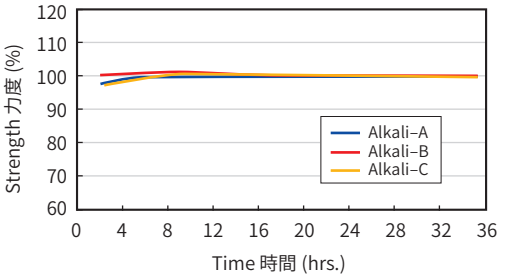


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

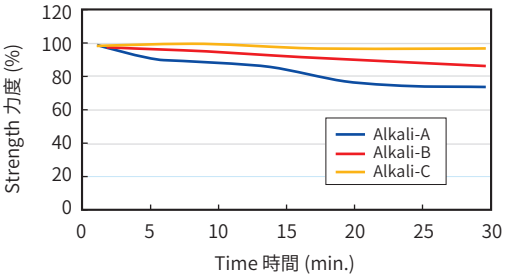

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

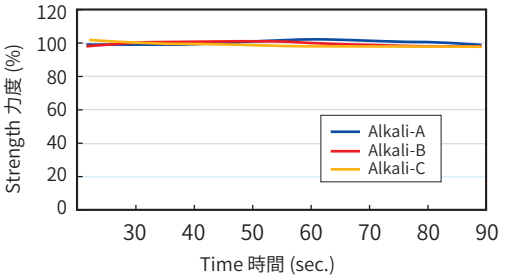

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

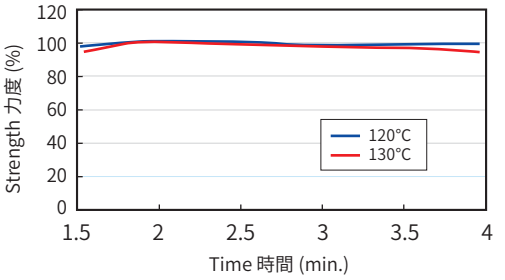

Everzol Bordeaux ERC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	5	5	5	5	5
	ISO C10 D		4–5	5	4–5	5	5	5	5
	ISO C06–C1S		4–5	5	5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	2–3	–	3	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	–	–	4–5	–
		Wet 溼	–	–	2	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	2–3	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	2–3	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	4–5
		10g/l	3–4	5
		30g/l	4	5–6
		60g/l	4	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	2–3	4
		10g/l	3	4–5
		30g/l	3–4	5
		60g/l	4	5–6
	Alkali 鹼	5g/l	2–3	4
		10g/l	3	4–5
		30g/l	3–4	5
		60g/l	4	5–6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Blue ERC

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	G(B)
	TL84 Lamp	G(B)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	1–2
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	4–5
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4
Discharge Ability 拔染性	Neutral 中性	2–3
	Alkaline 鹼性	3

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25° C)

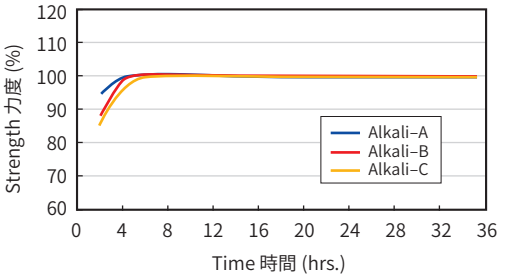


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

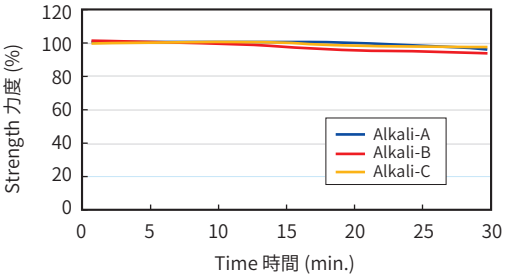

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

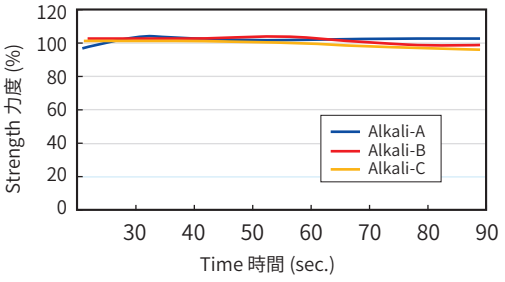

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

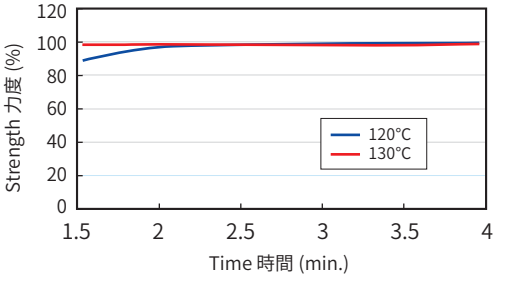

Everzol Blue ERC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	4–5	5	5	5	5
	ISO C10 D		4–5	5	4–5	5	5	5	3
	ISO C06–C1S		4–5	5	4–5	5	5	5	5
	ISO C06–C2S		4–5	5	4–5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	2–3	–	3–4	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	–	–	4–5	–
		Wet 溼	–	–	2–3	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	3	–
		Peroxide Bleaching 雙氧水漂白	–	–	3–4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	3	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	4–5	5–6
		10g/l	4–5	5–6
		30g/l	4–5	6
		60g/l	4–5	>6
Perspiration Light 耐汗日光	Acid 酸	5g/l	4	5
		10g/l	4	5–6
		30g/l	4–5	6
		60g/l	4–5	6
	Alkali 鹼	5g/l	4	4–5
		10g/l	4	4–5
		30g/l	4–5	5
		60g/l	4–5	6
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	–
		30g/l	–	4–5

Everlight Chemical

Everzol Dark Blue ERC

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	G(B)
	TL84 Lamp	B
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	2–3
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4
	Glyoxal 乙二醛	4
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	3–4

X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 30g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25° C)

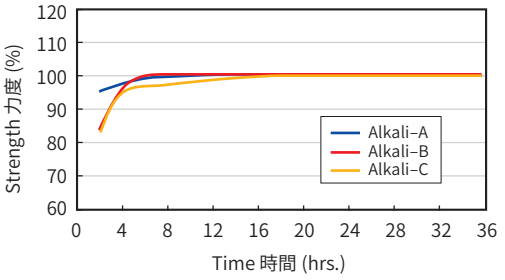


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

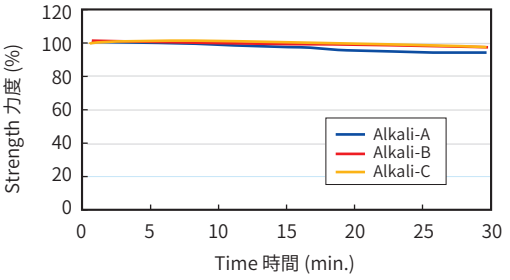

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

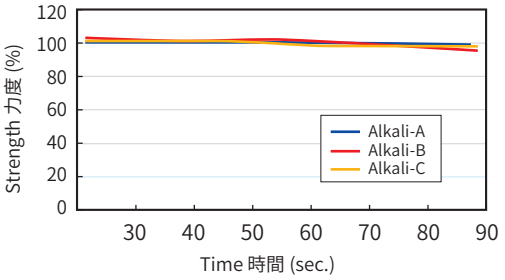

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

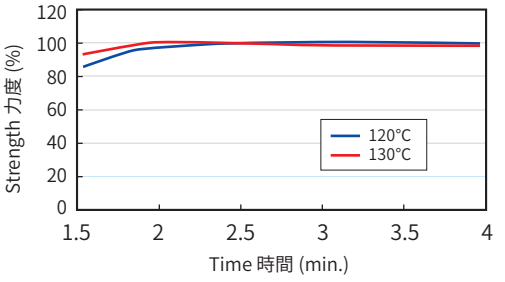

Everzol Dark Blue ERC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	5	5	5	5	5
	ISO C10 D		4–5	5	4–5	5	5	5	4–5
	ISO C06–C1S		4–5	5	4–5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		30g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	3	–	3–4	–			
Acid Hydrolysis 酸水解		30g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	5	5	5	5
		Wet 溼	3–4	4–5	2–3	2–3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	2–3	–
		Peroxide Bleaching 雙氧水漂白	–	–	4	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3–4	4
		10g/l	4	4–5
		30g/l	4–5	5
		60g/l	5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	3	4
		10g/l	3–4	4–5
		30g/l	4	5
		60g/l	4–5	5–6
	Alkali 鹼	5g/l	3	3–4
		10g/l	3–4	4
		30g/l	4	4–5
		60g/l	4–5	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		30g/l	–	5

Everlight Chemical

Everzol Marine ERC

Dyeing Properties 染料特性


Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	△
	Reduction-Oxidization 還原處理後再氧化處理	△
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	G(Y)
	TL84 Lamp	G(Y)
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	2–3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4
	Acetic Acid 醋酸	4
Alkali Spotting 鹼滴	Ammonia Water 氨水	4
	Soda Ash Solution 純鹼	3–4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	–
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	4

X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 30g/l depth.


Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花			✓


Dependency of Batching Time 捲置時間依存性 (CPB)
(Dyeing temperature at 25° C)

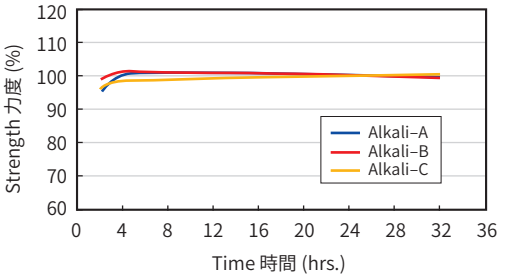


Stability of Padding Liquor 染液安定性 (CPB)
(Dyeing temperature at 25°C)

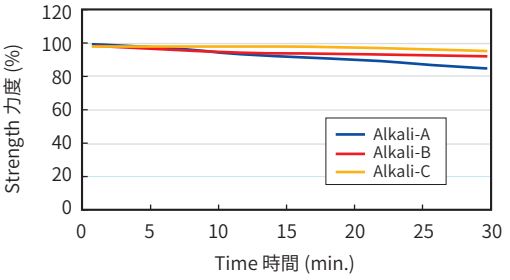

Dependency of Steaming Time 蒸處時間依存性 (PD/PS)
(Saturated steam at 102°C)

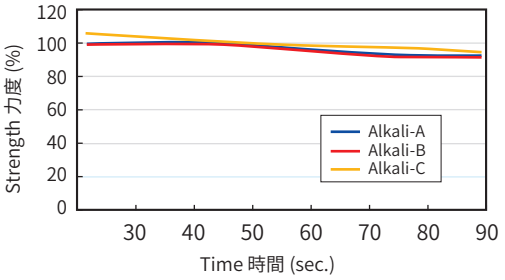

Dependency of Fixation Time 固著時間依存性 (Emoistfix)
(Substrate:130x70/32x20 1/3 twill cotton)

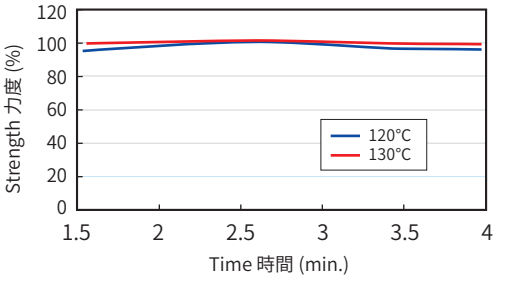

Everzol Marine ERC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	30g/l	5	5	5	5	5	5	5
	ISO C10 C		5	5	4–5	5	5	5	4–5
	ISO C10 D		4–5	5	5	5	5	4–5	3–4
	ISO C06–C1S		5	5	5	5	5	5	5
	ISO C06–C2S		5	5	5	5	5	5	5
	M&S C4A		5	5	5	5	5	5	5
Water 耐水		30g/l	5	5	5	5	5	5	5
Hot Water 耐熱水		30g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		30g/l	5	5	5	5	5	5	5
Post Mercerizing 後絲光		30g/l	3–4	–	2	–			
Acid Hydrolysis 酸水解		30g/l	5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	30g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	30g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			5g/l	10g/l	30g/l	60g/l
Rubbing 耐磨擦		Dry 乾	4–5	4–5	4–5	4
		Wet 溼	4	3–4	2–3	1–2
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	3–4	–	4	4–5
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	3–4	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	3	–
		4 Hours after	–	–	4	–
Multi-Laundering (M&S C10A) 耐多次水洗			4	4	4–5	4–5
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		5g/l	3	3
		10g/l	3–4	3–4
		30g/l	4	5
		60g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	5g/l	2	2–3
		10g/l	2–3	3
		30g/l	3–4	4
		60g/l	4–5	5
	Alkali 鹼	5g/l	2–3	2–3
		10g/l	3	3
		30g/l	4	4
		60g/l	4–5	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4
		30g/l	–	4–5

Everlight Chemical

Everzol Black ERC

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	X
	Reduction 還原處理	X
	Reduction-Oxidization 還原處理後再氧化處理	X
	Oxidization-Reduction 氧化處理後再還原處理	X
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	G
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	5
	Cu^{2+} 銅離子	3
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	4
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3–4
	Alkaline 鹼性	4–5


X: un-suitable, △ : moderate, ○ : suitable, Dyeing properties are based on 60g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

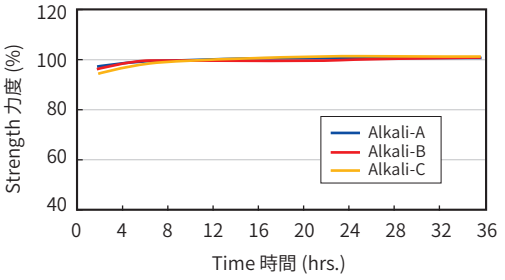


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

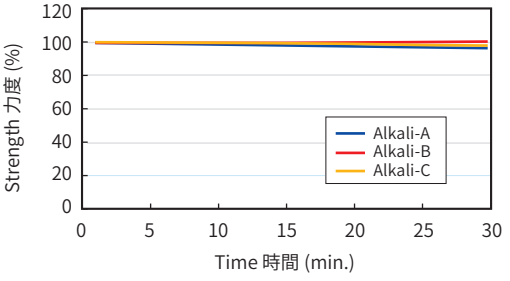


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

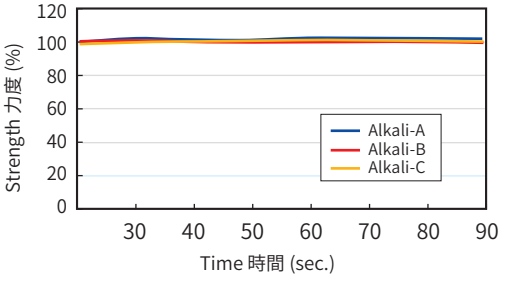

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

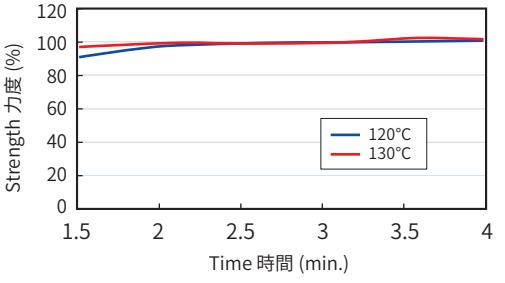

Everzol Black ERC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	60g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	4–5	5	5	5	5
	ISO C10 D		4–5	5	3	5	5	5	2–3
	ISO C06–C1S		4–5	5	4–5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		60g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		60g/l	4–5	5	4–5	5	5	5	5
Sea Water 耐海水		60g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		60g/l	4	–	4	–			
Acid Hydrolysis 酸水解		60g/l	4–5	5	4–5	4–5	5	5	5
Perspiration 耐汗	Acid 酸	60g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	60g/l	4–5	5	4–5	5	5	5	5

Dyeing Depth 染色濃度			10g/l	30g/l	60g/l	80g/l
Rubbing 耐磨擦		Dry 乾	4–5	4–5	4–5	4–5
		Wet 溼	4	3–4	3	3
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4–5	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4–5	–
Saliva (DIN) 耐唾液			–	–	4–5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	4–5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		10g/l	3	4
		30g/l	3–4	4–5
		60g/l	4	4–5
		80g/l	4–5	5
Perspiration Light 耐汗日光	Acid 酸	10g/l	2	3–4
		30g/l	3	4
		60g/l	3–4	4–5
		80g/l	4	5
	Alkali 鹼	10g/l	2–3	3
		30g/l	3–4	3–4
		60g/l	4	4–5
		80g/l	4–5	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4
		60g/l	–	4–5

Everlight Chemical

Everzol Jet Black ERC

Dyeing Properties 染料特性

Characteristics 特性		Evaluation 評級
Solubility 溶解度 (g/l)	25°C water 水	100
	50°C water 水 + 50g/l Salt 鹽	100
Solubility in Alkali 耐鹼溶解度 (g/l)	Alkali 鹼劑 A	100
	Alkali 鹼劑 A + 100g/l Urea 尿素	100
	Alkali 鹼劑 B	100
	Alkali 鹼劑 B + 100g/l Urea 尿素	100
	Alkali 鹼劑 C	100
	Alkali 鹼劑 C + 100g/l Urea 尿素	100
Stripping 脫色性	Alkali 鹼處理	△
	Reduction 還原處理	○
	Reduction-Oxidization 還原處理後再氧化處理	○
	Oxidization-Reduction 氧化處理後再還原處理	○
Color Constancy 色恆性	Tungsten Lamp 鎢絲燈	R
	TL84 Lamp	G
Metallic Ions 金屬離子	Fe^{2+} 鐵離子	4–5
	Cu^{2+} 銅離子	4–5
Acid Spotting 酸滴	Hydrochloric Acid 鹽酸	4–5
	Acetic Acid 醋酸	4–5
Alkali Spotting 鹼滴	Ammonia Water 氨水	4–5
	Soda Ash Solution 純鹼	2–3
Shade Change After Fixing Treatment 固色後變色性	Polyamine 聚胺類	4–5
	Quaternary Ammonium Salt 四級胺鹽	4–5
Resin Finishing 樹脂加工	Melamine 三聚氰胺	4–5
	Glyoxal 乙二醛	4–5
Discharge Ability 拔染性	Neutral 中性	3
	Alkaline 鹼性	4


X: un-suitable, △: moderate, ○: suitable, Dyeing properties are based on 60g/l depth.

Recommended Dyeing Process 染程推薦

		Very Good 非常好	Moderate 適用
Exhaust Dyeing Process 浸染		✓	
Pad Dyeing Process 壓染	Cold Pad-Batch (CPB)	✓	
	Pad-Dry-Chemical Pad-Steam(PD/PS)	✓	
	Pad-Dry Baking (PDB)	✓	
	Pad-Steam (PS)	✓	
	Emoistfix	✓	
Discharge Printing 拔染印花		✓	


Dependency of Batching Time 捲置時間依存性 (CPB)

(Dyeing temperature at 25°C)

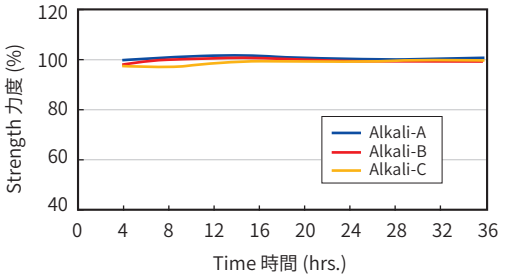


Stability of Padding Liquor 染液安定性 (CPB)

(Dyeing temperature at 25°C)

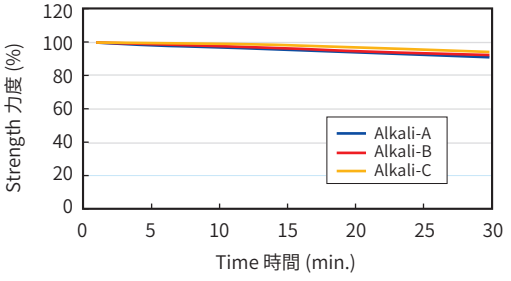


Dependency of Steaming Time 蒸處時間依存性 (PD/PS)

(Saturated steam at 102°C)

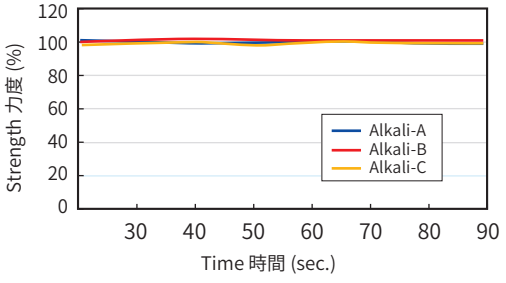

Dependency of Fixation Time 固著時間依存性 (Emoistfix)

(Substrate:130x70/32x20 1/3 twill cotton)

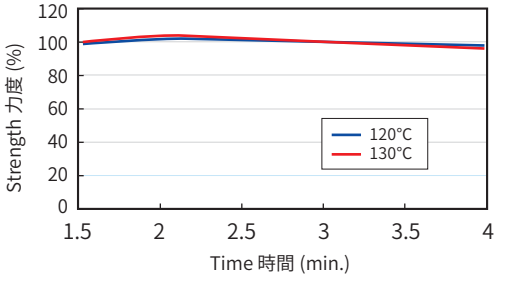

Everzol Jet Black ERC

Fastness Before Fixing Treatment 固色前牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色	Staining 污染					
				Acetate 醋酸纖維	Cotton 棉	Nylon 尼龍	Polyester 聚酯	Acrylic 壓克力	Wool 羊毛
Washing 耐水洗	ISO C10 B	60g/l	4–5	5	5	5	5	5	5
	ISO C10 C		4–5	5	4–5	5	5	5	5
	ISO C10 D		4–5	5	3	5	5	5	3
	ISO C06–C1S		4–5	5	5	5	5	5	5
	ISO C06–C2S		4–5	5	5	5	5	5	5
	M&S C4A		4–5	5	5	5	5	5	5
Water 耐水		60g/l	4–5	5	5	5	5	5	5
Hot Water 耐熱水		60g/l	4–5	5	5	5	5	5	5
Sea Water 耐海水		60g/l	4–5	5	5	5	5	5	5
Post Mercerizing 後絲光		60g/l	4	–	3	–			
Acid Hydrolysis 酸水解		60g/l	4–5	5	5	5	5	5	5
Perspiration 耐汗	Acid 酸	60g/l	4–5	5	5	5	5	5	5
	Alkali 鹼	60g/l	4–5	5	5	5	5	5	5

Dyeing Depth 染色濃度			10g/l	30g/l	60g/l	80g/l
Rubbing 耐磨擦		Dry 乾	–	–	4–5	–
		Wet 溼	–	–	2–3	–
			Color Change 變褪色	Color Change 變褪色	Color Change 變褪色	Color Change 變褪色
Bleach 耐漂白		Chlorinated Water (20ppm) 耐氯水	–	–	4	–
		Peroxide Bleaching 雙氧水漂白	–	–	4–5	–
Hot-Pressing 耐熱壓	Dry 乾	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
	Wet 溼	Immediately	–	–	4–5	–
		4 Hours after	–	–	4–5	–
Multi-Laundering (M&S C10A) 耐多次水洗			–	–	4	–
Saliva (DIN) 耐唾液			–	–	5	–
Nitrogen Oxides (NOx) 氮氧化物氣體變褪色			–	–	5	–

Light Fastness 日光堅牢度表

Fastness 牢度 \ Evaluation 評級		Dyeing Depth 染色濃度	Color Change 變褪色 20 AFU	Grade 級數 ISO Blue Scale (藍色票)
Artificial Light 耐日光 (Xenon-Arc Lamp)		10g/l	3	4
		30g/l	4	4–5
		60g/l	4–5	5
		80g/l	4–5	5–6
Perspiration Light 耐汗日光	Acid 酸	10g/l	1–2	3–4
		30g/l	2	4
		60g/l	3	4–5
		80g/l	4	5
	Alkali 鹼	10g/l	1–2	3–4
		30g/l	2–3	4
		60g/l	3–4	4–5
		80g/l	4	5
M&S C9A (Detergent Light) 擬濕日光		10g/l	–	4–5
		60g/l	–	5

Note

Note

本資料所提供的資訊與建議是以我們最大的用心完成，但不能含括所有可能的狀況。使用相關產品或搭配其他產品時，請先自行測試。本資料並不具保證及法律效用，僅供參考使用。使用者必須自行承擔所有的風險與法律責任。

臺灣永光化學工業股份有限公司－技術行銷處

Warnings: The information and recommendations presented here were completed with the utmost care, but can't be extended to cover every possible case. They are intended to serve as non–binding guidelines and must be adapted to the prevailing condition. The product whether used singly or in combination with other substances, should be carried out in lab test prior to bulk production. The user needs to assume all risk and liability no matter whatsoever results are.

Issued by Everlight Chemical Industrial Corporation
Tech. Marketing & Service Div.

Everlight Chemical