STANDARD OPERATING PROCEDURE OF Ultraviolet Light Discoloration VF-E03

Lab /SOP/ 45



1.Ultraviolet light oven with revolving pan
2.OSRAM Ultra –Vitalux or similar 300 watt UV light bulb
3.Masking tape, non transparent.
4. AATCC Chromatic Transference Scale
5. Light box : D65 light




Set the speed of the rotating table to 3 ± 1 revolution per minute.
Adjust the rotating table such that it is 250±2 mm below the bottom of the ultra light source.



Sample size:6cmX3cm,Maximum thickness of the sample is 5.0mm.
Test two (2) samples per material



Mask the first and last 2cm of the test sample with a piece of paper at least 4 layers, then fasten with tape but ensure that the tape should not touch the test sample. This will leave the center 2cm unmasked.

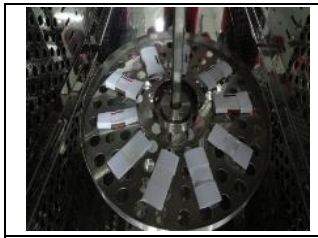

Place the test sample on a rotating table such that the closest edge is 6.0± 0.5 cm from the center of the table.



Expose the test sample to the ultraviolet ray for 12 hours or 24 hours at a temperature of 50±1°C.
Light bulb must be replaced at least every 1000 hours actual usage.



Remove the test sample from the chamber.
Remove the masking tape from the test sample.



Compare the color of the darkest portion of the uncovered area of the test sample to the AATCC Chromatic Transference Scale and rate to the nearest 0.5.
Chromatic Transference Scales must be replaced at least every 24 months.

Prepared by	Approved by	REVISION		DATE	