Bonding Test Results
胶着力测试

SATRA Accredited Laboratory No. 08A03

Form # : Lab VF 001

PASS

ETRF No: A005489060

Lab Ref.No:**DTP20260612SHB11-L**


● Pro. Shoes 量产鞋 ○ Pro. Re-test 量产重测
○ NewDevelopment 开发
○ Tech 1 ○ Tech 2 ○ Tech 3 ○ Tech 4
○ Sales Sample 销样 ○ 试胶试验

Received Date 收到日期: 2026-06-12
Tested Date 测试日期: 2026-06-13
Finished Date 完成日期: 2026-06-13
Technician 技术员: L. Tuddao

Factory (工厂):	DATIAN SUBIC SHOES INC. (DTP)		
Adhesive supplier 胶水供应商:	NANPAO	**Shipped Date (出货日期):**	-
Model/Style/PGSC (英文鞋型):	UA KNU SKOOL	**Color (颜色):**	BLACK/TRUE WHITE
Production Date (生产日期):	2026-06-13	**PO/Lot No (订单号码):**	5200652846
PO Quantity (订单数量):	1386	**Send by (送达):**	-

Shoe Part	VF Test Method	STD kgf/cm (Tolerable)	Test Result kgf/cm		Status		Mode of Failure(s) 失败的方式	Possible Cause(s) 可能的原因
			Min	Max	Pass	Fail		
Upper/Foxing Tape (鞋面/围条)	VF-F01 (2019/05)	2.5 (≥ 2)	3.45	6.29	PASS		**AF**= Failure at the adhesive/substrate interface or the adhesive/primer interface **CF**= Cohesive Failure of the adhesive (failure within the adhesive or between the two layers of adhesive) **PF**= Failure at the primer/substrate interface **SF**= Failure of the substrate, including the location of the failure within the substrate	(a) Poor Priming 药水不良 (b) Poor cementing 胶水不良 (c) Over-dried cement (d) Wet primer 湿的药水 (e) Wet cement 湿的胶水 (f) Poor pressing 压机不良 (g) Poor Roughing 打粗不良 (h) Upper material - weak 鞋面材料不良 (i) EVA-Weak EVA不良 (j) Dusty component 粉沫 (k) Splitting of foxing tape 围条分层
Foxing Tape / OS (围条/橡胶大底)	VF-F01 (2019/05)	2.5 (≥ 2)	3.49	5.33	PASS			
Center : IS/OS (中插 / 大底)	VF-F01 (2019/05)	1 (≥ 0.8)	1.54	1.80	PASS			


1. Outside Value: Fabric / PU / EVA kgf/cm
2. Inside Value:

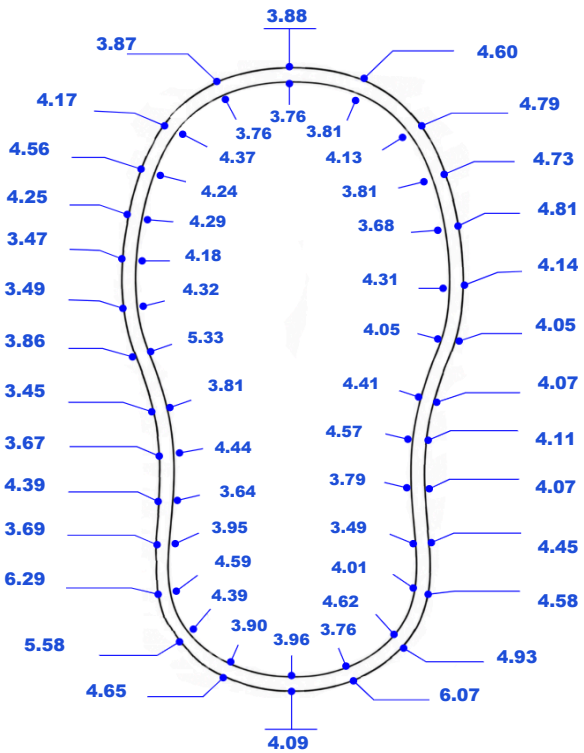

Center: Fabric / PU / EVA kgf/cm

Left	Right
1.73	
1.54	
1.80	
1.56	
1.58	
1.55	

1. Outside Value: Fabric / PU / EVA kgf/cm
2. Inside Value:

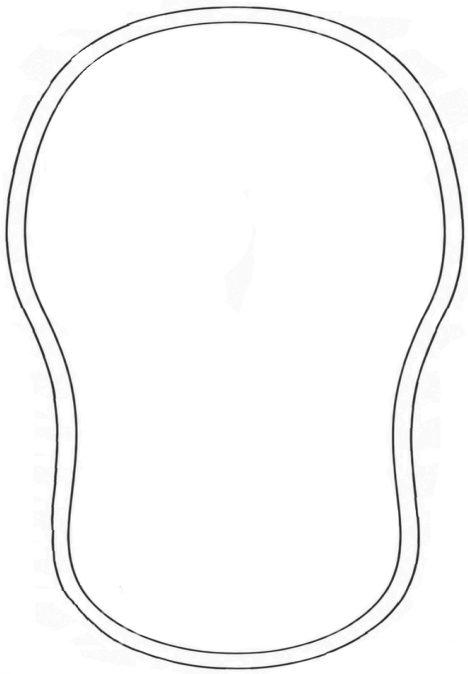

Comments 备注:
Tested in accordance with VF Laboratory Standards.

Reviewed by 审查:
KATE G.

Approved by 核准:
QA Laboratory Head

Bonding Test Results
胶着力测试


PASS

Form # : Lab VF 001	**ETRF No:** A005489060	**Lab Ref.No:** DTP20260612SHB11-L

Factory (工厂):	DATIAN SUBIC SHOES INC. (DT	● Pro. Shoes 量产鞋	O Pro. Re-test 量产重测
Adhesive supplier胶水供应商:	NANPAO	O New/Development 开发	
Shipped Date (出货日期):	06-19-2026	o Tech 1 o Tech 2 o Tech 3 o Tech 4	
Model/Style/PGSC (英文鞋型):	UA KNU SKOOL	O Sales Sample 销样	
Color (颜色):	BLACK/TRUE WHITE	O Trial experiment试胶试验	
Production Date (生产日期):	2026-06-12	Received Date 收到日期:	2026-06-12
PO/Lot No (订单号码):	5200652846	Tested Date 测试日期:	2026-06-13
PO Quantity (订单数量):	1386	Finished Date 完成日期:	2026-06-13
Send by (送达):		Technician 技术员:	L. Tuddao

Shoe Part	VF Test Method	STD kgf/cm	Test Result kgf/cm		Status		Mode of Failure(s) 失败的方式	Possible Cause(s) 可能的原因
			Min	Max	Pass	Fail		
Upper/Foxing Tape (鞋面/围条)	VF-F01 (2019/05)	3	3.45	6.29	PASS		AF= Failure at the adhesive/substrate interface or the adhesive/primer interface	(a) Poor Priming 药水不良
Foxing Tape / OS (围条/橡胶大底)	VF-F01 (2019/05)	3	3.49	5.33	PASS			(b) Poor cementing 胶水不良
Center : IS/OS (中插 / 大底)	VF-F01 (2019/05)	1	1.54	1.8	PASS			(c) Over-dried cement
							CF= Cohesive Failure of the adhesive (failure within the adhesive or between the two layers of adhesive	(d) Wet primer 湿的药水
								(e) Wet cement 湿的胶水
								(f) Poor pressing 压机不良
							PF= Failure at the primer/substrate interface	(g) Poor Roughing 打粗不良
								(h) Upper material - weak 鞋面材料不良
							SF= Failure of the substrate, including the location of the failure within the substrate	(i) EVA-Weak EVA 不良
								(j) Dusty component 粉沫
								(k) Splitting of foxing tape 围条分层


1.Outside Value:Fabric / PU / EVA kgf/cm
2.Inside Value:

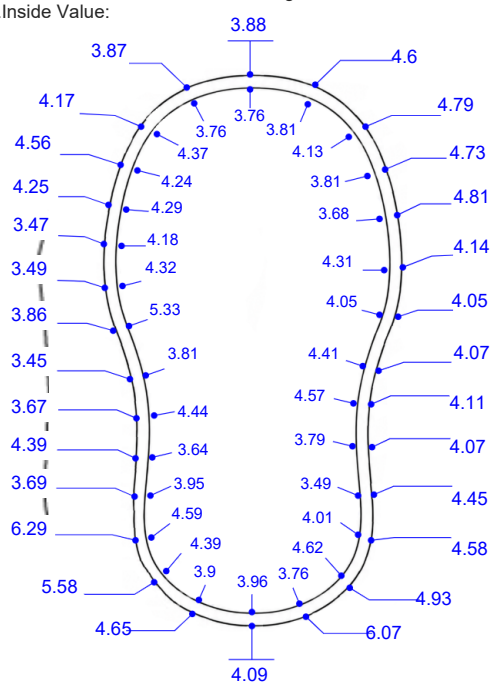

Center: Fabric / PU / EVA kgf/cm

Left	Right
1.73	
1.54	
1.8	
1.56	
1.58	
1.55	

1.Outside Value:Fabric / PU / EVA kgf/cm
2.Inside Value:

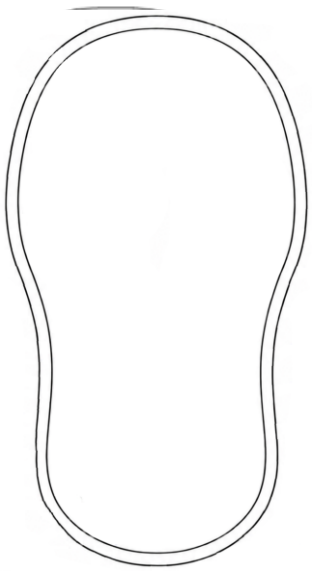

Comments 备注:

Reviewed by 审查: KATE G.

Approved by 核准:

VANS
Bonding Test Result

Equip Code: DTP-QC-002

Test Date	Test Speed mm/min	Test Report	Style Color Way	Test No.	MTL#	Width mm
2026-06-13	100	DTP20260612SHB11-L	UA KNU Skool Black True White	1		10.00
2026-06-13	100	DTP20260612SHB11-L		2		10.00
2026-06-13	100	DTP20260612SHB11-L		3		25.40

Report No.	M1 kgf/cm	M2 kgf/cm	M3 kgf/cm	M4 kgf/cm	M5 kgf/cm	M6 kgf/cm	M7 kgf/cm	M8 kgf/cm	M9 kgf/cm	M10 kgf/cm	M11 kgf/cm	M12 kgf/cm	M13 kgf/cm	M14 kgf/cm	M15 kgf/cm	M16 kgf/cm	M17 kgf/cm
Upper To Foxing	6.29	3.69	4.39	3.67	3.45	3.86	3.49	3.47	4.25	4.56	4.17	3.87	3.88	4.60	4.79	4.73	4.81
Foxing To Outsole	4.59	3.95	3.64	4.44	3.81	5.33	4.32	4.18	4.29	4.24	4.37	3.76	3.76	3.81	4.13	3.81	3.68
Filler To Outsole	1.73	1.54	1.80	1.56	1.58	1.55	-	-	-	-	-	-	-	-	-	-	-

Report No.	M18 kgf/cm	M19 kgf/cm	M20 kgf/cm	M21 kgf/cm	M22 kgf/cm	M23 kgf/cm	M24 kgf/cm	M25 kgf/cm	M26 kgf/cm	M27 kgf/cm	M28 kgf/cm	M29 kgf/cm	M30 kgf/cm	M31 kgf/cm	M32 kgf/cm	M33 kgf/cm	M34 kgf/cm
Upper To Foxing	4.14	4.05	4.07	4.11	4.07	4.45	4.58	4.93	6.07	4.09	4.65	5.58	-	-	-	-	-
Foxing To Outsole	4.31	4.05	4.41	4.57	3.79	3.49	4.01	4.62	3.76	3.96	3.90	4.39	-	-	-	-	-
Filler To Outsole	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-

