

Chemical Science

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: P. Su, K. Iwase, T. Harada, K. Kamiya and S. Nakanishi, *Chem. Sci.*, 2018, DOI: 10.1039/C8SC00604K.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.



Chemical Sciences

ARTICLE

Covalent triazine framework modified with coordinatively-unsaturated Co or Ni atoms for CO₂ electrochemical reduction

Panpan Su,^{†a} Kazuyuki Iwase,^{†b} Takashi Harada,^a Kazuhide Kamiya,^{*a,c,d} and Shuji Nakanishi^{*a,c}

Received 00th January 20xx,
Accepted 00th January 20xx


DOI: 10.1039/x0xx00000x

www.rsc.org/

The electrochemical reduction of carbon dioxide (CO₂) has attracted considerable attention as a means of maintaining the carbon cycle. This process still suffers from poor performance, including low faradaic efficiencies and high overpotential. Herein, we attempted to use coordination number as a control parameter to improve the electrocatalytic performance of metal species that have previously been thought to have no CO₂ reduction activity. Covalent triazine frameworks (CTF) modified with coordinatively-unsaturated 3d metal atoms (Co, Ni or Cu) were developed for efficient electroreduction of CO₂. Co-CTF and Ni-CTF materials effectively reduced CO₂ to CO from -0.5 V versus RHE. The faradaic efficiency of the Ni-CTF during CO formation reached 90% at -0.8 V versus RHE. The performance of Ni-CTF is much higher than that of the corresponding metal-porphyrin (using tetraphenylporphyrin; TPP). First principles calculations demonstrated that the intermediate species (adsorbed COOH) was stabilized on the metal atoms in the CTF due to the low-coordination structure of this support. Thus, the free energy barriers for the formation of adsorbed COOH on the metal atoms in the CTF supports were lower than those on the TPP supports.

Introduction

The electrochemical carbon dioxide reduction reaction (CO₂RR) in aqueous media is a promising approach to closing the carbon cycle, and as such has attracted significant attention.¹ The reduction of CO₂ to CO summarized in the following equations is an important step in the CO₂RR and represents the first two-electron reaction.²



Here, the asterisk represents free adsorption site. Previous studies have shown that either reaction (1) or (3) can become the rate-determining step, depending on the relative magnitudes of the COOH* and CO* adsorption energies.^{2e-g}

Importantly, there is a linear relationship (scaling relation) between the COOH and CO adsorption energies, such that these values do not change independently of one another.^{2e,2f} For this reason, the adsorption energy of COOH* (or CO*) can serve as an indicator of the CO generation activity, and a so-called volcano-type relationship has been established between the adsorption energy and the catalytic activity.^{2e,2f} Therefore, developing a highly efficient CO generating electrocatalyst requires precise tuning of the adsorption energies of critical intermediate species.

There are two important factors determining the adsorption energies of intermediates on electrocatalysts. The first is the metal species in the catalyst. i.e. transition metals at active sites having a greater number of d-electrons tend to lower the adsorption energy.³ For this reason, the effects of metal species on the CO₂RR have been systematically investigated using tetraphenylporphyrin (TPP),^{2c,4} which can serve as a platform to support various metals via coordination bonds. It is known that cobalt modified-TPP (Co-TPP) has an appropriate bond strength with COOH* and thus shows efficient CO₂RR activity, whereas the catalytic activities of nickel (Ni) or copper (Cu) modified-TPP are low because the COOH* binding energy is insufficient.^{4c-e} The second critical factor is the coordination structure (or the coordination number) of the metal.⁵ First principles calculations have demonstrated that a decrease in coordination number of bulk Pt or Cu leads to an increase in the CO* binding strength,^{5a-b} thus affecting the CO₂RR activity. Therefore, it may be possible to use the coordination number as a control parameter to improve the performance of metal species that have previously been thought to have no CO₂RR activity.

^a Research Center for Solar Energy Chemistry, Osaka University, 1-3 Machikaneyama, Toyonaka, Osaka 560-8531, Japan
E-mail: kamiya@chem.es.osaka-u.ac.jp; nakanishi@chem.es.osaka-u.ac.jp

^b Department of Applied Chemistry, The University of Tokyo, 7-3-1 Hongo, Bunkyo-ku, Tokyo 113-8656, Japan

^c Graduate School of Engineering Science, Osaka University, 1-3 Machikaneyama, Toyonaka, Osaka 560-8531, Japan

^d Japan Science and Technology Agency (JST) PRESTO, 4-1-8 Honcho, Kawaguchi, Saitama 332-0012, Japan

[†] Both authors equally contributed to this work.

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x



Covalent triazine frameworks (CTF), consisting of microporous conjugated polymers with 1,3,5-triazine linker units,⁶ are promising platforms for metal species with coordination unsaturation. Our group has previously reported that the adsorption energies of dioxygen and nitrogen oxides on Cu-CTF are larger than those on Cu-TPP or bulk Cu, respectively.⁷ This increase in the adsorption energy was attributed to the coordinatively unsaturated nature of the Cu atoms in the CTF. In the present work, we synthesized CTFs modified with coordinatively-unsaturated 3d metal atoms as electrocatalysts for CO₂RR with the aim of eliciting the potential performance of metals that have, to date, been regarded as inactive.

Results and discussion

The CTF was synthesized via the polymerization of 2,6-dicyanopyridine in the presence of conductive carbon particles (CPs; KetchenBlack EC600JD, please see the synthesis part) in the same manner as described in our previous reports.^{7,8} The obtained CTF was subsequently impregnated with aqueous solutions of various divalent metal chlorides to obtain M(II)-CTF (M = Co, Ni or Cu). The full details of the synthesis are provided in the Experimental Section. The elemental analyses were conducted by semi-quantitative X-ray photoelectron spectroscopy (XPS) and inductively coupled plasma atomic emission spectroscopy (ICP-AES) (Table S1 and S2). The CTF layer was uniformly polymerized on CPs, which has been proven by N-1s XPS spectra and transmission electron microscopy (TEM) energy dispersive X-ray (EDX) mapping in our previous reports.^{8b} In addition, the SEM pictures for CTF (Fig. S1) show that the particle size of 20-80 nm, which corresponded to the size of the CPs, also revealed that CTF was well mixed with CPs.^{7,8} The powder XRD patterns for CTF (Fig. S2) indicated that our M-CTFs have amorphous structure, which is consistent with the reported CTF originated from 2,6-dicyanopyridine.^{6a,6d} The high-resolution TEM images (Fig. S3) suggested that no metal or metal oxide nanoparticles was formed on M-CTF, which are consistent with the previous results.^{7a,8b} The nitrogen adsorption-desorption isotherms indicates that CTF and Ni-CTF have a hierarchical pore system composed of micro- and mesopores (see Fig. S4 for the detail.).

Electronic and structural characterizations of the metal sites in M-CTF specimens were conducted using extended X-ray absorption fine structure (EXAFS) analyses. Previously, we demonstrated that the Cu atoms in Cu-CTF are in the form of Cu(II) and have a lower first coordination number of 3.4 compared to the value of 4 in Cu-TPP.^{7b} The present study focused on the characterization of Ni-CTF (as presented herein) and Co-CTF (as presented in Supporting Information, see Fig. S6 and the associated caption). Fig. S5 shows the Ni-K XANES spectra for Ni-CTF and the reference samples. The XANES absorption edge corresponding to 1s → 4p transitions⁹ for Ni-CTF located at 8333 eV, which is consistent with that for NiO and Ni(II)-TPP. These results indicated that the Ni(II) valence state was dominant in Ni-CTF. Similarly, Fig. S6a indicated that the Co(II) valence state was dominant in Co-CTF.

We also acquired EXAFS data to assess the molecular structure of the Ni-CTF (Fig. 1a). Ni-CTF shows one strong peak

at 1.7 Å, whereas no strong peak corresponds to Ni-Ni bond and Ni-O-Ni bonds were not observed.¹⁰ We previously demonstrated that no metal species were found on CPs that were treated with MCl₂ solutions^{7a}, indicating that metal species were anchored on CTFs. In addition, the TEM results showed that no NiO nanoparticle was formed. Thus, the first coordination sphere (the peak at 1.7 Å) was composed of N atoms of CTF. The curve fitting for EXAFS spectra were performed for Ni-CTF (detail see Table S3 and its captions). The coordination number of N atoms in the first coordination sphere of Ni-CTF is 3.4. These data indicate that the Ni atoms in the Ni-CTF were individually isolated and had an unsaturated first coordination sphere in the pores of the CTF (Fig. 1b), identical result is also obtained for Co-CTF (Fig. S6).

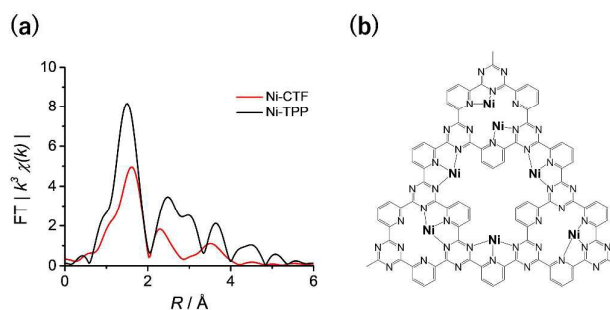


Fig. 1 (a) the k^3 -weighted Fourier transform EXAFS spectra at the Ni K-edge of Ni-CTF (red), Ni-TPP (black), Ni foil (gray) and NiO (dark yellow), and (b) an illustration showing the Ni sites in Ni-CTF. (Weakly adsorbed molecules in electrolyte, such as water and ethanol used for the preparation of electrode, are not shown for clarity.)

Because the data confirmed that the metal centers in the M-CTF had lower coordination numbers than those in the corresponding M-TPP, we next evaluated and compared the CO₂RR activities of these samples. Changes in current density (j) at different potentials (U) were examined using M-CTF electrodes in Ar-saturated phosphate buffer solutions (PBS, pH 6.8) and CO₂-saturated KHCO₃ solutions (pH 6.8). As shown in Fig. 2b, the cathodic current produced by the Ni-CTF was significantly increased when CO₂ was present in the electrolyte. The onset potential for the reduction reaction in CO₂-saturated solutions was -0.48 V versus RHE, whereas a current attributed solely to the hydrogen evolution reaction (HER) was observed from -0.72 V vs. RHE in the absence of CO₂. In contrast, little or no increase in the reduction current in the presence of CO₂ was observed when using the Co-CTF, Cu-CTF or bare CTF (Figs. 2b, c and d, respectively). The reduction peak of metal centers was not observed for M-CTF in the absence of CO₂. This is likely because these peaks were overlapped with the HER current.

CVs alone cannot provide conclusive evidence for CO₂ reduction because the different electrolytes (PBS and KHCO₃ solutions) were used for the comparison. Thus, subsequently, we quantitatively analysed the CO₂ reduction products in the gas phase using gas chromatography - mass spectrometry (GC-MS). A representative GC-MS chart is shown in Fig. S7. The effects of potential on the Faradaic efficiency (FE) of the CO generation reaction using M-CTFs in neutral solutions are



summarized in Fig. 3. At the appropriate potential, the main product of the electrolysis in the presence of CO₂ when employing either Ni-CTF or Co-CTF was CO, whereas almost no CO evolution was observed with the Cu-CTF or bare CTF throughout the entire experimental potential region. In particular, the Ni-CTF exhibited CO formation with a FE exceeding 90% over the range of -0.8 to -0.9 V. It should be noted that the extent of CO evolution by the bare CTF was almost negligible, indicating that the Ni/Co sites in the CTF served as the catalytic centers. In contrast, the FE of Cu-CTF was similar with that of bare CTF, meaning that the FE of Cu-CTF was affected by the CO₂RR activity of CTF frameworks to some extent. GC-MS and nuclear magnetic resonance (NMR, Fig. S8) data showed that H₂ was the other major product in all cases, along with trace amounts of methane (< 0.5 %). Note that only H₂ was observed in the absence of CO₂, indicating that the CO was generated not from the degradation of CTF but from CO₂RR. (Fig. S7). The partial current density values (Fig. 4) during the CO generation using Ni-CTF and Co-CTF (3–4 A/g) were equivalent to those reported for a carbon-supported Au catalyst and metal-modified nitrogen-doped carbon catalysts.¹¹ The Tafel plots of M-CTF are shown in Fig. S9. The slope of Tafel plots for Ni-CTF and Co-CTF is 154 mV dec⁻¹ and 162 mV dec⁻¹, respectively. In contrast, the Tafel slopes for Cu-CTF (305 mV dec⁻¹) and CTF (272 mV dec⁻¹) were much larger than that of Ni-CTF and Co-CTF, implying the inefficiency of Cu-CTF and CTF for CO₂ electrochemical reduction. The electrocatalytic stability of Ni-CTF was evaluated at -0.65 V (vs. RHE) for 3 h in CO₂ saturated KHCO₃ electrolyte. As Fig. S10 shows, the FE for CO displayed almost negligible change, while the reduction current exhibited mildly decreased. As the stability for our catalyst is not enough for the real application, further experiments to improve the stability by choosing the appropriate framework are ongoing in our laboratory.

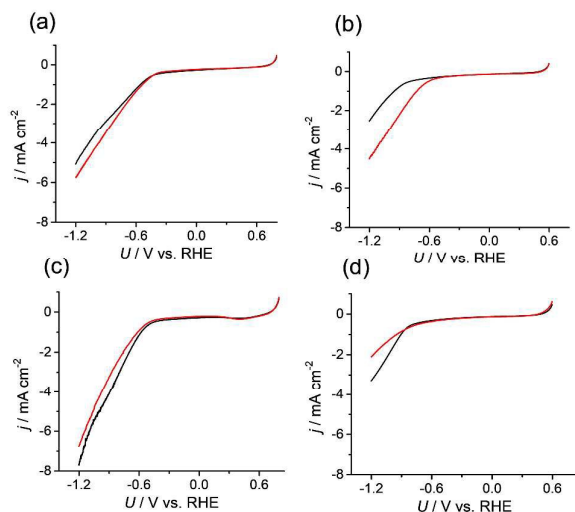


Fig. 2 Current density (j) versus potential (U) curves obtained from (a) Co-CTF, (b) Ni-CTF, (c) Cu-CTF, and (d) CTF in a phosphate buffer (saturated with Ar, black line) and a KHCO₃ electrolyte (saturated with CO₂, red line).

For comparison purposes, the CO₂ reduction activities of M-TPP were also tested. In the present work, the M-TPP

samples were adsorbed on carbon nanoparticles prior to electro-chemical measurements. An increase in the cathodic current from -0.5 V was observed when using Co-TPP in the presence of CO₂, whereas the Ni- and Cu-TPP showed no such increase (Fig. S11). The FE and partial current density values during the CO generation reaction in association with Co, Ni and Cu-TPP were 1.3, 0.04 and 0.04 mA cm⁻² at -0.9 V vs. RHE, respectively, as shown in Figs. S12a and S12b. The major product resulting from the use of Ni- and Cu-TPP was H₂ at all potentials. Therefore, only Co-TPP exhibited effective CO₂RR activity among these three TPPs, a result that is consistent with previous studies.^{4b-e}

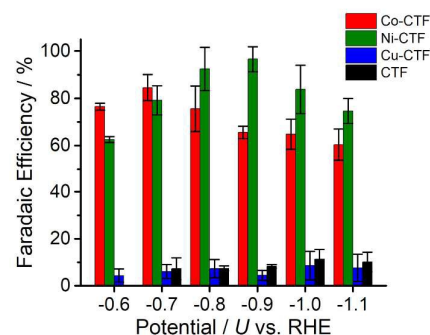


Fig. 3 Effect of potential on the faradaic efficiency values during the CO₂RR to generate CO using Co-CTF (red), Ni-CTF (green), Cu-CTF (blue) and CTF (black) in a KHCO₃ electrolyte (saturated with CO₂) at pH 6.8. The error bar represents the standard deviation from three experimental trial.

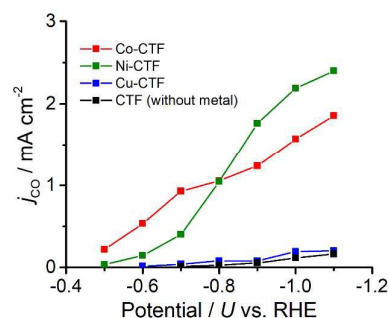


Fig. 4 Partial current density values during the CO generation reaction using Co-CTF (red), Ni-CTF (green), Cu-CTF (blue) and CTF (black).

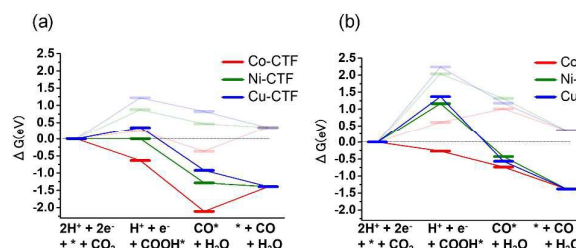


Fig. 5 Free energy diagrams for CO₂ reduction to CO on Co (red), Ni (green) and Cu (blue)-modified (a) CTF, and (b) TPP at 0 V (pale lines) and -0.87 V (dark lines).



The origin of the differences in the activities during CO₂ reduction to CO of the M-CTF and M-TPP were subsequently examined, employing DFT calculations. After structural optimization of M-CTF, the 3-coordination metal site was the most stable, as represented in Fig. S13 (see the Experimental Section for the detail). Thus, the DFT results also revealed that the low coordination metal sites were stabilized by the CTF frameworks, which is basically consistent with the EXFAS results. Fig. 5 and Table S4 shows the free energy diagrams for the electrochemical reduction of CO₂ to CO on M-CTF and M-TPP at 0 V and -0.87 V vs. RHE, based on the computational hydrogen electrode model.^{2g,11b,12} Notably, an increase in the number of d-electrons of the transition metal representing the active sites increased the Gibbs free energy change (ΔG) value associated with the formation of COOH* and CO* in the case of both the CTFs and TPPs (although the energy change was in the order of Co < Ni < Cu). These data are consistent with results reported for work with M-porphyrins in association with the CO₂RR and also the HER and oxygen reduction reaction.^{3,4c,4e} The rate determining step when using these materials is evidently the first reduction reaction: the formation of COOH* (reaction (1)). The free energy barrier of this step depends on the applied potential,^{2g,11b,12a} and so we calculated the CO₂ limiting potential ($U_L(\text{CO}_2)$) for each catalyst, defined as the potential at which all elementary steps become exergonic, as summarized in Table S5. The $U_L(\text{CO}_2)$ obtained with the Co-TPP was approximately -0.6 V vs. RHE, whereas the values for the Cu-TPP and Ni-TPP were much more negative (< -2.0 V). Therefore, a low energy barrier to the formation of COOH* apparently resulted in the high CO₂ reduction activity exhibited by the Co-TPP. In addition, the $U_L(\text{CO}_2)$ values of the CTFs were smaller than those of the corresponding TPP. In particular, the overall reaction pathway on the Ni-CTF becomes exergonic at -0.87 V vs. RHE (Fig. 5a), which essentially coincides with the potential range at which CO formation was observed on the same material. In contrast, the $U_L(\text{CO}_2)$ of the Cu-CTF (-1.2 V) was 0.33 V more negative, and so the formation of COOH* is still endothermic at -0.87 V on the latter. We expect that Cu-based catalysts with a further low-coordination number (less than 3) exhibit efficient CO₂RR activity.

The partial current densities during CO generation are plotted against $\Delta G(\text{COOH}^*)$ in Fig. 6, clearly indicating that the low $\Delta G(\text{COOH}^*)$ is important for high CO₂RR activity, and also showing that the Ni active sites appear quite high on the plot of CO₂RR activity upon changing the ligand from TPP to CTF. That is, by transitioning the ligand from TPP to CTF, a lower $\Delta G(\text{COOH}^*)$ was obtained such that Ni became the optimal metal species. In the case of the Co-CTF, the release of CO (reaction (3)), which is independent of the applied potential, was an endothermic reaction. As mentioned in the Introduction, the rate-determining step for CO₂RR, which depends on the adsorption energy of CO and COOH, is the reaction (1) or the reaction (3). However, the existence of the scaling relationship of them does not allow us to independently control these two adsorption energies.^{2e,2f,13} Therefore, on the basis of the DFT calculations, there should be the volcano-type relation accompanied with the single peak which locates between Co-CTF and Co-TPP in Figure 6. The rate-determining step can be evaluated by the position in the volcano plot against the peak.

Co-CTF has lower $\Delta G(\text{COOH}^*)$ than the optimal value (the peak of the volcano plot), resulting that the rate-determining step was the reaction (3) (CO desorption). Thus, in contrast to Cu-based catalysts, Co based catalysts with a further low-coordination number, which bind CO more strongly, should show poor CO₂RR activity. In contrast, the rate-determining step of the other catalysts in the higher $\Delta G(\text{COOH}^*)$ side was the reaction (1) (CO₂ activation). To complete the wide range of volcano-type curve, the investigation of CO₂RR activity of catalysts with different metal species and coordination numbers is under progress in our laboratory.

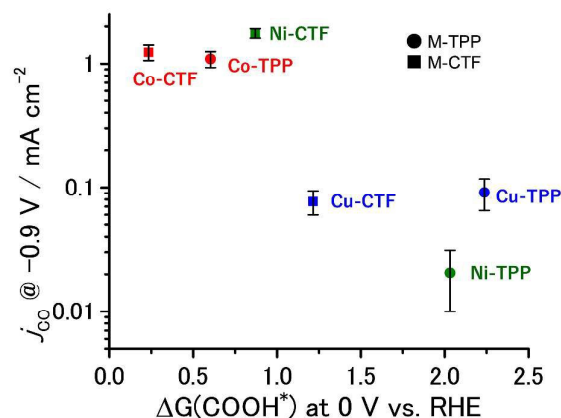


Fig. 6 Relationship between $\Delta G(\text{COOH}^*)$ at 0 V and j_{CO} at -0.9 V. The error bar represents the standard deviation from three experimental trial.

At this point, we can explain the origin of the lower $\Delta G(\text{COOH})$ values exhibited by the M-CTF compared to those for the corresponding M-TPP. The EXAFS results demonstrate that the metal atoms in the CTF have unsaturated coordination structures (that is, low coordination numbers, as shown in Fig. 1b), compared with the metals in the porphyrin-like ligands. Calle-vallejo and co-authors have used first principles calculations to show that metal sites with lower coordination values have higher adsorption energies because they possess numerous accessible d-orbitals as well as low steric hindrance.^{5a,5c-d} Therefore, metal atoms in CTF with low coordination numbers can more strongly bind small molecules than those in N4 macrocycles, resulting in a low free energy barrier to the first reaction step.

Conclusions

In the present work, we developed a novel route to precisely tune the adsorption energies of critical intermediate species for efficient CO₂RR through the modulation of the coordination number of active centers. The Ni and Co-CTF effectively reduced CO₂ to CO, whereas, among the M-TPP, only the Co-TPP showed any activity. DFT calculations demonstrated that the free energy barrier of the first reduction step, the formation of adsorbed COOH, was decreased by changing the ligands from TPP to CTF. The lower coordination metal sites were stabilized on the CTF due to their rigid framework, allowing COOH* species to be absorbed at these low



coordination sites. Consequently, the Ni-based catalyst obtained using CTF rather than TPP ligands was situated at a higher position on the volcano-like CO₂RR activity plot. Thus, our work provides a new avenue to design efficient catalysts for CO₂RR.

Experimental

Synthesis of CTF.

Each CTF was prepared using essentially the same method described in our previous publications⁷. Briefly, 2,6-dicyanopyridine (64.5 mg, Koei Kagaku) and Ketjen Black EC600JD (64.5 mg, Lion Corp.) were mixed with ZnCl₂ (6.82 g, Wako) in a glass vacuum tube and then heated to 400 °C at 3.3 °C/min and held at that temperature for 40 h. The resulting powder was washed with deionized water, tetrahydrofuran (THF, Wako), HCl (1 M, Wako) and aqueous ammonia (1 M, Wako). The obtained CTF was dispersed in a 10 mM aqueous solution of MCl₂ (M = Co, Ni or Cu) and stirred at 80 °C for 3 h. Subsequently, the product was collected by centrifugation and thoroughly washed with deionized water to remove any unbound metal salt, followed by drying at 60 °C in a vacuum oven for 1 day.

Loading of M-TPP onto carbon particles.

Here, we take Co-TPP electrode as an example to show the preparation procedure of M-TPP electrode. Firstly, Co-TPP (9.5mg) and EC600JD (90mg) were dispersed in 20mL DMF solvent using an ultrasonic bath, and then, the mixture was dried at 80 °C with a rotary evaporator. The metal concentration of the mixture of M-TPP and EC600JD is the same with that of the corresponding M-CTF (determined by the XPS measurements). These loaded M-TPP are denoted as M-TPP.

Characterizations.

XPS (Axis Ultra, Kratos Analytical Co.) spectra were obtained using monochromatic Al K α X-rays at $h\nu = 1486.6$ eV. XAFS data were acquired by the transmission method using the hard X-ray BL01B01 beam line at the SPring-8 facility, Japan. Transmitted X-rays were detected using a double-crystal Si (111) monochromator. Surface inspection was carried out with a scanning electron microscope (SEM; JEOL, JSM-7600F.) and high-resolution transmission electron microscope (TEM; Hitachi, H-9000NAR.). XANES spectra and EXAFS were analysed using Athena, ARTEMIS and FEFF6L software. A powder X-ray diffraction (XRD) pattern was recorded on a PANalytical X'Pert PRO diffractometer with Cu K α radiation. Metal content was determined by inductively coupled plasma atomic emission

spectroscopy (ICP-AES; Optima 8300, PerkinElmer). The N₂ adsorption-desorption isotherm was obtained by a Micromeritics 3 Flex at 77K.

Electrochemical measurements.

Electrochemical measurements were performed using a Hokuto Denko Electrochemical Station (Model HZ-5000) in a two-compartment electrochemical cell (separated by a Nafion membrane) in conjunction with three electrodes. A Ag/AgCl electrode (with saturated KCl as the internal solution) and platinum wire were used as the reference and counter electrodes, respectively. Each working electrode was fabricated by dispersing 3 mg of the desired M-CTF (or CTF) and 28.5 μ L Nafion (5 wt.%, Aldrich) in 300 μ L ethanol using an ultrasonic bath to generate a catalyst ink. A 60 μ L quantity of this ink was dropped onto a glassy carbon plate (2 cm²), which was then left to dry in air at room temperature, to yield a catalyst layer with a loading of 0.3 mg cm⁻². The gaseous products that accumulated in the cathodic part of the reaction cell were analyzed by GC-MS (GCMS-QP 2010 Plus, Shimadzu, Japan), calibrated using CO and H₂ samples diluted with air to various concentrations. Products in liquid phase were analyzed on a Varian 500 MHz NMR spectrometer. A 0.5 mL electrolyte (0.1 M KHCO₃) after electrolysis was mixed with D₂O (0.1 mL) and dimethyl sulphoxide (32 μ L) as internal standard.

DFT calculations

Density functional theory (DFT) calculations of the adsorption energies of intermediates on the M-CTF and M-TPP were performed using the OpenMX code.¹⁴ The generalized gradient approximation of the Perdew–Burke–Ernzerhof model (GGA-PBE) was applied, and a kinetic energy cutoff of 120 Ryd was selected. The detailed structural parameters of the M-CTF can be found in our previous publication^{7b}. The structure of CTF frameworks without metals was first relaxed. Then, we doped metal sites and relaxed the metal configuration, while the frameworks were fixed. The optimized Ni-CTF structure is shown in Fig. S13. One COOH or CO molecules were adsorbed on one metal sites, and their configurations were relaxed to calculate the free energy diagram. To simplify the DFT calculations, we used a slab consisting of a single CTF layer as the model structure of M-CTFs. A slab model was used with a 15 Å vacuum layer between the CTF layers. Zero-point energy and entropic corrections were applied based on reported values^{4c,12a} to convert electronic energies into Gibbs free energies. In this work, the solvation energy was not applied and a -0.24 eV correction was added to CO to compensate for a limitation of the PBE model.^{4c,15} Reaction free energies were calculated using the computational hydrogen electrode (CHE) model, following the same method as described in previous reports^{12a,2g,11b}. Briefly, in this model, the chemical potential of a proton-electron pair in solution is equal to half that of a gas phase H₂ molecule at 0 V vs. RHE. Thus, we utilized the



ARTICLE

Journal Name

following equation to apply the overpotential when calculating the free energy diagram.

$$G[\text{H}^+ + \text{e}^-] = 0.5 G[\text{H}_2] - eU \quad (4)$$

Here, U is the applied overpotential and e is the elementary charge.

Conflicts of interest

There are no conflicts to declare.


Acknowledgements

The XAFS data were acquired at the SPring-8 facility (proposal nos. 2016A1120, 2016A1464, 2016B1098, 2016B1696 and 2017A1790). This research was also supported by the PRESTO Program (grant no. JPMJPR1415) of the Japan Science and Technology Agency (JST) and by a JSPS KAKENHI Program (grant nos. 16J09552 and 17H04798). TEM measurement was carried out by using a facility in the Research Center for Ultra-High Voltage Electron Microscopy, Osaka University and TEM observation was supported by Dr Takao Sakata.

Notes and references

- (a) C. Costentin, M. Robert and J. M. Saveant, *Chem. Soc. Rev.*, 2013, **42**, 2423; (b) J. L. Qiao, Y. Y. Liu, F. Hong and J. J. Zhang, *Chem. Soc. Rev.*, 2014, **43**, 631; (c) R. J. Lim, M. S. Xie, M. A. Sk, J. M. Lee, A. Fisher, X. Wang and K. H. Lim, *Catal. Today*, 2014, **233**, 169; (d) Q. Lu, J. Rosen, Y. Zhou, G. S. Hutchings, Y. C. Kimmel, J. G. Chen and F. Jiao, *Nat. Commun.*, 2014, **5**, 3243.
- a) M. Liu, Y. J. Pang, B. Zhang, P. De Luna, O. Voznyy, J. X. Xu, X. L. Zheng, C. T. Dinh, F. J. Fan, C. H. Cao, F. P. G. de Arquer, T. S. Safaei, A. Mepham, A. Klinkova, E. Kumacheva, T. Filleter, D. Sinton, S. O. Kelley and E. H. Sargent, *Nature*, 2016, **537**, 382; b) C. Costentin, S. Drouet, M. Robert and J. M. Saveant, *Science*, 2012, **338**, 90; (c) S. Lin, C. S. Diercks, Y. B. Zhang, N. Kornienko, E. M. Nichols, Y. B. Zhao, A. R. Paris, D. Kim, P. Yang, O. M. Yaghi and C. J. Chang, *Science*, 2015, **349**, 1208; (d) D. Ren, B. S. H. Ang and B. S. Yeo, *ACS Catal.*, 2016, **6**, 8239; (e) K. P. Kuhl, T. Hatsukade, E. R. Cave, D. N. Abram, J. Kibsgaard and T. F. Jaramillo, *J. Am. Chem. Soc.*, 2014, **136**, 14107; (f) A. A. Peterson and J. K. Nørskov, *J. Phys. Chem. Lett.*, 2012, **3**, 251; (g) K. Chan, C. Tsai, H. A. Hansen and J. K. Nørskov, *ChemCatChem*, 2014, **6**, 1899.
- a) F. Calle-Vallejo, N. G. Inoglu, H.-Y. Su, J. I. Martínez, I. C. Man, M. T. M. Koper, J. R. Kitchin and J. Rossmeisl, *Chem. Sci.*, 2013, **4**, 1245; b) F. Calle-Vallejo, J. I. Martínez, J. M. García-Lastra, J. Rossmeisl and M. T. M. Koper, *Phys. Rev. Lett.*, 2012, **108**, 116103; (c) F. Calle-Vallejo, J. I. Martínez and J. Rossmeisl, *Phys. Chem. Chem. Phys.*, 2011, **13**, 15639.
- a) C. Costentin, M. Robert and J. M. Saveant, *Acc. Chem. Res.*, 2015, **48**, 2996; b) G. F. Manbeck and E. Fujita, *J. Porphyrins Phthalocyanines*, 2015, **19**, 45; (c) M.-J. Cheng, Y. Kwon, M. Head-Gordon and A. T. Bell, *J. Phys. Chem. C*, 2015, **119**, 21345; (d) N. Sonoyama, M. Kirii and T. Sakata, *Electrochem. Commun.*, 1999, **1**, 213; (e) V. Tripkovic, M. Vanin, M. Karamad, M. E. Björketun, K. W. Jacobsen, K. S. Thygesen and J. Rossmeisl, *J. Phys. Chem. C*, 2013, **117**, 9187.
- a) H. Li, Y. Li, M. T. M. Koper and F. Calle-Vallejo, *J. Am. Chem. Soc.*, 2014, **136**, 15694; b) Z. Zhao, Z. Chen, X. Zhang and G. Lu, *J. Phys. Chem. C*, 2016, **120**, 28125; (c) F. Calle-Vallejo, J. I. Martínez, J. M. García-Lastra, P. Sautet and D. Loffreda, *Angew. Chem. Int. Ed.*, 2014, **53**, 8316; (d) F. Calle-Vallejo, D. Loffreda, M. T. M. Koper and P. Sautet, *Nat. Chem.*, 2015, **7**, 403; (e) X. F. Ma and H. L. Xin, *Phys. Rev. Lett.*, 2017, **118**, 036101.
- a) P. Kuhn, M. Antonietti and A. Thomas, *Angew. Chem. Int. Ed.*, 2008, **47**, 3450; b) K. Sakaushi and M. Antonietti, *Bull. Chem. Soc. Jpn.*, 2015, **88**, 386; (c) C. E. Chan-Thaw, A. Villa, P. Katekomol, D. Su, A. Thomas and L. Prati, *Nano Lett.*, 2010, **10**, 537; (d) R. Palkovits, M. Antonietti, P. Kuhn, A. Thomas and F. Schüth, *Angew. Chem. Int. Ed.*, 2009, **48**, 6909; (e) P. Kuhn, A. I. Forget, D. Su, A. Thomas and M. Antonietti, *J. Am. Chem. Soc.*, 2008, **130**, 13333; (f) P. Puthiaraj, Y.-R. Lee, S. Zhang and W.-S. Ahn, *J. Mater. Chem. A*, 2016, **4**, 16288.
- a) K. Iwase, T. Yoshioka, S. Nakanishi, K. Hashimoto and K. Kamiya, *Angew. Chem. Int. Ed.*, 2015, **54**, 11068; b) T. Yoshioka, K. Iwase, S. Nakanishi, K. Hashimoto and K. Kamiya, *J. Phys. Chem. C*, 2016, **120**, 15729.
- a) R. Kamai, K. Kamiya, K. Hashimoto and S. Nakanishi, *Angew. Chem. Int. Ed.*, 2016, **55**, 13184; b) K. Kamiya, R. Kamai, K. Hashimoto and S. Nakanishi, *Nat. Commun.*, 2014, **5**, 5040.
- G. Kwag, E. Park, and S. Kim, *Bull. Korean Chem. Soc.* 2004, **25**, 298.
- a) A. K. Agegnehu, C.-J. Pan, J. Rick, J.-F. Lee, W.-N. Su and B.-J. Hwang, *J. Mater. Chem.*, 2012, **22**, 13849. b) A. Anspoks, A. Kuzimn, *J. Non-Cryst. Solids*, 2011, **357**, 2604.
- a) W. Zhu, R. Michalsky, Ö. Metin, H. Lv, S. Guo, C. J. Wright, X. Sun, A. A. Peterson and S. Sun, *J. Am. Chem. Soc.*, 2013, **135**, 16833; b) W. Zhu, Y.-J. Zhang, H. Zhang, H. Lv, Q. Li, R. Michalsky, A. A. Peterson and S. Sun, *J. Am. Chem. Soc.*, 2014, **136**, 16132; (c) A. S. Varela, N. R. Sahaie, J. Steinberg, W. Ju, H. S. Oh and P. Strasser, *Angew. Chem. Int. Ed.*, 2015, **54**, 10758; (d) H. Nishihara, T. Hirota, K. Matsuura, M. Ohwada, N. Hoshino, T. Akutagawa, T. Higuchi, H. Jinnai, Y. Koseki, H. Kasai, Y. Matsuo, J. Maruyama, Y. Hayasaka, H. Konaka, Y. Yamada, S. Yamaguchi, K. Kamiya, T. Kamimura, H. Nobukuni and F. Tani, *Nat. Commun.*, 2017, **8**, 109; (e) P. Su, K. Iwase, S. Nakanishi, K. Hashimoto and K. Kamiya, *Small*, 2016, **12**, 6083.
- a) H. Mistry, R. Reske, Z. Zeng, Z.-J. Zhao, J. Greeley, P. Strasser and B. R. Cuenya, *J. Am. Chem. Soc.*, 2014, **136**, 16473; b) J. K. Nørskov, J. Rossmeisl, A. Logadottir, L. Lindqvist, J. R. Kitchin, T. Bligaard and H. Jónsson, *J. Phys. Chem. B*, 2004, **108**, 17886.
- H. A. Hansen, J. B. Varley, A. A. Peterson and J. K. Nørskov, *J. Phys. Chem. Lett.* 2013, **4**, 388.
- (a) T. Ozaki, *Phys. Rev. B*, 2003, **67**, 155108; (b) T. Ozaki and H. Kino, *Phys. Rev. B*, 2004, **69**, 195113.
- F. Calle-Vallejo and M. T. M. Koper, *Angew. Chem. Int. Ed.*, 2013, **52**, 7282.



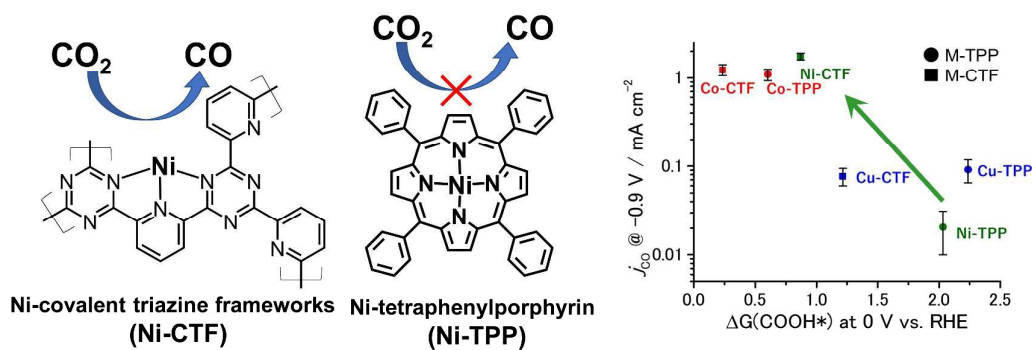

Nickel-modified covalent triazine frameworks effectively reduced CO₂ to CO because adsorbed COOH was stabilized on the coordinatively-unsaturated Ni atoms in CTF.

