

TEST REPORT

APPLICANT : ZHUHAI KELITONG ELECTRONIC CO.,LTD.

ADDRESS : YONGAN SECOND ROAD,LIANGANG INDUSTRY
ZONE,JINWAN DISTRICT,ZHUHAI CITY,GUANGDONG
PROVINCE ,CHINA 519090

TESTED SAMPLE DESCRIPTION : VACUUM CONTAINER, VACUUM LID, VACUUM BAG,
AIRTIGHT CONTAINER

ITEM NO. : KZ-001, KZ-002, KZ-007, CJ-VST07, CJ-VST04, KZ-004-130,
KZ-004-250, CJ-VST11,CJ-VSB01-S, CJ-VSB01-M, CJ-VSB01,
KZ-006, CJ-VST13, CJ-VST14, KZ-005, CL-AC01, CL-AC02,
CL-AC XX(XX=01-99),CJ-VSBX(X=01-99), CJ-VSBX-Y(X=1-99,
Y=A-Z),CJ-VSTXX(XX=01-99),KZ-XXX-YYYY(XXX=001-999;
YYYY=0100-9999)

AGE REQUESTED ON APPLICATION FORM : NOT PRESENT

SAMPLE RECEIVED DATE : 21-Nov-2022; 01-Dec-2022; 17-Jan-2023; 03-Mar-2023

TEST PERIOD : 27-Nov-2022 to 14-Mar-2023

The following test item(s) was/were performed on submitted sample(s) and/or component(s) confirmed by applicant

TEST REQUESTED	RESULT
Selected tests for the suitability for contact with foodstuffs compliant with the following regulations: - Regulation (EC) No 1935/2004. - Regulation (EU) No 10/2011 and its amendments (including(EU) No 2020/1245). - European Council Resolution ResAP (2004)5. - Directive 84/500/EEC and corresponding amendment 2005/31/EC. - European Council Resolution AP(89)1. - German § 30 and § 31 LFGB. (Lebensmittel-, Bedarfsgegenstände- und Futtermittelgesetzbuch)	Please refer to next page(s).
Specific Migration of Phthalates according to customer's requirement.	Please refer to next page(s).
Total Phthalates Content according to customer's requirement.	PASS
Total Cadmium Content according to Entry 23 of Annex XVII to Regulation (EC) No 1907/2006 and its amendments Regulation (EC) No 552/2009, (EU) No 494/2011, (EU) No 835/2012 and (EU) No 2016/217.	PASS
Total Lead Content according to Entry 63 of Annex XVII to Regulation (EC) No 1907/2006 and its amendments Regulation (EU) No 836/2012 and (EU) No 2015/628.	PASS

The above sample(s) and sample information was/were submitted and identified on behalf of the applicant. Eurofins will not be liable for the authenticity of the information. This test report is valid for the tested sample only. Without permission of the test center this test report is not permitted to be duplicated in extracts. This test report does not entitle to carry any safety mark on this or similar products.
Unless otherwise required by the applicant or method/regulation, decision rule in this report did not consider the measurement uncertainty.

***** FOR FURTHER DETAILS, PLEASE REFER TO THE FOLLOWING PAGE(S) *****

SIGNED FOR AND ON BEHALF OF
EUROFINS TESTING TECHNOLOGY (SHENZHEN) CO., LTD.




Harry Chen
Senior R&D Manager



Coco Luo
Senior Lab Manager



TESTED SAMPLE PHOTO(S)

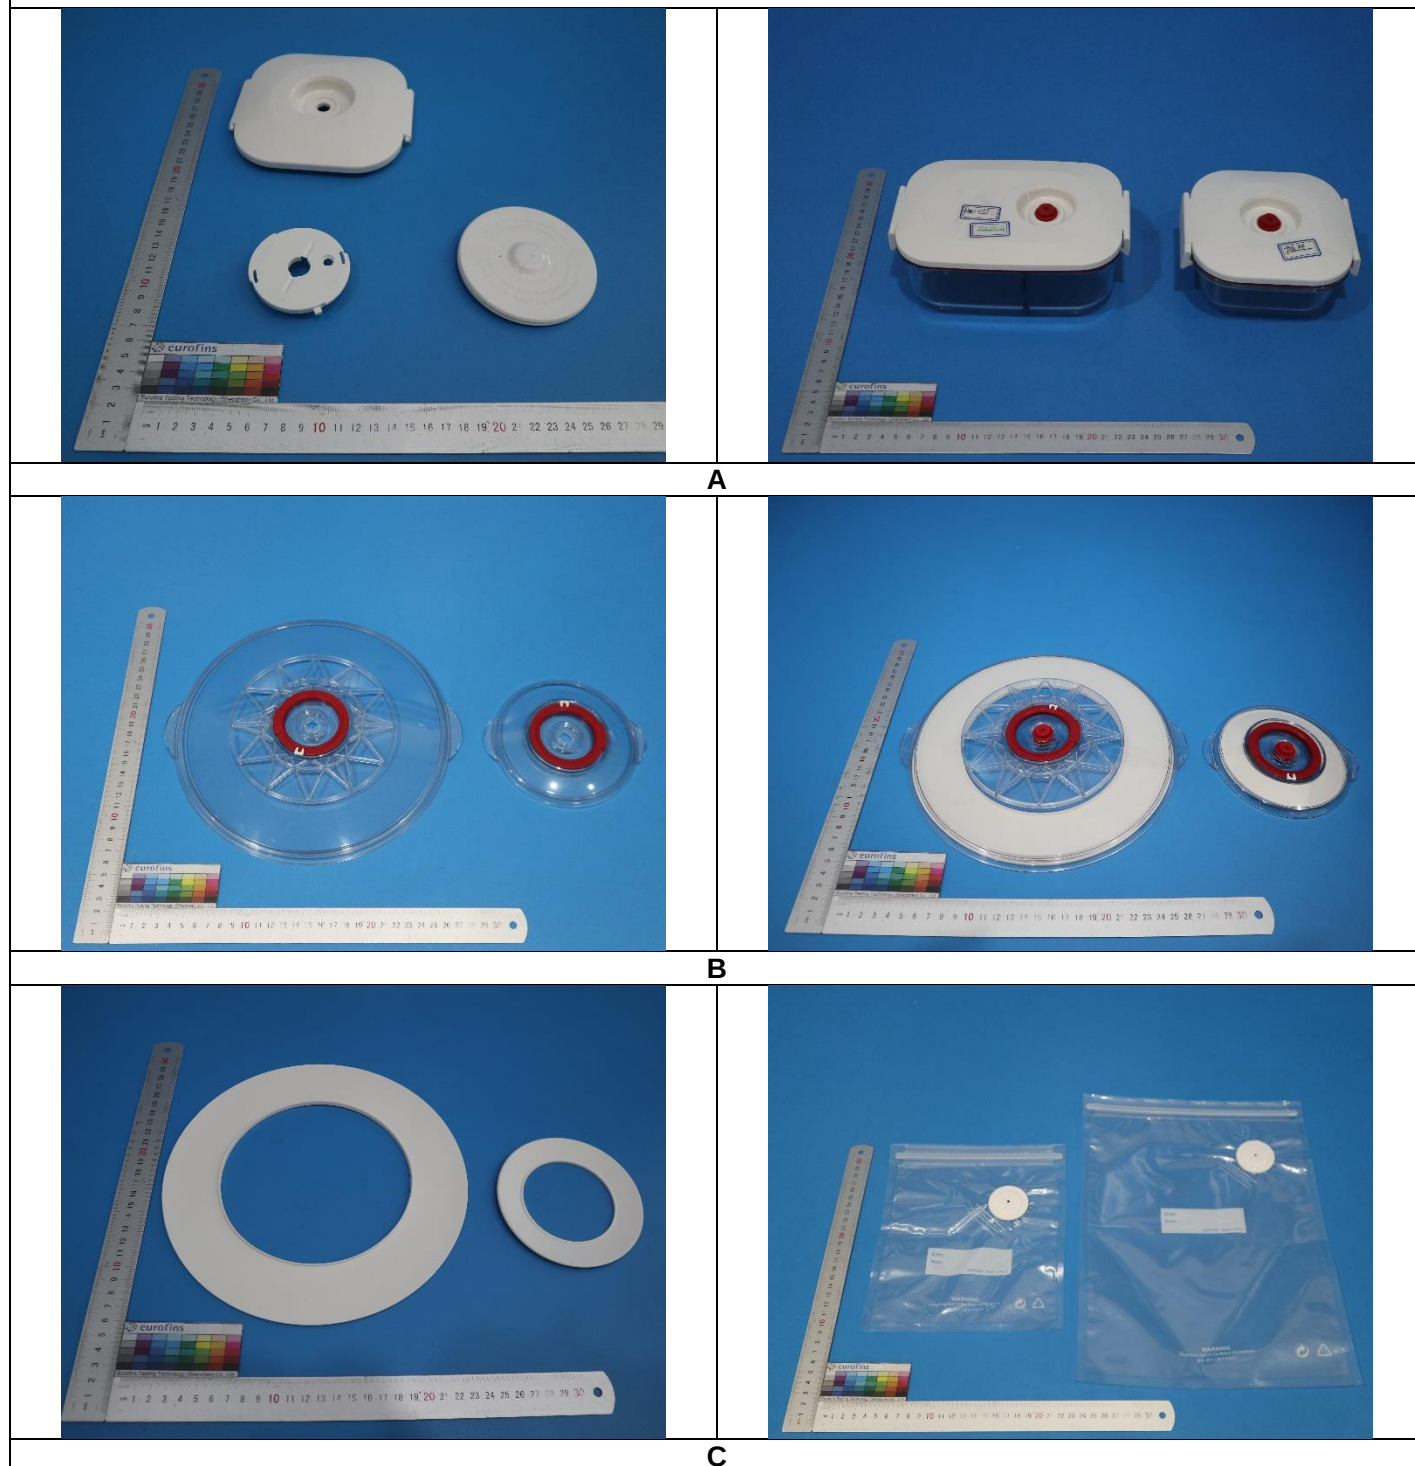


EFSN22111091-C-0102

TO BE CONTINUED

Eurofins Testing Technology (Shenzhen) Co., Ltd.

4/F., Building 3, Building 2, Runheng Electronic Park, Liuxian 2nd Road, Xin'an Street, Bao'an District, Shenzhen, Guangdong, China
Tel.: +86 755 8358 5700 • Fax: +86 755 8358 5701 • Email: info.hk@eurofins.com • Website: www.eurofins.com / www.pt.eurofins.com

TESTED SAMPLE PHOTO(S)

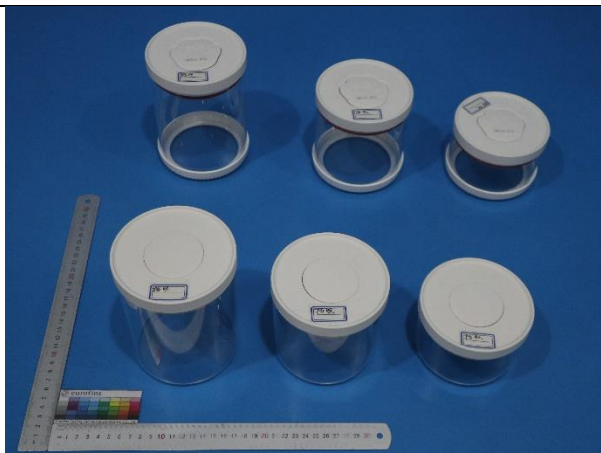

D

EFSN22111091-C-0102

TO BE CONTINUED

Eurofins Testing Technology (Shenzhen) Co., Ltd.

4/F., Building 3, Building 2, Runheng Electronic Park, Liuxian 2nd Road, Xin'an Street, Bao'an District, Shenzhen, Guangdong, China
 Tel.: +86 755 8358 5700 • Fax: +86 755 8358 5701 • Email: info.hk@eurofins.com • Website: www.eurofins.com / www.pt.eurofins.com

COMPONENT LIST

- A Vacuum Container
 B Lid
 C Bag
 D Airtight Container

Component No.	Component	Material	Color	Sample No.
1	Lid of Vacuum Container and inner lid of Airtight Container	ABS	Off-white	A
2	Vacuum Container	AS	Transparent	A
3	Lid	ABS	Transparent	B
3a	Lid-2 nd submission	ABS	Transparent	B
5	Vacuum valve of bag	PE	Snow white	C
6	Seal ring of Vacuum Container, Lid and Airtight Container	Silicone	Red	A/B
7	Seal ring of Lid	Silicone	White	B
8	Seal ring of Airtight Container	Silicone	Grey	D
8a	Seal ring of Airtight Container-2 nd submission	Silicone	Grey	D
9	Silicone of Airtight Container	Silicone	Translucent	D
9a	Silicone of Airtight Container-2 nd submission	Silicone	Translucent	D
10	Airtight Container	Glass	Transparent	D
11	Whole product(Small Vacuum Container)	-	-	A
12	Whole product(Lid)	-	-	B
13	Whole product(Bag)	-	-	C
14	Whole product(Big Airtight Container with base)	-	-	D
15	Inner of bag	PE	Transparent	C

TO BE CONTINUED

TEST RESULT

Sensorial Examination

It is examined to what extent food simulant, which comes into contact with the product, undergoes detectable changes in taste and smell. For this purpose the food simulant is stored in the product for the below mentioned time and temperature. After this time the food simulant is examined by an appropriate number of tasters with regard to any divergence in smell and taste. Another test sample, which is used as a reference, is treated the same way except that it has no contact with the product to be tested.

Before testing, the product has been cleaned three times with hot water (60°C).

The test is carried out on the basis of DIN 10955:2004.

Assessment intensity scale for the transfer of taste and smell:

0 = no discernible deviation

1 = barely discernible deviation

2 = weak deviation

3 = clear deviation

4 = strong deviation

Limit : 3

Test condition :

Food simulant	Test duration/temperature
Distilled water	10 days / 40°C

Testing Material No.	11	12	13	14
Parameter	Test result	Test result	Test result	Test result
Smell	0	0	0	0
Taste	0	0	0	0

Note: - The submitted product is inconspicuous with regard to the transfer of smell and taste bearing substances to the used food simulant(s).

TO BE CONTINUED

TEST RESULT

Overall Migration

The migratory behaviour is examined in accordance with the Regulation (EU) No 10/2011 and its amendments.

Test condition :

Food simulant	Test duration/temperature
3% Acetic acid	10 days / 40°C
10% Ethanol	10 days / 40°C
Isooctane	2 days / 20°C
95% Ethanol	10 days / 40°C

Testing Material No.		1			Detection limit	Limit
Parameter	Unit	Test result				
		Trial I	Trial II	Trial III		
3% Acetic acid	mg/dm ²	N.D.	N.D.	N.D.	2	10
10% Ethanol	mg/dm ²	N.D.	N.D.	N.D.	2	10
Isooctane	mg/dm ²	N.D.	N.D.	N.D.	3	10
95% Ethanol	mg/dm ²	N.D.	N.D.	N.D.	3	10

Testing Material No.		2			Detection limit	Limit
Parameter	Unit	Test result				
		Trial I	Trial II	Trial III		
3% Acetic acid	mg/dm ²	N.D.	N.D.	N.D.	2	10
10% Ethanol	mg/dm ²	N.D.	N.D.	N.D.	2	10
Isooctane	mg/dm ²	N.D.	N.D.	N.D.	3	10
95% Ethanol	mg/dm ²	N.D.	N.D.	N.D.	3	10

Testing Material No.		3		
Parameter	Unit	Test result		
		Trial I	Trial II	Trial III
3% Acetic acid	mg/article	<2	<2	<2
10% Ethanol	mg/article	<2	<2	<2
Isooctane	mg/article	<3	<3	<3
95% Ethanol	mg/article	484(*)	176(*)	33(*)

Testing Material No.		5			Detection limit	Limit
Parameter	Unit	Test result				
		Trial I	Trial II	Trial III		
3% Acetic acid	mg/dm ²	N.D.	N.D.	N.D.	2	10
10% Ethanol	mg/dm ²	N.D.	N.D.	N.D.	2	10
Isooctane	mg/dm ²	N.D.	N.D.	N.D.	3	10
95% Ethanol	mg/dm ²	13	N.D.	N.D.	3	10

TO BE CONTINUED

TEST RESULT

Testing Material No.		15			Detection limit	Limit
Parameter	Unit	Test result				
		Trial I	Trial II	Trial III		
3% Acetic acid	mg/dm ²	N.D.	N.D.	N.D.	2	10
10% Ethanol	mg/dm ²	N.D.	N.D.	N.D.	2	10
Isooctane	mg/dm ²	N.D.	N.D.	N.D.	3	10
95% Ethanol	mg/dm ²	N.D.	N.D.	N.D.	3	10

Food simulant	Test duration/temperature
3% Acetic acid	10 days / 40°C
10% Ethanol	10 days / 40°C
Rectified olive oil	10 days / 40°C

Testing Material No.		6			Detection limit	Limit
Parameter	Unit	Test result				
		Trial I	Trial II	Trial III		
3% Acetic acid	mg/dm ²	N.D.	N.D.	N.D.	2	10
10% Ethanol	mg/dm ²	N.D.	N.D.	N.D.	2	10
Rectified olive oil	mg/dm ²	N.D.	N.D.	N.D.	3	10

Testing Material No.		7		
Parameter	Unit	Test result		
		Trial I	Trial II	Trial III
3% Acetic acid	mg/article	<2	<2	<2
10% Ethanol	mg/article	<2	<2	<2
Rectified olive oil	mg/article	110	227	291

Testing Material No.		8			Detection limit	Limit
Parameter	Unit	Test result				
		Trial I	Trial II	Trial III		
3% Acetic acid	mg/dm ²	N.D.	N.D.	N.D.	2	10
10% Ethanol	mg/dm ²	N.D.	N.D.	N.D.	2	10
Rectified olive oil	mg/dm ²	N.D.	N.D.	N.D.	3	10

Testing Material No.		9			Detection limit	Limit
Parameter	Unit	Test result				
		Trial I	Trial II	Trial III		
3% Acetic acid	mg/dm ²	N.D.	N.D.	N.D.	2	10
10% Ethanol	mg/dm ²	N.D.	N.D.	N.D.	2	10
Rectified olive oil	mg/dm ²	N.D.	N.D.	N.D.	3	10

TO BE CONTINUED

TEST RESULT

Note: - mg/dm² = milligram per square decimetre

- °C = degree Celsius

- N.D. = Not Detected

- *. The tested sample becomes white.

- According to the Regulation (EU) No 10/2011 and its amendments, synthetic material with contact to food may not transfer more than 10 mg/dm² of substance (Overall Migration).

- According to European Council Resolution ResAP (2004)5, silicones material with contact to food may not transfer more than 10 mg/dm² of substance (Overall Migration).

TO BE CONTINUED

Eurofins Testing Technology (Shenzhen) Co., Ltd.

4/F., Building 3, Building 2, Runheng Electronic Park, Liuxian 2nd Road, Xin'an Street, Bao'an District, Shenzhen, Guangdong, China
Tel.: +86 755 8358 5700 • Fax: +86 755 8358 5701 • Email: info.hk@eurofins.com • Website: www.eurofins.com / www.pt.eurofins.com

TEST RESULT

Specific Migration of Heavy Metals

Test method : The concentration of the following elements is examined by means of inductively coupled plasma mass spectroscopy.

Limit according to Regulation (EU) No 10/2011 and its amendments.

Test condition :

Food simulant	Test duration/temperature
3% Acetic acid	10 days / 40°C

Testing Material No.		1			Detection limit	Limit
Parameter	Unit	Test result				
		Trial I	Trial II	Trial III		
Barium (Ba)	mg/kg	N.D.	N.D.	N.D.	0.1	1
Cobalt (Co)	mg/kg	N.D.	N.D.	N.D.	0.01	0.05
Copper (Cu)	mg/kg	N.D.	N.D.	N.D.	0.1	5
Iron (Fe)	mg/kg	N.D.	N.D.	N.D.	1	48
Lithium (Li)	mg/kg	N.D.	N.D.	N.D.	0.1	0.6
Manganese (Mn)	mg/kg	N.D.	N.D.	N.D.	0.1	0.6
Zinc (Zn)	mg/kg	N.D.	N.D.	N.D.	1	5
Aluminum (Al)	mg/kg	N.D.	N.D.	N.D.	0.1	1
Nickel (Ni)	mg/kg	N.D.	N.D.	N.D.	0.01	0.02
Arsenic (As)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Antimony (Sb)	mg/kg	N.D.	N.D.	N.D.	0.01	0.04
Cadmium (Cd)	mg/kg	N.D.	N.D.	N.D.	0.002	N.D
Chromium (Cr)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Europium (Eu)	mg/kg	N.D.	N.D.	N.D.	0.01	0.05
Gadolinium (Gd)	mg/kg	N.D.	N.D.	N.D.	0.01	
Lanthanum (La)	mg/kg	N.D.	N.D.	N.D.	0.01	
Terbium (Tb)	mg/kg	N.D.	N.D.	N.D.	0.01	
Lead (Pb)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Mercury (Hg)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D

TO BE CONTINUED

Eurofins Testing Technology (Shenzhen) Co., Ltd.

4/F., Building 3, Building 2, Runheng Electronic Park, Liuxian 2nd Road, Xin'an Street, Bao'an District, Shenzhen, Guangdong, China
Tel.: +86 755 8358 5700 • Fax: +86 755 8358 5701 • Email: info.hk@eurofins.com • Website: www.eurofins.com / www.pt.eurofins.com

TEST RESULT

Testing Material No.		2			Detection limit	Limit
Parameter	Unit	Test result				
		Trial I	Trial II	Trial III		
Barium (Ba)	mg/kg	N.D.	N.D.	N.D.	0.1	1
Cobalt (Co)	mg/kg	N.D.	N.D.	N.D.	0.01	0.05
Copper (Cu)	mg/kg	N.D.	N.D.	N.D.	0.1	5
Iron (Fe)	mg/kg	N.D.	N.D.	N.D.	1	48
Lithium (Li)	mg/kg	N.D.	N.D.	N.D.	0.1	0.6
Manganese (Mn)	mg/kg	N.D.	N.D.	N.D.	0.1	0.6
Zinc (Zn)	mg/kg	N.D.	N.D.	N.D.	1	5
Aluminum (Al)	mg/kg	N.D.	N.D.	N.D.	0.1	1
Nickel (Ni)	mg/kg	N.D.	N.D.	N.D.	0.01	0.02
Arsenic (As)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Antimony (Sb)	mg/kg	N.D.	N.D.	N.D.	0.01	0.04
Cadmium (Cd)	mg/kg	N.D.	N.D.	N.D.	0.002	N.D
Chromium (Cr)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Europium (Eu)	mg/kg	N.D.	N.D.	N.D.	0.01	0.05
Gadolinium (Gd)	mg/kg	N.D.	N.D.	N.D.	0.01	
Lanthanum (La)	mg/kg	N.D.	N.D.	N.D.	0.01	
Terbium (Tb)	mg/kg	N.D.	N.D.	N.D.	0.01	
Lead (Pb)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Mercury (Hg)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D

Testing Material No.		3		
Parameter	Unit	Test result		
		Trial I	Trial II	Trial III
Barium (Ba)	mg/article	<0.1	<0.1	<0.1
Cobalt (Co)	mg/article	<0.01	<0.01	<0.01
Copper (Cu)	mg/article	<0.1	<0.1	<0.1
Iron (Fe)	mg/article	<1	<1	<1
Lithium (Li)	mg/article	<0.1	<0.1	<0.1
Manganese (Mn)	mg/article	<0.1	<0.1	<0.1
Zinc (Zn)	mg/article	<1	<1	<1
Aluminum (Al)	mg/article	<0.1	<0.1	<0.1
Nickel (Ni)	mg/article	<0.01	<0.01	<0.01
Arsenic (As)	mg/article	<0.01	<0.01	<0.01
Antimony (Sb)	mg/article	<0.01	<0.01	<0.01
Cadmium (Cd)	mg/article	<0.002	<0.002	<0.002
Chromium (Cr)	mg/article	<0.01	<0.01	<0.01
Europium (Eu)	mg/article	<0.01	<0.01	<0.01
Gadolinium (Gd)	mg/article	<0.01	<0.01	<0.01
Lanthanum (La)	mg/article	<0.01	<0.01	<0.01
Terbium (Tb)	mg/article	<0.01	<0.01	<0.01
Lead (Pb)	mg/article	<0.01	<0.01	<0.01
Mercury (Hg)	mg/article	<0.01	<0.01	<0.01

TO BE CONTINUED

Eurofins Testing Technology (Shenzhen) Co., Ltd.

4/F., Building 3, Building 2, Runheng Electronic Park, Liuxian 2nd Road, Xin'an Street, Bao'an District, Shenzhen, Guangdong, China

Tel.: +86 755 8358 5700 • Fax: +86 755 8358 5701 • Email: info.hk@eurofins.com • Website: www.eurofins.com / www.pt.eurofins.com

TEST RESULT

Testing Material No.		5			Detection limit	Limit
Parameter	Unit	Test result				
		Trial I	Trial II	Trial III		
Barium (Ba)	mg/kg	N.D.	N.D.	N.D.	0.1	1
Cobalt (Co)	mg/kg	N.D.	N.D.	N.D.	0.01	0.05
Copper (Cu)	mg/kg	N.D.	N.D.	N.D.	0.1	5
Iron (Fe)	mg/kg	N.D.	N.D.	N.D.	1	48
Lithium (Li)	mg/kg	N.D.	N.D.	N.D.	0.1	0.6
Manganese (Mn)	mg/kg	N.D.	N.D.	N.D.	0.1	0.6
Zinc (Zn)	mg/kg	N.D.	N.D.	N.D.	1	5
Aluminum (Al)	mg/kg	N.D.	N.D.	N.D.	0.1	1
Nickel (Ni)	mg/kg	N.D.	N.D.	N.D.	0.01	0.02
Arsenic (As)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Antimony (Sb)	mg/kg	N.D.	N.D.	N.D.	0.01	0.04
Cadmium (Cd)	mg/kg	N.D.	N.D.	N.D.	0.002	N.D
Chromium (Cr)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Europium (Eu)	mg/kg	N.D.	N.D.	N.D.	0.01	0.05
Gadolinium (Gd)	mg/kg	N.D.	N.D.	N.D.	0.01	
Lanthanum (La)	mg/kg	N.D.	N.D.	N.D.	0.01	
Terbium (Tb)	mg/kg	N.D.	N.D.	N.D.	0.01	
Lead (Pb)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Mercury (Hg)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D

Testing Material No.		15			Detection limit	Limit
Parameter	Unit	Test result				
		Trial I	Trial II	Trial III		
Barium (Ba)	mg/kg	N.D.	N.D.	N.D.	0.1	1
Cobalt (Co)	mg/kg	N.D.	N.D.	N.D.	0.01	0.05
Copper (Cu)	mg/kg	N.D.	N.D.	N.D.	0.1	5
Iron (Fe)	mg/kg	N.D.	N.D.	N.D.	1	48
Lithium (Li)	mg/kg	N.D.	N.D.	N.D.	0.1	0.6
Manganese (Mn)	mg/kg	N.D.	N.D.	N.D.	0.1	0.6
Zinc (Zn)	mg/kg	N.D.	N.D.	N.D.	1	5
Aluminum (Al)	mg/kg	N.D.	N.D.	N.D.	0.1	1
Nickel (Ni)	mg/kg	N.D.	N.D.	N.D.	0.01	0.02
Arsenic (As)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Antimony (Sb)	mg/kg	N.D.	N.D.	N.D.	0.01	0.04
Cadmium (Cd)	mg/kg	N.D.	N.D.	N.D.	0.002	N.D
Chromium (Cr)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Europium (Eu)	mg/kg	N.D.	N.D.	N.D.	0.01	0.05
Gadolinium (Gd)	mg/kg	N.D.	N.D.	N.D.	0.01	
Lanthanum (La)	mg/kg	N.D.	N.D.	N.D.	0.01	
Terbium (Tb)	mg/kg	N.D.	N.D.	N.D.	0.01	
Lead (Pb)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D
Mercury (Hg)	mg/kg	N.D.	N.D.	N.D.	0.01	N.D

Note: - 1 mg/kg = 1 ppm = 0.0001%

- °C = degree Celsius

- N.D. = Not Detected

TO BE CONTINUED

Eurofins Testing Technology (Shenzhen) Co., Ltd.

4/F., Building 3, Building 2, Runheng Electronic Park, Liuxian 2nd Road, Xin'an Street, Bao'an District, Shenzhen, Guangdong, China

Tel.: +86 755 8358 5700 • Fax: +86 755 8358 5701 • Email: info.hk@eurofins.com • Website: www.eurofins.com / www.pt.eurofins.com

TEST RESULT

Specific Migration of Acrylonitrile

Limit according to the Regulation (EU) No 10/2011 and its amendments.

Test condition :

Food simulant	Test duration/temperature
3% Acetic acid	10 days / 40°C

Testing material No.			1			Detection limit	Limit
Parameter	CAS No.	Unit	Test result				
			Trial I	Trial II	Trial III		
Acrylonitrile	107-13-1	mg/kg	N.D.	N.D.	N.D.	0.010	Not detectable

Testing material No.			2			Detection limit	Limit
Parameter	CAS No.	Unit	Test result				
			Trial I	Trial II	Trial III		
Acrylonitrile	107-13-1	mg/kg	N.D.	N.D.	N.D.	0.010	Not detectable

Testing material No.			3		
Parameter	CAS No.	Unit	Test result		
			Trial I	Trial II	Trial III
Acrylonitrile	107-13-1	mg/article	<0.010	<0.010	<0.010

Note: - 1 mg/kg = 1 ppm = 0.0001%

- °C = degree Celsius

- N.D. = Not Detected

TO BE CONTINUED

TEST RESULT

Specific Migration of Butadiene

Limit according to the Regulation (EU) No 10/2011 and its amendments.

Test condition :

Food simulant	Test duration/temperature
3% Acetic acid	10 days / 40°C

Testing Material No.			1			Detection limit	Limit
Parameter	CAS No.	Unit	Test result				
			Trial I	Trial II	Trial III		
Butadiene	106-99-0	mg/kg	N.D.	N.D.	N.D.	0.01	Not Detectable

Testing Material No.			3		
Parameter	CAS No.	Unit	Test result		
			Trial I	Trial II	Trial III
Butadiene	106-99-0	mg/article	<0.01	<0.01	<0.01

Note: - 1 mg/kg = 1 ppm = 0.0001%

- °C = degree Celsius

- N.D. = Not Detected

TO BE CONTINUED

TEST RESULT

Colorfastness

Test method : According to European Council Resolution AP(89)1 , place the four different filter papers on the colored plastic and wait for 5 hours at 50°C.

Limit : Negative – according to European Council Resolution AP(89)1

Test condition :

Food simulant	Test duration/temperature
Distilled water	5 hours / 50°C
3% Acetic acid	5 hours / 50°C
15% Ethanol	5 hours / 50°C
Coco nut oil	5 hours / 50°C

Testing material No.	6	8
Parameter	Test result	Test result
Distilled water	Negative	Negative
3% Acetic acid	Negative	Negative
15% Ethanol	Negative	Negative
Coco nut oil	Negative	Negative

Note: -°C = degree Celsius

- Negative = No visible colour migration
- Positive = Visible colour migration

TO BE CONTINUED

TEST RESULT

Remaining Peroxides

Test method : According to the recommendation of the BfR (German Institute for Risk Assessment) Part VI, III, XV

Testing material No.		1	2	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Peroxides	%(w/w)	N.D.	N.D.	0.01	Not detectable

Testing material No.		3	5	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Peroxides	%(w/w)	N.D.	N.D.	0.01	Not detectable

Testing material No.		6	7	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Peroxides	%(w/w)	N.D.	N.D.	0.01	Not detectable

Testing material No.		8	9	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Peroxides	%(w/w)	N.D.	N.D.	0.01	Not detectable

Testing material No.		15	Detection limit	Limit
Parameter	Unit	Test result		
Peroxides	%(w/w)	N.D.	0.01	Not detectable

Note: - %(w/w) = percentage of weight by weight

- N.D. = Not Detected

- According to the recommendation of the BfR (German Institute for Risk Assessment) Part XV "Silicones" serves as basis for the evaluation of the test results. The finished products must not test positively for peroxides.

- According to the recommendation of the BfR (German Institute for Risk Assessment) Part VI "Styrene Copolymers and Graft Polymers, and Mixtures of Polystyrene with other Polymers (Peroxides)" serves as basis for the evaluation of the test results. The finished products must not test positively for peroxides.

- According to the recommendation of the BfR (German Institute for Risk Assessment) Part III "Polyethylene" serves as basis for the evaluation of the test results. The finished products must not test positively for peroxides.

TO BE CONTINUED

TEST RESULT

Volatile Organic Compounds, silicones

Test method : According to the recommendation of the BfR (German Institute for Risk Assessment) Part XV

Test condition :

test duration/temperature

10 days / 40°C

Testing material No.		6	7	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Volatile Organic Compounds	%	0.40	0.30	0.01	0.5

Test condition :

test duration/temperature

4 hours / 200°C

Testing material No.		8a	9a	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Volatile Organic Compounds	%	0.26	0.38	0.01	0.5

Note: - 1 mg/kg = 1 ppm = 0.0001%

- °C = degree Celsius

- N.D. = Not Detected

- According to the recommendation of the BfR (German Institute for Risk Assessment) Part XV "Silicones" serves as a basis for the evaluation of these results. The silicone elastomeres should not emit more than 0.5 % volatile organic substances.

TO BE CONTINUED

TEST RESULT

Volatile Organic Compounds, ABS

Test method : According to the recommendation of the BfR (German Institute for Risk Assessment) Part VI

Test condition :

test duration/temperature

24 hours / 90°C

Testing material No.		1	3a	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Volatile Organic Compounds	mg/dm ²	8.4	10.60	0.01	15

Note: - mg/dm² = milligram per square decimetre

- °C = degree Celsius

- According to the recommendation of the BfR (German Institute for Risk Assessment) Part VI "Styrene Copolymers and Graft Polymers, and Mixtures of polystyrene with other polymers" serves as basis for the evaluation of the test results. The total emission of volatile organic compounds must not exceed 15mg/dm².

TO BE CONTINUED

TEST RESULT

Extractable substances

Test method : According to the recommendation of the BfR (German Institute for Risk Assessment) Part XV.

Testing material No.		6	7	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Distilled Water	%	0.09	0.10	0.01	0.5
3% Acetic Acid	%	0.10	0.11	0.01	0.5
10% Ethanol	%	0.11	0.10	0.01	0.5

Testing material No.		8	9	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Distilled Water	%	0.10	N.D.	0.01	0.5
3% Acetic Acid	%	0.12	N.D.	0.01	0.5
10% Ethanol	%	0.11	N.D.	0.01	0.5

Note: - 1 mg/kg = 1 ppm = 0.0001%

- N.D. = Not Detected

- According to the recommendation of the BfR (German Institute for Risk Assessment) Part XV "Silicones" serves as a basis for the evaluation of these results. The silicone elastomeres should not release more than 0.5 % extractable substances.

Remaining Catalyst Residue

Test method : According to the recommendation of the BfR (German Institute for Risk Assessment) Part III

Testing Material No.		5	15	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Chromium (Cr)	mg/kg	N.D.	N.D.	5	10
Vanadium (V)	mg/kg	N.D.	N.D.	10	20
Zirconium (Zr)	mg/kg	N.D.	N.D.	10	100
Hafnium (Hf)	mg/kg	N.D.	N.D.	10	100

Note: - 1 mg/kg = 1 ppm = 0.0001%

- N.D. = Not Detected

- Limit according to the recommendation of the BfR (German Institute for Risk Assessment) Part III "Polyethylene."

TO BE CONTINUED

TEST RESULT

Catalyst Residue Pt

Test method : According to the recommendation of the BfR (German Institute for Risk Assessment) Part XV

Testing Material No.		6	7	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Platinum (Pt)	mg/kg	N.D.	N.D.	10	50

Testing Material No.		8	9	Detection limit	Limit
Parameter	Unit	Test result	Test result		
Platinum (Pt)	mg/kg	N.D.	N.D.	10	50

Note: - 1 mg/kg = 1 ppm = 0.0001%

- N.D. = Not Detected

- According to the recommendation of the BfR (German Institute for Risk Assessment) Part XV "Silicones" serves as a basis for the evaluation of these results. The final product must not contain >50mg/kg of platinum.

Butadiene

Test method : Extract with organic solvent, determined by HS-GC-MS.

Limit according to the Regulation (EU) No 10/2011 and its amendments.

Testing material No.			1	3	Detection limit	Limit
Parameter	CAS No.	Unit	Test result	Test result		
Butadiene	106-99-0	mg/kg	N.D.	0.6	0.5	1

Note: - 1 mg/kg = 1 ppm = 0.0001%

- N.D. = Not Detected

TO BE CONTINUED

TEST RESULT

Polycyclic Aromatic Hydrocarbons (PAHs)

Test method : 18 Polycyclic Aromatic Hydrocarbons (PAHs) in polymers according to German GS Specification document: AfPS GS 2014:01 PAK (PAK=PAHs)

Detection limit : 0.10 mg/kg per each PAH.

Limit : See below – Reference limits are quoted from German commission for Product Safety (AfPS) – AfPS GS 2014:01 PAK.

Test No.				PAHs-1	PAHs-2	PAHs-3
Material No.				1	2	3
Parameter	CAS No.	Unit	Limit	Test result	Test result	Test result
Benzo(a)pyrene	50-32-8	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(e)pyrene	192-97-2	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(a)anthracene	56-55-3	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(b)fluoranthene	205-99-2	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(j)fluoranthene	205-82-3	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(k)fluoranthene	207-08-9	mg/kg	0.2	N.D.	N.D.	N.D.
Chrysene	218-01-9	mg/kg	0.2	N.D.	N.D.	N.D.
Dibenzo(a,h)anthracene	53-70-3	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(g,h,i)perylene	191-24-2	mg/kg	0.2	N.D.	N.D.	N.D.
Indeno(1,2,3-cd)pyrene	193-39-5	mg/kg	0.2	N.D.	N.D.	N.D.
Acenaphthene	83-32-9	mg/kg	1	N.D.	N.D.	N.D.
Acenaphthylene	208-96-8					
Fluorene	86-73-7					
Phenanthrene	85-01-8					
Pyrene	129-00-0					
Anthracene	120-12-7					
Fluoranthene	206-44-0					
Naphthalene	91-20-3	mg/kg	1	N.D.	N.D.	N.D.
Sum 18 PAHs	-	mg/kg	1	N.D.	N.D.	N.D.

TO BE CONTINUED

Eurofins Testing Technology (Shenzhen) Co., Ltd.

4/F., Building 3, Building 2, Runheng Electronic Park, Liuxian 2nd Road, Xin'an Street, Bao'an District, Shenzhen, Guangdong, China
Tel.: +86 755 8358 5700 • Fax: +86 755 8358 5701 • Email: info.hk@eurofins.com • Website: www.eurofins.com / www.pt.eurofins.com

TEST RESULT

Test No.				PAHs-4	PAHs-5	PAHs-6
Material No.				5	6	7
Parameter	CAS No.	Unit	Limit	Test result	Test result	Test result
Benzo(a)pyrene	50-32-8	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(e)pyrene	192-97-2	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(a)anthracene	56-55-3	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(b)fluoranthene	205-99-2	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(j)fluoranthene	205-82-3	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(k)fluoranthene	207-08-9	mg/kg	0.2	N.D.	N.D.	N.D.
Chrysene	218-01-9	mg/kg	0.2	N.D.	N.D.	N.D.
Dibenzo(a,h)anthracene	53-70-3	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(g,h,i)perylene	191-24-2	mg/kg	0.2	N.D.	N.D.	N.D.
Indeno(1,2,3-cd)pyrene	193-39-5	mg/kg	0.2	N.D.	N.D.	N.D.
Acenaphthene	83-32-9	mg/kg	1	N.D.	N.D.	N.D.
Acenaphthylene	208-96-8					
Fluorene	86-73-7					
Phenanthrene	85-01-8					
Pyrene	129-00-0					
Anthracene	120-12-7					
Fluoranthene	206-44-0					
Naphthalene	91-20-3	mg/kg	1	N.D.	N.D.	N.D.
Sum 18 PAHs	-	mg/kg	1	N.D.	N.D.	N.D.

Test No.				PAHs-7	PAHs-8	PAHs-9
Material No.				8	9	15
Parameter	CAS No.	Unit	Limit	Test result	Test result	Test result
Benzo(a)pyrene	50-32-8	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(e)pyrene	192-97-2	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(a)anthracene	56-55-3	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(b)fluoranthene	205-99-2	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(j)fluoranthene	205-82-3	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(k)fluoranthene	207-08-9	mg/kg	0.2	N.D.	N.D.	N.D.
Chrysene	218-01-9	mg/kg	0.2	N.D.	N.D.	N.D.
Dibenzo(a,h)anthracene	53-70-3	mg/kg	0.2	N.D.	N.D.	N.D.
Benzo(g,h,i)perylene	191-24-2	mg/kg	0.2	N.D.	N.D.	N.D.
Indeno(1,2,3-cd)pyrene	193-39-5	mg/kg	0.2	N.D.	N.D.	N.D.
Acenaphthene	83-32-9	mg/kg	1	N.D.	N.D.	N.D.
Acenaphthylene	208-96-8					
Fluorene	86-73-7					
Phenanthrene	85-01-8					
Pyrene	129-00-0					
Anthracene	120-12-7					
Fluoranthene	206-44-0					
Naphthalene	91-20-3	mg/kg	1	N.D.	N.D.	N.D.
Sum 18 PAHs	-	mg/kg	1	N.D.	N.D.	N.D.

Note: - 1 mg/kg = 1 ppm = 0.0001%

- N.D. = Not Detected, less than 0.10 mg/kg

TO BE CONTINUED

Eurofins Testing Technology (Shenzhen) Co., Ltd.

4/F., Building 3, Building 2, Runheng Electronic Park, Liuxian 2nd Road, Xin'an Street, Bao'an District, Shenzhen, Guangdong, China

Tel.: +86 755 8358 5700 • Fax: +86 755 8358 5701 • Email: info.hk@eurofins.com • Website: www.eurofins.com / www.pt.eurofins.com

TEST RESULT

Determination of the leachable Lead and Cadmium

Test method : DIN EN 1388-2: 1995.

Testing material No.			10				Detection limit
Parameter	Category ^(^)	Unit	Test result				
			1	2	3	4	
Leachable of Lead content (Pb)	2	mg/L	N.D.	N.D.	N.D.	N.D.	0.1
Leachable of Cadmium content (Cd)	2	mg/L	N.D.	N.D.	N.D.	N.D.	0.01

Remark:

(^) According to Directive 84/500/EEC and corresponding amendment 2005/31/EC, the permissible limit of leachable lead and cadmium content are as follow:

No.	Category	Permissible Limit of Lead and Cadmium extracted	
		Lead (Pb)	Cadmium (Cd)
1.	Articles which cannot be filled and articles which can be filled, the internal depth of which, measured from the lowest point to the horizontal plane passing through the upper rim, does not exceed 25 mm.	0.8mg/dm ²	0.07mg/dm ²
2.	All other articles which can be filled.	4.0mg/L	0.3mg/L
3.	Cooking ware; packaging and storage vessels having a capacity of more than three litres.	1.5mg/L	0.1mg/L

Note: - mg/L = milligram per liter
- mg/dm² = milligram per square decimetre
- N.D. = Not Detected

TO BE CONTINUED

TEST RESULT

Specific Migration of Phthalates

Test method : Sample preparation refers to EN13130-1:2004, determination by GC-MS.

Limit according to customer's requirement.

Test condition :

Food simulant	Test duration/temperature
Rectified olive oil	10 days / 40°C

Testing material No.			1	2	Detection limit	Limit
Parameter	CAS No.	Unit	Test result	Test result		
Diethylhexylphthalate (DEHP)	117-81-7	mg/kg	N.D.	N.D.	0.3	1.5
Dibutylphthalate (DBP)	84-74-2	mg/kg	N.D.	N.D.	0.3	0.3
Diisononylphthalate (DINP)	28553-12-0	mg/kg	N.D.	N.D.	0.3	9
Diisodecylphthalate (DIDP)	26761-40-0	mg/kg	N.D.	N.D.	0.3	
Benzylbutylphthalate (BBP)	85-68-7	mg/kg	N.D.	N.D.	0.3	30
Diallyl phthalate (DAP)	131-17-9	mg/kg	N.D.	N.D.	0.01	N.D.
Di-(2-ethylhexyl) adipate (DEHA)	103-23-1	mg/kg	N.D.	N.D.	2	18

Testing material No.			5	15	Detection limit	Limit
Parameter	CAS No.	Unit	Test result	Test result		
Diethylhexylphthalate (DEHP)	117-81-7	mg/kg	N.D.	N.D.	0.3	1.5
Dibutylphthalate (DBP)	84-74-2	mg/kg	N.D.	N.D.	0.3	0.3
Diisononylphthalate (DINP)	28553-12-0	mg/kg	N.D.	N.D.	0.3	9
Diisodecylphthalate (DIDP)	26761-40-0	mg/kg	N.D.	N.D.	0.3	
Benzylbutylphthalate (BBP)	85-68-7	mg/kg	N.D.	N.D.	0.3	30
Diallyl phthalate (DAP)	131-17-9	mg/kg	N.D.	N.D.	0.01	N.D.
Di-(2-ethylhexyl) adipate (DEHA)	103-23-1	mg/kg	N.D.	N.D.	2	18

Testing material No.			3
Parameter	CAS No.	Unit	Test result
Diethylhexylphthalate (DEHP)	117-81-7	mg/article	<0.3
Dibutylphthalate (DBP)	84-74-2	mg/article	<0.3
Diisononylphthalate (DINP)	28553-12-0	mg/article	<0.3
Diisodecylphthalate (DIDP)	26761-40-0	mg/article	<0.3
Benzylbutylphthalate (BBP)	85-68-7	mg/article	<0.3
Diallyl phthalate (DAP)	131-17-9	mg/article	<0.01
Di-(2-ethylhexyl) adipate (DEHA)	103-23-1	mg/article	<2

Note: - 1 mg/kg = 1 ppm = 0.0001%

- °C = degree Celsius

- N.D. = Not Detected

TO BE CONTINUED

Eurofins Testing Technology (Shenzhen) Co., Ltd.

4/F., Building 3, Building 2, Runheng Electronic Park, Liuxian 2nd Road, Xin'an Street, Bao'an District, Shenzhen, Guangdong, China
Tel.: +86 755 8358 5700 • Fax: +86 755 8358 5701 • Email: info.hk@eurofins.com • Website: www.eurofins.com / www.pt.eurofins.com

TEST RESULT

Total Phthalates Content

Test method : Sample preparation refers to EPA 3540C:1996, determination by GC-MS.

Limit according to customer's requirement.

Detection limit : 0.005% per substance

Testing Material No.			1	2	Limit
Parameter	CAS No.	Unit	Test result	Test result	
Dibutylphthalate (DBP)	84-74-2	%	N.D.	N.D.	0.05
Benzylbutylphthalate (BBP)	85-68-7	%	N.D.	N.D.	0.1
Diethylhexylphthalate (DEHP)	117-81-7	%	N.D.	N.D.	0.1
Diisodecylphthalate (DIDP)	26761-40-0	%	N.D.	N.D.	0.1
Diisononylphthalate (DINP)	28553-12-0	%	N.D.	N.D.	0.1
Diallyl phthalate (DAP)	131-17-9	%	N.D.	N.D.	N.D.
Di-(2-ethylhexyl) adipate (DEHA)	103-23-1	%	N.D.	N.D.	N.D.

Testing Material No.			3	5	Limit
Parameter	CAS No.	Unit	Test result	Test result	
Dibutylphthalate (DBP)	84-74-2	%	N.D.	N.D.	0.05
Benzylbutylphthalate (BBP)	85-68-7	%	N.D.	N.D.	0.1
Diethylhexylphthalate (DEHP)	117-81-7	%	N.D.	N.D.	0.1
Diisodecylphthalate (DIDP)	26761-40-0	%	N.D.	N.D.	0.1
Diisononylphthalate (DINP)	28553-12-0	%	N.D.	N.D.	0.1
Diallyl phthalate (DAP)	131-17-9	%	N.D.	N.D.	N.D.
Di-(2-ethylhexyl) adipate (DEHA)	103-23-1	%	N.D.	N.D.	N.D.

Testing Material No.			15	Limit
Parameter	CAS No.	Unit	Test result	
Dibutylphthalate (DBP)	84-74-2	%	N.D.	0.05
Benzylbutylphthalate (BBP)	85-68-7	%	N.D.	0.1
Diethylhexylphthalate (DEHP)	117-81-7	%	N.D.	0.1
Diisodecylphthalate (DIDP)	26761-40-0	%	N.D.	0.1
Diisononylphthalate (DINP)	28553-12-0	%	N.D.	0.1
Diallyl phthalate (DAP)	131-17-9	%	N.D.	N.D.
Di-(2-ethylhexyl) adipate (DEHA)	103-23-1	%	N.D.	N.D.

Note: - 1 mg/kg = 1 ppm = 0.0001%

- N.D. = Not Detected

TO BE CONTINUED

Eurofins Testing Technology (Shenzhen) Co., Ltd.

4/F., Building 3, Building 2, Runheng Electronic Park, Liuxian 2nd Road, Xin'an Street, Bao'an District, Shenzhen, Guangdong, China
Tel.: +86 755 8358 5700 • Fax: +86 755 8358 5701 • Email: info.hk@eurofins.com • Website: www.eurofins.com / www.pt.eurofins.com

TEST RESULT

Total Cadmium Content(REACH) - Substrate or wet paint

Test Request: Total Cadmium Content according to Entry 23 of Annex XVII to Regulation (EC) No 1907/2006 and its amendments Regulation (EC) No 552/2009, (EU) No 494/2011, (EU) No 835/2012 and (EU) No 2016/217

Test Method: EPA 3052: 1996, EPA 6010D: 2018.

Test Item(s)	Unit	Limit	MDL	Result			
				6	7	8	9
Cadmium(Cd)	mg/kg	100	10	ND	ND	ND	ND

Remark:

- MDL = Method Detection Limit
- 1 mg/kg = 1 ppm = 0.0001%
- ND = Not Detected

Total Lead Content (REACH)

Test Request: Total Lead Content according to Entry 63 of Annex XVII to Regulation (EC) No 1907/2006 and its amendments Regulation (EU) No 836/2012 and (EU) No 2015/628.

Test Method: EPA 3052: 1996, EPA 6010D: 2018.
The sample was digested with acid. Then the lead content was determined by Inductively Coupled Plasma Optical Emission Spectrometry (ICP-OES)

Test Item(s)	Unit	Limit	MDL	Result			
				6	7	8	9
Lead (Pb)	mg/kg	500	10	ND	ND	ND	ND

Remark:

- MDL = Method Detection Limit
- 1 mg/kg = 1 ppm = 0.0001%
- ND = Not Detected

Other Information / Remark:

(1)According to the customer's requirement, the appointed material has been tested.
(2)Food contact area to food simulant (S/V in dm²/ L): Material No. 1 (6.0:1), Material No. 2 (3.9:1), Material No. 5 (6.0:1), Material No. 6 (6.0:1), Material No. 8 (6.0:1), Material No. 9 (6.0:1), Material No. 15 (6.0:1).

END OF THE REPORT

Eurofins Testing Technology (Shenzhen) Co., Ltd.

4/F., Building 3, Building 2, Runheng Electronic Park, Liuxian 2nd Road, Xin'an Street, Bao'an District, Shenzhen, Guangdong, China
Tel.: +86 755 8358 5700 • Fax: +86 755 8358 5701 • Email: info.hk@eurofins.com • Website: www.eurofins.com / www.pt.eurofins.com