

# Energy release rate of the fiber/matrix interface crack in UD composites under transverse loading: ~~effect of the fiber volume fraction and of the distance to the free surface and to non-adjacent debonds~~ ~~debond-debond and debond-free boundary interactions~~

Luca Di Stasio<sup>a,b,1</sup>, Janis Varna<sup>b</sup>, Zoubir Ayadi<sup>a</sup>

<sup>a</sup> *Université de Lorraine, EEIGM, IJL, 6 Rue Bastien Lepage, F-54010 Nancy, France*

<sup>b</sup> *Luleå University of Technology, University Campus, SE-97187 Luleå, Sweden*

---

## Abstract

The effects of crack shielding, finite thickness of the composite and fiber content on fiber/matrix debond growth in thin unidirectional composites are investigated analyzing Representative Volume Elements (RVEs) of different ordered microstructures. Debond growth is characterized by estimation of the Energy Release Rates (ERRs) in Mode I and Mode II using the Virtual Crack Closure Technique (VCCT) and the J-integral. It is found that increasing fiber content, a larger distance between debonds in the loading direction and the presence of a free surface close to the debond have all a strong enhancing effect on the ERR. The presence of fully bonded fibers in the composite thickness direction has instead a constraining effect, and it is shown to be very localized. An explanation of these observations is proposed based on mechanical considerations.

*Keywords:* Polymer-matrix Composites (PMCs), Thin-ply, Energy Release Rate, Debonding, Finite Element Analysis (FEA)

---

## 1. Introduction

Stimulated by the ever more stringent requirements in terms of weight and mechanical performances of the aerospace industry, in recent years the com-

---

<sup>1</sup>Corresponding author: luca.di.stasio@ltu.se .

posite community has returned its attention to the mechanisms of intralam-  
 5 inar crack initiation with a focus on thin-ply laminates. Alternative design  
 approaches are now considered based on this non-conventional laminate in ap-  
 plications ranging from cryogenic pressure vessels [1], to airplanes' wings [2],  
 and even reusable space launchers [3].

*Thin-ply* laminates are the result of a technological innovation, the *spread tow*  
 10 *technology*, which consists in opening or spreading the tows, in which fibers  
 (carbon, glass, aramid, basalt among others) are usually shipped in, into very  
 thin tapes used for laminate production. Ply thicknesses of less than 50  $\mu m$   
 can nowadays be mass-produced, and record thicknesses of around 20 – 25  $\mu m$ ,  
 or  $\sim 4 - 5$  times the average fiber's diameter, have been achieved. In its cur-  
 15 rent form the technique, sometimes referred to as "FUKUI method", was firstly  
 proposed towards the end of the 1990s [4] and perfected in the subsequent  
 decade [5, 6].

Several experimental investigations on *thin ply* laminates have highlighted their  
 main properties [7, 10, 11, 12, 15, 16, 19]: increased fiber content; more uniform  
 20 packing of fibers; delay and even suppression of intralaminar cracking (called  
 also transverse-, matrix- or micro-cracking) and delamination. A very insight-  
 ful work documenting how these phenomena are affected by the morphology of  
*thin-ply* laminates is the microscopic study of Saito & al. [20], which focuses on  
 the effect of ply thickness on the onset and propagation of intralaminar crack-  
 25 ing. In their investigation, tensile tests were performed on carbon fiber/epoxy  
 [0<sub>2</sub>, 90<sub>*n*</sub>, 0<sub>2</sub>] *thin-ply* laminates for  $n = 1, 2, 4$  and the crack density was mea-  
 sured with a digital microscope at several levels of applied tensile strain in the  
 range between 0% and 1.5%. Furthermore, they performed microscopic obser-  
 vations on the specimen's edge at each level of strain. They observed the onset  
 30 of fiber/matrix interface cracks (referred to as debonds in the following) at lower  
 levels of strain in thinner plies, while at the same time coalescence of debonds  
 and through-the-thickness propagation of transverse cracks in thin plies were  
 delayed and even suppressed as ply thickness decreased. In particular, they  
 reported the first onset of debonds at 0.4% for  $n = 1, 2$  and 0.7% for  $n = 4$ . For

35  $n = 1$ , however, at  $\varepsilon = 1.5\%$  coalescence of debonds had started to take place  
 but the crack had not completely propagated through the thickness, while for  
 $n = 2$  and  $n = 4$  the latter already happened at a value of strain respectively  
 of 1.3% and 1%. Our inability to explain these observations with the currently  
 accumulated knowledge demonstrates the necessity of further investigation of  
 40 interactions between debonds and studies of the constraining (or accelerating)  
 effect of presence of bonded fibers, free and constrained boundaries in the vicinity  
 of a partially debonded fiber.

Early studies on the effect of ply thickness on the onset and propagation of  
 transverse cracks were conducted on glass fiber/epoxy cross-ply laminates by  
 45 Bailey, Parvizi and collaborators [21, 22, 23], who firstly observed the beneficial  
 effect of thickness reduction on the delay of transverse cracking. They further-  
 more pointed the attention to the appearance of debonds at the fiber/matrix  
 interface and their subsequent coalescence as the mechanism at the origin of  
 transverse cracks [24]. Moreover, they identified the main mechanical driver of  
 50 the damage process in the mismatch of elastic properties, and particularly of  
 Poisson's ratios, between fibers and matrix [25]. A full understanding of dam-  
 age onset and propagation in *thin-ply* laminates thus requires comprehension  
 of the mechanisms governing its very first stage, i.e. the fiber/matrix interface  
 crack. First results were obtained through analytical models in the case of a  
 55 single fiber with an arc crack (debond) in an infinite matrix under transverse  
 tension by England [26] and Perlman & Sih [27], who obtained the stresses at  
 the interface and calculated the stress intensity factors at the crack tip, and  
 by Toya [28], who evaluated the Energy Release Rate (ERR). Drawing upon  
 the results for the straight bi-material interface crack by Comninou [29], the ef-  
 60 fect of crack face contact in fiber-matrix debonding was investigated in [30, 31].  
 In [32], it was showed in terms of ERR why the case of a single asymmetric  
 debond is more likely to be observed under remote transverse tension than two  
 symmetric debonds on the same fiber. The effect of different types and com-  
 binations of loads on debonding have been studied for the single fiber model:  
 65 compression [33], residual thermal stresses [34], and biaxial configurations with

different combinations of tension and compression [35, 36]. The effect of the presence of nearby bonded fibers on the debonding of a fiber embedded in an infinite matrix has been studied under uniaxial transverse tension [37], biaxial tension [38] and uniaxial transverse compression [39]. The effect of inter-fiber distance on debond growth has been studied for a partially debonded fiber at the center of a hexagonal cluster inside a homogenized UD composite in the case of fully bonded neighbouring fibers [40] and of two partially debonded fibers out of the surrounding six [41]. An understanding of crack shielding and finite ply thickness effects on debond growth in non-homogenized microstructural models of UD seems thus to be lacking: this is the problem that we want to address in the present work. Mode I and Mode II energy release rates will be analyzed using stress fields calculated with the FEM for a variety of Repeating Unit Cell (RUC) of the composite with square packing of fibers under transverse tensile loading. These RUCs represent composites with different distances between partially debonded fibers and a varying number of bonded fibers between them, which allows to study the effect of crack shielding on the ERR. In the ply thickness direction, the varying number of perfectly bonded fiber rows exposes the effect of the proximity of the free boundary of the composite on debond growth. Finally, using coupling of thickness direction displacements on horizontal boundaries of the RUC, the accelerating effect of the interaction between debonds of fibers located on the same vertical line is studied.

## 2. RVE models & FE discretization


### 2.1. Introduction & Nomenclature

In this paper, we analyze debond development in unidirectional (UD) composites subjected to in-plane transverse tensile loading. The interaction between debonds in UD composites is studied developing models of different Repeating Unit Cells (RUC) of laminates (see Fig. 1 to Fig. 3) where only the central fiber in the cell has a damage in the form of a fiber/matrix interface crack (debond). The composite RUC may be repeating in the in-plane transverse


95 direction only (representing an ultra-thin composite) or repeating also in the  
 composite thickness direction, representing an infinite composite in a limiting  
 case. Thus, the conditions at the UD composite's upper and lower bound-  
 aries are one of the parameters for the investigation. The used RUCs allow  
 for considering the composite with debonds as a sequence of stacked damaged  
 100 and undamaged fiber rows, each row with only one fiber in the thickness direc-  
 tion. Since all of these RUCs feature regular microstructures with fibers placed  
 according to a square-packing configuration, they are Representative Volume  
 Elements (RVE) of composites with a certain distribution of debonds. Intro-  
 ducing in-plane coordinates  $x$  and  $y$ , where  $x$  is in the transverse direction of  
 105 the UD composite under consideration, the strain in the  $y$ -direction due to a  
 load in the  $x$ -direction is small, caused in turn by the very small minor Pois-  
 son's ratio of the UD composite. Additionally, debonds are considered to be  
 significantly longer in the fiber direction than in the arc direction. Therefore,  
 we use 2D models under the assumption of plane strain, defined in the  $x - z$   
 110 section of the composite. Thus, the analysis presented applies to long debonds,  
 with a focus on understanding the mechanisms of growth along their arc di-  
 rection. The composites are subjected to transverse tensile strain, applied as  
 a constant displacement in the  $x$ -direction along the vertical boundary of the  
 RUC as shown in Figures 1 to 4. As the models are differentiated by the num-  
 115 ber of rows of fibers and by the spacing between debonds along the vertical and  
 horizontal directions, the corresponding RUCs can be distinguished from each  
 other based on the number  $n$  of fibers in the horizontal direction and  $k$  in the  
 vertical direction. Furthermore, the horizontal surfaces can be either free or  
 vertical displacement coupling can be applied. We thus introduce a common  
 120 notation  $n \times k - free$  and  $n \times k - coupling$  to denote a RUC with  $n \times k$  fibers  
 and, respectively, a free upper surface or with kinematic coupling applied to it.  
 The specific combinations of particular choices of  $n$ ,  $k$ , and boundary conditions  
 are detailed in Section 2.2, together with the description of the corresponding  
 models of damaged composite they are representing.

125 *2.2. Models of Representative Volume Element (RVE)*

The first two models feature, as shown in Fig. 1, an ultra-thin UD laminate with only one row of fibers across its thickness,  $k = 1$ . This is quite an extreme model from the microstructural point of view; however, it allows to focus the analysis on the interaction between debonded fibers placed along the x-direction. Furthermore, as the horizontal surfaces are considered free, the interaction is stronger in this case than in any other, making the trends very clear and the predictions of this model rather conservative. In retrospective, if only 20 years ago such a model would have been considered too abstracted from the physical reality, the recent advancements in the spread tow technology make this approach appealing also as a limiting case for practical considerations.

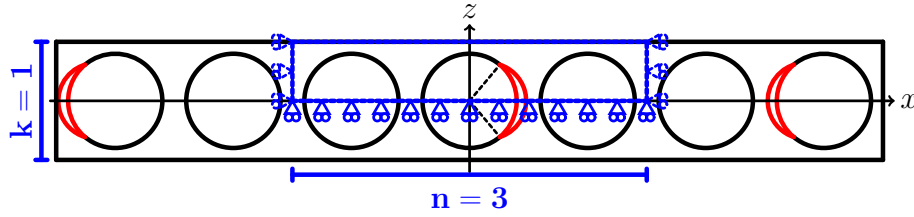

(a) Single row of fibers with a debond appearing every  $n$  fibers: model  $n \times 1 - free$  ( $n = 3$  in the figure).

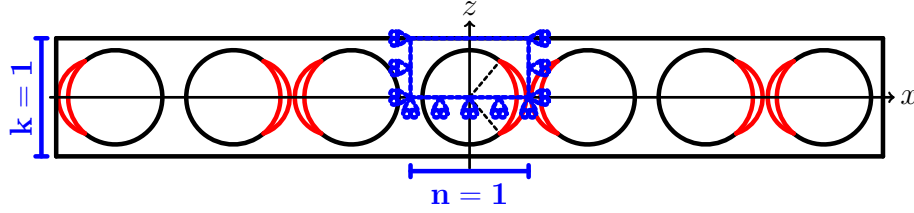


(b) Single row of fibers with debonds appearing on each fiber: model  $1 \times 1 - free$ .


Figure 1: Models of ultra-thin UD composites with a single “row” of fibers and debonds repeating at different distances.

In the sub-model of Fig. 1a, every  $n^{th}$  fiber in the composite is partially debonded on alternating sides of the fiber. The symmetries of the model allow the use of the upper part of the RUC, as highlighted in Fig. 1 to 3. Following the notation introduced in Section 2.1, we will refer to this model as  $n \times 1 - free$ .

140 In the sub-model  $n = 1$ , Fig. 1b, a debond appears on each fiber on alternating sides and the corresponding RUC contains only one fiber. We will refer to this model as  $1 \times 1 - free$ .

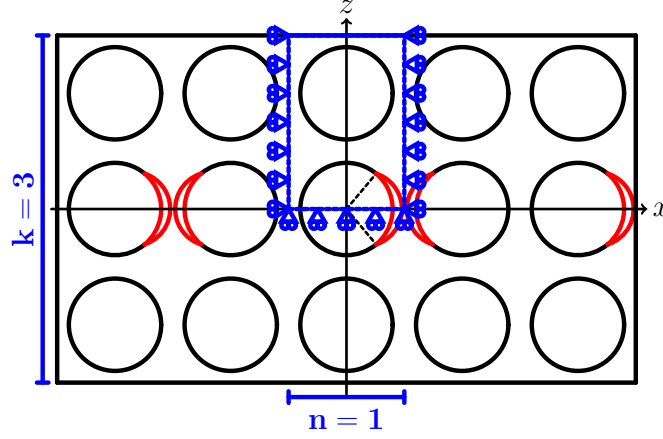

(a) Multiple rows of fibers with debonds appearing on each fiber belonging to the central row: model  $1 \times k - free$  ( $k = 3$  in the figure).

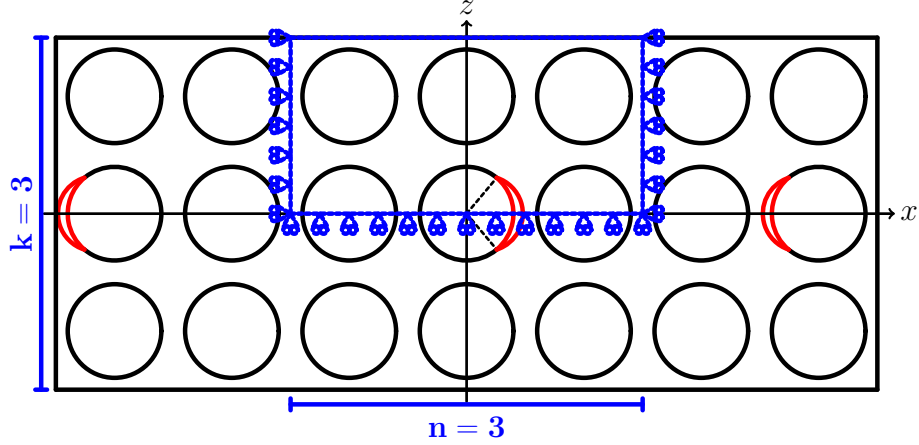

(b) Multiple rows of fibers with a debond appearing every  $n$  fibers within the central row: model  $n \times k - free$  ( $n = 3$  and  $k = 3$  in the figure).

Figure 2: Models of UD composites with different “rows” of fibers and debonds repeating at different distances.

The second set of models in Fig. 2 and Fig. 3 considers laminates with

multiple rows of fibers across the thickness: a finite number of rows in the first  
 145 two sub-models in Fig. 2; an infinite number in the model of Fig. 3. In Fig. 2a,  
 the RUC contains  $n = 1$  fiber in the x-direction,  $k$  fibers across the thickness  
 and the central fiber is debonded. This model will be referred to in the following  
 as  $1 \times k - free$ . Thinking in terms of rows, in this model we have a central row  
 where each fiber is debonded. This row is surrounded from each side by  $(k-1)/2$   
 150 rows with perfectly bonded fibers. In the sub-model in Fig. 2b, each  $n^{th}$  fiber  
 in the central row is debonded and this row is surrounded by  $(k-1)/2$  rows of  
 undamaged fibers from each side. We will refer to this model as  $n \times k - free$   
 (because the horizontal boundary of the RUC is free of any constraint).

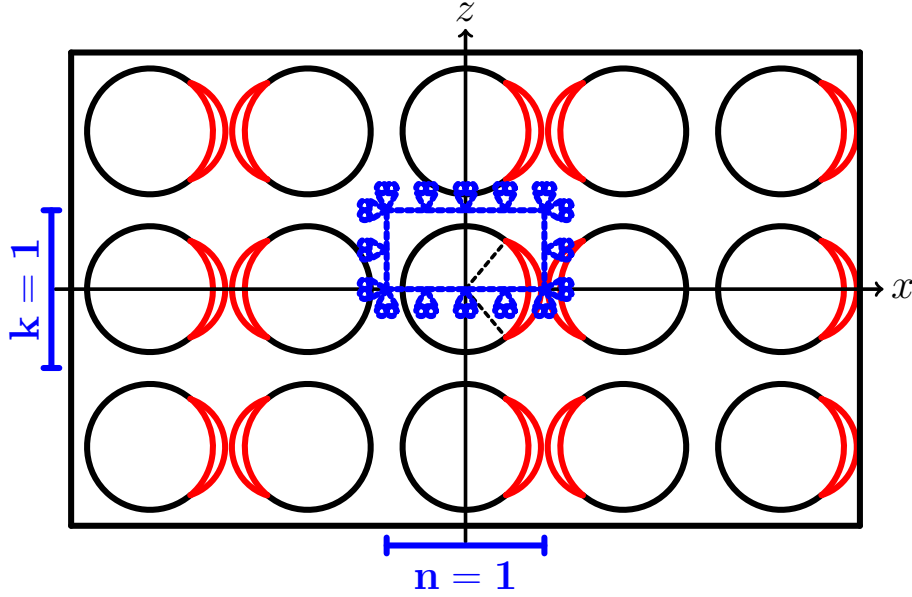


Figure 3: Model of UD composites with an infinite number of “rows” of fibers and debonds appearing on each fiber: model  $1 \times 1 - coupling$ .

Finally, the model in Fig. 3 represents an UD composite with an infinite  
 155 number of rows; all of them with partially debonded fibers. As all fibers have  
 debonds, the corresponding RUC is made of a single partially debonded fiber  
 with kinematic coupling conditions applied to the upper boundary to assure  
 periodicity. This model is referred to as  $1 \times 1 - coupling$ .



### 2.3. Finite Element (FE) discretization

Each RUC is discretized using the Finite Element Method (FEM) within the Abaqus environment, a commercial FEM package [42]. The length  $l$  and height  $h$  of the model are determined by the number of fibers  $n$  in the horizontal direction and  $k$  across the thickness (see 2.2) according to Eq. 1:

$$l = 2nL \quad h = kL; \quad (1)$$

where  $2L$  is the length of a one-fiber unit, see Fig. 4, defined as a function of the fiber volume fraction  $V_f$  and the fiber radius according to

$$L = \frac{R_f}{2} \sqrt{\frac{\pi}{V_f}}. \quad (2)$$

The fiber radius  $R_f$  is assumed to be the same for each fiber in the model and equal to  $1 \mu m$ . The latter value is not physical and it has been chosen for simplicity. It is worth to note at this point that, in a linear elastic solution as the one presented here, the ERR is proportional to the geometrical dimensions and recalculation of the ERR for fibers of any size, thus, requires a simple multiplication. Furthermore, notice that the relationships in Eqs. 1 and 2 ensure that the local and global  $V_f$  are everywhere equal.

The debond is placed symmetrically with respect to the  $x$  axis (see Fig. 4) and we characterize it with an angular size of  $\Delta\theta$  (the full debond size is thus  $2\Delta\theta$ ). For large debond sizes ( $\geq 60^\circ - 80^\circ$ ), a region of variable size  $\Delta\Phi$  appears at the crack tip in which the crack faces are in contact and slide on each other. Due to its appearance, frictionless contact is considered between the two crack faces to allow free sliding and avoid interpenetration. Symmetry with respect to the  $x$  axis is applied on the lower boundary. The upper boundary is in general free, except for the model  $1 \times 1 - coupling$  (Fig. 3) which requires kinematic coupling of vertical displacements also on the upper side. Kinematic coupling on the  $x$ -displacement is applied along the left and right sides of the model in the form of a constant  $x$ -displacement  $\pm \bar{\varepsilon}_x l$ , corresponding to transverse strain  $\bar{\varepsilon}_x$  equal to 1%.



Figure 4: Schematic of the model with its main parameters.

Table 1: Summary of the mechanical properties of fiber and matrix.  $E$  stands for Young's modulus,  $\mu$  for shear modulus and  $\nu$  for Poisson's ratio.

Material	$E$ [GPa]	$\mu$ [GPa]	$\nu$ [-]
Glass fiber	70.0	29.2	0.2
Epoxy	3.5	1.25	0.4

185 The model is meshed using second order, 2D, plane strain triangular (CPE6)  
 and rectangular (CPE8) elements. A regular mesh of quadrilateral elements with  
 an almost unitary aspect ratio is required at the crack tip. The angular size  $\delta$  of  
 an element in the crack tip region is always equal to  $0.05^\circ$ . The crack faces are  
 modeled as element-based surfaces and a small-sliding contact pair interaction  
 190 with no friction is established between them. The Mode I, Mode II and total  
 Energy Release Rates (ERRs) (respectively referred to as  $G_I$ ,  $G_{II}$  and  $G_{TOT}$ )  
 represent the main output of the FEM analysis; they are evaluated using the  
 VCCT [43] implemented in a custom Python routine and, for the total ERR, the  
 J-integral [44] is obtained by application of the Abaqus built-in functionality. A  
 195 glass fiber-epoxy system is considered throughout this paper, and it is assumed  
 that their response lies always in the linear elastic domain. The properties used

are listed in Table 1.

#### 2.4. Validation of the model

The model is validated in Fig. 5 against the results reported in [45, 37],  
 200 obtained with the Boundary Element Method (BEM) for a single fiber with a  
 symmetric debond placed in an infinite matrix. This situation is modeled using  
 the  $1 \times 1 - free$  RVE with  $V_f = 0.0079\%$ , which corresponds to a RUC's length  
 and height of respectively  $\sim 200R_f$  and  $\sim 100R_f$ .



Figure 5: Validation of the single fiber model for the infinite matrix case with respect to the BEM solution in [37].

To allow for a comparison, the results are normalized following [37] with  
 205 respect to a reference Energy Release Rate  $G_0$  defined as

$$G_0 = \frac{1 + k_m}{8\mu_m} \sigma_0^2 \pi R_f \quad (3)$$


where  $\mu$  is the shear modulus,  $k$  is the Kolosov's constant defined as  $3 - 4\nu$  for plane strain conditions,  $R_f$  is the fiber radius and the index  $m$  refers to the properties of the matrix.  $\sigma_0$  is the stress at the boundary, computed as the average of the stress extracted at each boundary node along the right side (arithmetic average as nodes are equispaced by design along both the left and right sides). The agreement is good: the difference between the BEM solution, which is considered more accurate, and the FEM solution does not exceed 5%. The ERRs' maxima are in the same positions and the size of the contact zone is the same. Nevertheless, an analysis of phenomena leading to less than 5% differences in ERR would not be reliable and, therefore, it is not recommended.

### 3. Results & Discussion


#### 3.1. Effect of Fiber Volume Fraction

As shown in Figs. 6 and 7, respectively for Mode I and Mode II, the fiber content has a drastic effect on the Energy Release Rate at the tip of the fiber/matrix interface crack. The effect of four levels of fiber volume fraction are compared, 30%, 50%, 60% and 65%, on two microstructural models: a  $11 \times 11$  - *free* (every  $11^{th}$  fiber in the central fiber row is partially debonded and, on the top of this row, we have 5 undamaged fiber rows), Figs. 6a and 7a, and a  $21 \times 21$  - *free* (every  $21^{th}$  fiber in the central fiber row is partially debonded and, on the top of this row, we have 10 undamaged fiber rows), Figs. 6b and 7b.

Comparing Fig. 6a with 6b, and Fig. 7a with 7b, we can observe that the ERRs' values are very similar for RUCs with  $11 \times 11$  and  $21 \times 21$  fibers, though they are slightly higher for the larger RUC where the next debonded fiber and the free surface are further away from the debonded fiber. From these results we conclude that both RUCs are large enough to represent a single debonded fiber in an infinite array of bonded fibers. Obviously, there exists a specific effect of the fiber content. For Mode I, Fig. 6, the maximum value of the ERR increases by  $\sim 5.2$  times when  $V_f$  changes from 30% to 65%. The debond's angular size for which the peak value occurs remains unchanged at  $20^\circ$ , but for  $V_f = 60\%$

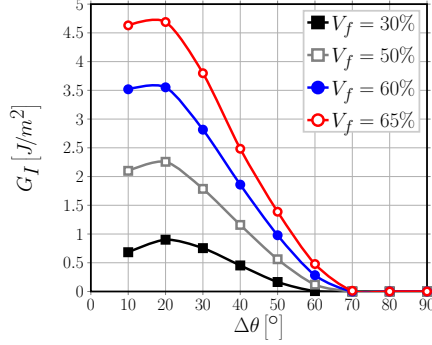


(a) Model  $11 \times 11$  – *free*.

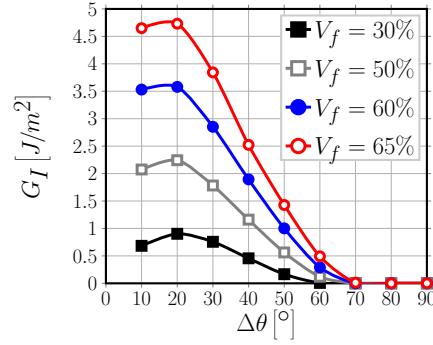


(b) Model  $21 \times 21$  – *free*.

Figure 6: A view of the effect of fiber volume fraction on Mode I ERR in two exemplificative models, subject to an applied transverse strain  $\varepsilon_x$  of 1%.

and 65% the values of Mode I ERR are rather similar when measured at  $10^\circ$  and at  $20^\circ$ , approximately creating a plateau. Furthermore, increasing the fiber volume fraction delays the onset of the contact zone, which corresponds in Fig. 6 to the first value of  $\Delta\theta$  for which  $G_I$  is equal to zero. For  $V_f = 30\%$ , the contact zone first appears for a debond of  $60^\circ$ , similarly to what happens in the single fiber in infinite matrix model (Fig. 5). For higher fiber contents, the contact zone's onset is delayed to a debond's size approximately equal to  $70^\circ$ .

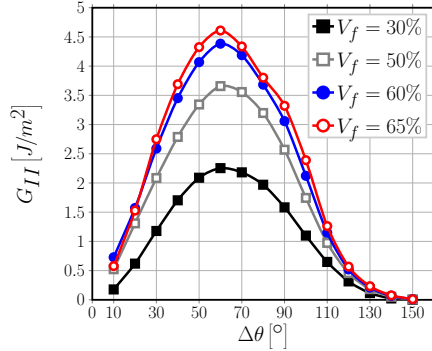

(a) Model  $11 \times 11$  – *free*.

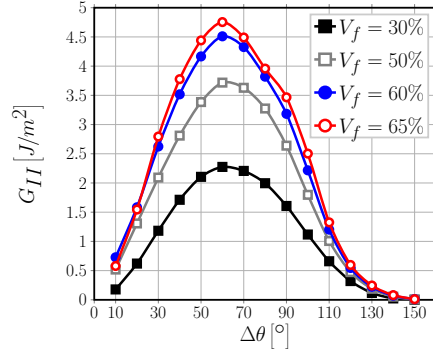

(b) Model  $21 \times 21$  – *free*.

Figure 7: A view of the effect of fiber volume fraction on Mode II ERR in two exemplificative models, subject to an applied transverse strain  $\varepsilon_x$  of 1%.

For Mode II, Fig. 7, there is a distinct maximum in the curve and its shape does not depend on the fiber content. The maximum value of the ERR increases by  $\sim 2.1$  times when  $V_f$  changes from 30% to 65%. The effect is thus similar to Mode I, but with a significantly lower magnitude. Similar to Mode I, the debond's size for which the peak value of Mode II occurs remains unchanged, at  $60^\circ$ . It is worthwhile to notice that the ratio of Mode II to Mode I peak values is  $\frac{\max(G_{II})}{\max(G_I)} \sim \frac{2.2}{0.9} \sim 2.4$  for  $V_f = 30\%$ , while it is  $\sim \frac{4.7}{4.7} \sim 1$  for  $V_f = 65\%$ . The general increasing trends observed in Figs. 6 and 7 are related to the fact that, given that the global and local  $V_f$  are everywhere identical in the models presented, an increase in fiber content corresponds to a decrease in the average distance between fibers. Thus, the distances for the decay of the local stress and strain fields in the matrix domain become shorter, leading to higher stresses in general and causing higher values at the crack tip. The difference in relative magnitude between Mode I and Mode II and the delay in the contact zone's onset are instead due to the interplay between two different mechanisms, both caused by the ordered microstructural arrangement of the model. In the models considered, a fully bonded fiber is always placed along the horizontal direction, aligned with the partially debonded fiber and exactly in front of the debond. By increasing  $V_f$ , the former moves closer to the latter and for small debonds this causes a magnification of the  $x$ -strain at the crack tip. For small debonds ( $\leq 20^\circ - 30^\circ$ ) in fact, the crack tip is approximately normal to the  $x$ -direction and thus an increase in  $\varepsilon_x$  causes an increase in  $G_I$ . On the other hand, for large debonds ( $\geq 70^\circ - 80^\circ$ ) the crack growth direction is almost aligned with the  $x$ -axis, thus a magnification in the  $x$ -strain translates into an increase of Mode II ERR. However, this increasing effect on  $G_{II}$  is partially counteracted by the presence of a fully bonded fiber on top of the debonded fiber and aligned with it. As fibers are more rigid than the surrounding matrix, the presence of the former will restrain horizontal displacements, thus hampering strong increases in  $G_{II}$  for large debonds. Furthermore, due to the mismatch in the Poisson's ratios, the fully bonded fiber placed above generates an upward-directed component of the vertical displacement field in the matrix, which tends to open the debond

and causes the delay in the contact zone's onset. The interplay between these mechanisms is governed by the average inter-fiber distance and, in turn, by the fiber volume fraction.

These observations are in agreement with the results reported in [37], where the effect on the ERR of a partially debonded fiber of two fully bonded nearby fibers, placed symmetrically with respect to the loading direction, is studied for different angular positions (denoted as  $\theta_2$ ) and radial distances in a model with an effectively infinite matrix ( $V_f \sim 0.09\%$ ). The effect of the former is studied for a constant value of the radial distance between the debonded and bonded fibers, which corresponds to a local  $V_f^{local}$  of  $\sim 62\%$  assuming hexagonal packing. They report an increase in both Mode I and Mode II ERR with respect to the single fiber case when the two fibers are placed at an angle of respectively  $\pm 25^\circ, \pm 30^\circ, \pm 140^\circ, \pm 150^\circ, \pm 155^\circ$ , i.e. closest to the loading direction. Notice that for  $\pm 25^\circ$  and  $\pm 155^\circ$  the two fully bonded fibers are almost in contact, with an inter-fiber distance of  $\sim 0.04$  times their radius. This result confirms the considerations made in the previous paragraph about the  $x$ -strain magnification caused by the presence of fully bonded fibers along the loading direction. The effect is further analyzed and discussed in Sec. 3.2 and Sec. 3.4. In the range  $\pm 40^\circ - \pm 130^\circ$  instead, the presence of the other fibers causes a reduction of the ERR and, particularly in the range  $80^\circ - 120^\circ$ , results are very close and almost insensitive to variations in  $\theta_2$ , which supports the previous conclusion about the effect of a fully bonded fiber on top the partially debonded one. This effect is treated in more detail in Sec. 3.3.

Comparing the results from [37] with those presented in this paper, an hypothesis can be furthermore formulated about the robustness of the results of the present article with respect to deviations in fiber position: it seems reasonable to assume a tolerance to deviations of max.  $\pm 30^\circ$  with respect to the loading direction and of max.  $\pm 20^\circ$  with respect to the through-the-thickness direction. The effect of the local fiber content is also investigated in [37], by changing the radial distance between the partially debonded fiber and the fully bonded ones. They observe that the further the fully bonded fibers are placed from the

central one, i.e. the lower the local  $V_f$ , the lower is their effect on the ERR.

305 The magnitude of the effect is however small: the maximum increase of the total ERR is of  $\sim 1.15$  times for  $\theta_2 = 30^\circ$  and  $150^\circ$  when increasing  $V_f^{local}$  from 28% to 62%; the total ERR decreases by a factor of  $\sim 0.62$  for  $\theta_2 = 60^\circ$ ,  $\sim 0.74$  for  $\theta_2 = 90^\circ$  and  $\sim 0.5$  for  $\theta_2 = 120^\circ$  when increasing  $V_f^{local}$  from 28% to 62%. Analogous results can be found in [40], where the authors consider

310 a centrally-placed partially debonded fiber sorrounded by an hexagonal cluster inside an homogenized UD composite. They observe a reduction in the ERR when the local fiber volume fraction is increased, i.e. when the spacing between fibers is reduced. The strongest change is reported for Mode II, which decreases by a factor of  $\sim 0.73$  when the local fiber volume fraction is decreased from

315 66% to 78%. Thus, the trends presented in [37, 40] are in agreement with our results on the effect of  $V_f$  and support the considerations made so far. The stark difference in magnitude however highlights the contrast between the effect of the local fiber volume fraction of a cluster of fibers inside an infinite medium and of the global  $V_f$  of long-range microstructural arrangements, such

320 the ones considered in this article. The similarity in trends with the concurrent difference in magnitudes can be explained in relation to the characteristics of the elastic solution computed. In the first case the local fiber volume fraction controls the distance, with respect to the central partially debonded fiber, at which a localized perturbation zone appears in the far-field elastic solution; in

325 the second case the global  $V_f$  determines the characteristic lengths of a global periodic solution.

### 3.2. Interaction between debonds in UD composites with a single row of fibers

The interaction of debonds appearing at regular intervals in an ultra-thin UD composite with a single row of fibers is studied for Mode I (Fig. 8) and Mode

330 II (Fig. 9) and fiber content equal to 30% (Figs. 8a and 9a) and 60% (Figs. 8b and 9b). The models treated are  $3 \times 1 - free$ ,  $5 \times 1 - free$ ,  $7 \times 1 - free$ ,  $11 \times 1 - free$ ,  $21 \times 1 - free$ ,  $101 \times 1 - free$  and  $201 \times 1 - free$ , corresponding respectively to a debond every  $3^{rd}$ ,  $5^{th}$ ,  $7^{th}$ ,  $11^{th}$ ,  $21^{st}$ ,  $101^{st}$  and  $201^{st}$  fiber



(Fig. 1a). Given that the upper surface of the UD row is left free, the interaction  
 335 with the debonded fiber in the next RUC is stronger than in any other case and  
 the results of this section are thus the most conservative in terms of debond's  
 growth: the ERRs should be the largest. The effect is enhanced in composites  
 with high  $V_f$  and especially for  $G_{II}$ : at  $V_f = 60\%$  the highest  $G_{II}$  value for the  
 $201 \times 1 - free$  composite in Fig. 9b is more than 3 times higher than the  $G_{II}$   
 340 value value for the  $21 \times 21 - free$  composite in Fig. 7b. Even the maximum is  
 shifted to larger angles. The  $G_I$  value is for some cases only 30% higher.  
 From both Fig. 8 and Fig. 9, it can be seen that the presence of a debond close  
 to the analyzed debond decreases the strain magnification effect discussed in  
 Sec. 3.1 and thus reduces the value of the ERR. This phenomenon is called  
 345 “crack shielding” [32].

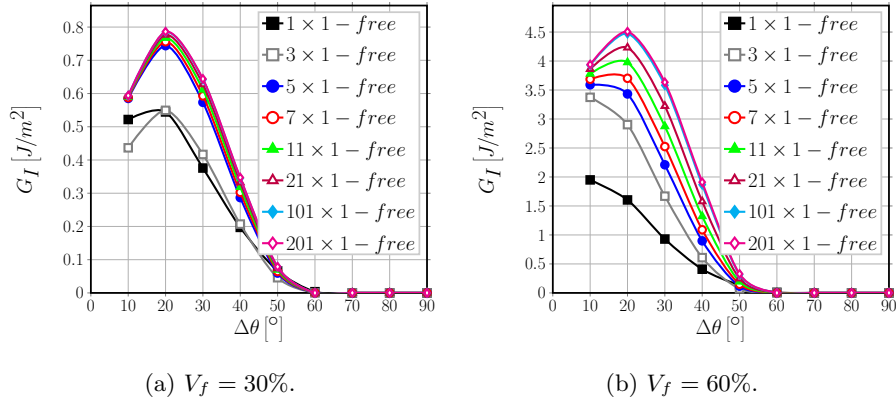


Figure 8: Effect of the interaction between debonds appearing at regular intervals on Mode I ERR in an UD with a single row of fibers at different levels of fiber volume fraction  $V_f$ , subject to an applied transverse strain  $\varepsilon_x$  of 1%.

For Mode I, the presence of a free surface, and inversely the absence of  
 a fully bonded fiber along the vertical direction, implies the absence of the  
 counteracting upward-oriented vertical component of the displacement field due  
 to the mismatch in Poisson's ratios. This in turn translates into the constancy  
 350 of the value of  $\Delta\theta$  corresponding to contact zone's onset, always equal to  $60^\circ$ .  
 For  $V_f = 30\%$ , Mode I is reduced when the spacing between debonds (in terms

of number of fully bonded fibers between them in our models) decreases, but the magnitude of change is significant only in the range when the spacing is reduced from a debond every 5<sup>th</sup> fiber to one every 3<sup>rd</sup>. For comparison, the difference of peak  $G_I$  values for  $V_f = 30\%$  between  $5 \times 1 - free$  and  $3 \times 1 - free$  is  $\sim 0.2 \frac{J}{m^2}$  (around 30% of the lower value), while between  $201 \times 1 - free$  and  $5 \times 1 - free$  is  $\sim 0.05 \frac{J}{m^2}$  (around 7% of the lower value). A similar observation can be made for  $V_f = 60\%$ , but for larger spacings: no difference can be seen between the case of a debond placed every 101<sup>st</sup>101<sup>th</sup> and every 201<sup>st</sup>201<sup>th</sup> fiber. These observations suggest the existence of characteristic distance dependent on the fiber volume fraction which governs the interaction between debonds: in low  $V_f$  composites ( $V_f = 30\%$ ) the convergence to a non-interactive solution is faster (less interaction between debonded fibers in neighboring RUCs).

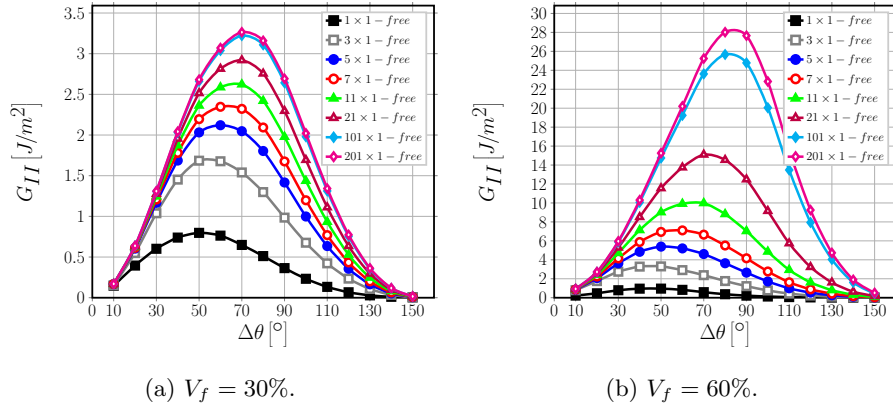


Figure 9: Effect of the interaction between debonds appearing at regular intervals on Mode II ERR in an UD with a single row of fibers at different levels of fiber volume fraction  $V_f$ , subject to an applied transverse strain  $\varepsilon_x$  of 1%.

Without constraint on the upper surface, the strain magnification effect creates a larger displacement gap in the  $x$ -direction, which increases Mode II for larger debonds. When debonds are far apart, the series of rigid elements in the ultra-thin composite row (constituted by fully bonded fibers and their surrounding matrix) creates higher  $x$ -strains than in average in the element with the debonded fiber, which in turn generates higher tangential displacements at the

370 crack tip for larger debonds. Conversely, when debonds are closer (smaller number of rigid elements between them), the strain concentration in the debonded element is more similar to the applied strain (the magnification is reduced) and the tangential displacement component at the crack tip decreases for large  $\Delta\theta$ . This is the mechanism behind the change in the value of  $\Delta\theta$  for which the peak  
 375 of  $G_{II}$  occurs: from  $70^\circ$  to  $50^\circ$  at 30%, and from  $80^\circ$  to  $40^\circ$  at 60% going from the higher to the smaller spacing of debonds. Differently from Mode I, the presence of a characteristic distance is harder to establish. For  $V_f = 30\%$  (Fig. 9a), it seems reasonable to establish it at around 100 fully bonded fibers between each debond. For  $V_f = 60\%$  (Fig. 9b), the difference between models  
 380  $101 \times 1 - free$  and  $201 \times 1 - free$  is still sizable, thus preventing the establishment of such characteristic distance. It is possible to observe, however, that the change between  $101 \times 1 - free$  and  $201 \times 1 - free$  is significantly smaller than between  $21 \times 1 - free$  and  $101 \times 1 - free$  ( $2 \left[\frac{J}{m^2}\right]$  vs  $11 \left[\frac{J}{m^2}\right]$ ), thus suggesting the existence of the characteristic distance outside the range studied. Nevertheless, one should question whether the single row composite with free  
 385 surface is an appropriate RUC for defining the upper bound for  $G_{II}$ :  $G_{II}$  may be more affected by the free surface than by the effect of the interaction between debonds in the row.

### 3.3. Influence of rows of fully bonded fibers on debond's ERR in the middle row

390 The effect of the presence of rows of fully bonded fibers on debond's growth in the central row with all fibers partially debonded is studied for Mode I (Fig. 10) and Mode II (Fig. 11) and fiber content equal to 30% (Figs. 10a and 11a) and 60% (Figs. 10b and 11b). The models treated are  $1 \times 3 - free$ ,  $1 \times 5 - free$ ,  $1 \times 7 - free$ ,  $1 \times 11 - free$ ,  $1 \times 21 - free$ ,  $1 \times 101 - free$  and  $1 \times 201 - free$ ,  
 395 corresponding to a UD composite with respectively 3, 5, 7, 11, 21, 101 and 201 rows of fibers (Fig. 2a).

The results shown strengthen the arguments made in Sec. 3.1 and Sec. 3.2. It can, in fact, be seen in Fig. 10 that an increasing number of bonded fiber rows across the thickness delays the onset of the contact zone to a debond of  $70^\circ$  in

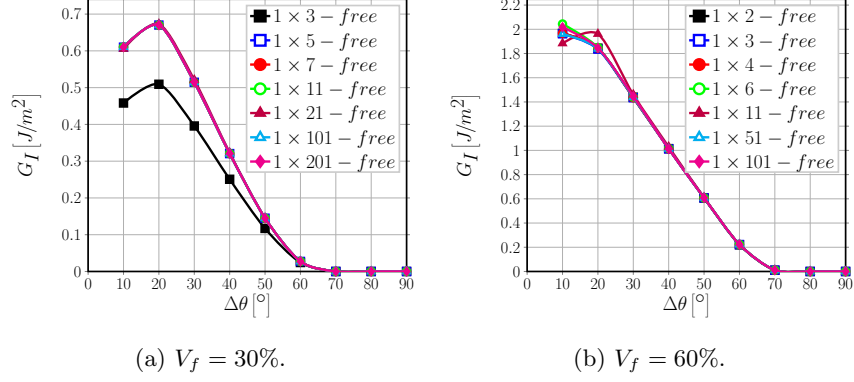


Figure 10: Influence of rows of fully bonded fibers on debond's growth in Mode I ERR in a centrally located row of debonded fibers at different levels of fiber volume fraction  $V_f$ , subject to an applied transverse strain  $\varepsilon_x$  of 1%.

size, due to the introduction of an additional positive component of the vertical displacement which translates into an opening displacement at the debond's tip. Comparing Fig. 9b with Fig. 11b, we observe that the presence of bonded fiber rows significantly reduce the  $G_{II}$  and its maximum is shifted back to  $60^\circ$ , thus confirming the hypothesis in Section 3.2 that the absence of  $G_{II}$  convergence with the increasing distance in a single-row composite is caused more by the free surface than by the interaction between debonds.

The results of both Mode I and Mode II show that the introduction of an increasing number of fully bonded fiber rows doesn't change the ERR calculated at the crack tip after adding more than one row (the convergence is very fast). A small effect, mostly on Mode I, of the number of bonded fiber rows can be observed at low fiber content (Figs. 10a and 11a), while for high fiber content the smaller model with only one fiber row above the partially debonded one is already representative.

#### 3.4. Effect of multiple rows of bonded fibers on debonding in the central row of a UD composite with different distances between debonded fibers

The ERR of debonds appearing at regular intervals in the central row of fibers in UD composites is affected by the number of rows with bonded fibers.

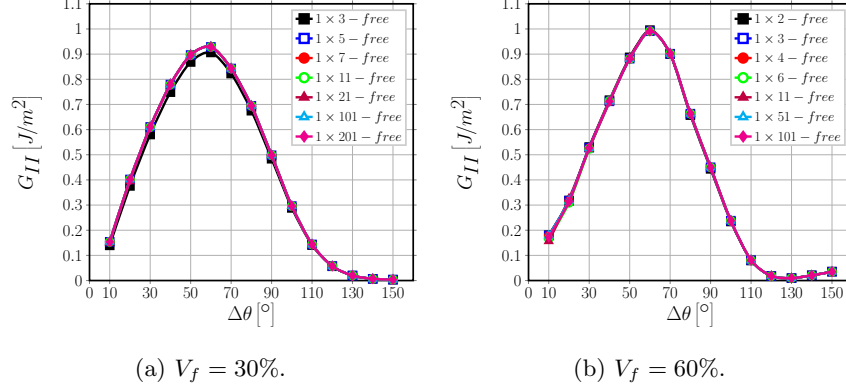


Figure 11: Influence of rows of fully bonded fibers on debond's growth in Mode II ERR in a centrally located row of debonded fibers at different levels of fiber volume fraction  $V_f$ , subject to an applied transverse strain  $\varepsilon_x$  of 1%.

The effect is investigated using different combinations of horizontal debond spacing, controlled by the number of bonded fibers in the central row of the RUC, and the number of rows of bonded fibers on top of it. The following models have been studied:  $3 \times 3 - free$ ,  $5 \times 3 - free$ ,  $5 \times 5 - free$ ,  $7 \times 3 - free$ ,  $7 \times 5 - free$ ,  $7 \times 7 - free$ ,  $11 \times 3 - free$ ,  $11 \times 5 - free$ ,  $11 \times 7 - free$ ,  $11 \times 11 - free$ ,  $21 \times 3 - free$ ,  $21 \times 5 - free$ ,  $21 \times 7 - free$ ,  $21 \times 11 - free$ ,  $21 \times 21 - free$ ,  $101 \times 3 - free$ ,  $101 \times 5 - free$ ,  $101 \times 7 - free$ ,  $101 \times 11 - free$ ,  $201 \times 3 - free$ ,  $201 \times 5 - free$ ,  $201 \times 7 - free$ ,  $201 \times 11 - free$  (Fig. 2b).

The results shown in Fig. 12 confirm the observations discussed in Sec. 3.2 and Sec. 3.3: the presence of fully bonded fiber rows on top of the central row with debonded fibers reduces the interaction with the free surface and thus has a restraining effect on the ERR, that counteracts the magnification due to an increasing number of fully bonded fibers in the horizontal direction. The interplay is further modulated by the fiber content. Observing Fig. 12, it is possible to note how the free surface interaction decays fast: the presence of 5 fiber rows across the thickness is already sufficient to prevent any significant effect of additional fiber rows on the ERR of a debond in the central row.

The results in Fig. 13 show instead the effect of increasing the distance

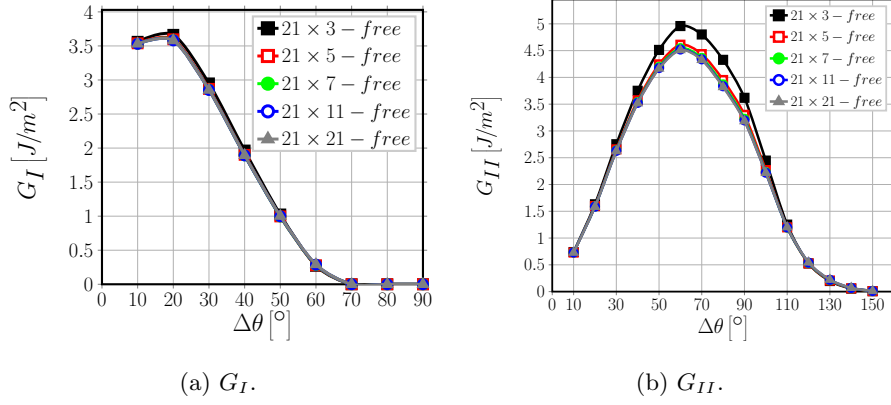


Figure 12: Effect on Mode I and Mode II ERR of the presence of an increasing number of rows of fully bonded fibers in UD composites with debonds appearing every  $10^{th}$  fiber (model  $21 \times k - free$ ).  $V_f = 60\%$  and  $\varepsilon_x = 1\%$ .

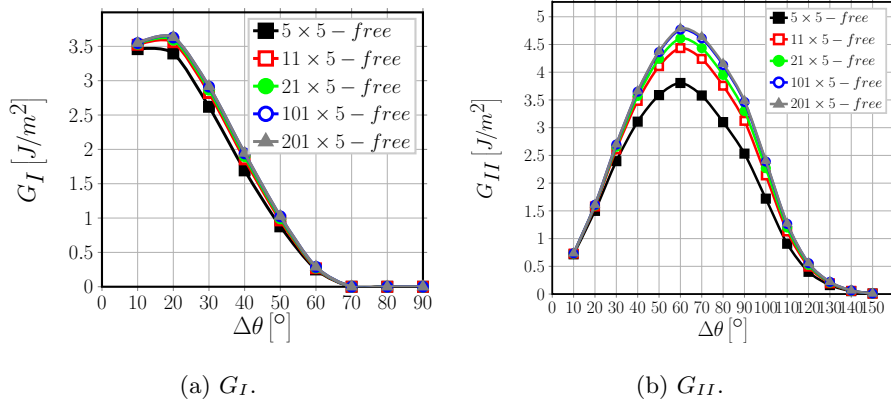


Figure 13: Effect on Mode I and Mode II ERR of increasing the spacing between debonds appearing in the central row of fibers in a UD composite with a fixed number of rows across the thickness.  $V_f = 60\%$ ,  $k = 5$  and  $\varepsilon_x = 1\%$ .

between two consecutive debonds in the central row of a UD composite of given thickness. In agreement with the observations of Section 3.2, increasing the distance between debonds (measured in terms of fully bonded fibers between them) causes an increase in the ERR in both Mode I and Mode II. For both

440 Mode I and Mode II, it is possible to observe the existence of a characteristic distance which defines the limit between the interactive and the non-interactive

solution. Furthermore, comparing Figure 13a and 13b, it is possible to notice that Mode I is less sensitive than Mode II to the horizontal spacing of debonds.

### 3.5. Comparison with the single fiber model with equivalent boundary conditions

445 The single fiber RUC ( $1 \times 1$ –*free* or  $1 \times 1$ –*coupling*) corresponds to the most damaged state of the composite, i.e. the state in which all fibers have debonds. The  $1 \times 1$ –*free* model represents an ultra-thin UD composite with a single row of partially debonded fibers. The  $1 \times 1$ –*coupling* model, where the displacement coupling is used to enforce periodic boundary conditions, represents an infinite  
450 composite.

The comparison of the  $1 \times 1$ –*free* model with one row multi-fiber models  $n \times 1$ –*free* in Figure 8 and Figure 9 show that the former provides in general the lowest value of the ERR (the highest crack shielding case).

The  $1 \times 1$ –*coupling* model is compared with  $1 \times 3$ –*free* and  $1 \times 201$ –*free*  
455 models in Fig. 14. In all three models the distance between debonds in the  $x$ -direction is the same and the difference is in the vertical direction. The  $1 \times 1$ –*coupling* model describes the interaction between debonds in different rows of debonded fibers whereas the  $1 \times k$ –*free* models describe the effect of the proximity of the composite’s free surface. The Mode I ERR in the  $1 \times 3$ –*free*  
460 and  $1 \times 201$ –*free* model is very similar to the  $1 \times 1$ –*coupling* model, which leads to a rather surprising conclusion. In both models we have, on the top of the central one, a large amount of fibers (bonded in two cases and debonded in the third case). It appears that the effect of bonded and debonded fibers on the central debond is the same. This implies that, for Mode I ERR, the interaction  
465 between debonds in elements placed on top of each other is small.

The same comparison for Mode II shows a sizeable difference in the range  $50^\circ - 90^\circ$ , while the results almost coincide for smaller values of  $\Delta\theta$ . The lower values of  $G_{II}$  of the  $1 \times 1$ –*coupling* model in the range  $50^\circ - 90^\circ$  are due to the shielding effect of a debond of the same size in the fiber just above the central  
470 one (modeled by the coupling boundary condition), which leaves the strip of matrix between the two fibers free to deform away from both of them due to

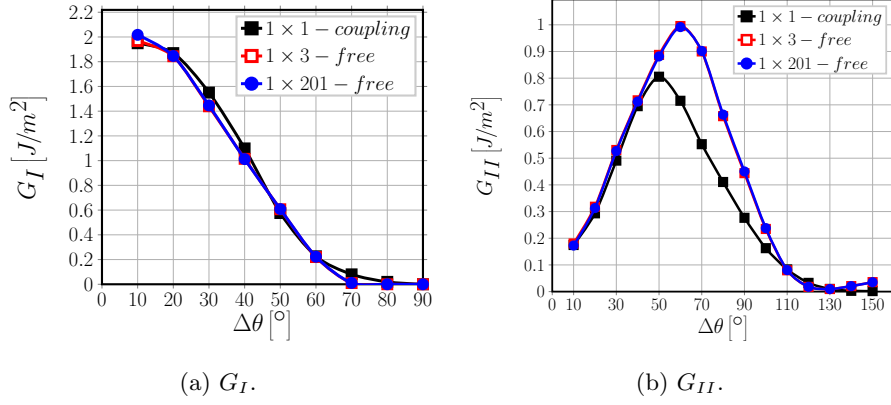


Figure 14: Comparison of the ERR between the single fiber model with coupling conditions along the upper boundary and the  $1 \times k - \text{free}$  model.  $V_f = 60\%$  and  $\varepsilon_x = 1\%$ .

the Poissons effect and thus favors Mode I and reduces Mode II. This translates into the delay in the appearance of the contact zone, particularly evident in Fig. 14a.

#### 4. Conclusions & Outlook

Several models of Repeating Unit Cell, representative of different microstructural arrangements of a unidirectional (UD) composite, have been studied in order to investigate the effect on fiber/matrix interface crack growth of the presence of partially debonded and/or fully bonded fibers. Regular microstructures based on square-packing arrangements of fibers have been loaded in transverse tension, with debonds appearing in the central row of fibers at regular intervals measured in terms of number of fully bonded fibers between them. This central row is embedded in-between a varying number of rows with perfectly bonded fibers. The surface of the composite is either traction-free or with imposed vertical displacement constraint imitating a periodic structure in the composite thickness direction.

The fiber volume fraction is the same everywhere and the fiber distribution is uniform by design, which establishes a direct relationship between fiber content



and inter-fiber distance. The main conclusions of this work are summarized  
here.

1. With a decreasing number of fully bonded fibers between two partially debonded fibers in the central row, the ERR decreases. It seems to exist a characteristic distance between debonds which defines the transition to a non-interactive solution. However, this distance depends on the number of perfectly bonded fiber rows surrounding the central row.
2. The presence of a free surface close to the debond leads to higher Mode I and Mode II ERRs and a shift of the peak  $G$  values to larger debonds.
3. The presence of fibers (fully or partially bonded) in the composite thickness direction, along the same vertical line as the analyzed central fiber, appears to have a restraining effect on both  $G_I$  and  $G_{II}$ . The free composite surface effect on the ERR decays very fast: adding more than 2 fully bonded fibers below and above the central row leads to stable constant values of ERR.
4. The presence of a debond in the fiber above the central partially debonded one only delays the appearance of the contact zone, while no significant effect on the ERR has been observed.
5. Increasing the fiber content (decreasing the inter-fiber distance), magnifies in general the effects described in the previous points.
6. The results and conclusions presented agree well with previous observations reported in the literature [37, 40]. A mechanical explanation of the observed trends has been presented based on the mismatch in elastic properties, particularly Poisson's ratios, and the positions of fibers and debonds with respect to the loading direction.

## Acknowledgements

Luca Di Stasio gratefully acknowledges the support of the European School of Materials (EUSMAT) through the DocMASE Doctoral Programme and the European Commission through the Erasmus Mundus Programme.

## References

- [1] D. A. McCarville, J. C. Guzman, A. K. Dillon, J. R. Jackson, J. O. Birkland, 3.5 Design, Manufacture and Test of Cryotank Components, Elsevier, 2018, pp. 153–179. doi:10.1016/b978-0-12-803581-8.09958-6.  
URL <https://doi.org/10.1016/b978-0-12-803581-8.09958-6>
- [2] Y. H. N. Kim, S. Ko, W.-S. Lay, J. Tian, P. Chang, S. U. Thielk, H.-J. Bang, J. Yang, Effects of shallow biangle, thin-ply laminates on structural performance of composite wings, AIAA Journal 55 (6) (2017) 2086–2092. doi:10.2514/1.j055465.  
URL <https://doi.org/10.2514/1.j055465>
- [3] A. Kopp, S. Stappert, D. Mattsson, K. Olofsson, E. Marklund, G. Kurth, E. Mooij, E. Roorda, The aurora space launcher concept, CEAS Space Journal 10 (2) (2017) 167–187. doi:10.1007/s12567-017-0184-2.  
URL <https://doi.org/10.1007/s12567-017-0184-2>
- [4] K. Kawabe, S. Tomoda, T. Matsuo, A pneumatic process for spreading reinforcing fiber tow, in: Proceedings of the 42<sup>nd</sup> International SAMPE Symposium and Exhibition, SAMPE, pp. 65–76.
- [5] K. Kawabe, New spreading technology for carbon fiber tow and its application to composite materials, Sen'i Gakkaishi 64 (8) (2008) 262–267. doi:10.2115/fiber.64.p\_262.  
URL [https://doi.org/10.2115/fiber.64.p\\_262](https://doi.org/10.2115/fiber.64.p_262)
- [6] K. Kawabe, H. Sasayama, S. Tomoda, New carbon fiber tow-spread technology and applications to advanced composite materials, SAMPE Journal 45 (2) (2008) 6–17.  
URL [https://researchmap.jp/?action=cv\\_download\\_main&upload\\_id=161885](https://researchmap.jp/?action=cv_download_main&upload_id=161885)
- [7] H. Sasayama, K. Kawabe, S. Tomoda, I. Ohsawa, K. Kageyama, N. Ogata, Effect of lamina thickness on first ply failure in multidirectionally lami-

nated composites, in: Proceedings of the 8<sup>th</sup> Japan SAMPE Symposium, SAMPE, 2003.

- [8] S. Tsai, S. Sihh, R. Kim, Thin ply composites, in: Proceedings of 46<sup>th</sup> AIAA/ASME/AHS/ASC Structures, Structural Dynamics & Materials Conference, 2005.

550

- [9] K. Yamaguchi, H. Hahn, The improved ply cracking resistance of thin-ply laminates, in: Proceedings of the 15<sup>th</sup> International Conference on Composite Materials (ICCM-15), SAMPE, 2005.

- [10] S. Sihh, R. Kim, K. Kawabe, S. Tsai, Experimental studies of thin-ply laminated composites, Composites Science and Technology 67 (6) (2007) 996–1008. doi:10.1016/j.compscitech.2006.06.008.  
URL <https://doi.org/10.1016/j.compscitech.2006.06.008>

555

- [11] T. Yokozeiki, Y. Aoki, T. Ogasawara, Experimental characterization of strength and damage resistance properties of thin-ply carbon fiber/toughened epoxy laminates, Composite Structures 82 (3) (2008) 382–389. doi:10.1016/j.compstruct.2007.01.015.  
URL <https://doi.org/10.1016/j.compstruct.2007.01.015>

560

- [12] T. Yokozeiki, A. Kuroda, A. Yoshimura, T. Ogasawara, T. Aoki, Damage characterization in thin-ply composite laminates under out-of-plane transverse loadings, Composite Structures 93 (1) (2010) 49–57. doi:10.1016/j.compstruct.2010.06.016.  
URL <https://doi.org/10.1016/j.compstruct.2010.06.016>

565

- [13] J.-B. Moon, M.-G. Kim, C.-G. Kim, S. Bhowmik, Improvement of tensile properties of CFRP composites under LEO space environment by applying MWNTs and thin-ply, Composites Part A: Applied Science and Manufacturing 42 (6) (2011) 694–701. doi:10.1016/j.compositesa.2011.02.011.  
URL <https://doi.org/10.1016/j.compositesa.2011.02.011>

570

- [14] A. Arteiro, G. Catalanotti, J. Xavier, P. Camanho, Notched response of non-crimp fabric thin-ply laminates, *Composites Science and Technology* 79 (2013) 97–114. doi:10.1016/j.compscitech.2013.02.001.  
575 URL <https://doi.org/10.1016/j.compscitech.2013.02.001>
- [15] A. Arteiro, G. Catalanotti, J. Xavier, P. Camanho, Large damage capability of non-crimp fabric thin-ply laminates, *Composites Part A: Applied Science and Manufacturing* 63 (2014) 110–122. doi:10.1016/j.compositesa.2014.04.002.  
580 URL <https://doi.org/10.1016/j.compositesa.2014.04.002>
- [16] R. Amacher, J. Cugnoni, J. Botsis, L. Sorensen, W. Smith, C. Dransfeld, Thin ply composites: Experimental characterization and modeling of size-effects, *Composites Science and Technology* 101 (2014) 121–132. doi:10.1016/j.compscitech.2014.06.027.  
585 URL <https://doi.org/10.1016/j.compscitech.2014.06.027>
- [17] G. Guillaumet, A. Turon, J. Costa, J. Renart, P. Linde, J. Mayugo, Damage occurrence at edges of non-crimp-fabric thin-ply laminates under off-axis uniaxial loading, *Composites Science and Technology* 98 (2014) 44–50. doi:10.1016/j.compscitech.2014.04.014.  
590 URL <https://doi.org/10.1016/j.compscitech.2014.04.014>
- [18] C. Huang, S. Ju, M. He, Q. Zheng, Y. He, J. Xiao, J. Zhang, D. Jiang, Identification of failure modes of composite thin-ply laminates containing circular hole under tension by acoustic emission signals, *Composite Structures* 206 (2018) 70–79. doi:10.1016/j.compstruct.2018.08.019.  
595 URL <https://doi.org/10.1016/j.compstruct.2018.08.019>
- [19] J. Cugnoni, R. Amacher, S. Kohler, J. Brunner, E. Kramer, C. Dransfeld, W. Smith, K. Scobbie, L. Sorensen, J. Botsis, Towards aerospace grade thin-ply composites: Effect of ply thickness, fibre, matrix and interlayer toughening on strength and damage tolerance, *Composites Science and Technology* 168 (2018) 467–477. doi:10.1016/j.compscitech.2018.08.  
600

037.

URL <https://doi.org/10.1016/j.compscitech.2018.08.037>

- [20] H. Saito, H. Takeuchi, I. Kimpara, Experimental evaluation of the damage growth restraining in 90 layer of thin-ply cfrp cross-ply laminates, Advanced Composite Materials 21 (1) (2012) 57–66. doi:10.1163/156855112X629522.
- [21] K. W. Garrett, J. E. Bailey, Multiple transverse fracture in 90° cross-ply laminates of a glass fibre-reinforced polyester, Journal of Materials Science 12 (1) (1977) 157–168. doi:10.1007/bf00738481.
- URL <https://doi.org/10.1007/bf00738481>
- [22] A. Parvizi, J. E. Bailey, On multiple transverse cracking in glass fibre epoxy cross-ply laminates, Journal of Materials Science 13 (10) (1978) 2131–2136. doi:10.1007/bf00541666.
- URL <https://doi.org/10.1007/bf00541666>
- [23] A. Parvizi, K. W. Garrett, J. E. Bailey, Constrained cracking in glass fibre-reinforced epoxy cross-ply laminates, Journal of Materials Science 13 (1) (1978) 195–201. doi:10.1007/bf00739291.
- URL <https://doi.org/10.1007/bf00739291>
- [24] J. E. Bailey, A. Parvizi, On fibre debonding effects and the mechanism of transverse-ply failure in cross-ply laminates of glass fibre/thermoset composites, Journal of Materials Science 16 (3) (1981) 649–659. doi:10.1007/bf02402782.
- URL <https://doi.org/10.1007/bf02402782>
- [25] J. E. Bailey, P. T. Curtis, A. Parvizi, On the transverse cracking and longitudinal splitting behaviour of glass and carbon fibre reinforced epoxy cross ply laminates and the effect of poisson and thermally generated strain, Proceedings of the Royal Society A: Mathematical, Physical and Engineering

- Sciences 366 (1727) (1979) 599–623. doi:10.1098/rspa.1979.0071.  
 630 URL <https://doi.org/10.1098/rspa.1979.0071>
- [26] A. H. England, An arc crack around a circular elastic inclusion, Journal of Applied Mechanics 33 (3) (1966) 637. doi:10.1115/1.3625132.  
 URL <https://doi.org/10.1115/1.3625132>
- [27] A. Perlman, G. Sih, Elastostatic problems of curvilinear cracks in bonded  
 635 dissimilar materials, International Journal of Engineering Science 5 (11)  
 (1967) 845–867. doi:10.1016/0020-7225(67)90009-2.  
 URL [https://doi.org/10.1016/0020-7225\(67\)90009-2](https://doi.org/10.1016/0020-7225(67)90009-2)
- [28] M. Toya, A crack along the interface of a circular inclusion embedded in an  
 infinite solid, Journal of the Mechanics and Physics of Solids 22 (5) (1974)  
 640 325–348. doi:10.1016/0022-5096(74)90002-7.  
 URL [https://doi.org/10.1016/0022-5096\(74\)90002-7](https://doi.org/10.1016/0022-5096(74)90002-7)
- [29] M. Comninou, The interface crack, Journal of Applied Mechanics 44 (4)  
 (1977) 631. doi:10.1115/1.3424148.  
 URL <https://doi.org/10.1115/1.3424148>
- [30] F. París, J. C. Caño, J. Varna, The fiber-matrix interface crack — a nu-  
 645 merical analysis using boundary elements, International Journal of Fracture  
 82 (1) (1996) 11–29. doi:10.1007/bf00017861.  
 URL <https://doi.org/10.1007/bf00017861>
- [31] J. Varna, F. París, J. C. Caño, The effect of crack-face contact on  
 650 fiber/matrix debonding in transverse tensile loading, Composites Science  
 and Technology 57 (5) (1997) 523–532. doi:10.1016/s0266-3538(96)  
 00175-3.  
 URL [https://doi.org/10.1016/s0266-3538\(96\)00175-3](https://doi.org/10.1016/s0266-3538(96)00175-3)
- [32] I. García, V. Mantić, E. Graciani, Debonding at the fibre–matrix interface  
 655 under remote transverse tension. one debond or two symmetric debonds?,  
 European Journal of Mechanics - A/Solids 53 (2015) 75–88. doi:10.1016/

j.euomechsol.2015.02.007.

URL <https://doi.org/10.1016/j.euomechsol.2015.02.007>

[33] E. Correa, E. Gamstedt, F. París, V. Mantič, Effects of the presence of  
660 compression in transverse cyclic loading on fibre–matrix debonding in uni-  
directional composite plies, *Composites Part A: Applied Science and Man-  
ufacturing* 38 (11) (2007) 2260–2269. doi:10.1016/j.compositesa.2006.  
11.002.  
URL <https://doi.org/10.1016/j.compositesa.2006.11.002>

[34] E. Correa, V. Mantič, F. París, Effect of thermal residual stresses on matrix  
665 failure under transverse tension at micromechanical level: A numerical and  
experimental analysis, *Composites Science and Technology* 71 (5) (2011)  
622–629. doi:10.1016/j.compscitech.2010.12.027.  
URL <https://doi.org/10.1016/j.compscitech.2010.12.027>

[35] E. Correa, F. París, V. Mantič, Effect of the presence of a secondary trans-  
670 verse load on the inter-fibre failure under tension, *Engineering Fracture Me-  
chanics* 103 (2013) 174–189. doi:10.1016/j.engfracmech.2013.02.026.  
URL <https://doi.org/10.1016/j.engfracmech.2013.02.026>

[36] E. Correa, F. París, V. Mantič, Effect of a secondary transverse load on  
675 the inter-fibre failure under compression, *Composites Part B: Engineering*  
65 (2014) 57–68. doi:10.1016/j.compositesb.2014.01.005.  
URL <https://doi.org/10.1016/j.compositesb.2014.01.005>

[37] C. Sandino, E. Correa, F. París, Numerical analysis of the influence of a  
nearby fibre on the interface crack growth in composites under transverse  
680 tensile load, *Engineering Fracture Mechanics* 168 (2016) 58–75. doi:10.  
1016/j.engfracmech.2016.01.022.  
URL <https://doi.org/10.1016/j.engfracmech.2016.01.022>

[38] C. Sandino, E. Correa, F. París, Composite materials under transverse  
biaxial loads: Study of the influence of a nearby fibre on the interface crack

- 685 growth under tension, in: Proceeding of the 17<sup>th</sup> European Conference on  
Composite Materials (ECCM-17), 2016.
- [39] C. Sandino, E. Correa, F. París, Interface crack growth under transverse  
compression: nearby fibre effect, in: Proceeding of the 18<sup>th</sup> European Con-  
ference on Composite Materials (ECCM-18), 2018.
- 690 [40] L. Zhuang, A. Pupurs, J. Varna, R. Talreja, Z. Ayadi, Effects of inter-fiber  
spacing on fiber-matrix debond crack growth in unidirectional composites  
under transverse loading, Composites Part A: Applied Science and Man-  
ufacturing 109 (2018) 463–471. doi:10.1016/j.compositesa.2018.03.  
031.  
695 URL <https://doi.org/10.1016/j.compositesa.2018.03.031>
- [41] J. Varna, L. Q. Zhuang, A. Pupurs, Z. Ayadi, Growth and interaction  
of debonds in local clusters of fibers in unidirectional composites during  
transverse loading, Key Engineering Materials 754 (2017) 63–66. doi:  
10.4028/www.scientific.net/kem.754.63.  
700 URL <https://doi.org/10.4028/www.scientific.net/kem.754.63>
- [42] Simulia, Providence, RI, USA, ABAQUS/Standard User’s Manual, Version  
6.12 (2012).
- [43] R. Krueger, Virtual crack closure technique: History, approach, and appli-  
cations, Applied Mechanics Reviews 57 (2) (2004) 109. doi:10.1115/1.  
705 1595677.  
URL <https://doi.org/10.1115/1.1595677>
- [44] J. R. Rice, A path independent integral and the approximate analysis of  
strain concentration by notches and cracks, Journal of Applied Mechanics  
35 (2) (1968) 379. doi:10.1115/1.3601206.  
710 URL <https://doi.org/10.1115/1.3601206>
- [45] F. París, E. Correa, V. Mantič, Kinking of transversal interface cracks  
between fiber and matrix, Journal of Applied Mechanics 74 (4) (2007) 703.



doi:10.1115/1.2711220.

URL <https://doi.org/10.1115/1.2711220>