


LIQUID LIMIT DETERMINATION - FLOW CURVE

Test Method: IS 2720 (Part 5)

Borehole ID : CBH-11

Sample Type & Sample Depth from top : UDS & 1.50 m

FLOW CURVE

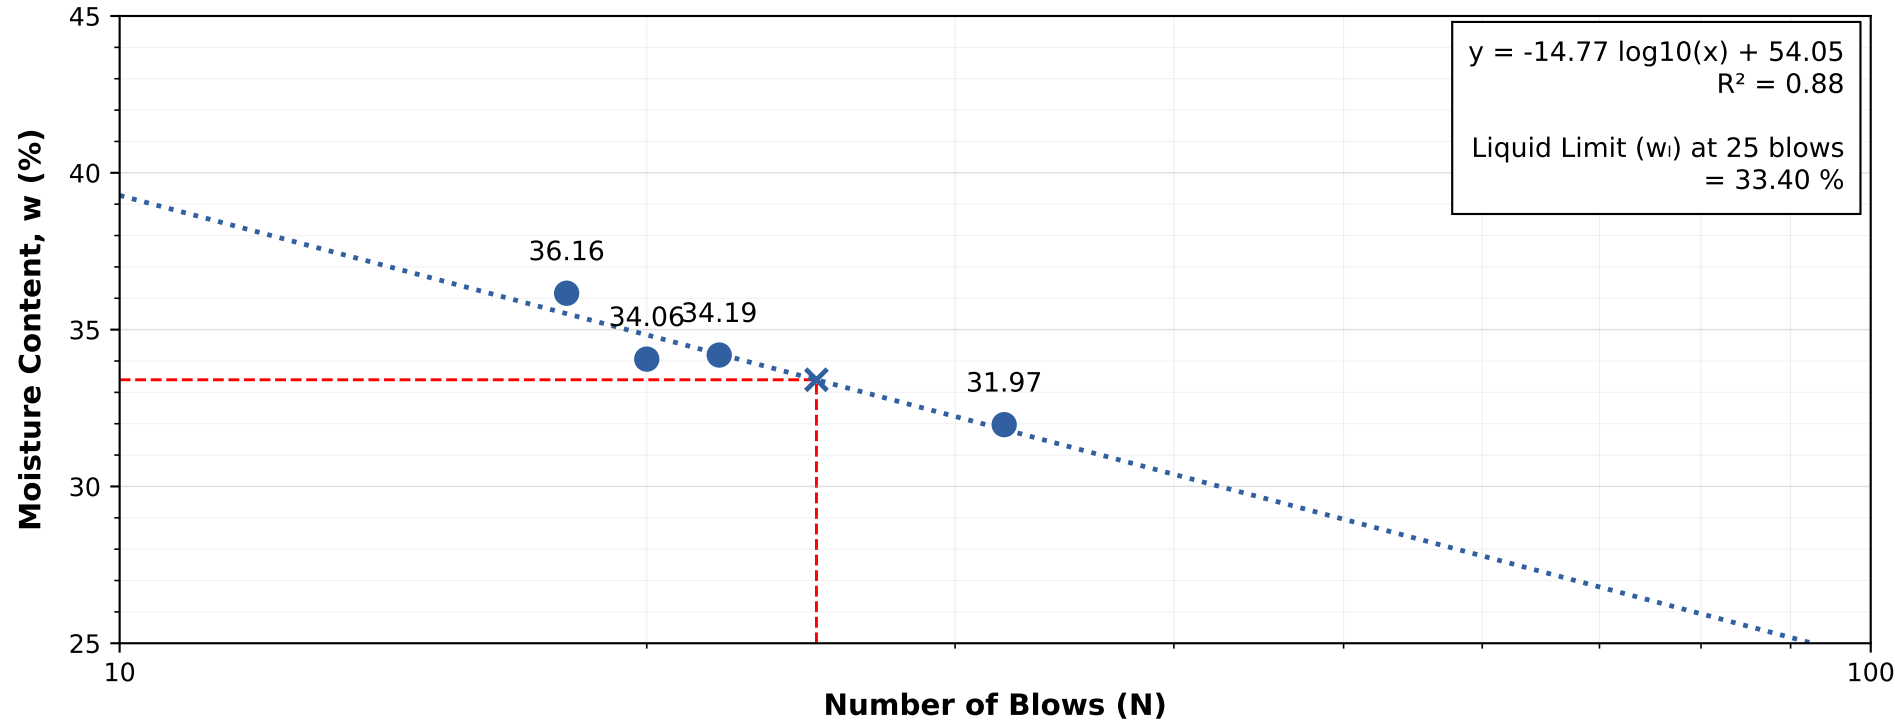

LIQUID LIMIT TEST OBSERVATIONS

Trial No.	Number of Blows (N)	Moisture Content, w (%)
1	18	36.16
2	20	34.06
3	22	34.19
4	32	31.97

TEST RESULTS

Liquid Limit (w_L)	: 33.40 %
Plastic Limit (w_P)	: 16.80 %
Plasticity Index (PI)	: 16.60 %

Remarks / Note:

- Flow curve plotted as per IS 2720 (Part 5) using semi-logarithmic scale.
- Liquid Limit reported at 25 blows from the best fit line.


LIQUID LIMIT DETERMINATION - FLOW CURVE

Test Method: IS 2720 (Part 5)

Borehole ID : CBH-11

Sample Type & Sample Depth from top : SPT & 3.50 m

FLOW CURVE

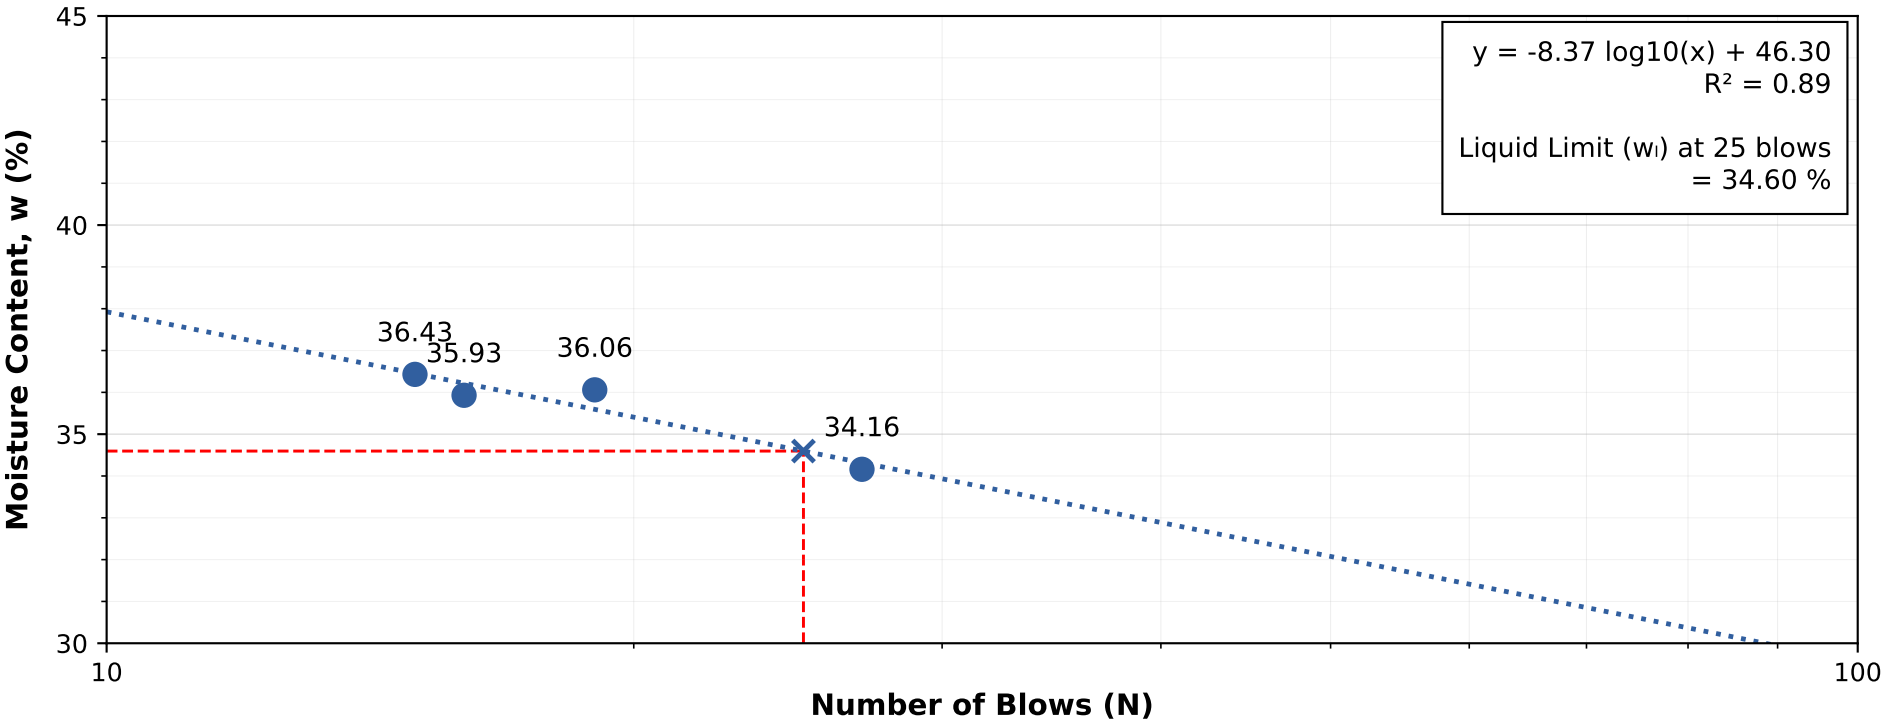

LIQUID LIMIT TEST OBSERVATIONS

Trial No.	Number of Blows (N)	Moisture Content, w (%)
1	15	36.43
2	16	35.93
3	19	36.06
4	27	34.16

TEST RESULTS

Liquid Limit (w _L)	: 34.60 %
Plastic Limit (w _p)	: 16.50 %
Plasticity Index (PI)	: 18.10 %

Remarks / Note:


- Flow curve plotted as per IS 2720 (Part 5) using semi-logarithmic scale.
- Liquid Limit reported at 25 blows from the best fit line.

LIQUID LIMIT DETERMINATION - FLOW CURVE

Test Method: IS 2720 (Part 5)

Borehole ID : CBH-11

Sample Type & Sample Depth from top : UDS & 4.50 m

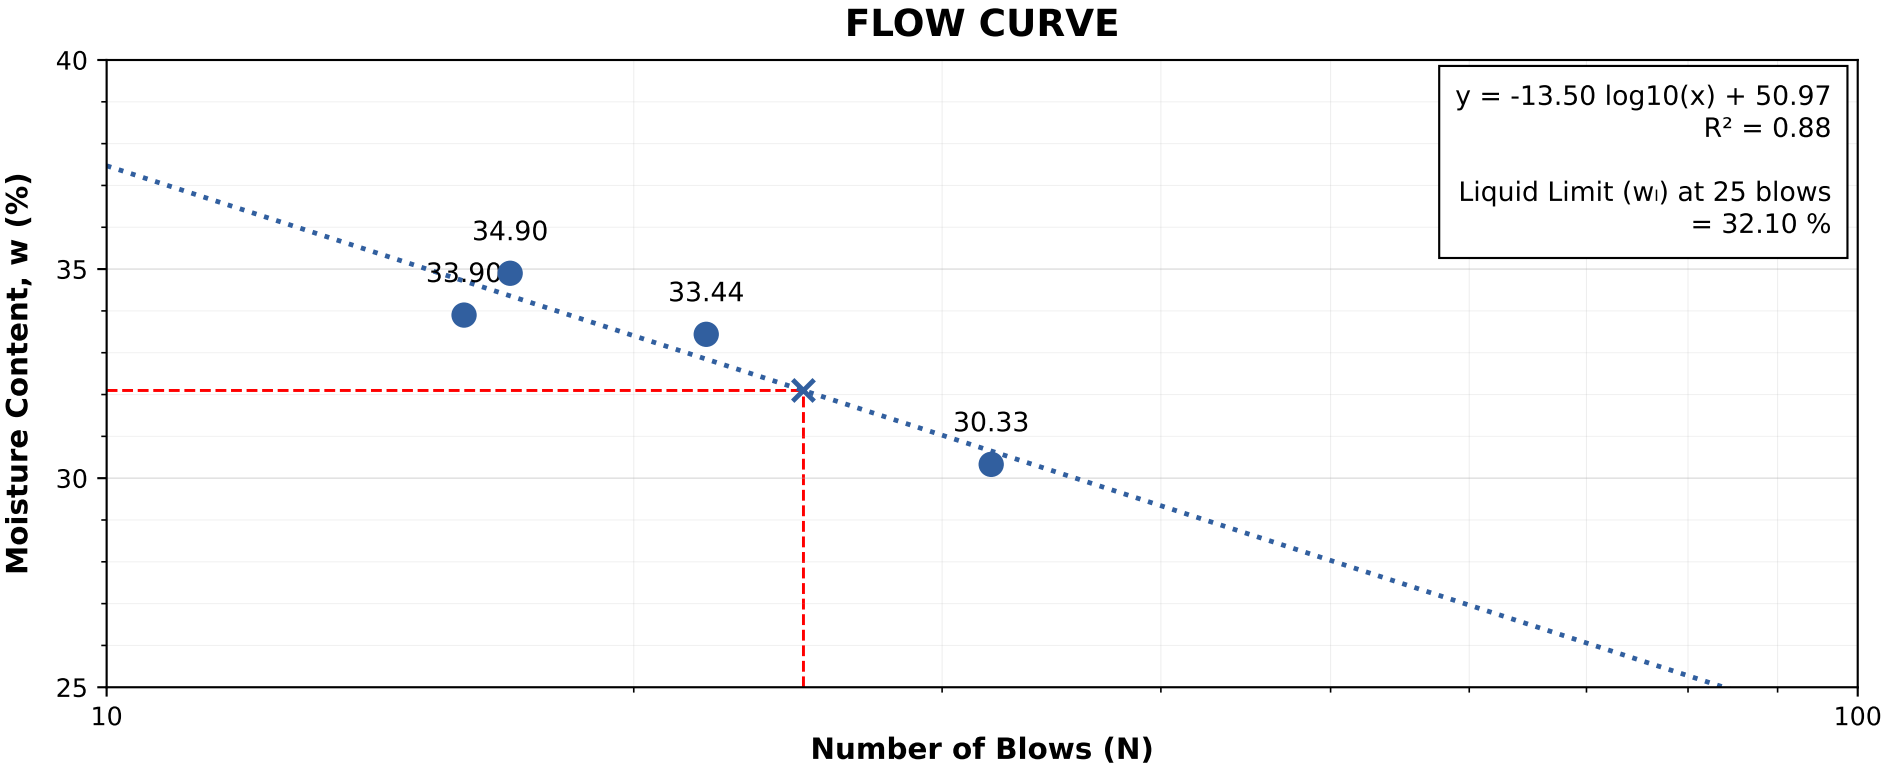

LIQUID LIMIT TEST OBSERVATIONS

Trial No.	Number of Blows (N)	Moisture Content, w (%)
1	16	33.90
2	17	34.90
3	22	33.44
4	32	30.33

TEST RESULTS

Liquid Limit (w_L)	: 32.10 %
Plastic Limit (w_P)	: 15.30 %
Plasticity Index (PI)	: 16.80 %

Remarks / Note:

- Flow curve plotted as per IS 2720 (Part 5) using semi-logarithmic scale.
- Liquid Limit reported at 25 blows from the best fit line.


LIQUID LIMIT DETERMINATION - FLOW CURVE

Test Method: IS 2720 (Part 5)

Borehole ID : CBH-11

Sample Type & Sample Depth from top : SPT & 6.50 m

FLOW CURVE

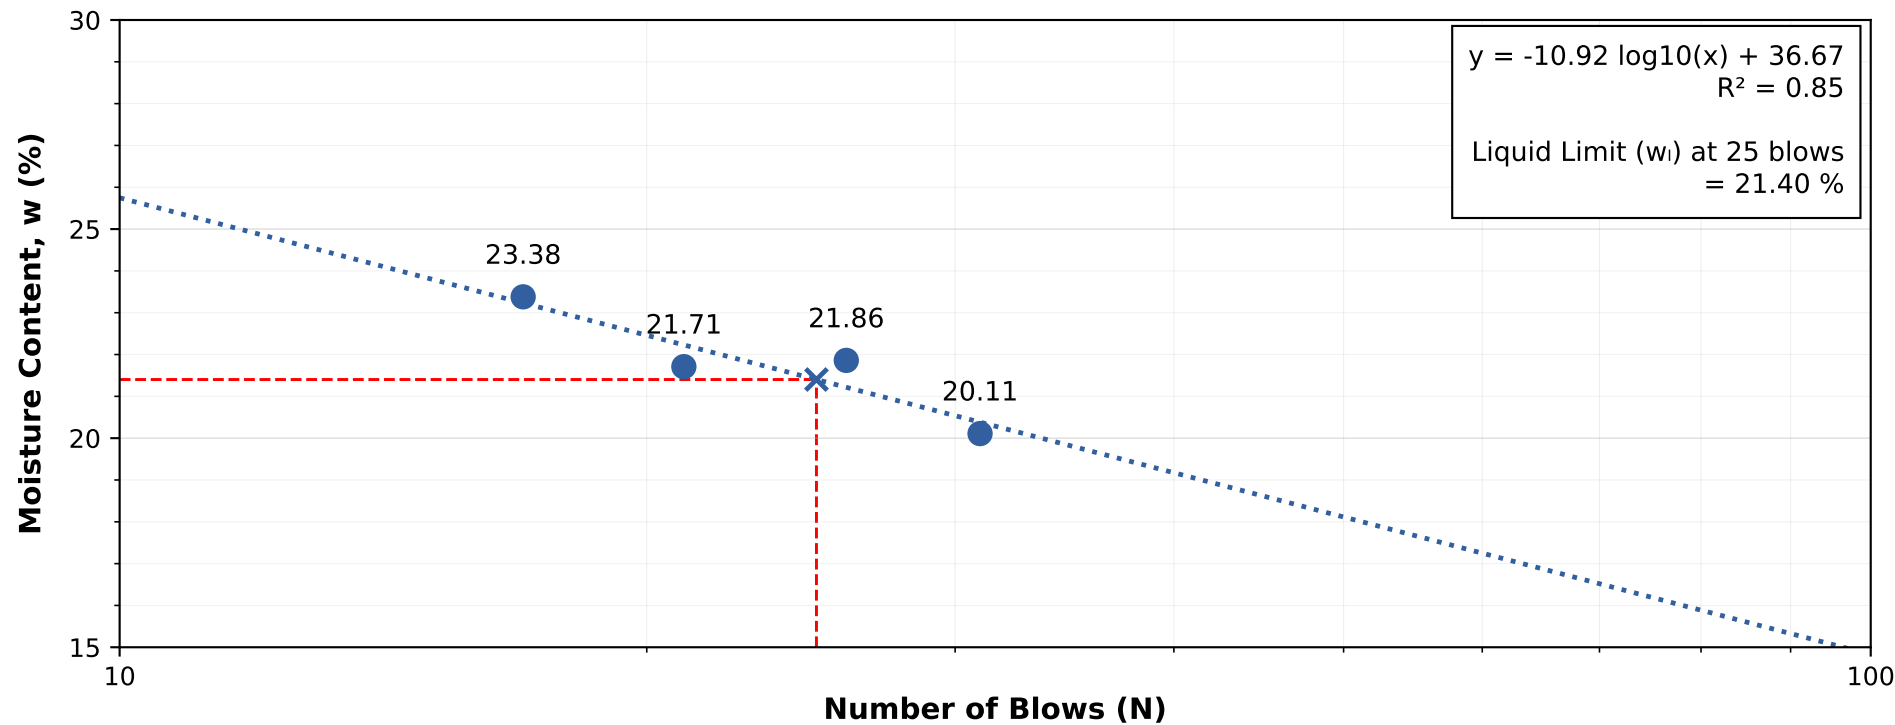

LIQUID LIMIT TEST OBSERVATIONS

Trial No.	Number of Blows (N)	Moisture Content, w (%)
1	17	23.38
2	21	21.71
3	26	21.86
4	31	20.11

TEST RESULTS

Liquid Limit (w_L)	: 21.40 %
Plastic Limit (w_P)	: 10.70 %
Plasticity Index (PI)	: 10.70 %

Remarks / Note:


- Flow curve plotted as per IS 2720 (Part 5) using semi-logarithmic scale.
- Liquid Limit reported at 25 blows from the best fit line.

LIQUID LIMIT DETERMINATION - FLOW CURVE

Test Method: IS 2720 (Part 5)

Borehole ID : CBH-11

Sample Type & Sample Depth from top : UDS & 7.50 m

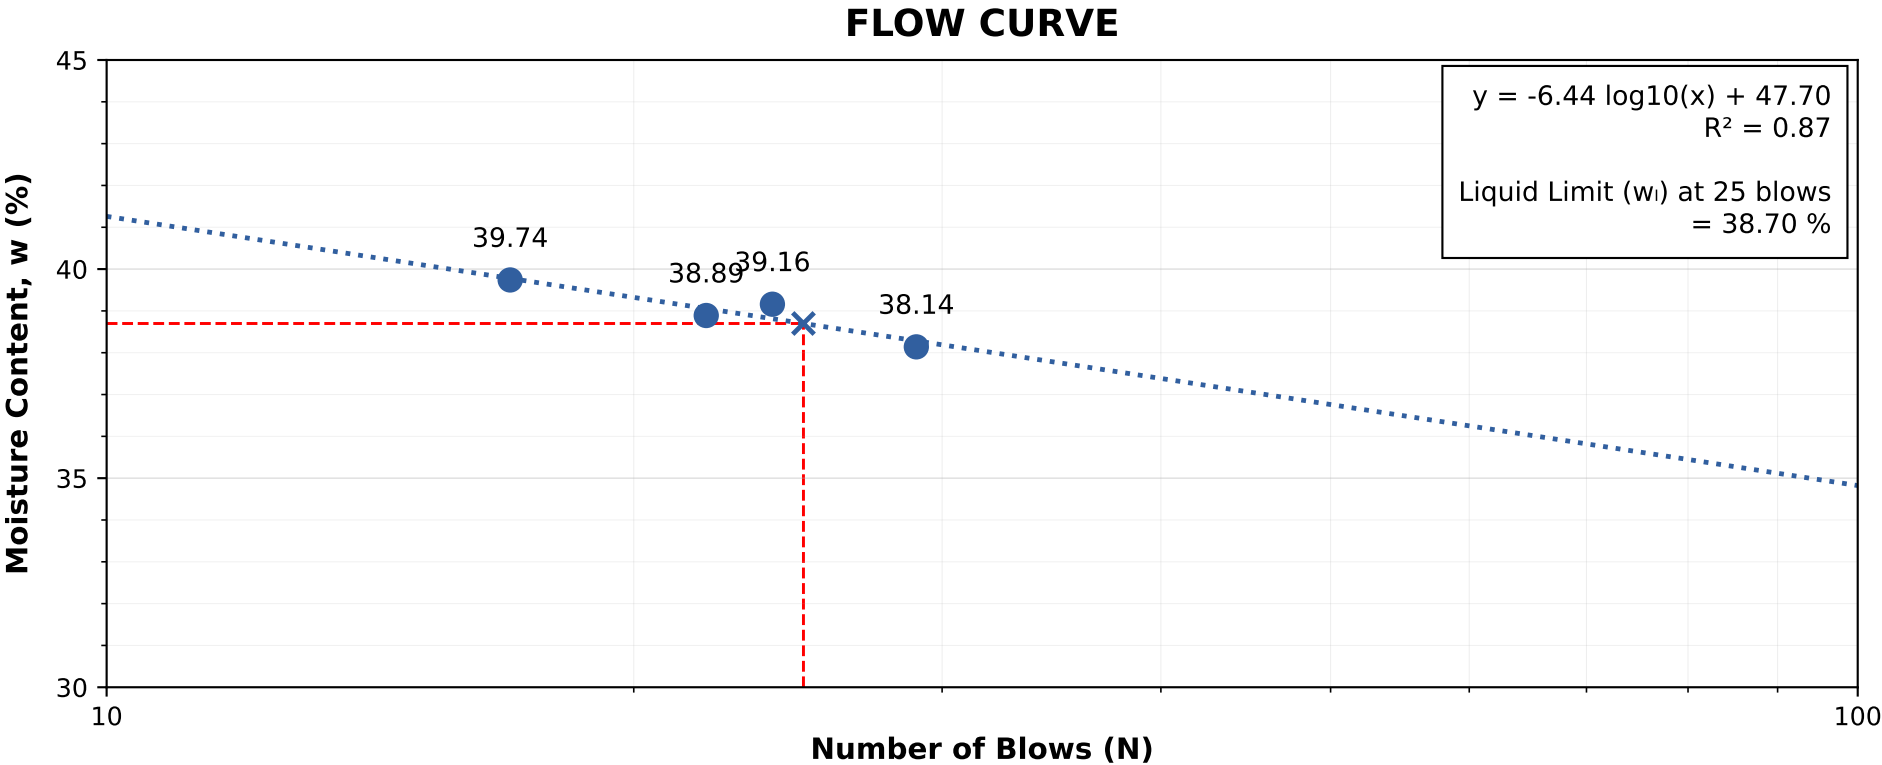

LIQUID LIMIT TEST OBSERVATIONS

Trial No.	Number of Blows (N)	Moisture Content, w (%)
1	17	39.74
2	22	38.89
3	24	39.16
4	29	38.14

TEST RESULTS

Liquid Limit (w_l)	: 38.70 %
Plastic Limit (w_p)	: 17.60 %
Plasticity Index (PI)	: 21.10 %

Remarks / Note:


- Flow curve plotted as per IS 2720 (Part 5) using semi-logarithmic scale.
- Liquid Limit reported at 25 blows from the best fit line.

LIQUID LIMIT DETERMINATION - FLOW CURVE

Test Method: IS 2720 (Part 5)

Borehole ID : CBH-11

Sample Type & Sample Depth from top : SPT & 13.50 m

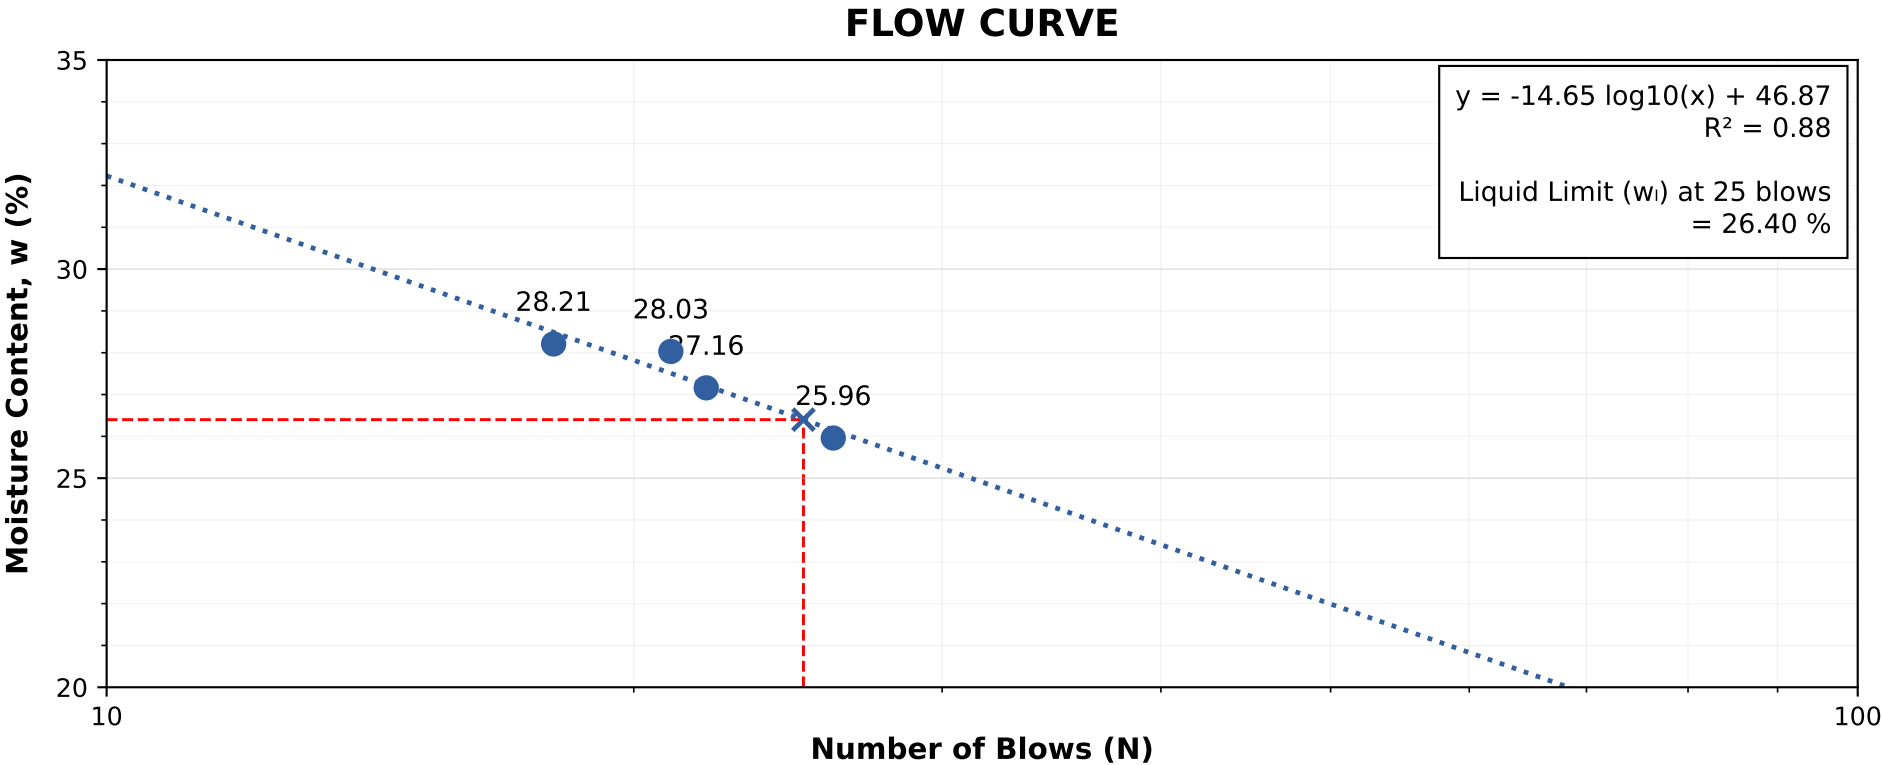

LIQUID LIMIT TEST OBSERVATIONS

Trial No.	Number of Blows (N)	Moisture Content, w (%)
1	18	28.21
2	21	28.03
3	22	27.16
4	26	25.96

TEST RESULTS

Liquid Limit (w_l)	: 26.40 %
Plastic Limit (w_p)	: —
Plasticity Index (PI)	: —

Remarks / Note:

- Flow curve plotted as per IS 2720 (Part 5) using semi-logarithmic scale.
- Liquid Limit reported at 25 blows from the best fit line.