


输入信息一：材料物性数据


材料类型	材料ID	HOMO (eV)	LUMO (eV)	Tg (°C)	S1 (eV)	T1 (eV)	PL Peak (nm)	激发态寿命 (t1/t2)	溶解性 (溶剂: 苯甲酸甲酯)	空穴迁移率	电子迁移率	分子化学结构
P-host	SGH5549	-5.33	-2.13	120	3.1	2.65	404/426	5.6ns/-	20mg/mL	SGH5549>P1230>1206	/	
N-host	SGH5516	-5.74	-2.84	125	2.8	2.58	445	5.6ns/-	20mg/mL		SGH5516>N911	
P-host	P1206	-5.25	/	112	3.4	2.74	405/426	4.6ns/-	>80 mg/mL		/	
P-host	P1230	-5.31	/	121	3.39	2.74			30 mg/mL		/	
N-host	N911	-5.71	/	125	2.8	2.72	473	4.8ns/-	>80 mg/mL	/	N911>PH120	
N-host	N1095	-5.69	/	118	2.89	2.81			>80 mg/mL	/		
N-host	N981	-5.65	-2.28	121	2.8	2.74			>80 mg/mL	/		
P-host	PH119	-5.30	-5.30	110	/		407/429	5.3 ns/-	40 mg/mL	/	/	
N-host	PH120	-5.64	-2.34	115	/	2.75	507	22.3ns/1.67us	30 mg/mL	PH120>SGH5516	PH122>PH120	
N-host	PH122	-5.70	-2.40	131	/	2.74	511	23.6ns/5.55us	40 mg/mL			
N-host	SGH531	-5.75	-2.86	130	2.59	2.57	472	7.1ns/-	30 mg/mL	/	SGH5549>SGH531	
磷光敏化剂	PGD508	-5.21	-2.47	/	/	2.34	533	1.5us	10 mg/mL	/	/	
荧光 dopoant	FGD5563	-5.36	/	/	/		535	0.1us	3 mg/mL	/	/	

光物理性质分析


P-host结构

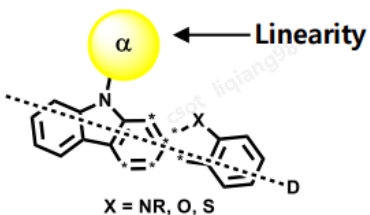


PL of P-host

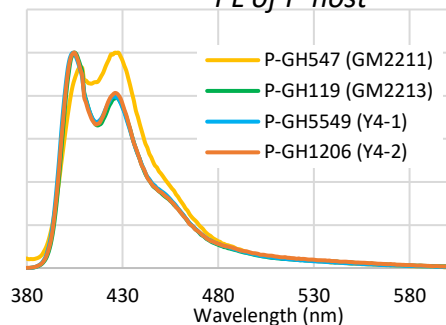


TRPL of P-host

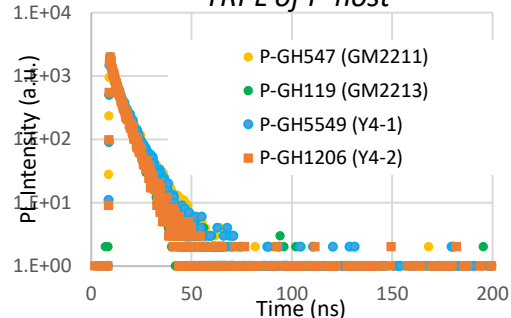


N-host结构

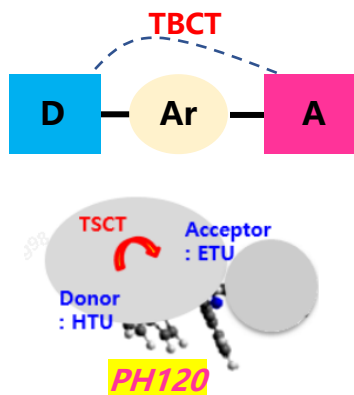

PL of N-host

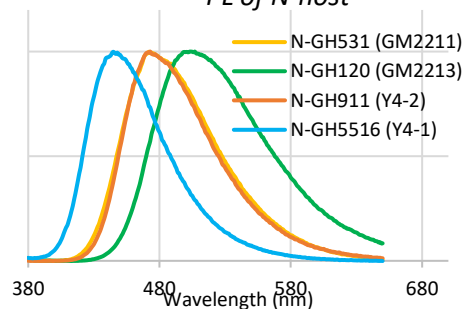

TRPL of N-host

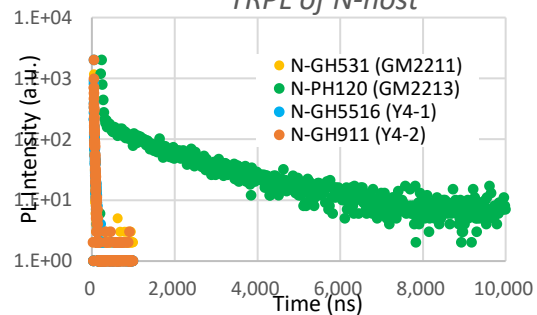

P-HOST	Peak (nm)	τ_1/τ_2 (ns/us)	N-HOST	Peak (nm)	τ_1/τ_2 (ns/us)
GH547	408/426	5.8/---	GH531	472	7.1/---
GH119	405/427	5.3/---	GH120	507	160ns/2.5us
GH5549	404/426	5.6/---	GH5516	445	5.6/---
GH1206	405/426	4.6/---	GH911	473	4.8/---