

Design and Manufacture of an Open-Hardware University Rocket Airframe using Carbon Fiber

Joe Shields * Leslie Elwood*

The amateur and university rocketry communities are rapidly reaching higher altitudes with more sophisticated rockets. However, most groups are still using heavy airframes made of metal or fiberglass. Commercial off-the-shelf airframes are either too expensive for low-budget university groups or too small to use as a platform for high altitude experiments. A capstone team of mechanical engineering seniors at Portland State University has developed a low-weight, modular carbon fiber airframe as an open-hardware technology for university rocketry. This project continues the work of a 2014 capstone team, who developed a carbon fiber layup process with promising results. This will enable low-budget groups like the Portland State Aerospace Society to explore high altitude science and compete in the university space race.

Nomenclature

CF	Carbon Fiber
CFD	Computational Fluid Dynamics
CTE	Coefficient of Thermal Expansion
GPS	Global Positioning System
LV2	Launch Vehicle 2
LV3	Launch Vehicle 3
PSAS	Portland State Aerospace Society
PSU	Portland State University

I. Introduction

PSAS is an interdisciplinary group of engineering students, alumni of PSU, and aerospace enthusiasts with the vision statement of putting a cubesat into orbit with their own rocket. Their current airframe, named LV2, has served for over 12 years, representing 10 of the group's 13 launches, and hosted experiments ranging from custom patch antennas and long range WiFi technology to GPS navigation and a cold gas reaction control system (figure 1). The LV2 platform is mostly constructed of aluminum with a fiberglass shell, with many of the parts fabricated in home garages. This makes for a robust but heavy design. Additionally, this airframe is built with a 4.5 inch inner diameter which PSAS's experiments have outgrown.

The new airframe, named LV3, aims to address these issues and create a test platform for the technologies PSAS will use for their eventual shot at a 100 km launch. The LV3 platform uses a 6 inch inner diameter, modules composed of CF and thin aluminum coupling rings, a CF nose cone, and a CF fin section. All of the airframe components connect via standardized rings, to accommodate future experimental modules and flight configurations. The cylindrical LV3 airframe modules outperform the old design with an 80% reduction in weight.

*Portland State University, 1930 SW 4th Ave, Portland, OR 97201

A. Basic Design

The majority of the LV3 airframe uses a sandwich shell composed of CF faces surrounding an aramid honeycomb core (see figure 2). This provides a rigid structure while minimizing weight. Single sheets of CF are rigid when subjected to in-plane loading, and very flexible in bending. Meanwhile, the core is flexible in bending, and rigid under out-of-plane loading. When laminated together, these form a plate which is rigid in all loading conditions. The core material separates the rigid CF faces, greatly increasing the second moment of inertia of the plate. There is much more to the theory of sandwich plates and beams, but that is outside the scope of this paper.

The body of the airframe is composed of modular cylindrical sections using this sandwich design with aluminum coupling rings co-molded to each end. Each module can hold avionics, experiments, or other equipment with six tapped holes around the inside of the female coupling ring. For the radio module, fiberglass takes the place of the CF to allow radio transparency.

The fins use the same sandwich design, with an aluminum frame defining their planform. The center of the frame is filled with core material, and the whole surface is covered in CF. The leading and trailing edges of the fins are machined out of the aluminum frame. The fins are attached to a module with epoxy fillets, using chopped CF as a filler, and “tip-to-tip” CF sheets running from the tip of one fin across the module to the tip of the other fin.

The nose cone uses the same coupling ring system as the modules. It is a von Kármán ogive formed from two molded CF shells. Unlike the rest of the airframe, the nose cone uses a thin shell of two CF sheets, rather than a sandwich design (see section IV for details). The tip of the nose cone is machined out of aluminum and is removed when assembling the recovery system inside the nose cone.

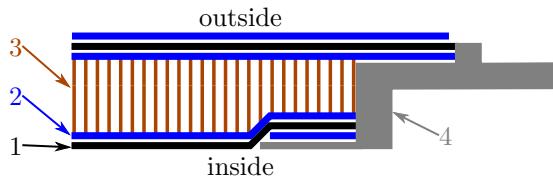


Figure 2. Diagram of the male end of a module. The CF (1) is bonded to the honeycomb core (3) and the aluminum coupling ring (4) using structural adhesive (2). The adhesive also serves as a protective coating for the CF and provides a smooth outer surface. See figure 3 for a picture of this design.

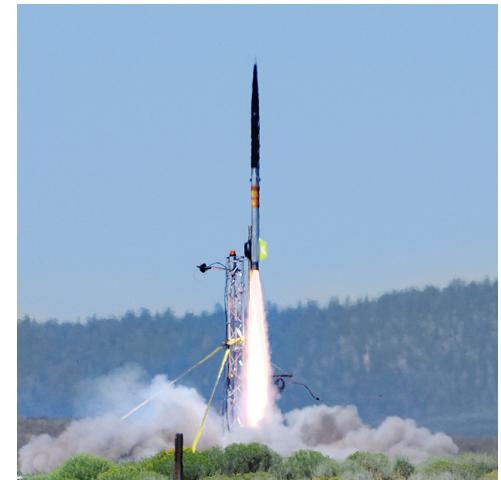


Figure 1. PSAS' LV2 rocket lifting off for the group's 13th launch. The custom cylindrical patch antenna can be seen as a brown band around the middle of the rocket.

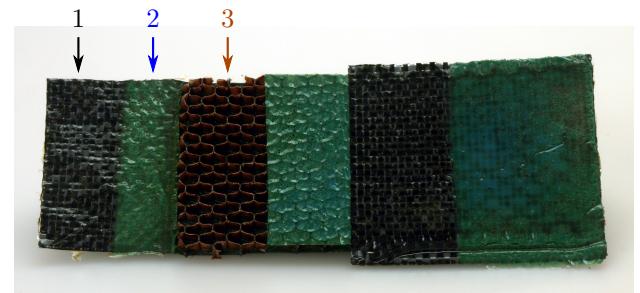


Figure 3. A cut-away sample displaying the layers used in the LV3 sandwich shells. See figure 2 for a diagrammatic depiction.

B. Significance

Many amateur and university rocketry groups use composite airframes. However, these designs use many layers of fabric, with low fiber volume fractions. While easy and durable, this does not fully take advantage of their materials. The LV3 design achieves a much higher specific strength and rigidity, enabling greater altitudes with a given motor.

This design also occupies an uncommon regime for sandwich shell designs. Most such designs use sandwich shells in large, low curvature parts, whereas the LV3 modules have a relatively small size and high curvature.

This is currently also the only fully open-hardware rocket airframe in the high power rocketry Level 3 range. All of the documentation, design, and testing information is freely available on PSAS's Github page.¹

II. Materials

Nearly all of the materials used in the LV3 airframe were donated. The pre-impregnated CF and the structural adhesive were made available after they expired for use in commercial aircraft. Acquiring expired materials from large manufacturers and distributors is the strongly preferred over purchasing them outright or simply using cheaper materials. Distributors are unlikely to offer these materials in quantities appropriate to this type of project, and purchasing them would be outside the budget of many university and amateur groups. Using CF cloth with painted-on epoxy could change the manufacturing significantly, and would increase the weight of the airframe. Acquiring donations is also a good way for university groups to form industry contacts. It can even become an opportunity to collaborate with other university groups, through the re-donation of excess material.

The CF is a plain weave design that is pre-impregnated with epoxy resin which cures at 350 °F. Meanwhile, the adhesive is an epoxy film which cures between 250 °F and 350 °F, intended for bonding metals and composites. This allows for co-curing of both materials together. The core material is an over-expanded honeycomb Nomex® mat which bonds well to the adhesive. Finally, the coupling rings are machined out of 6061-T6 aluminum.

Any groups obtaining materials through donations will likely not have much control over what materials they get, let alone be able to obtain the exact same materials listed here. As such, any potential donations should be researched before they are accepted and should be tested afterwards. The vast majority of person-hours for this project were spent characterizing the materials, and adapting the manufacturing to them. Any weave of CF will work, though satin is preferred. Pre-impregnated CF should be tacky at room temperature. Adhesive should either be tacky at room temperature or become tacky when heated. Ideally, it should flow at higher temperatures. The core material for the modules should be over-expanded or under-expanded. Optimally expanded honeycomb cannot be used for the modules, since it “potato chips”, bending away from the module along the axis when it is bent around the circumference. The fin core material may use any cell shape and should be 1/8 inch or smaller.

III. Cylindrical Modules

Each module has a male coupling ring on the end facing the direction of travel and a female coupling ring on the other end. Each ring has six pillars (see figure 9) which along the inside, which transfer the axial load to the adjacent rings. The motor is retained by a “spider” ring which screws into the six pillars, and a plate attaches to the last female ring to bear the thrust. Modules were made in both 18 inch and 24 inch lengths, to accommodate different lengths of motors and equipment. By exchanging modules of different lengths, this also allows the overall length of the rocket to be adjusted in increments of 6 inches. The body of the module consists of two concentric CF tubes separated by a honeycomb core, with adhesive bonding the CF to the core and rings (see figure 2). A layer of adhesive also covers the outer layer of CF, serving three roles. First, it ensures the outer layer of CF is completely wetted. The pre-impregnated CF used here did not completely wet when cured alone, however this will not be true for every product. Second, it serves as a protective coating for the CF. Third, it can be sanded to improve the surface roughness (see figures 4 and 5). Using a profilometer, the surface feature height of the uncoated modules was found to be 179 µm (7.1×10^{-3} in), while the surface features of the adhesive-coated modules could be sanded to 3.3 µm (1.3×10^{-4} in) (see figure 6).

The modules are formed by wrapping the layers around a male mandrel with the coupling rings secured to the mandrel. The coupling rings are each screwed to a dummy ring which emulates a connection to another module. The dummy rings are then screwed to the mandrel. This prevents any shifting during the cure due to thermal expansion or compaction from the vacuum bag and shrink tape (discussed later). The coupling rings are also chemically treated before the layup to prevent galvanic corrosion with the CF. A layer of release film is used to prevent the inner layer of CF from adhering to the mandrel. The adhesive layers naturally adhere to the CF layers with body heat from gloved hands, but a heat gun is required for adhering to the core. The core is compressed significantly in the circumferential direction and slightly in the axial direction to compensate for thermal expansion. This helps prevent grooves from forming at the edges of the core.

The entire layup is wrapped in shrink tape. Non-perforated, release-coated tape is preferred, but perforated tape is necessary if the adhesive or epoxy used out-gasses. The shrink tape compacts the module,



Figure 4. A sandwich plate sample which has been coated with structural adhesive. The left side has been sanded and polished. See figure 6 for a plot of the surface profile.



Figure 5. A sandwich plate sample which has *not* been coated with structural adhesive. See figure 6 for a plot of the surface profile. Note the dry cells where the epoxy has not wetted the CF.

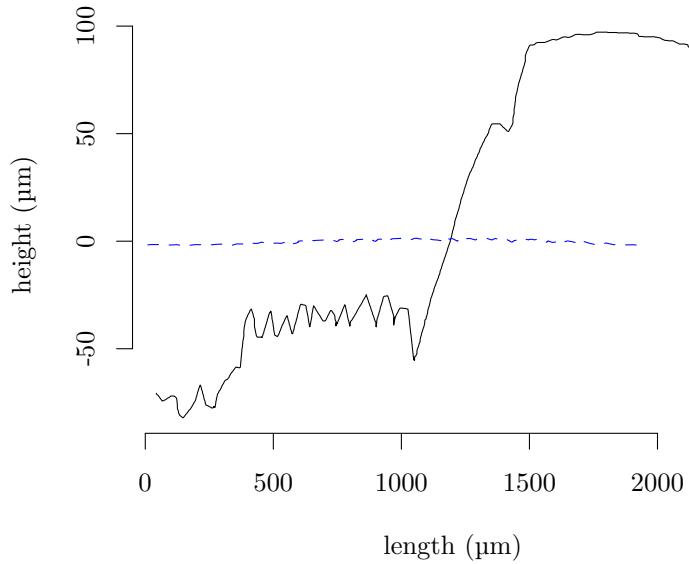


Figure 6. Surface roughness profile for unsurfaced CF (black, solid) and polished, adhesive-surfaced CF (blue, dashed). The mean height has been removed from both. Note the dry (400 μm to 1000 μm) and wet (1500 μm to 2500 μm) cells in the unsurfaced CF. See figures 4 and 5 for pictures of the two surfaces.

strengthening the bond between the CF and core while also flattening any irregularities in the surface of the module. After curing, the outer layer of adhesive is sanded and polished to obtain a smooth surface, completing the module.

A. Destructive Testing

Rather than yielding like traditional engineering materials, this design “pings” as the most heavily loaded fibers begin to break and sections of core material experience small delaminations from the faces.

A complete 18 inch CF module was subjected to compressive loading along its axis. This was done by attaching dummy rings, which emulate a connection to another module, and loading the dummy rings through a flat plate. A load cell was used to record the load, while strain gauges recorded axial strain in two locations (see figure 7). The time and corresponding load at which audible pinging occurred was also recorded. The load was slowly increased using a hydraulic press. Similar tests were performed with a fiberglass module, a CF module where the CF layers were delaminated from the core, and a CF module with the load applied laterally via a 2 inch wide beam, to puncture the module. These results can be seen



Figure 7. Positioning of the strain gauges referred to in figure 8. The gauges have been circled with colors corresponding to figure 8. Both are aligned with one of the pillars shown in figures 9 and 10. The bottom gauge is positioned directly above the point of failure.

in table 1.

In compressive loading, both the CF and fiberglass modules failed through buckling of the composite layers at the interface between the inner layer and one of the coupling rings. This resulted in the composite layers subducting under themselves (see figure 10). Failure occurred uniformly around the inner and outer layers, both at the same distance along the axis of the modules. In the delaminated module, one of the coupling rings was simply pushed into the space occupied by the core material.

The CF modules exhibited linear-elastic behavior, as shown in figure 8, with the stress being concentrated near the pillars shown in figure 9. This suggests that if more pillars were added, the stress concentration would be reduced, increasing the strength of the module.

The modules are much more susceptible to concentrated surface loading than to axial loading (see table 1). The deformation from the beam delaminated the CF layers from the core and eventually tore the outer layer of CF. This mode of failure poses a significant threat to the modules when the rocket lands. During this phase of the flight, the airframe could impact rocks or bushes, potentially delaminating or puncturing the outer CF layer.

The poor performance of the delaminated module and the module subjected to concentrated surface loading suggest that all flight modules should be thoroughly checked for delaminations after landing. Currently, delaminations are located by squeezing modules by hand, looking for sections which are not rigid.

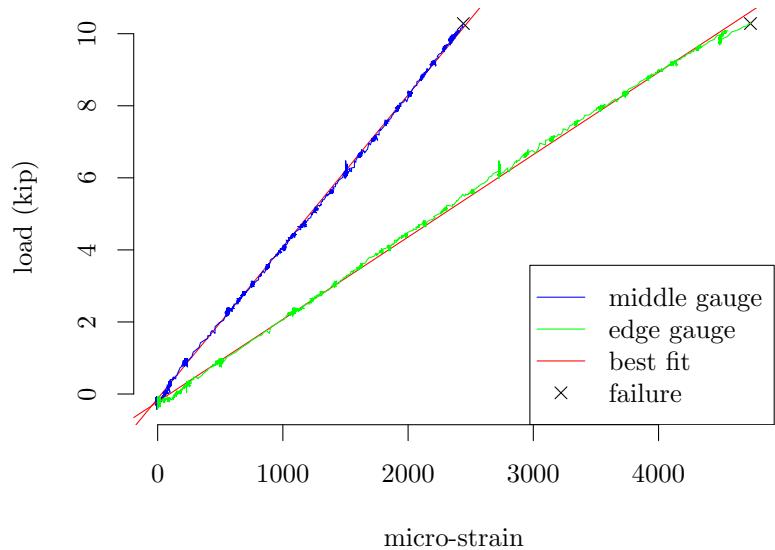


Figure 8. Axial strain data from an axial compression test of an 18 inch CF module. Data was recorded at locations directly above the point of failure (green) and near the middle of the module (blue), both on the outside surface (see figure 7).

Table 1. Failure strengths for different modules.

Material	Loading	Pinging Strength	Ultimate Strength
CF	axial	7×10^3 lb	10×10^3 lb
CF	puncture	<100 lb	<100 lb
delaminated CF	axial	<100 lb	<100 lb
fiberglass	axial	2×10^3 lb	5×10^3 lb

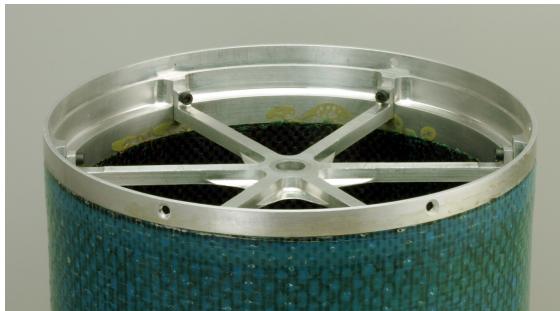


Figure 9. A CF module with the “spider” attachment, which retains the motor in the rocket. The female end is shown.

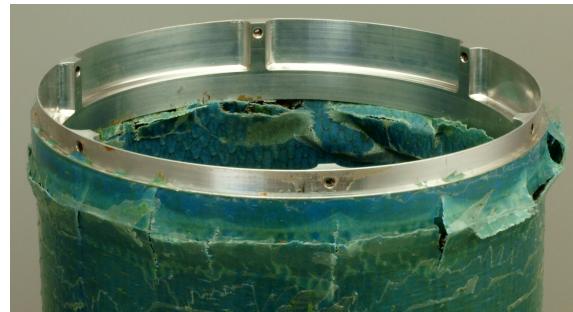


Figure 10. A fiberglass module after failing in compression. Note that the failure on the inner and outer layers occurred at the same height. The male end is shown.

IV. Nose Cone

The nose cone consists of a removable aluminum tip, a curved von Kármán body, a 6 inch cylindrical section, and a female coupling ring. The aluminum tip provides a smooth leading surface, avoids the problems with forming CF to small radii, and can be removed to assist with assembling the recovery system. Unlike the modules, most of the nose cone does not use a sandwich design. The von Kármán section does not contain any core material, instead using multiple layers of pre-impregnated CF. This is intended to mitigate puncturing of the nose cone during landing (see section III A). Rather than remaining rigid, this section should bend under impacts with rocks, bushes, or the airframe. Additionally, the buckling strength added by the core is unnecessary in the nose cone, since it experiences very little load. The cylindrical section uses core material to ensure a good connection to the coupling ring. The extra length added by this section helps accommodate the recovery system.

Several manufacturing processes were considered for the nose cone, including a curved aluminum mandrel similar to the one used for the modules, a two-part aluminum mold, and various half molds. The limiting factor in the manufacturing was the fact that any material used must be compatible with the 350°F cure cycle required by the pre-impregnated CF. The final design uses a half mold made of laminated high-temperature machinable foam sheets, with a von Kármán shaped cavity machined out and sealed with epoxy. Although this material is not typically used for final molds, it is a solution with relatively low cost and high ease of manufacturing, which is important for low-budget university teams.

Thermal expansion presented several challenges during manufacturing. The sheets of machinable foam had to be vacuum bagged during lamination, to prevent warping. Pre-impregnated CF has a CTE of only $10 \times 10^{-6} \text{ K}^{-1}$, unlike the machinable foam which has a larger CTE of $48 \times 10^{-6} \text{ K}^{-1}$. If the CF of the nose cone spans the inside of the mold, it can fracture the mold. This is because the CF cures while the mold is expanded, but does not shrink with the mold when it cools. Thus, it pushes out on the mold.

The nose cone is molded as two separate halves. These are then co-bonded together with the aluminum coupling ring and a small mounting ring which attaches to the aluminum tip. After curing, the outside of the nose cone is sprayed with a high temperature paint, which is then lightly sanded and polished.

A. OpenFOAM

OpenFOAM is an open-source application which provides a common interface for a wide range of CFD solvers. Although it requires more up-front effort, it allows a more detailed perspective on what features of an airframe's geometry are the most critical. CFD analysis is probably not necessary for most amateur and university level airframe design, but this provides a good option for groups that can't afford a licence for a commercial CFD suite.

OpenFoam was used to asses the heating at the tip of the nose, to determine if the epoxy matrix of the CF would degrade over repeated flights. It was determined that heating at the tip of the nose cone was not a significant issue for this size of rocket.

V. Fin Section

The fins are constructed around a 1/8 inch aluminum frame filled with core material and co-molded with CF sheets on either side. These fins are then aligned to a 24 inch module using a jig, and attached with epoxy fillets, using chopped CF as a filler. After curing the fillets, the fins have CF sheets laid "tip-to-tip," running from the tip of one fin across the module to another fin. Structural adhesive is used to surface the fins, similar to the modules.

Like the nose cone, many manufacturing options were available for the fins. Initially, the frames were to include a flange at their root and be machined out of a single block of aluminum. However, the machining for this part would be prohibitively difficult or expensive for most university groups. Laser cutting the frames would be more viable, but could result in a warped frame. Cutting with a water jet was chosen, since it does not cause warping and is still viable for university and amateur groups. Machining the frames would also be a good option for such groups.

A. OpenRocket

For the early design of amateur and university scale rockets, OpenRocket² is highly recommended. It is an open-source Java application which simulates a rocket's flight. It provides a convenient interface for configuring the rocket, selecting commercial or custom parts, viewing the predictions, and performing some basic optimization.

Using OpenRocket to guide the initial design allowed for rapid iteration of the fin geometry and the placement of non-airframe components. It is also useful for keeping track of payloads and estimating mass budgets.

VI. Future Research

The nonuniform stress in the compressed CF modules (section III A) presents an opportunity to compare these results to a finite element model. Due to the required time and lack of immediate benefits, this has not been pursued.

The surface finish of this design could be improved by filling the small voids in the adhesive coating. This would not provide much benefit to the LV3 platform, but may be useful in other applications.

It may be possible to adapt this design into an inline fuel tank, further reducing the rocket's total weight. This would provide another significant advantage over other university and amateur groups, which continue to use much heavier tanks. PSAS plans to develop inline fuel tanks based on this design in the near future.

Any groups hoping to copy or build on this design, will likely need to adapt their design and manufacturing to their particular materials. Such groups should refer to this project's Github repository¹ for details on the particular materials, CAD models, experimental data, simulations, and design logs.

VII. Conclusions

This design provides a strong, lightweight, low-cost testing platform which will be a significant advantage in PSAS' race towards 100 km. Any university or amateur groups able to acquire the necessary materials should be able to build similar rockets, reaching much higher altitudes without upgrading to larger motors. It is strongly advised, however, that such groups thoroughly inspect their modules for delaminations, since

these will compromise their strength.

VIII. Acknowledgements

This project was made possible by donations from Boeing, Machine Sciences Corporation, Pacific Coast Composites, Esco, the Maseeh College Innovation Council's Beta Project grant, and the many individual donors who support PSAS.

The authors gratefully acknowledge Andrew Greenberg, Erin Schmidt, and Dr. Mark Weislogel for their guidance throughout the project. Special thanks also goes to Jack Slocum, Sam Arnold, Erik Nelson, Jacob East, Robert Melchione, Marett Strecker, and Tung Nguyen for their work prototyping the cylindrical modules, to Ian Zabel and Alex Farias for designing parts to interface with the avionics and recovery systems, and to Alexander Chally for his work creating tooling for the nose cone.

References

¹Shields, J., Zabel, I., Elwood, L., Slocum, J., and Arnold, S., "LV3 Airframe Repository," <https://github.com/psas/lv3-airframe>, Aug. 2016.

²Niskanen, S., "OpenRocket technical documentation," 2013.