MAELAS code

User manual v1.0.1

Authors:
P. Nieves
S. Arapan
S.H. Zhang
A.P. Kądzielawa
R.F. Zhang
D. Legut

August 6, 2020

MAELAS: MAgneto-ELAStic properties calculation via computational high-throughput approach

VSB TECHNICAL UNIVERSITY OF OSTRAVA | IT4INNOVATIONS NATIONAL SUPERCOMPUTING CENTER

Outline

- WHAT IS MAGNETOSTRICTION?
- WHAT IS MAELAS CODE?
- INSTALLATION
- HOW TO USE MAELAS CODE
- METHODOLOGY
- WORKFLOW
- BRIEF REVIEW OF KNOWN MAGNETOSTRICTIVE MATERIALS
- MAELAS TESTS
- BIBLIOGRAPHY

WHAT IS MAGNETOSTRICTION?

Magnetostriction is a physical phenomenon in which the process of magnetization induces a change in shape or dimension of a magnetic material.
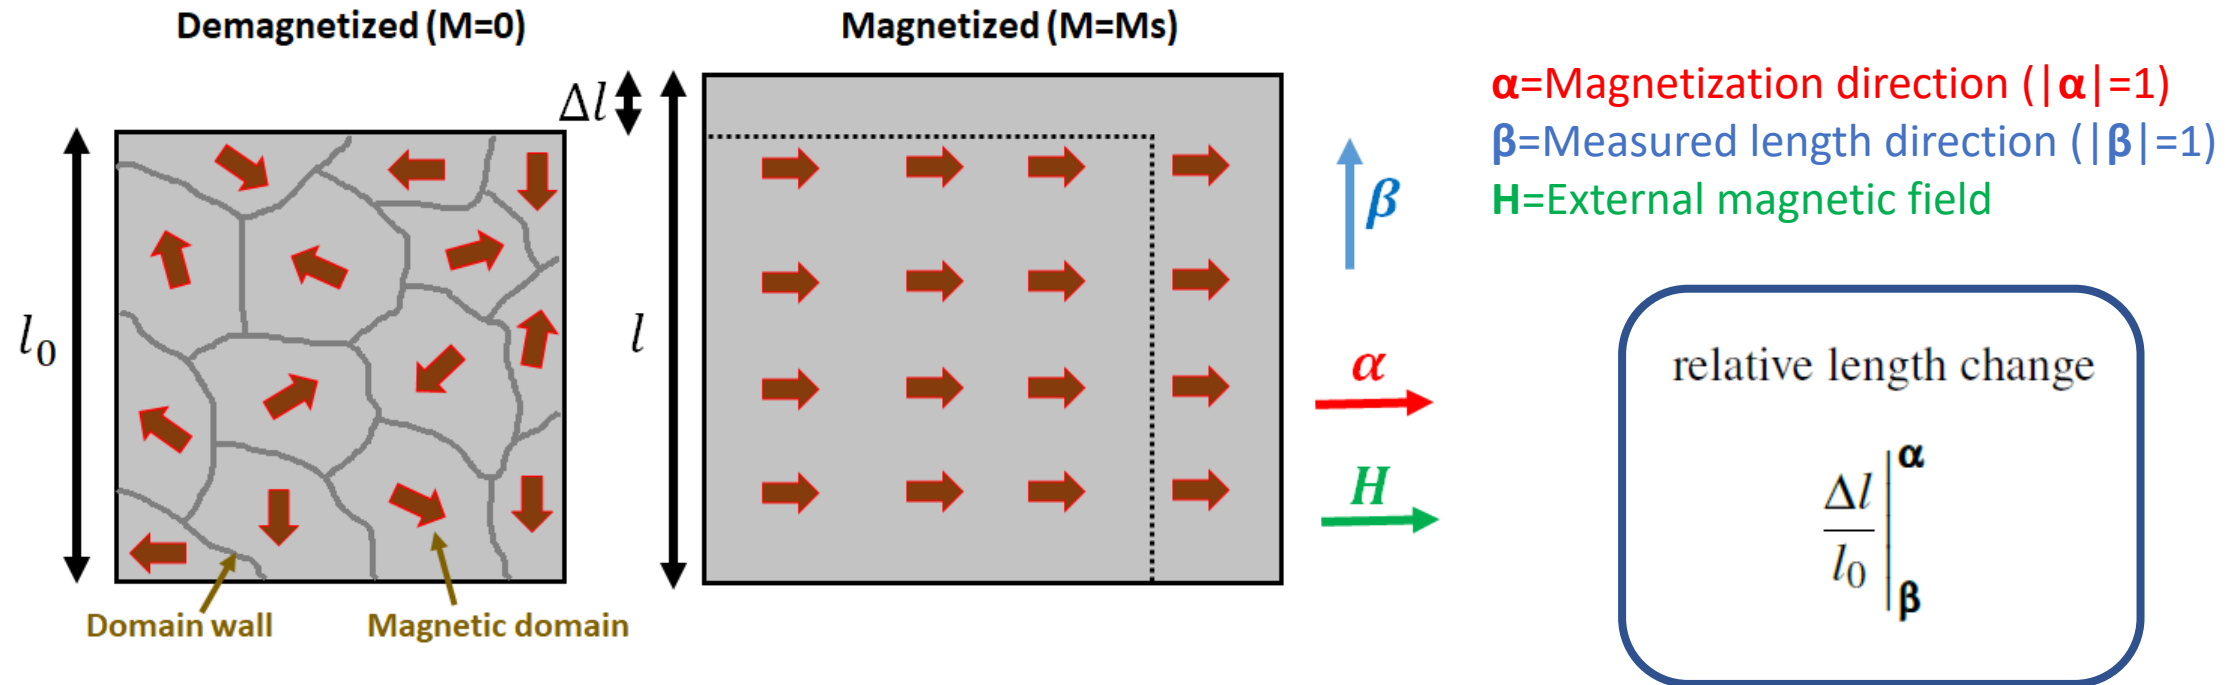

Demagnetized (M=0)

Magnetized (M=Ms)

Δl

l_0

l

Domain wall   **Magnetic domain**

β

α

H

α=Magnetization direction (|**α**|=1)
β=Measured length direction (|**β**|=1)
H=External magnetic field

relative length change

$$\left.\frac{\Delta l}{l_0}\right|_{\beta}^{\alpha}$$

Figure 1: Magnetostriction of a single crystal under an external magnetic field ($\boldsymbol{\alpha}\|\boldsymbol{H}$) perpendicular to the measured length direction ($\boldsymbol{\beta}\perp\boldsymbol{H}$). Symbols M and M_s stand for macroscopic magnetization and saturation magnetization, respectively. Dash line on the right represents the original size of the demagnetized material. The magnetostriction effect has been magnified in order to help to visualize it easily, in real materials it is smaller ($\Delta l/l_0 \sim 10^{-3} - 10^{-6}$).

WHAT IS MAELAS CODE?

➢ MAELAS code is a software to calculate anisotropic magnetostriction coefficients and magnetoelastic constants up to second order.

➢ It generates required input files for VASP code to perform Density Functional Theory calculations, and it deduces the value of magnetostriction coefficients from the calculated energies given by VASP.

➢ If the elastic tensor is provided, then it can also calculate the magnetoelastic constants.

➢ MAELAS can also be used with other DFT codes instead of VASP, after file conversion to VASP format files.

INSTALLATION

The MAELAS code requires to have Python3(>=3.6). For example, in Ubuntu Linux machine you can check the installed version of python3 by opening a terminal and typing

python3 --version

In case you need to install python3 in your machine, you can type

sudo apt-get update
sudo apt-get install python3

Note that in some HPC clusters you might need to load the Python module (ml Python). The MAELAS code can be easily installed with pip3 as

pip3 install maelas

This procedure will also install all required dependencies automatically

pymatgen(>=2020.4.29), scikit-learn(>=0.23.1), pyfiglet(>=0.8.post0), argparse(>=1.4.0), numpy(>=1.18.4), matplotlib(>=3.2.1), scipy(>=1.4.1)

The executable file "maelas" is installed in the folder /home/user_name/.local/bin/ where "user_name" is the name of your user name folder. This folder should be added to the PATH by adding the following line in the file /home/user_name/.bashrc
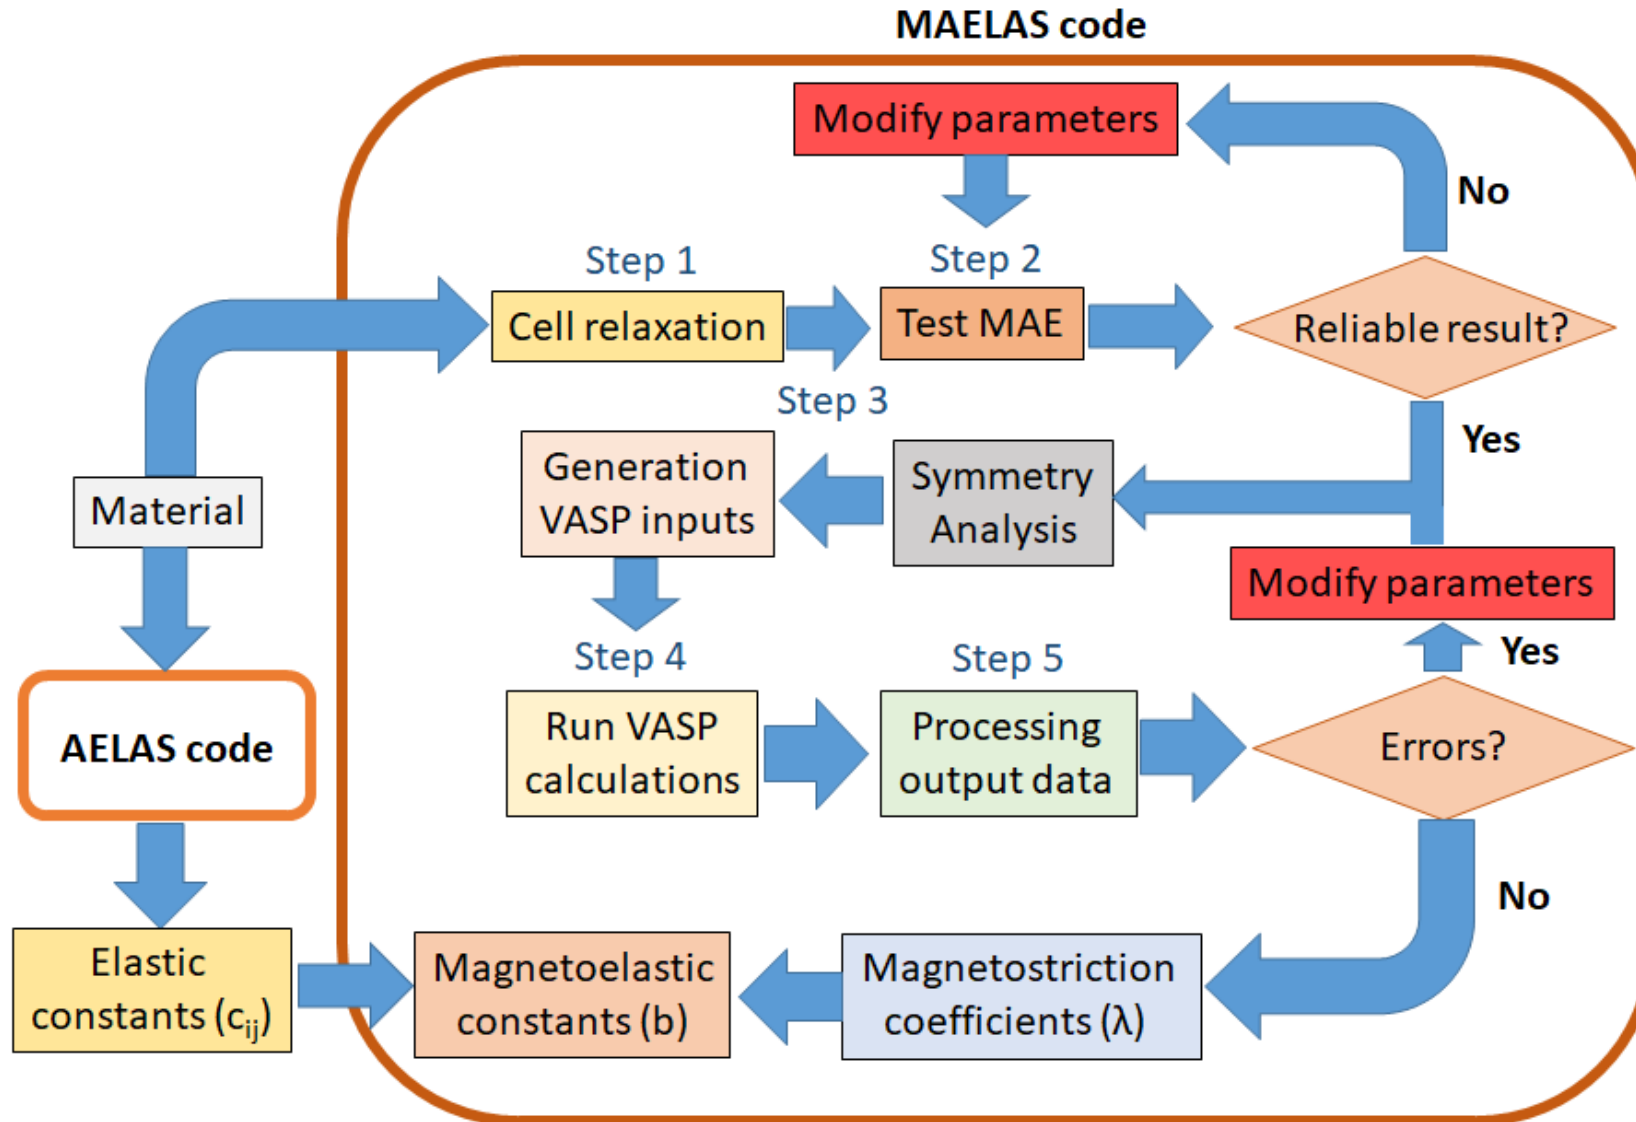
export PATH=/home/user_name/.local/bin/:$PATH

Then you should close the terminal and open the terminal again.

If you need to install pip3 in Ubuntu Linux, then type

sudo apt-get update
sudo apt-get install python3-pip

HOW TO USE MAELAS CODE

HOW TO USE MAELAS CODE

Step 1: Cell relaxation

If your initial POSCAR is not relaxed and you want to perform a cell relaxation before calculating the magnetostriction coefficients, then you can use MAELAS code to generate INCAR and KPOINTS files to relax the structure with VASP. To do so, in the terminal you should copy your initial POSCAR in the same folder where you want to generate the input files for VASP, and after going to this folder then type

maelas -r -i POSCAR0 -k 40

where tag -r indicates that you want to generate VASP files for cell relaxation, -i POSCAR0 is the input non-relaxed POSCAR file (you can name it whatever you want) and -k 40 is the length parameter that determines a regular mesh of k-points. It will generate 4 files: POSCAR, INCAR, KPOINTS and vasp_jsub_rlx. Here, one still needs to copy manually the POTCAR file in this folder in order to have all required files for VASP run. The generated file vasp_jsub_rlx is a script to submit jobs in HPC facilities, one can specify some settings in this script by adding more tags in the command line. For instance,

maelas -r -i POSCAR0 -k 40 -t 48 -c 24 -q qprod -a OPEN-00-00 -f /scratch/example_rlx

where -t 48 indicates that the number of maximum CPU hours for the VASP calculation is 48 hours,-c 24 means that the number of cores for the VASP calculation is 24, -q qprod set the type of queue in HPC facilities, -a OPEN-00-00 is the project identification number for running jobs in HPC facilities and -f /scratch/example_rlx is the folder where you want to run VASP calculations. All these data are included in the vasp_jsub_rlx file, so one can submit this VASP job immediately in HPC facilities by typing

qsub vasp_jsub_rlx

This procedure might be helpful for high-throughput routines. Note that the user might need to modify vasp_jsub_rlx (it is in PBS Pro format) depending on the cluster or local computer batch scheduling. More options can be added in vasp_jsub_rlx file through the terminal command line, to see them just type

maelas –h

Note that generated INCAR and KPOINTS files contain standard setting for cell relaxation. The user might need to change these files in order to include more advanced settings. In case your structure is already relaxed or you do not want to perform a cell relaxation, then you can skip this step and move to step 2.

HOW TO USE MAELAS CODE

Step 2: Test MAE

Copy the relaxed POSCAR and POTCAR files in the same folder where you want to generate the input files for VASP jobs. In the terminal, after going to this folder then type

maelas -m -i POSCAR_rlx -k 70 -s1 1 0 0 -s2 0 0 1

where -m indicates that you want to generate input VASP files for the calculation of MAE, -i POSCAR_rlx is the initial relaxed POSCAR file (you can name it whatever you want), -k 70 is the length parameter that determines a regular mesh of k-points, -s1 1 0 0 is the first spin direction to calculate MAE: s1x s1y s1z and –s2 0 0 1 is the second spin direction to calculate MAE: s2x s2y s2z . It will generate the following files:

POSCAR_0_0 (it is the same POSCAR as)
INCAR_0_C (non-collinear calculation where C=1,2 is the spin orientation case)
INCAR_std (collinear calculation to generate the WAVECAR and CHGCAR files to run non-collinear calculations)
KPOINTS (file for the kpoint generation of VASP)
vasp_mae, vasp_mae_jsub and vasp_mae_0 (interconnected bash scripts to run VASP calculations automatically)
vasp_mae_cp_oszicar (bash script to get the calculated OSZICAR_0_0_C files after VASP calculation is finished)

The generated files vasp_mae, vasp_mae_jsub and vasp_mae_0 are interconnected scripts to submit jobs in HPC facilities. One needs only to execute the file vasp_mae in order to run all VASP jobs automatically. You can specify some job settings in these scripts by adding more tags in the command line. For instance,

maelas -m -i POSCAR_rlx -k 70 -s1 1 0 0 -s2 0 0 1 -t 48 -c 24 -q qprod -a OPEN-00-00 -f /scratch/example_mag

where -t 48 indicates that the number of maximum CPU hours for the VASP calculation is 48 hours,-c 24 means that the number of cores for the VASP calculation is 24, -q qprod set to production queuethe type of queue in HPC facilities, -a OPEN-00-00 is the project identification number for running jobs in HPC facilities and -f /scratch/example_mag is the folder where you want to run VASP calculations. This procedure might be helpful for high-throughput routines. Note that the user might need to modify vasp_mae_jsub (it is in PBS Pro format) depending on the cluster or local computer batch scheduling. More options can be added in these script files through the terminal command line, to see them just type

maelas -h

HOW TO USE MAELAS CODE

Step 3: Generation of VASP files for the calculation of anisotropic magnetostriction coefficients

Copy the relaxed POSCAR and POTCAR files in the same folder where you want to generate the input files for VASP run. In the terminal, after going to this folder then type

maelas -g -i POSCAR_rlx -k 70 -n 7 -s 0.1

where -g indicates that you want to generate input VASP files for the calculation of anisotropic magnetostriction coefficients, -i POSCAR_rlx is the initial relaxed POSCAR file (you can name it whatever you want), -k 70 is the length parameter that determines a regular mesh of k-points, -n 7 means that it will generate 7 distorted states for each magentostriction mode and -s 0.1 is the maximum strain applied for distorting the structure. It will generate the following files:

POSCAR_A_B (volume-conserving distorted cell where A=magnetostriction mode, B=1,...,n distorted cell for each magentostriction mode)
INCAR_A_C (non-collinear calculation where A=magnetostriction mode, C=1,2 is the spin orientation case)
INCAR_std (collinear calculation to generate the WAVECAR and CHGCAR files to run non-collinear calculations)
KPOINTS
vasp_maelas, vasp_jsub and vasp_0 (interconnected bash scripts to run VASP calculations automatically)
vasp_cp_oszicar (bash script to get the calculated OSZICAR_A_B_C files after VASP calculation is finished)

The generated files vasp_maelas, vasp_jsub and vasp_0 are interconnected scripts to submit jobs in HPC facilities, one can specify some job settings in these scripts by adding more tags in the command line. For instance,

maelas -g -i POSCAR_rlx -k 70 -n 7 -s 0.1 -t 48 -c 24 -q qprod -a OPEN-00-00 -f /scratch/example_mag

where -t 48 indicates that the number of maximum CPU hours for the VASP calculation is 48 hours, -c 24 means that the number of cores for the VASP calculation is 24, -q qprod set the type of queue in HPC facilities, -a OPEN-00-00 is the project identification number for running jobs in HPC facilities and -f /scratch/example_mag is the folder where you want to run VASP calculations. This procedure might be helpful for high-throughput routines. Note that the user might need to modify vasp_jsub (it is in PBS Pro format) depending on the cluster or local computer batch scheduling. More options can be added in these script files through the terminal command line, to see them just type

maelas –h

HOW TO USE MAELAS CODE

Step 4: Run VASP calculations

For each generated POSCAR_A_B one should run first a collinear calculation using INCAR_std and use the generated WAVECAR and CHGCAR files to run non-collinear calculations for each INCAR_A_C (C=1,2) using the same POSCAR_A_B. This procedure can be automatically done in HPC facilities just by running the generated bash script

./vasp_maelas

This will launch independent jobs for each POSCAR_A_B. Each job will run 3 VASP calculations: a collinear one (VASP executable "vasp_std") to generate WAVECAR and CHGCAR files, and two non-collinear (VASP executable "vasp_ncl") for INCAR_A_1 and INCAR_A_2. The jobs will be executed in subfolders P_A_B inside the folder indicated by tag -f in the step 2. Note that the user might need to modify vasp_jsub depending on the cluster or local computer queuing system.

Once all jobs are finished, then one can easily get calculated non-collinear OSZICAR files (needed in step 4), by running the bash script

./vasp_cp_oszicar

it will copy these OSZICAR files and name them as OSZICAR_A_B_C (C=1,2) in the same folder where this script is executed.

VASP executables:

"vasp_std" is the standard version of vasp without spin-orbit coupling (LNONCOLLINEAR = .FALSE., LSORBIT = .FALSE.)

"vasp_ncl" is for non-collinear calculations for instance to perform fully non-collinear magnetic structure calculations or to include spin-orbit interactions in the calculations (LSORBIT = .TRUE.)

HOW TO USE MAELAS CODE

Step 5: Derivation of anisotropic magnetostriction coefficients and magnetoelastic constants

Finally, to derive the anisotropic magnetostriction coefficients one needs to have in the same folder the following files:

POSCAR_rlx (the relaxed POSCAR file used as input in step 3)
POSCAR_A_B (distorted POSCAR generated in step 3)
OSZICAR_A_B_C (non-collinear OSZICAR files calculated in step 4 for each POSCAR_A_B and INCAR_A_C)

Next, in the terminal go to this folder a type

maelas -d -i POSCAR_rlx -n 7

where -d indicates that you want to derive the spin-dependent magnetostriction coefficients from the calculated OSZICAR files, -i POSCAR_rlx is the relaxed POSCAR file used as input in step 3 (you can name it whatever you want) and -n 7 is the number of distorted states for each magentostriction mode used in step 3.

It will derive and print the calculated anisotropic magnetostriction coefficients in the terminal. If you want to print it in a file (for example, "results.out"), then you can type

maelas -d -i POSCAR_rlx -n 7 > results.out

Additionally, the energy values extracted from OSZICAR_A_B_C files are shown in generated files ene_A_C.dat and fit_ene_A_C.png. The energy difference between the two spin configurations for each magnetostriction mode are shown in Fig. dE_A.png. If the elastic tensor is provided as input, then MAELAS can also calculate the magnetoelastic constants. To do so, one needs to add tags -b and -e with the name of the file containing the elastic tensor with the same format and units (GPa) as it is written by AELAS code (file ELADAT). Hence, you could type

maelas -d -i POSCAR_rlx -n 7 -b -e ELADAT

where ELADAT is the name of the file (it could be whatever name you want) with the elastic tensor data.

Format of the elastic tensor file →

```
Elastic tensor:
262.03  186.20  186.20    0.00    0.00    0.00
186.20  262.03  186.20    0.00    0.00    0.00
186.20  186.20  262.03    0.00    0.00    0.00
  0.00    0.00    0.00  116.63    0.00    0.00
  0.00    0.00    0.00    0.00  116.63    0.00
  0.00    0.00    0.00    0.00    0.00  116.63
```

Full list of arguments in MAELAS code

User can see all possible optional arguments by typing

maelas -h

The optional arguments are the following:

-h, --help   Show this help message and exit
 -i POS   Name of the initial non-distorted POSCAR file (default: POSCAR)
-n NDIST   Number of distorted states for each magnetostriction mode (default: 7)
-s STRAIN   Maximum value of the parameter epsilon for the strain tensor to generate the distorted POSCAR files (default: 0.01)
-k KP   VASP automatic k-point mesh generation to create the KPOINTS file (default: 60)
-g   Generation of required VASP files for the calculation of magnetostriction coefficients.
-d   Derivation of magnetostriction coefficients from the energy written in the OSZICAR files.
-r   Generation of required VASP files for the cell relaxation
-m   Generation of required VASP files to test MAE
-s1 s1x s1y s1z   First spin direction to calculate MAE
-s2 s2x s2y s2z   Second spin direction to calculate MAE
-b   Calculation of the magnetoelastic constants from the calculated magnetostriction coefficients and provided elastic tensor.
-e ELAS   File with the elastic tensor data in the same format and units (GPa) as it is written by ELAS code (file ELADAT).
-sp SYMPRE   Tolerance for symmetry finding (default: 0.01)
-sa SYMANG   Angle tolerance for symmetry finding (default: 5.0)
-sg SG0   Space group number 1-230. If it is equal to 0, then it will be determined by a symmetry analysis (default: 0)
-c CORE   Number of cores for the VASP calculation (default: 24)
-t TIME   Number of maximum CPU hours for the VASP calculation (default: 48)
-f VASP_FOLD   Folder where you will run VASP calculations (default: /scratch)
-mp MPI   Command for mpi run of VASP (default: mpiexec.hydra)
-a P_ID   Project id for running jobs in HPC facilities (default: OPEN-X-X)
-l LOAD_MODULE Module of VASP that should be loaded (default: VASP/5.4.4-intel-2017c-mkl=cluster)
-q QUEUE   Type of queue to be used for VASP calculations in HPC facilities (default: qprod)

HOW TO USE MAELAS CODE

Summary: In a nutshell

Step 1: Cell relaxation

maelas -r -i POSCAR0 -k 40

qsub vasp_jsub_rlx

Step 2: Test MAE

maelas -m -i POSCAR_rlx -k 70 -s1 1 0 0 -s2 0 0 1

./vasp_mae

./vasp_mae_cp_oszicar

Step 3: Generate VASP inputs for calculation of magnetostriction coefficients

maelas -g -i POSCAR_rlx -k 70 -n 7 -s 0.1

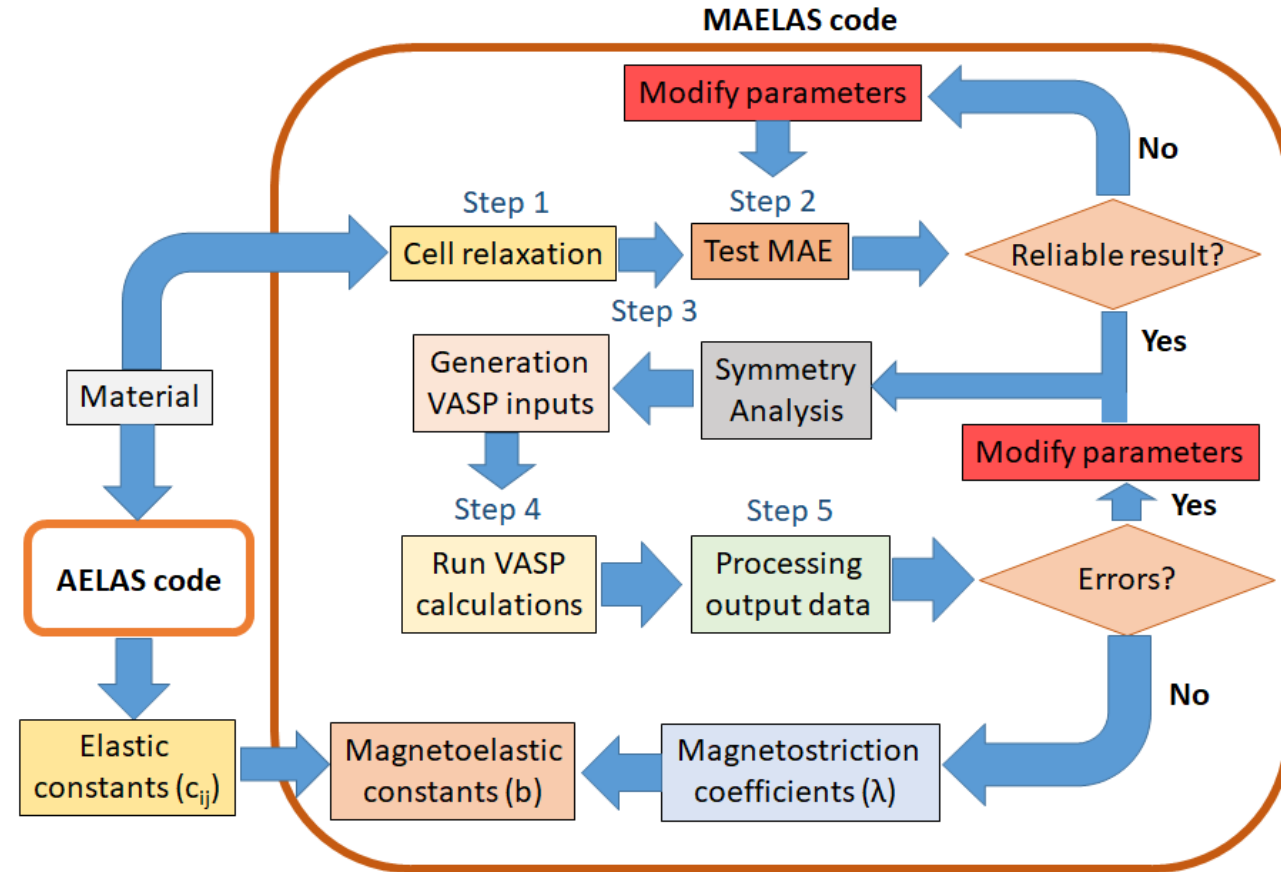**Step 4:** Run VASP calculations

./vasp_maelas

./vasp_cp_oszicar

Step 5: Derivation of anisotropic magnetostriction coefficients

maelas -d -i POSCAR_rlx -n 7

Step 5: Derivation of anisotropic magnetostriction coefficients and magnetoelastic constants

maelas -d -i POSCAR_rlx -n 7 -b -e ELADAT

See all optional arguments: maelas -h

Using MAELAS with other DFT codes instead of VASP

MAELAS has been designed to read and write files for VASP code automatically. However, it is possible to use MAELAS with other DFT codes instead of VASP, after file conversion to VASP format files. Although, this process might require some extra work for the user. Namely, converting initial and distorted POSCAR files into the other DFT code format, reading the spin direction of each state from INCAR_A_C files (variable SAXIS) and write the calculated energies in a OSZICAR-like file (called OSZICAR_A_B_C) on the penultimate line and third column with same format as in VASP (this is the place where MAELAS reads the energy value of each OSZICAR_A_B_C file). For instance, in the following OSZICAR-like file, one should write the calculated energy value at "**Energy_DFT_code**":

```
       N           E                    dE              d eps          ncg        rms            rms(c)
DAV:   1      -0.219086777516E+02   -0.21909E+02     0.99185E+02******   0.709E+00
DAV:   2      -0.219092777733E+02   -0.60002E-03    -0.60002E-03******   0.452E-01
DAV:   3      -0.219092846144E+02   -0.68411E-05    -0.68405E-05******   0.485E-02
DAV:   4      -0.219092847670E+02   -0.15258E-06    -0.15274E-06******   0.641E-03
DAV:   5      -0.219092847725E+02    0.55161E-08    -0.52995E-08******   0.117E-03
DAV:   6       **Energy DFT code**  -0.19827E-09    -0.11530E-09868760   0.143E-04
     1 F= -.21909285E+02 E0= -.21909330E+02   d E =0.135168E-03   mag=      0.0000      0.0000    2.5077
```
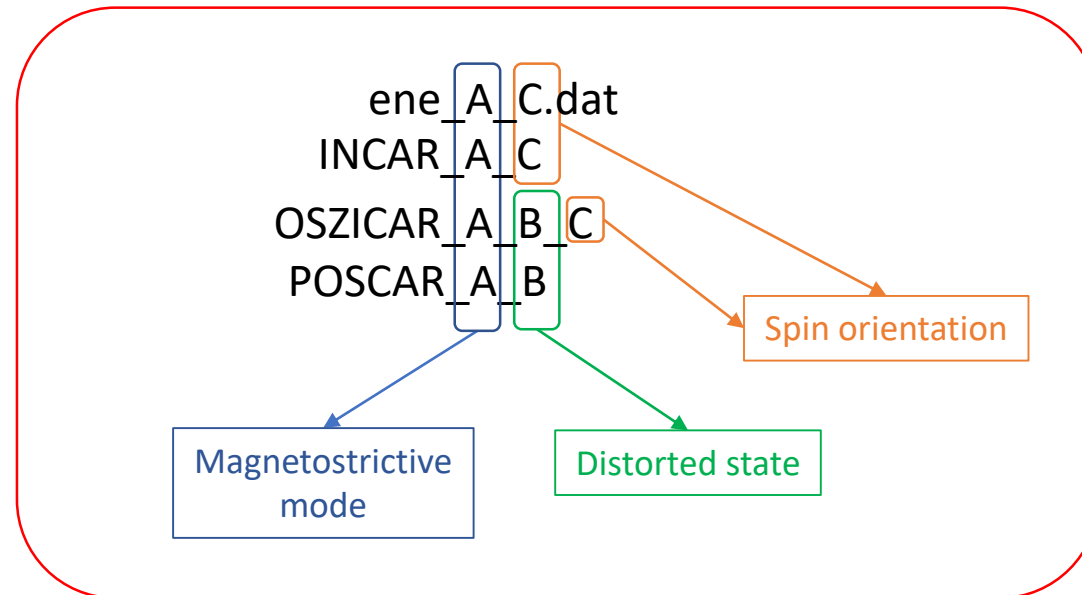
Crystal systems supported by MAELAS v1.0

Table 1: Number of independent second-order elastic constants of each crystal system. Number of independent magnetoelastic and magnetostriction coefficients up to second-order of the direction cosine polynomial in the first-order magnetoelastic energy. In the last column we specify which crystal systems are supported by the current version of MAELAS.

Crystal system	Point groups	Space groups	Elastic constants (c_{ij})	Magnetoelastic constants (b)	Magnetostriction coefficients (λ)	MAELAS
Triclinic	$1, \bar{1}$	$1-2$	21	36	36	No
Monoclinic	$2, m, 2/m$	$3-15$	13	20	20	No
Orthorhombic	$222, 2mm, mmm$	$16-74$	9	12	12	Yes
Tetragonal (II)	$4, \bar{4}, 4/m$	$75-88$	7	10	10	No
Tetragonal (I)	$4mm, 422, \bar{4}2m, 4/mmm$	$89-142$	6	7	7	Yes
Trigonal (II)	$3, \bar{3}$	$143-148$	7	12	12	No
Trigonal (I)	$32, 3m, \bar{3}m$	$149-167$	6	8	8	Yes
Hexagonal(II)	$6, \bar{6}, 6/m$	$168-176$	5	8	8	No
Hexagonal (I)	$6mm, 622, \bar{6}2m, 6/mmm$	$177-194$	5	6	6	Yes
Cubic (II)	$23, m\bar{3}$	$195-206$	3	4	4	No
Cubic (I)	$432, \bar{4}3m, m\bar{3}m$	$207-230$	3	3	3	Yes

The crystal systems not supported by MAELAS might be included in the new versions of the code

HOW TO USE MAELAS CODE

MAELAS file notation

ene_A_C.dat
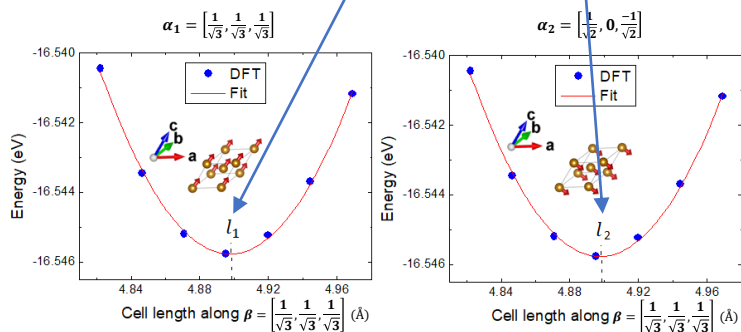INCAR_A_C
OSZICAR_A_B_C
POSCAR_A_B

Magnetostrictive mode

Distorted state

Spin orientation

Methodology

$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}^i}^{\boldsymbol{\alpha}_1^i} - \left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}^i}^{\boldsymbol{\alpha}_2^i} = \eta^i \lambda^i$$

$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}^i}^{\boldsymbol{\alpha}_1^i} - \left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}^i}^{\boldsymbol{\alpha}_2^i} = \frac{l_1 - l_0}{l_0} - \frac{l_2 - l_0}{l_0} = \frac{2(l_1 - l_2)}{(l_1 + l_2)\left[1 - \frac{l_1 + l_2 - 2l_0}{l_1 + l_2}\right]}$$

$$= \frac{2(l_1 - l_2)}{l_1 + l_2}\left[1 + \frac{l_1 + l_2 - 2l_0}{l_1 + l_2} + \ldots\right] \approx \frac{2(l_1 - l_2)}{\boxed{l_1} + \boxed{l_2}}$$

Fitting to a quadratic function
$$f(l) = Al^2 + Bl + C$$

Minimum: $l_{1(2)} = -B_{1(2)}/(2A_{1(2)})$

$\alpha_1 = \left[\frac{1}{\sqrt{3}}, \frac{1}{\sqrt{3}}, \frac{1}{\sqrt{3}}\right]$ $\alpha_2 = \left[\frac{1}{\sqrt{2}}, 0, \frac{-1}{\sqrt{2}}\right]$

Cell length along $\boldsymbol{\beta} = \left[\frac{1}{\sqrt{3}}, \frac{1}{\sqrt{3}}, \frac{1}{\sqrt{3}}\right]$ (Å)

Cell length along $\boldsymbol{\beta} = \left[\frac{1}{\sqrt{3}}, \frac{1}{\sqrt{3}}, \frac{1}{\sqrt{3}}\right]$

Crystal system	Eq.	Magnetostriction coefficient	$\boldsymbol{\beta}$	$\boldsymbol{\alpha}_1$	$\boldsymbol{\alpha}_2$	η
Cubic (I)	10	λ_{001}	$(0,0,1)$	$(0,0,1)$	$(1,0,0)$	$\frac{3}{2}$
		λ_{111}	$\left(\frac{1}{\sqrt{3}},\frac{1}{\sqrt{3}},\frac{1}{\sqrt{3}}\right)$	$\left(\frac{1}{\sqrt{3}},\frac{1}{\sqrt{3}},\frac{1}{\sqrt{3}}\right)$	$\left(\frac{1}{\sqrt{2}},0,\frac{-1}{\sqrt{2}}\right)$	$\frac{3}{2}$
Hexagonal (I)	16	$\lambda^{\alpha1,2}$	$(1,0,0)$	$\left(\frac{1}{\sqrt{3}},\frac{1}{\sqrt{3}},\frac{1}{\sqrt{3}}\right)$	$\left(\frac{1}{\sqrt{2}},\frac{1}{\sqrt{2}},0\right)$	$\frac{1}{3}$
		$\lambda^{\alpha2,2}$	$(0,0,1)$	$(0,0,1)$	$(1,0,0)$	1
		$\lambda^{\gamma,2}$	$(1,0,0)$	$(1,0,0)$	$(0,1,0)$	1
		$\lambda^{\varepsilon,2}$	$\left(\frac{1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	$\left(\frac{1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	$\left(\frac{-1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	1
Trigonal (I)	20	$\lambda^{\alpha1,2}$	$(1,0,0)$	$(0,0,1)$	$\left(\frac{1}{\sqrt{2}},\frac{1}{\sqrt{2}},0\right)$	1
		$\lambda^{\alpha2,2}$	$(0,0,1)$	$(0,0,1)$	$(1,0,0)$	1
		$\lambda^{\gamma,1}$	$(1,0,0)$	$(1,0,0)$	$(0,1,0)$	1
		$\lambda^{\gamma,2}$	$\left(\frac{1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	$\left(\frac{1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	$\left(\frac{1}{\sqrt{2}},0,\frac{-1}{\sqrt{2}}\right)$	$\frac{1}{2}$
		λ_{12}	$\left(\frac{1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	$\left(0,\frac{1}{\sqrt{2}},\frac{1}{\sqrt{2}}\right)$	$\left(0,\frac{1}{\sqrt{2}},\frac{-1}{\sqrt{2}}\right)$	$\frac{1}{4}$
		λ_{21}	$\left(\frac{1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	$\left(\frac{1}{\sqrt{2}},\frac{1}{\sqrt{2}},0\right)$	$\left(\frac{1}{\sqrt{2}},\frac{-1}{\sqrt{2}},0\right)$	$\frac{1}{2}$
Tetragonal (I)	24	$\lambda^{\alpha1,2}$	$(1,0,0)$	$\left(\frac{1}{\sqrt{3}},\frac{1}{\sqrt{3}},\frac{1}{\sqrt{3}}\right)$	$\left(\frac{1}{\sqrt{2}},\frac{1}{\sqrt{2}},0\right)$	$\frac{1}{3}$
		$\lambda^{\alpha2,2}$	$(0,0,1)$	$(0,0,1)$	$(1,0,0)$	1
		$\lambda^{\gamma,2}$	$(1,0,0)$	$(1,0,0)$	$(0,1,0)$	1
		$\lambda^{\varepsilon,2}$	$\left(\frac{1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	$\left(\frac{1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	$\left(\frac{-1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	1
		$\lambda^{\delta,2}$	$\left(\frac{1}{\sqrt{2}},\frac{1}{\sqrt{2}},0\right)$	$\left(\frac{1}{\sqrt{2}},\frac{1}{\sqrt{2}},0\right)$	$\left(\frac{-1}{\sqrt{2}},\frac{1}{\sqrt{2}},0\right)$	1
Orthorhombic	27	λ_1	$(1,0,0)$	$(1,0,0)$	$(0,0,1)$	1
		λ_2	$(1,0,0)$	$(0,1,0)$	$(0,0,1)$	1
		λ_3	$(0,1,0)$	$(1,0,0)$	$(0,0,1)$	1
		λ_4	$(0,1,0)$	$(0,1,0)$	$(0,0,1)$	1
		λ_5	$(0,0,1)$	$(1,0,0)$	$(0,0,1)$	1
		λ_6	$(0,0,1)$	$(0,1,0)$	$(0,0,1)$	1
		λ_7	$\left(\frac{1}{\sqrt{2}},\frac{1}{\sqrt{2}},0\right)$	$\left(\frac{1}{\sqrt{2}},\frac{1}{\sqrt{2}},0\right)$	$(0,0,1)$	1
		λ_8	$\left(\frac{1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	$\left(\frac{1}{\sqrt{2}},0,\frac{1}{\sqrt{2}}\right)$	$(0,0,1)$	1
		λ_9	$\left(0,\frac{1}{\sqrt{2}},\frac{1}{\sqrt{2}}\right)$	$\left(0,\frac{1}{\sqrt{2}},\frac{1}{\sqrt{2}}\right)$	$(0,0,1)$	1

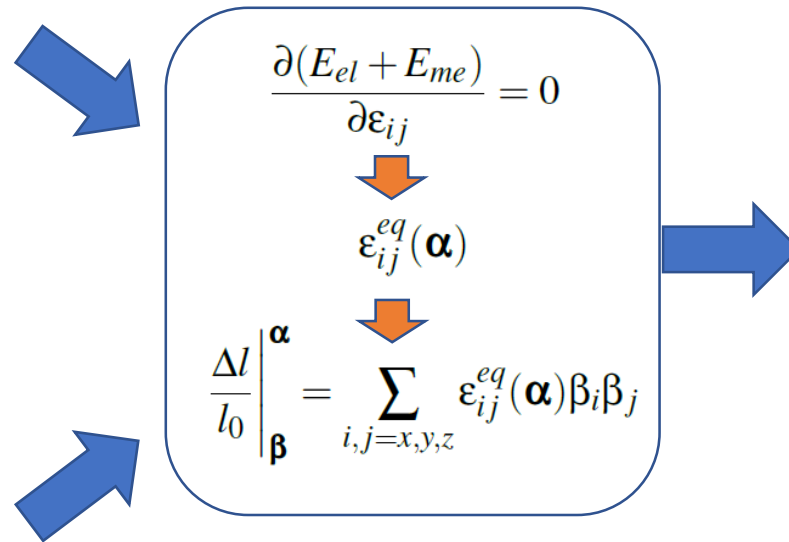# CUBIC (I)

SG 207-230

Workflow

Cubic (I)

Elastic energy

$$E_{el}^{cub} = \frac{c_{11}}{2}(\varepsilon_{xx}^2 + \varepsilon_{yy}^2 + \varepsilon_{zz}^2) + c_{12}(\varepsilon_{xx}\varepsilon_{yy} + \varepsilon_{xx}\varepsilon_{zz} + \varepsilon_{yy}\varepsilon_{zz}) + \frac{c_{44}}{2}(\varepsilon_{xy}^2 + \varepsilon_{yz}^2 + \varepsilon_{xz}^2)$$

$$\frac{\partial(E_{el} + E_{me})}{\partial \varepsilon_{ij}} = 0$$

$$\varepsilon_{ij}^{eq}(\boldsymbol{\alpha})$$

Magnetoelastic energy

$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \sum_{i,j=x,y,z} \varepsilon_{ij}^{eq}(\boldsymbol{\alpha})\beta_i\beta_j$$

$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \lambda^\alpha + \frac{3}{2}\lambda_{001}\left(\alpha_x^2\beta_x^2 + \alpha_y^2\beta_y^2 + \alpha_z^2\beta_z^2 - \frac{1}{3}\right)$$
$$+ 3\lambda_{111}(\alpha_x\alpha_y\beta_x\beta_y + \alpha_y\alpha_z\beta_y\beta_z + \alpha_x\alpha_z\beta_x\beta_z)$$

$$E_{me}^{cub(I)} = b_0(\varepsilon_{xx} + \varepsilon_{yy} + \varepsilon_{zz}) + b_1(\alpha_x^2\varepsilon_{xx} + \alpha_y^2\varepsilon_{yy} + \alpha_z^2\varepsilon_{zz})$$
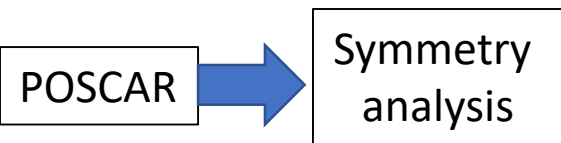$$+ b_2(\alpha_x\alpha_y\varepsilon_{xy} + \alpha_x\alpha_z\varepsilon_{xz} + \alpha_y\alpha_z\varepsilon_{yz})$$

$$\lambda^\alpha = \frac{-b_0 - \frac{1}{3}b_1}{c_{11} + 2c_{12}},$$

$$\lambda_{001} = \frac{-2b_1}{3(c_{11} - c_{12})},$$

$$\lambda_{111} = \frac{-b_2}{3c_{44}}.$$

Workflow

$$\frac{\Delta l}{l_0}\bigg|_{\beta}^{\alpha} = \lambda^{\alpha} + \frac{3}{2}\lambda_{001}\left(\alpha_x^2\beta_x^2 + \alpha_y^2\beta_y^2 + \alpha_z^2\beta_z^2 - \frac{1}{3}\right)$$
$$+ 3\lambda_{111}(\alpha_x\alpha_y\beta_x\beta_y + \alpha_y\alpha_z\beta_y\beta_z + \alpha_x\alpha_z\beta_x\beta_z)$$

POSCAR → Symmetry analysis → (Space group: 207-230) → Cubic (I)

λ_{001}

POSCAR_1_X (N POSCAR: Distortion along [0,0,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_1_1 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
INCAR_1_2 (1 INCAR: non-collinear with SOC, SPIN=[1,0,0])

→ OSZICAR_1_X_1

OSZICAR_1_X_2

λ_{111}

POSCAR_2_X (N POSCAR: Distortion along [1,1,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_2_1 (1 INCAR: non-collinear with SOC, SPIN=[1,1,1])
INCAR_2_2 (1 INCAR: non-collinear with SOC, SPIN=[1,0,-1])

→ OSZICAR_2_X_1

OSZICAR_2_X_2

x=cell length along deformation

Fitting: E(x)=a*x^2+b*x+c
Minimum (E$_{min}$): x_{min}=-b/(2*a)

Volume-conserving transformations
(determinant of transformation matrix = 1)

λ^γ λ^ε

$$\underline{\underline{\varepsilon}}\bigg|_{\beta=(0,0,1)}^{\lambda_{001}} = \begin{pmatrix} \frac{1}{\sqrt{1+\varepsilon}} & 0 & 0 \\ 0 & \frac{1}{\sqrt{1+\varepsilon}} & 0 \\ 0 & 0 & 1+\varepsilon \end{pmatrix}, \quad \underline{\underline{\varepsilon}}\bigg|_{\beta=\left(\frac{1}{\sqrt{3}},\frac{1}{\sqrt{3}},\frac{1}{\sqrt{3}}\right)}^{\lambda_{111}} = \zeta\begin{pmatrix} 1 & \frac{\varepsilon}{2} & \frac{\varepsilon}{2} \\ \frac{\varepsilon}{2} & 1 & \frac{\varepsilon}{2} \\ \frac{\varepsilon}{2} & \frac{\varepsilon}{2} & 1 \end{pmatrix}$$

$$\zeta = \sqrt[3]{4/(4 - 3\varepsilon^2 + \varepsilon^3)}$$

The maximum value of ε is set with tag-s

$$\lambda_{001\atop 111} = \frac{4}{3}\cdot\frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}}$$

Polycrystal: $\lambda_S = \frac{2}{5}\lambda_{100} + \frac{3}{5}\lambda_{111}$

HEXAGONAL (I)

SG 177-194
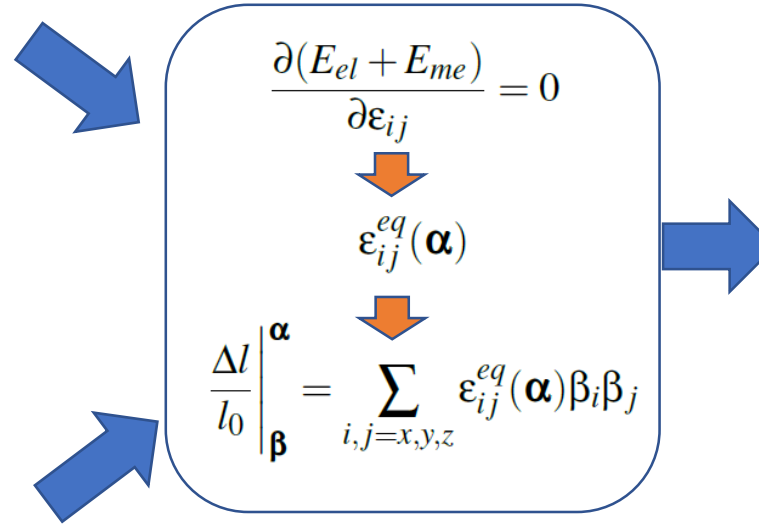
Workflow

Hexagonal (I)

Elastic energy

$$E_{el}^{hex} = \frac{1}{2}c_{11}(\varepsilon_{xx}^2 + \varepsilon_{yy}^2) + c_{12}\varepsilon_{xx}\varepsilon_{yy} + c_{13}(\varepsilon_{xx} + \varepsilon_{yy})\varepsilon_{zz} + \frac{1}{2}c_{33}\varepsilon_{zz}^2$$

$$+ \frac{1}{2}c_{44}(\varepsilon_{yz}^2 + \varepsilon_{xz}^2) + \frac{1}{4}(c_{11} - c_{12})\varepsilon_{xy}^2.$$

$$\frac{\partial(E_{el} + E_{me})}{\partial \varepsilon_{ij}} = 0$$

$$\varepsilon_{ij}^{eq}(\boldsymbol{\alpha})$$

$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \sum_{i,j=x,y,z} \varepsilon_{ij}^{eq}(\boldsymbol{\alpha})\beta_i\beta_j$$

Magnetoelastic energy

$$E_{me}^{hex(I)} = b_{11}(\varepsilon_{xx} + \varepsilon_{yy}) + b_{12}\varepsilon_{zz} + b_{21}\left(\alpha_z^2 - \frac{1}{3}\right)(\varepsilon_{xx} + \varepsilon_{yy}) + b_{22}\left(\alpha_z^2 - \frac{1}{3}\right)\varepsilon_{zz}$$

$$+ \frac{1}{2}b_3[(\alpha_x^2 - \alpha_y^2)(\varepsilon_{xx} - \varepsilon_{yy}) + 2\alpha_x\alpha_y\varepsilon_{xy}] + b_4(\alpha_x\alpha_z\varepsilon_{xz} + \alpha_y\alpha_z\varepsilon_{yz}).$$

$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \lambda^{\alpha1,0}(\beta_x^2 + \beta_y^2) + \lambda^{\alpha2,0}\beta_z^2 + \lambda^{\alpha1,2}\left(\alpha_z^2 - \frac{1}{3}\right)(\beta_x^2 + \beta_y^2)$$

$$+ \lambda^{\alpha2,2}\left(\alpha_z^2 - \frac{1}{3}\right)\beta_z^2 + \lambda^{\gamma,2}\left[\frac{1}{2}(\alpha_x^2 - \alpha_y^2)(\beta_x^2 - \beta_y^2) + 2\alpha_x\alpha_y\beta_x\beta_y\right]$$

$$+ 2\lambda^{\varepsilon,2}(\alpha_x\alpha_z\beta_x\beta_z + \alpha_y\alpha_z\beta_y\beta_z),$$

$$\lambda^{\alpha1,0} = \frac{b_{11}c_{33} + b_{12}c_{13}}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

$$\lambda^{\alpha2,0} = \frac{2b_{11}c_{33} - b_{12}(c_{11} + c_{22})}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

$$\lambda^{\alpha1,2} = \frac{-b_{21}c_{33} + b_{22}c_{13}}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

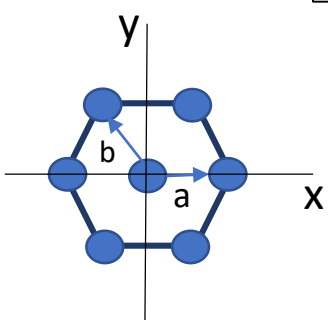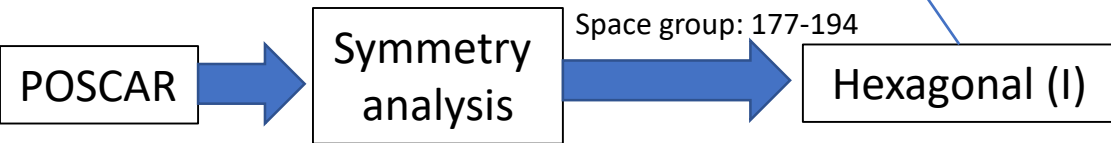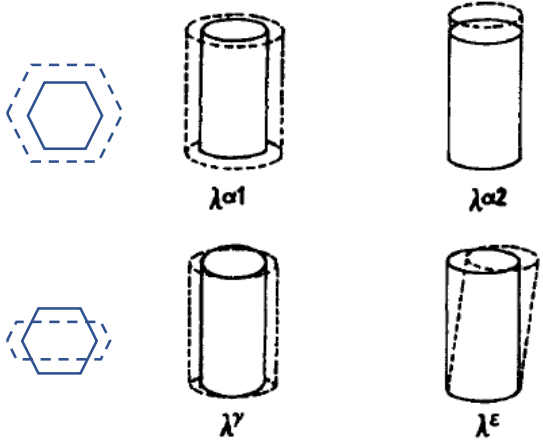$$\lambda^{\alpha2,2} = \frac{2b_{21}c_{33} - b_{22}(c_{11} + c_{22})}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

$$\lambda^{\gamma,2} = \frac{-b_3}{c_{11} - c_{12}},$$

$$\lambda^{\varepsilon,2} = \frac{-b_4}{2c_{44}}.$$

Workflow

$$\frac{\Delta l}{l_0}\bigg|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \lambda^{\alpha 1,0}(\beta_x^2 + \beta_y^2) + \lambda^{\alpha 2,0}\beta_z^2 + \lambda^{\alpha 1,2}\left(\alpha_z^2 - \frac{1}{3}\right)(\beta_x^2 + \beta_y^2)$$

$$+ \lambda^{\alpha 2,2}\left(\alpha_z^2 - \frac{1}{3}\right)\beta_z^2 + \lambda^{\gamma,2}\left[\frac{1}{2}(\alpha_x^2 - \alpha_y^2)(\beta_x^2 - \beta_y^2) + 2\alpha_x\alpha_y\beta_x\beta_y\right]$$

$$+ 2\lambda^{\varepsilon,2}(\alpha_x\alpha_z\beta_x\beta_z + \alpha_y\alpha_z\beta_y\beta_z),$$

$\lambda^{\alpha 1}$ $\lambda^{\alpha 2}$

λ^{γ} λ^{ε}

POSCAR → Symmetry analysis → Space group: 177-194 → Hexagonal (I)

$\lambda^{\alpha 1,2}$

POS_1_X (N POSCAR: Distortion along [1,0,0])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_1_1 (1 INCAR: non-collinear with SOC, SPIN=[1,1,1])
INCAR_1_2 (1 INCAR: non-collinear with SOC, SPIN=[1,1,0])

→ OSZICAR_1_X_1 OSZICAR_1_X_2

$\lambda^{\alpha 2,2}$

POS_2_X (N POSCAR: Distortion along [0,0,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_2_1 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
INCAR_2_2 (1 INCAR: non-collinear with SOC, SPIN=[1,0,0])

→ OSZICAR_2_X_1 OSZICAR_2_X_2

$\lambda^{\gamma,2}$

POS_3_X (N POSCAR: Distortion along [1,0,0])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_3_1 (1 INCAR: non-collinear with SOC, SPIN=[1,0,0])
INCAR_3_2 (1 INCAR: non-collinear with SOC, SPIN=[0,1,0])

→ OSZICAR_3_X_1 OSZICAR_3_X_2

$\lambda^{\varepsilon,2}$

POS_4_X (N x POSCAR: Distortion along [1,0,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_4_1 (1 INCAR: non-collinear with SOC, SPIN=[1,0,1])
INCAR_4_2 (1 INCAR: non-collinear with SOC, SPIN=[-1,0,1])
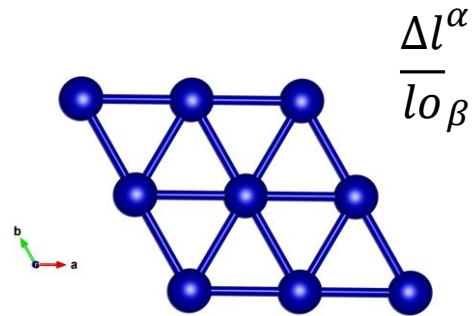
→ OSZICAR_4_X_1 OSZICAR_4_X_2

x=cell length along deformation

Fitting: E(x)=a*x²+b*x+c
Minimum (E_min): x_min=-b/(2*a)

$$\lambda^{\alpha 1,2} = 6 \cdot \frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}} \qquad \lambda^{\alpha 2,2} = 2\frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}} \qquad \lambda^{\gamma,2} = 2\frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}} \qquad \lambda^{\varepsilon,2} = 2\frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}}$$

y

b a

x

Distorted states

$$\frac{\Delta l^{\alpha}}{l o}_{\beta}$$

$$|\boldsymbol{\alpha}| = 1, |\boldsymbol{\beta}| = 1$$

strain along x-axis: $\beta = (1,0,0)$

$$\boldsymbol{\underline{\varepsilon}}\bigg|_{\boldsymbol{\beta}=(1,0,0)}^{\lambda^{\alpha 1,2}} = \begin{pmatrix} 1+\varepsilon & 0 & 0 \\ 0 & \frac{1}{\sqrt{1+\varepsilon}} & 0 \\ 0 & 0 & \frac{1}{\sqrt{1+\varepsilon}} \end{pmatrix}$$

$\lambda^{\alpha 1,2}$

ε_{xx}

volume-conserving

S=(1,1,1)

S=(1,1,0)

y

x

b

a
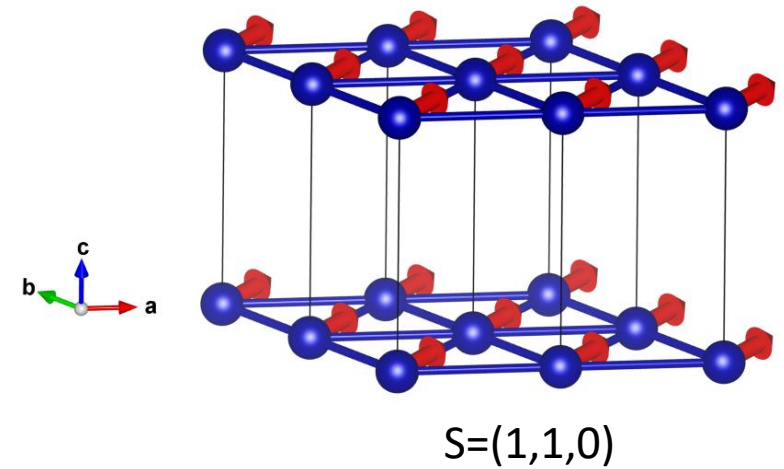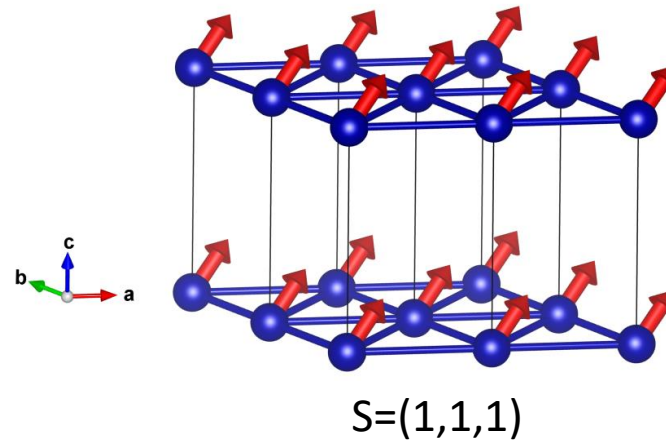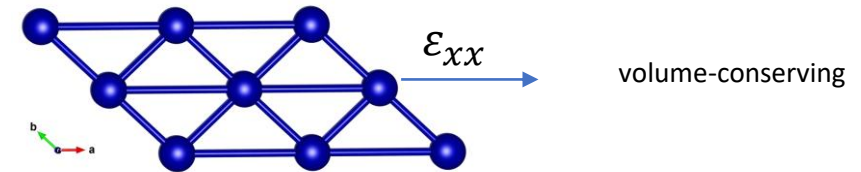
$$A = \begin{pmatrix} a1 & 0 & 0 \\ b1 & b2 & 0 \\ 0 & 0 & c3 \end{pmatrix}$$

$$\lambda^{\alpha 1,2} = 6 \cdot \frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}}$$

Distorted states

$$\frac{\Delta l^{\alpha}}{lo_{\beta}}$$

$$|\boldsymbol{\alpha}| = 1, |\boldsymbol{\beta}| = 1$$

strain along z-axis: $\beta = (0,0,1)$

$$\underline{\underline{\varepsilon}}\Big|^{\lambda^{\alpha2,2}}_{\boldsymbol{\beta}=(0,0,1)} = \begin{pmatrix} \frac{1}{\sqrt{1+\varepsilon}} & 0 & 0 \\ 0 & \frac{1}{\sqrt{1+\varepsilon}} & 0 \\ 0 & 0 & 1+\varepsilon \end{pmatrix}$$

ε_{zz}

volume-conserving

$$\lambda^{\alpha2,2}$$

S=(0,0,1)
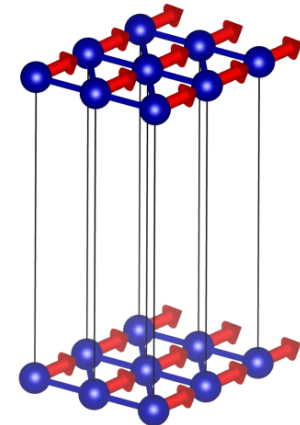
S=(1,0,0)

$$A = \begin{pmatrix} a1 & 0 & 0 \\ b1 & b2 & 0 \\ 0 & 0 & c3 \end{pmatrix}$$

$$\lambda^{\alpha2,2} = 2\frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}}$$

Distorted states

$$\frac{\Delta l^{\alpha}}{lo_{\beta}}$$

$$|\boldsymbol{\alpha}| = 1, |\boldsymbol{\beta}| = 1$$

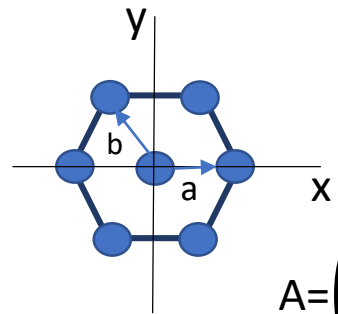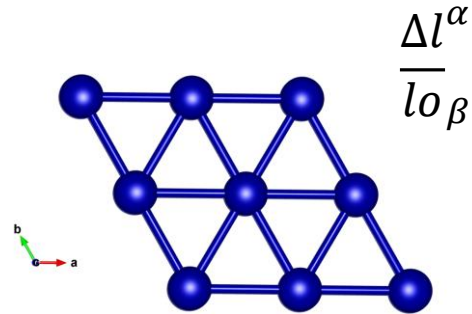$$\underline{\underline{\boldsymbol{\varepsilon}}}\Big|_{\boldsymbol{\beta}=(1,0,0)}^{\lambda^{\gamma,2}} = \begin{pmatrix} 1+\varepsilon & 0 & 0 \\ 0 & \frac{1}{\sqrt{1+\varepsilon}} & 0 \\ 0 & 0 & \frac{1}{\sqrt{1+\varepsilon}} \end{pmatrix}$$

volume-conserving

$$\lambda^{\gamma,2}$$

$$\varepsilon_{xx}$$

S=(1,0,0)

S=(0,1,0)

$$A = \begin{pmatrix} a1 & 0 & 0 \\ b1 & b2 & 0 \\ 0 & 0 & c3 \end{pmatrix}$$

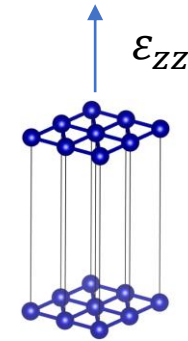$$\lambda^{\gamma,2} = 2\frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}}$$

Distorted states

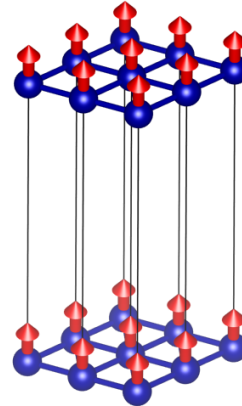$$\frac{\Delta l^{\alpha}}{lo_{\beta}}$$

$$|\boldsymbol{\alpha}| = 1, |\boldsymbol{\beta}| = 1$$

shear along xz: $\boldsymbol{\beta} = \left(\frac{1}{\sqrt{2}}, 0, \frac{1}{\sqrt{2}}\right)$

$$\underline{\underline{\varepsilon}}\bigg|_{\boldsymbol{\beta} = \left(\frac{1}{\sqrt{2}}, 0, \frac{1}{\sqrt{2}}\right)}^{\lambda^{\varepsilon,2}} = \omega \begin{pmatrix} 1 & 0 & \frac{\varepsilon}{2} \\ 0 & 1 & 0 \\ \frac{\varepsilon}{2} & 0 & 1 \end{pmatrix}$$

$$\varepsilon_{xz}$$

$$\omega = \sqrt[3]{4/(4-\varepsilon^2)}$$

volume-conserving
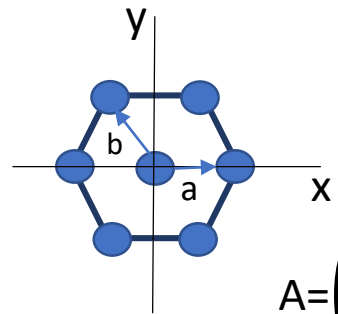
$$\lambda^{\varepsilon,2}$$
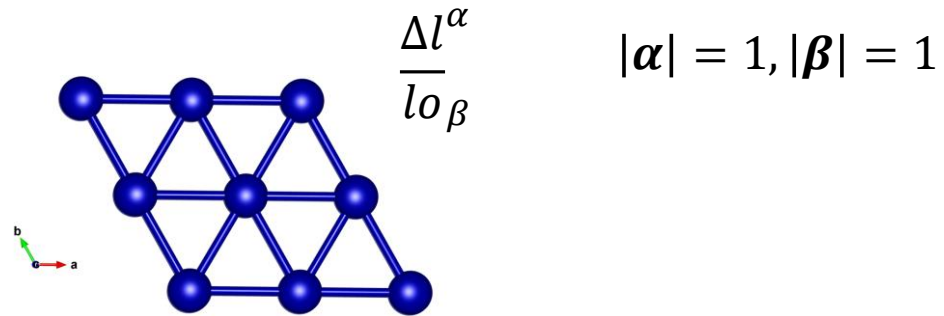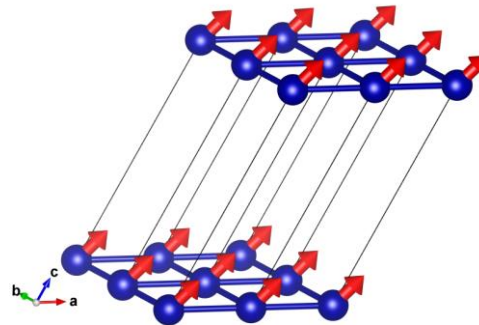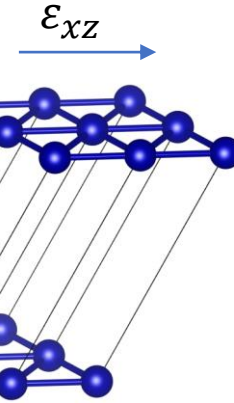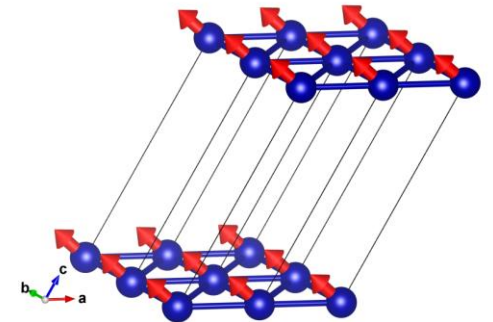
S=(1,0,1)

S=(-1,0,1)

$$A = \begin{pmatrix} a1 & 0 & 0 \\ b1 & b2 & 0 \\ 0 & 0 & c3 \end{pmatrix}$$

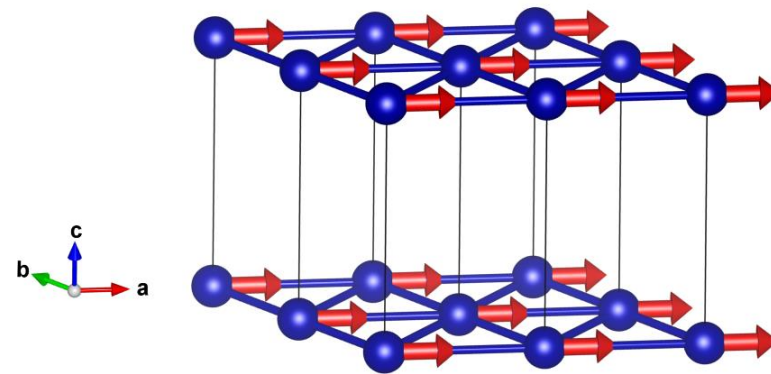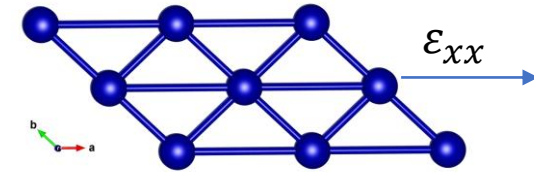$$\lambda^{\varepsilon,2} = 2 \frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}}$$
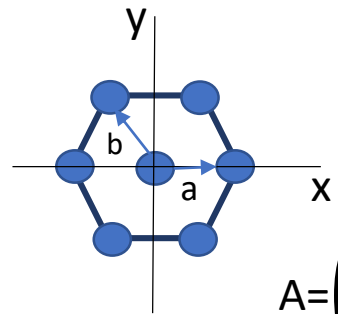
Relation between different notations
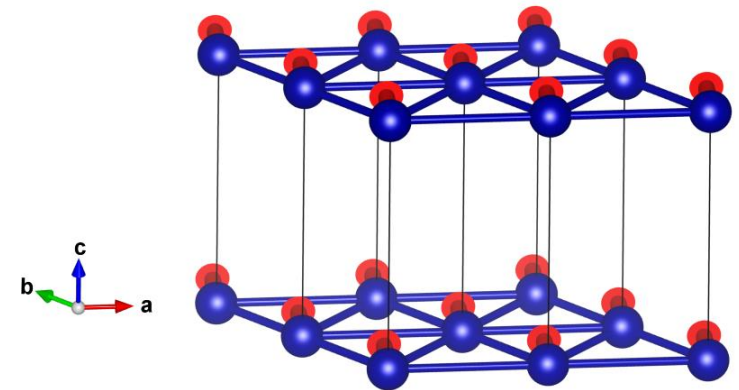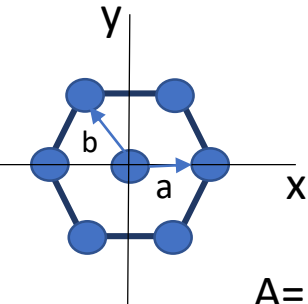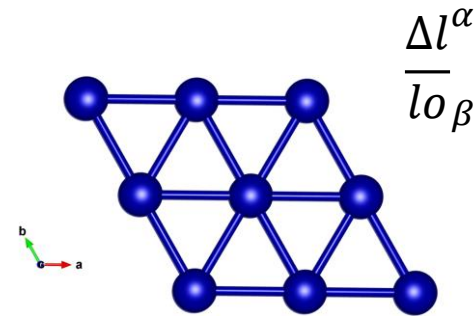
Clark

Hexagonal system

Callen

Gauge direction			Magnetization direction						$\lambda(x,y)_0 - \lambda(x,y)_f$	Magnetostriction coefficients		
			Initial			Final				Eq. (3)	Mason[a]	Birss[b]
β_x	β_y	β_z	α_x	α_y	α_z	α_x	α_y	α_z				
1	0	0	1	0	0	0	1	0	$\lambda(a,a) - \lambda(b,a)$	$\lambda^{\gamma,2}$	$\lambda_A - \lambda_B$	Q_8
0	0	1	0	0	1	1	0	0	$\lambda(c,c) - \lambda(a,c)$	$\lambda_2^{\alpha,2}$	$-\lambda_C$	$-Q_2 - Q_4$
1	0	0	1	0	0	0	0	1	$\lambda(a,a) - \lambda(c,a)$	$-\lambda_1^{\alpha,2} + \frac{1}{2}\lambda^{\gamma,2}$	λ_A	$-Q_2$
$\frac{\sqrt{2}}{2}$	0	$\frac{\sqrt{2}}{2}$	$\frac{\sqrt{2}}{2}$	0	$\frac{\sqrt{2}}{2}$	$\frac{\sqrt{2}}{2}$	0	$\frac{\sqrt{2}}{2}$	$\lambda(d,d) - \lambda(e,d)$	$\lambda^{\epsilon,2}$	$-\frac{1}{2}\lambda_A - \frac{1}{2}\lambda_C + 2\lambda_D$	$\frac{1}{2}Q_6$

[a] W. P. Mason, Phys. Rev. 96, 302 (1954).
[b] R. R. Birss, *Advances in Physics* (Francis & Taylor, Ltd., London, 1959), Vol. 8, p. 252.

MAELAS notation

$$\lambda_{11}^{\alpha} = 2\lambda_1^{\alpha,0} + \lambda_2^{\alpha,0} + 2\lambda_1^{\alpha,2} + \lambda_2^{\alpha,2}$$

$$(\sqrt{3}/2)\lambda_{12}^{\alpha} = 2\lambda_1^{\alpha,2} + \lambda_2^{\alpha,2},$$

$$2\lambda_{21}^{\alpha} = -\lambda_1^{\alpha,0} + \lambda_2^{\alpha,0},$$

$$\sqrt{3}\lambda_{22}^{\alpha} = -\lambda_1^{\alpha,2} + \lambda_2^{\alpha,2}.$$

$$\lambda^{\epsilon} = \lambda^{\epsilon,2}$$

$$\lambda^{\gamma} = \lambda^{\gamma,2}$$

The calculated magnetostriction coefficients are written in Clark, Mason, Birss and Callen notation in MAELAS code

TRIGONAL (I)

SG 149-167

Workflow

Elastic energy

$$E_{el}^{trig(I)} = \frac{1}{2}c_{11}(\varepsilon_{xx}^2 + \varepsilon_{yy}^2) + c_{12}\varepsilon_{xx}\varepsilon_{yy} + c_{13}(\varepsilon_{xx} + \varepsilon_{yy})\varepsilon_{zz} + \frac{1}{2}c_{33}\varepsilon_{zz}^2$$

$$+ \frac{1}{2}c_{44}(\varepsilon_{xz}^2 + \varepsilon_{yz}^2) + \frac{1}{4}(c_{11} - c_{12})\varepsilon_{xy}^2 + c_{14}(\varepsilon_{xy}\varepsilon_{xz} + \varepsilon_{xx}\varepsilon_{yz} - \varepsilon_{yy}\varepsilon_{yz})$$

$$\frac{\partial(E_{el} + E_{me})}{\partial\varepsilon_{ij}} = 0$$

$$\varepsilon_{ij}^{eq}(\boldsymbol{\alpha})$$

$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \sum_{i,j=x,y,z} \varepsilon_{ij}^{eq}(\boldsymbol{\alpha})\beta_i\beta_j$$

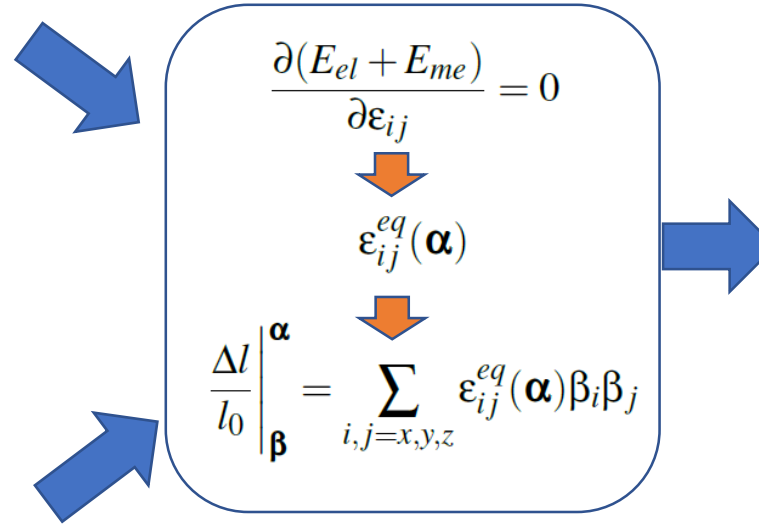$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \lambda^{\alpha1,0}(\beta_x^2 + \beta_y^2) + \lambda^{\alpha2,0}\beta_z^2 + \lambda^{\alpha1,2}\left(\alpha_z^2 - \frac{1}{3}\right)(\beta_x^2 + \beta_y^2)$$

$$+ \lambda^{\alpha2,2}\left(\alpha_z^2 - \frac{1}{3}\right)\beta_z^2 + \lambda^{\gamma,1}\left[\frac{1}{2}(\alpha_x^2 - \alpha_y^2)(\beta_x^2 - \beta_y^2) + \alpha_x\alpha_y\beta_x\beta_y\right]$$

$$+ \lambda^{\gamma,2}(\alpha_x\alpha_z\beta_x\beta_z + \alpha_y\alpha_z\beta_y\beta_z) + \lambda_{12}\left[\frac{1}{2}\alpha_y\alpha_z(\beta_x^2 - \beta_y^2) + \alpha_x\alpha_z\beta_x\beta_y\right]$$

$$+ \lambda_{21}\left[\frac{1}{2}(\alpha_x^2 - \alpha_y^2)\beta_y\beta_z + \alpha_x\alpha_y\beta_x\beta_z\right],$$

Magnetoelastic energy

$$E_{me}^{trig(I)} = b_{11}(\varepsilon_{xx} + \varepsilon_{yy}) + b_{12}\varepsilon_{zz} + b_{21}\left(\alpha_z^2 - \frac{1}{3}\right)(\varepsilon_{xx} + \varepsilon_{yy}) + b_{22}\left(\alpha_z^2 - \frac{1}{3}\right)\varepsilon_{zz}$$

$$+ \frac{1}{2}b_3[(\alpha_x^2 - \alpha_y^2)(\varepsilon_{xx} - \varepsilon_{yy}) + 2\alpha_x\alpha_y] + b_4(\alpha_x\alpha_z\varepsilon_{xz} + \alpha_y\alpha_z\varepsilon_{yz})$$

$$+ b_{14}\left[\frac{1}{2}(\alpha_x^2 - \alpha_y^2)\varepsilon_{yz} + \alpha_x\alpha_y\varepsilon_{xz}\right] + b_{34}\left[\frac{1}{2}\alpha_y\alpha_z(\varepsilon_{xx} - \varepsilon_{yy}) + \alpha_x\alpha_z\varepsilon_{xy}\right].$$

$$\lambda^{\alpha1,0} = \frac{b_{11}c_{33} + b_{12}c_{13}}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

$$\lambda^{\alpha2,0} = \frac{2b_{11}c_{33} - b_{12}(c_{11} + c_{22})}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

$$\lambda^{\alpha1,2} = \frac{-b_{21}c_{33} + b_{22}c_{13}}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

$$\lambda^{\alpha2,2} = \frac{2b_{21}c_{33} - b_{22}(c_{11} + c_{22})}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

$$\lambda^{\gamma,1} = \frac{c_{14}b_{14} - c_{44}b_3}{\frac{1}{2}c_{44}(c_{11} - c_{12}) - c_{14}^2},$$

$$\lambda^{\gamma,2} = \frac{\frac{1}{2}b_4(c_{11} - c_{12}) - b_{34}c_{14}}{\frac{1}{2}c_{44}(c_{11} - c_{12}) - c_{14}^2},$$

$$\lambda_{12} = \frac{c_{14}b_4 - c_{44}b_{34}}{\frac{1}{2}c_{44}(c_{11} - c_{12}) - c_{14}^2},$$

$$\lambda_{21} = \frac{\frac{1}{2}b_{14}(c_{11} - c_{12}) - b_3c_{14}}{\frac{1}{2}c_{44}(c_{11} - c_{12}) - c_{14}^2}.$$

$$\left.\frac{\Delta l}{l_0}\right|_{\beta}^{\alpha} = \lambda^{\alpha1,0}(\beta_x^2 + \beta_y^2) + \lambda^{\alpha2,0}\beta_z^2 + \lambda^{\alpha1,2}\left(\alpha_z^2 - \frac{1}{3}\right)(\beta_x^2 + \beta_y^2)$$
$$+ \lambda^{\alpha2,2}\left(\alpha_z^2 - \frac{1}{3}\right)\beta_z^2 + \lambda^{\gamma,1}\left[\frac{1}{2}(\alpha_x^2 - \alpha_y^2)(\beta_x^2 - \beta_y^2) + \alpha_x\alpha_y\beta_x\beta_y\right]$$
$$+ \lambda^{\gamma,2}(\alpha_x\alpha_z\beta_x\beta_z + \alpha_y\alpha_z\beta_y\beta_z) + \lambda_{12}\left[\frac{1}{2}\alpha_y\alpha_z(\beta_x^2 - \beta_y^2) + \alpha_x\alpha_z\beta_x\beta_y\right]$$
$$+ \lambda_{21}\left[\frac{1}{2}(\alpha_x^2 - \alpha_y^2)\beta_y\beta_z + \alpha_x\alpha_y\beta_x\beta_z\right],$$

POSCAR → Symmetry analysis → Space group: 143-167 → Trigonal

$\lambda^{\alpha1,2}$

POS_1_X (N POSCAR: Distortion along [1,0,0])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_1_1 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
INCAR_1_2 (1 INCAR: non-collinear with SOC, SPIN=[1,1,0])
→ OSZICAR_1_X_1 / OSZICAR_1_X_2

$\lambda^{\alpha2,2}$

POS_2_X (N POSCAR: Distortion along [0,0,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_2_1 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
INCAR_2_2 (1 INCAR: non-collinear with SOC, SPIN=[1,0,0])
→ OSZICAR_2_X_1 / OSZICAR_2_X_2

$\lambda^{\gamma1}$

POS_3_X (N POSCAR: Distortion along [1,0,0])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_3_1 (1 INCAR: non-collinear with SOC, SPIN=[1,0,0])
INCAR_3_2 (1 INCAR: non-collinear with SOC, SPIN=[0,1,0])
→ OSZICAR_3_X_1 / OSZICAR_3_X_2

$\lambda^{\gamma2}$

POS_4_X (N POSCAR: Distortion along [1,0,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_4_1 (1 INCAR: non-collinear with SOC, SPIN=[1,0,1])
INCAR_4_2 (1 INCAR: non-collinear with SOC, SPIN=[1,0,-1])
→ OSZICAR_4_X_1 / OSZICAR_4_X_2

λ_{12}

POS_5_X (N POSCAR: Distortion along [1,0,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_5_1 (1 INCAR: non-collinear with SOC, SPIN=[0,1,1])
INCAR_5_2 (1 INCAR: non-collinear with SOC, SPIN=[0,1,-1])
→ OSZICAR_5_X_1 / OSZICAR_5_X_2

λ_{21}

POS_6_X (N POSCAR: Distortion along [1,0,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_6_1 (1 INCAR: non-collinear with SOC, SPIN=[1,1,0])
INCAR_6_2 (1 INCAR: non-collinear with SOC, SPIN=[1,-1,0])
→ OSZICAR_6_X_1 / OSZICAR_6_X_2

Fitting: E(x)=a*x²+b*x+c
Minimum (E_min): x_min=-b/(2*a)

$$\lambda^{\gamma2} = 4 \cdot \frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}} \quad \lambda^{\alpha1,2(\alpha2,2)} = 2\frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}} \quad \lambda^{\gamma1} = 2\frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}} \quad \lambda_{12} = 8 \cdot \frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}} \quad \lambda_{21} = 4 \cdot \frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}}$$

TETRAGONAL (I)

SG 89-142

Workflow

Tetragonal (I)

Elastic energy

$$E_{el}^{tet} = \frac{1}{2}c_{11}(\varepsilon_{xx}^2 + \varepsilon_{yy}^2) + c_{12}\varepsilon_{xx}\varepsilon_{yy} + c_{13}(\varepsilon_{xx} + \varepsilon_{yy})\varepsilon_{zz} + \frac{1}{2}c_{33}\varepsilon_{zz}^2$$

$$+ \frac{1}{2}c_{44}(\varepsilon_{xz}^2 + \varepsilon_{yz}^2) + \frac{1}{2}c_{66}\varepsilon_{xy}^2.$$

$$\frac{\partial(E_{el} + E_{me})}{\partial\varepsilon_{ij}} = 0$$

$$\varepsilon_{ij}^{eq}(\boldsymbol{\alpha})$$

$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \sum_{i,j=x,y,z} \varepsilon_{ij}^{eq}(\boldsymbol{\alpha})\beta_i\beta_j$$

Magnetoelastic energy

$$E_{me}^{tet(I)} = b_{11}(\varepsilon_{xx} + \varepsilon_{yy}) + b_{12}\varepsilon_{zz} + b_{21}\left(\alpha_z^2 - \frac{1}{3}\right)(\varepsilon_{xx} + \varepsilon_{yy}) + b_{22}\left(\alpha_z^2 - \frac{1}{3}\right)\varepsilon_{zz}$$

$$+ \frac{1}{2}b_3(\alpha_x^2 - \alpha_y^2)(\varepsilon_{xx} - \varepsilon_{yy}) + b_3'\alpha_x\alpha_y\varepsilon_{xy} + b_4(\alpha_x\alpha_z\varepsilon_{xz} + \alpha_y\alpha_z\varepsilon_{yz}).$$

$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \lambda^{\alpha 1,0}(\beta_x^2 + \beta_y^2) + \lambda^{\alpha 2,0}\beta_z^2 + \lambda^{\alpha 1,2}\left(\alpha_z^2 - \frac{1}{3}\right)(\beta_x^2 + \beta_y^2)$$

$$+ \lambda^{\alpha 2,2}\left(\alpha_z^2 - \frac{1}{3}\right)\beta_z^2 + \frac{1}{2}\lambda^{\gamma,2}(\alpha_x^2 - \alpha_y^2)(\beta_x^2 - \beta_y^2) + 2\lambda^{\delta,2}\alpha_x\alpha_y\beta_x\beta_y$$

$$+ 2\lambda^{\varepsilon,2}(\alpha_x\alpha_z\beta_x\beta_z + \alpha_y\alpha_z\beta_y\beta_z),$$

$$\lambda^{\alpha 1,0} = \frac{b_{11}c_{33} + b_{12}c_{13}}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

$$\lambda^{\alpha 2,0} = \frac{2b_{11}c_{33} - b_{12}(c_{11} + c_{22})}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

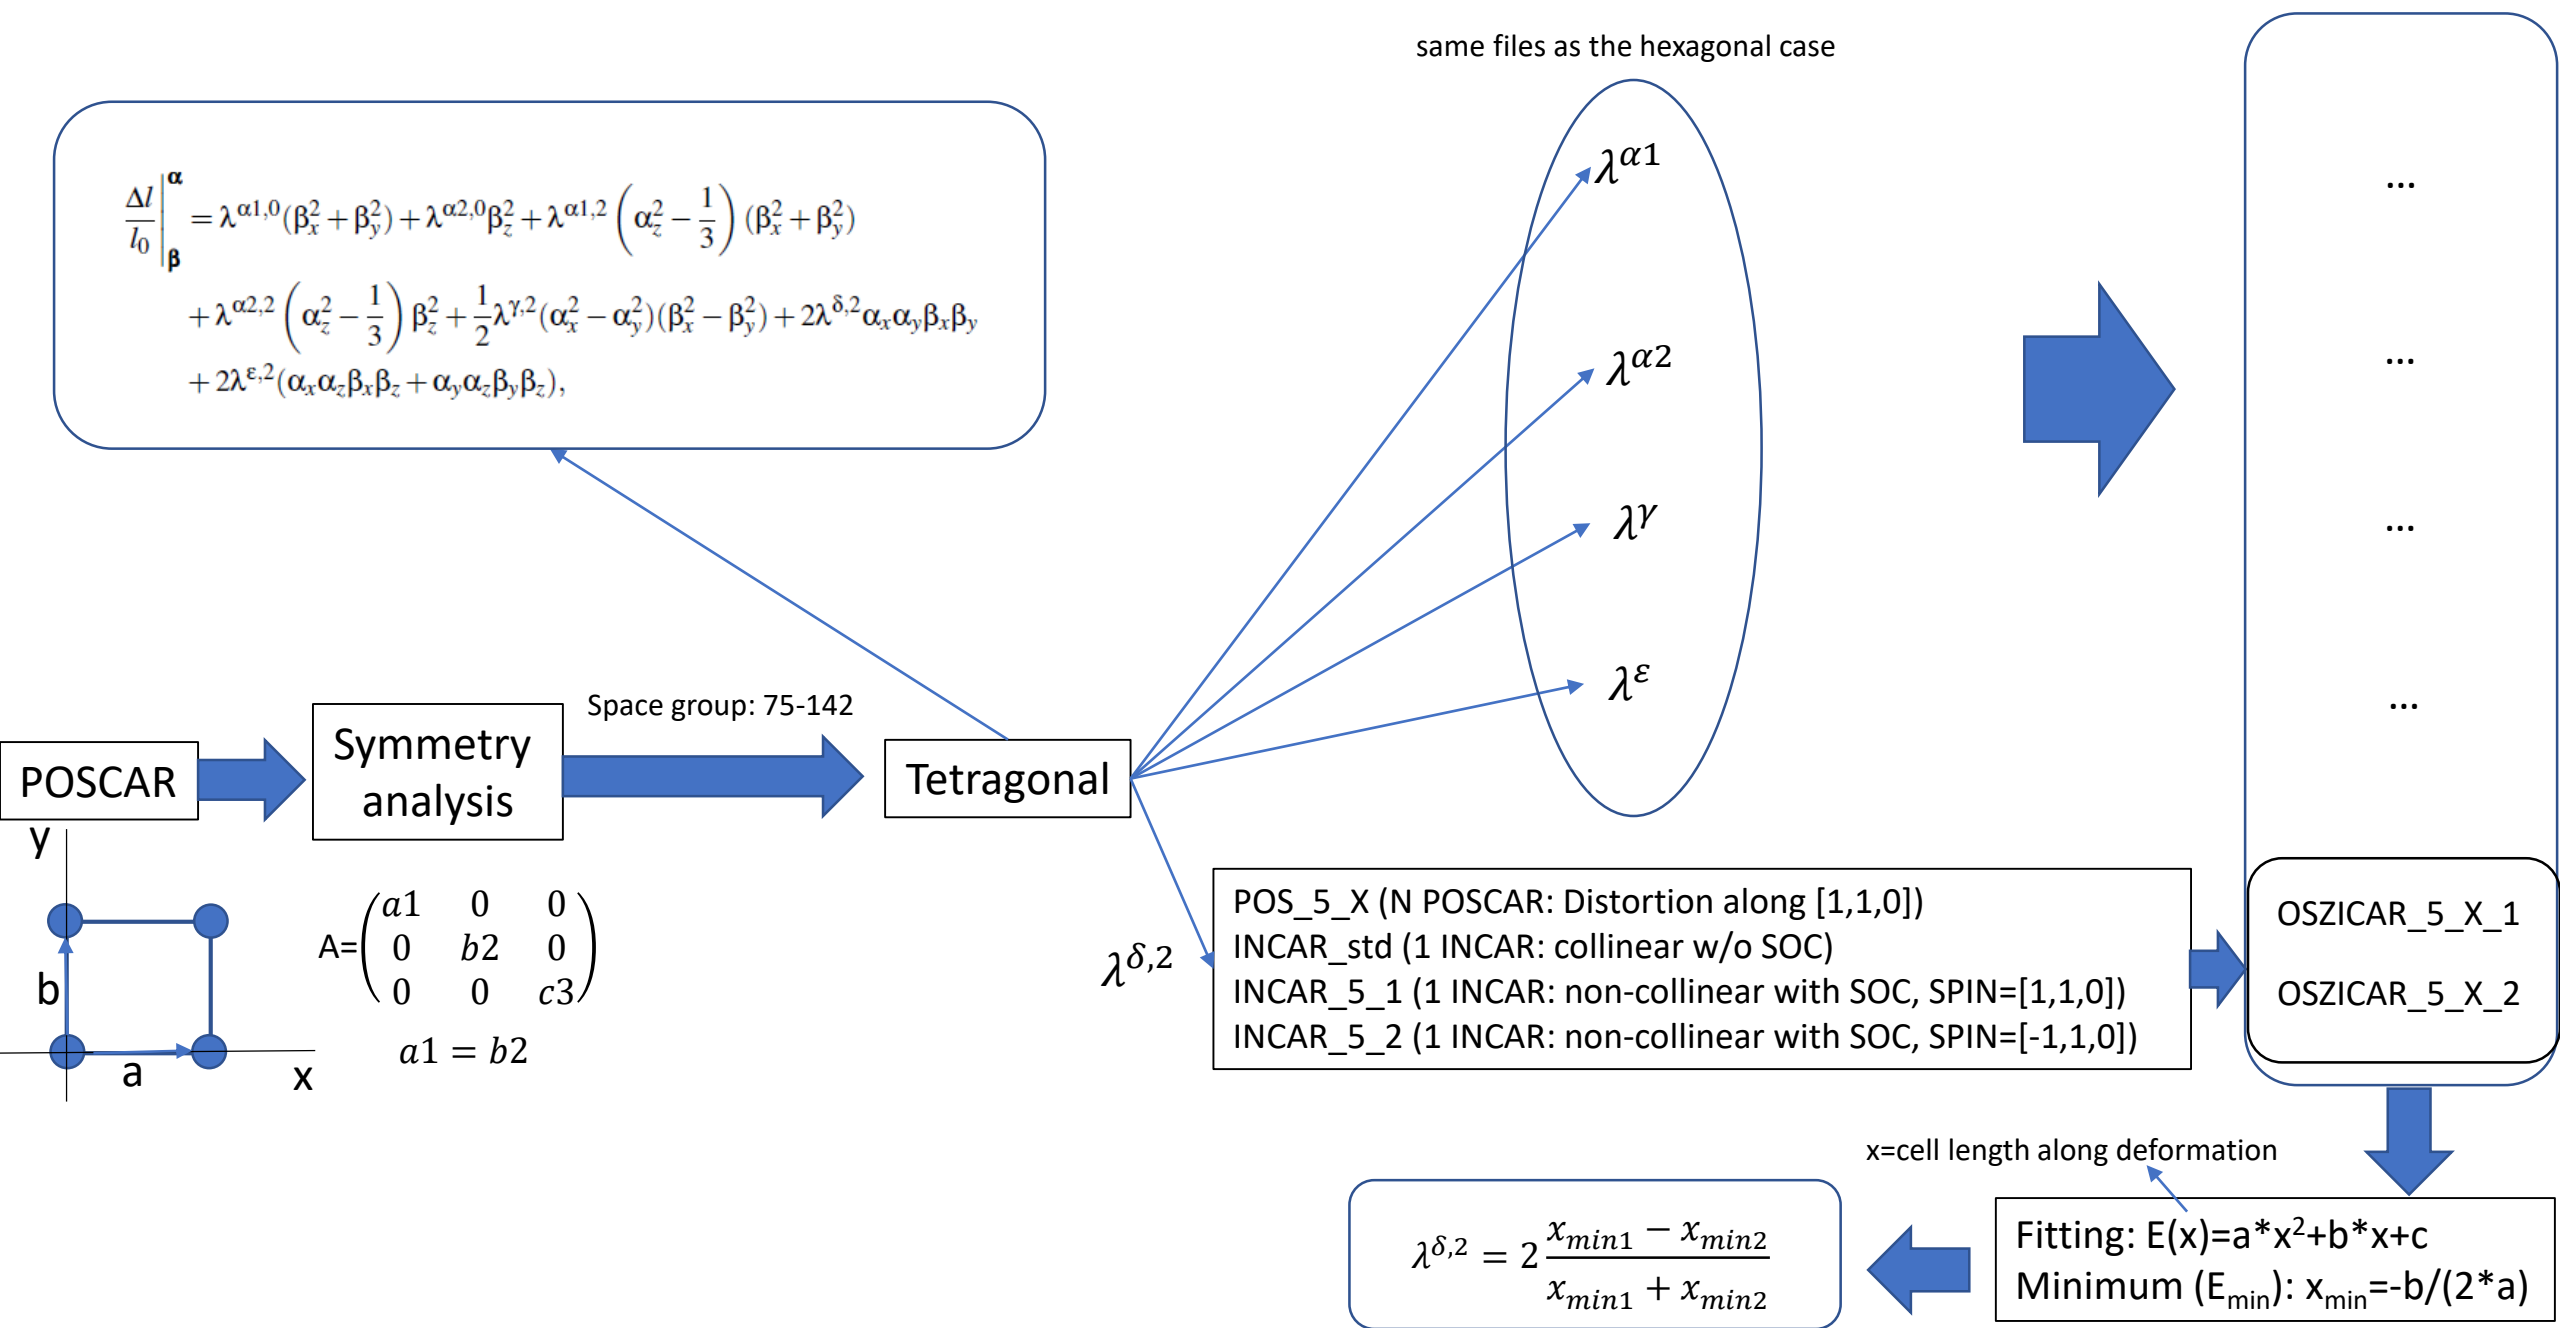$$\lambda^{\alpha 1,2} = \frac{-b_{21}c_{33} + b_{22}c_{13}}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

$$\lambda^{\alpha 2,2} = \frac{2b_{21}c_{33} - b_{22}(c_{11} + c_{22})}{c_{33}(c_{11} + c_{12}) - 2c_{13}^2},$$

$$\lambda^{\gamma,2} = \frac{-b_3}{c_{11} - c_{12}},$$

$$\lambda^{\delta,2} = \frac{-b_3'}{2c_{66}},$$

$$\lambda^{\varepsilon,2} = \frac{-b_4}{2c_{44}}.$$

Workflow

same files as the hexagonal case

$$\frac{\Delta l}{l_0}\bigg|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \lambda^{\alpha 1,0}(\beta_x^2 + \beta_y^2) + \lambda^{\alpha 2,0}\beta_z^2 + \lambda^{\alpha 1,2}\left(\alpha_z^2 - \frac{1}{3}\right)(\beta_x^2 + \beta_y^2)$$

$$+ \lambda^{\alpha 2,2}\left(\alpha_z^2 - \frac{1}{3}\right)\beta_z^2 + \frac{1}{2}\lambda^{\gamma,2}(\alpha_x^2 - \alpha_y^2)(\beta_x^2 - \beta_y^2) + 2\lambda^{\delta,2}\alpha_x\alpha_y\beta_x\beta_y$$

$$+ 2\lambda^{\varepsilon,2}(\alpha_x\alpha_z\beta_x\beta_z + \alpha_y\alpha_z\beta_y\beta_z),$$

$\lambda^{\alpha 1}$

$\lambda^{\alpha 2}$

λ^{γ}

λ^{ε}

...

...

...

...

POSCAR

y

$A = \begin{pmatrix} a1 & 0 & 0 \\ 0 & b2 & 0 \\ 0 & 0 & c3 \end{pmatrix}$

$a1 = b2$

b

a   x

Symmetry analysis

Space group: 75-142

Tetragonal

$\lambda^{\delta,2}$

POS_5_X (N POSCAR: Distortion along [1,1,0])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_5_1 (1 INCAR: non-collinear with SOC, SPIN=[1,1,0])
INCAR_5_2 (1 INCAR: non-collinear with SOC, SPIN=[-1,1,0])

OSZICAR_5_X_1

OSZICAR_5_X_2

x=cell length along deformation

Fitting: E(x)=a*x^2+b*x+c
Minimum (E$_{min}$): x$_{min}$=-b/(2*a)

$$\lambda^{\delta,2} = 2\frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}}$$

Relation between different notations

Tetragonal (I)

Cullen

Mason

$$\frac{\Delta l}{l_0}\bigg|_{\beta}^{\alpha} = \lambda^{\alpha 1,0}(\beta_x^2 + \beta_y^2) + \lambda^{\alpha 2,0}\beta_z^2 + \lambda^{\alpha 1,2}\left(\alpha_z^2 - \frac{1}{3}\right)(\beta_x^2 + \beta_y^2)$$

$$+ \lambda^{\alpha 2,2}\left(\alpha_z^2 - \frac{1}{3}\right)\beta_z^2 + \frac{1}{2}\lambda^{\gamma,2}(\alpha_x^2 - \alpha_y^2)(\beta_x^2 - \beta_y^2) + 2\lambda^{\delta,2}\alpha_x\alpha_y\beta_x\beta_y$$

$$+ 2\lambda^{\varepsilon,2}(\alpha_x\alpha_z\beta_x\beta_z + \alpha_y\alpha_z\beta_y\beta_z),$$

$$\frac{\Delta l}{l_0}\bigg|_{\beta}^{\alpha} = \lambda_{Mason}^{\alpha 1,0}(\beta_x^2 + \beta_y^2) + \lambda_{Mason}^{\alpha 2,0}\beta_z^2 + \frac{1}{2}\lambda_1[(\alpha_x\beta_x - \alpha_y\beta_y)^2 - (\alpha_x\beta_y + \alpha_y\beta_x)^2$$

$$+ (1 - \beta_z^2)(1 - \alpha_z^2) - 2\alpha_z\beta_z(\alpha_x\beta_x + \alpha_y\beta_y)] + 4\lambda_2\alpha_z\beta_z(\alpha_x\beta_x + \alpha_y\beta_y)$$

$$+ 4\lambda_3\alpha_x\alpha_y\beta_x\beta_y + \lambda_4[\beta_z^2(1 - \alpha_z^2) - \alpha_z\beta_z(\alpha_x\beta_x + \alpha_y\beta_y)]$$

$$+ \frac{1}{2}\lambda_5[(\alpha_x\beta_y - \alpha_y\beta_x)^2 - (\alpha_x\beta_x + \alpha_y\beta_y)^2 + (1 - \beta_z^2)(1 - \alpha_z^2)].$$

$$\lambda_{Mason}^{\alpha 1,0} = \lambda^{\alpha 1,0} + \frac{2}{3}\lambda^{\alpha 1,2}$$

$$\lambda_{Mason}^{\alpha 2,0} = \lambda^{\alpha 2,0} + \frac{2}{3}\lambda^{\alpha 2,2}$$

$$\lambda_1 = -\lambda^{\alpha 1,2} + \frac{1}{2}\lambda^{\gamma,2}$$

$$\lambda_2 = \frac{1}{2}\lambda^{\varepsilon,2} - \frac{1}{4}\lambda^{\alpha 2,2} - \frac{1}{4}\lambda^{\alpha 1,2} + \frac{1}{8}\lambda^{\gamma,2}$$

$$\lambda_3 = \frac{1}{2}\lambda^{\delta,2} - \lambda^{\alpha 1,2}$$

$$\lambda_4 = -\lambda^{\alpha 2,2}$$

$$\lambda_5 = -\lambda^{\alpha 1,2} - \frac{1}{2}\lambda^{\gamma,2}.$$

ORTHORHOMBIC

SG 16-74

Workflow

Orthorhombic

Elastic energy

$$E_{el}^{ortho} = \frac{1}{2}c_{11}\varepsilon_{xx}^2 + \frac{1}{2}c_{22}\varepsilon_{yy}^2 + c_{12}\varepsilon_{xx}\varepsilon_{yy} + c_{13}\varepsilon_{xx}\varepsilon_{zz} + c_{23}\varepsilon_{yy}\varepsilon_{zz} + \frac{1}{2}c_{33}\varepsilon_{zz}^2$$
$$+ \frac{1}{2}c_{44}\varepsilon_{yz}^2 + \frac{1}{2}c_{55}\varepsilon_{xz}^2 + \frac{1}{2}c_{66}\varepsilon_{xy}^2.$$

$$\frac{\partial(E_{el}+E_{me})}{\partial\varepsilon_{ij}} = 0$$

$$\varepsilon_{ij}^{eq}(\boldsymbol{\alpha})$$

$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \sum_{i,j=x,y,z} \varepsilon_{ij}^{eq}(\boldsymbol{\alpha})\beta_i\beta_j$$

Magnetoelastic energy

$$E_{me}^{ortho} = b_{01}\varepsilon_{xx} + b_{02}\varepsilon_{yy} + b_{03}\varepsilon_{zz} + b_1\alpha_x^2\varepsilon_{xx} + b_2\alpha_y^2\varepsilon_{xx} + b_3\alpha_x^2\varepsilon_{yy} + b_4\alpha_y^2\varepsilon_{yy}$$
$$+ b_5\alpha_x^2\varepsilon_{zz} + b_6\alpha_y^2\varepsilon_{zz} + b_7\alpha_x\alpha_y\varepsilon_{xy} + b_8\alpha_x\alpha_z\varepsilon_{xz} + b_9\alpha_y\alpha_z\varepsilon_{yz},$$

$$\left.\frac{\Delta l}{l_0}\right|_{\boldsymbol{\beta}}^{\boldsymbol{\alpha}} = \lambda^{\alpha1,0}\beta_x^2 + \lambda^{\alpha2,0}\beta_y^2 + \lambda^{\alpha3,0}\beta_z^2 + \lambda_1(\alpha_x^2\beta_x^2 - \alpha_x\alpha_y\beta_x\beta_y - \alpha_x\alpha_z\beta_x\beta_z)$$
$$+ \lambda_2(\alpha_y^2\beta_x^2 - \alpha_x\alpha_y\beta_x\beta_y) + \lambda_3(\alpha_x^2\beta_y^2 - \alpha_x\alpha_y\beta_x\beta_y)$$
$$+ \lambda_4(\alpha_y^2\beta_y^2 - \alpha_x\alpha_y\beta_x\beta_y - \alpha_y\alpha_z\beta_y\beta_z) + \lambda_5(\alpha_x^2\beta_z^2 - \alpha_x\alpha_z\beta_x\beta_z)$$
$$+ \lambda_6(\alpha_y^2\beta_z^2 - \alpha_y\alpha_z\beta_y\beta_z) + 4\lambda_7\alpha_x\alpha_y\beta_x\beta_y + 4\lambda_8\alpha_x\alpha_z\beta_x\beta_z + 4\lambda_9\alpha_y\alpha_z\beta_y\beta_z.$$

$$b_{01} = -c_{11}\lambda^{\alpha1,0} - c_{12}\lambda^{\alpha2,0} - c_{13}\lambda^{\alpha3,0}$$
$$b_{02} = -c_{12}\lambda^{\alpha1,0} - c_{22}\lambda^{\alpha2,0} - c_{23}\lambda^{\alpha3,0}$$
$$b_{03} = -c_{13}\lambda^{\alpha1,0} - c_{23}\lambda^{\alpha2,0} - c_{33}\lambda^{\alpha3,0}$$
$$b_1 = -c_{11}\lambda_1 - c_{12}\lambda_3 - c_{13}\lambda_5$$
$$b_2 = -c_{11}\lambda_2 - c_{12}\lambda_4 - c_{13}\lambda_6$$
$$b_3 = -c_{12}\lambda_1 - c_{22}\lambda_3 - c_{23}\lambda_5$$
$$b_4 = -c_{12}\lambda_2 - c_{22}\lambda_4 - c_{23}\lambda_6$$
$$b_5 = -c_{13}\lambda_1 - c_{23}\lambda_3 - c_{33}\lambda_5$$
$$b_6 = -c_{13}\lambda_2 - c_{23}\lambda_4 - c_{33}\lambda_6$$
$$b_7 = c_{66}(\lambda_1 + \lambda_2 + \lambda_3 + \lambda_4 - 4\lambda_7)$$
$$b_8 = c_{55}(\lambda_1 + \lambda_5 - 4\lambda_8)$$
$$b_9 = c_{44}(\lambda_4 + \lambda_6 - 4\lambda_9).$$

$$\frac{\Delta l}{l_0}\bigg|^{\boldsymbol{\alpha}}_{\boldsymbol{\beta}} = \lambda^{\alpha1,0}\beta_x^2 + \lambda^{\alpha2,0}\beta_y^2 + \lambda^{\alpha3,0}\beta_z^2 + \lambda_1(\alpha_x^2\beta_x^2 - \alpha_x\alpha_y\beta_x\beta_y - \alpha_x\alpha_z\beta_x\beta_z)$$

$$+ \lambda_2(\alpha_y^2\beta_x^2 - \alpha_x\alpha_y\beta_x\beta_y) + \lambda_3(\alpha_x^2\beta_y^2 - \alpha_x\alpha_y\beta_x\beta_y)$$

$$+ \lambda_4(\alpha_y^2\beta_y^2 - \alpha_x\alpha_y\beta_x\beta_y - \alpha_y\alpha_z\beta_y\beta_z) + \lambda_5(\alpha_x^2\beta_z^2 - \alpha_x\alpha_z\beta_x\beta_z)$$

$$+ \lambda_6(\alpha_y^2\beta_z^2 - \alpha_y\alpha_z\beta_y\beta_z) + 4\lambda_7\alpha_x\alpha_y\beta_x\beta_y + 4\lambda_8\alpha_x\alpha_z\beta_x\beta_z + 4\lambda_9\alpha_y\alpha_z\beta_y\beta_z.$$

POSCAR → Symmetry analysis → SG: 16-74 → Orthorhombic

λ_1
POS_1_X (N POSCAR: Distortion along [1,0,0])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_1_1 (1 INCAR: non-collinear with SOC, SPIN=[1,0,0])
INCAR_1_2 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
→ OSZICAR_1_X_1 / OSZICAR_1_X_2

λ_2
POS_2_X (N POSCAR: Distortion along [1,0,0])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_2_1 (1 INCAR: non-collinear with SOC, SPIN=[0,1,0])
INCAR_2_2 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
→ OSZICAR_2_X_1 / OSZICAR_2_X_2

λ_3
POS_3_X (N POSCAR: Distortion along [0,1,0])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_3_1 (1 INCAR: non-collinear with SOC, SPIN=[1,0,0])
INCAR_3_2 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
→ OSZICAR_3_X_1 / OSZICAR_3_X_2

λ_4
POS_4_X (N POSCAR: Distortion along [0,1,0])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_4_1 (1 INCAR: non-collinear with SOC, SPIN=[0,1,0])
INCAR_4_2 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
→ OSZICAR_4_X_1 / OSZICAR_4_X_2

λ_5
POS_5_X (N POSCAR: Distortion along [0,0,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_5_1 (1 INCAR: non-collinear with SOC, SPIN=[1,0,0])
INCAR_5_2 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
→ OSZICAR_5_X_1 / OSZICAR_5_X_2

λ_6
POS_6_X (N POSCAR: Distortion along [0,0,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_6_1 (1 INCAR: non-collinear with SOC, SPIN=[0,1,0])
INCAR_6_2 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
→ OSZICAR_6_X_1 / OSZICAR_6_X_2

λ_7
POS_7_X (N POSCAR: Distortion along [1,1,0])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_7_1 (1 INCAR: non-collinear with SOC, SPIN=[1,1,0])
INCAR_7_2 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
→ OSZICAR_7_X_1 / OSZICAR_7_X_2

λ_8
POS_8_X (N POSCAR: Distortion along [1,0,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_8_1 (1 INCAR: non-collinear with SOC, SPIN=[1,0,1])
INCAR_8_2 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
→ OSZICAR_8_X_1 / OSZICAR_8_X_2

λ_9
POS_9_X (N POSCAR: Distortion along [0,1,1])
INCAR_std (1 INCAR: collinear w/o SOC)
INCAR_9_1 (1 INCAR: non-collinear with SOC, SPIN=[0,1,1])
INCAR_9_2 (1 INCAR: non-collinear with SOC, SPIN=[0,0,1])
→ OSZICAR_9_X_1 / OSZICAR_9_X_2

MAELAS uses the same lattice convention as AELAS code:

c < a < b

Fitting: E(x)=a*x²+b*x+c
Minimum (E$_{min}$): x$_{min}$=-b/(2*a)

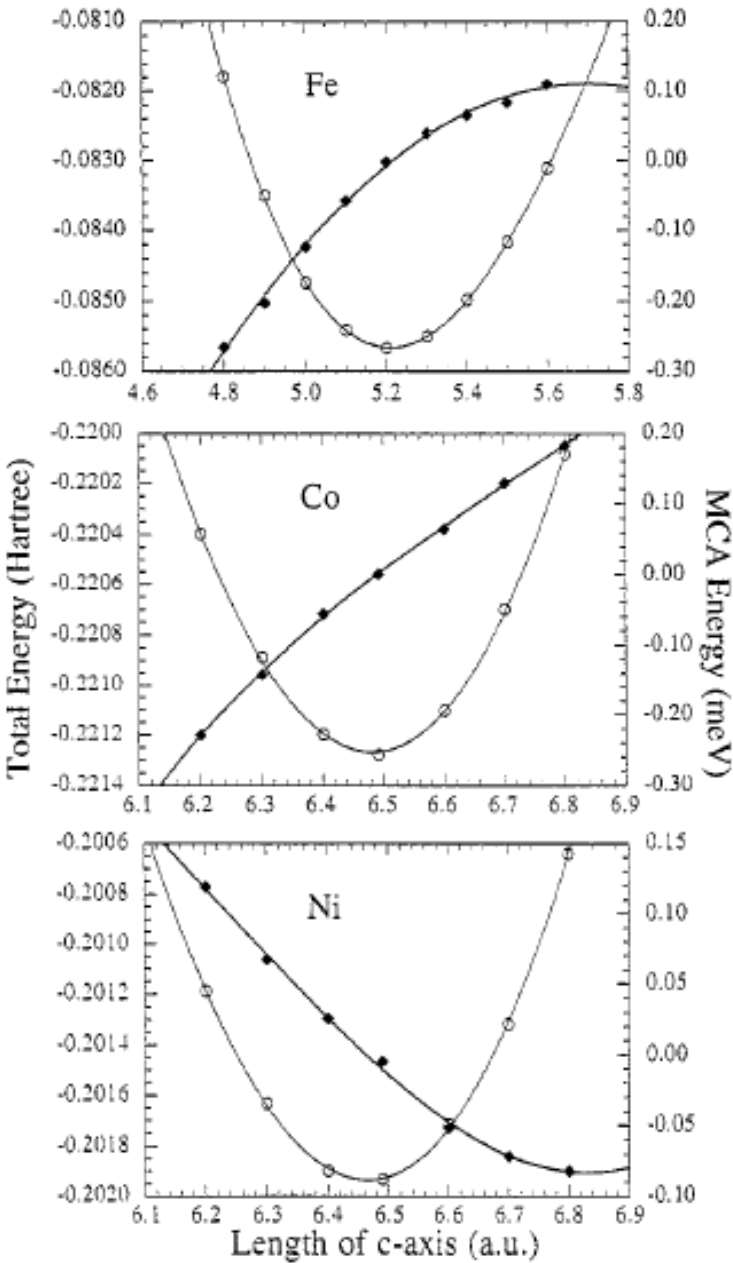$$\lambda_{1,2,3,4,5,6,7,8,9} = 2\frac{x_{min1} - x_{min2}}{x_{min1} + x_{min2}}$$

Cubic systems: Itenerant magnets

R.Q. Wu et al. /Journal of Magnetism and Magnetic Materials 177–181 (1998) 1216–1219

	a (a.u.)	σ	$M_s(\mu_B)$	$M_L(\mu_B)$	$\lambda_{001}(10^{-6})$
bcc Fe					
LDA	5.20	-0.409	2.05	0.048	52
GGA	5.37	-0.486	2.17	0.045	29
EXP	5.41	-0.368	2.22	0.08	21
fcc Co					
LDA	6.48	-0.374	1.59	0.076	92
GGA	6.67	-0.396	1.66	0.073	56
EXP	6.70	---	1.72	0.12	79
fcc Ni					
LDA	6.46	-0.332	0.62	0.049	-63
GGA	6.64	-0.3376	0.66	0.050	-56
EXP	6.66	-0.376	0.57	0.05	-49

R. C. O'Handley,
Modern magnetic materials,
Wiley, 2000.

	T = 4.2 K		Room Temperature		
	$\lambda_{100}(\lambda^{\gamma,2})$	$\lambda_{111}(\lambda^{\varepsilon,2})$	$\lambda_{100}(\lambda^{\gamma,2})$	$\lambda_{111}(\lambda^{\varepsilon,2})$	Polycrystal λ_s
3d Metals					
BCC-Fe	26	−30	21	−21	−7
HCP-Co^a	(−150)	(45)	(−140)	(50)	(−62)
FCC-Ni	−60	−35	−46	−24	−34
BCC-FeCo	—	—	140	30	—
a-Fe$_{80}$B$_{20}$	48 (isotropic)	—	—	—	+32
a-Fe$_{40}$Ni$_{40}$B$_{20}$	+20	—	—	—	+14
a-Co$_{80}$B$_{20}$	−4	—	—	—	−4

Cubic systems: Itenerant magnets

M. Gibbs, Modern trends in magnetostriction, Springer, 2001.

B2(L2$_0$)

bcc   fcc   fcc   fcc   fcc   fcc
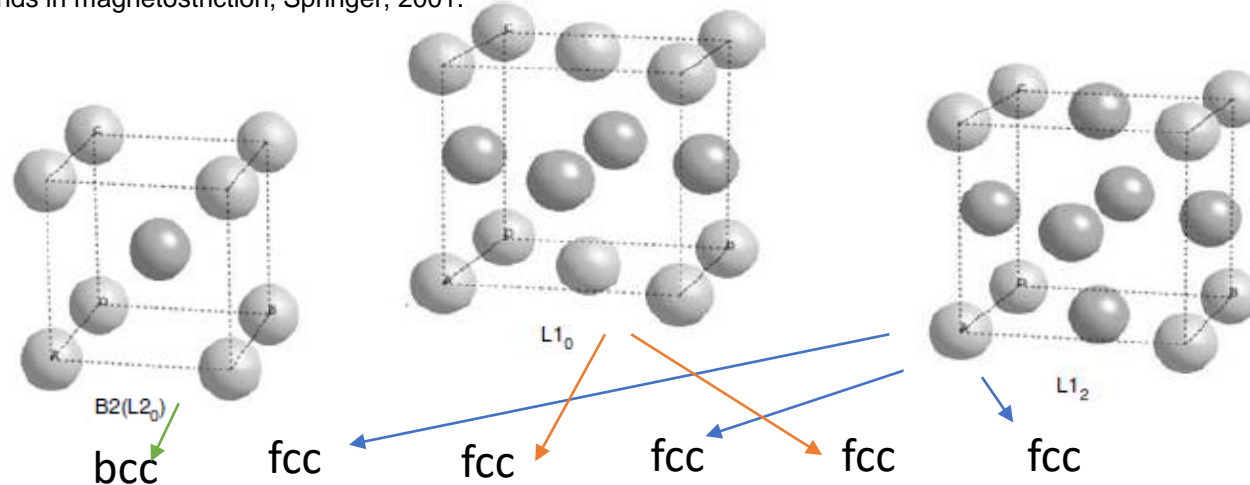
	FeCo	FeCo$_3$	FeNi	FeNi$_3$	CoNi	CoNi$_3$
a (a.u.)	5.38	6.70	6.76	6.70	6.62	6.66
	(5.39)		(6.76)	(6.71)	(6.67)	(6.65)
c (a.u.)	5.38	6.70	6.76	6.70	6.78	6.66
	(5.39)		(6.76)	(6.71)	(6.67)	(6.65)
E$_{MCA}$(µeV)	0	0	63	0	143	0
σ	-0.35	-0.36	-0.33	-0.35	-0.34	-0.36
λ$_{001}$ (10^{-6})	83	-68	10	27	42	33
	(125)		(12)	(13)	(42-100)	

BRIEF REVIEW OF KNOWN MAGNETOSTRICTIVE MATERIALS

G. Engdahl, Handbook of giant magnetostrictive materials, Academic Press,1999

Cubic systems: Rare-Earth magnets

M. Gibbs, Modern trends in magnetostriction, Springer, 2001.

DyFe$_2$

C15 cubic Laves phase

	Theory	Experiment
λ_{001} (GdCo$_2$)	-407	-1200
λ_{111} (GdCo$_2$)	19	< 10
λ_{001} (SmCo$_2$)	-290	---
λ_{001} (ErCo$_2$)	-516	-1000
λ_{001} (GdFe$_2$)	44	39
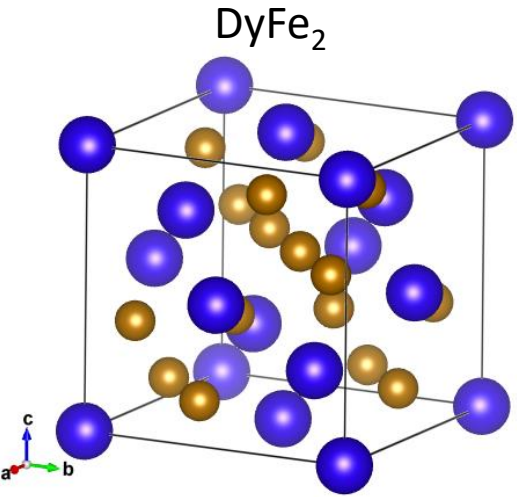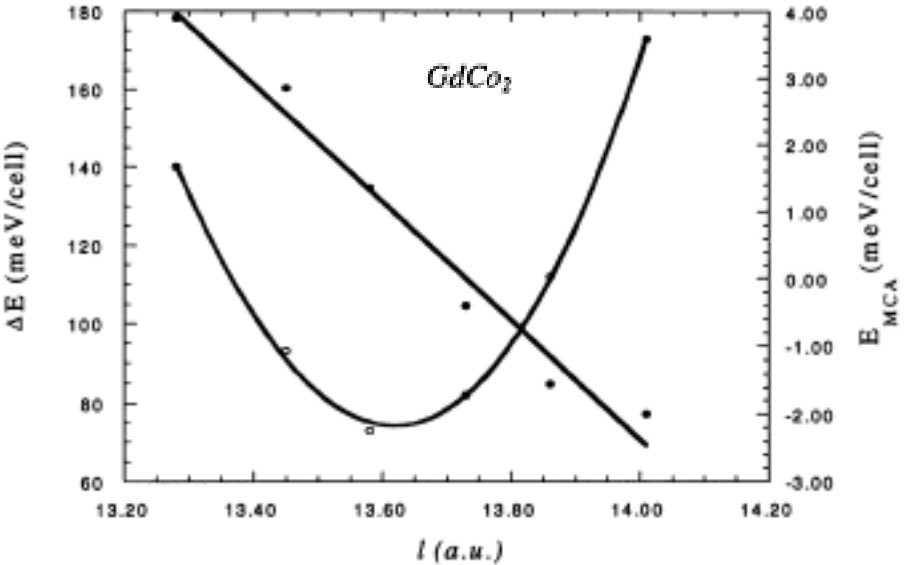
Table 16-10. Low-temperature magnetostriction constants for RCo$_2$ crystals [from Levitin and Markosyan (1990) unless otherwise noted].

R in RCo$_2$	$10^6 \lambda_{111}$	$10^6 \lambda_{100}$	T_c (K)[a]
Gd	$<10^{-5}$	-1200	409
Tb	4500	-1200[b]	256
Dy	5000[b, c]	-2000[d]	159
		-1300[e]	
Ho	300, 600[c]	-2000	85
Er	-2500	-1000	36
Tm	-4100[b]	750[c]	18

Table 1.6. Magnetostriction of Cubic Laves Phase Compounds with Rare Earths at $T = 0$

Compound	$\lambda_{111}(10^{-6})$	$\lambda_{100}(10^{-6})$	T_c (K)
NdAl$_2$	—	-700	61
TbAl$_2$	-3000	—	114
DyAl$_2$	—	-1700	68
TbMn$_2$	-3000	—	40
TbFe$_2$	4000, 4500	—	711
DyFe$_2$	—	-70	635
HoFe$_2$	—	-750	612
TmFe$_2$	-3500, -2600	—	610
TbCo$_2$	4400	—	256
DyCo$_2$	—	-2000	159
HoCo$_2$	—	-2200	85
ErCo$_2$	-2500	—	36
TbNi$_2$	1500	—	45
DyNi$_2$	—	-1300	30
HoNi$_2$	—	-1000	22

Table 1.7. Magnitudes of Single-Crystal Magnetostriction in Rare Earth–Fe$_2$ Compounds

Compound	$\frac{3}{2}\lambda_{111}$ (10^{-6}) (calculated at 0 K)	$\frac{3}{2}\lambda_{111}$ (10^{-6}) (measured at room temperature)	T_c
SmFe$_2$	-4800	-3150	676
TbFe$_2$	6600	3690	697, 711
DyFe$_2$	6300	1890	635
HoFe$_2$	2400	288	606
ErFe$_2$	-2250	-450	590, 597
TmFe$_2$	-5550	-315	560

TABLE 6

Magnetostriction coefficients at zero Kelvin in units of 10^{-3}

Hexagonal Rare-Earth

Element	$\lambda_1^{\alpha,2}$	$\lambda_2^{\alpha,2}$	$\lambda^{\gamma,2}$	$\lambda^{\epsilon,2}$	$\lambda_1^{\alpha,0} - \frac{1}{3}\lambda_1^{\alpha,2}$	$\lambda_2^{\alpha,0} - \frac{1}{3}\lambda_2^{\alpha,2}$	$\lambda^{\gamma,4}$
Gadolinium[a]	0.14	−0.13	0.11	0.02	–	–	–
Terbium[b]	−2.6[c]	9.0[c]	8.7	15.0[c]	−0.8	4.3	−2.1
Dysprosium[b]	–	–	9.4	5.5	−2.0	7.3	1.5
Holmium[b]	–	–	2.5[c]	--	−3.9	7.1	–
Erbium[b]	–	–	−5.1[c]	–	+0.3	6.2	–

[a] After Mishima et al. (1976).
[b] After Rhyne (1972).
[c] Extrapolated from paramagnetic range using single-ion theory.

Oxide magnets

	T = 4.2 K		Room Temperature		
	$\lambda_{100}(\lambda^{\gamma,2})$	$\lambda_{111}(\lambda^{\epsilon,2})$	$\lambda_{100}(\lambda^{\gamma,2})$	$\lambda_{111}(\lambda^{\epsilon,2})$	Polycrystal λ_s
Spinel Ferrites					
Fe_3O_4	0	50	−15	56	+40
$MnFe_2O_4$	—	—	(−54)	(10)	—
$CoFe_2O_4$	—	—	−670	120	−110
Garnets					
YIG	−0.6	−2.5	−1.4	−1.6	−2

MAELAS TESTS

Table 3: Anisotropic magnetostriction coefficients and MAE calculated by the program MAELAS and measured in experiment ($T \approx 0$ K) for a set of magnetic materials. In parenthesis we show the magnetostriction coefficients with Mason's definitions obtained using the relations given by Eq. A.2.

| Material	Crystal system	Space group	Magnetostriction coefficient	MAELAS ($\times 10^{-6}$)	Expt. ($\times 10^{-6}$)	MAE	MAELAS (μeV/atom)	Expt. (μeV/atom)
Fe bcc	Cubic (I)	229	λ_{001}	23	26 [44]	$E(110) - E(001)$	0.1	1.0 [43]
			λ_{111}	19	-30 [44]	$E(111) - E(001)$	0.21	1.3 [43]
Co hcp	Hexagonal (I)	194	$\lambda^{\alpha1,2}$ (λ_A)	85 (-78)	95 (-66) [47]	$E(100) - E(001)$	53	61 [43]
			$\lambda^{\alpha2,2}$ (λ_B)	-115 (-92)	-126 (-123) [47]			
			$\lambda^{\gamma,2}$ (λ_C)	15 (115)	57 (126) [47]			
			$\lambda^{\varepsilon,2}$ (λ_D)	-17 (1)	-286 (-128) [47]			
Gd hcp	Hexagonal (I)	194	$\lambda^{\alpha1,2}$	-67	$145^\dagger$ [49]	$E(100) - E(001)$	32	35 [48]
			$\lambda^{\alpha2,2}$	145	$-125^\dagger$ [49]			
			$\lambda^{\gamma,2}$	143	$108^\dagger$ [49]			
			$\lambda^{\varepsilon,2}$	-95	$22^\dagger$ [49]			
YCo$_5$	Hexagonal (I)	191	$\lambda^{\alpha1,2}$	-90	$\|\lambda^{\alpha1,2}\| < 100$ [4]	$E(100) - E(001)$	365	567 [50]
			$\lambda^{\alpha2,2}$	115	$\|\lambda^{\alpha2,2}\| < 100$ [4]			
			$\lambda^{\gamma,2}$	73				
			$\lambda^{\varepsilon,2}$	147				
FePd L1$_0$	Tetragonal (I)	123	$\frac{-\lambda^{\alpha1,2}}{3} + \frac{\lambda^{\gamma,2}}{2}$	12	$100^\ddagger$ [52]	$E(100) - E(001)$	109	181 [51]
			$\lambda^{\alpha1,2}$	-23				
			$\lambda^{\alpha2,2}$	83				
			$\lambda^{\gamma,2}$	8				
			$\lambda^{\varepsilon,2}$	25				
			$\lambda^{\delta,2}$	61				

†Terms higher than second-order direction cosine polynomial were included.

‡The experimental measurement corresponds to $\lambda^{\alpha1,0} + \frac{-\lambda^{\alpha1,2}}{3} + \frac{\lambda^{\gamma,2}}{2}$ with composition Fe$_{48}$Pd$_{52}$.

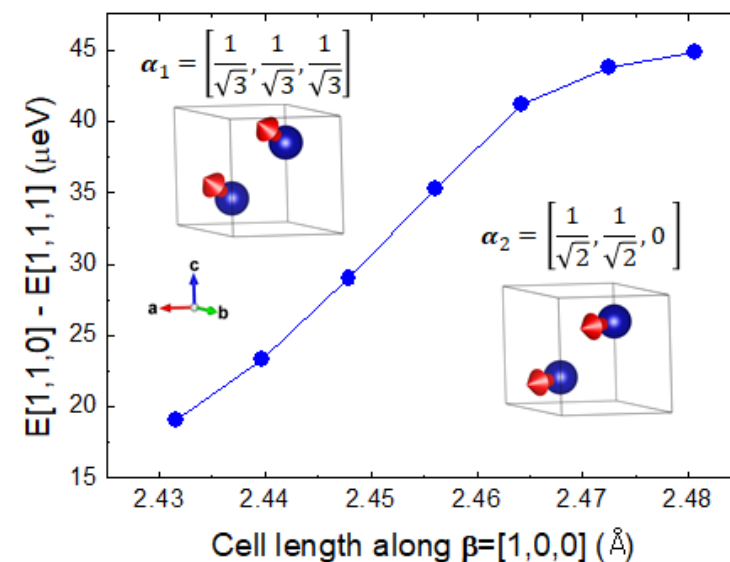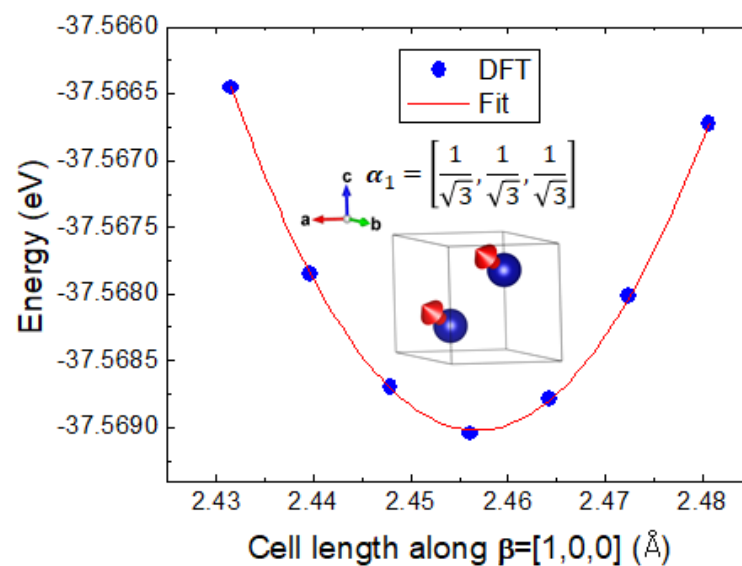# MAELAS TESTS: Co hcp
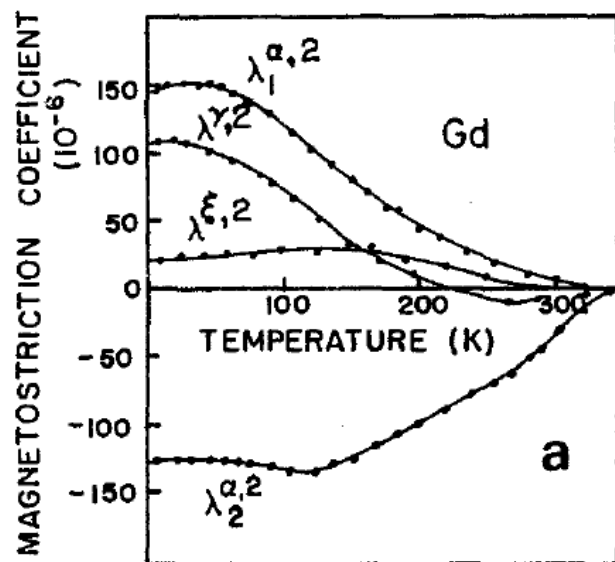
Experimental results

Z. Physik 224, 148—155 (1969)
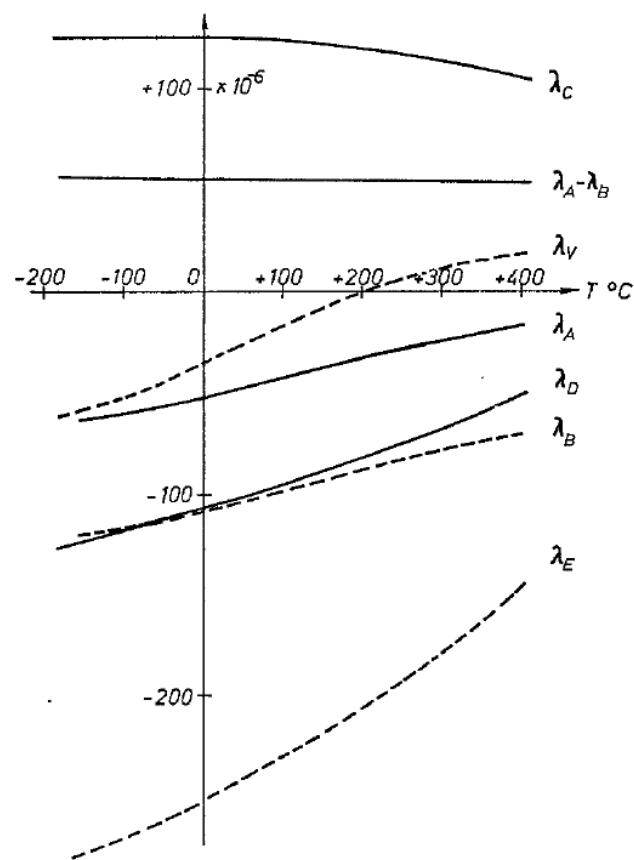
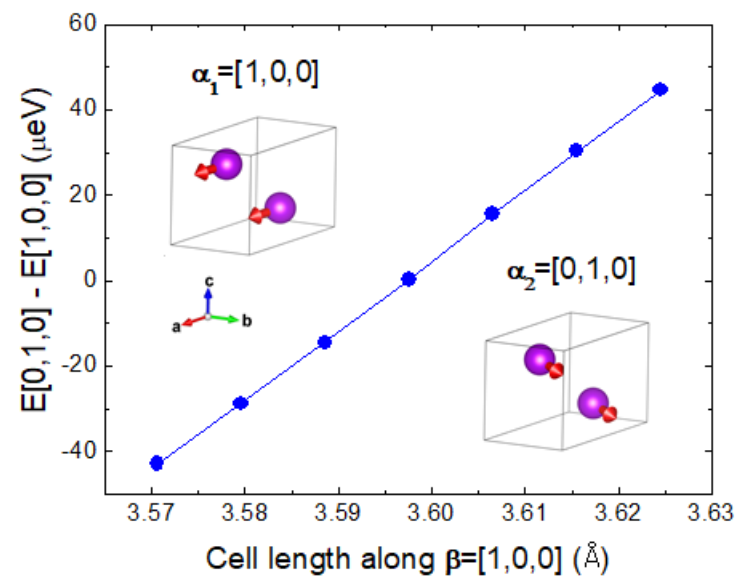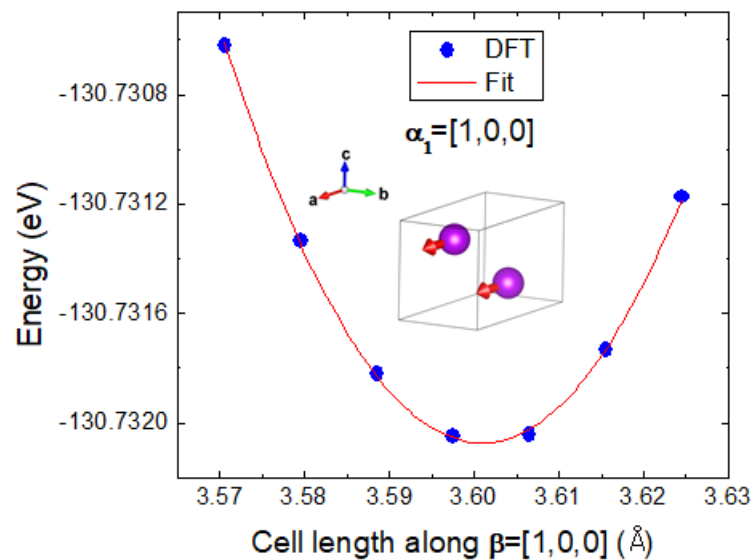Calculation of $\lambda^{\alpha1,2}$ for Co hcp using MAELAS

MAELAS TESTS: Gd hcp

Experimental results

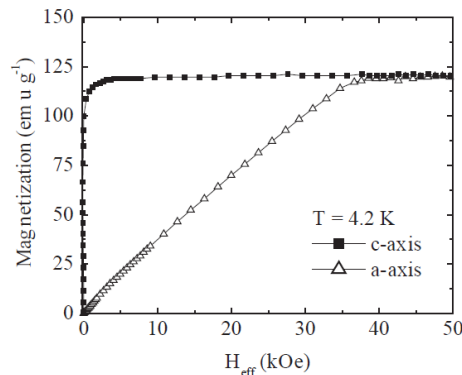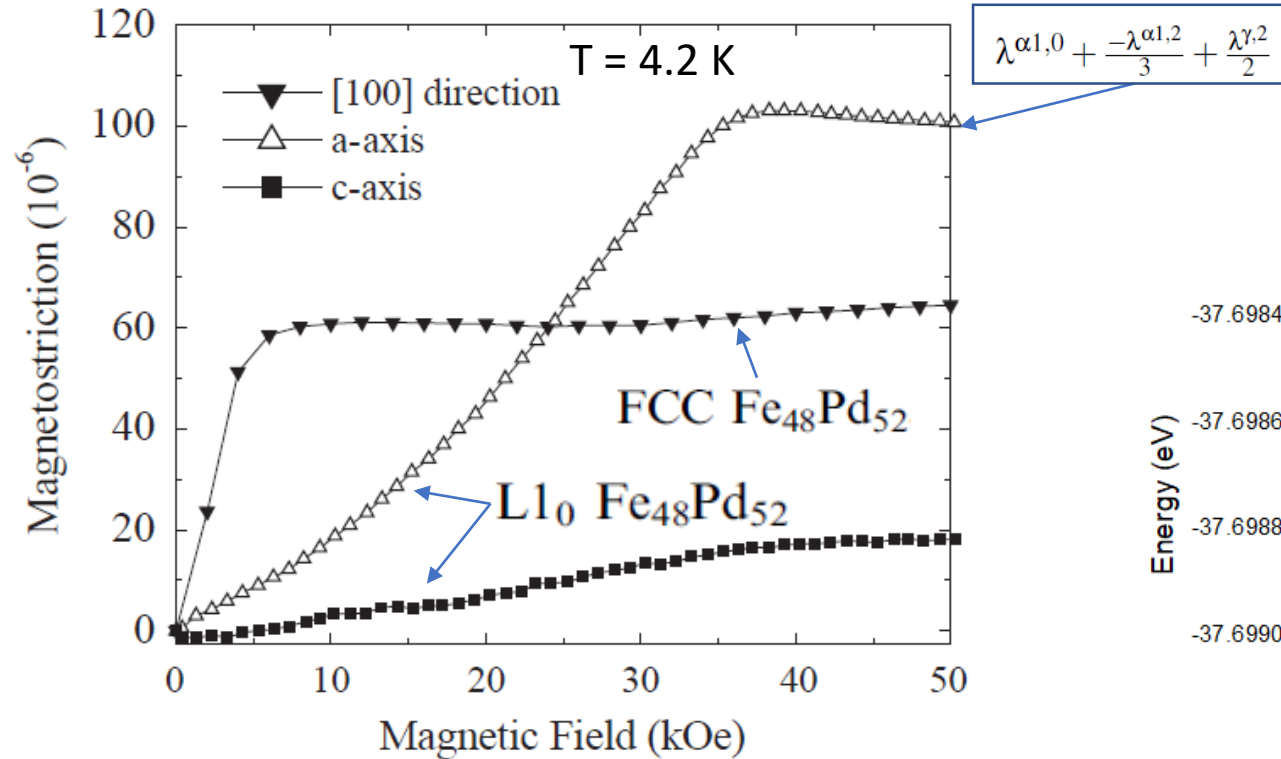Mishima, A., H. Fujii and T. Okamoto, 1976, J. Phys. Soc. Jap. 40, 962.

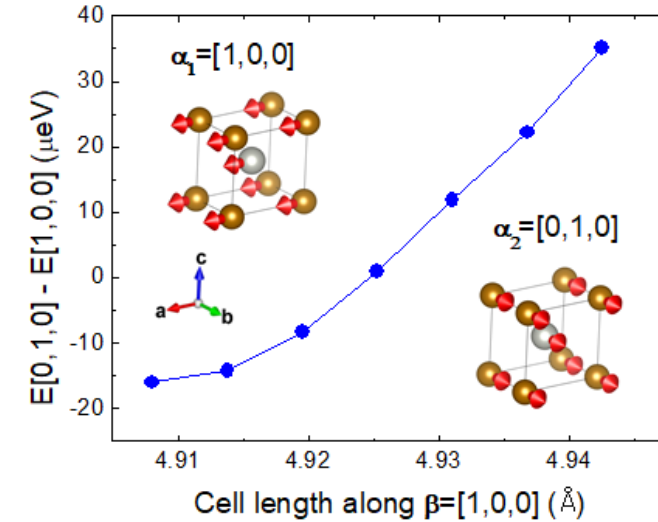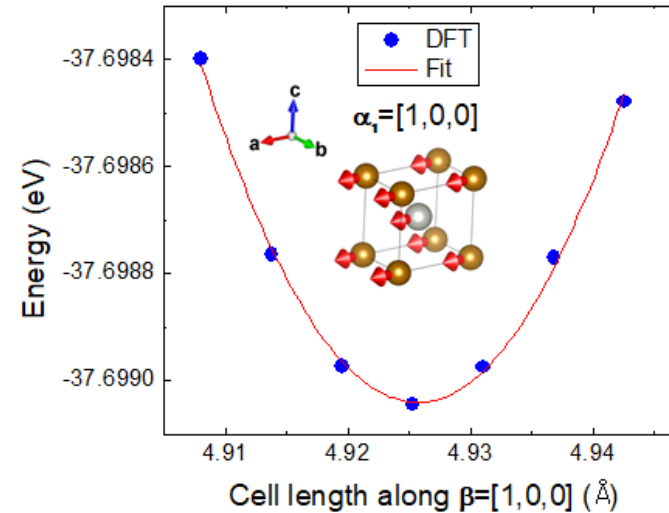Calculation of $\lambda^{\gamma,2}$ for Gd hcp using MAELAS

MAELAS TESTS: L1_0 FePd

Experimental results

$$\lambda^{\alpha1,0} + \frac{-\lambda^{\alpha1,2}}{3} + \frac{\lambda^{\gamma,2}}{2}$$

T = 4.2 K

Calculation of $\lambda^{\gamma,2}$ for FePd L1$_0$ using MAELAS

Bibliography

- J. R. Cullen, A. E. Clark, and K. B. Hathaway, in Materials, Science and Technology (VCH Publishings, 1994), pp. 529 – 565.

- R.Q. Wu et al. Journal of Magnetism and Magnetic Materials 177-181 (1998) 1216-1219.

- M.R.J.Gibbs, Modern Trends in Magnetostriction, Springer Netherlands (2001).

- Göran Engdahl, Isaak D. Mayergoyz, Handbook of Giant Magnetostrictive Materials, Academic Press (1999).