Instituto Federal de São Paulo

Campus Birigui

Relatório de Ensaio


Máquina: **Emic DL30000N** Célula: **Trd 24** Extensômetro: **-** Data: **10/06/2013** Hora: **14:28:22** Trabalho n° **0053**

Programa: **Tesc versão 3.04** Método de Ensaio: **Davi IC PLA**

Ident. Amostra: >>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>> Identificação: **Amostras A00** Material: **PLA Maker** Operador: **Vicente**

Corpo de Prova	Compr. Base (mm)	Força @Força Max. (N)	Força @Ruptura (N)	Tensão @Ruptura (MPa)	Tensão @Escoam. ES1 (MPa)	Mod.Elástic. (MPa)
CP 1	**50.00**	**2011.59**	**2011.59**	**38.33**	**21.05**	**516.66**
CP 2	**50.00**	**2068.06**	**2053.09**	**42.23**	**24.27**	**563.91**
CP 3	**50.00**	**1853.57**	**1849.99**	**37.15**	**24.04**	**509.69**
CP 4	**50.00**	**2120.28**	**2105.31**	**43.51**	**27.21**	**575.14**
CP 5	**50.00**	**2000.36**	**1985.05**	**39.68**	**21.68**	**559.02**
Número CPs	**5**	**5**	**5**	**5**	**5**	**5**
Média	**50.00**	**2011**	**2001**	**40.18**	**23.65**	**544.9**
Desv.Padrão	**0.0000**	**100.1**	**95.87**	**2.651**	**2.440**	**29.63**
Coef.Var.(%)	**0.0000**	**4.979**	**4.791**	**6.598**	**10.32**	**5.438**
Mínimo	**50.00**	**1854**	**1850**	**37.15**	**21.05**	**509.7**
Máximo	**50.00**	**2120**	**2105**	**43.51**	**27.21**	**575.1**

Tensão (MPa)

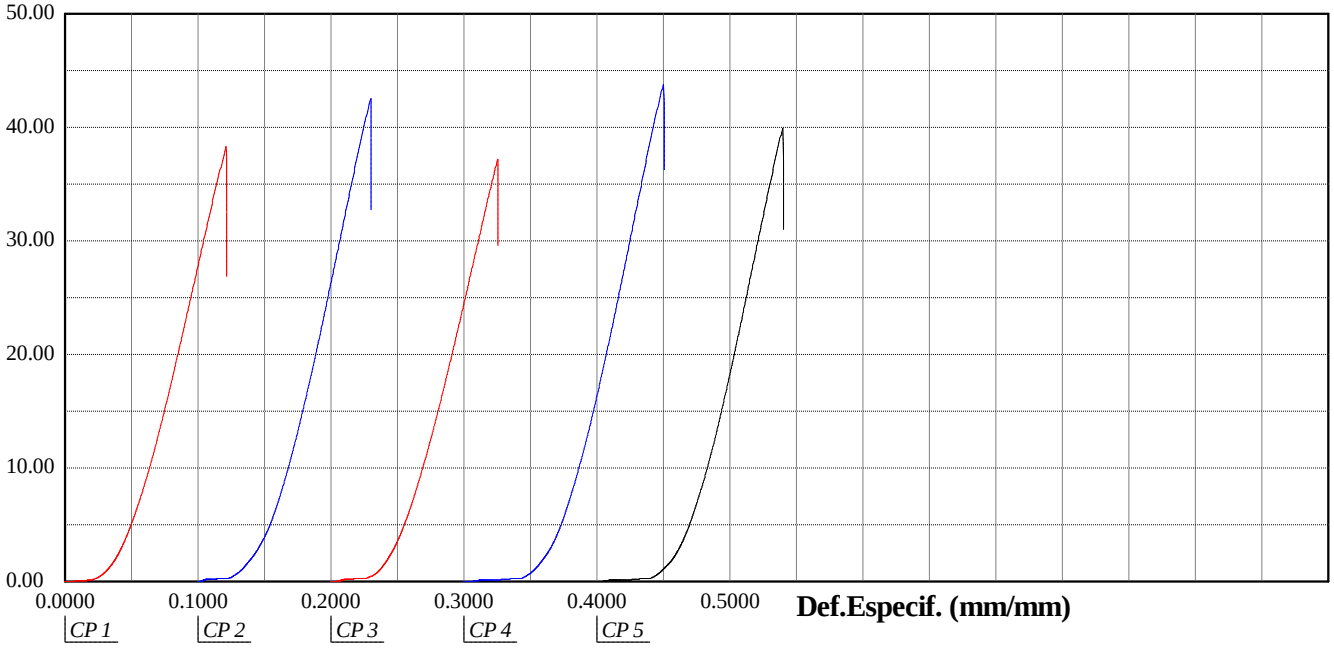

Observação: Ensaios realizados em 21/06/2024 período da manhã - CPs 1 e 2, velocidade 5 mm/min, CP 3 velocidade 2 mm/min



This document was created with the Win2PDF “Print to PDF” printer available at

https://www.win2pdf.com

This version of Win2PDF 10 is for evaluation and non-commercial use only.
Visit https://www.win2pdf.com/trial/ for a 30 day trial license.

This page will not be added after purchasing Win2PDF.

https://www.win2pdf.com/purchase/