Instituto Federal de São Paulo

Campus Birigui

Relatório de Ensaio


Máquina: **Emic DL30000N** Célula: **Trd 24** Extensômetro: **-** Data: **21/06/2024** Hora: **10:21:24** Trabalho n° **0054**

Programa: **Tesc versão 3.04** Método de Ensaio: **Davi IC PLA**

Ident. Amostra: >>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>> Identificação: **Amostras A01** Material: **PLA Maker** Operador: **Vicente**

Corpo de Prova	Compr. Base (mm)	Força @Força Max. (N)	Força @Ruptura (N)	Tensão @Ruptura (MPa)	Tensão @Escoam. ES1 (MPa)	Mod.Elástic. (MPa)
CP 1	**50.00**	**2170.63**	**2170.63**	**45.03**	**25.37**	**577.32**
CP 2	**50.00**	**2092.73**	**2076.40**	**42.27**	**22.14**	**574.40**
CP 3	**50.00**	**2127.09**	**2127.09**	**44.26**	**23.31**	**587.18**
CP 4	**50.00**	**2036.93**	**2036.93**	**42.00**	**22.41**	**571.49**
CP 5	**50.00**	**2116.54**	**2116.54**	**43.28**	**23.52**	**567.73**
Número CPs	**5**	**5**	**5**	**5**	**5**	**5**
Média	**50.00**	**2109**	**2106**	**43.37**	**23.35**	**575.6**
Desv.Padrão	**0.0000**	**49.09**	**50.94**	**1.291**	**1.270**	**7.372**
Coef.Var.(%)	**0.0000**	**2.328**	**2.419**	**2.977**	**5.441**	**1.281**
Mínimo	**50.00**	**2037**	**2037**	**42.00**	**22.14**	**567.7**
Máximo	**50.00**	**2171**	**2171**	**45.03**	**25.37**	**587.2**

Tensão (MPa)

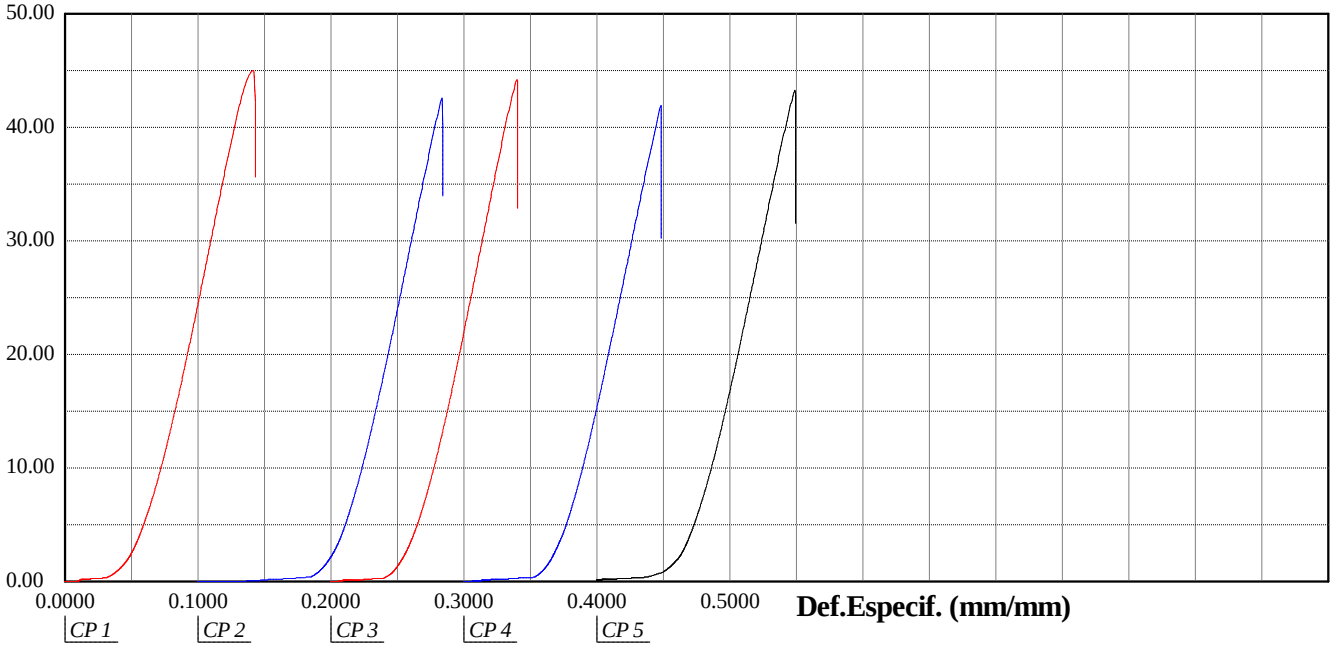

Observação: Ensaios realizados em 21/06/2024 período da manhã - CPs 1 e 2, velocidade 5 mm/min, CP 3 velocidade 2 mm/min



This document was created with the Win2PDF “Print to PDF” printer available at

https://www.win2pdf.com

This version of Win2PDF 10 is for evaluation and non-commercial use only.
Visit https://www.win2pdf.com/trial/ for a 30 day trial license.

This page will not be added after purchasing Win2PDF.

https://www.win2pdf.com/purchase/