Instituto Federal de São Paulo

Campus Birigui

Relatório de Ensaio


Máquina: **Emic DL30000N** Célula: **Trd 24** Extensômetro: **-** Data: **21/06/2024** Hora: **10:41:43** Trabalho n° **0055**

Programa: **Tesc versão 3.04** Método de Ensaio: **Davi IC PLA**

Ident. Amostra: >>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>> Identificação: **Amostras A02** Material: **PLA Maker** Operador: **Vicente**

Corpo de Prova	Compr. Base (mm)	Força @Força Max. (N)	Força @Ruptura (N)	Tensão @Ruptura (MPa)	Tensão @Escoam. ES1 (MPa)	Mod.Elástic. (MPa)
CP 1	**50.00**	**2151.75**	**2088.47**	**44.34**	**24.85**	**587.29**
CP 2	**50.00**	**2172.84**	**2172.84**	**46.37**	**23.98**	**586.83**
CP 3	**50.00**	**2193.42**	**2193.08**	**45.78**	**22.94**	**576.41**
CP 4	**50.00**	**2168.42**	**2168.42**	**45.53**	**23.21**	**568.09**
CP 5	**50.00**	**2016.86**	**2016.86**	**42.52**	**20.68**	**599.03**
Número CPs	**5**	**5**	**5**	**5**	**5**	**5**
Média	**50.00**	**2141**	**2128**	**44.91**	**23.13**	**583.5**
Desv.Padrão	**0.0000**	**70.78**	**73.81**	**1.526**	**1.562**	**11.77**
Coef.Var.(%)	**0.0000**	**3.306**	**3.469**	**3.398**	**6.751**	**2.017**
Mínimo	**50.00**	**2017**	**2017**	**42.52**	**20.68**	**568.1**
Máximo	**50.00**	**2193**	**2193**	**46.37**	**24.85**	**599.0**

Tensão (MPa)

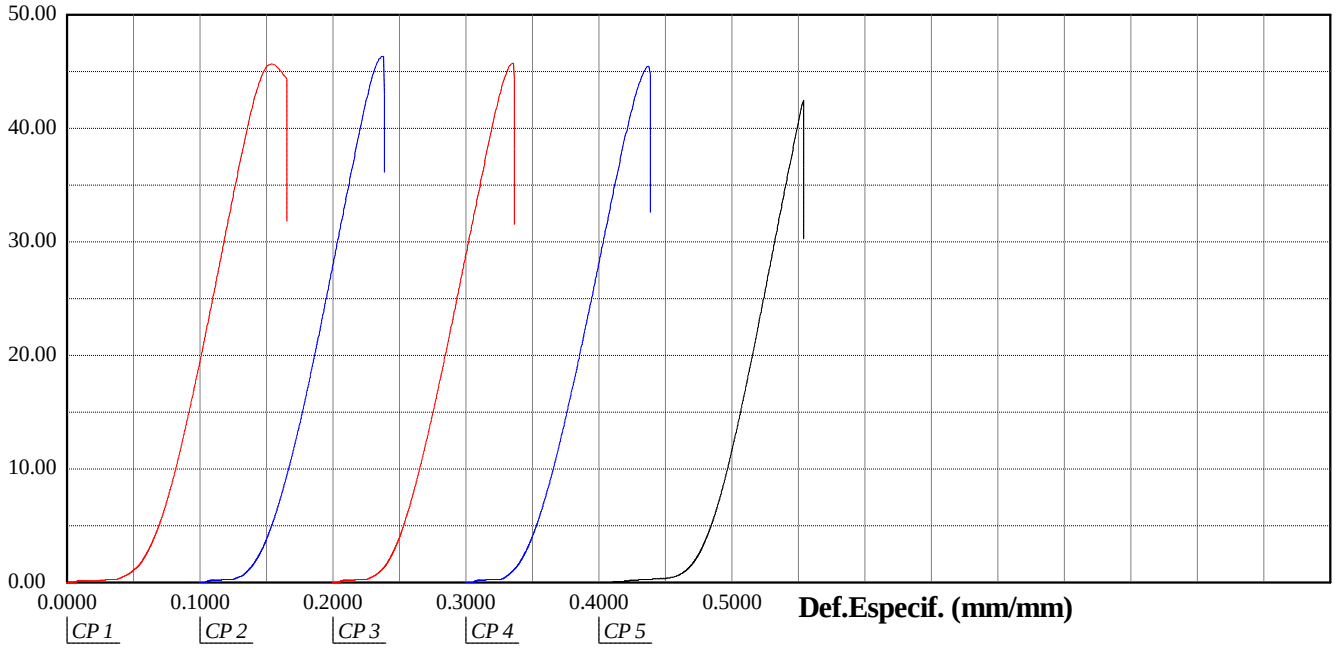

Observação: Ensaios realizados em 21/06/2024 período da manhã - CPs 1 e 2, velocidade 5 mm/min, CP 3 velocidade 2 mm/min



This document was created with the Win2PDF “Print to PDF” printer available at

https://www.win2pdf.com

This version of Win2PDF 10 is for evaluation and non-commercial use only.
Visit https://www.win2pdf.com/trial/ for a 30 day trial license.

This page will not be added after purchasing Win2PDF.

https://www.win2pdf.com/purchase/