Instituto Federal de São Paulo

Campus Birigui

Relatório de Ensaio


Máquina: **Emic DL30000N** Célula: **Trd 24** Extensômetro: **-** Data: **10/06/2013** Hora: **16:03:29** Trabalho n° **0061**

Programa: **Tesc versão 3.04** Método de Ensaio: **Davi IC PLA**

Ident. Amostra: >>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>> Identificação: **Amostras A20** Material: **PLA Maker** Operador: **Vicente**

Corpo de Prova	Compr. Base (mm)	Força @Força Max. (N)	Força @Ruptura (N)	Tensão @Ruptura (MPa)	Tensão @Escoam. ES1 (MPa)	Mod.Elástic. (MPa)
CP 1	**50.00**	**1922.46**	**1911.23**	**44.97**	**27.74**	**638.11**
CP 2	**50.00**	**1674.62**	**1674.62**	**39.76**	**25.53**	**597.06**
CP 3	**50.00**	**1682.96**	**1677.00**	**39.54**	**24.33**	**632.87**
CP 4	**50.00**	**1992.88**	**1981.31**	**46.87**	**26.15**	**633.24**
CP 5	**50.00**	**1923.48**	**1917.35**	**45.01**	**25.92**	**632.33**
Número CPs	**5**	**5**	**5**	**5**	**5**	**5**
Média	**50.00**	**1839**	**1832**	**43.23**	**25.93**	**626.7**
Desv.Padrão	**0.0000**	**149.3**	**145.5**	**3.354**	**1.231**	**16.74**
Coef.Var.(%)	**0.0000**	**8.117**	**7.939**	**7.759**	**4.748**	**2.672**
Mínimo	**50.00**	**1675**	**1675**	**39.54**	**24.33**	**597.1**
Máximo	**50.00**	**1993**	**1981**	**46.87**	**27.74**	**638.1**

Tensão (MPa)

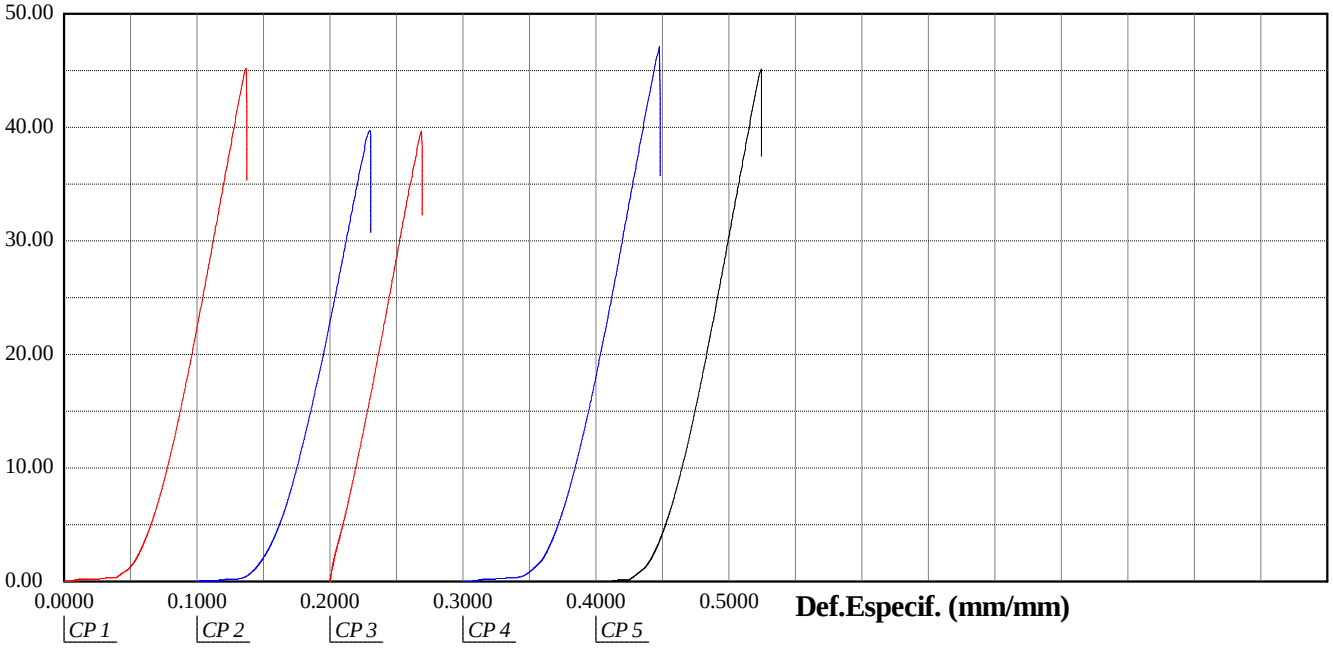

Observação: Ensaios realizados em 05/08/2024 período da NOITE



This document was created with the Win2PDF “Print to PDF” printer available at

https://www.win2pdf.com

This version of Win2PDF 10 is for evaluation and non-commercial use only.
Visit https://www.win2pdf.com/trial/ for a 30 day trial license.

This page will not be added after purchasing Win2PDF.

https://www.win2pdf.com/purchase/