Instituto Federal de São Paulo

Campus Birigui

Relatório de Ensaio

Máquina: **Emic DL30000N** Célula: **Trd 24** Extensômetro: **-** Data: **10/06/2013** Hora: **16:15:55** Trabalho n° **0062**

Programa: **Tesc versão 3.04** Método de Ensaio: **Davi IC PLA**

Ident. Amostra: >>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>> Identificação: **Amostras A21** Material: **PLA Maker** Operador: **Vicente**

Corpo de Prova	Compr. Base (mm)	Força @Força Max. (N)	Força @Ruptura (N)	Tensão @Ruptura (MPa)	Tensão @Escoam. ES1 (MPa)	Mod.Elástic. (MPa)
CP 1	**50.00**	**1698.61**	**1698.61**	**40.08**	**28.64**	**635.02**
CP 2	**50.00**	**1785.36**	**1774.64**	**41.40**	**23.85**	**604.26**
CP 3	**50.00**	**1898.47**	**1883.50**	**44.79**	**29.71**	**640.44**
CP 4	**50.00**	**1885.21**	**1870.75**	**43.55**	**24.92**	**625.82**
CP 5	**50.00**	**1909.70**	**1894.90**	**44.71**	**27.86**	**650.51**
Número CPs	**5**	**5**	**5**	**5**	**5**	**5**
Média	**50.00**	**1835**	**1824**	**42.91**	**27.00**	**631.2**
Desv.Padrão	**0.0000**	**91.10**	**85.02**	**2.089**	**2.500**	**17.52**
Coef.Var.(%)	**0.0000**	**4.963**	**4.660**	**4.869**	**9.261**	**2.775**
Mínimo	**50.00**	**1699**	**1699**	**40.08**	**23.85**	**604.3**
Máximo	**50.00**	**1910**	**1895**	**44.79**	**29.71**	**650.5**

Tensão (MPa)

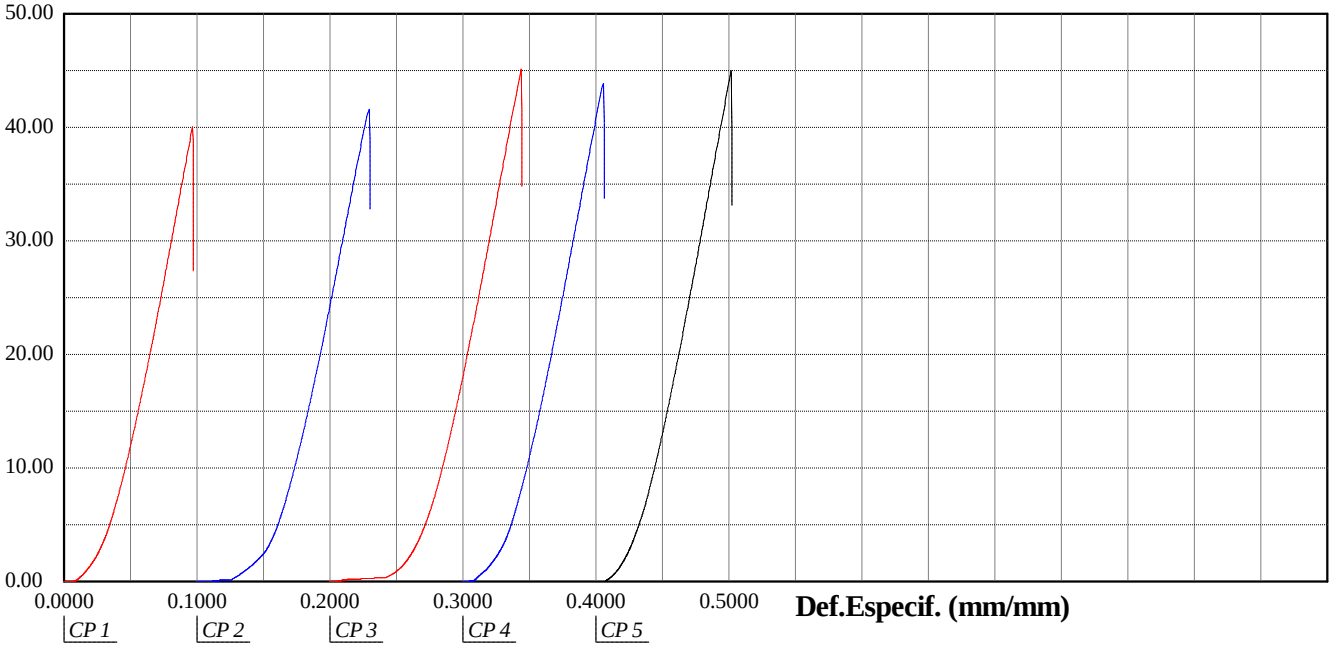

Observação: Ensaios realizados em 21/06/2024 período da NOITE

This document was created with the Win2PDF “Print to PDF” printer available at

https://www.win2pdf.com

This version of Win2PDF 10 is for evaluation and non-commercial use only.
Visit https://www.win2pdf.com/trial/ for a 30 day trial license.

This page will not be added after purchasing Win2PDF.

https://www.win2pdf.com/purchase/