Instituto Federal de São Paulo

Campus Birigui

Relatório de Ensaio


Máquina: **Emic DL30000N** Célula: **Trd 24** Extensômetro: **-** Data: **10/06/2013** Hora: **16:31:43** Trabalho n° **0063**

Programa: **Tesc versão 3.04** Método de Ensaio: **Davi IC PLA**

Ident. Amostra: >>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>>> Identificação: **Amostras A22** Material: **PLA Maker** Operador: **Vicente**

Corpo de Prova	Compr. Base (mm)	Força @Força Max. (N)	Força @Ruptura (N)	Tensão @Ruptura (MPa)	Tensão @Escoam. ES1 (MPa)	Mod.Elástic. (MPa)
CP 1	**50.00**	**2045.44**	**2029.45**	**48.08**	**22.67**	**687.50**
CP 2	**50.00**	**1937.94**	**1922.80**	**45.41**	**24.77**	**614.63**
CP 3	**50.00**	**2076.40**	**2076.40**	**48.78**	**29.57**	**631.36**
CP 4	**50.00**	**1753.38**	**1739.94**	**41.06**	**27.96**	**622.53**
CP 5	**50.00**	**2133.21**	**2133.21**	**50.34**	**28.54**	**632.89**
Número CPs	**5**	**5**	**5**	**5**	**5**	**5**
Média	**50.00**	**1989**	**1980**	**46.74**	**26.70**	**637.8**
Desv.Padrão	**0.0000**	**149.8**	**155.0**	**3.638**	**2.880**	**28.75**
Coef.Var.(%)	**0.0000**	**7.530**	**7.827**	**7.785**	**10.79**	**4.507**
Mínimo	**50.00**	**1753**	**1740**	**41.06**	**22.67**	**614.6**
Máximo	**50.00**	**2133**	**2133**	**50.34**	**29.57**	**687.5**

Tensão (MPa)

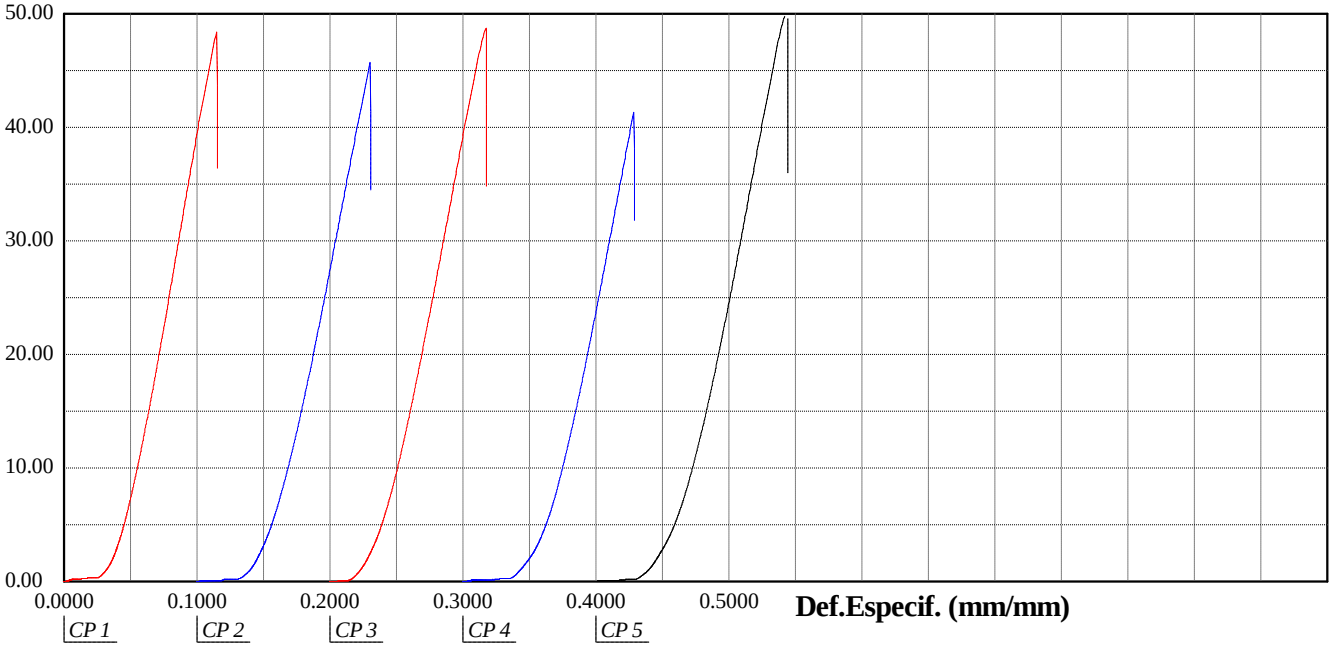

Observação: Ensaios realizados em 03/08/2024 período da NOITE



This document was created with the Win2PDF “Print to PDF” printer available at

https://www.win2pdf.com

This version of Win2PDF 10 is for evaluation and non-commercial use only.
Visit https://www.win2pdf.com/trial/ for a 30 day trial license.

This page will not be added after purchasing Win2PDF.

https://www.win2pdf.com/purchase/