

THERMOCHEMICAL MODELING OF A PHENOLIC LINER IN A SOLID ROCKET MOTOR USING ANSYS MECHANICAL

MIT ROCKET TEAM — M. NICHITIU — SOLID PROPULSION SIMULATIONS

SEPTEMBER 18, 2026



Contents

1	Context: Solid Rocket Motor and Casing Layup	2
1.1	Physical Scope	2
1.2	Dimensions and Mesh Characteristics	2
1.3	Materials and Interfaces	3
2	Simulation 1: Volumetric Pyrolysis of the First Phenolic Layer	4
2.1	Theory and Derivation	4
2.2	Current ANSYS Mechanical Configuration	5
2.3	Simulation 1 Results	11
3	Simulation 2: Outgassing and Element Deactivation in Mechanical	21
3.1	Proposed Theory and Derivation	21
3.2	Implementation in Mechanical	23
3.3	Simulation 2 Results and Performance	24
4	Simulation 3: Corrected Thin Sector and Refined Radial Mesh	35
4.1	Objective and Executed Configuration	35
4.2	Final Status and Performance	35
4.3	Final Thermochemical Results	36
4.4	Virtual Recession and Element Deactivation	37
4.5	Final Spatial Analysis of State Variables	39
4.6	Scope and Reproducibility	45

Purpose of this document. *This report describes the transient thermal model for phenolic-liner pyrolysis and its extension, now implemented in ANSYS Mechanical, to represent outgassing, blowing, and discrete recession by element deactivation. The Simulation 2 section presents the numerical architecture and the final campaign assessment, intentionally stopped at the last fully synchronized state, $t = 6.45\text{s}$, after 129 of the 140 planned macro-steps. No extrapolation to 7s is used. Fluent and propellant combustion are outside the scope of this study. Computed quantities remain model results: they must be compared with measurements of the material actually manufactured, and the radial geometry must be corrected before any design or safety decision is made. A third simulation uses the corrected radii and a 0.10° angular sector. It reached its 7s horizon normally; its section presents all 140 converged states, both deleted phenolic rows, and the final spatial analysis.*

1 Context: Solid Rocket Motor and Casing Layup

1.1 Physical Scope

The system under study is a solid-propellant rocket motor whose casing is modeled as four contacting coaxial tubes: an inner phenolic layer, a thin epoxy layer, a second phenolic layer, and an aluminum shell. The geometry file contains the bodies **Phenolic0**, **Epoxy**, **Phenolic1**, and **Alu**, which correspond respectively to the Mechanical named selections **phe0**, **epo**, **phe1**, and **alu**. Mechanical nevertheless meshes only an axially truncated portion of this baseline model: the radial layup is preserved, but the reduced height simplifies the mesh and keeps the solution time reasonable. The dimensions below describe the complete motor, so extensive results must be scaled before extrapolation to the full motor.

The propellant is not included in the geometry. Its effect is represented by a prescribed gas temperature and convection coefficient on the inner surface of **phe0**. It should also be noted that ammonium perchlorate (AP) is the *oxidizer* in a composite propellant, not a fuel by itself. The composition of the fuel binder, any aluminum fraction, chamber pressure, and combustion history are not documented in the present model. Consequently, a wall heat flux cannot be derived from first principles: the current hot-side boundary condition remains an input that must be calibrated against a motor firing or supplied by a separate internal-flow model.

1.2 Dimensions and Mesh Characteristics

The dimensional review identified a factor-of-two error in the interpretation of the radial dimensions. Interface values from 133.350 to 152.400 mm are *nominal diameters*, not radii. The corrected motor is therefore a straight cylinder of length $L = 1.8288$ m, exactly 72 in, with a 133.35 mm (5.25 in) bore and a 152.40 mm (6 in) outside diameter. The total radial buildup is 9.525 mm.

Difference between the design and the executed model. The AP214 STEP file and MAPDL database currently use these same values as *radii*; MAPDL confirms, in particular, $R_{\text{in}} = 0.13335$ m. Simulations 1 and 2 were therefore executed with a numerical bore of 266.7 mm and a numerical outside diameter of 304.8 mm, i.e. a geometry that is twice too large radially. Existing results remain results for this numerical geometry and must not be presented as quantitative predictions for the nominal motor until the model is corrected and rerun.

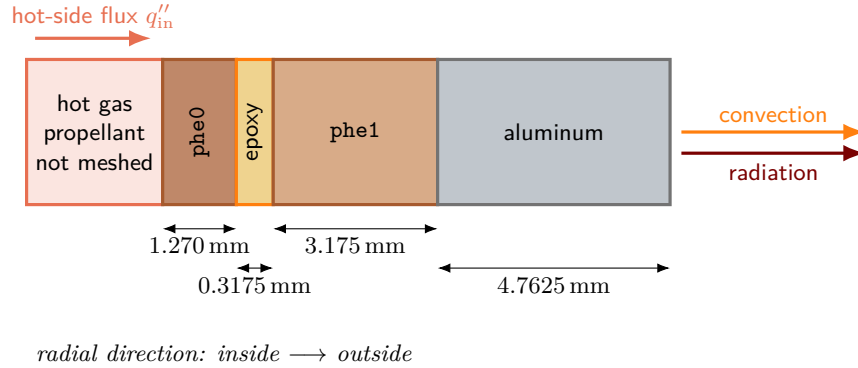


Figure 1. Corrected nominal radial layup. Layer widths are schematic; the stated dimensions are radial thicknesses.

Body	Inner diameter (mm)	Outer diameter (mm)	Radial thickness (mm)
phe0	133.350	135.890	1.2700
epo	135.890	136.525	0.3175
phe1	136.525	142.875	3.1750
alu	142.875	152.400	4.7625

Table 1. Corrected nominal motor dimensions. A radial thickness is half the difference between the outside and inside diameters.

For the nominal motor, the hot-side cylindrical area is $2\pi r_i L = 0.7662 \text{ m}^2$, and the outside area is 0.8756 m^2 . In the numerical model that was actually executed, these areas are 1.5323 m^2 and 1.7512 m^2 , respectively. At unchanged length and density, tube masses in the oversized numerical model are four times those of the nominal geometry.

Mechanical meshes a complete 50 mm central axial slice, or 2.73% of the nominal length. Table 2 summarizes dimensions and mesh characteristics verified against the `ds.dat` export, the restart database, and the Simulation 2 state. The topology can be retained when the geometry is corrected, but every radial dimension and radial element size must be divided by two.

Characteristic	Verified value
Current meshed domain	50 mm slice, full circumference; $r = 133.350 \text{ mm}$ to 152.400 mm in the numerical database
Corrected nominal domain	$r = 66.675 \text{ mm}$ to 76.200 mm ; same axial slice if the mesh is regenerated without any other change
Element type and organization	Three-dimensional thermal SOLID279 elements; four coaxial volumes and three bonded thermal contacts
Radial divisions in phe0/epo/phe1/alu	8 / 1 / 6 / 9 layers; current mean sizes 0.3175 mm / 0.6350 mm / 1.0583 mm / 1.0583 mm
Radial sizes after correction	0.15875 mm / 0.3175 mm / 0.5292 mm / 0.5292 mm , with unchanged topology
Exported volume mesh	482 900 solid elements and 2 242 327 nodes
MAPDL restart database	630 881 elements defined after adding contacts and other auxiliary elements
Simulation 2 hot surface	135 900 nodes and 43 488 surface-effect elements; first phe0 band: 39 808 elements

Table 2. Dimensions and principal characteristics of the numerical mesh.

1.3 Materials and Interfaces

The inner body **phe0** uses the user material **PHENOLIC_PYROLYSIS**; **phe1** uses **PHENOLIC_VIRGIN**; the epoxy and aluminum bodies use the project’s generic materials. All three concentric interfaces are program-controlled bonded thermal contacts. This configuration represents perfect adhesion with neither debonding nor thermal contact resistance. It is appropriate for an initial study, but it does not investigate delamination, epoxy charring, or the formation of a gas-filled gap.

The initial density is 1250 kg m^{-3} for virgin phenolic, 1150 kg m^{-3} for epoxy, and 2700 kg m^{-3} for aluminum. The aluminum alloy and exact epoxy grade are unspecified. Their associated properties are therefore generic approximations, not qualified material data.

2 Simulation 1: Volumetric Pyrolysis of the First Phenolic Layer

2.1 Theory and Derivation

2.1.1 Local Conservation of Energy

Consider a fixed material volume V of phenolic, bounded by ∂V , with no macroscopic motion of the solid. The first law of thermodynamics requires the rate of change of internal energy to equal the net heat input by conduction plus the volumetric heat generation:

$$\frac{d}{dt} \int_V \rho u \, dV = - \int_{\partial V} \mathbf{q} \cdot \mathbf{n} \, dS + \int_V \rho \dot{q}_m \, dV. \quad (1)$$

Here, u is the specific internal energy, ρ is the density of the condensed medium, $\dot{q}_m$ is a specific heat source, and $\mathbf{q}$ is the heat flux. Applying the divergence theorem to the surface integral and noting that the volume is arbitrary gives

$$\frac{\partial(\rho u)}{\partial t} = -\nabla \cdot \mathbf{q} + \rho \dot{q}_m. \quad (2)$$

Using Fourier's law, $\mathbf{q} = -k\nabla T$, and identifying $\partial u / \partial T$ with c_p in the Mechanical thermal formulation yields the form used in the model:

$$\rho c_p \frac{\partial T}{\partial t} = \nabla \cdot (k \nabla T) + \rho \dot{q}_m. \quad (3)$$

Pyrolysis is endothermic. If $\Delta H_p > 0$ is the enthalpy absorbed per kilogram of converted material and α is the degree of conversion, the specific heat source is

$$\dot{q}_m = -\Delta H_p \dot{\alpha}, \quad (4)$$

and therefore

$$\boxed{\rho c_p \frac{\partial T}{\partial t} = \nabla \cdot (k \nabla T) - \rho \Delta H_p \dot{\alpha}.} \quad (5)$$

This first simulation does not transport the enthalpy of the pyrolysis gases and does not move the hot boundary. Equation (5) is therefore a conduction–reaction equation, not a complete ablation model.

2.1.2 Conversion Variable and Mass Loss

At a given temperature, the model interpolates between the virgin state v and the char residue c . The apparent density of the solid is written as

$$\rho_s(T, \alpha) = (1 - \alpha)\rho_v(T) + \alpha\rho_c(T). \quad (6)$$

The equivalent definition of conversion is

$$\alpha = \frac{\rho_v - \rho_s}{\rho_v - \rho_c}, \quad 0 \leq \alpha \leq 1. \quad (7)$$

Thus, $\alpha = 0$ denotes virgin material and $\alpha = 1$ denotes the residual *char*. This distinction is essential: $\alpha = 1$ means neither a void nor a fully consumed element. In this single-reaction model, the rate of volatile matter released per unit volume is

$$\dot{\omega}_g''' = (\rho_v - \rho_c)\dot{\alpha}. \quad (8)$$

The other properties are mixed linearly:

$$X(T, \alpha) = (1 - \alpha)X_v(T) + \alpha X_c(T), \quad X \in \{k, c_p, \rho\}. \quad (9)$$

This rule is simple and monotonic, but it is not a universal constitutive law for porous composites. Its validation requires measurements at intermediate conversion states or a sensitivity analysis.

2.1.3 Arrhenius Kinetics and Integration over an Increment

The frequency of activated molecular events is represented by the Arrhenius rate constant

$$k_r(T) = A \exp\left(-\frac{E_a}{RT}\right), \quad (10)$$

where A is the pre-exponential factor, E_a is the activation energy, and $R = 8.314462618 \, \text{J mol}^{-1} \text{K}^{-1}$. Assuming that the remaining quantity of reactive sites is proportional to $(1 - \alpha)^n$,

$$\boxed{\dot{\alpha} = k_r(T)(1 - \alpha)^n.} \quad (11)$$

During the current increment $[t, t + \Delta t]$, the code evaluates T at the midpoint temperature and treats k_r as constant. Let $\beta = 1 - \alpha$. Then $\dot{\beta} = -k_r \beta^n$. For $n = 1$,

$$\int_{\beta_0}^{\beta_1} \frac{d\beta}{\beta} = -k_r \int_t^{t+\Delta t} dt, \quad (12)$$

hence

$$\beta_1 = \beta_0 \exp(-k_r \Delta t), \quad \boxed{\alpha_1 = 1 - (1 - \alpha_0) \exp(-k_r \Delta t)}. \quad (13)$$

For $n \neq 1$, integration gives

$$\frac{\beta_1^{1-n} - \beta_0^{1-n}}{1-n} = -k_r \Delta t, \quad (14)$$

or

$$\boxed{\beta_1 = [\beta_0^{1-n} - (1-n)k_r \Delta t]^{1/(1-n)}, \quad \alpha_1 = 1 - \beta_1.} \quad (15)$$

The bracketed term is bounded to prevent a nonphysical value. The stored rate is the average over the increment, $\dot{\alpha} = (\alpha_1 - \alpha_0)/\Delta t$. The code requests a time-step cutback if $\Delta\alpha > 0.05$, thereby limiting excessively abrupt numerical conversion. The *current increment* specifically means the substep attempted or accepted by the solver between two converged time points, not the complete seven-second load step.

2.1.4 Finite-Element Weak Form

Multiplying Equation (5) by a test function N_i and integrating the conduction term by parts gives

$$\int_V N_i \rho c_p \frac{\partial T}{\partial t} dV + \int_V \nabla N_i \cdot k \nabla T dV = - \int_{\partial V} N_i \mathbf{q} \cdot \mathbf{n} dS \quad (16)$$

$$- \int_V N_i \rho \Delta H_p \dot{\alpha} dV. \quad (17)$$

After applying the approximation $T = \sum_j N_j T_j$, the matrix form is

$$\mathbf{C}(T, \alpha) \dot{\mathbf{T}} + \mathbf{K}(T, \alpha) \mathbf{T} = \mathbf{f}_q - \mathbf{f}_p(T, \alpha). \quad (18)$$

The dependence of k , c_p , ρ , and $\dot{\alpha}$ on temperature and history makes the problem nonlinear. **UserMatTh** is called at every integration point and returns the heat flux, its tangent, the heat capacity, the density, the specific heat source, and the state variables [1].

2.2 Current ANSYS Mechanical Configuration

2.2.1 Discretization, Contacts, and Boundary Conditions

All four bodies use SOLID279 three-dimensional thermal elements. The inspected export contains approximately 482 900 solid elements and 2 242 327 equations. Their distribution is given in Table 3. The eight layers through **phe0** yield an average radial thickness of only 0.318 mm, which is suitable for resolving a pyrolysis front. Even with the axial truncation described above, this radial resolution remains computationally expensive.

Body	Elements	Mean radial layers	Material
phe0	315536	8	PHENOLIC_PYROLYSIS
epo	9516	1	generic epoxy
phe1	59028	6	PHENOLIC_VIRGIN
alu	98820	9	generic aluminum

Table 3. Mesh of the axially truncated domain exported by Mechanical.

The three contact pairs are bonded: **phe0_ext-epo_int**, **epo_ext-phe1_int**, and **phe1_ext-alu_int**. The initial temperature is $T_0 = 295.15$ K. The inner face is subjected to

$$q''_{\text{in}} = h_{\text{in}}(T_g - T_s), \quad h_{\text{in}} = 1000 \text{ W m}^{-2} \text{ K}^{-1}, \quad T_g = 2504 \text{ K}. \quad (19)$$

This corresponds to 2230.85 °C in the Mechanical interface. On the outside, the model combines natural convection with $h_{\text{out}} = 8 \text{ W m}^{-2} \text{ K}^{-1}$ toward 295.15 K and gray-body radiation:

$$q''_{\text{rad}} = \varepsilon \sigma (T_s^4 - T_\infty^4), \quad \varepsilon_{\text{Al}} = 0.25. \quad (20)$$

The coefficients h_{in} and h_{out} , the gas temperature, and the emissivity are project assumptions, not outputs from a combustion calculation.

The study is a full 7 s transient thermal analysis with automatic time stepping: $\Delta t_{\text{initial}} = 0.05$ s, $\Delta t_{\text{min}} = 0.001$ s, $\Delta t_{\text{max}} = 0.05$ s. The user routine adds its own criterion, $\Delta\alpha \leq 0.05$. State-variable results are requested at every substep through `OUTRES,SVAR,ALL`. The inspected configuration launches eight DMP processes; the routine uses no mutable global variables and is therefore also suitable for a future distributed run, provided that the DLL is accessible to every process.

2.2.2 Thermal Properties and Kinetic Parameters

Table 4 reproduces the property curves actually passed to `UserMatTh`. Mechanical uses degrees Celsius in this export, whereas the table is presented in kelvins. ANSYS interpolates the properties between the tabulated points; extrapolation beyond the final point should be avoided.

T (K)	k_v (W m ⁻¹ K ⁻¹)	k_c	$c_{p,v}$ (J kg ⁻¹ K ⁻¹)	$c_{p,c}$	ρ_v (kg m ⁻³)	ρ_c
300	0.25	0.30	900	800	1250	700
600	0.32	0.35	1100	900	1200	650
900	0.36	0.40	1300	1000	1150	600
1050	0.36	0.44	1300	1250	1150	600
1200	0.36	0.49	1300	1550	1150	600
1500	0.36	0.68	1300	1950	1150	600
1700	0.36	0.81	1300	2060	1150	600
2200	0.36	1.24	1300	2085	1150	600
2750	0.36	1.73	1300	2090	1150	600

Table 4. Currently encoded virgin/char property curves for the `PHENOLIC_PYROLYSIS` material. These are project engineering curves, not yet a certified characterization of the manufactured grade.

Parameter	Current value	Status and source
A	333 s ⁻¹	Value read from <code>phenolic_pyrolysis_native.apdl</code> ; its experimental origin is not included in the project. To be recalibrated using TGA at multiple heating rates.
E_a	64.081 kJ mol ⁻¹	Same status as A ; the pair (A, E_a) must be identified jointly.
n	1	Assumption of a global first-order reaction.
ΔH_p	418 kJ kg ⁻¹	Endothermic enthalpy encoded in the project; to be replaced by a DSC measurement of the actual resin/fiber system.
R	8.314 46 J mol ⁻¹ K ⁻¹	Universal gas constant.
$\Delta\alpha_{\text{max}}$	0.05 per increment	Numerical criterion encoded in <code>usermatth.F</code> , not a physical property.

Table 5. Pyrolysis kinetics used in Simulation 1.

The virgin phenolic body `phe1` uses the virgin columns of Table 4 without conversion. The generic epoxy has $\rho = 1150$ kg m⁻³; its conductivity is 0.25 W m⁻¹ K⁻¹ and 0.30 W m⁻¹ K⁻¹ at 300 K and 600 K, respectively, and its specific heat capacity is 1000 J kg⁻¹ K⁻¹ and 1100 J kg⁻¹ K⁻¹ at the same temperatures. The generic aluminum has $\rho = 2700$ kg m⁻³, $k = 167$ W m⁻¹ K⁻¹, and $c_p = 896$ J kg⁻¹ K⁻¹. Within the project, neither material has a complete property curve extending to 2750 K; constant extrapolation is a major risk if heat reaches the outer layers. A qualified study requires the epoxy grade and aluminum alloy to be identified, followed by the addition of their temperature-dependent properties, transitions, decomposition, or melting over the temperature range actually reached.

The char trends—increasing conductivity at high temperature, mass loss, and high heat capacity—are qualitatively consistent with historical charring ablator models [7, 4]. They do not, however, justify the specific numerical values for an unidentified phenolic. NASA uses TGA to measure mass loss and char yield, DSC to determine c_p and enthalpies, and LFA to determine thermal diffusivity/conductivity [9].

2.2.3 MAPDL Code

The following MAPDL block is the file actually associated with the inner material. It creates nine TB,USER points, eleven properties at each temperature, and two state variables: `SVAR1`= α and `SVAR2`= $\dot{\alpha}$. The `matid` variable is resolved by the Mechanical command context; it must not be hard-coded without first checking the identifier produced by the export.

Complete MAPDL listing — file `phenolic_pyrolysis_native.apdl`.

```

1 ! -----
2 ! Prebuilt native Fortran UserMatTh material for inner body phe0
3 ! Solver units: m, kg, s, W, degree C
4 ! -----
5
6 /COM,Prebuilt Fortran UserMatTh pyrolysis model requested
7
8 PYRA   = 333.0
9 PYREA  = 64081.0
10 PYRN   = 1.0
11 PYRDH  = 418000.0
12 TO_K   = 273.15
13
14 ! TB,USER properties:
15 ! 1  virgin conductivity
16 ! 2  char conductivity
17 ! 3  virgin specific heat
18 ! 4  char specific heat
19 ! 5  virgin density
20 ! 6  char density
21 ! 7  Arrhenius A
22 ! 8  activation energy Ea
23 ! 9  reaction order n
24 ! 10 positive endothermic pyrolysis enthalpy
25 ! 11 Celsius-to-Kelvin offset
26
27 TB,USER,matid,9,11,THERM
28
29 TBTEMP,26.85
30 TBDATA,1,0.25,0.30,900,800,1250,700
31 TBDATA,7,PYRA,PYREA,PYRN,PYRDH,TO_K
32
33 TBTEMP,326.85
34 TBDATA,1,0.32,0.35,1100,900,1200,650
35 TBDATA,7,PYRA,PYREA,PYRN,PYRDH,TO_K
36
37 TBTEMP,626.85
38 TBDATA,1,0.36,0.40,1300,1000,1150,600
39 TBDATA,7,PYRA,PYREA,PYRN,PYRDH,TO_K
40
41 TBTEMP,776.85
42 TBDATA,1,0.36,0.44,1300,1250,1150,600
43 TBDATA,7,PYRA,PYREA,PYRN,PYRDH,TO_K
44
45 TBTEMP,926.85
46 TBDATA,1,0.36,0.49,1300,1550,1150,600
47 TBDATA,7,PYRA,PYREA,PYRN,PYRDH,TO_K
48
49 TBTEMP,1226.85
50 TBDATA,1,0.36,0.68,1300,1950,1150,600
51 TBDATA,7,PYRA,PYREA,PYRN,PYRDH,TO_K
52
53 TBTEMP,1426.85
54 TBDATA,1,0.36,0.81,1300,2060,1150,600
55 TBDATA,7,PYRA,PYREA,PYRN,PYRDH,TO_K
56
57 TBTEMP,1926.85
58 TBDATA,1,0.36,1.24,1300,2085,1150,600
59 TBDATA,7,PYRA,PYREA,PYRN,PYRDH,TO_K
60
61 TBTEMP,2476.85
62 TBDATA,1,0.36,1.73,1300,2090,1150,600
63 TBDATA,7,PYRA,PYREA,PYRN,PYRDH,TO_K
64
65 ! SVAR1 = alpha; SVAR2 = alpha rate
66 TB,STATE,matid,,2
67 TBDATA,1,0.0,0.0

```

2.2.4 Fortran UserMatTh Code

The native routine below is the one compiled into `usermatthLib.dll`. It interpolates the TB,USER properties, integrates the kinetics analytically, updates both state variables, and returns $\mathbf{q} = -k\nabla T$, $\partial u/\partial T = c_p$, the density, and the specific heat generation $-\Delta H_p \dot{\alpha}$. According to the ANSYS documentation, `hgen` is indeed a source per unit mass for purely thermal elements [1].

Complete Fortran listing — file `usermatth.F`.

```

1 *deck,usermatth                                USERDISTRIB
2   subroutine usermatth(matId, elemId, kDomIntPt, kLayer,
3   &                    kSectPt, ldstep, isubst, keycut,
4   &                    ncomp, nStatev, nProp, Time, dTime,
5   &                    Temp, dTemp, tgrad, ustatev, prop,
6   &                    coords, dudt, dudg, flux, dfdt,
7   &                    dfdg, cutFactor, hgen, dens,
8   &                    var1, var2, var3, var4, var5, var6)
9 c
10 c   Native UserMatTh model for phenolic pyrolysis.
11 c
12 c   Properties in TB,USER (SI units):
13 c       1   virgin thermal conductivity          [W/(m K)]
14 c       2   char thermal conductivity           [W/(m K)]
15 c       3   virgin specific heat                 [J/(kg K)]
16 c       4   char specific heat                  [J/(kg K)]
17 c       5   virgin density                       [kg/m3]
18 c       6   char density                        [kg/m3]
19 c       7   Arrhenius pre-exponential factor A   [1/s]
20 c       8   activation energy Ea                 [J/mol]
21 c       9   reaction order n                    [-]
22 c      10   positive endothermic enthalpy        [J/kg]
23 c      11   temperature offset                  [K]
24 c
25 c   State variables:
26 c       1   alpha, 0 = virgin and 1 = char
27 c       2   alpha rate                          [1/s]
28 c
29 c   Kinetics:
30 c       d(alpha)/dt = A exp(-Ea/(R T)) (1-alpha)**n
31 c
32 c   The equation is integrated analytically over the current time
33 c   increment. No mutable global state is used, so the routine is
34 c   suitable for shared- and distributed-memory solves.
35 c
36   implicit none
37
38   integer matId, elemId, kDomIntPt, kLayer, kSectPt
39   integer ldstep, isubst, keycut, ncomp, nStatev, nProp
40   integer i, j
41
42   double precision Time, dTime, Temp, dTemp
43   double precision tgrad(ncomp), ustatev(nStatev)
44   double precision prop(nProp), coords(3)
45   double precision dudt, dudg(ncomp), flux(ncomp)
46   double precision dfdt(ncomp), dfdg(ncomp,ncomp)
47   double precision cutFactor, hgen, dens
48   double precision var1, var2, var3, var4, var5, var6
49
50   double precision gasr, minTemp, maxDAlpha, minCut
51   parameter (gasr=8.31446261815324d0)
52   parameter (minTemp=1.0d0)
53   parameter (maxDAlpha=5.0d-2)
54   parameter (minCut=1.0d-1)
55
56   double precision kv, kc, cpv, cpc, rhov, rhoc
57   double precision apre, ea, ordern, deltaH, tempOffset
58   double precision temperatureMid, exponent, rateConstant
59   double precision alphaOld, alphaNew, alphaDot, deltaAlpha
60   double precision betaOld, betaNew, power, bracket
61   double precision conductivity, specificHeat, densityNew
62
63 c   Always initialize every output controlled by UserMatTh.
64   keycut = 0
65   cutFactor = 1.0d0
66   dudt = 1.0d0
67   do i = 1, ncomp
68     dudg(i) = 0.0d0
69     flux(i) = 0.0d0
70     dfdt(i) = 0.0d0
71     do j = 1, ncomp
72       dfdg(i,j) = 0.0d0
73     enddo
74   enddo
75
```

```

76 c      A cutback is safer than accessing an incomplete material table.
77       if (nProp .lt. 11 .or. nStatev .lt. 2) then
78         keycut = 1
79         cutFactor = minCut
80         return
81       endif
82
83       kv          = prop(1)
84       kc          = prop(2)
85       cpv         = prop(3)
86       cpc         = prop(4)
87       rhov        = prop(5)
88       rhoc        = prop(6)
89       apre        = prop(7)
90       ea          = prop(8)
91       ordern      = prop(9)
92       deltaH      = prop(10)
93       tempOffset  = prop(11)
94
95 c      Reject nonphysical values without allowing NaNs into the solve.
96       if (kv .le. 0.0d0 .or. kc .le. 0.0d0 .or.
97 &        cpv .le. 0.0d0 .or. cpc .le. 0.0d0 .or.
98 &        rhov .le. 0.0d0 .or. rhoc .le. 0.0d0 .or.
99 &        apre .lt. 0.0d0 .or. ea .lt. 0.0d0 .or.
100 &        ordern .le. 0.0d0 .or. deltaH .lt. 0.0d0) then
101         keycut = 1
102         cutFactor = minCut
103         return
104       endif
105
106       alphaOld = dmax1(0.0d0, dmin1(1.0d0, ustatev(1)))
107       temperatureMid = Temp + 0.5d0*dTemp + tempOffset
108       temperatureMid = dmax1(temperatureMid, minTemp)
109
110       exponent = -ea/(gasr*temperatureMid)
111       exponent = dmax1(-700.0d0, dmin1(700.0d0, exponent))
112       rateConstant = apre*dexp(exponent)
113
114       alphaNew = alphaOld
115       if (dTime .gt. 0.0d0 .and. rateConstant .gt. 0.0d0
116 &        .and. alphaOld .lt. 1.0d0) then
117         betaOld = dmax1(1.0d0-alphaOld, 0.0d0)
118         if (dabs(ordern-1.0d0) .le. 1.0d-10) then
119           betaNew = betaOld*dexp(-rateConstant*dTime)
120         else
121           power = 1.0d0-ordern
122           bracket = betaOld**power
123           &      - power*rateConstant*dTime
124           if (bracket .le. 0.0d0) then
125             betaNew = 0.0d0
126           else
127             betaNew = bracket**(1.0d0/power)
128           endif
129         endif
130         alphaNew = 1.0d0-betaNew
131         alphaNew = dmax1(alphaOld, dmin1(1.0d0, alphaNew))
132       endif
133
134       deltaAlpha = alphaNew-alphaOld
135       alphaDot = 0.0d0
136       if (dTime .gt. 0.0d0) alphaDot = deltaAlpha/dTime
137
138 c      Linear virgin/char mixture at the updated conversion.
139       conductivity = (1.0d0-alphaNew)*kv + alphaNew*kc
140       specificHeat = (1.0d0-alphaNew)*cpv + alphaNew*cpc
141       densityNew = (1.0d0-alphaNew)*rhov + alphaNew*rhoc
142
143       dudt = specificHeat
144       dens = densityNew
145       do i = 1, ncomp
146         flux(i) = -conductivity*tgrad(i)
147         dfdg(i,i) = -conductivity
148       enddo
149
150       ustatev(1) = alphaNew
151       ustatev(2) = alphaDot
152
153 c      For pure thermal elements hgen is heat generation per unit mass.
154 c      Positive deltaH is endothermic, hence the minus sign.
155       hgen = hgen-deltaH*alphaDot
156
157 c      Limit conversion to five percent per accepted increment.
158       if (deltaAlpha .gt. maxDAlpha) then
159         keycut = 1
160         cutFactor = maxDAlpha/dmax1(deltaAlpha, 1.0d-30)

```

```

161         cutFactor = dmax1(minCut, dmin1(0.95d0, cutFactor))
162     endif
163
164     return
165 end

```

The Windows x64 build uses Visual Studio 2022 C++ and Intel oneAPI Classic Fortran 2023.1. The `build_usermatth_x64.cmd` script compiles with `/O2 /MD`, links the ANSYS v261 customization libraries, and verifies that the `USERMATTH` symbol is exported. This toolchain must remain aligned with the solver version.

2.2.5 Step-by-Step Simulation Preparation

- 1. Identify the physical materials.** Record the manufacturer, grade, reinforcement fraction and orientation of the phenolic, the epoxy system, and the aluminum alloy. In the absence of this information, retain an explicit “preliminary data” designation.
- 2. Characterize the phenolic.** Perform TGA in an inert atmosphere at several heating rates to obtain $\rho(T)$, the char yield, and the kinetics; use DSC for $c_p(T)$ and ΔH_p , LFA for $k(T)$, and then measure the apparent density of the char. First fit A, E_a, n against all TGA curves and validate against a heating rate not used in the fit. A multiple-reaction kinetic model is preferable if a single law cannot reproduce the peaks.
- 3. Complete Engineering Data.** Enter the virgin and char tables up to at least the maximum gas temperature, with explicit units. Add the epoxy and aluminum curves over the temperature range actually reached. Do not blindly extrapolate a polymer to 2750 K.
- 4. Assign the bodies.** In Mechanical, verify `phe0=PHENOLIC_PYROLYSIS`, `phe1=PHENOLIC_VIRGIN`, `epo=epoxy`, and `alu=aluminum`. Check the assignment in the `ds.dat` export, not solely from the interface color.
- 5. Prepare named selections.** Retain the four bodies, the three interface pairs, the hot inner face, and the outer face. Stable names prevent MAPDL commands from being attached to a fragile geometric selection.
- 6. Define the contacts.** For this simulation, use bonded thermal contacts and verify that each pair is closed. If an adhesive is meshed as a volume, do not also add a contact resistance that would count the same effect twice.
- 7. Mesh and test mesh independence.** Retain at least eight layers through `phe0` for the reference calculation, then compare the wall temperature and the $\alpha = 0.5$ depth against a finer radial mesh. Mesh independence must be assessed using these observables, not only the maximum temperature.
- 8. Build the DLL.** From a properly initialized x64 command prompt, run `build_usermatth_x64.cmd`; check the return code, `compile.log`, `link.log`, and the `USERMATTH` export. Copy the DLL to the solver directory, or otherwise make it accessible there, before starting the run.
- 9. Insert the MAPDL block.** Under the thermal-analysis branch, insert a command object that applies the contents of Section 2.2.3 to the `phe0` material. After generating the solver input, verify the presence of `TB,USER`, `TB,STATE`, and nine `TBTEMP` entries.
- 10. Define the loading.** Prescribe 295.15 K initially, the hot convection of Equation (19), and then the outer convection and radiation. Ultimately, replace $T_g(t)$ and $h(t)$ with profiles from a test or a chamber calculation. Also vary h over at least 500 to 2000 W m⁻² K⁻¹ to quantify its influence.
- 11. Set time stepping and convergence controls.** Use automatic time stepping between 0.001 s and 0.05 s, retain the $\Delta\alpha \leq 0.05$ limit, and save `SVAR`. A single 7 s step would eliminate resolution of the front and would not be physically acceptable, even though the local law is integrated analytically.
- 12. Verify solver startup.** In the solver output, confirm that the user library is loaded, that the requested number of processes is used, that no `UserMatTh` error occurs, and that the state variables are present. First run a coupon or a very small sector for 0.1 s.
- 13. Validate using conservation balances.** For every result set, check $0 \leq \alpha \leq 1$, the monotonicity of α in time, the heat balance, and the integrated volatile mass obtained from Equation (8). Finally, compare a case without pyrolysis and a simplified adiabatic case against an analytical conduction solution.

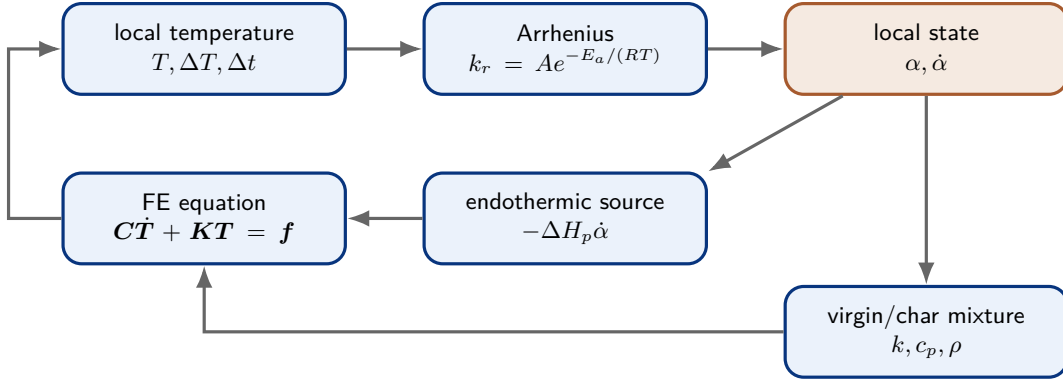


Figure 2. Local coupling in Simulation 1. Conversion modifies both the heat source and the properties at the following substep.

2.3 Simulation 1 Results

2.3.1 Data Scope and Numerical Convergence

The analyzed results come from the eight DMP partitions `file0.rth-file7.rth`, the `file.nlh` history, and the `solve.out` output [12]. The last saved and readable state is set 140 at

$$t = 6.385\,616\,94\,\text{s}.$$

The requested solution was intended to reach 7 s; the values below therefore describe a converged intermediate state rather than the final seven-second result. Any linear extrapolation to 7 s is not a substitute for the missing 0.614 s of computation.

At this time, the solver has accepted 140 substeps and accumulated 293 equilibrium iterations. The last substep is 0.05 s, converges in two iterations, and ends with a heat-flow norm of 0.01694, well below the 0.6255 criterion. The reported wall time is approximately 90 883 seconds, or 25.2 h, on eight DMP processes. These indicators show good *numerical* convergence of the saved state; they are neither a validation of the material properties nor evidence of mesh independence.

2.3.2 Temperature Field

Table 6 collects the robust extrema obtained by scanning the partitions. Interface nodes can be duplicated by contact elements; partition-wise nodal averages are therefore not used as volume averages.

Observable at $t = 6.3856\,\text{s}$	Temperature ($^{\circ}\text{C}$)	Temperature (K)
Hot inner face, nodal range	1754.06–1755.39	2027.21–2028.54
Maximum in <code>phe0</code>	1755.39	2028.54
Maximum in the epoxy	453.41	726.56
Maximum in <code>phe1</code>	208.05	481.20
Maximum in the aluminum	22.0012	295.1512
Maximum on the outer aluminum face	22.000005	295.150005

Table 6. Temperatures extracted from the last converged state.

The hot face is nearly isothermal and reaches 1755.39 $^{\circ}\text{C}$, or 2028.54 K. It remains approximately 475.5 K below the imposed gas temperature. The prescribed convection therefore corresponds at this instant to an inward heat flux of only $0.475 - -0.477\,\text{MW m}^{-2}$, compared with approximately $2.21\,\text{MW m}^{-2}$ immediately after the hot condition is applied as a step. This flux is a direct consequence of h_{in} and T_g , not an independent prediction of combustion.

The most concerning design point is not yet the aluminum, which remains essentially at its initial temperature, but the epoxy: its maximum of 453.41 $^{\circ}\text{C}$ is 726.56 K, beyond the final material property point currently defined at 600 K. Its temperature is therefore computed using constant extrapolation of a generic material, while decomposition and loss of adhesion are not represented. The maximum in `phe1`, 208.05 $^{\circ}\text{C}$, shows that the thermal wave has crossed the epoxy but has not traversed the 6.35 mm second phenolic layer. The nearly ambient aluminum temperature must not be extrapolated to the head-end, nozzle, or attachment regions absent from the 50 mm slice, nor to the heat-soak phase after motor shutdown.

2.3.3 Pyrolysis Conversion SVAR1

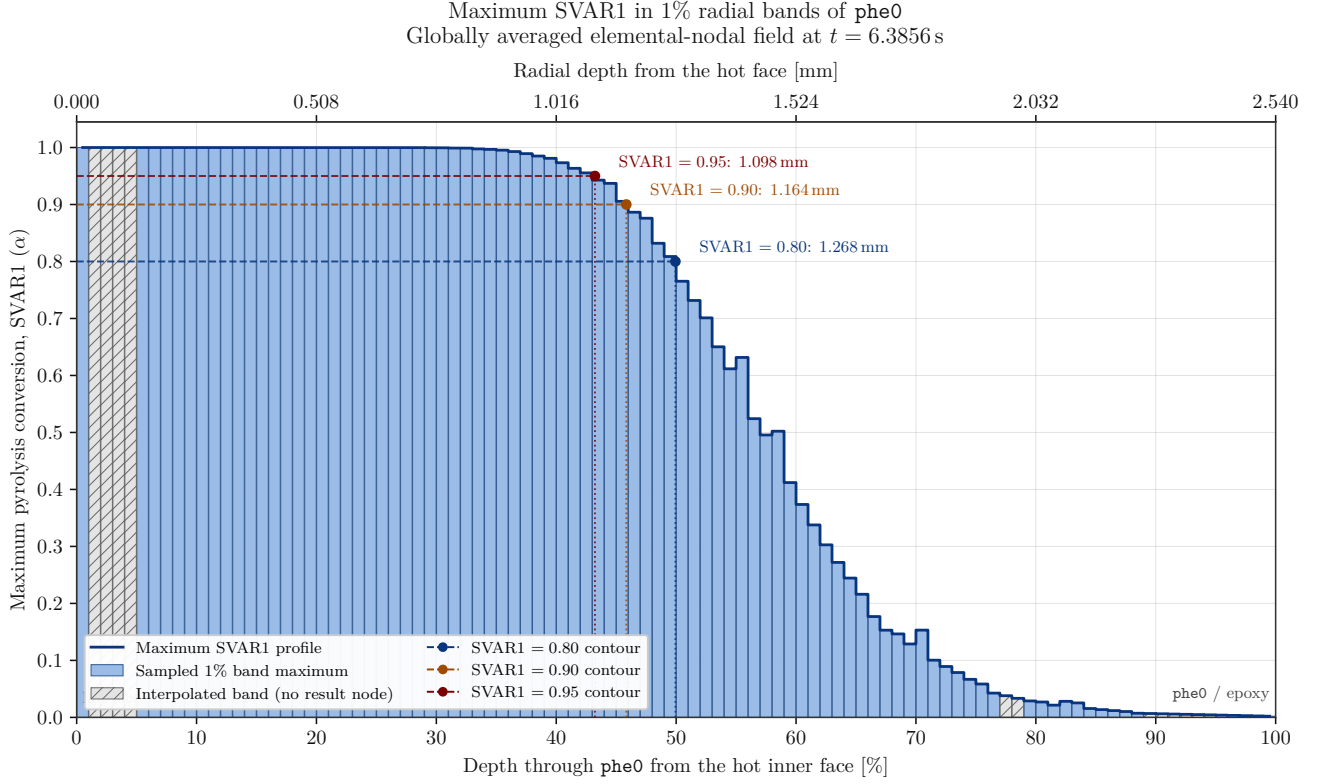


Figure 3. Maximum SVAR1 in one-percent radial bands of phe0 at the last converged state. Hatched bands contain no result node and are filled by linear interpolation.

Figure 3 shows the maximum radial envelope of the globally averaged elemental-nodal field. The global maximum reaches $\alpha = 1$: the zone near the hot face is fully converted according to the kinetic law. This does not mean that the char has been removed or that a void has been created.

The isoconversion depths are given in Table 7. The region with at least 95% conversion reaches 1.098 mm, or 43.2% of the phe0 thickness; the 80% level reaches almost exactly half of the layer.

Threshold α_c	Depth d_{α_c} (mm)	Fraction of phe0	Apparent speed d_{α_c}/t (mm s^{-1})
0.80	1.26845	49.94%	0.19864
0.90	1.16440	45.84%	0.18235
0.95	1.09800	43.23%	0.17195

Table 7. Depth and apparent mean speed of the conversion fronts.

The speeds in the last column are only the ratios d_{α_c}/t . They assume that the contour starts at the hot face at $t = 0$ and provide a mean penetration speed since ignition. They are not instantaneous front speeds. A rigorous front speed in mm s^{-1} must be calculated by differencing the positions of the same contour at several saved times.

One band in the figure is $25.4 \mu\text{m}$ wide, whereas the mean radial thickness of one phe0 element is 0.318 mm . The 100 bars improve profile readability and integration, but do not create a physical resolution of 100 cells. Sixteen bands without a node had to be interpolated; the front-location uncertainty remains on the order of a fraction of an element and must be measured through mesh refinement.

2.3.4 Time Evolution of Conversion

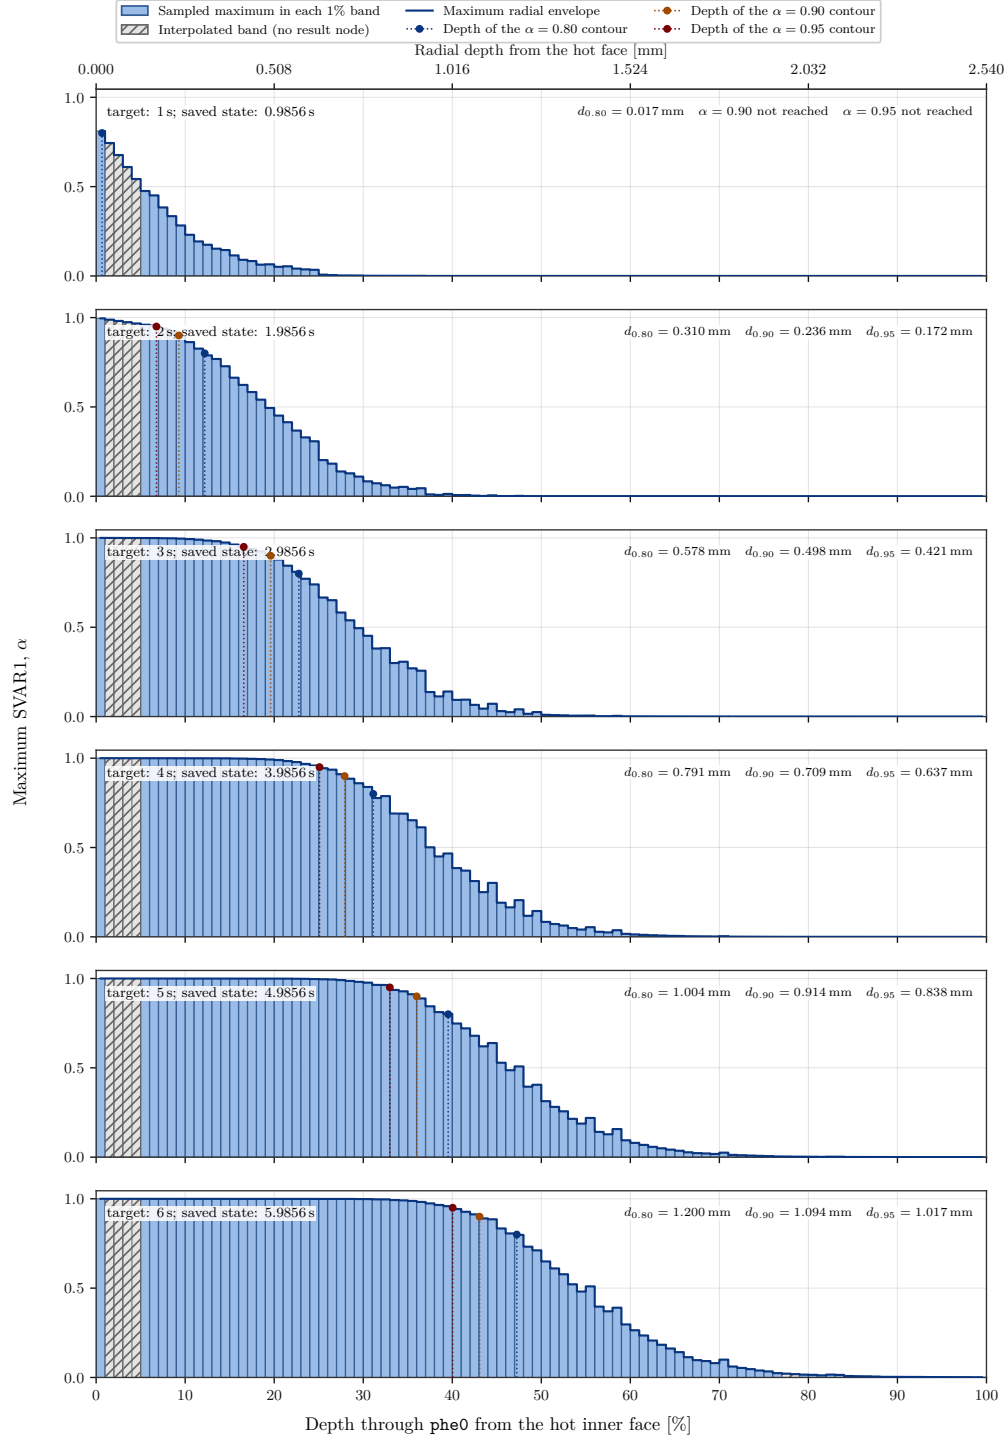


Figure 4. Evolution of the maximum radial SVAR1 in phe0 for the saved states closest to 1 through 6 s. The six plots are stacked vertically and use identical axes. The dotted lines and points mark the depths of the 0.80, 0.90, and 0.95 isoconversion levels when they are reached.

Figure 4 complements, without replacing, the last-converged-state profile in Figure 3. It applies exactly the same elemental-nodal averaging and the same one-percent radial bands to the six saved states closest to $t = 1, \dots, 6$ s. The available outputs precede each integer second by 0.014383 s; the time actually read is shown in every panel so that a temporal interpolation is not presented as an ANSYS result.

Table 8 collects the values used in the annotations. At 0.9856 s, the maximum value is still only $\alpha = 0.811$, and the 0.80 contour barely enters the layer: the 0.90 and 0.95 levels have not yet been reached. This is a thermal initiation phase, not an already established front.

Target time (s)	Saved time (s)	$\alpha_{\max}$	$d_{0.80}$ (mm)	$d_{0.90}$ (mm)	$d_{0.95}$ (mm)
1	0.9856	0.81114	0.01691	—	—
2	1.9856	0.99560	0.30979	0.23605	0.17200
3	2.9856	0.99997	0.57818	0.49786	0.42106
4	3.9856	1.00000	0.79069	0.70892	0.63735
5	4.9856	1.00000	1.00433	0.91446	0.83788
6	5.9856	1.00000	1.20013	1.09392	1.01716

Table 8. Time progression of the isoconversion depths computed from the maximum radial envelope.

Between the states near 1 and 2 s, the 0.80 contour advances at an incremental mean speed of 0.293 mm s^{-1} . This speed subsequently falls to 0.268 mm s^{-1} , then approximately 0.213 mm s^{-1} , 0.214 mm s^{-1} , and 0.196 mm s^{-1} over the successive intervals. Once it has appeared, the 0.95 contour slows in a similar manner, from 0.249 mm s^{-1} between 2 and 3 s to 0.179 mm s^{-1} between 5 and 6 s. The general trend is therefore a slowing front, with a small non-monotonic variation consistent with the substeps, nodal smoothing, and radial mesh resolution.

The profiles also show that there is no infinitely thin pyrolysis interface: a broad transition zone separates the almost fully converted char from material that is still virgin. Near 6 s, the 0.95 contour is at 1.017 mm, the 0.80 contour is at 1.200 mm, and measurable conversion extends substantially farther. At the last available state, 6.3856 s, these depths reach 1.098 mm and 1.268 mm, respectively, extending the trend of the six panels without a discontinuity.

For design, a single d/t speed therefore hides both the initiation delay and the subsequent slowing. Any extrapolation to the end of firing must state the chosen conversion threshold and use at least a recent incremental speed, rather than conflating conversion, char depth, and geometric recession. Finally, because every curve is a maximum radial envelope, it remains conservative for reconstructed conversion but represents neither a volume average nor a directly measured ablation depth.

2.3.5 Local Pyrolysis Rate SVAR2

SVAR2 is a local conversion rate in s^{-1} , distinct from the geometric speed in Table 7. The global maximum over the partitions containing `phe0` is

$$\dot{\alpha}_{\max} = 0.326660 \text{ s}^{-1}.$$

It occurs 1.44221 mm from the hot face, or 56.78% through the thickness, where $\alpha = 0.54721$ and $T = 956.67^\circ\text{C} = 1229.82 \text{ K}$. This position is physically consistent: near the surface, the $1 - \alpha$ factor is almost zero because the material is already converted; farther into the material, the temperature is too low to activate the Arrhenius law rapidly. The maximum rate therefore lies in the transition zone.

Over the last 0.05 s substep, this maximum corresponds to $\Delta\alpha \simeq 0.01633$, well below the numerical limit of 0.05. The `UserMatTh` criterion therefore does not force an additional reduction of the last increment. At this point,

$$k_r = \frac{\dot{\alpha}}{1 - \alpha} = 0.7214 \text{ s}^{-1}, \quad \tau_r = k_r^{-1} = 1.386 \text{ s}.$$

If the temperature were held artificially constant, it would take approximately 3.05 s to progress from $\alpha = 0.547$ to $\alpha = 0.95$. The local temperature is still changing in reality, so this characteristic time is not an extrapolation to the end of the firing.

With $\rho_v - \rho_c \simeq 550 \text{ kg m}^{-3}$ at this temperature, the maximum local source suggested for Simulation 2 would be

$$\dot{\omega}_{g,\max}''' \simeq (\rho_v - \rho_c)\dot{\alpha}_{\max} = 180 \text{ kg m}^{-3} \text{ s}^{-1}.$$

The mass-specific thermal sink already applied by Simulation 1 is locally $-\Delta H_p \dot{\alpha} \simeq -136.5 \text{ kW kg}^{-1}$. Gas generation is therefore potentially significant, but its transport, pressure, and heat exchange are not solved in the current model.

2.3.6 Time Evolution of the Local Rate

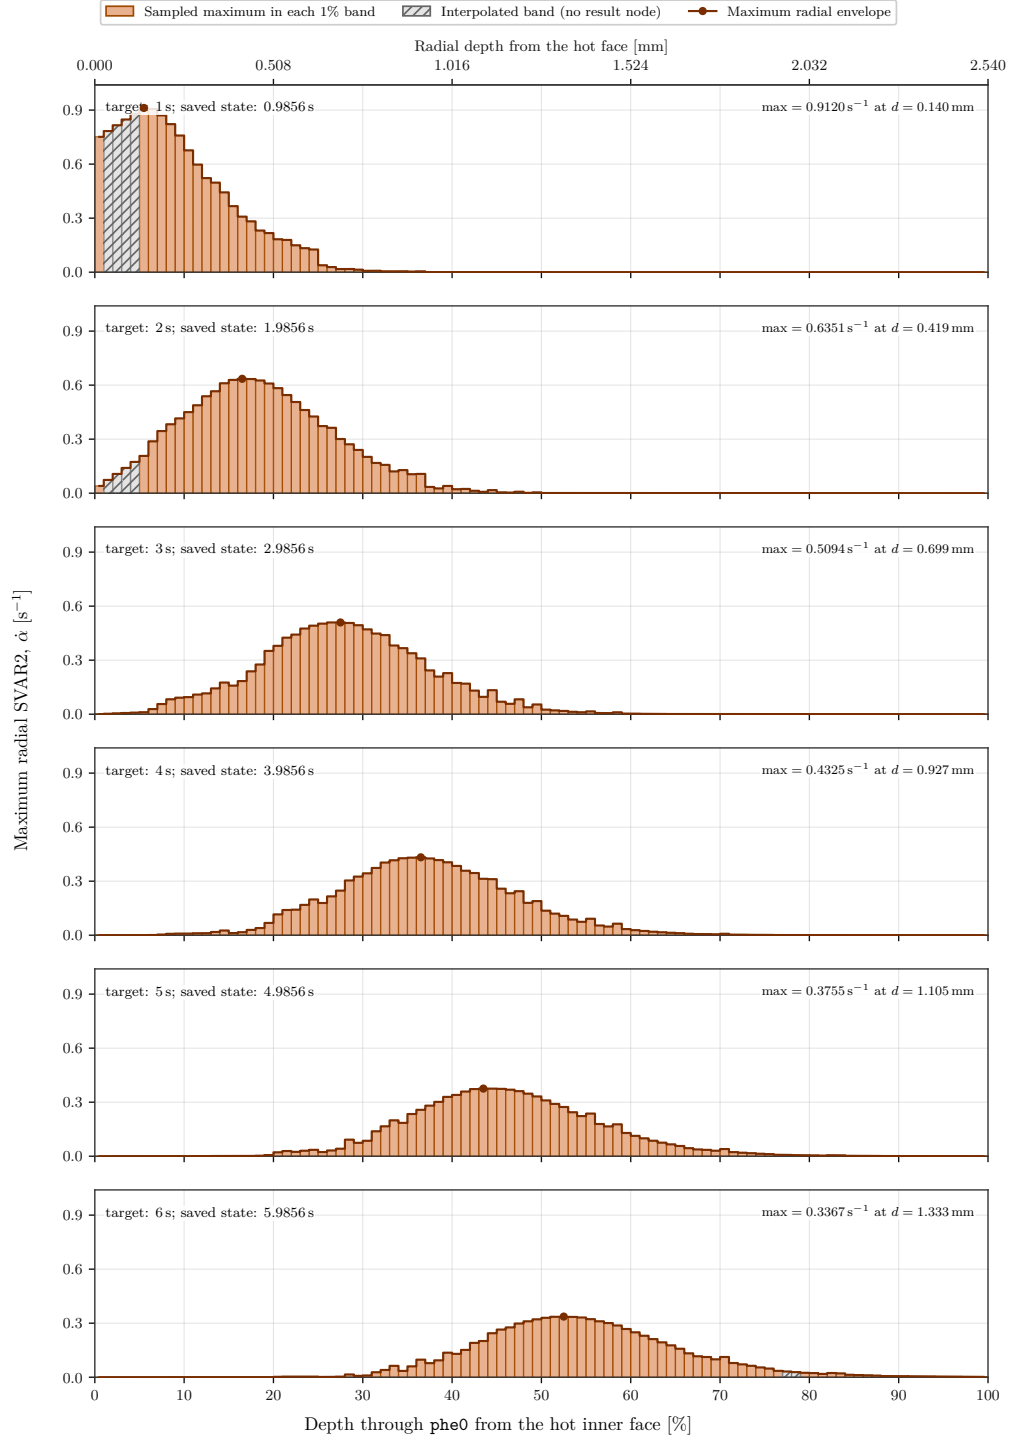


Figure 5. Evolution of the maximum radial SVAR2 in phe0, for the saved states nearest 1 to 6 s. Every panel uses the same vertical scale; hatched bands contain no result node and are linearly interpolated.

Figure 5 applies to **SVAR2** the same time study as Figure 4. Table 9 shows both the decrease of the maximum rate and its motion inwards. Between the states near 1 and 6 s, the maximum drops from 0.9120 s^{-1} to 0.3367 s^{-1} , a 63.1% decrease, while its depth increases from 0.140 mm to 1.333 mm.

Target time (s)	Saved time (s)	$\dot{\alpha}_{\max}$ (s^{-1})	Depth of maximum (mm)
1	0.9856	0.9120	0.140
2	1.9856	0.6351	0.419
3	2.9856	0.5094	0.699
4	3.9856	0.4325	0.927
5	4.9856	0.3755	1.105
6	5.9856	0.3367	1.333

Table 9. Time migration of the maximum radial pyrolysis rate.

The trajectory is not a geometric recession. It identifies the location where the product of the Arrhenius factor and the remaining virgin fraction is largest. The hot face saturates rapidly, so $1 - \alpha$ becomes nearly zero there; the maximum of $\dot{\alpha}$ then moves towards deeper material that is still partly virgin but sufficiently hot. The decrease of the maximum reflects thermal attenuation with depth, not the cessation of pyrolysis. It also explains why the gas source in Simulation 2 must be volumetric and mobile: using only the surface rate would strongly underestimate production in the transition zone after the first seconds.

2.3.7 Axial Dependence on the Hot Inner Surface

The axial coordinate is measured from the lower plane of the meshed slice, $y = 0.9144\text{ m}$, over its 50 mm length. In every one-percent axial band, the following figures retain the maximum over nodes on the hot inner surface of **phe0**. This restriction avoids replacing a band with no surface node by a cold node located deeper in the material. Values are obtained with DPF's native elemental-nodal averaging and then by merging duplicate global nodes at DMP boundaries. Eighty-three of the 100 bands are sampled directly; the other 17 are clearly hatched and interpolated between their neighbours.

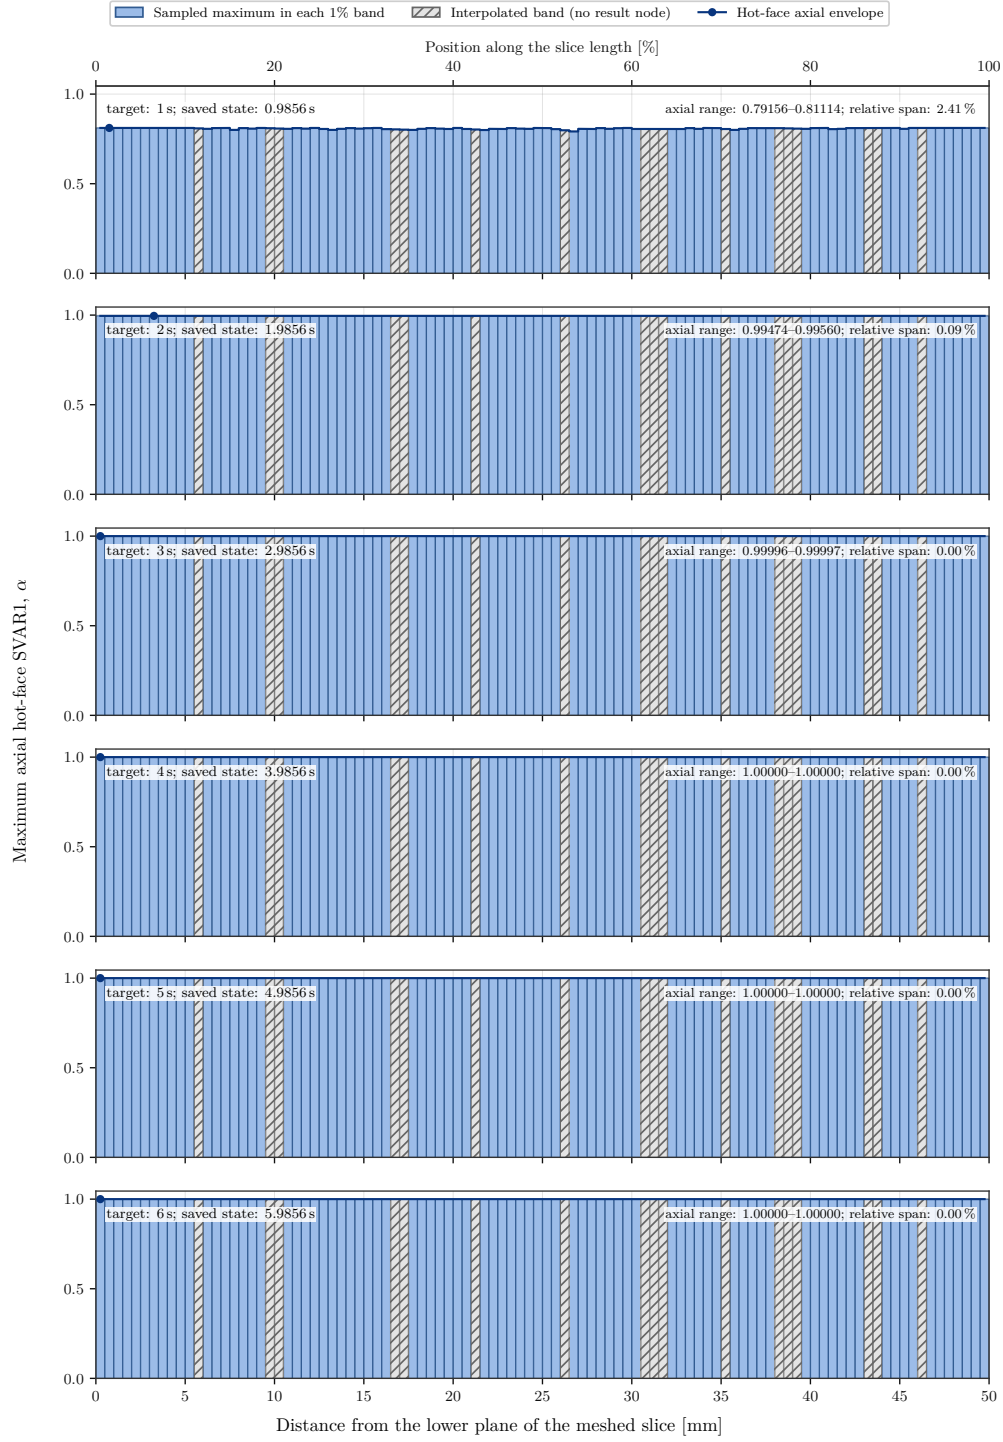


Figure 6. Axial dependence of SVAR1 on the hot inner surface of phe0, measured from the lower plane of the meshed slice. All six panels use the same $0 \leq \alpha \leq 1$ scale.

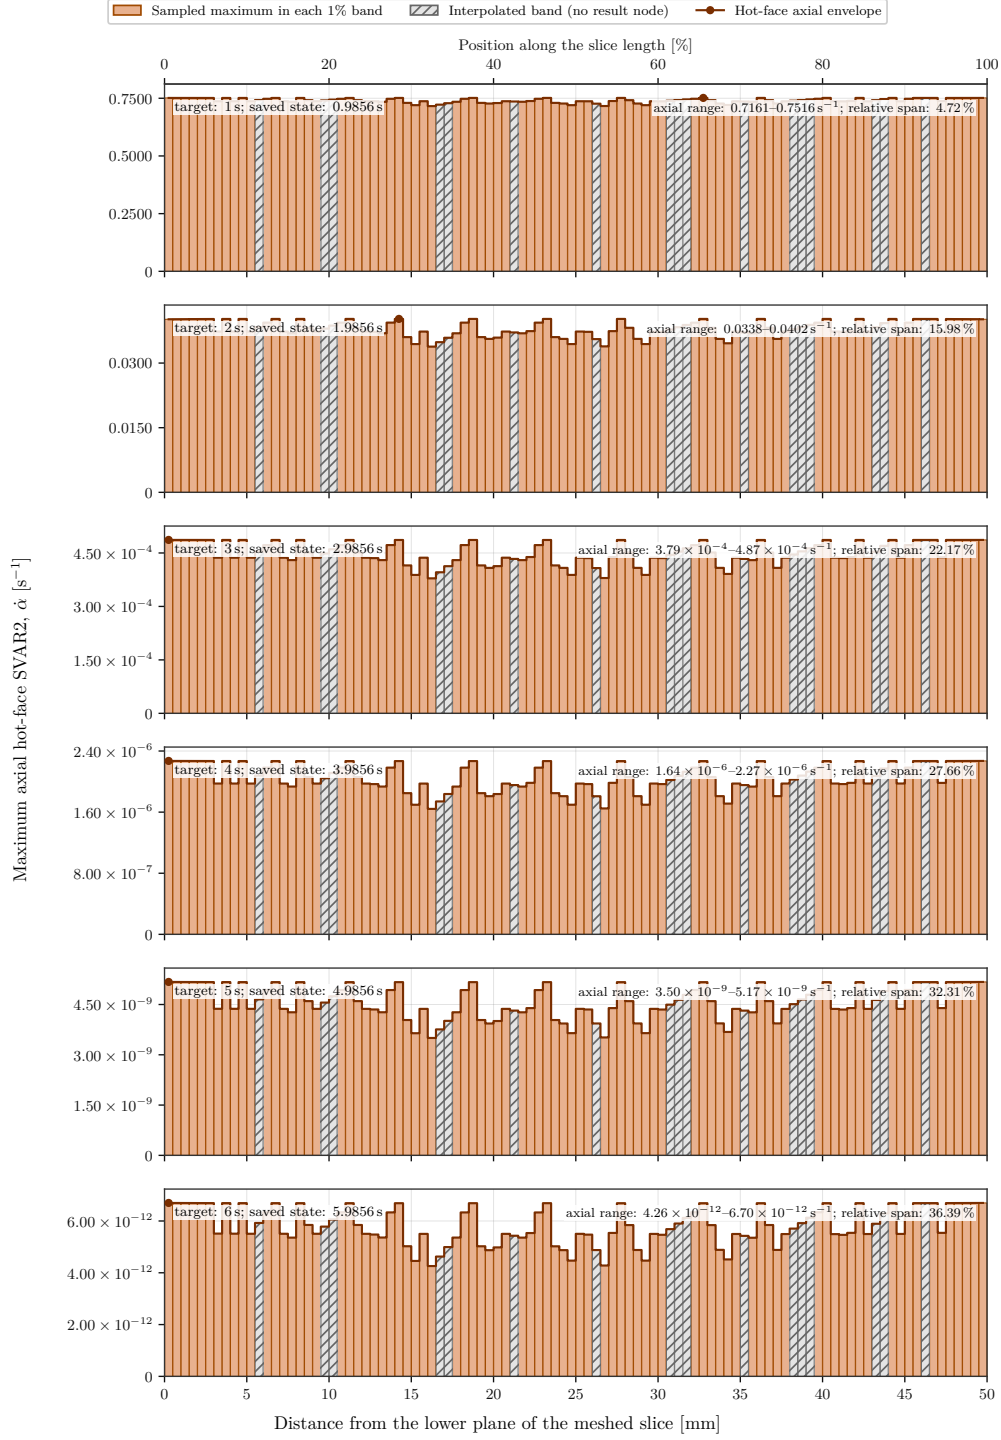


Figure 7. Axial dependence of SVAR2 on the hot inner surface of phe0. The vertical scale is independent in every panel so that the small late rates remain visible; absolute values, not relative bar heights between panels, must be compared.

Figure 6 shows nearly uniform surface conversion. At 0.9856 s, α ranges from 0.79156 to 0.81114, a 2.41% relative span. At 1.9856 s, the range narrows to 0.99474–0.99560; at 2.9856 s, it is 0.999959–0.999968. The hot face is numerically fully converted from the state near 4 s. This means “char fully formed” according to the state variable, not “material removed”.

Figure 7 provides the complementary information. The hot-face rate is still $0.7161 - -0.7516 \text{ s}^{-1}$ near 1 s, but drops to $0.03382 - -0.04025 \text{ s}^{-1}$ near 2 s, then to $3.79 \times 10^{-4} - -4.87 \times 10^{-4} \text{ s}^{-1}$ near 3 s. It falls below $2.3 \times 10^{-6} \text{ s}^{-1}$ near 4 s and is practically zero afterwards. This sharp drop is the expected consequence of the $1 - \alpha$ factor: the surface has almost no virgin material left to convert, while Figure 5 confirms that the volumetric front remains active deeper in the material.

The relative axial span of **SVAR2** increases from 4.72% at 1 s to 36.39% at 6 s, but this increase is misleading if read alone: the denominator has fallen by about eleven orders of magnitude. Late variations are therefore negligible in absolute value and mostly reflect mesh, nodal smoothing, and numerical saturation. Under the uniform boundary conditions of this central slice, both figures validate the assumption of a nearly axially-uniform response. They support the future use of a much cheaper axisymmetric model for the central region, but say nothing about the ends, the nozzle, joints, or real combustion-flux variations.

2.3.8 Bracket on Conversion and Potential Outgassing

Two simple reconstructions provide an order-of-magnitude bracket without claiming a statistical uncertainty. The lower reconstruction sets $\alpha = 0.95$ between the hot face and the contour at 1.098 mm, then $\alpha = 0$ beyond it. Accounting for cylindrical geometry gives $\bar{\alpha}_{\text{low}} = 0.408$. Integration of the maximum envelope of the 100 bands gives $\bar{\alpha}_{\text{high}} = 0.581$. Table 10 then uses the nominal gas yield $Y_g = 0.47$.

Reconstruction	$\bar{\alpha}$	Equivalent converted thickness	Potential gas
Lower: 95% step front	0.408	1.04 mm	0.943 kg full motor; 25.8 g slice
Upper: maximum radial envelope	0.581	1.48 mm	1.340 kg full motor; 36.6 g slice

Table 10. Engineering bracket on conversion and potential gas mass at $t = 6.3856 \text{ s}$.

These values assume that the profile is representative over the full circumference and length, then use the complete **phe0** mass of 4.911 kg. In the meshed model, the length is only 50 mm and the corresponding initial mass is approximately 0.134 kg. The upper reconstruction uses radial maxima and is intentionally conservative for an average. The lower reconstruction is not a mathematical bound on the 3D solution because the figure does not contain circumferential and axial minima. Finally, “potential gas mass” is the mass that would be released according to the density law; the solver does not demonstrate that this mass has actually left the solid.

2.3.9 Physical and Motor-Design Consequences

- 1. Inner-liner margin.** A thickness of approximately 1.10–1.27 mm is already 80–95% converted, and the maximum **SVAR2** lies at 1.44 mm. The front remains active and is advancing toward the epoxy. The difference $2.54 - d_{\alpha_c}$ cannot be treated directly as an ablation margin, but it shows that the first layer is heavily loaded before the intended end of the firing.
- 2. Critical epoxy condition.** The model predicts 453°C in an epoxy layer that is nevertheless assumed inert and bonded. This value lies beyond the range of its thermal-property table. The model therefore cannot establish that either the **phe0-epo** or **epo-phe1** bond survives. Characterization of the epoxy, a thicker thermal barrier, or a high-temperature adhesive must be considered before the bond can be treated as safe.
- 3. Aluminum protected only over the short term.** The ideal central slice keeps the aluminum near 22°C at 6.39 s. This is favorable, but does not cover delayed heating after shutdown, thermal bridges, or nozzle and end regions. A transient cooldown phase must be added to search for the delayed maximum aluminum temperature.
- 4. Non-negligible outgassing.** The **SVAR2** value implies a high local gas source. Without porous transport, the simulation cannot predict internal char pressure, blowing cooling, or gas-assisted delamination risk. These phenomena directly motivate Simulation 2.
- 5. Front resolution.** Eight elements over 2.54 mm provide only three to four element layers across the main transition zone. Runs with 16 and then 24 radial layers should compare $d_{0.8}$, $d_{0.95}$, $\dot{\alpha}_{\text{max}}$, and the epoxy temperature.

6. Central-slice limitation. The 50 mm mesh represents a uniform mid-length region, but not end-region flux concentrations or conduction paths. The masses in Table 10 can be scaled to the full motor only if axial uniformity is verified.

2.3.10 Comparison with Reality and Direction of the Bounds

There is currently no TGA/DSC/LFA curve for the phenolic actually manufactured, no thermocouple record from a motor firing, and no post-fire measurement of mass, char depth, or recession. It would therefore be incorrect to claim quantitative agreement with reality. The available comparison concerns the mechanisms: NASA-verified charring-ablator models include conduction, decomposition, pyrolysis-gas flow, gas-solid heat exchange, thermochemical erosion, and surface motion [4, 5, 6]. Simulation 1 represents only conduction, local kinetics, virgin/char properties, and the endothermic sink.

Assumption or omission	Missing physical effect	Likely bias
Constant T_g and h_{in} from $t = 0$	No ignition ramp or pressure decay	High tendency if the real firing has ramps; unknown direction if the actual flux or particulate radiation is higher.
No mobile pyrolysis gas	No wall blowing, advected enthalpy, or pore pressure	Often a high tendency for net penetrating heat flux, but not a one-sided bound for internal temperature.
No oxidation, erosion, or particles	No thermochemical or mechanical char consumption	Lower bound for recession and geometric mass loss.
Char retained and no elements removed	The surface never recedes	Exactly zero computed recession: a model-imposed lower bound.
Perfectly bonded contacts	No gap, delamination, or evolving resistance	High tendency for ideal heat transmission, but an overly optimistic view of adhesive integrity.
Uncalibrated properties and kinetics	Unknown grade, fibers, char yield, and multiple reactions	No defensible bias direction; this uncertainty can dominate all others.
Maximum radial profile	Envelope rather than volume average	Engineering upper bound for reconstructed mean conversion.

Table 11. Expected direction of the main biases relative to a real firing.

For *geometric recession*, the lower bound of the current model is therefore 0 mm. A simple upper bound assumes that the entire equivalent converted thickness, approximately 1.0–1.5 mm, is also stripped away; it is intentionally severe because 52–56% of the condensed mass remains as char according to the current tables. Reality may lie between these values if the char remains partly attached, but strong oxidation or mechanical erosion can invalidate this bracket. Only an instrumented firing and post-fire measurement can close it.

The validation priorities are therefore to: (i) characterize the actual phenolic and epoxy by TGA, DSC, and LFA, methods explicitly used by NASA for residual mass, heat capacity, and thermal diffusivity measurements [9]; (ii) measure $T_g(t)$, pressure, and temperatures at the interfaces and on the aluminum during a firing; (iii) measure mass, residual thickness, and char depth after the firing; (iv) extend the computation to 7 s and then through cooldown; and (v) perform sensitivity studies on h_{in} , A , E_a , ΔH_p , char properties, contacts, time step, and mesh.

3 Simulation 2: Outgassing and Element Deactivation in Mechanical

3.1 Proposed Theory and Derivation

3.1.1 Solid Mass Balance and Gas Generation

Simulation 2 retains the kinetics used in Simulation 1, but distinguishes the solid residue from the gaseous products. Over an initial volume, the loss of condensed-phase mass is the gas source:

$$\frac{\partial \rho_s}{\partial t} = -\dot{\omega}_g''', \quad \dot{\omega}_g''' = (\rho_v - \rho_c)\dot{\alpha}. \quad (21)$$

The final gas yield of the single-reaction model is therefore

$$Y_g = \frac{\rho_v - \rho_c}{\rho_v} = 1 - \frac{\rho_c}{\rho_v}. \quad (22)$$

With the current tables, Y_g ranges from 0.44 to 0.48. A nominal value of $Y_g = 0.47$ is consistent with the model, but must be confirmed using the residual mass measured by TGA.

In a complete porous-ablator model, conservation of gas mass is written as

$$\frac{\partial(\phi \rho_g)}{\partial t} + \nabla \cdot (\rho_g \mathbf{u}_g) = \dot{\omega}_g''', \quad (23)$$

where ϕ is the porosity and $\mathbf{u}_g$ is the superficial velocity. For slow flow through the char, Darcy's law and the ideal-gas law give

$$\mathbf{u}_g = -\frac{K(\alpha, T)}{\mu_g} \nabla p_g, \quad \rho_g = \frac{p_g M_g}{RT_g}. \quad (24)$$

Ablative-material response codes such as CHAR solve coupled forms of these mass and energy balances [5, 6, 4]. A standard thermal element in Mechanical, however, has no pressure degree of freedom. Consequently, **UserMatTh** cannot solve Equation (23) by itself. Remaining within Mechanical therefore requires either a substantially more complex user-defined multiphysics element or a reduced-order model.

3.1.2 Reduced Radial Closure Compatible with Mechanical

The proposed model assumes that the gases generated in **phe0** escape rapidly toward the hot wall and that their accumulation is negligible. In cylindrical axisymmetry, the gas mass flux reaching the surface at radius r_s is then obtained directly by integrating the source:

$$\dot{m}_g''(r_s) = \frac{1}{r_s} \int_{r_s}^{R_0} \dot{\omega}_g'''(r) r \, dr, \quad (25)$$

where R_0 is the outer boundary of **phe0**. This expression follows from the balance $2\pi r_s L \dot{m}_g'' = \int_{r_s}^{R_0} 2\pi r L \dot{\omega}_g''' \, dr$. It conserves total gas mass even when pressure is not solved explicitly.

The gas carries sensible enthalpy. A minimal local closure adds the following term to the solid energy equation:

$$\dot{q}_{m,g} = -\frac{\dot{\omega}_g'''}{\rho_s} c_{p,g} (T - T_{\text{ref}}). \quad (26)$$

This term must be used only if ΔH_p does not already include this enthalpy; otherwise it would be counted twice. A more faithful formulation adds $-\nabla \cdot (\dot{m}_g'' h_g)$ to the energy balance, as is done in material-response models [4, 5].

3.1.3 Reduction of Convective Heat Flux by Blowing

Outgassing into the chamber produces a blowing flow that opposes heat transfer. For a steady, planar gas film with constant properties, the source-free energy equation is

$$\dot{m}_g'' c_{p,g} \frac{dT}{dy} = k_g \frac{d^2 T}{dy^2}. \quad (27)$$

Integrating between the wall and the outer edge of the film, and expressing the film thickness in terms of the no-blowing coefficient $h_0 = k_g/\delta$, gives the classical correction in the form

$$B_h = \frac{\dot{m}_g'' c_{p,g}}{h_0}, \quad F(B_h) = \frac{B_h}{\exp(B_h) - 1}, \quad (28)$$

$$q''_{\text{conv}} = h_0 F(B_h)(T_g - T_s). \quad (29)$$

Because $F(0) = 1$ and $F(B_h) < 1$ for $B_h > 0$, the model recovers the current convection condition in the absence of outgassing and progressively reduces the heat flux as gas production increases. This law is an engineering closure; it does not replace a boundary-layer calculation and must be calibrated against chamber pressure, propellant composition, and test data.

3.1.4 Surface Balance, Recession, and Element-Deactivation Criterion

Pyrolysis produces char; it does not automatically remove that char. Recession requires a second mechanism—oxidation, sublimation, or mechanical erosion—and a surface energy balance:

$$q''_{\text{conv}} + q''_{\text{rad}} = q''_{\text{cond}} + \dot{m}_g'' \Delta h_g + \dot{m}_{\text{abl}}'' H_{\text{eff}}. \quad (30)$$

In the absence of sufficient chemical data, the following bounded, energy-controlled law is proposed:

$$\dot{m}_{\text{abl}}'' = \max \left[0, \frac{q''_{\text{conv}} + q''_{\text{rad}} - q''_{\text{cond}} - \dot{m}_g'' \Delta h_g}{H_{\text{eff}}} \right], \quad \dot{s} = \frac{\dot{m}_{\text{abl}}''}{\rho_c}. \quad (31)$$

The recession depth is $s(t) = \int_0^t \dot{s} dt$. The **phe0** elements are arranged in radial bands; a band is deactivated only when s exceeds its cumulative thickness. The criterion is therefore the integrated recession, possibly combined with $\alpha \geq 0.99$, but never $\alpha = 1$ alone.

In MAPDL, **EKILL** multiplies an element's contribution by a near-zero factor; the element remains in the mesh. A deactivated thermal element no longer contributes heat capacity or applied loads, and its state variables are reset when it is killed [2, 3]. Any residual mass and energy must therefore be recorded before **EKILL** and included in the balance. After each band is deactivated, the hot-side convection and surface elements must be transferred to the newly exposed face. With only eight layers through **phe0**, recession would advance in increments of approximately 0.318 mm. A credible recession study should use 20 to 40 radial bands, or demonstrate that the existing increment is sufficiently small.

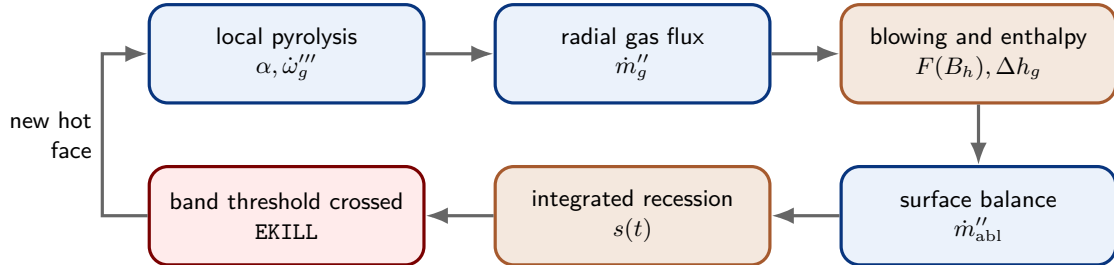


Figure 8. Proposed physical sequence for Simulation 2 in Mechanical. Element deactivation is driven by recession, not directly by **SVAR1**.

3.1.5 Proposed Initial Values and Sensitivity Studies

Table 12 provides an initial parameter set for prototyping, not for qualification. The permeability values are taken from the **CHAR PICA** model and are only surrogates for a dense phenolic [6]. Phenolic resin products include, among others, H_2 , water vapor, and aromatic hydrocarbons, and depend on heating rate [8]; representing them with a single pseudo-species is therefore a major simplification.

Quantity	Proposed nominal	Sensitivity range	Rationale / required measurement
Gas yield Y_g	0.47	0.44–0.50	Derived from the current virgin/char densities using Equation (22); replace with TGA data.
Virgin porosity ϕ_v	0.13	0.05–0.20	Derived from $1 - \rho_v / \rho_{\text{skeletal}}$, with $\rho_{\text{skeletal}} = 1430 \text{ kg m}^{-3}$, a historical phenolic-nylon value [7].
Char porosity ϕ_c	0.55	0.45–0.65	Same calculation using $\rho_c = 600 - -700 \text{ kg m}^{-3}$; measure by pycnometry/porosimetry.
Virgin permeability K_v	10^{-12} m^2	10^{-14} – 10^{-11} m^2	PICA “Model A” value used as a surrogate [6]; not transferable without testing.
Char permeability K_c	10^{-10} m^2	10^{-12} – 10^{-9} m^2	Same source; logarithmic interpolation with respect to α is recommended.
Gas viscosity μ_g	$4 \times 10^{-5} \text{ Pa s}$	2 – $6 \times 10^{-5} \text{ Pa s}$	Provisional hot pseudo-gas value; a mixture calculation is required.
Molar mass M_g	$0.024 \text{ kg mol}^{-1}$	0.018–0.030	Pseudo-species spanning light gases and vapor; calculate from the measured composition.
Gas heat capacity $c_{p,g}$	$1.5 \text{ kJ kg}^{-1} \text{ K}^{-1}$	1.2–2.0	Initial pseudo-gas value; use a $c_p(T, p)$ table after characterization.
Char emissivity ε_c	0.80	0.70–0.90	Historical phenolic-nylon starting point [7]; high-temperature measurement required.
Ablation enthalpy H_{eff}	35 MJ kg^{-1}	20, 35, and 50 MJ kg^{-1}	Effective recession parameter. 50 MJ kg^{-1} is a historical sublimation anchor [7]; calibrate against thickness loss.
Reference temperature T_{ref}	295.15 K	fixed	Consistent with the initial state.
Recession increment	$\dot{s}\Delta t \leq 0.2\Delta r$	0.1–0.25 Δr	Numerical criterion to prevent several bands from being crossed in one substep.

Table 12. Proposed initial parameters for Simulation 2. They must be treated as uncertain variables until they have been characterized.

Before a complete motor simulation is attempted, three separate validation campaigns are required: (i) TGA/DSC/LFA coupon testing for decomposition, (ii) permeability and gas-pressure measurements in a heated coupon for outgassing, and (iii) an instrumented flame or motor test for h_0 , blowing, and recession. The model must not compensate for an incorrect chamber boundary condition by artificially adjusting H_{eff} .

3.2 Implementation in Mechanical

3.2.1 Computational Architecture

Simulation 2 was implemented and executed with ANSYS Mechanical APDL 2026 R1.02. It reuses the validated three-dimensional mesh from Simulation 1 and the native `UserMatTh` library. The five state variables stored in `phe0` are:

$$\text{SVAR1} = \alpha, \quad \text{SVAR2} = \dot{\alpha}, \quad \text{SVAR3} = \dot{\omega}_g''', \quad \text{SVAR4} = \int \dot{\omega}_g''' dt, \quad \text{SVAR5} = \dot{q}_{m,g}. \quad (32)$$

The first Mechanical command object configures the user material; the second drives the transient loop. Each macro-step follows the sequence

$$\text{SOLVE} \longrightarrow \text{gas and energy balance} \longrightarrow \text{blowing and recession update} \longrightarrow \text{multiframe restart}.$$

After the first macro-step, `ANTYPE,,REST,,CONTINUE` explicitly resumes the last converged state. Temperature and the SVARs are therefore not recomputed from $t = 0$.

The computation targets 7 s using 140 uniform macro-steps of $\Delta t = 0.05 \text{ s}$. The 2.54 mm-thick inner `phe0` layer is divided into eight radial bands, each 0.3175 mm thick. The controller uses $T_g = 2230.85^\circ \text{C}$, $h_0 = 1000 \text{ W m}^{-2} \text{K}^{-1}$, $c_{p,g} = 1600 \text{ J kg}^{-1} \text{K}^{-1}$, $\rho_c = 600 \text{ kg m}^{-3}$, and $H_{\text{eff}} = 35 \text{ MJ kg}^{-1}$. A band is deactivated only when all three conditions below are satisfied:

$$\bar{\alpha} \geq 0.99, \quad \alpha_{\min} \geq 0.90, \quad s \geq (i + 1)\Delta r.$$

After the surface-effect elements have been installed, the current model contains approximately 2.24 million nodes and 7.15×10^5 elements. The inner surface contains 135,900 nodes and 43,488 surface-effect elements; the first candidate band contains 39,808 elements.

Numerical parameter	Executed value
Version and solver	MAPDL 2026 R1.02, nonlinear transient thermal analysis
Parallel execution	distributed memory, Intel MPI, 10 ranks, one thread per rank
Time horizon	7 s, 140 macro-steps of 0.05 s
Global mesh	2,242,327 nodes; approximately 714,676 elements after setup
Hot surface	135,900 nodes; 43,488 surface-effect elements
phe0 bands	8 bands, each 0.3175 mm thick
Persistence	CSV history at every step and distributed restart files retained on all 10 ranks

Table 13. Executed numerical configuration for Simulation 2.

3.2.2 Persistence, Recovery, and Consistency Checks

The `simulation2_history.csv` file is closed and reopened in append mode after every macro-step. A `simulation2_state.parm` file stores the last solved time, balances, recession, and active band. Restart files remain distributed; a recovery is valid only when the ten rank-specific sets, the history, and the parameter state point to the same load step.

The first campaign was stopped cleanly after load step 15 at $t = 0.75$ s, then resumed from load step 16. The continuation restored the result at 0.80 s and proceeded without reinitializing temperature or the SVARs. This recovery is an important robustness check because a complete computation requires several days of wall-clock time. The campaign was then stopped intentionally on July 23, 2026. Load step 130 had converged at 6.50 s, but global result assembly was still in progress: the history and parameter state remained synchronized at load step 129, 6.45 s. Accordingly, all final statistics and figures exclude the unsynchronized 6.50 s state.

Recession-rate statistics are extracted read-only with DPF from the ten `file0.rth` through `file9.rth` files. For each state, the extraction checks all 135,900 inner-surface nodes and matches the result times against the history. Figures are published only after the distributed result files have stabilized.

3.3 Simulation 2 Results and Performance

3.3.1 Run Status and Numerical Performance

The campaign is complete by user decision. The last fully synchronized state is load step 129 at $t = 6.45$ s, or 92.1% of the target physical duration. The remaining 0.55 s was not computed, and no extrapolation is presented as a result.

The observed continuation from load step 17 through load step 129 contains 113 synchronized macro-steps and no MAPDL errors. Of these steps, 93 converged in two equilibrium iterations and 20 in three. Load step 130 also converged in two iterations, but is excluded from the balance because it was not synchronized. The median wall time per macro-step is 45.1 minutes over the synchronized continuation. It increases as the result files grow: over the latest 24 steps, the median is 60.3 minutes, corresponding to approximately 0.050 s of simulated time per wall-clock hour. Over the latest ten steps, the median reaches 67.1 minutes, with an observed range of 59.1 to 125.8 minutes; the largest values are primarily associated with result assembly.

Thermal solution time is not the only dominant cost. After every convergence, MAPDL assembles and interprets the distributed results; this phase can currently take approximately 40 minutes. The resident database allocation had to grow automatically from 1 to 4 GB. The PCG solver also reports more than 1,000 linear iterations per load step and suggests the direct SPARSE solver. Any solver change, however, must be evaluated in a separate controlled comparison using the same mesh and result-storage settings.

The continuation log contains zero errors. The `RESCONTROL,DEFINE` warning stating that the command is ignored during a restart repeats at every macro-step, with no observed loss of checkpoints. Eight initial warnings concern material-property tables evaluated slightly outside their tabulated ranges; those ranges must be extended before qualification, even though the warnings did not prevent convergence.

Performance indicator	Final observed value
Synchronized progress	129/140 steps; 6.45 s/7 s; 92.1%
Analyzed continuation	113 steps, from load step 17 through load step 129
Nonlinear convergence	93 steps at 2 iterations; 20 steps at 3 iterations
Median time per step, full continuation	45.1 min
Median time per step, latest 24 steps	60.3 min
Recent throughput	approximately 0.050 s simulated per wall-clock hour
Observed parallel chain	10 ANSYS ranks, 1 <code>mpiexec</code> , 1 <code>hydra_pmi_proxy</code>
Final stop	intentional; last coherent checkpoint at 6.45 s
Diagnostics	0 MAPDL errors; non-blocking restart warnings

Table 14. Final numerical performance of the campaign stopped at 6.45 s.

3.3.2 Thermochemical Evolution and Outgassing

Table 15 lists the values recorded by the controller. Mean conversion reaches 0.50 at approximately 1.20 s, 0.90 at 2.40 s, and 0.99 at 3.50 s. The spatial minimum reaches 0.90 at 3.00 s and 0.99 at 4.00 s. At 6.45 s, the active layer is almost fully converted, with $\bar{\alpha} = 0.99999962$ and $\alpha_{\min} = 0.99999779$.

The gas flow rate first rises as pyrolysis activates, reaches 4.849 g s^{-1} at 1.90 s, then slowly decreases to 3.756 g s^{-1} at 6.45 s. Trapezoidal integration of the sampled values, completed by a linear ramp from zero flow at $t = 0$, gives approximately 26.47 g of gas generated by that time. This mass is a balance from the reduced-order model; it is not a measurement of composition, pore pressure, or the actual instantaneous chamber flow rate.

The effective convection coefficient follows the blowing correction. It reaches a minimum of $843.75 \text{ W m}^{-2} \text{ K}^{-1}$ at the outgassing peak, a maximum reduction of 15.6% relative to h_0 . It then recovers to $874.53 \text{ W m}^{-2} \text{ K}^{-1}$, still 12.5% below the no-blowing value. Despite this reduction, the maximum hot-surface temperature continues to rise and reaches 1644.11°C at 6.45 s; a final thermal steady regime has therefore not yet been demonstrated.

t [s]	$\bar{\alpha}$	$\alpha_{\min}$	$\dot{m}_g$ [g/s]	h [$\text{W}/\text{m}^2/\text{K}$]	$T_{s,\max}$ [$^\circ\text{C}$]	s [μm]
0.05	0.002295	0.00000002	0.293	988.95	615.97	3.80
1.00	0.415457	0.110712	4.382	856.64	1262.14	48.56
1.90	0.786302	0.523440	4.849	843.75	1366.28	81.67
3.00	0.968921	0.906589	4.527	852.58	1466.32	117.62
4.00	0.997463	0.990541	4.276	859.62	1532.90	147.31
5.00	0.999894	0.999518	4.021	866.89	1585.39	174.83
6.15	0.999999	0.999993	3.809	873.01	1633.23	204.36
6.45	1.000000	0.999998	3.756	874.53	1644.11	211.74

Table 15. Simulation 2 snapshots through the last fully synchronized state at 6.45 s.

3.3.3 Virtual Recession and Deactivation Criterion

The accumulated energy-based recession reaches $211.74 \mu\text{m}$ at 6.45 s. This is 66.7% of the first-band thickness, $\Delta r = 317.5 \mu\text{m}$. The conversion criteria are already satisfied, but the geometric criterion is not; no band has therefore been deactivated. This result is physically consistent with the controller logic: complete pyrolysis is not automatically treated as material removal. The equivalent char mass associated with this virtual recession is approximately 5.32 g over the modeled surface, but it remains present in the mesh until the band threshold is crossed.

The final DPF extraction through 6.45 s confirms an almost uniform hot surface: mean temperature 1643.67°C , standard deviation 0.069°C , and range 1643.25 – 1644.11°C . Mean recession rate decreases from $78.21 \mu\text{m s}^{-1}$ at 0.05 s to $24.453 \mu\text{m s}^{-1}$ at 6.45 s. At the latter time, the spatial standard deviation is only $0.0029 \mu\text{m s}^{-1}$, indicating strong spatial uniformity in the truncated model. This uniformity must not be extrapolated to ends, joints, or the full motor without a corresponding geometric model.

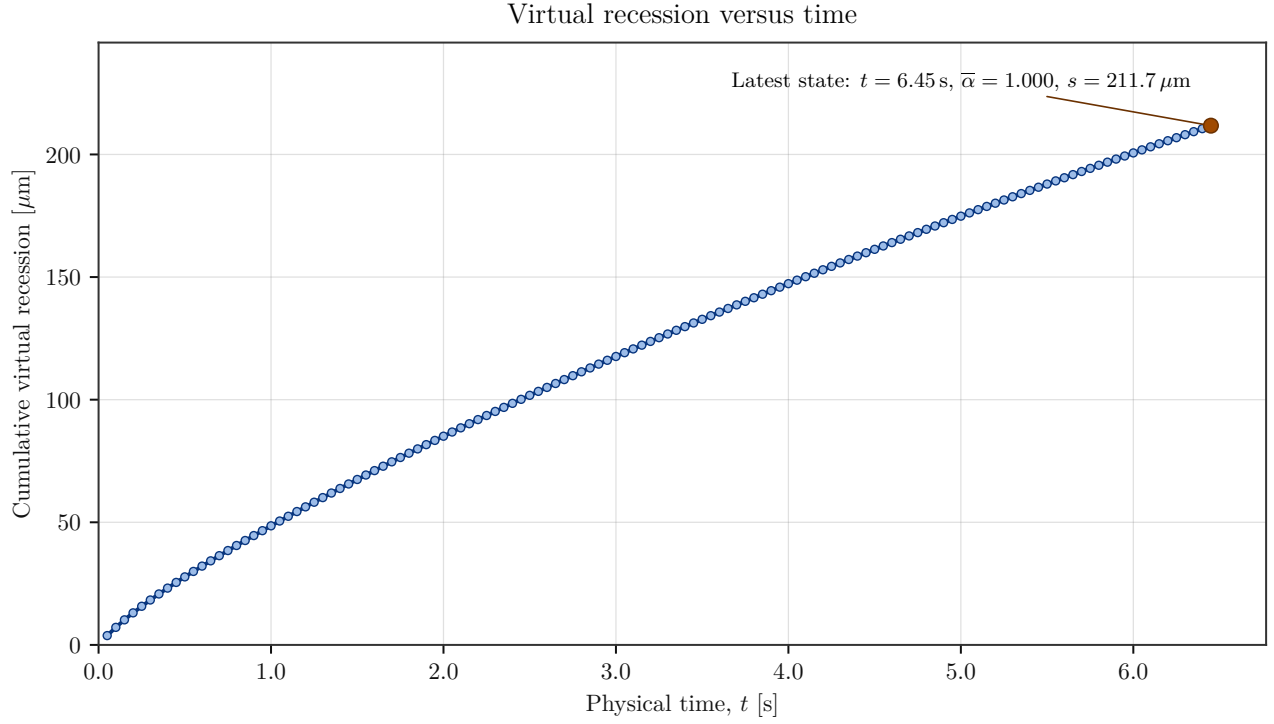


Figure 9. Accumulated virtual recession versus physical time. The curve is updated from fully synchronized states.

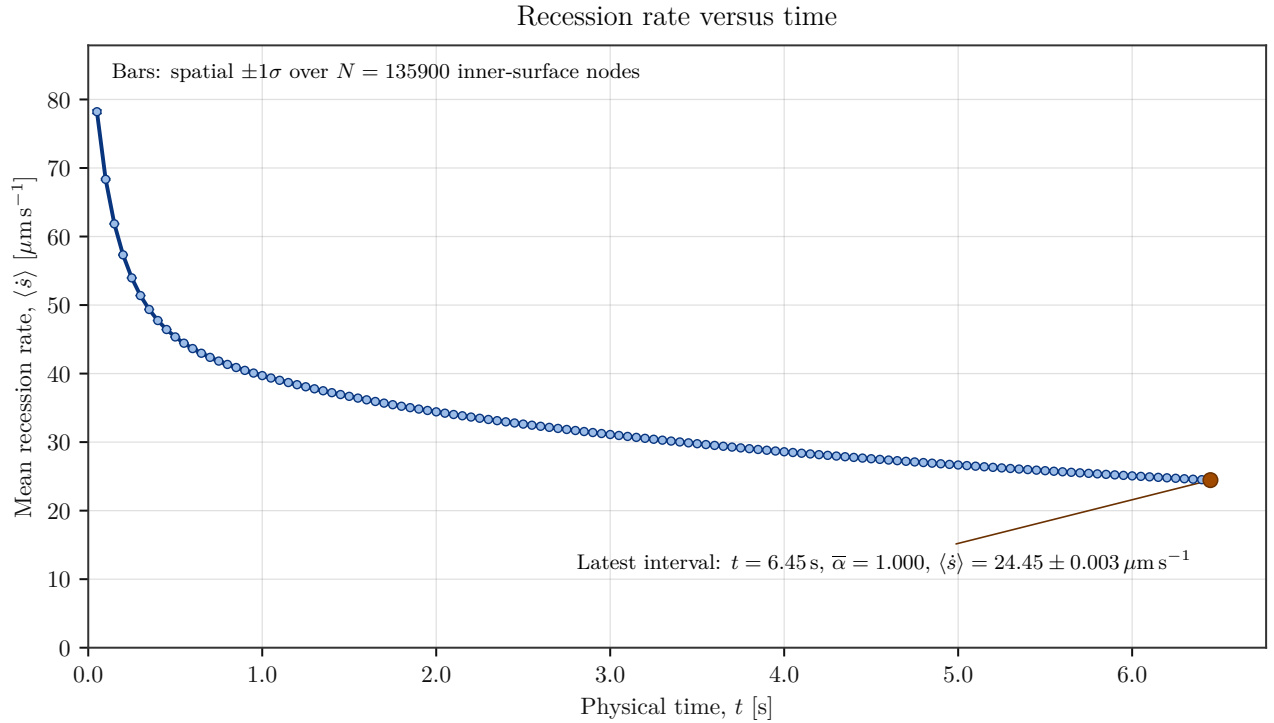


Figure 10. Mean recession rate over the 135,900 inner-surface nodes. Error bars represent spatial $\pm 1\sigma$.

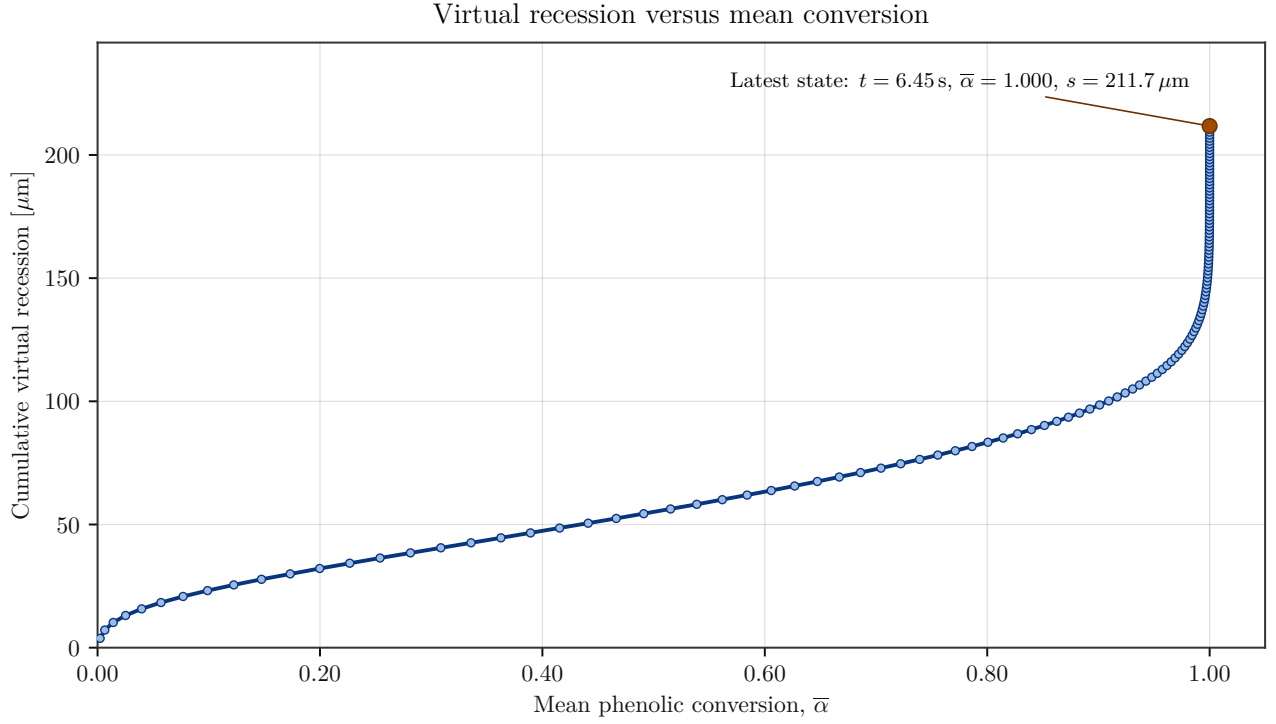


Figure 11. Virtual recession versus mean conversion. The curve shows that recession continues after $\bar{\alpha}$ has nearly saturated.

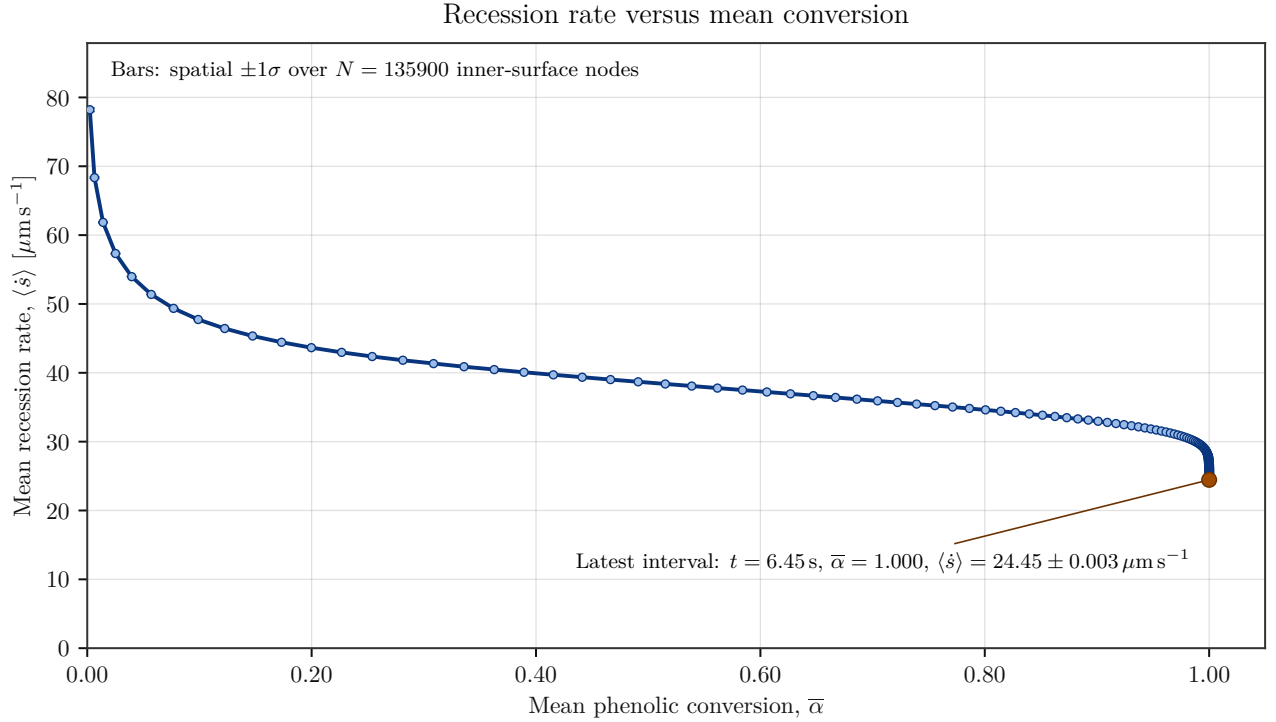


Figure 12. Recession rate versus mean conversion, with spatial $\pm 1\sigma$.

3.3.4 Spatial Conversion and Pyrolysis-Rate Profiles

To enable a direct comparison with Simulation 1, the same five profile families were reconstructed from the ten DMP partitions of Simulation 2. The saved states at $t = 1, \dots, 6 \text{ s}$ are available exactly, so no temporal interpolation is

used. The radial mesh, however, does not provide a node in every one of the one hundred 1% bands. Bands with no observation are hatched, and only the plotted envelope is linearly interpolated through them. This convention improves visual continuity without creating additional physical resolution.

The radial graphs also show the vertical line $d = s(t)$, where $s(t)$ is the cumulative recession computed by the controller's energy balance. No band has yet been deactivated; the line is therefore a *virtual* recession position inside the still-meshed first layer, rather than a geometric boundary that has already moved. It must not be confused with an α conversion contour.

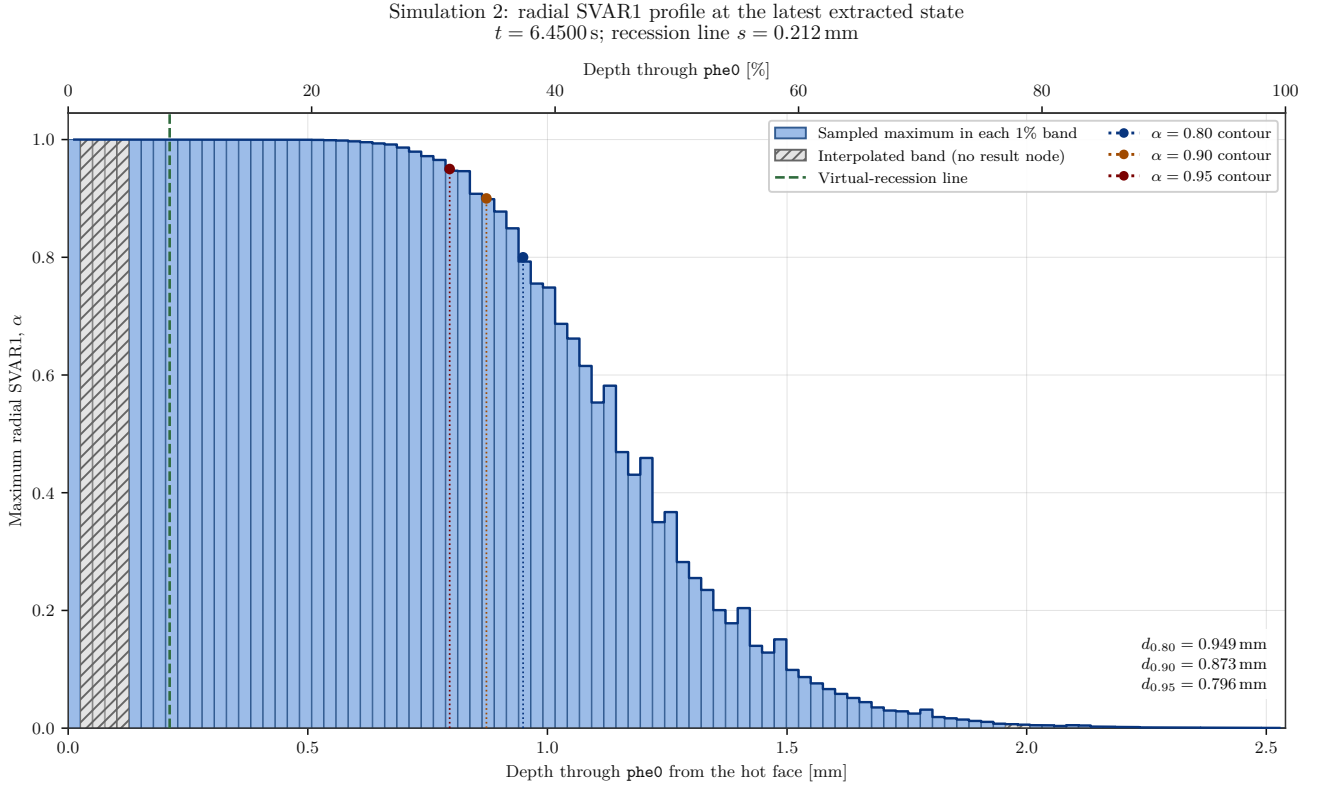


Figure 13. Radial maximum-SVAR1 profile at the latest common extracted state, including conversion contours and the virtual-recession line. Hatched bands contain no result node.

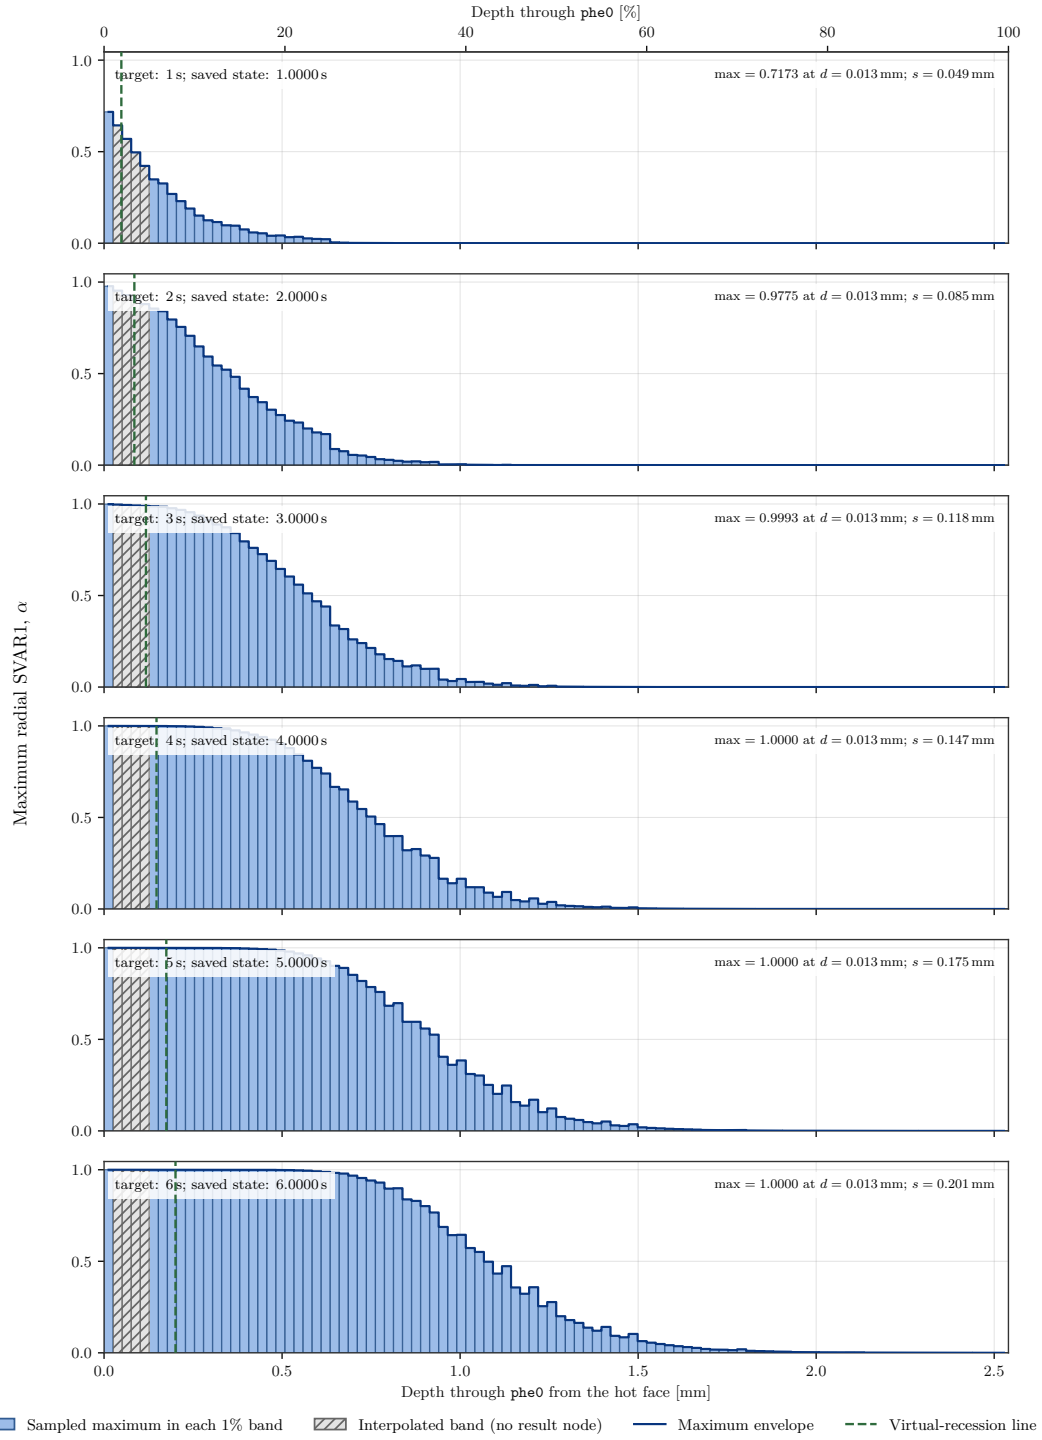


Figure 14. Evolution of the radial maximum of SVAR1 in Simulation 2. The dashed green line in each panel marks the cumulative virtual-recession position.

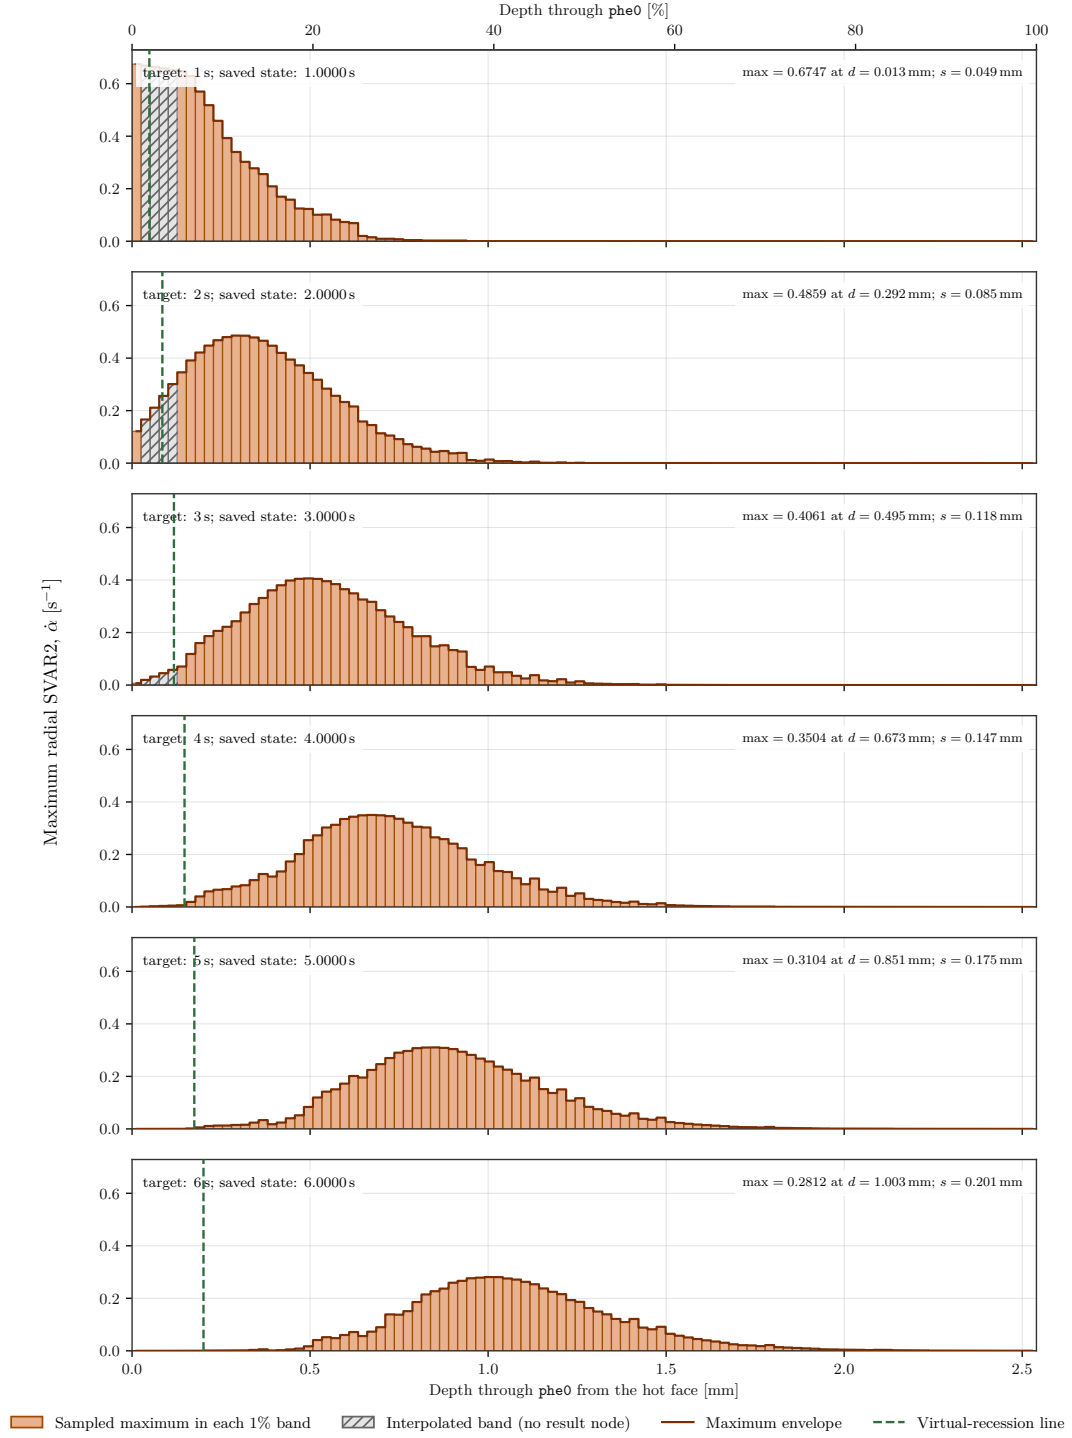


Figure 15. Evolution of the radial maximum of SVAR2. Migration of the maximum pyrolysis rate and progression of the virtual-recession line are shown on the same radial coordinate.

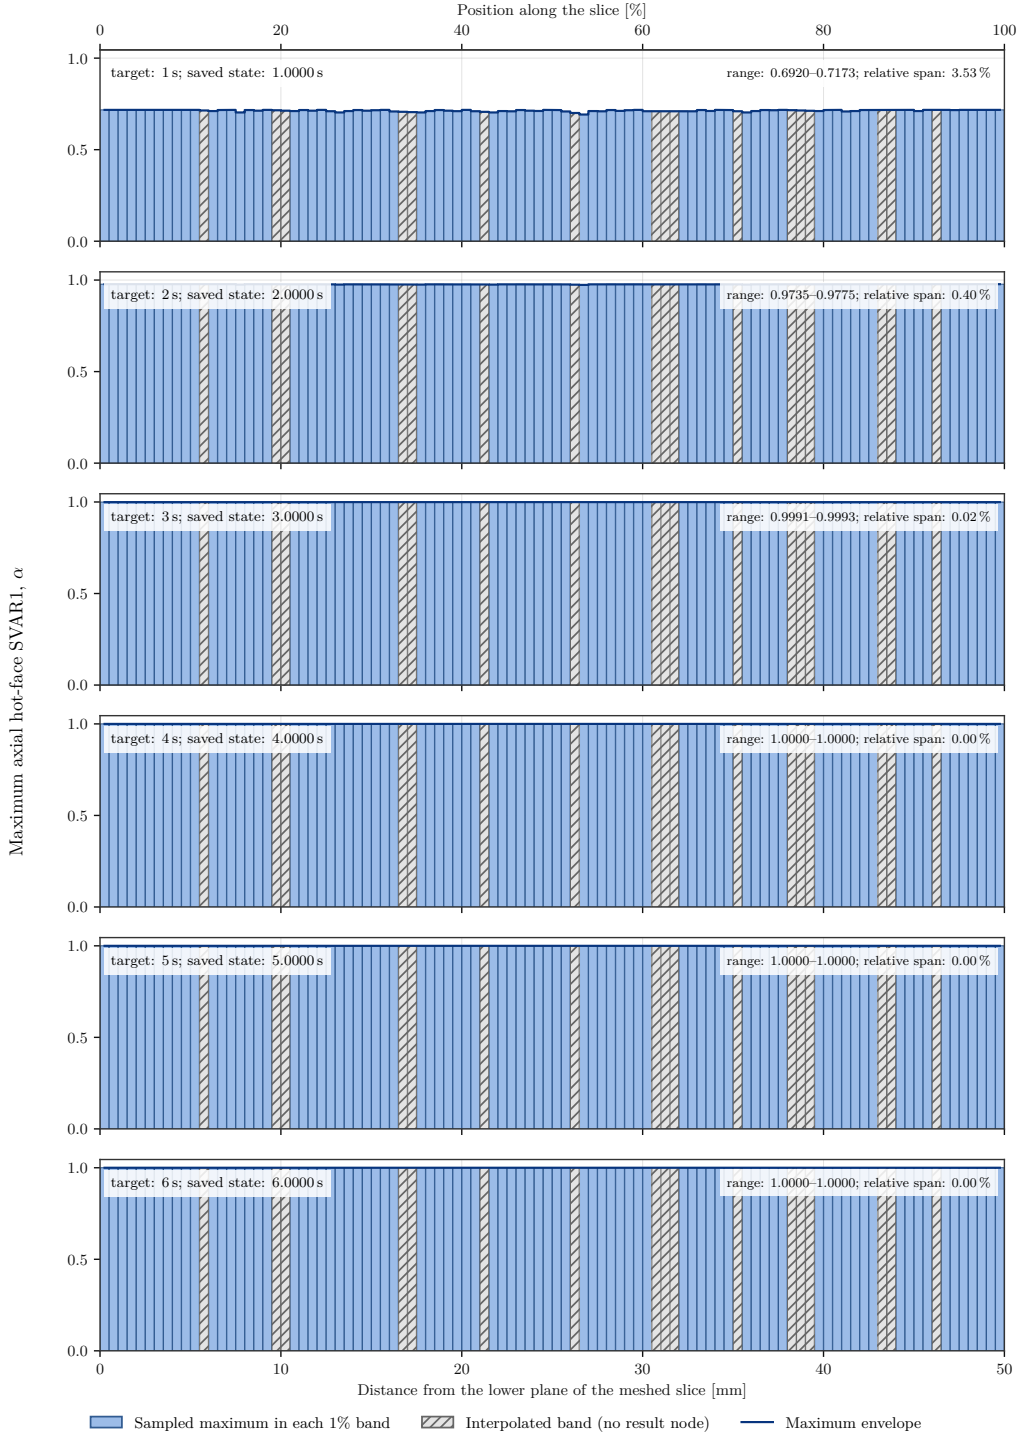


Figure 16. Axial dependence of SVAR1 on the hot inner surface in Simulation 2. No recession line is drawn on the axial axis because recession is defined along the radial coordinate.

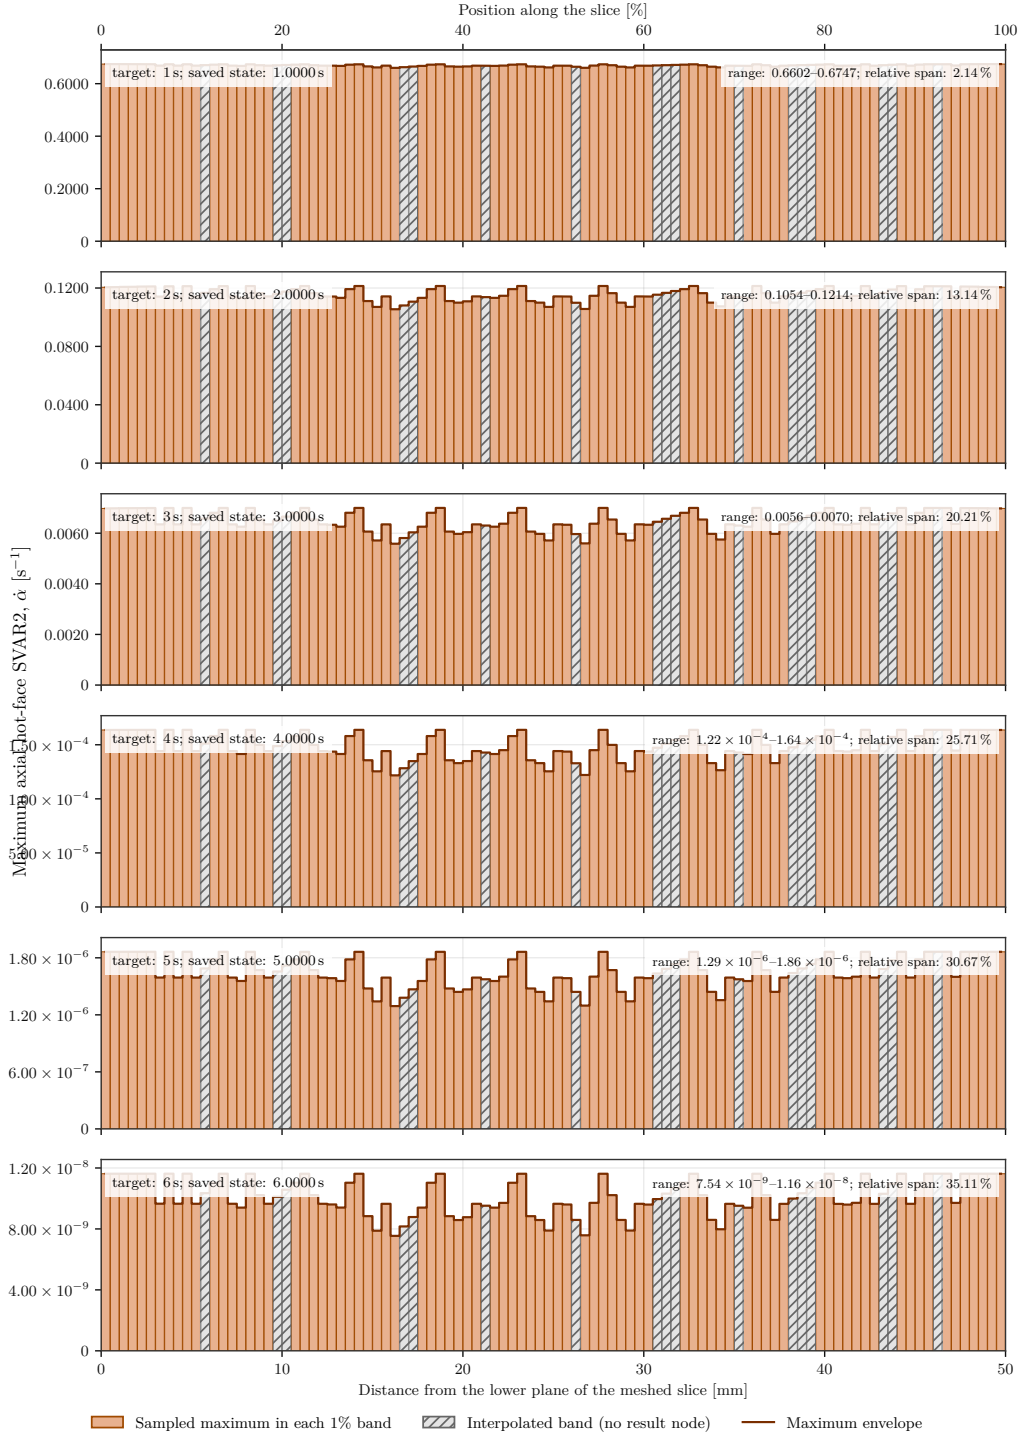


Figure 17. Axial dependence of SVAR2 on the hot inner surface in Simulation 2. An independent vertical scale in each panel reveals the small values after surface saturation.

The data retain 16 radial bands and 17 axial bands with no result node, all explicitly marked by hatching. At 1 s, the maximum radial conversion is $\alpha_{\max} = 0.7173$; it reaches numerical unity at 6 s. At the same time, the maximum pyrolysis rate decreases from 0.6747 s^{-1} to 0.2812 s^{-1} and migrates from 0.0127 mm to 1.0033 mm from the hot face. At the latest extracted state, 6.45 s, it is 0.2703 s^{-1} at 1.0795 mm.

The recession line progresses from 0.0486 mm at 1 s to 0.2006 mm at 6 s, and then to 0.2044 mm at 6.15 s and 0.2117 mm at 6.45 s. From 2 s onward, it remains well upstream of the SVAR2 maximum. The figures thus distinguish two different mechanisms visually: the volumetric zone where pyrolysis is most active and the cumulative material position that the energy balance would allow to recede. On the hot surface, SVAR1 becomes axially uniform at unity. Late relative variations of SVAR2 reach approximately 35%, but only for absolute values of order 10^{-8} s^{-1} , and are therefore physically negligible.

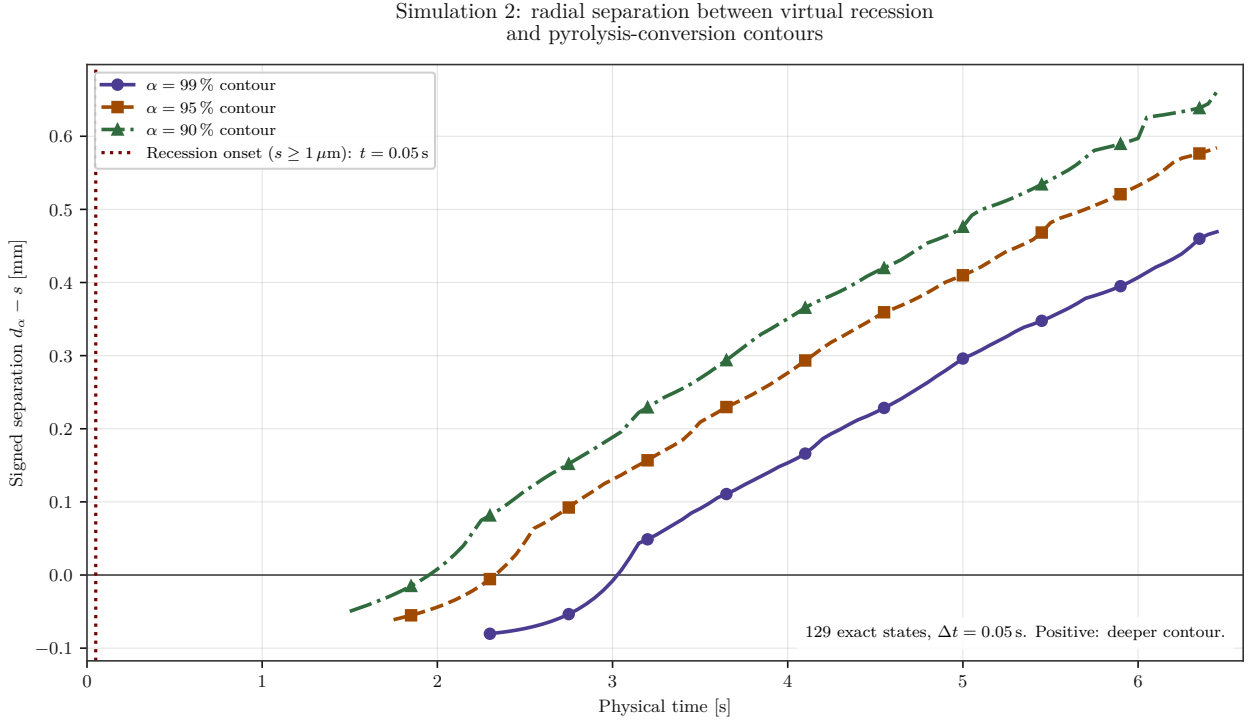


Figure 18. Signed radial separation between the virtual-recession line and the 99%, 95%, and 90% pyrolysis-conversion contours. The separation is defined as $\Delta d_\alpha = d_\alpha - s$: a positive value places the contour deeper into the wall than recession. The vertical dotted line marks the first state at which virtual recession reaches $1\ \mu\text{m}$.

The contours are obtained by spatial interpolation of the radial **SVAR1** envelope at all 129 synchronized states, spaced by $0.05\ \text{s}$ from $0.05\ \text{s}$ to $6.45\ \text{s}$; no temporal interpolation is introduced. The vertical line at $0.05\ \text{s}$ identifies the first state for which $s \geq 1\ \mu\text{m}$, with $s = 3.802\ \mu\text{m}$. This micrometre-scale threshold avoids treating round-off residue as front onset while remaining far below the radial resolution of the model. A curve starts only once its conversion threshold has actually been reached, so missing observations are not replaced by artificial zeros. The 90%, 95%, and 99% contours first appear at $1.50\ \text{s}$, $1.75\ \text{s}$, and $2.30\ \text{s}$, respectively, initially upstream of recession with $\Delta d_\alpha = -0.0497\ \text{mm}$, $-0.0611\ \text{mm}$, and $-0.0803\ \text{mm}$. They then pass the recession line at $2.00\ \text{s}$, $2.35\ \text{s}$, and $3.05\ \text{s}$. At the latest extracted state, $6.45\ \text{s}$, the separations reach $0.4693\ \text{mm}$, $0.5843\ \text{mm}$, and $0.6610\ \text{mm}$ for the 99%, 95%, and 90% contours, respectively. The growth of all three separations shows that the conversion front advances through the thickness faster than virtual recession.

3.3.5 Campaign Conclusion and Remaining Work

The main result of the campaign is twofold. First, the **UserMatTh**-outgassing-blowing-recession-distributed-restart chain has operated over 129 synchronized macro-steps without loss of continuity. Second, with $H_{\text{eff}} = 35\ \text{MJ kg}^{-1}$, recession remains below one band at $6.45\ \text{s}$; the pilot therefore predicted no discrete movement of the hot boundary before the intentional stop. Conversion advances deeper than virtual recession, while outgassing and blowing decrease after their peak.

This conclusion is strictly limited to the computed $0\text{--}6.45\ \text{s}$ interval. It does not determine whether the first band would be crossed during the uncomputed $0.55\ \text{s}$. More importantly, the executed geometry uses nominal diameters as radii, so the quantitative values do not describe the nominal motor. Before qualification, the geometry must be corrected and the analysis repeated; mass and energy balances must be closed; PCG and SPARSE must be compared; mesh convergence with 20 to 40 radial bands must be demonstrated; sensitivity to H_{eff} , h_0 , the time step, and char properties must be evaluated; and the model must be compared with an instrumented test. Without these steps, computed recession remains a model-performance indicator, not a qualified motor prediction.

4 Simulation 3: Corrected Thin Sector and Refined Radial Mesh

4.1 Objective and Executed Configuration

Simulation 3 transfers the Simulation 2 thermochemical chain to a corrected geometry that is strongly reduced in the circumferential direction. The model represents a 0.10° sector with an axial length of 50 mm. It retains the four coaxial layers at their actual radii: **phe0** from 66.675–67.945 mm, epoxy from 67.945–68.2625 mm, **phe1** from 68.2625–71.4375 mm, and aluminum from 71.4375–76.2 mm. A full ring contains 3,600 such sectors; only extensive quantities are multiplied by this factor. Temperatures, conversions, surface fluxes, and recession depths are not rescaled.

The sector is discretized with 35,200 linear eight-node hexahedra and 54,540 nodes. The mesh contains 100 axial divisions, two circumferential divisions, and 64, 16, 64, and 32 radial divisions in **phe0**, epoxy, **phe1**, and aluminum, respectively. The nominal radial pitch of the first layer is therefore

$$\Delta r_{\text{phe0}} = \frac{1.27 \text{ mm}}{64} = 19.84375 \text{ }\mu\text{m},$$

which is sixteen times finer than the $317.5 \text{ }\mu\text{m}$ bands used in Simulation 2. Three bonded interfaces provide thermal continuity between the four bodies.

The nonlinear transient thermal solve was executed in Mechanical/MAPDL 2026 R1.02 on ten DMP ranks. Its horizon remains 7 s, divided into 140 macro-steps of 0.05 s. The controller appends one history row after every converged macro-step and retains four restart generations. This design supports a controlled stop without losing already converged states.

Parameter	Executed Simulation 3 value
Sector and length	0.10° ; 50 mm
Hot / outer radius	66.675 mm / 76.2 mm
Mesh	54,540 nodes; 35,200 linear hexahedra
z/θ divisions	100 / 2
Radial divisions	64 / 16 / 64 / 32
Radial pitch in phe0	19.84375 μm
Contacts	3 bonded interfaces
Parallel execution	10 DMP ranks
Time horizon	7 s; 140 steps of 0.05 s
Full-ring scale factor	3,600, for extensive quantities only

Table 16. Geometry and mesh of the executed Simulation 3.

4.2 Final Status and Performance

The run completed normally on September 18, 2026. All 140 macro-steps converged through $t = 7.00 \text{ s}$, and the 140 history rows are uniformly spaced by 0.05 s, with no missing or duplicated time. MAPDL explicitly reports **RUN COMPLETED**; no **ANSYS.exe**, **mpiexec.exe**, or **hydra_pmi_proxy.exe** process remains after completion.

Total elapsed time is 5188.519 s, or 86 min 28.5 s, corresponding to an average of 37.1 s per macro-step. Solution computation accounts for 984.3 s (19.0%), while solution post-processing accounts for 3765.9 s (72.6%). This distribution shows that result writing and assembly dominate the cost of the thin-sector run. The ten ranks wrote 396.2 GB and read 82.5 GB; working files occupy 7656.1 MB. Aggregate memory use reached 828 MB, with 4032 MB allocated.

The log contains no error and twelve warnings. They concern disabled element shape checking, the standard **USERCK** implementation, evaluation at 22°C below the first tabulated temperature of several material properties, and one ignored **CEWRITE** command after the solve. None of these messages prevented convergence, production of all ten RTH partitions, or recording of the 140 states.

Metric	Final value
Converged states	140 of 140; 0.05–7.00 s
Parallel execution	10 DMP ranks, sparse direct solver
Elapsed / aggregate CPU time	5188.519 s / 5882.922 s
Solution computation time	984.3 s
Solution post-processing time	3765.9 s
Disk I/O read / written	82.5 GB / 396.2 GB
Errors / warnings	0 / 12
MAPDL outcome	RUN COMPLETED

Table 17. Final Simulation 3 performance summary.

4.3 Final Thermochemical Results

The first active row crosses the $\alpha = 0.99$ threshold at 2.60 s, with $\alpha = 0.99050948$; the controller then deactivates 200 **phe0** hexahedra. The second row crosses the same threshold at 2.95 s, with $\alpha = 0.99021488$, and another 200 hexahedra are deactivated. In total, 400 phenolic elements are deleted and no epoxy, **phe1**, or aluminum element is removed. The discrete hot radius advances from 66.675 mm to 66.714688 mm, or two radial pitches. The third row remains active: its conversion is 0.98643222 at 3.00 s and 0.98962501 at 7.00 s, just below the deletion criterion. Equality of the mean and minimum history values is consistent with sector symmetry and is checked below by the spatial DPF extraction.

The wall gas mass flux peaks at $0.1220 \text{ kg m}^{-2} \text{ s}^{-1}$ at 1.80 s, then decreases to $0.001636 \text{ kg m}^{-2} \text{ s}^{-1}$ at 7.00 s. Sector flow peaks at 0.7099 mg s^{-1} and ends at $0.009522 \text{ mg s}^{-1}$. Its time integral is 1.689 mg for the sector, or 6.080 g for the complete ring by the simple factor of 3,600. The effective convection coefficient reaches a minimum of $836.67 \text{ W m}^{-2} \text{ K}^{-1}$ at peak outgassing and recovers to $997.39 \text{ W m}^{-2} \text{ K}^{-1}$. Maximum temperature peaks at 1400.50°C at 2.60 s, then falls to 435.36°C at completion as inner rows are exposed.

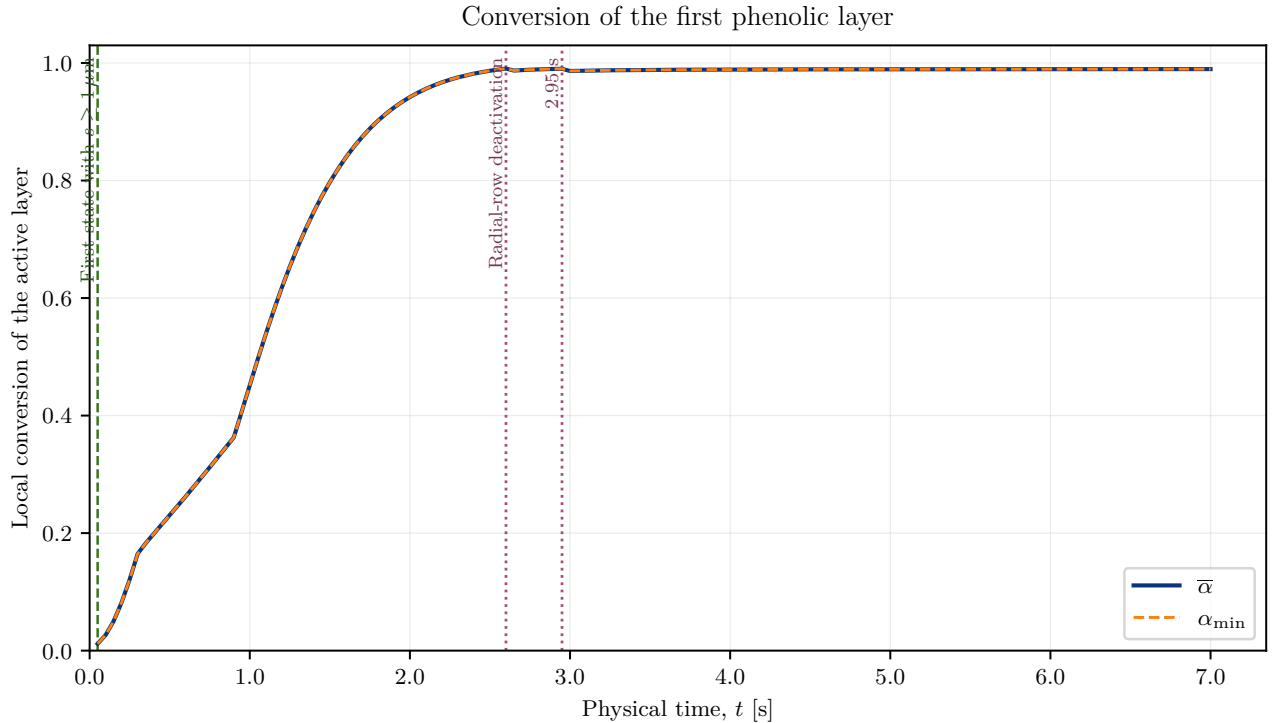


Figure 19. Mean and minimum conversion recorded in the thin sector’s active layer over all 140 converged states. Vertical lines mark the two radial-row deactivations.

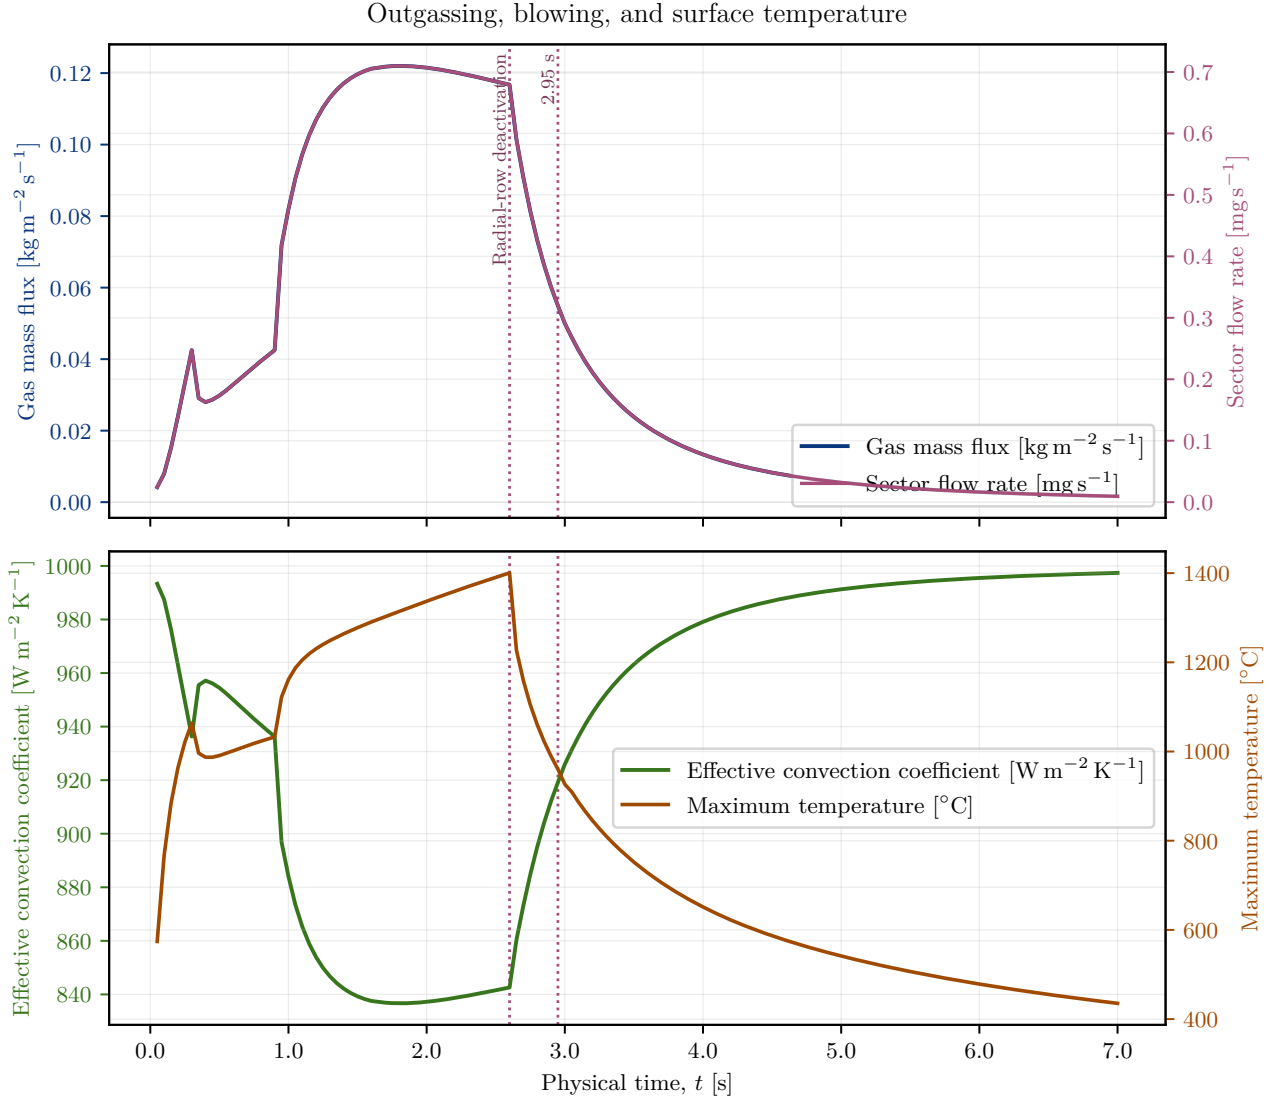


Figure 20. Evolution of outgassing, effective convection coefficient, and maximum hot-surface temperature. Total flow is for the 0.10° sector.

4.4 Virtual Recession and Element Deactivation

Accumulated energy-based recession reaches $446.254 \mu\text{m}$ at 7.00 s . The discrete surface has moved by only $39.6875 \mu\text{m}$, because deletion requires both the geometric threshold and $\alpha \geq 0.99$. Virtual recession therefore exceeds the third-row threshold of $59.53125 \mu\text{m}$, but that row's final conversion remains at 0.98962501 , so the controller correctly keeps it active. The final state confirms `SIM2_ILAY=2` and `SIM2_NEL=200`. The history's narrow integer fields display `****` and `**`; the plots ignore only those two unreadable fields and retain every valid physical column.

Numerically significant recession onset is defined as $s \geq 1 \mu\text{m}$. It occurs in the first recorded macro-step at 0.05 s , where $s = 3.918 \mu\text{m}$. The time plots mark this instant with a vertical line; two dotted lines mark deactivations at 2.60 s and 2.95 s . The rate shown below is the finite difference of accumulated recession between successive macro-steps; it is $78.37 \mu\text{m s}^{-1}$ over the first interval and $85.28 \mu\text{m s}^{-1}$ over the final interval. Plots against $\bar{\alpha}$ preserve the discontinuities caused by switching from one active row to the next.

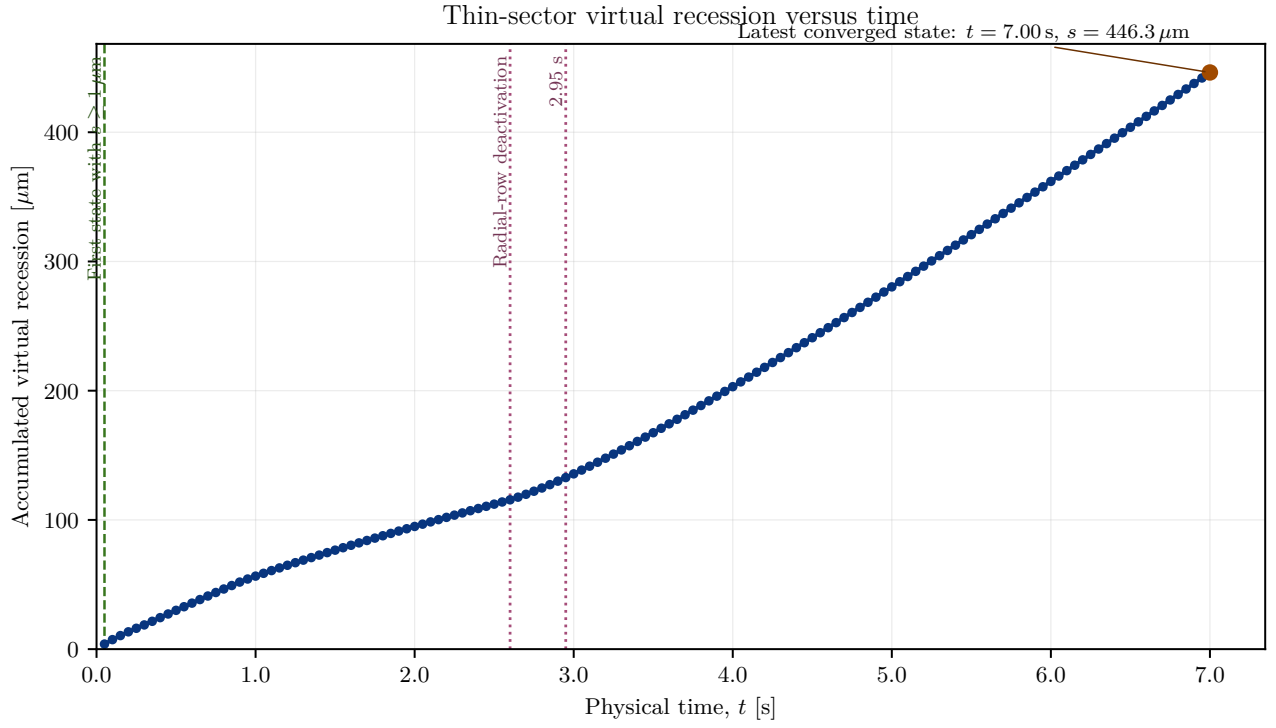


Figure 21. Accumulated virtual recession versus time for Simulation 3. The vertical lines mark numerical onset of the recession front and both radial-row deactivations.

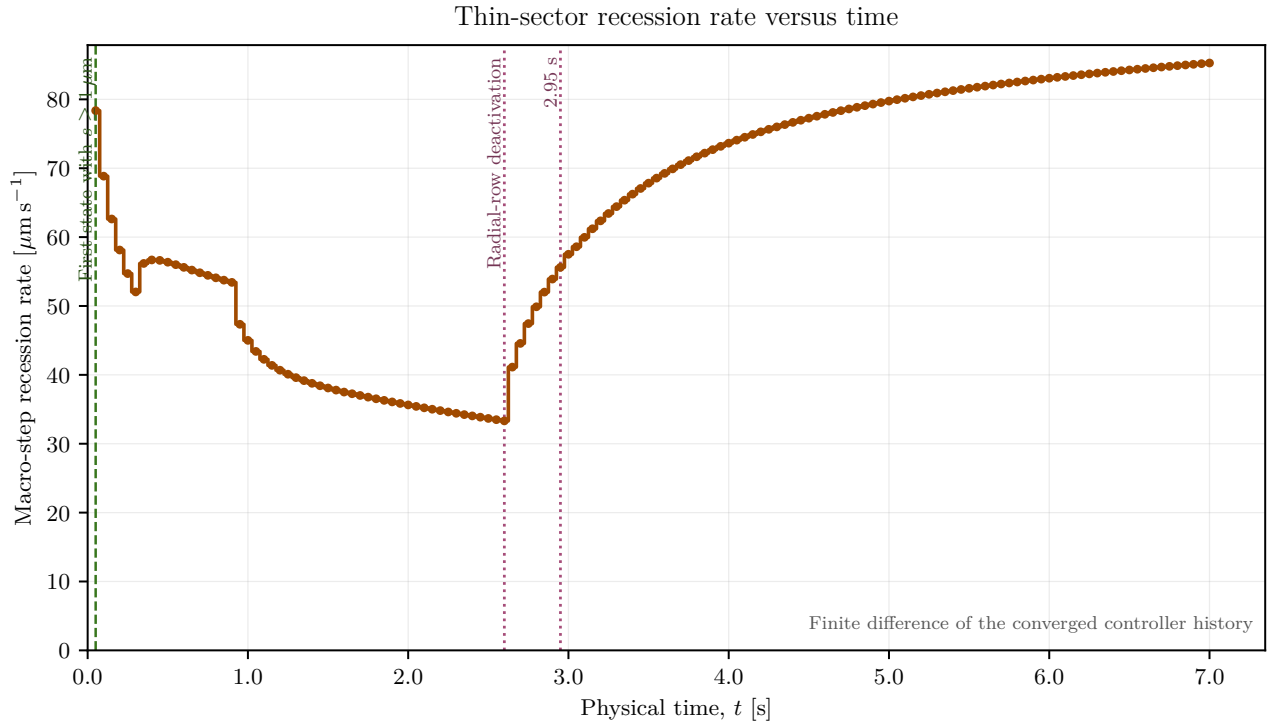


Figure 22. Macro-step recession rate. This is a temporal derivative of the controller history, without a spatial standard-deviation bar.

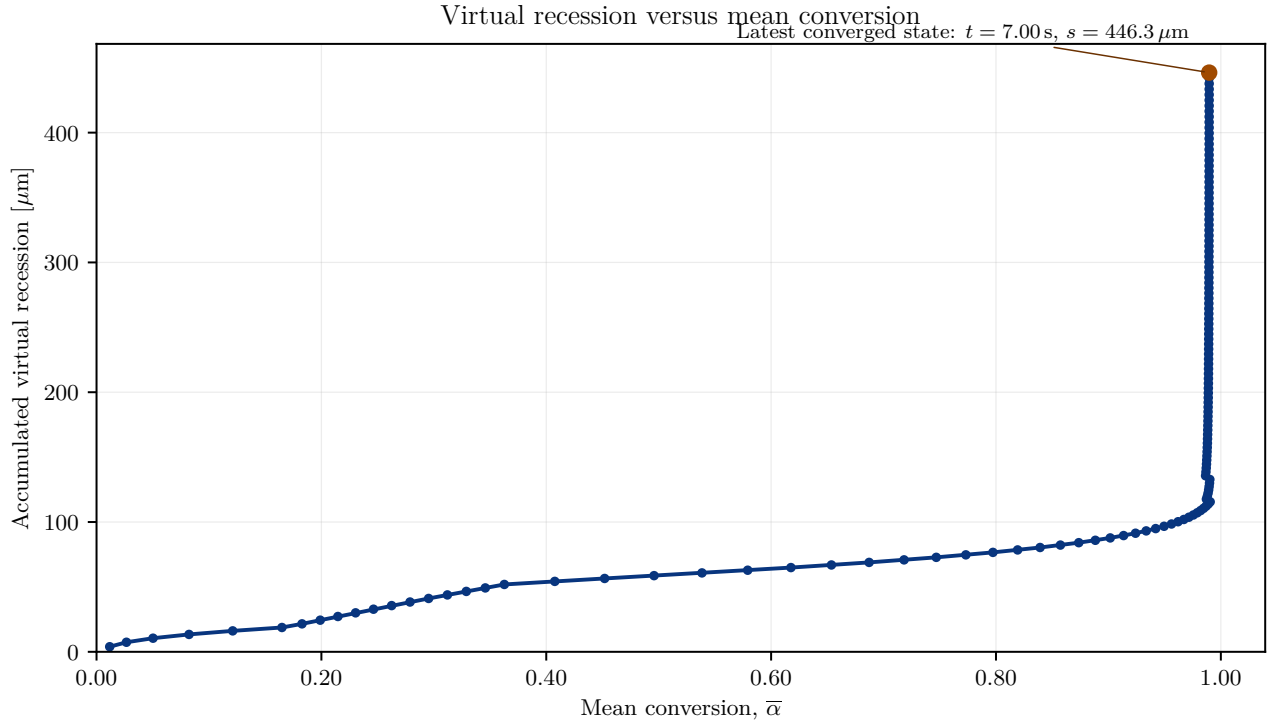


Figure 23. Accumulated virtual recession versus active-layer mean conversion.

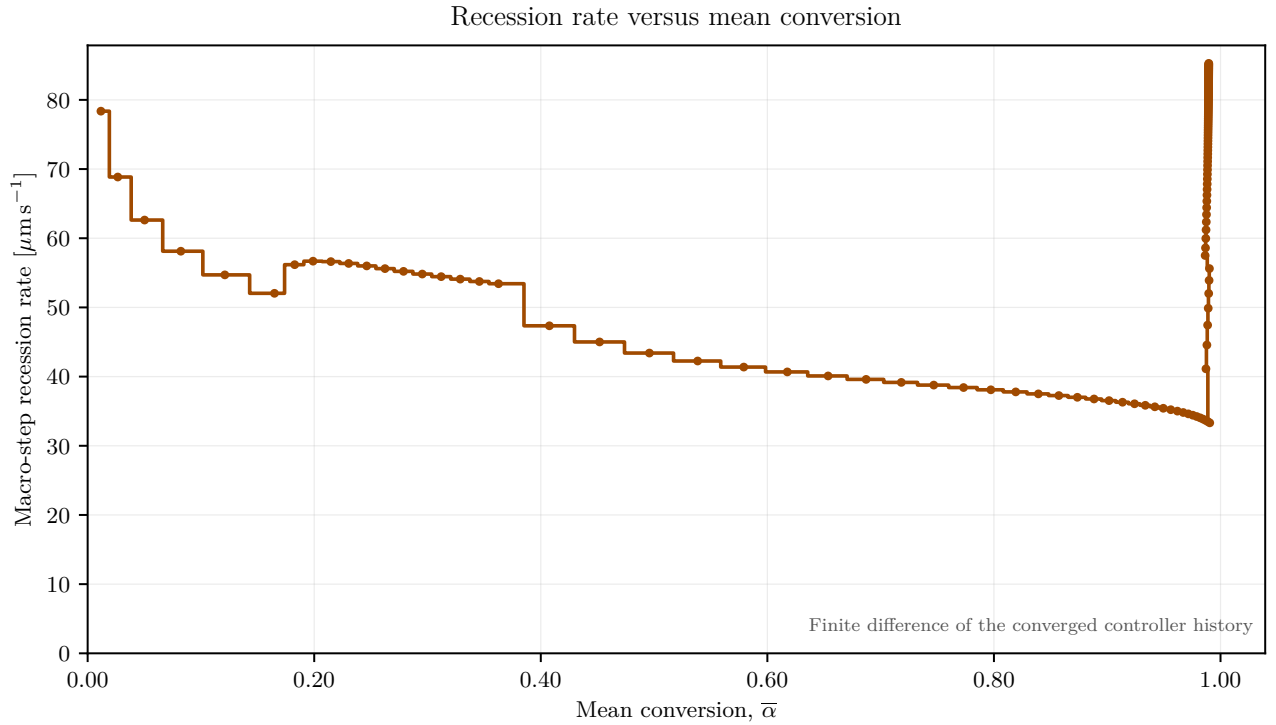


Figure 24. Macro-step recession rate versus mean conversion.

4.5 Final Spatial Analysis of State Variables

After normal completion, the ten `file0.rth` through `file9.rth` partitions were read in strictly non-destructive mode. All 140 DPF times match the 140 history times exactly. Element-node contributions sharing a global node

identifier are averaged across elements and partitions, then grouped in 100 radial bands of 1%. The extractor handles each state's topology separately so that profiles remain valid after both deletion events.

The 90%, 95%, and 99% contours first appear at 1.80 s, 2.05 s, and 2.55 s, respectively. At 7.00 s, their depths from the initial hot face are 0.223 066 mm, 0.156 483 mm, and 0.048 842 mm. The signed separations $d_\alpha - s$ are therefore $-0.223\,188$ mm, $-0.289\,771$ mm, and $-0.397\,412$ mm. The energy-based virtual-recession coordinate is thus deeper than all three conversion fronts, confirming that it must not be interpreted as a **SVAR1** contour.

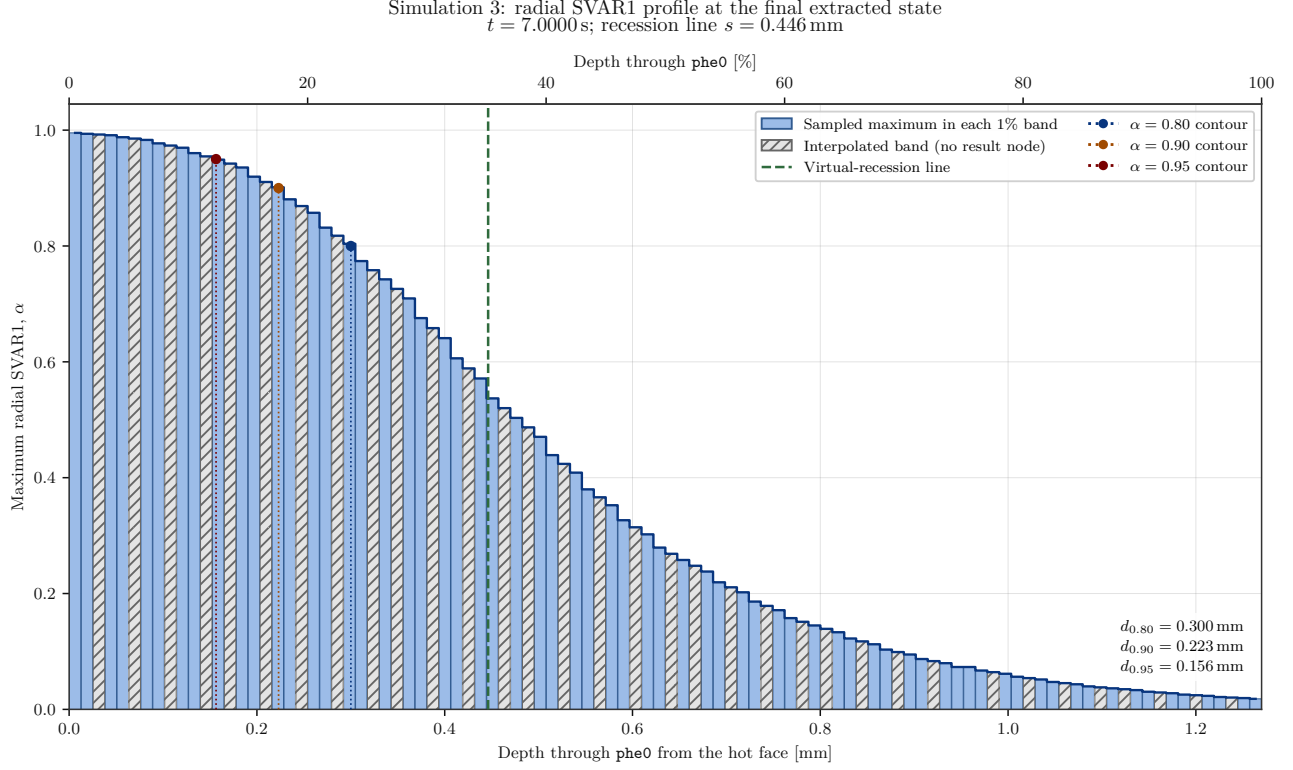


Figure 25. Final radial SVAR1 profile at 7 s, including conversion contours and the virtual-recession line.

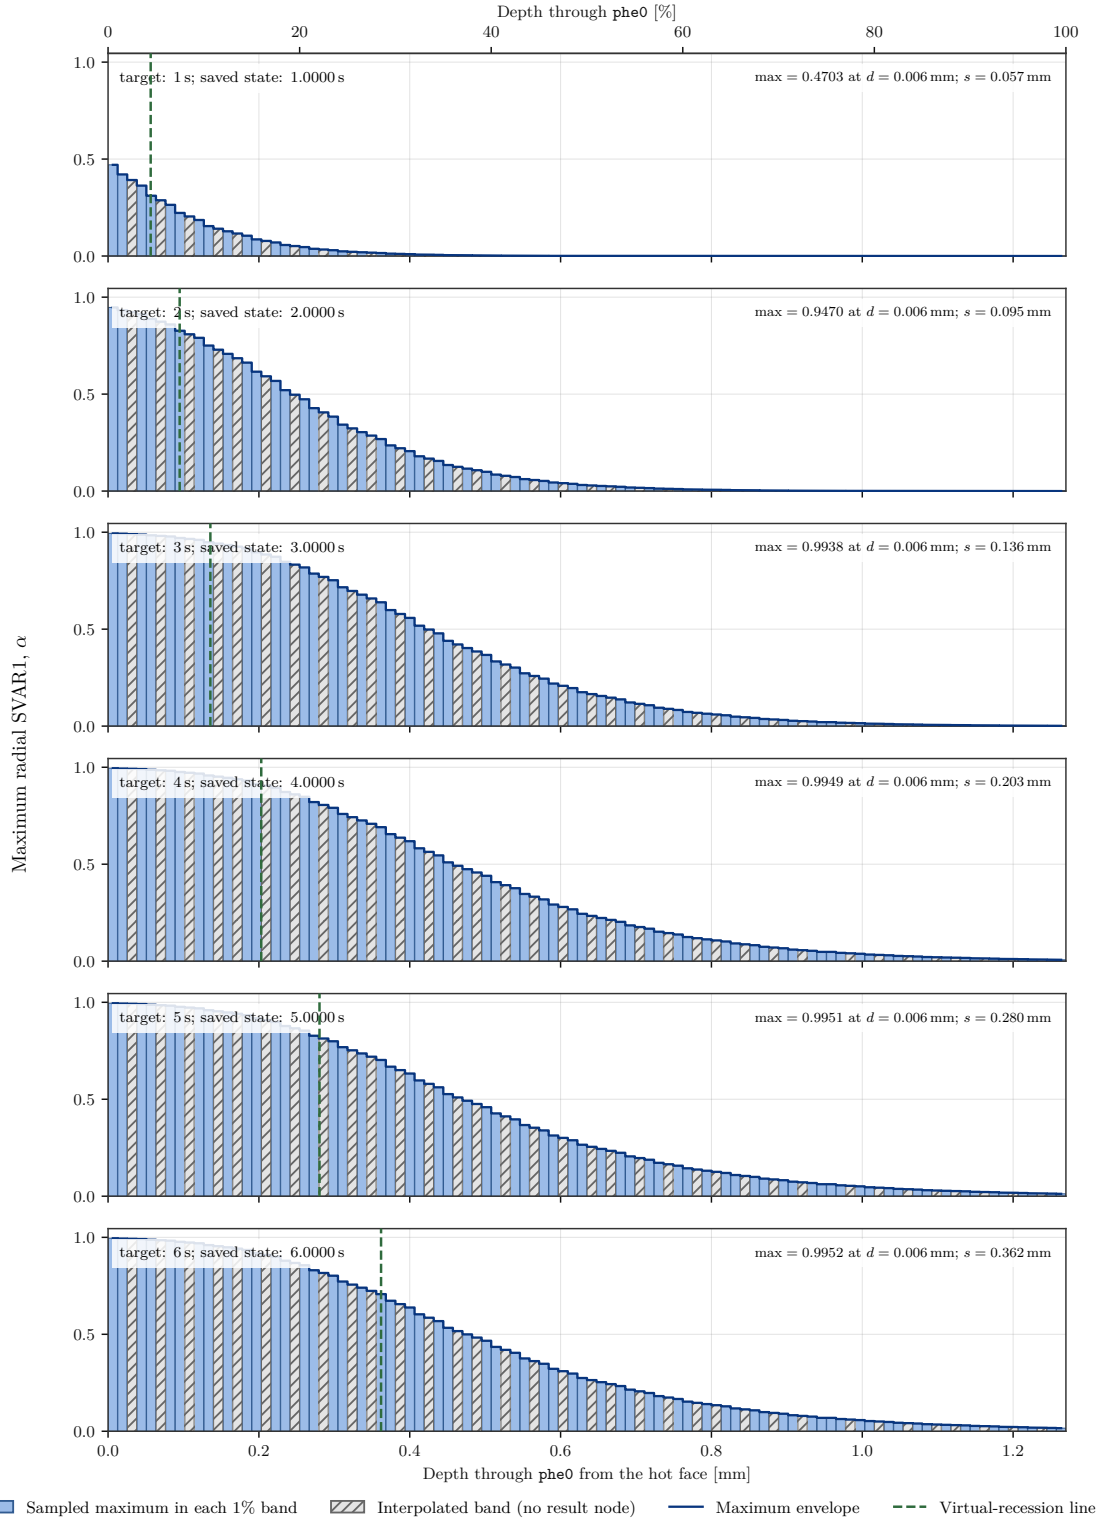


Figure 26. Evolution of radial SVAR1 profiles from 1 to 6 s. The recession line is shown in every panel.

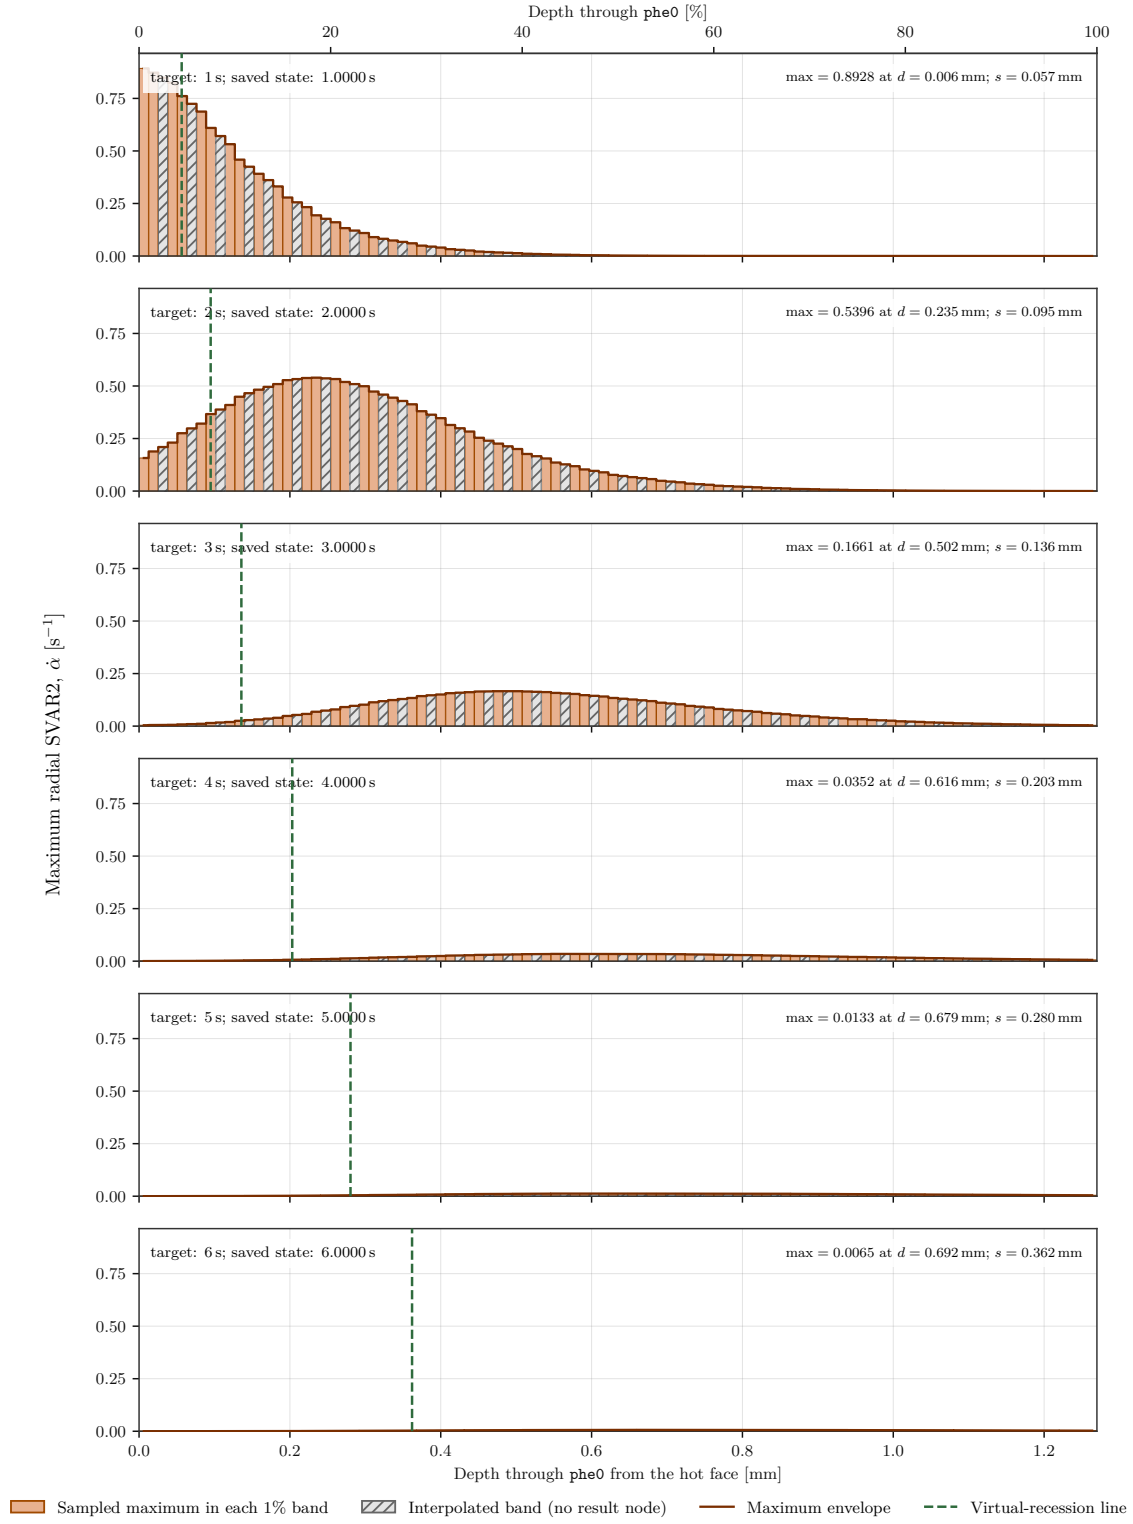


Figure 27. Evolution of radial SVAR2 profiles; the maximum identifies the region where pyrolysis remains active.

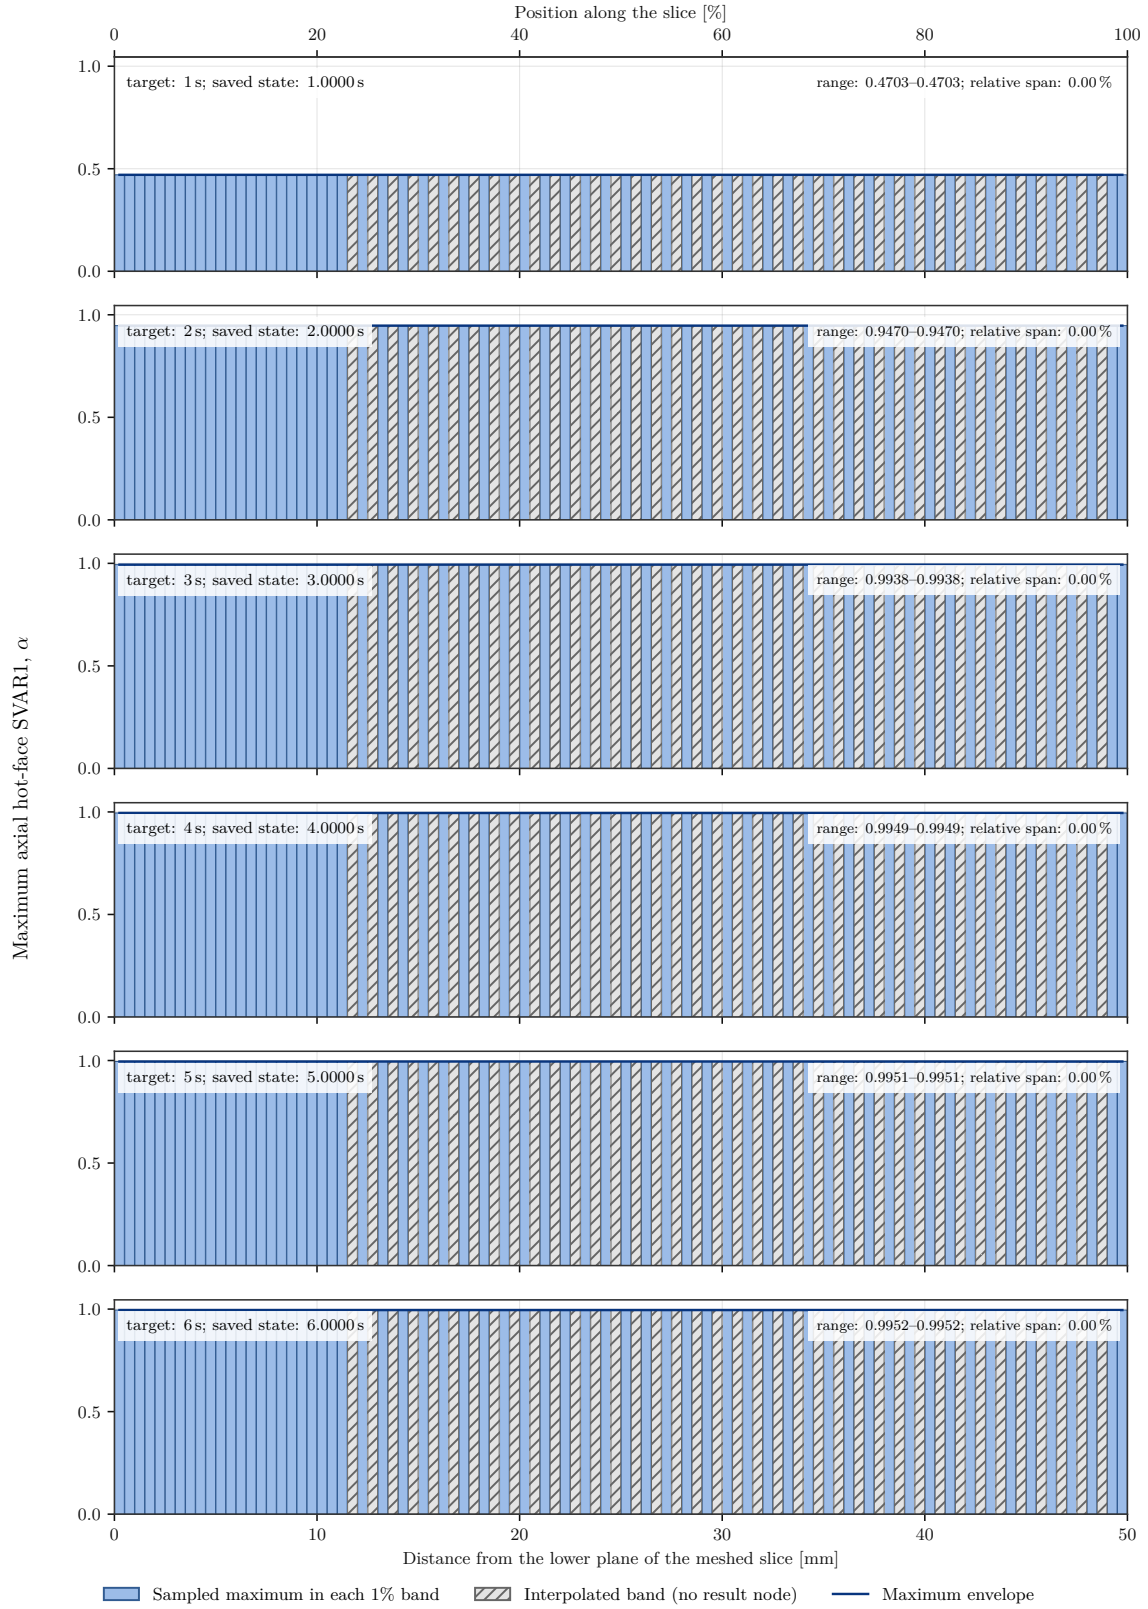


Figure 28. Axial uniformity of SVAR1 along the thin sector's hot face.

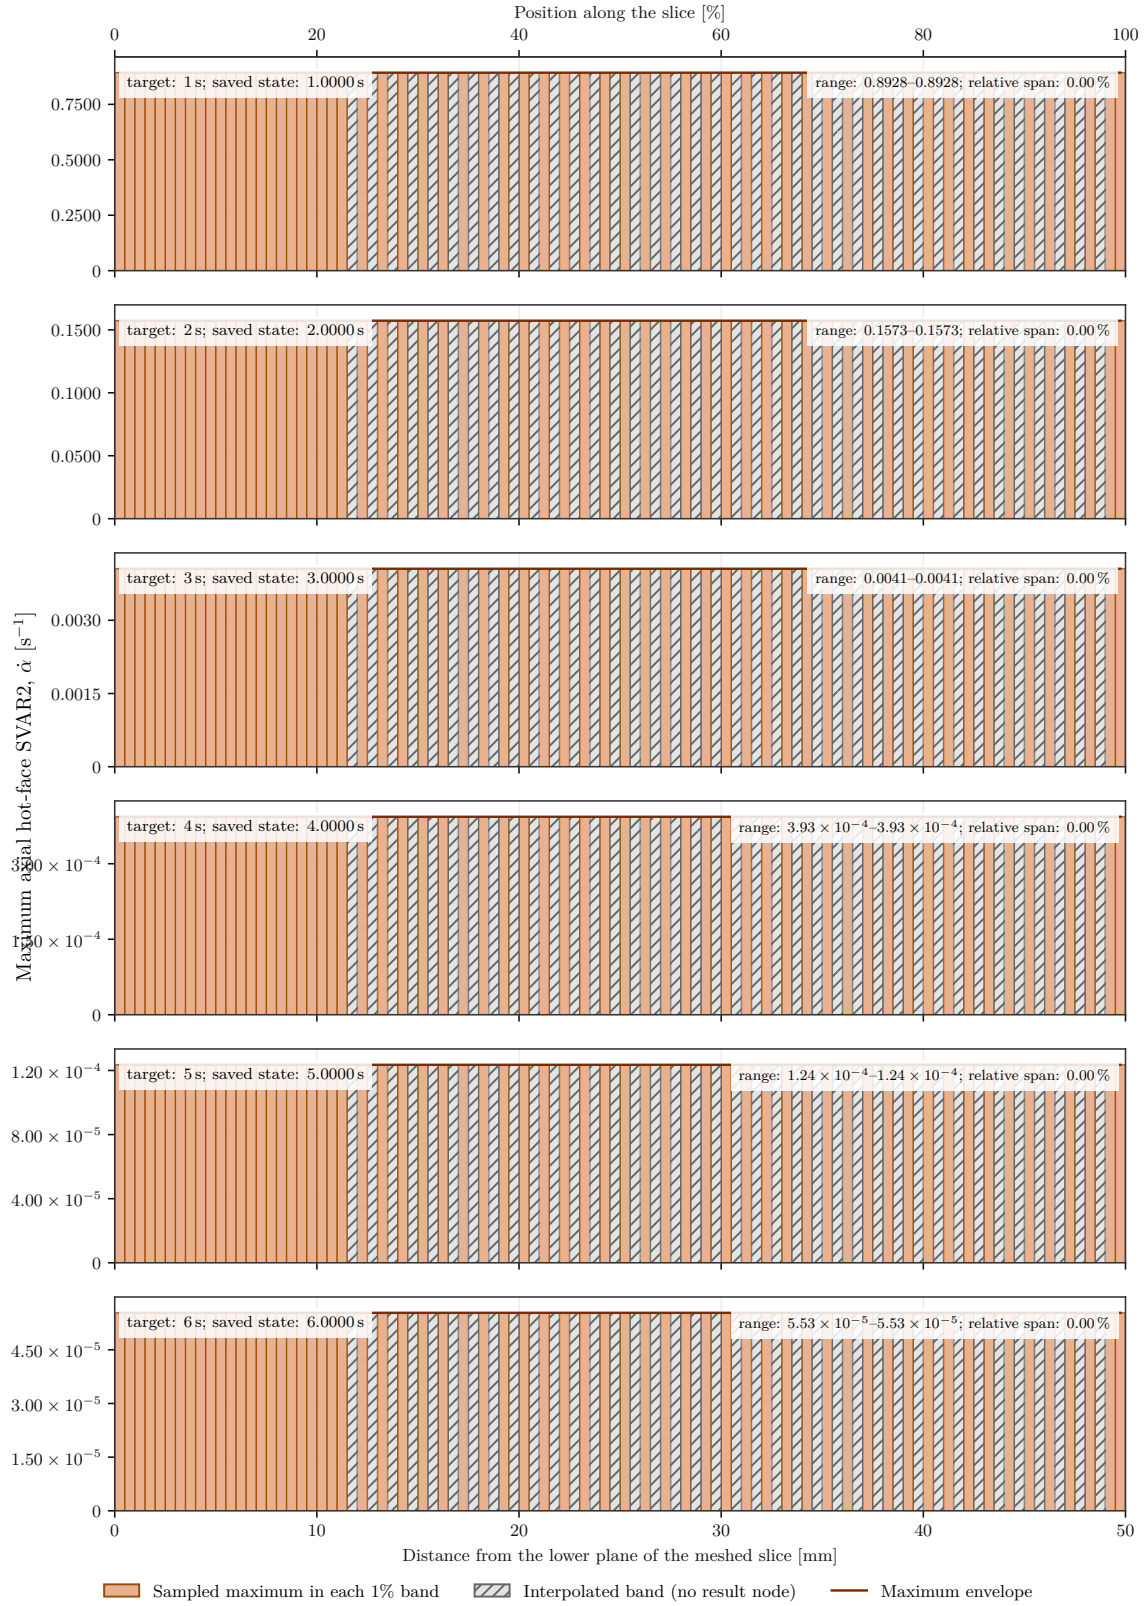


Figure 29. Axial uniformity of SVAR2 along the thin sector's hot face.

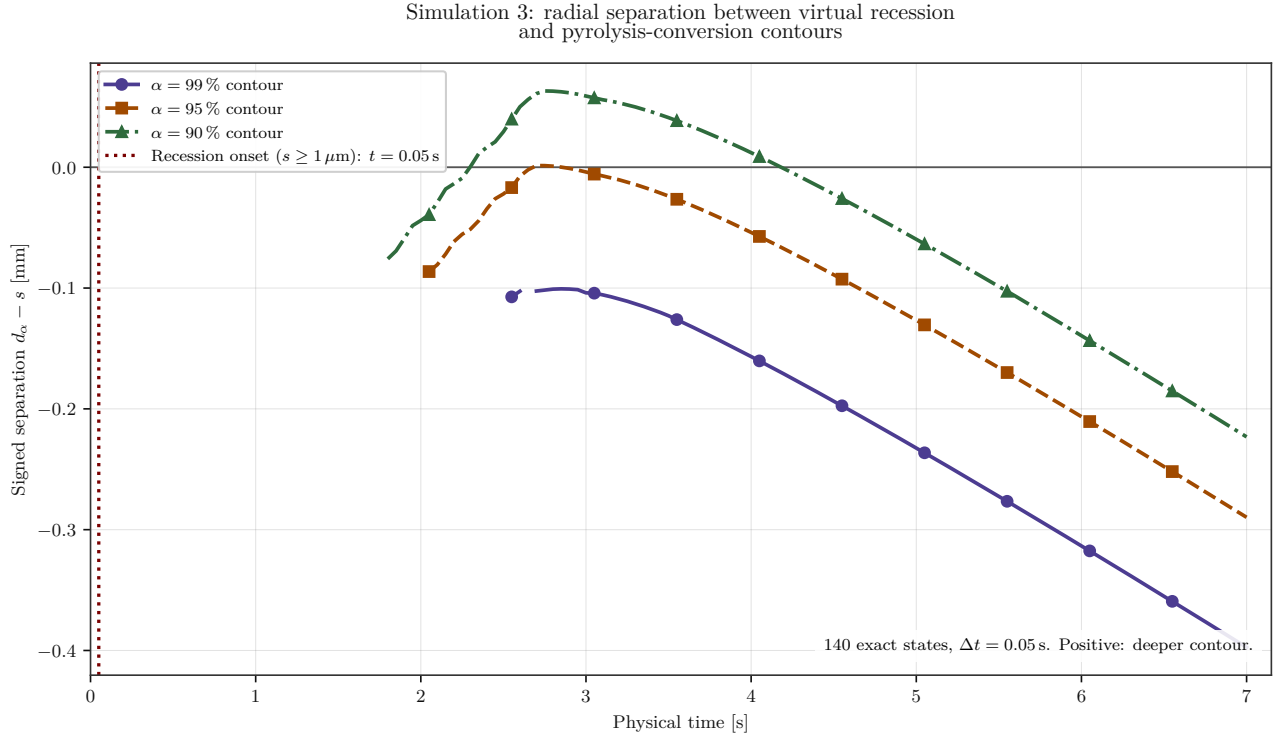


Figure 30. Signed separation between the recession line and the 99%, 95%, and 90% conversion contours over all 140 states. Positive values place the contour deeper into the wall. The vertical line marks the first numerically significant recession.

4.6 Scope and Reproducibility

The Simulation 3 campaign is closed at 7 s. Temporal results come from the synchronized final history and spatial results from the ten stable RTH partitions. Conclusions remain conditional on the material laws, low-temperature property extrapolation, and the numerical criteria $\alpha_c = 0.99$ and $\Delta r = 19.84375 \mu\text{m}$. They do not, by themselves, constitute experimental validation of ablation. All CSV files and bilingual figures in this section can be reproduced from the preserved final result files.

References

- [1] ANSYS, Inc., *UserMatTh — User-Defined Thermal Material Model*, Mechanical APDL Programmer’s Reference, version 2026 R1, https://ansyshelp.ansys.com/public/Views/Secured/corp/v261/en/ans_prog/Z7K4r1e5lcd.html, accessed July 15, 2026.
- [2] ANSYS, Inc., *Using Element Birth and Death*, Mechanical APDL Advanced Analysis Guide, https://ansyshelp.ansys.com/public/Views/Secured/corp/v251/en/ans_adv/Hlp_G_ADV6_2.html, accessed July 15, 2026.
- [3] ANSYS, Inc., *EKILL — Deactivates an element*, Mechanical APDL Command Reference, https://ansyshelp.ansys.com/public/Views/Secured/corp/v242/en/ans_cmd/Hlp_C_EKILL.html, accessed July 15, 2026.
- [4] M. E. Ewing, T. S. Laker, and D. T. Walker, *Numerical Modeling of Ablation Heat Transfer*, NASA NTRS 20140008557, 2013, <https://ntrs.nasa.gov/citations/20140008557>.
- [5] A. J. Amar, N. D. Calvert, and B. S. Kirk, *Development and Verification of the Charring Ablating Thermal Protection Implicit System Solver*, NASA NTRS 20110000471, 2010, <https://ntrs.nasa.gov/citations/20110000471>.
- [6] A. J. Amar, A. B. Oliver, B. S. Kirk, G. Salazar, and J. Droba, *Overview of the CHarring Ablator Response (CHAR) Code*, NASA NTRS 20160005889, 2016, <https://ntrs.nasa.gov/citations/20160005889>.
- [7] R. K. Clark, *A Numerical Analysis of the Transient Response of an Ablation System Including Effects of Thermal Nonequilibrium, Mass Transfer and Chemical Kinetics*, NASA-TM-X-68853, NASA NTRS 19730002381, 1972, <https://ntrs.nasa.gov/citations/19730002381>.
- [8] B. K. Bessire, *Analysis of Pyrolysis Products from Ablative TPS*, NASA NTRS 20230000843, 2023, <https://ntrs.nasa.gov/citations/20230000843>.
- [9] NASA Ames Research Center, *Thermal Protection Materials Branch — Testing and Fabrication*, description of TGA, DSC, and LFA measurements, <https://www.nasa.gov/thermal-protection-materials-branch-testing-and-fabrication/>, accessed July 15, 2026.
- [10] MIT Rocket Team, `motoren.stp`, project AP214 STEP geometry, local file analyzed July 15, 2026.
- [11] MIT Rocket Team, `EngineeringData.xml`, `ds.dat`, `phenolic_pyrolysis_native.apdl`, and `usermatth.F`, local artifacts from the ANSYS Mechanical 2026 R1 simulation, state analyzed July 15, 2026.
- [12] MIT Rocket Team, `file0.rth`-`file7.rth`, `file.nlh`, `file.mntr`, `solve.out`, and `svar1_radial_profile_1pct.csv`, local outputs from the ANSYS Mechanical 2026 R1 simulation, last converged state at $t = 6.38561694$ s, analyzed July 16, 2026.

List of Figures

1	Corrected nominal radial layup. Layer widths are schematic; the stated dimensions are radial thicknesses.	2
2	Local coupling in Simulation 1. Conversion modifies both the heat source and the properties at the following substep.	11
3	Maximum SVAR1 in one-percent radial bands of phe0 at the last converged state. Hatched bands contain no result node and are filled by linear interpolation.	12
4	Evolution of the maximum radial SVAR1 in phe0 for the saved states closest to 1 through 6 s. The six plots are stacked vertically and use identical axes. The dotted lines and points mark the depths of the 0.80, 0.90, and 0.95 isoconversion levels when they are reached.	13
5	Evolution of the maximum radial SVAR2 in phe0, for the saved states nearest 1 to 6 s. Every panel uses the same vertical scale; hatched bands contain no result node and are linearly interpolated.	15
6	Axial dependence of SVAR1 on the hot inner surface of phe0, measured from the lower plane of the meshed slice. All six panels use the same $0 \leq \alpha \leq 1$ scale.	17
7	Axial dependence of SVAR2 on the hot inner surface of phe0. The vertical scale is independent in every panel so that the small late rates remain visible; absolute values, not relative bar heights between panels, must be compared.	18
8	Proposed physical sequence for Simulation 2 in Mechanical. Element deactivation is driven by recession, not directly by SVAR1.	22
9	Accumulated virtual recession versus physical time. The curve is updated from fully synchronized states.	26
10	Mean recession rate over the 135,900 inner-surface nodes. Error bars represent spatial $\pm 1\sigma$.	26
11	Virtual recession versus mean conversion. The curve shows that recession continues after $\bar{\alpha}$ has nearly saturated.	27
12	Recession rate versus mean conversion, with spatial $\pm 1\sigma$.	27
13	Radial maximum-SVAR1 profile at the latest common extracted state, including conversion contours and the virtual-recession line. Hatched bands contain no result node.	28
14	Evolution of the radial maximum of SVAR1 in Simulation 2. The dashed green line in each panel marks the cumulative virtual-recession position.	29
15	Evolution of the radial maximum of SVAR2. Migration of the maximum pyrolysis rate and progression of the virtual-recession line are shown on the same radial coordinate.	30
16	Axial dependence of SVAR1 on the hot inner surface in Simulation 2. No recession line is drawn on the axial axis because recession is defined along the radial coordinate.	31
17	Axial dependence of SVAR2 on the hot inner surface in Simulation 2. An independent vertical scale in each panel reveals the small values after surface saturation.	32
18	Signed radial separation between the virtual-recession line and the 99%, 95%, and 90% pyrolysis-conversion contours. The separation is defined as $\Delta d_\alpha = d_\alpha - s$: a positive value places the contour deeper into the wall than recession. The vertical dotted line marks the first state at which virtual recession reaches 1 μm .	34
19	Mean and minimum conversion recorded in the thin sector's active layer over all 140 converged states. Vertical lines mark the two radial-row deactivations.	36
20	Evolution of outgassing, effective convection coefficient, and maximum hot-surface temperature. Total flow is for the 0.10° sector.	37
21	Accumulated virtual recession versus time for Simulation 3. The vertical lines mark numerical onset of the recession front and both radial-row deactivations.	38
22	Macro-step recession rate. This is a temporal derivative of the controller history, without a spatial standard-deviation bar.	38
23	Accumulated virtual recession versus active-layer mean conversion.	39
24	Macro-step recession rate versus mean conversion.	39
25	Final radial SVAR1 profile at 7 s, including conversion contours and the virtual-recession line.	40
26	Evolution of radial SVAR1 profiles from 1 to 6 s. The recession line is shown in every panel.	41
27	Evolution of radial SVAR2 profiles; the maximum identifies the region where pyrolysis remains active.	42
28	Axial uniformity of SVAR1 along the thin sector's hot face.	43
29	Axial uniformity of SVAR2 along the thin sector's hot face.	44

30	Signed separation between the recession line and the 99%, 95%, and 90% conversion contours over all 140 states. Positive values place the contour deeper into the wall. The vertical line marks the first numerically significant recession.	45
----	--	----

List of Tables

1	Corrected nominal motor dimensions. A radial thickness is half the difference between the outside and inside diameters.	2
2	Dimensions and principal characteristics of the numerical mesh.	3
3	Mesh of the axially truncated domain exported by Mechanical.	5
4	Currently encoded virgin/char property curves for the PHENOLIC_PYROLYSIS material. These are project engineering curves, not yet a certified characterization of the manufactured grade.	6
5	Pyrolysis kinetics used in Simulation 1.	6
6	Temperatures extracted from the last converged state.	11
7	Depth and apparent mean speed of the conversion fronts.	12
8	Time progression of the isoconversion depths computed from the maximum radial envelope.	14
9	Time migration of the maximum radial pyrolysis rate.	16
10	Engineering bracket on conversion and potential gas mass at $t = 6.3856$ s.	19
11	Expected direction of the main biases relative to a real firing.	20
12	Proposed initial parameters for Simulation 2. They must be treated as uncertain variables until they have been characterized.	23
13	Executed numerical configuration for Simulation 2.	24
14	Final numerical performance of the campaign stopped at 6.45 s.	25
15	Simulation 2 snapshots through the last fully synchronized state at 6.45 s.	25
16	Geometry and mesh of the executed Simulation 3.	35
17	Final Simulation 3 performance summary.	36

AI Usage Statement

Artificial intelligence was used to generate portions of this document and to assist with part of its technical content development.