


Instructions of use
for all
SC WearStop
qualities



In case that you have problems to handle
SC WearStop material, please use anytime our
emergency call number:
.-0049-2058-9245-29

1.Storage



SC WearStop is delivered in 25 kg multi-layer paper-bags, one layer of which is polyethylene-coated. Each bag is marked with the name of the product and instructions for use. The material is delivered on pallets, each pallet can carry 1,2 to of SC WearStop. The pallet is covered with shrink-fit film.

SC WearStop must be stored in a dry, ventilated room. the material has limited keeping qualities, approx. 1 year. Bags which containing hard lumps must be scrapped, as they have


probably absorbed moisture.

It is **absolutely necessary** that steel fibres be added. These are supplied also in 25 kg paper bags.

2. General information

SC WearStop consists of a cement-based binder and hard wearresisting aggregate of up to about 4 mm. **The consistency is available for trowelling, casting and spraying.**

3. Demand of the application

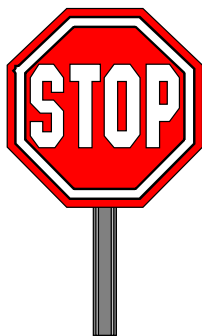

The **optimum temperature** while mixing is as mentioned **between 5 and 30° C. By application under 5° C it is absolutely necessary to use heating equipment during the lining work.** At higher temperature mixing in direct sunshine should be avoided in any case.

4. Preparation of the metal surface

Surface of steel or cast-iron must be cleaned of oil and fat and loose particles. When laying on galvanized surfaces or light alloy such as aluminium, these surfaces must be closed with a diffusionproof paint to avoid a chemical reaction between the metal and the SC WearStop material.


For ease of application and to ensure maximum adhesion, a reinforcement mesh of e. g. expanded metal must be fastened to the metal surface.

For a layer thickness up to 20 mm it is not necessary to use distance rods.

The mesh can directly be welded on the metal surface.

In case of overhanged areas and layer thickness above 20 mm, you have to use distance rods.

5. Mixing SC WearStop qualities

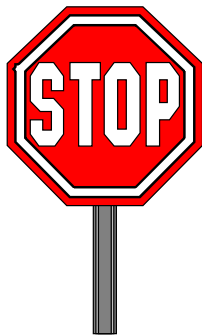

a. Adding water

The water must be so clean that you can drink it. **Under no circumstances may the water be polluted with residues of other cement, argilliferous and calcareous products, other SC WearStop materials or with salts of any kind.**

The optimal outside temperature is 25° C.

Among other things, the water temperature can be used for stabilizing the temperature of the SC WearStop material while mixing. The optimum temperature for mixing is between 10 and 20° C.

At air temperature around 5° C, the water should be between 10- 20° C.

When the temperature exceeds 25° C, the water should be below 5° C.


b. Mixing

Only a paddle/pan mixer may be used. Water must be added to the dry powder while mixing and depending on the efficiency of the mixer, the mixing must last for about **10 min.**, calculated from the commencement of the addition of water.

c. Adding fibres

After mixing for 10 min., a recommended amount of **1,13 kg** of steel fibres per bag SC WearStop should be added and mixing be continued for a further **3-4 min.**

6. Applikation of SC WearStop

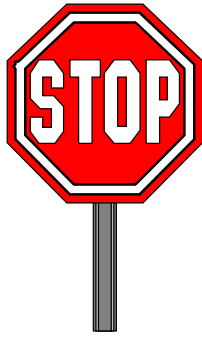


Immediately after finishing the surface, it must be protected against evaporation. This is normally done by spraying on a membrane sealer (curing). A garden spray with its associated nozzle is suitable. Approximately **0,2-0,3 litres per square metre** should be applied. In treating large surfaces with SC WearStop, this sealing process must be carried out in stages. This is especially important when the treatment is being done in surroundings likely to cause rapid drying out.

7. Starting

Given an ambient temperature of 20° C, the material begins to develop its strength after about 10 hours and can be used after about **48 hours**.


Given an ambient temperature of 5° C, a period of about **7 days** must be allowed before it is ready for use.

Recommended reinforcement


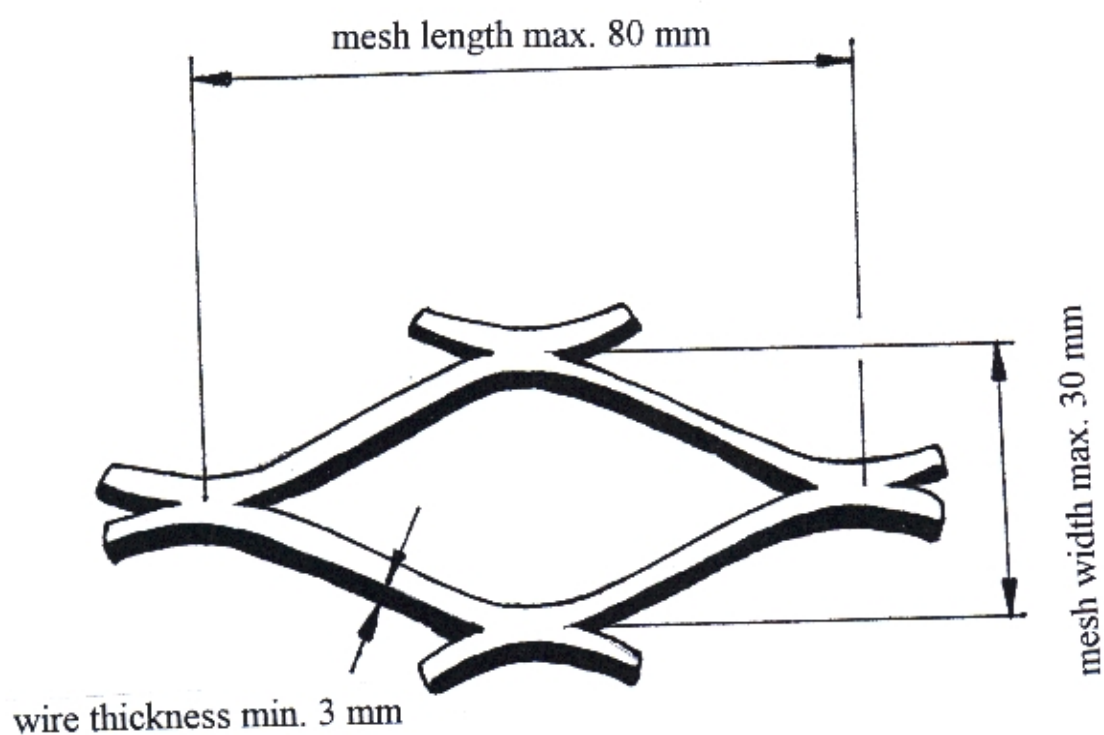


Installation of the reinforcement mesh

Installation without distance rods
by a layer thickness up to 20 mm


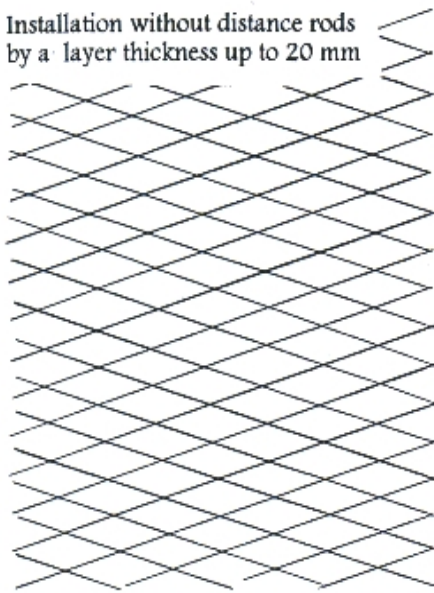


Installation with distance rods
by a layer thickness above 20 mm

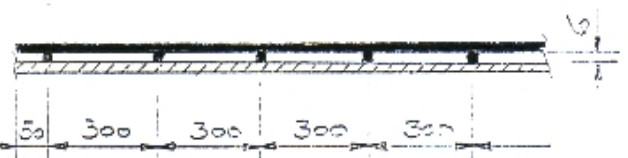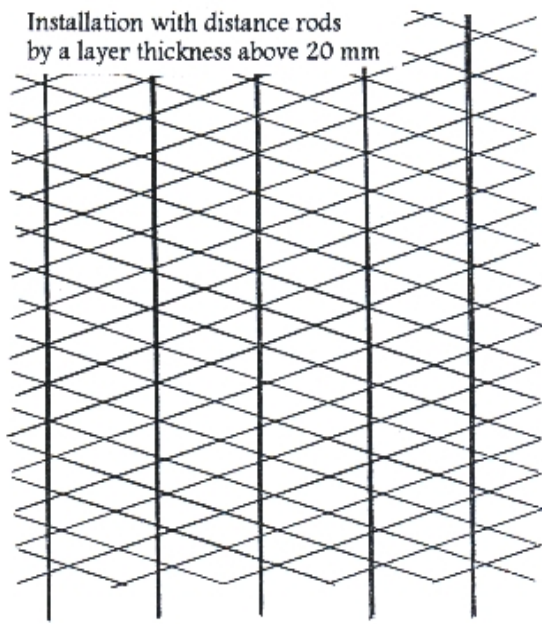

Distance rods
steel 6 x 6 mm

Arealining with reinforcement mesh

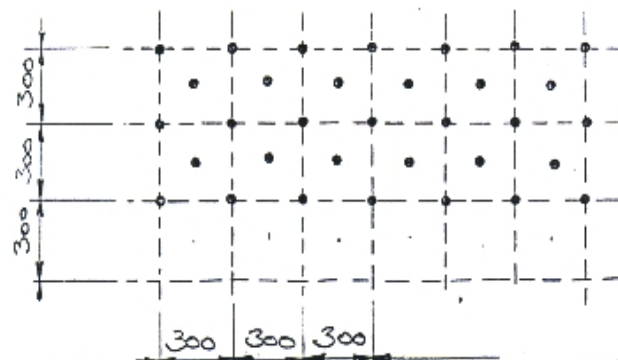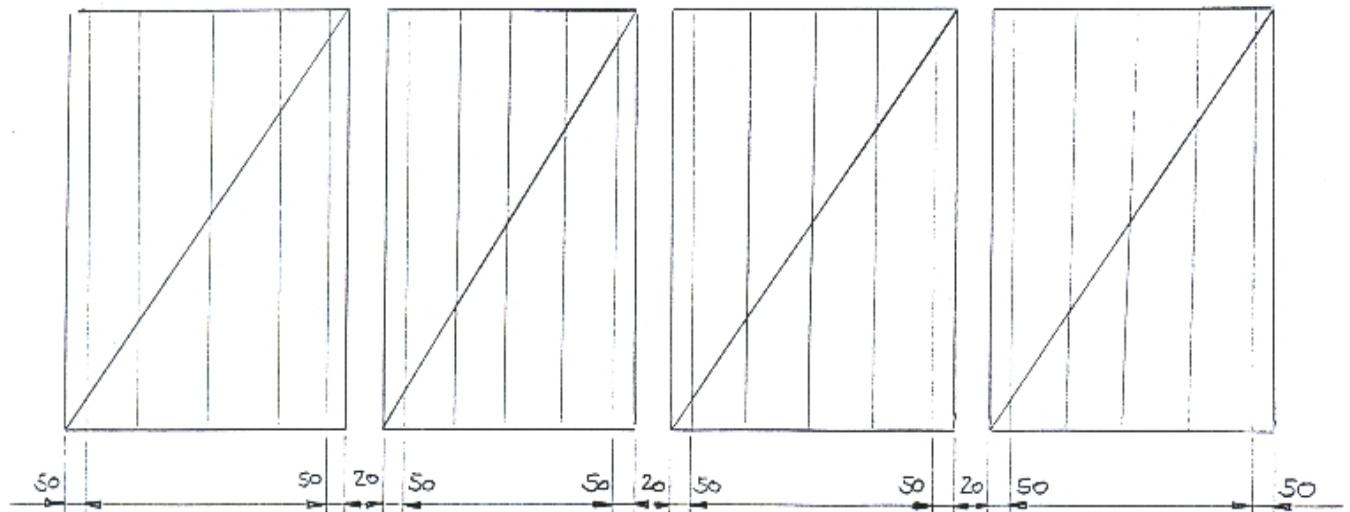

Welding points distance
300 x 300 mm in square



Th. Scholten GmbH & Co. Robert-Bosch-Straße 23-25 Postfach 1450 D-42489 Wülfrath
Telefon (02058) 9245-0 Telefax (02085) 72705