09 Towards Robust Machine-Learned Interatomic Potentials for Radiation-Damaged Waste Immobilization Materials

Rudenko M.A.[1] · Mitrofanov A.A.[1] [1] Chemistry Department, Lomonosov Moscow State University · Mirual02@gmail.com

Nuclear waste forms accumulate strongly non-equilibrium local environments — recoil events, transmutation, defect build-up. Interatomic potentials must stay **stable far from equilibrium** yet accurate for chemically complex oxides: on our distorted perovskite-family set (19 elements, DFT/VASP) force R^2 is 0.65 (MACE-MH-0) / −0.03 (DPA-3.1), and fine-tuning destroys the inherited baseline. We add analytic short-range physics **at inference time, only where the model is provably uncertain**.

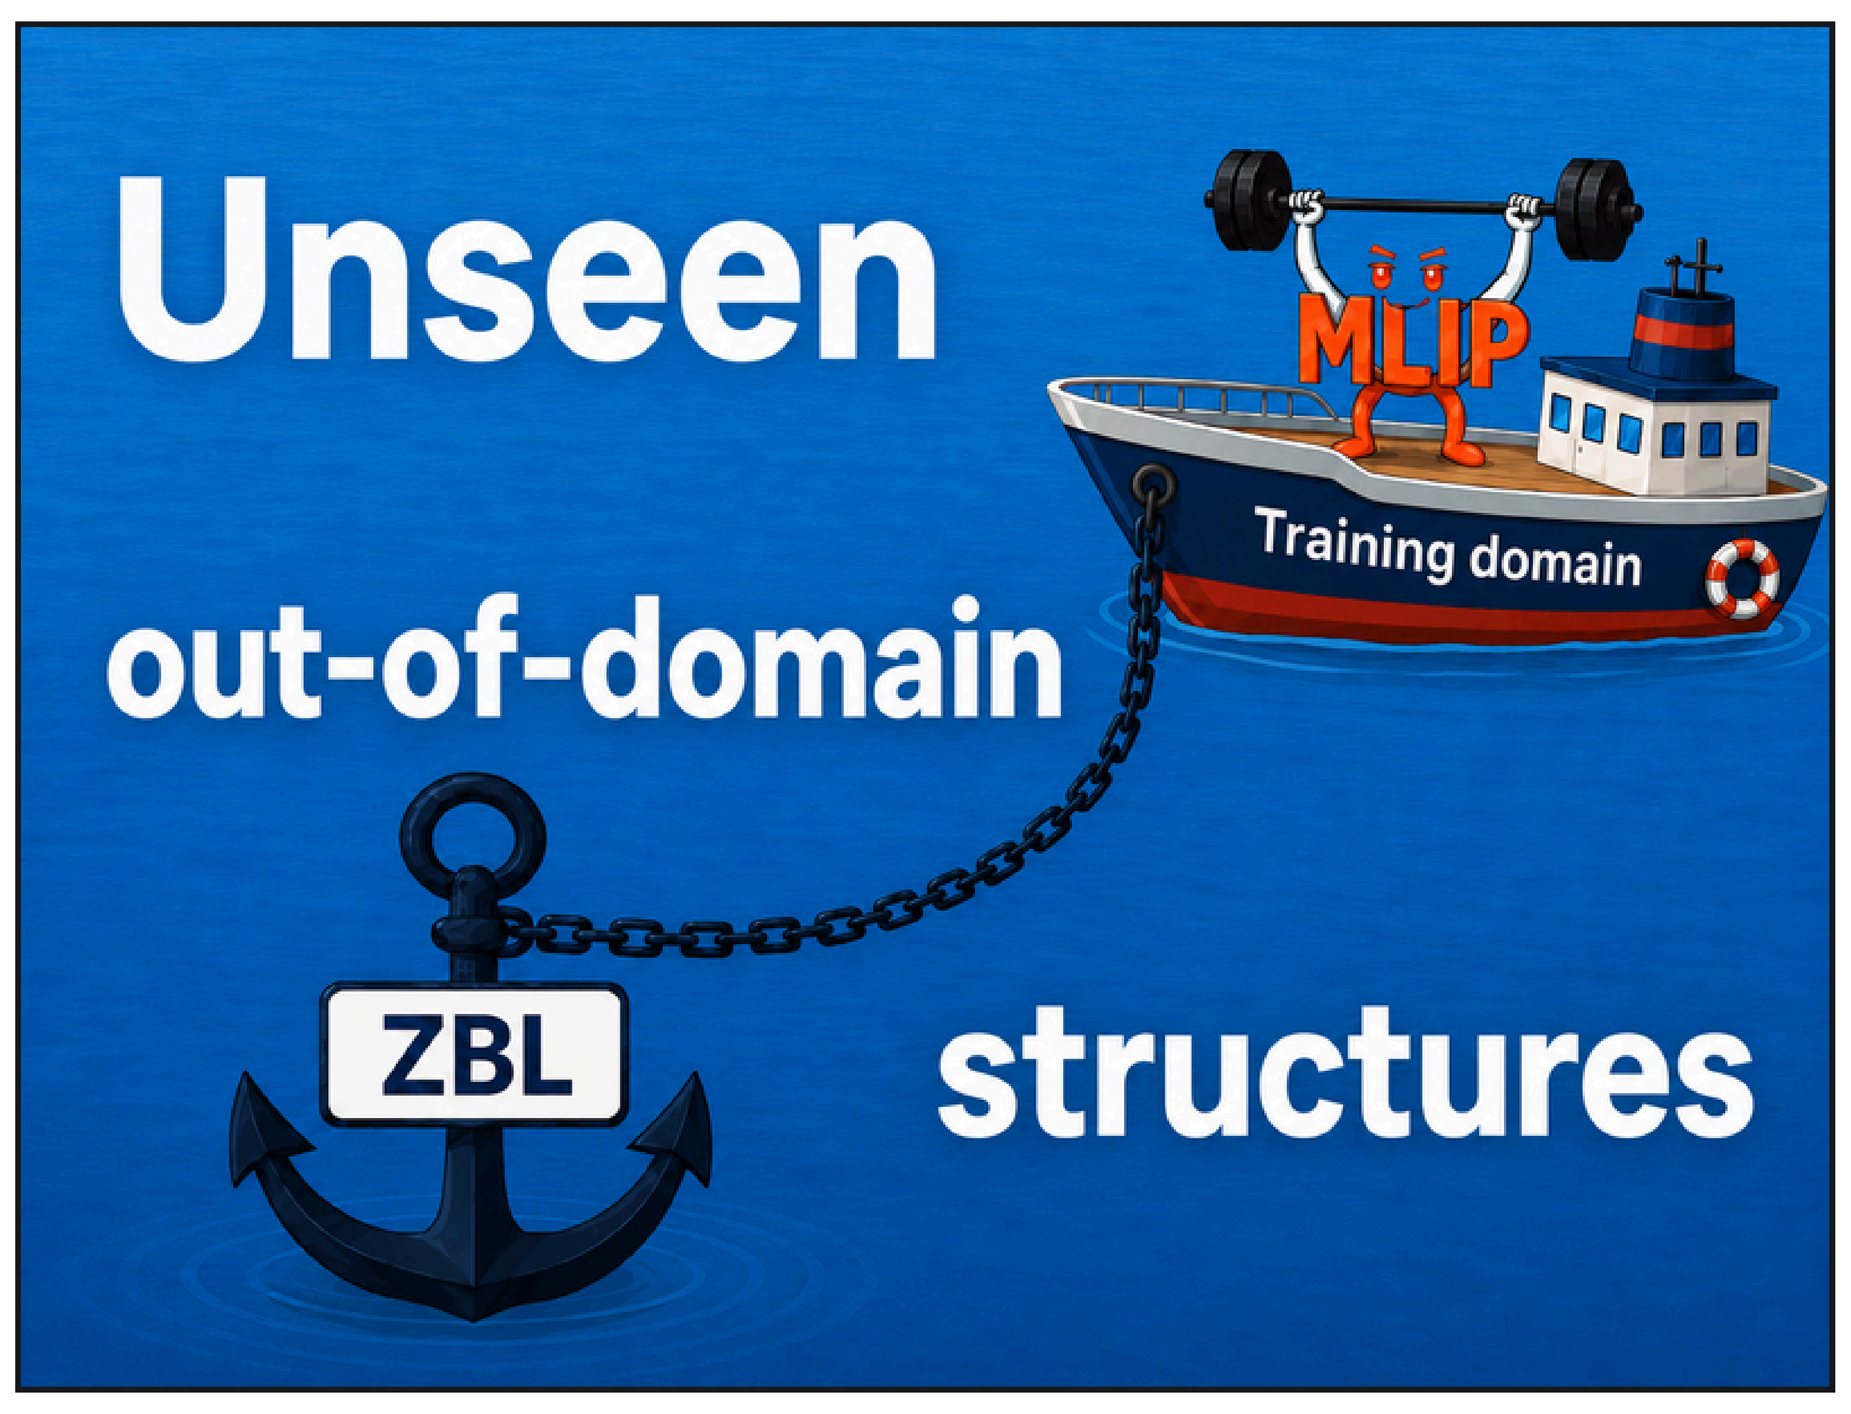

1. Method

`E = E_GNN + Σ w(ρ)·ΔV(r)  ·  F = F_GNN − λ Σ w(ρ)·ΔV′(r)`

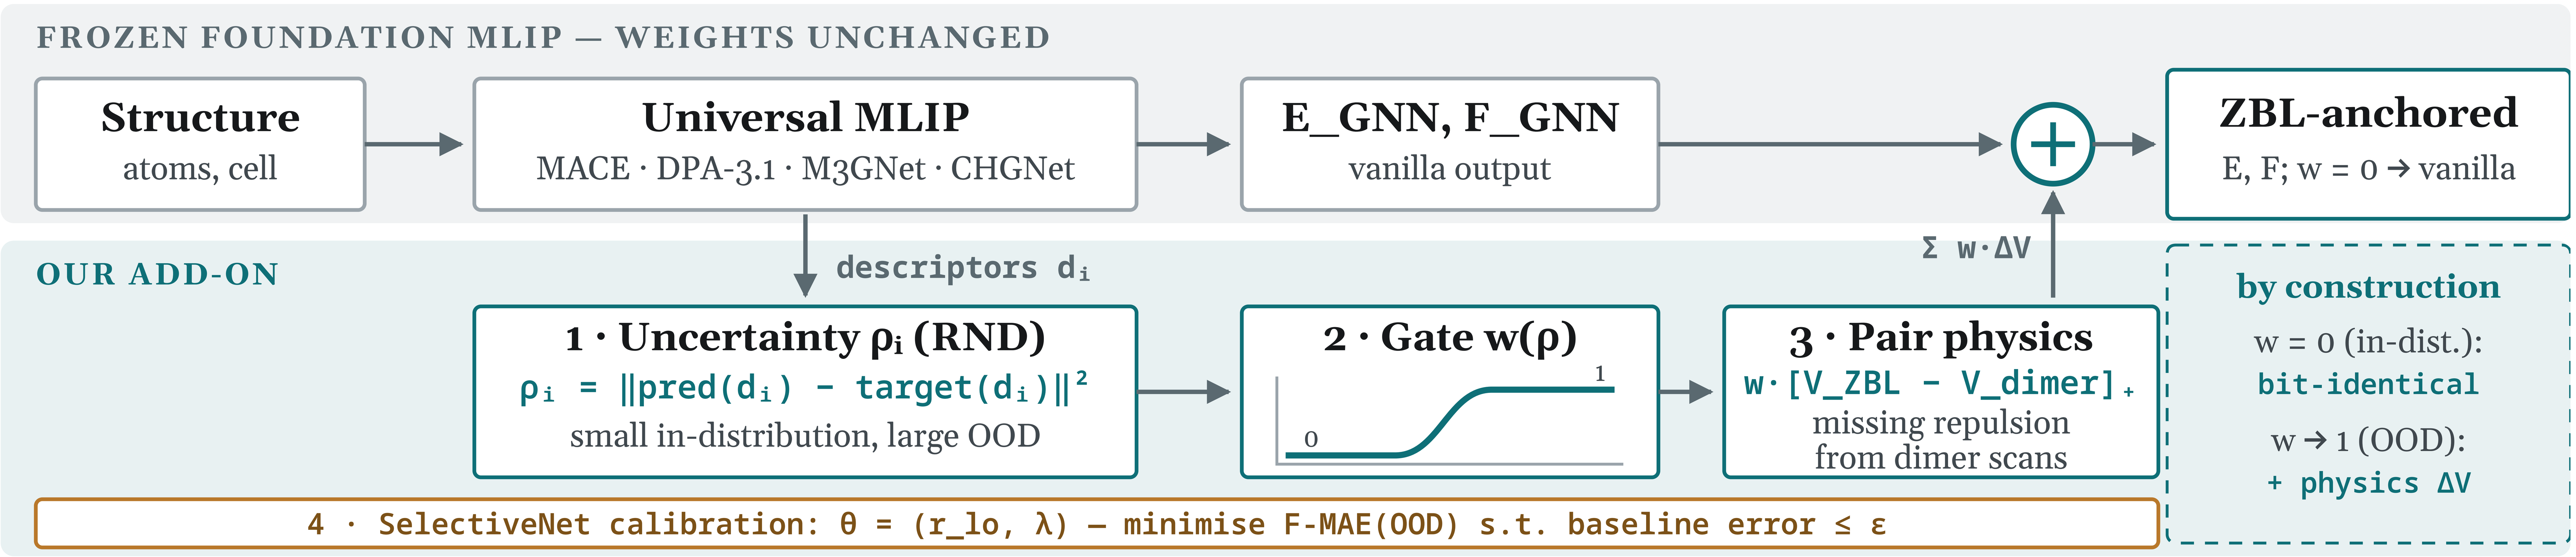

Scheme. Grey — frozen foundation model; teal — the add-on (steps 1–4). Where the gate is silent (w = 0) the output is exactly vanilla — the baseline is preserved bit-for-bit.

2. The gating signal decides everything: RND novelty vs k-NN distance

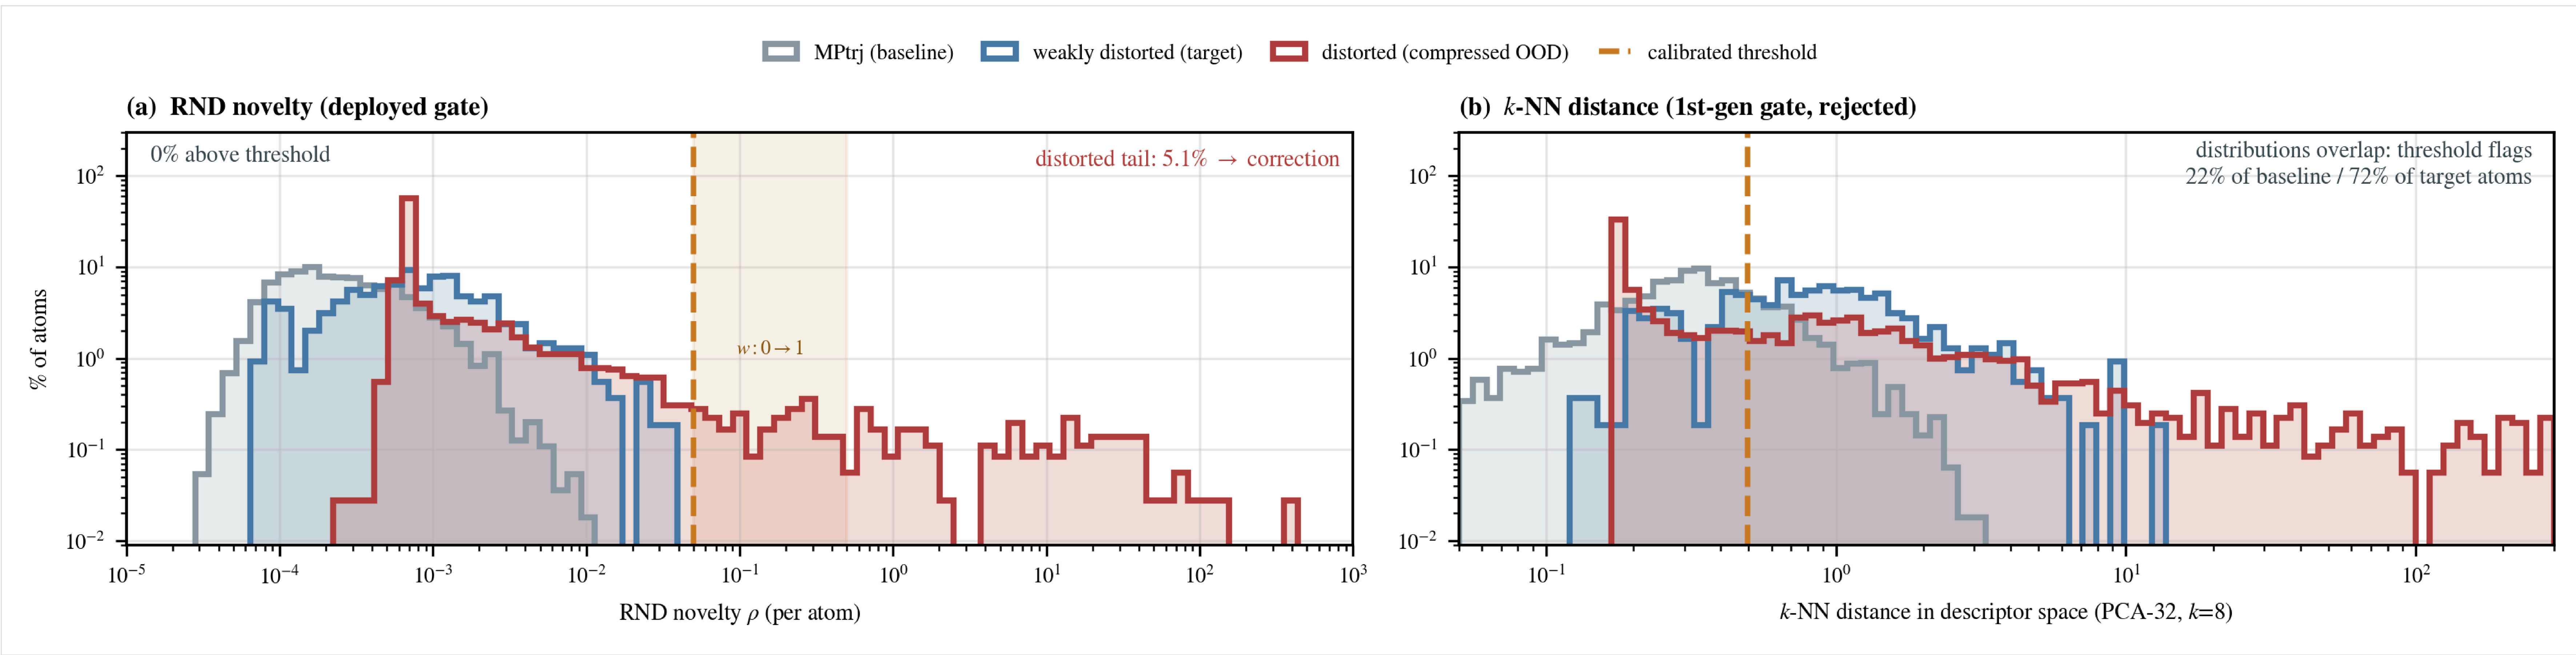

Fig. 1 | Both signals on the same atoms (11 099 baseline / 545 weakly distorted / 3 605 distorted). **(a)** RND separates with zero errors (max baseline ρ = 0.010, weakly distorted 0.037, vs r_lo = 0.05); the distorted tail (5.1%, ρ up to 395) receives the correction; over the shaded band w ramps smoothly to keep forces continuous. **(b)** The k-NN gate overlaps: p_{90} flags 22% of baseline / 72% of the weakly distorted set (force R^2 → −3.0 / −2.0) — rejected.

3. Accuracy on three held-out sets (force R^2, vanilla → anchor)

Model	MPtrj — baseline			weakly distorted — target			distorted (OOD)		distorted ΔF-MAE	overhead (fused)
	vanilla		*anchor*	*vanilla*		*anchor*	*vanilla*	*anchor*		
MACE-MH-0	0.986		0.986	0.998		0.998	0.650	0.829	-6.7%	×1.07
DPA-3.1	0.963	≡	0.963	0.995	≡	0.995	-0.033	0.733	-17.0%	×1.40
M3GNet	0.597		0.597	0.992		0.992	0.104	0.782	-17.1%	×1.17
CHGNet	0.936		0.936	0.990		0.990	0.005	0.014	-1.9%	×1.20

Tinted columns joined by ≡: anchor is bit-identical to vanilla there (gate silent → correction ≡ 0). Descriptor dims: 256 / 128 / 64 / 64. **CHGNet:** the physics works (ungated ZBL 0.36) but its 64-d descriptors give no novelty tail. Composition-disjoint split (MACE): 0.855 → 0.898. Energies excluded on the distorted set (inconsistent E0). Overhead on top of 12.9–50.1 ms vanilla E/F; physics ~2 ms; +1–4 MB.

4. Against fine-tuning

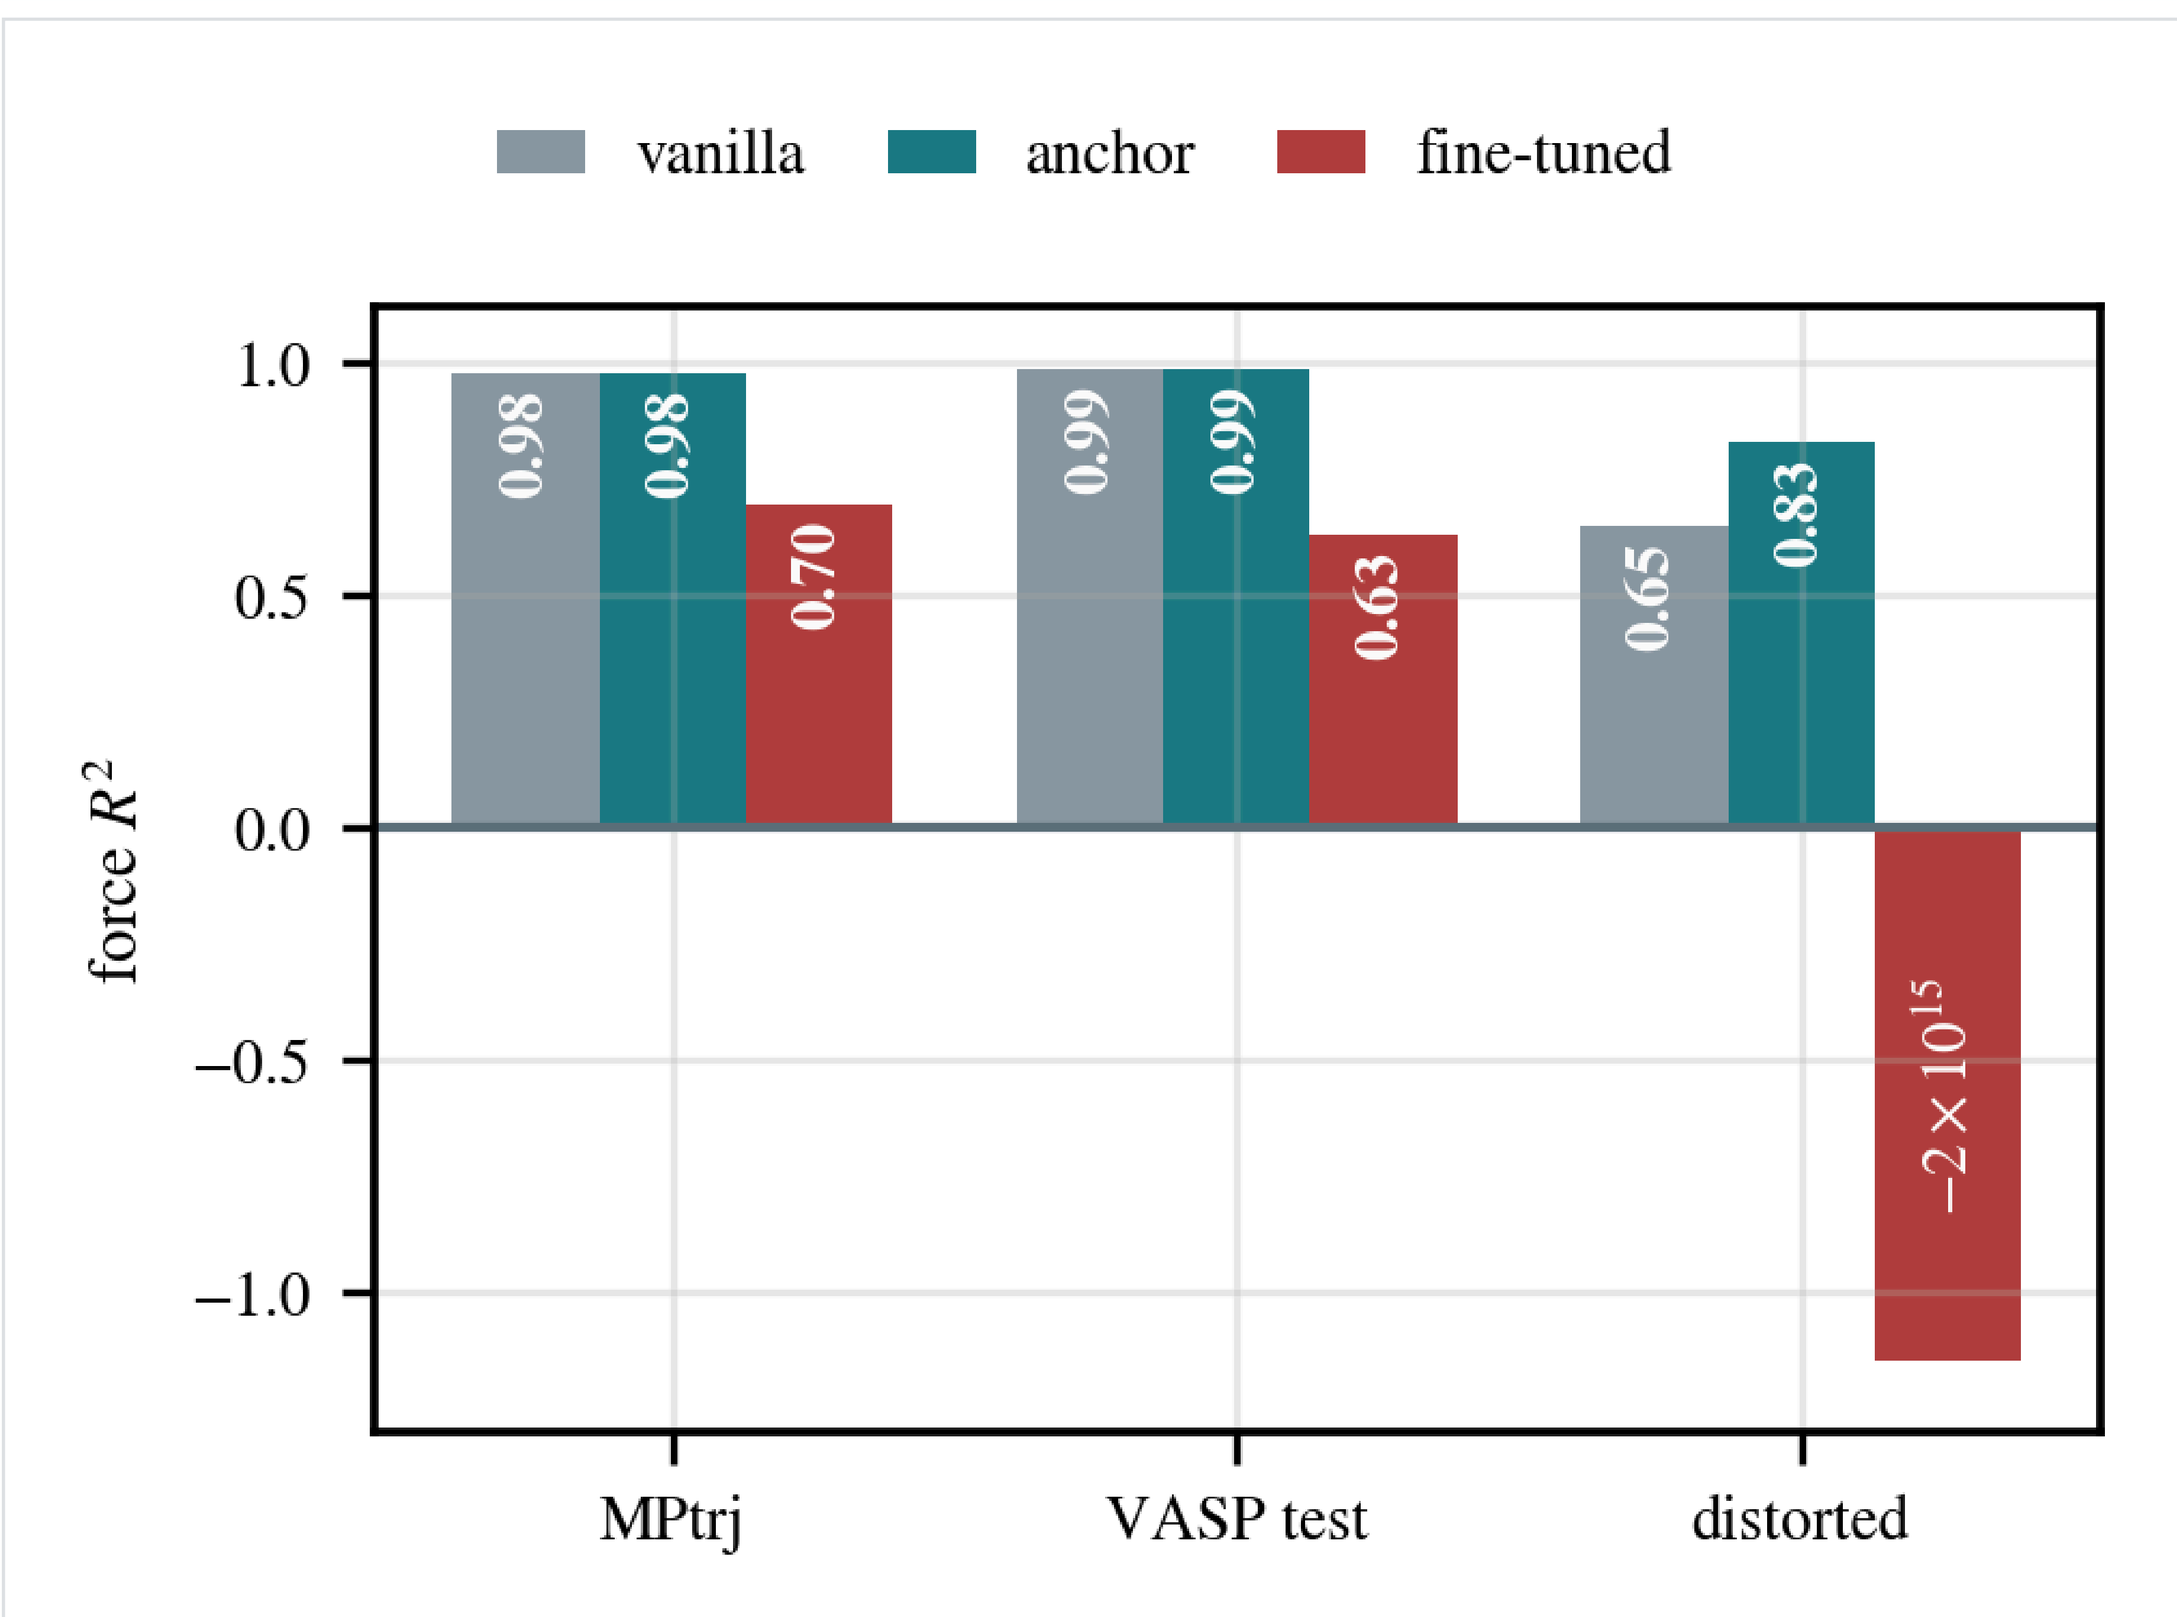

Fig. 2 | Fine-tuning degrades every in-distribution set (MPtrj 0.98 → 0.70, force MAE 0.044 → 0.145 eV/Å; VASP test 0.99 → 0.63), diverges on the distorted set and shrinks element coverage from 89 to 19 species; the anchor stays bit-identical wherever vanilla is good.

5. One recipe, four MLIPs

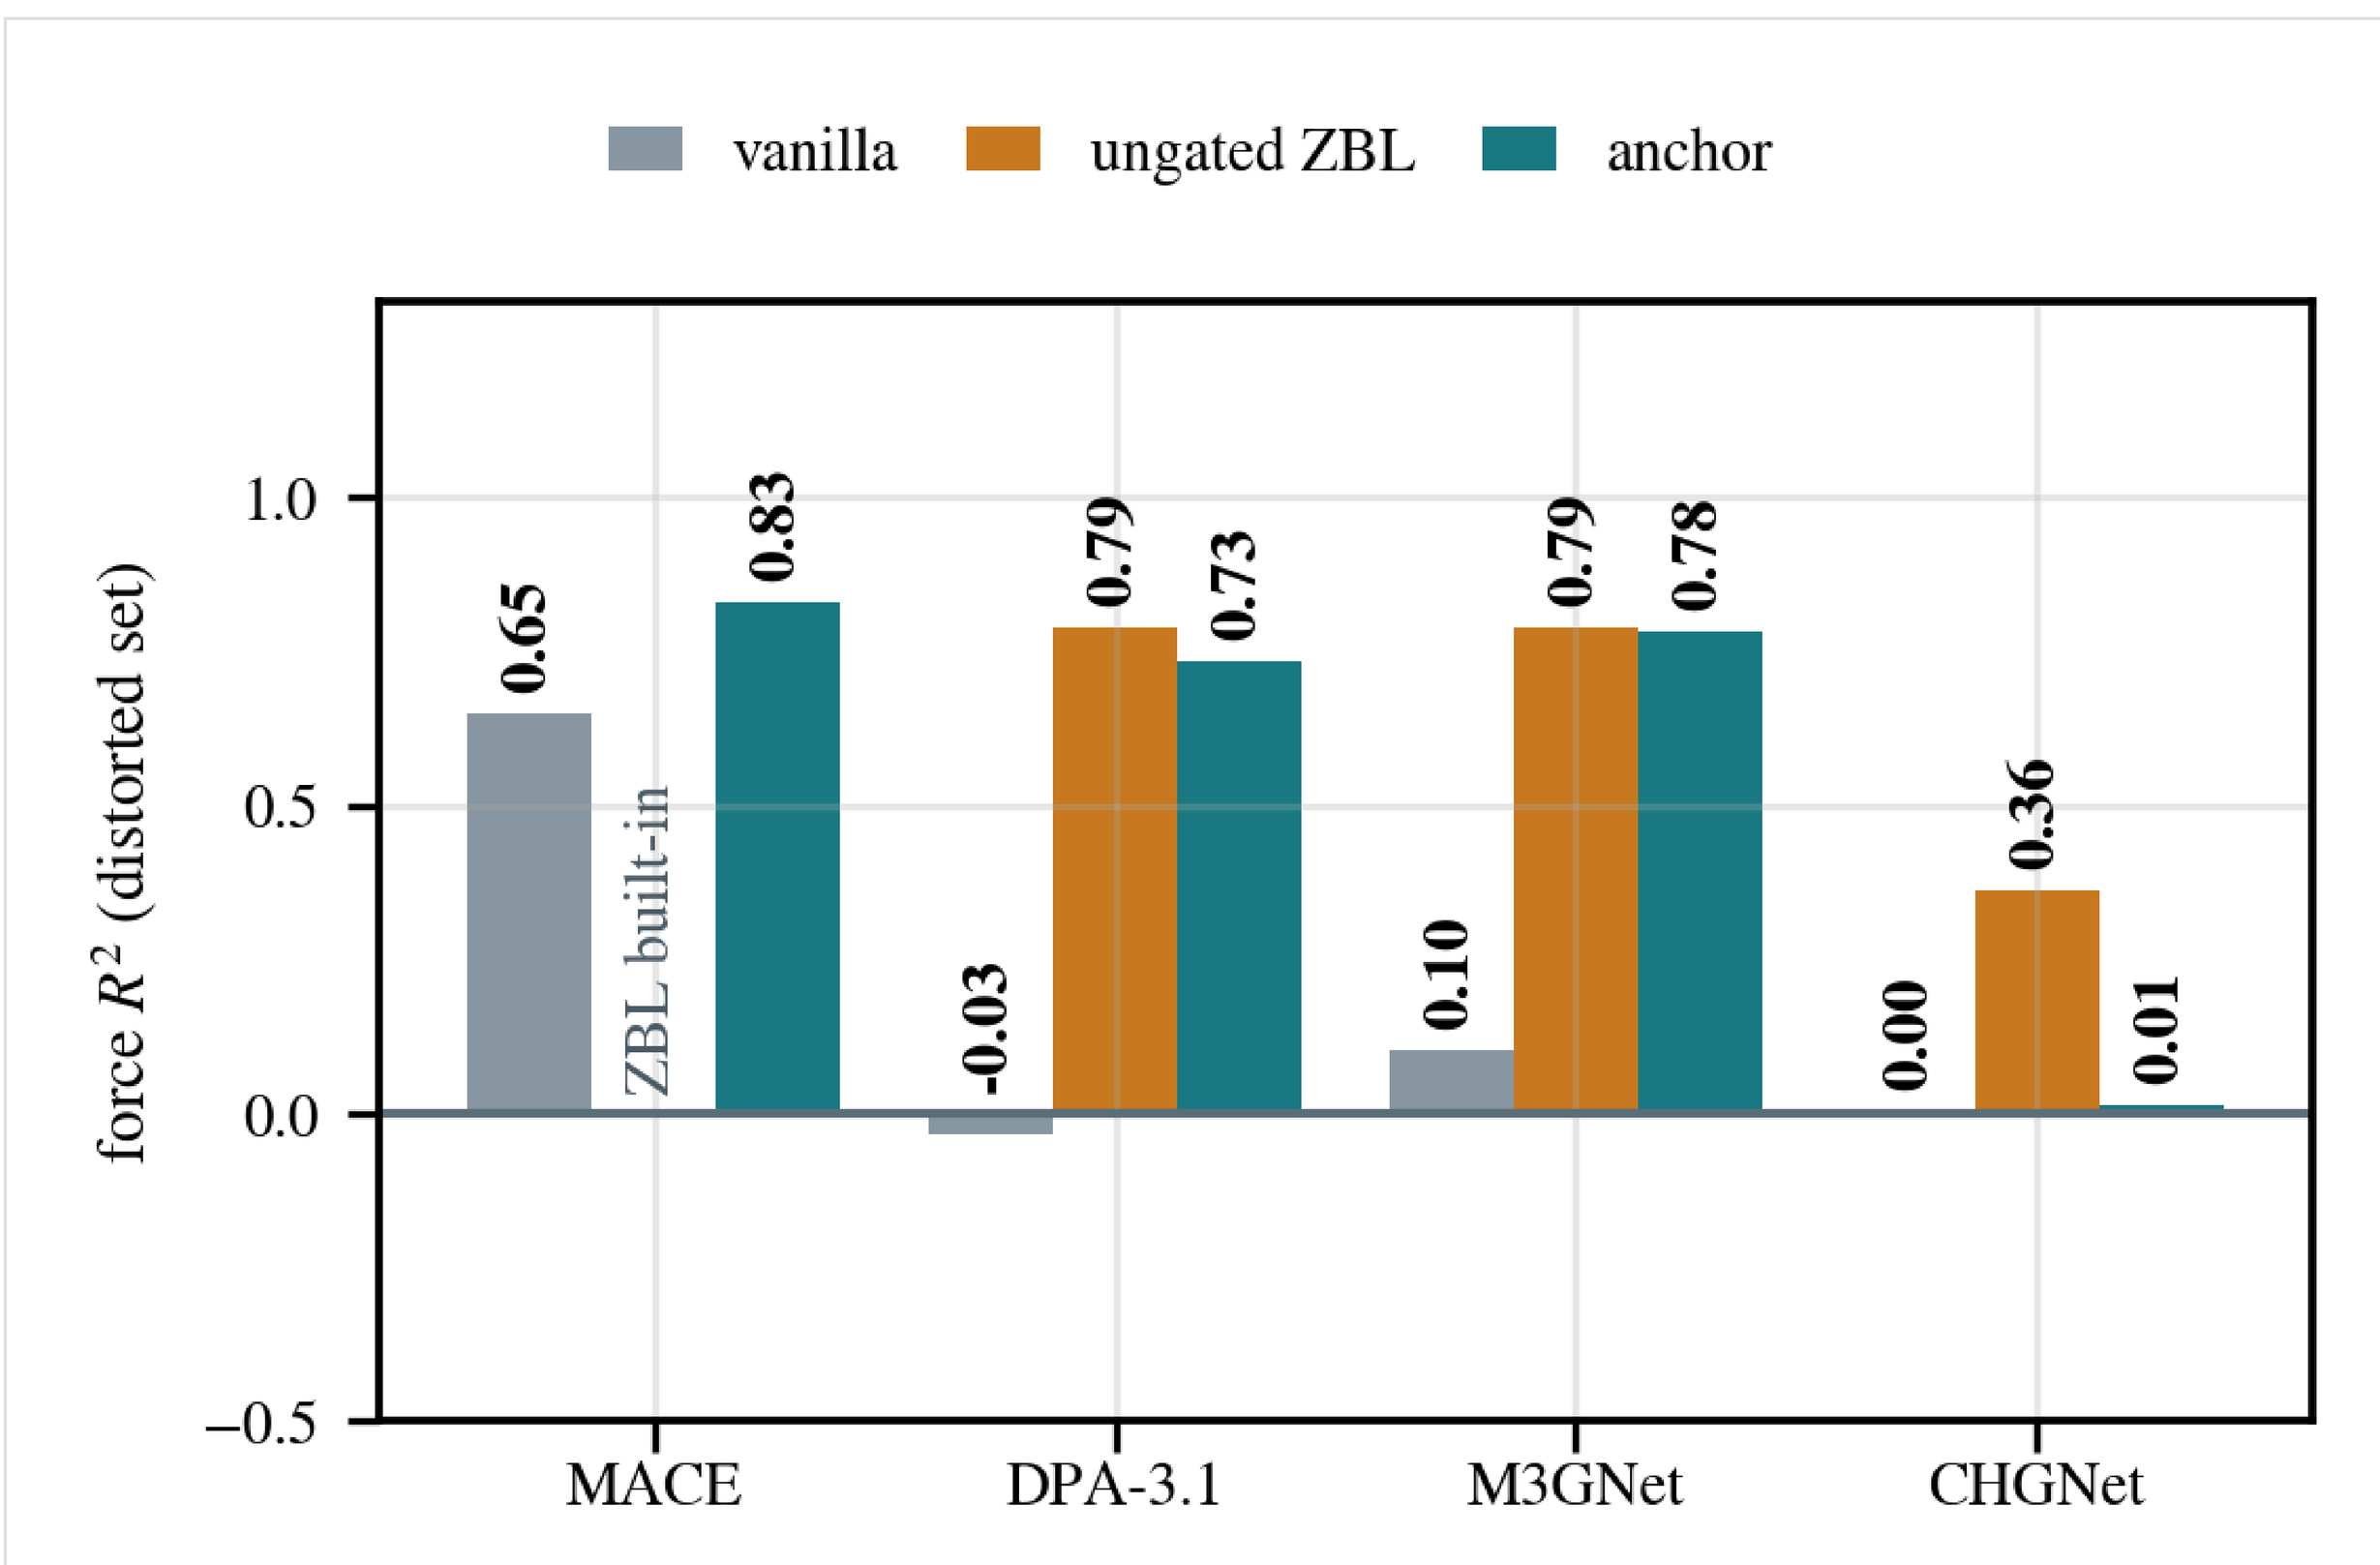

Fig. 3 | Identical pair-physics code on four MLIPs; only descriptors and thresholds are recalibrated. The same ungated ZBL, evaluated on the MPtrj baseline, collapses to force R^2 between −243 and −3609 — without the gate the physics destroys the baseline; the anchor keeps it bit-identical.

6. Compression stress test

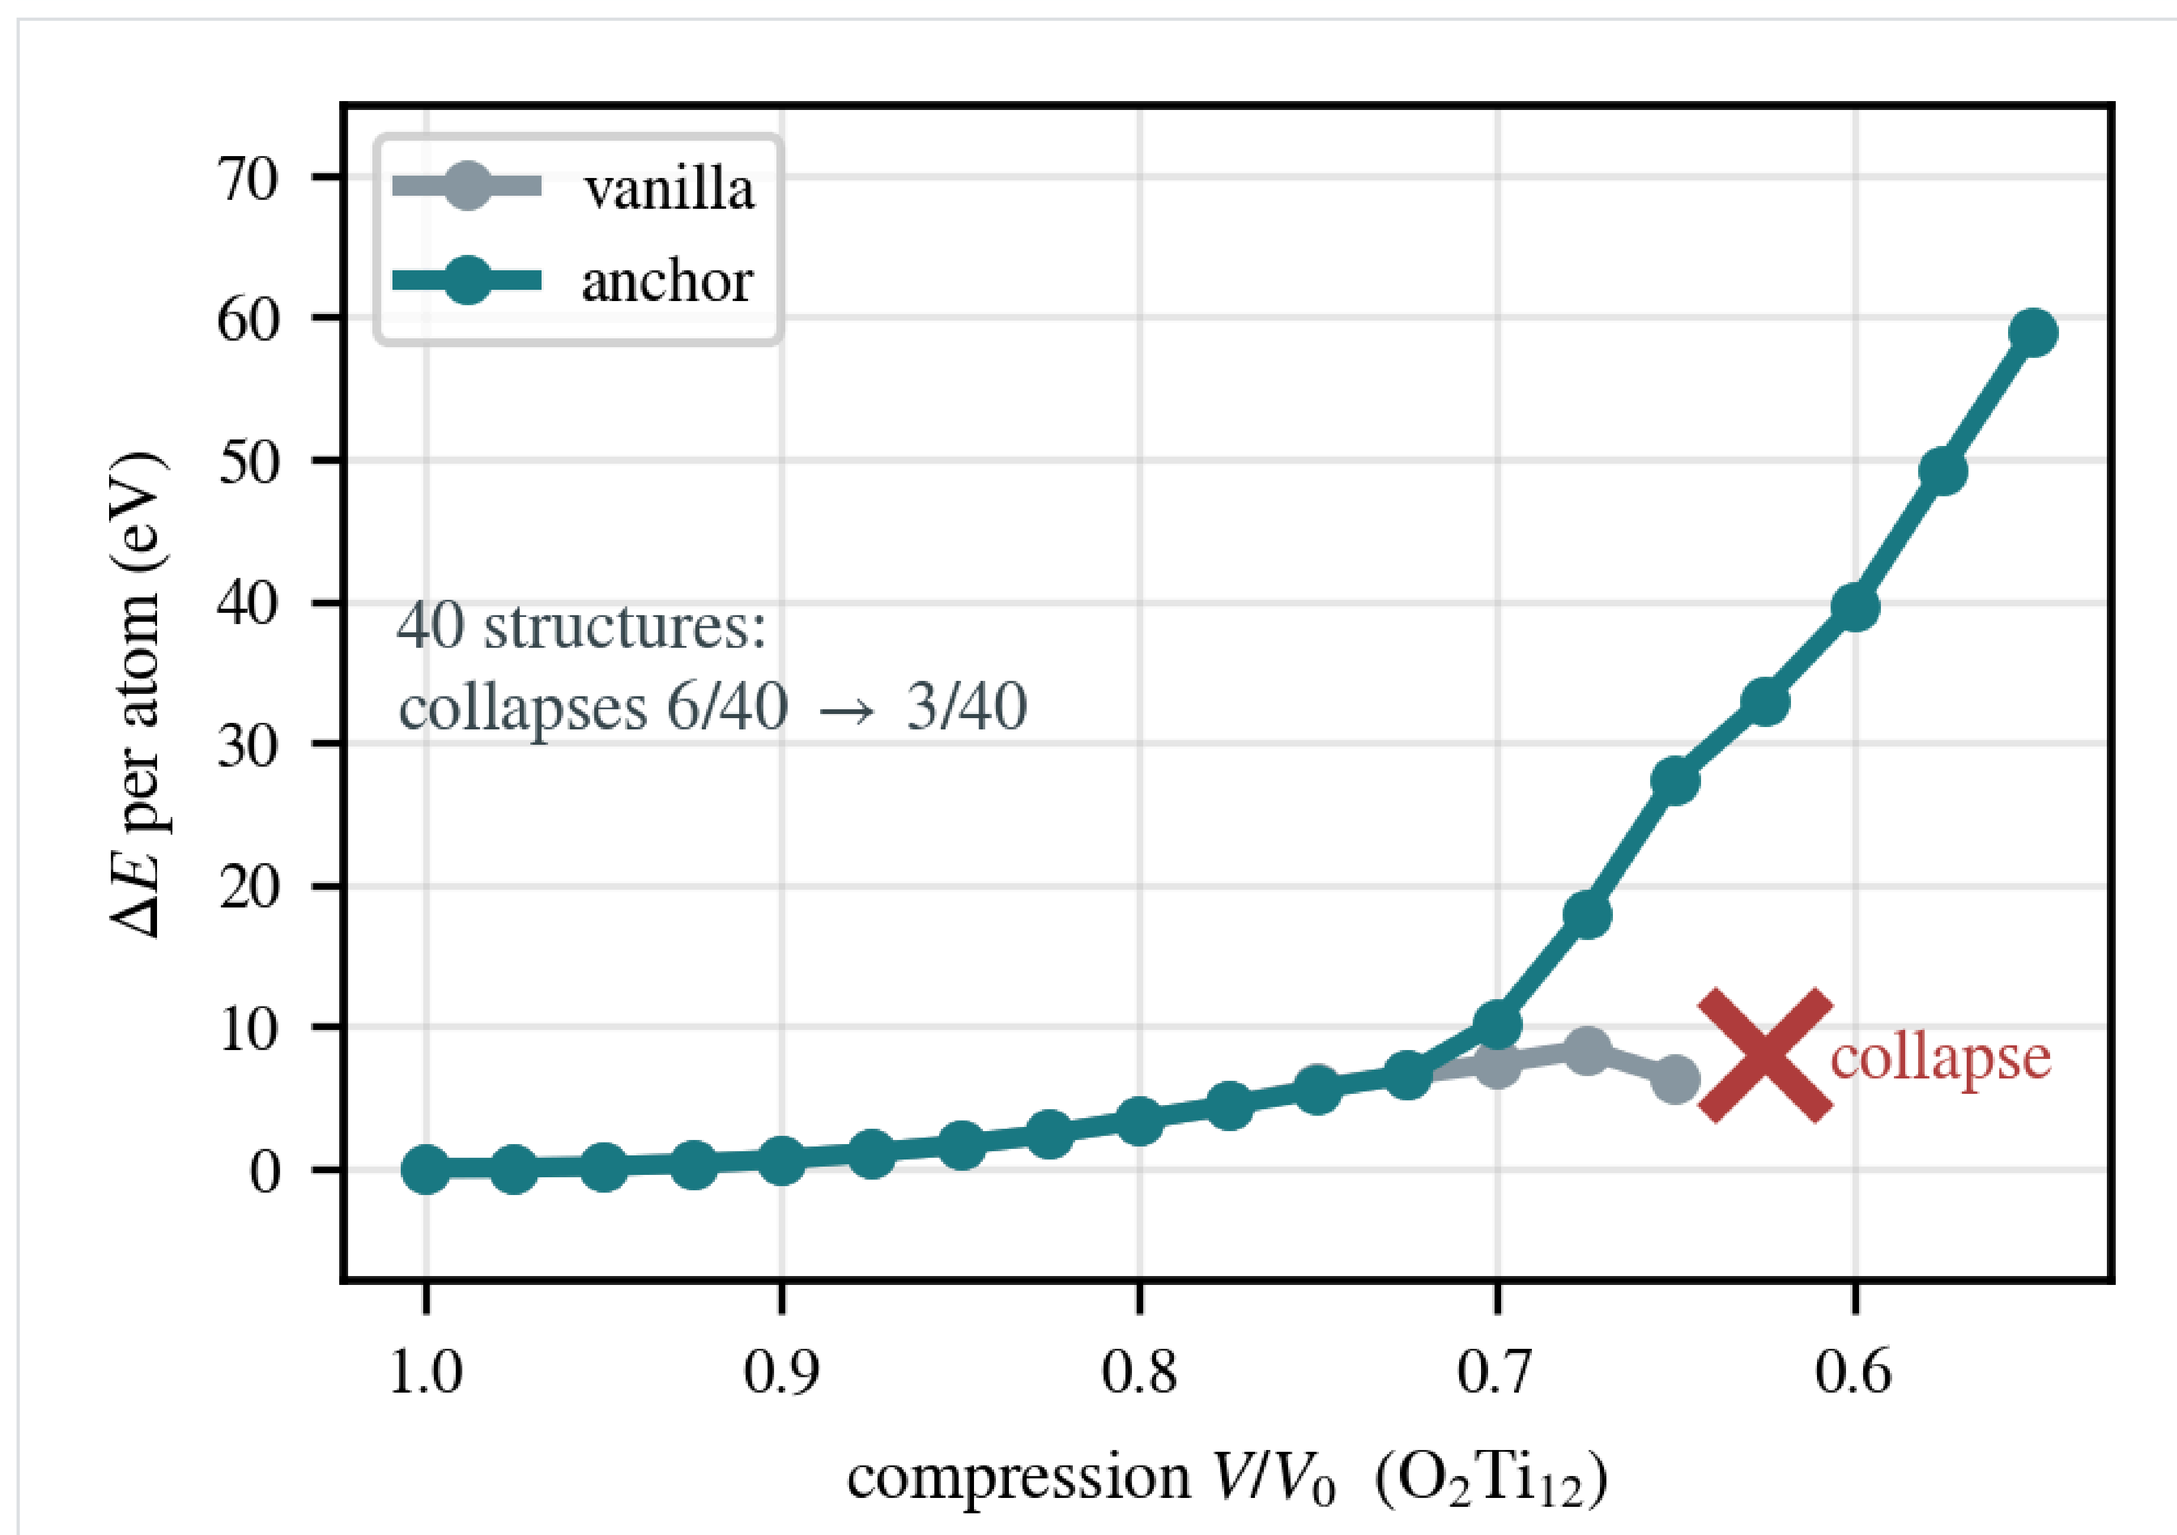

Fig. 4 | Isotropic compression with FIRE relaxation: vanilla collapses at V/V_0 = 0.625 (E → −946 eV/atom, d_min 0.22 Å), the anchored model stays smooth; over 40 structures collapses halve, never worse.

7. Conclusions

OOD forces restored
distorted-set force R^2 **0.73–0.83** on three of four MLIPs, zero weight updates.

Do-no-harm guaranteed
baseline/target bit-identical — in statics and MD; elasticity, WBM, 2-MeV cascades unchanged.

The signal is the method
RND novelty separates (**0%** false positives); k-NN does not; ungated physics destroys the baseline.

Deployment-ready
+1–4 MB, **×1.07–1.4** cost, LAMMPS MD to **70 k** atoms/GPU — groundwork for simulating radiation-induced disorder in waste forms.

[1] Y. Burda et al., Exploration by random network distillation, arXiv:1810.12894 (2018).
[2] Y. Geifman, R. El-Yaniv, SelectiveNet, ICML, arXiv:1901.09192 (2019).
[3] J. F. Ziegler, J. P. Biersack, U. Littmark, *The Stopping and Range of Ions in Solids*, Pergamon (1985).
[4] I. Batatia et al., MACE, NeurIPS, arXiv:2206.07697 (2022).
[5] B. Deng et al., CHGNet / MPtrj, Nat. Mach. Intell. 5, 1031 (2023).
[6] C. Chen, S. P. Ong, M3GNet, Nat. Comput. Sci. 2, 718 (2022).
[7] D. Zhang et al., DPA series, arXiv:2208.08236 (2022); arXiv:2312.15492 (2023).
[8] I. Batatia et al., A foundation model for atomistic materials chemistry (MACE-MP-0), arXiv:2401.00096 (2023).
[9] B. Deng et al., Overcoming systematic softening in universal MLIPs by fine-tuning, npj Comput. Mater. 11, 9 (2025).
[10] K. Nordlund, S. Lehtola, G. Hobler, Repulsive interatomic potentials at three levels of theory, Phys. Rev. A 111, 032818 (2025).
[11] G. Kresse, J. Furthmüller, Phys. Rev. B 54, 11169 (1996) — VASP.
[12] A. P. Thompson et al., LAMMPS, Comput. Phys. Commun. 271, 108171 (2022).
[13] W. J. Weber et al., Radiation effects in crystalline ceramics for the immobilization of high-level nuclear waste and plutonium, J. Mater. Res. 13, 1434 (1998).

github.com/Mirual/ZBL_anchored

researchgate.net/profile/Mikhail-Rudenko-5