

PAPER • OPEN ACCESS

First Principles Study of Molybdenum Disulfide Electronic Structure

To cite this article: Imam Abdul Rahman and Acep Purqon 2017 *J. Phys.: Conf. Ser.* **877** 012026

View the [article online](#) for updates and enhancements.

You may also like

- [Hydrogen evolution on non-metal oxide catalysts](#)
Stephen Rhatigan, Marie-Clara Michel and Michael Nolan
- [A computational study of MoS₂ for band gap engineering by substitutional doping of TMN \(T = transition metal \(Cu\), M = metalloid \(B\) and N = non-metal \(C\)\)](#)
Muhammad Tayyab, Akhtar Hussain, Qurat ul Ain Asif et al.
- [Effect of annealing temperature on the microstructure and optical properties of MoS₂ films](#)
Bianlian Zhang, Zhen Cheng and Yu Meng



The Electrochemical Society
Advancing solid state & electrochemical science & technology

243rd ECS Meeting with SOFC-XVIII

More than 50 symposia are available!

Present your research and accelerate science

Boston, MA • May 28 – June 2, 2023

[Learn more and submit!](#)

First Principles Study of Molybdenum Disulfide Electronic Structure

Imam Abdul Rahman¹, Acep Purqon²

Departement of Physics, Institut Teknologi Bandung

E-mail: ¹imamar@students.itb.ac.id, ²acep@fi.itb.ac.id

Abstract. The study of two dimensional material has gain interest due to unique properties which are different from the bulk precursors. Mono- and few-layered of Transition metal dichalcogenides (TMDCs) has band gap properties between 1-2 eV that suitable of FET devices or any optoelectronic devices. Among TMDCs, Molybdenum Disulfide (MoS₂) has gain interest due to its promising band gap-tuning and transition between direct to indirect band gap properties depends on its thickness. First principles calculation by Density Functional Theory has been performed to study the characteristic of MoS₂ electronic structure. Indirect band gap of MoS₂ lies between point Γ to Γ -K in first brillouine zone, while the direct bandgap lies in point-K. The indirect band gap became larger while the number of layer decreased due to quantum confinement effect in c axis direction. In monolayer MoS₂, the indirect band gap become larger than direct one, band gap properties transitioned from indirect to direct. The unique bandgap properties of MoS₂ can lead into better application in energy devices such as solar cell [11], FET [10], and photoluminescence device.

1. Introduction

The study of two dimensional material has gain interest due to unique properties which are different from the bulk precursors either in its electrical properties also in its optoelectronic properties. This kind of thin material also allowed to make very thin devices since its already two dimensional.

Most viral two dimensional material is graphene that has outstanding electrical properties [9]. Graphene is semi-metal material that has zero band gap. Its good electrical properties allow graphene to be a suitable material for any conductor application. But since graphene has zero bandgap, it can not be applied as semiconductor devices. Whereas a lot of technology developed based on semiconductor properties of material included energy devices such as photoluminescence device, Solar Cell, etc.

TMDCs (Transition Metal Dichalcogenide) group of material can be suitable candidate as two dimensional material that has band gap, since its band gap in range 1 to 2 eV [12]. Among TMDCs, MoS₂ (Molybdenum Disulfide) is the most interesting for its fine electrical and optoelectronic properties in two dimensional state. In bulk, MoS₂ known has 1.29 eV [2] band gap with indirect one yet shifted into 1.8-1.9 eV [7] with direct band gap in two dimensional single layer. This value of band gap allow MoS₂ to be applied in semiconductor based devices, including any energy devices. Several study show MoS₂ application in solar cell [11], FET [10], and photoluminescence devices.

Since its wide use of MoS₂, in this work will be focused in basic properties of MoS₂. This



will show how electronic structure of MoS₂ shifted by its structure and number of layer. This preliminary study using Density Functional Theory (DFT) for identifying theoretical electronic structure shift along its structure change.

2. Method

Structure electronic of material defined by interaction of its all of electron and nuclei. Density Functional Theory calculate these interaction with simplified quantum calculation. In DFT, Kohn Sham Equation used instead of classic Schrödinger equation [3]. K-S Equation shown,

$$\left(-\frac{1}{2}\nabla^2 + \int \frac{n(r')}{|r-r'|} d^3r' + \frac{\partial}{\partial n(r)} E_{xc} + v_{ext} \right) \phi_i = \lambda_i \phi_i \quad (1)$$

Since input of K-S Equation is electron density ($n(r)$) yet $n(r)$ it self is a square of solution wave function ϕ_i , this equation can be solved using Self Consistent Field algorithm. In this

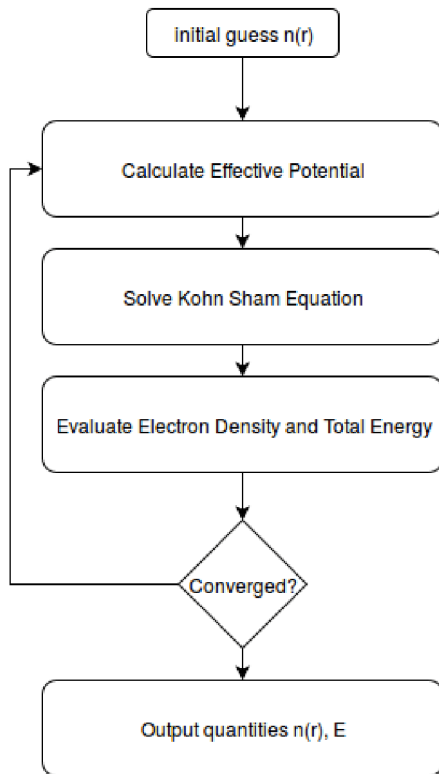


Figure 1. Self Consistent Field Flow Chart. First make initial guest in $n(r)$, then calculate effective potential and solve Kohn Sham Equation. Final step in iteration is to evaluate total energy which are converged or not, if not, make output of electron density as new $n(r)$ and do iteration again.

work PHASE0 package software used to calculate structure electronic of MoS₂. Structural optimization calculated with c/a optimization first then volume optimization. 10^{-9} Hartree used as converged energy criteria in SCF. K-point sampling used is $8 \times 8 \times 8$ for bulk and $8 \times 8 \times 1$ for two dimensional, with 50 Rydberg Wave Function cutoff.

MoS₂ bulk model used as in figure 2. 2H structure is known most stable structure for MoS₂, since 3R structure can be reformed into 2H trough heating [14]. For two dimensional model, single layer and double layer calculated with 15 Å vacuum gap to make sure no interaction between layer. Model shown in figure 3.

3. Result and Discussion

Lattice constant of MoS₂ calculated shown in table 1. It shown also total energy per MoS₂ in 2H structure has lower than in 3R. This show that 2H has more stable structure rather

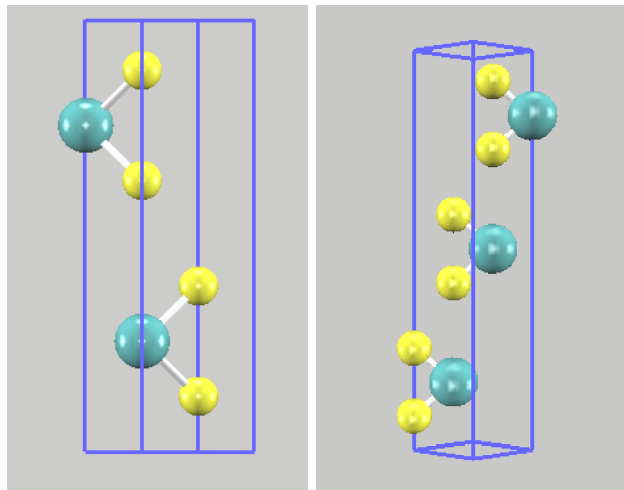


Figure 2. Bulk structure model of MoS₂ with 2H (left) and 3R (right). 2H has 2 molecule of MoS₂ in each cell while 3R has 3 molecule of MoS₂ in each cell.

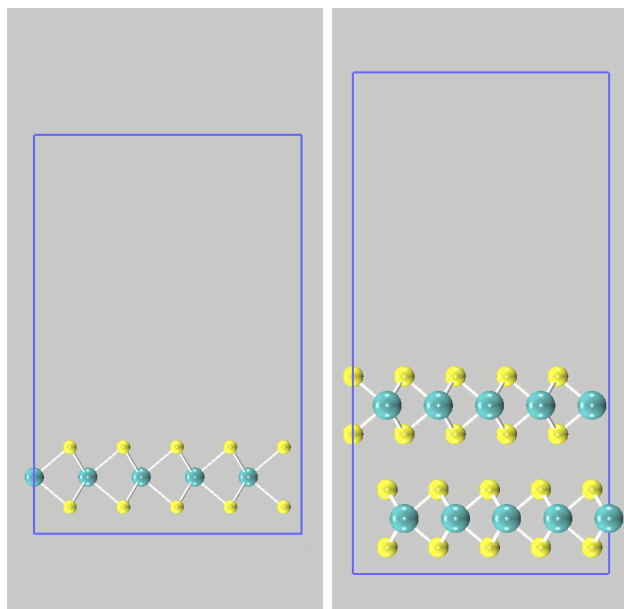


Figure 3. Model for monolayer (left) and dual layer (right) of MoS₂. 15 Å used as vacuum layer for each model.

than 3R. Also provided the comparison table between this work and some reference in table 2. Optimization of lattice constant show very close result for each reference and this work. This show optimization work well enough and can be used to calculate electronic structure of each model.

Table 1. Calculated lattice constant and total energy

	2H	3R
a (Å)	3.22	3.24
c (Å)	13.26	18.92
E (Hartree)	68.021	68.017

Calculated electronic structure represented in band structure and density of states for each structure shown in figure 4, 5, 6, and 7. Comparison of band gap calculation result with some reference shown in table 3. Some of theoretical result lies very close with result of this work,

Table 2. Lattice constant on 2H-Bulk and MoS₂ single layer comparison with some reference

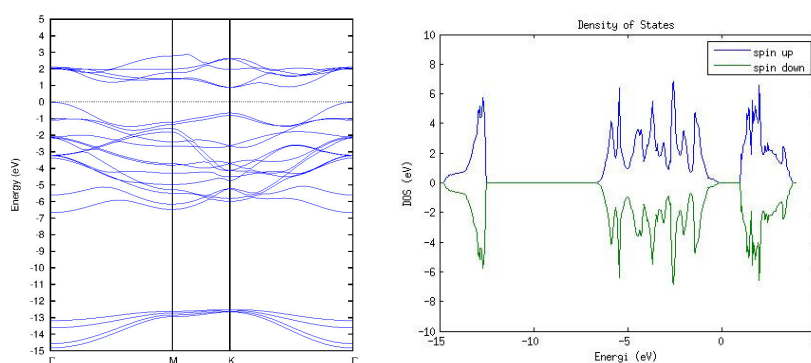
	MoS₂ Bulk		MoS₂ Monolayer	
	Result (Å)	Reference (Å)	Result (Å)	Referensi (Å)
Lattice Constant (a)	3.22	3.19 [1], 3.16 [13]	3.24	3.195 [1], 3.23 [6]
c/a ratio	3.84	3.86 [1], 3.89 [13]		

Table 3. Calculated band gap comparison with some reference

	MoS₂ Bulk		MoS₂ Monolayer	
	Result (eV)	Reference (eV)	Result (eV)	Reference (eV)
		Theoretical Study		Theoretical Study
Bandgap	0.9	0.89 [1], 0.7 [4], 1.15 [8]	1.6	1.57 [1], 1.9 [5]
		Eksperimen		Eksperimen
		1.23 [7], 1.29 [2]		1.80 [7]

while other result seems pretty much different. But it show that experimental result show significant shift from theoretical result. Theoretical result gives lower magnitude of band gap than experiment. This shows that DFT can not really be a good estimation in calculation of exact band gap, yet still can be used as preliminary study of band gap and knows the shift trends of band gap while structure of material modified.

From electronic structure shown that 3R structure have larger band gap compared to 2H one. While in 2 dimensional state, band gap of MoS₂ become larger from the bulk one, since in dual layer has 1.26 eV band gap meanwhile it has 1.6 eV in monolayer state. This indicated that band gap of MoS₂ become shifted up while there is few layer only because of quantum confinement effect in c-axis direction. Interesting case in monolayer MoS₂, since the characteristic of indirect band gap that naturally occur in MoS₂ change to direct one in point *K*. This characteristic make MoS₂ more applicable in wide kind of devices. This also shows that band gap of MoS₂ can be tunable with variety of its number of layer. Resume of MoS₂ band gap properties show in table 4.

**Figure 4.** Electronic structure of 2H Bulk MoS₂ represented as band diagram (left) and density of states (right), this shown that 2H structure has 0.9 eV band gap lies between point Γ to $\Gamma - K$. Spin density shown to be very simmetry for spin up and spin down.**Table 4.** Band gap of 2H, 3R, monolayer and dual layer MoS₂

	2H	3R	monolayer	dual layer
Band Gap (eV)	0.9	1.1	1.6	1.26
Band Gap Characteristic	indirect	indirect	direct	indirect

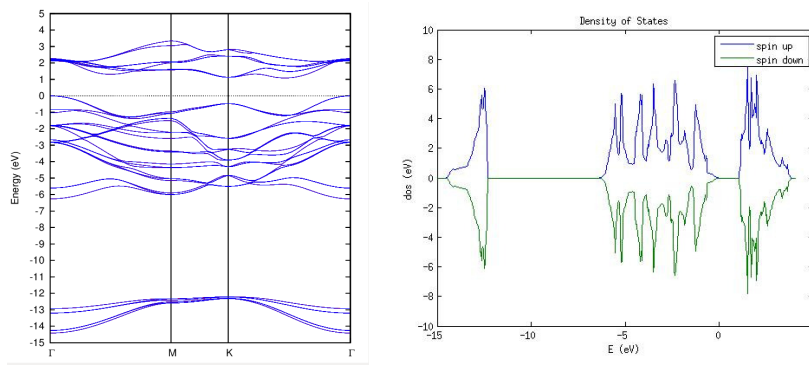


Figure 5. Electronic structure of 3R Bulk MoS₂ represented as band diagram (left) and density of states (right), this shown that 2H structure has 1.1 eV band gap lies between point Γ to $\Gamma - K$. Spin density shown to be very symmetry for spin up and spin down. This characteristic very similar with 2H, but with shifted up band gap.

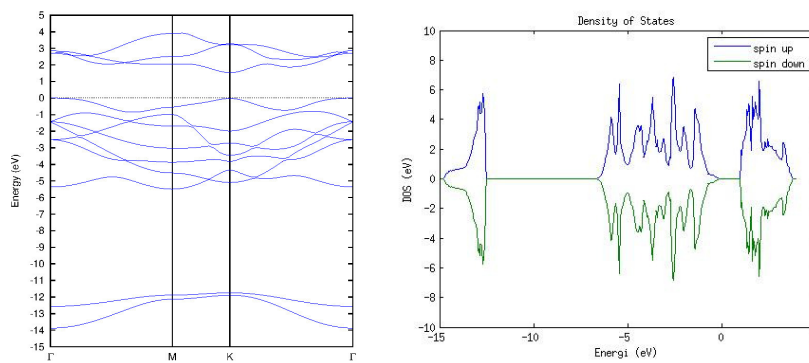


Figure 6. Electronic structure of monolayer MoS₂ represented as band diagram (left) and density of states (right), this shown that 2H structure has 1.6 eV band gap lies between point K to K . Spin density shown to be very symmetry for spin up and spin down. Interesting case within MoS₂ since in bulk phase, it has indirect band gap and yet shifted into direct one that lies in K point brillouin zone.

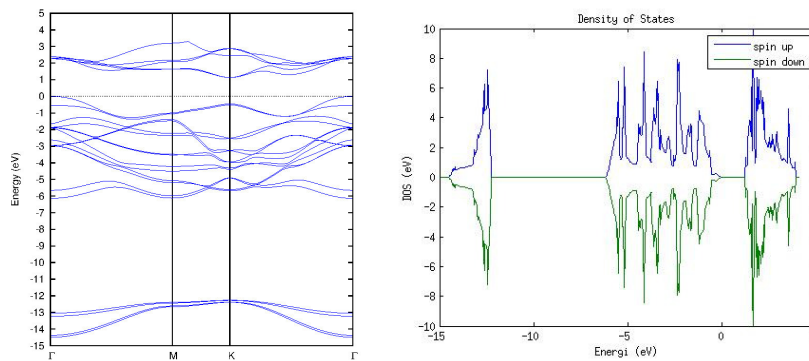


Figure 7. Electronic structure of dual MoS₂ represented as band diagram (left) and density of states (right), this shown that 2H structure has 1.26 eV band gap lies between point Γ to $\Gamma - K$. Spin density shown to be very symmetry for spin up and spin down.

From table 4, it shown that band gap of MoS₂ is varying around 0.9 eV to 1.6 eV. Also it properties is shifted from indirect band gap (bulk) into direct bandgap (monolayer). This unique properties of MoS₂ gives possibility on MoS₂ implementation on energy devices. Band gap with range 1-2 eV is suitable for application on semiconductor energy devices such as solar cell [11] and FET [10]. Also monolayer direct bandgap properties can lead into photoluminescence devices. This also shows that by shifting number of layer, also structure of MoS₂, can be tuned to suit more on energy devices design, which is, still open on future development.

Acknowledgments

The author(s) wish to acknowledge the contribution of LIPI high-performance computing facilities to the results of this research. URL <http://grid.lipi.go.id>.

References

- [1] S. Ahmad and S. Mukherjee. A comparative study of electronic properties of bulk mos2 and its monolayer using dft technique: Application of mechanical strain on mos2 monolayer. *Graphene*, 3:52–59, 2014.
- [2] Th. Böker, R. Severin, A. Müller, C. Janowitz, R. Manzke, D. Voß, P. Krüger, A. Mazur, and J. Pollmann. Band structure of mos₂, mose₂, and α – mote₂ : angle-resolved photoelectron spectroscopy and *ab initio* calculations. *Phys. Rev. B*, 64:235305, Nov 2001.
- [3] K. Capelle. A bird’s-eye view of density-functional theory. *eprint arXiv:cond-mat/0211443*, November 2002.
- [4] Katsuyoshi Kobayashi and Jun Yamauchi. Electronic structure and scanning-tunneling-microscopy image of molybdenum dichalcogenide surfaces. *Phys. Rev. B*, 51:17085–17095, Jun 1995.
- [5] A. Kuc, N. Zibouche, and T. Heine. Influence of quantum confinement on the electronic structure of the transition metal sulfide ts₂. *Phys. Rev. B*, 83:245213, Jun 2011.
- [6] Ashok Kumar and P.K. Ahluwalia. A first principle comparative study of electronic and optical properties of 1h mos2 and 2h mos2. *Materials Chemistry and Physics*, 135(23):755 – 761, 2012.
- [7] Kin Fai Mak, Changgu Lee, James Hone, Jie Shan, and Tony F. Heinz. Atomically thin mos₂: A new direct-gap semiconductor. *Phys. Rev. Lett.*, 105:136805, Sep 2010.
- [8] L. F. Mattheiss. Energy bands for 2h – Nbse₂ and 2h – Mos₂. *Phys. Rev. Lett.*, 30:784–787, Apr 1973.
- [9] K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva, and A. A. Firsov. Electric field effect in atomically thin carbon films. *Science*, 306(5696):666–669, 2004.
- [10] Xin Tong, Eric Ashalley, Feng Lin, Handong Li, and Zhiming M. Wang. Advances in mos2-based field effect transistors (fets). *Nano-Micro Letters*, 7(3):203–218, 2015.
- [11] Meng-Lin Tsai, Sheng-Han Su, Jan-Kai Chang, Dung-Sheng Tsai, Chang-Hsiao Chen, Chih-I Wu, Lain-Jong Li, Lih-Juann Chen, and Jr-Hau He. Monolayer mos2 heterojunction solar cells. *ACS Nano*, 8(8):8317–8322, 2014. PMID: 25046764.
- [12] J.A. Wilson and A.D. Yoffe. The transition metal dichalcogenides discussion and interpretation of the observed optical, electrical and structural properties. *Advances in Physics*, 18(73):193–335, 1969.
- [13] J.A. Wilson and A.D. Yoffe. The transition metal dichalcogenides discussion and interpretation of the observed optical, electrical and structural properties. *Advances in Physics*, 18(73):193–335, 1969.
- [14] Mingxiao Ye, Dustin Winslow, Dongyan Zhang, Ravindra Pandey, and Yoke Khin Yap. Recent advancement on the optical properties of two-dimensional molybdenum disulfide (mos2) thin films. *Photonics*, 2(1):288, 2015.