

IEEE Standard for Pad-Mounted Equipment—Enclosure Integrity for Coastal Environments

IEEE Power and Energy Society

Developed by the
Transformers Committee

IEEE Std C57.12.29™-2023
(Revision of IEEE Std C57.12.29-2014)

STANDARDS

IEEE Standard for Pad-Mounted Equipment—Enclosure Integrity for Coastal Environments

Developed by the

Transformers Committee
of the
IEEE Power and Energy Society

Approved 6 December 2023

IEEE SA Standards Board

Recognized as an American National Standard

Abstract: Conformance tests and requirements for the coating integrity of above grade pad-mounted enclosures for application in coastal environments that contain apparatus energized in excess of 600 V may be exposed to the general public. These include, but are not limited to, the following types of equipment enclosures: pad-mounted capacitors or inductors, pad-mounted distribution transformers, pad-mounted junction enclosures, pad-mounted metering equipment, and pad-mounted voltage regulators.

Keywords: coating integrity, enclosure integrity, IEEE C57.12.29™, pad-mounted equipment, transformers, voltage regulators

The Institute of Electrical and Electronics Engineers, Inc.
3 Park Avenue, New York, NY 10016-5997, USA

Copyright © 2024 by The Institute of Electrical and Electronics Engineers, Inc.
All rights reserved. Published 3 May 2024. Printed in the United States of America.

IEEE is a registered trademark in the U.S. Patent & Trademark Office, owned by The Institute of Electrical and Electronics Engineers, Incorporated.

PDF: ISBN 979-8-8557-0634-5 STD26869
Print: ISBN 979-8-8557-0635-2 STDPD26869

IEEE prohibits discrimination, harassment, and bullying.

For more information, visit <https://www.ieee.org/about/corporate/governance/p9-26.html>.

No part of this publication may be reproduced in any form, in an electronic retrieval system or otherwise, without the prior written permission of the publisher.

Important Notices and Disclaimers Concerning IEEE Standards Documents

IEEE Standards documents are made available for use subject to important notices and legal disclaimers. These notices and disclaimers, or a reference to this page (<https://standards.ieee.org/ipr/disclaimers.html>), appear in all IEEE standards and may be found under the heading “Important Notices and Disclaimers Concerning IEEE Standards Documents.”

Notice and Disclaimer of Liability Concerning the Use of IEEE Standards Documents

IEEE Standards documents are developed within IEEE Societies and subcommittees of IEEE Standards Association (IEEE SA) Board of Governors. IEEE develops its standards through an accredited consensus development process, which brings together volunteers representing varied viewpoints and interests to achieve the final product. IEEE standards are documents developed by volunteers with scientific, academic, and industry-based expertise in technical working groups. Volunteers involved in technical working groups are not necessarily members of IEEE or IEEE SA and participate without compensation from IEEE. While IEEE administers the process and establishes rules to promote fairness in the consensus development process, IEEE does not independently evaluate, test, or verify the accuracy of any of the information or the soundness of any judgments contained in its standards.

IEEE makes no warranties or representations concerning its standards, and expressly disclaims all warranties, express or implied, concerning all standards, including but not limited to the warranties of merchantability, fitness for a particular purpose and non-infringement. IEEE Standards documents do not guarantee safety, security, health, or environmental protection, or compliance with law, or guarantee against interference with or from other devices or networks. In addition, IEEE does not warrant or represent that the use of the material contained in its standards is free from patent infringement. IEEE Standards documents are supplied “AS IS” and “WITH ALL FAULTS.”

Use of an IEEE standard is wholly voluntary. The existence of an IEEE standard does not imply that there are no other ways to produce, test, measure, purchase, market, or provide other goods and services related to the scope of the IEEE standard. Furthermore, the viewpoint expressed at the time a standard is approved and issued is subject to change brought about through developments in the state of the art and comments received from users of the standard.

In publishing and making its standards available, IEEE is not suggesting or rendering professional or other services for, or on behalf of, any person or entity, nor is IEEE undertaking to perform any duty owed by any other person or entity to another. Any person utilizing any IEEE Standards document should rely upon their own independent judgment in the exercise of reasonable care in any given circumstances or, as appropriate, seek the advice of a competent professional in determining the appropriateness of a given IEEE standard.

IN NO EVENT SHALL IEEE BE LIABLE FOR ANY DIRECT, INDIRECT, INCIDENTAL, SPECIAL, EXEMPLARY, OR CONSEQUENTIAL DAMAGES (INCLUDING, BUT NOT LIMITED TO: THE NEED TO PROCURE SUBSTITUTE GOODS OR SERVICES; LOSS OF USE, DATA, OR PROFITS; OR BUSINESS INTERRUPTION) HOWEVER CAUSED AND ON ANY THEORY OF LIABILITY, WHETHER IN CONTRACT, STRICT LIABILITY, OR TORT (INCLUDING NEGLIGENCE OR OTHERWISE) ARISING IN ANY WAY OUT OF THE PUBLICATION, USE OF, OR RELIANCE UPON ANY STANDARD, EVEN IF ADVISED OF THE POSSIBILITY OF SUCH DAMAGE AND REGARDLESS OF WHETHER SUCH DAMAGE WAS FORESEEABLE.

Translations

The IEEE consensus balloting process involves the review of documents in English only. In the event that an IEEE standard is translated, only the English language version published by IEEE is the approved IEEE standard.

Use by artificial intelligence systems

In no event shall material in any IEEE Standards documents be used for the purpose of creating, training, enhancing, developing, maintaining, or contributing to any artificial intelligence systems without the express, written consent of IEEE SA in advance. “Artificial intelligence” refers to any software, application, or other system that uses artificial intelligence, machine learning, or similar technologies, to analyze, train, process, or generate content. Requests for consent can be submitted using the Contact Us form.

Official statements

A statement, written or oral, that is not processed in accordance with the IEEE SA Standards Board Operations Manual is not, and shall not be considered or inferred to be, the official position of IEEE or any of its committees and shall not be considered to be, or be relied upon as, a formal position of IEEE or IEEE SA. At lectures, symposia, seminars, or educational courses, an individual presenting information on IEEE standards shall make it clear that the presenter’s views should be considered the personal views of that individual rather than the formal position of IEEE, IEEE SA, the Standards Committee, or the Working Group. Statements made by volunteers may not represent the formal position of their employer(s) or affiliation(s). News releases about IEEE standards issued by entities other than IEEE SA should be considered the view of the entity issuing the release rather than the formal position of IEEE or IEEE SA.

Comments on standards

Comments for revision of IEEE Standards documents are welcome from any interested party, regardless of membership affiliation with IEEE or IEEE SA. However, **IEEE does not provide interpretations, consulting information, or advice pertaining to IEEE Standards documents.**

Suggestions for changes in documents should be in the form of a proposed change of text, together with appropriate supporting comments. Since IEEE standards represent a consensus of concerned interests, it is important that any responses to comments and questions also receive the concurrence of a balance of interests. For this reason, IEEE and the members of its Societies and subcommittees of the IEEE SA Board of Governors are not able to provide an instant response to comments or questions, except in those cases where the matter has previously been addressed. For the same reason, IEEE does not respond to interpretation requests. Any person who would like to participate in evaluating comments or revisions to an IEEE standard is welcome to join the relevant IEEE SA working group. You can indicate interest in a working group using the Interests tab in the Manage Profile & Interests area of the [IEEE SA myProject system](#).¹ An IEEE Account is needed to access the application.

Comments on standards should be submitted using the [Contact Us](#) form.²

Laws and regulations

Users of IEEE Standards documents should consult all applicable laws and regulations. Compliance with the provisions of any IEEE Standards document does not constitute compliance to any applicable regulatory

¹Available at: <https://development.standards.ieee.org/myproject-web/public/view.html#landing>.

²Available at: <https://standards.ieee.org/about/contact/>.

requirements. Implementers of the standard are responsible for observing or referring to the applicable regulatory requirements. IEEE does not, by the publication of its standards, intend to urge action that is not in compliance with applicable laws, and these documents may not be construed as doing so.

Data privacy

Users of IEEE Standards documents should evaluate the standards for considerations of data privacy and data ownership in the context of assessing and using the standards in compliance with applicable laws and regulations.

Copyrights

IEEE draft and approved standards are copyrighted by IEEE under U.S. and international copyright laws. They are made available by IEEE and are adopted for a wide variety of both public and private uses. These include both use by reference, in laws and regulations, and use in private self-regulation, standardization, and the promotion of engineering practices and methods. By making these documents available for use and adoption by public authorities and private users, neither IEEE nor its licensors waive any rights in copyright to the documents.

Photocopies

Subject to payment of the appropriate licensing fees, IEEE will grant users a limited, non-exclusive license to photocopy portions of any individual standard for company or organizational internal use or individual, non-commercial use only. To arrange for payment of licensing fees, please contact Copyright Clearance Center, Customer Service, 222 Rosewood Drive, Danvers, MA 01923 USA; +1 978 750 8400; <https://www.copyright.com/>. Permission to photocopy portions of any individual standard for educational classroom use can also be obtained through the Copyright Clearance Center.

Updating of IEEE Standards documents

Users of IEEE Standards documents should be aware that these documents may be superseded at any time by the issuance of new editions or may be amended from time to time through the issuance of amendments, corrigenda, or errata. An official IEEE document at any point in time consists of the current edition of the document together with any amendments, corrigenda, or errata then in effect.

Every IEEE standard is subjected to review at least every 10 years. When a document is more than 10 years old and has not undergone a revision process, it is reasonable to conclude that its contents, although still of some value, do not wholly reflect the present state of the art. Users are cautioned to check to determine that they have the latest edition of any IEEE standard.

In order to determine whether a given document is the current edition and whether it has been amended through the issuance of amendments, corrigenda, or errata, visit [IEEE Xplore](#) or [contact IEEE](#).³ For more information about the IEEE SA or IEEE's standards development process, visit the IEEE SA Website.

Errata

Errata, if any, for all IEEE standards can be accessed on the [IEEE SA Website](#).⁴ Search for standard number and year of approval to access the web page of the published standard. Errata links are located under the Additional

³Available at: <https://ieeexplore.ieee.org/browse/standards/collection/ieee>.

⁴Available at: <https://standards.ieee.org/standard/index.html>.

Resources Details section. Errata are also available in [IEEE Xplore](#). Users are encouraged to periodically check for errata.

Patents

IEEE standards are developed in compliance with the [IEEE SA Patent Policy](#).⁵

Attention is called to the possibility that implementation of this standard may require use of subject matter covered by patent rights. By publication of this standard, no position is taken by the IEEE with respect to the existence or validity of any patent rights in connection therewith. If a patent holder or patent applicant has filed a statement of assurance via an Accepted Letter of Assurance, then the statement is listed on the IEEE SA Website at <https://standards.ieee.org/about/sasb/patcom/patents.html>. Letters of Assurance may indicate whether the Submitter is willing or unwilling to grant licenses under patent rights without compensation or under reasonable rates, with reasonable terms and conditions that are demonstrably free of any unfair discrimination to applicants desiring to obtain such licenses.

Essential Patent Claims may exist for which a Letter of Assurance has not been received. The IEEE is not responsible for identifying Essential Patent Claims for which a license may be required, for conducting inquiries into the legal validity or scope of Patents Claims, or determining whether any licensing terms or conditions provided in connection with submission of a Letter of Assurance, if any, or in any licensing agreements are reasonable or non-discriminatory. Users of this standard are expressly advised that determination of the validity of any patent rights, and the risk of infringement of such rights, is entirely their own responsibility. Further information may be obtained from the IEEE Standards Association.

IMPORTANT NOTICE

Technologies, application of technologies, and recommended procedures in various industries evolve over time. The IEEE standards development process allows participants to review developments in industries, technologies, and practices, and to determine what, if any, updates should be made to the IEEE standard. During this evolution, the technologies and recommendations in IEEE standards may be implemented in ways not foreseen during the standard's development. IEEE standards development activities consider research and information presented to the standards development group in developing any safety recommendations. Other information about safety practices, changes in technology or technology implementation, or impact by peripheral systems also may be pertinent to safety considerations during implementation of the standard. Implementers and users of IEEE Standards documents are responsible for determining and complying with all appropriate safety, security, environmental, health, data privacy, and interference protection practices and all applicable laws and regulations.

⁵Available at: <https://standards.ieee.org/about/sasb/patcom/materials.html>.

Participants

At the time this IEEE standard was completed, the Enclosure Integrity Working Group had the following membership:

Dan Mulkey, *Chair*
Jeremy Van Horn, *Vice Chair*
Audrey Siebert-Timmer, *Secretary*

Scott Abbott
Martin Bachand
Israel Barrientos
David Blew
Darren Brown
Thomas Callsen
John Chisholm
Rhett Chrysler
Douglas Craig
John Crotty
Michael Dahlke
Thomas Dautat
William Elliott
Benjamin Garcia
James Gardner
Carlos Gaytan
Ali Ghafourian
Chris Guertin
Said Hachichi

Jane Hall
Kenneth Hampton
Ramadan Issack
Gael Kennedy
Gary King
Brad Kittrell
Brian Klaponski
Maria Lamorey
Andrew Larison
Alejandro Macias
Justin Minikel
Michael Morgan
Jerry Murphy
Dwight Parkinson
Vinay Patel
Ion Radu
Juan Ramirez
James Ratty
Martin Rave

Robert Reepe
Pedro Salgado
Jeffrey Schneider
Pugal Selvaraj
Avijit Shingari
Stephen Shull
Igor Simonov
Edward Smith
James Spaulding
Travis Spoone
Liz Sullivan
Michael Thibault
Alan Traut
Reinaldo Valentin
John Vartanian
Joshua Verdell
Shelby Walters
Alan Wilks
Michael Zarnowski

The following members of the individual Standards Association balloting group voted on this standard. Balloters may have voted for approval, disapproval, or abstention.

Boon Chong Ang	Werner Hoelzl	Caryn Riley
Charles Ball	Ramadan Issack	Ian Rokser
Peter Balma	Richard Jackson	Marnie Roussell
Gilles Bargone	John John	Mahesh Sampat
Paul Barnhart	Gael Kennedy	Albert Sanchez
Barry Beaster	Sheldon Kennedy	Daniel Sauer
Steven Bezner	Gary King	Bartien Sayogo
Wallace Binder	Brian Klaponski	Jeremy Sewell
Thomas Blackburn	Boris Kogan	Jaber Shalabi
David Blew	Mikhail Lagoda	Samuel Sharpless
Darren Brown	Wang Lei	Avijit Shingari
William Byrd	Colby Lovins	Stephen Shull
Eldridge Byron	Greg Luri	Jerry Smith
Thomas Callsen	Balakrishnan Mani	Jimmy Smith
Paul Cardinal	Lee Matthews	Travis Spoone
Paul Chisholm	Justin Minikel	David Tepen
Thomas Dauzat	Daniel Mulkey	Michael Thibault
Stacey Davies	Jerry Murphy	Alan Traut
Craig DeRouen	Arthur Neubauer	Karla Trost
Kurniawan Diharja	Joe Nims	Jeremy Van Horn
Donald Dunn	Lorraine Padden	Jason Varnell
Jorge Fernandez Daher	Dhiru Patel	John Vartanian
Paul Found	Howard Penrose	Roger Verdolin
Carl Fredericks	Matthew Pinard	John Vergis
Benjamin Garcia	Alvaro Portillo	David Wallace
Shubhanker Garg	Jarrod Prince	Shelby Walters
Jalal Gohari	Larry Putman	Bruce Webb
John Harley	Ion Radu	Daniel Weyer
Roger Hayes	Martin Rave	Alan Wilks
Thang Hochanh	Robert Reepe	Terry Woodyard

When the IEEE SA Standards Board approved this standard on 6 December 2023, it had the following membership:

David J. Law, *Chair*
Ted Burse, *Vice Chair*
Gary Hoffman, *Past Chair*
Konstantinos Karachalios, *Secretary*

Sara R. Biyabani	Joseph S. Levy	Paul Nikolich
Doug Edwards	Howard Li	Annette D. Reilly
Ramy Ahmed Fathy	Johnny Daozhuang Lin	Robby Robson
Guido R. Hiertz	Gui Lin	Lei Wang
Yousef Kimiagar	Xiaohui Liu	F. Keith Water
Joseph L. Koepfinger*	Kevin W. Lu	Karl Weber
Thomas Koshy	Daleep C. Mohla	Philip B. Winston
John D. Kulick	Andrew Myles	Don Wright

*Member Emeritus

Introduction

This introduction is not part of IEEE Std C57.12.29-2023™, IEEE Standard for Pad-Mounted Equipment—Enclosure Integrity for Coastal Environments.

The Accredited Standards Committee on Transformers, Regulators, and Reactors (C57) originally developed and correlated standards on these products, together with the Accredited Standards Committee on Power Switchgear (C37) through the Joint ASC C57/C37 Working Group on Enclosures with Joseph Martin and then Robert C. Olen as chairman. This group is now the Enclosure Integrity working group of the IEEE Transformers Committee.

The data used in this work have been gathered from many sources, including the standards of the Institute of Electrical and Electronics Engineers, the National Electrical Manufacturers Association, reports of committees of the Edison Electric Institute, and others.

Significant changes in this revision of the standard are: the mandatory IEEE Word Usage clause was added, normative references were updated, the gel coat definition was removed, information was re-organized and separated into Enclosure design in [Clause 4](#), and Coating system requirements in [Clause 5](#). The pull and push tools ([4.3.1.2](#) and [4.3.1.3](#)) were updated, the purpose of each test was clarified, and each test was generally updated and clarified. Two informative annexes were added: [Annex B](#) – Commonly used substrate steels and [Annex D](#) – Substrate surface preparation. Pad-mounted switchgear has been dropped from the scope as IEEE PC37.75, *Draft Standard for Pad-Mounted, Pole-Mounted and Submersible Switchgear Enclosures and Associated Control Enclosures—Coastal and Non-Coastal Environmental Integrity*, is in the final balloting stages. A warning was added to [4.2.3](#) about the possibility of burns from publicly accessible metal surfaces.

Contents

1. Overview	11
1.1 Scope	11
1.2 Purpose	11
1.3 Word usage	11
2. Normative references	12
3. Definitions, acronyms, and abbreviations	13
3.1 Definitions	13
3.2 Acronyms and abbreviations	14
4. Enclosure design, access, and security	14
4.1 General	14
4.2 Design requirements	14
4.3 Security requirements	19
5. Applied coating system requirements	22
5.1 General	22
5.2 Test repetition	22
5.3 Enclosure color	22
5.4 Test specimens	22
5.5 Applied coating system performance requirements	22
6. Labels	27
6.1 Purpose	27
6.2 Application	27
7. General	27
7.1 Shipment	27
7.2 Coating repair procedure	27
7.3 Coating touch-up prior to shipment	27
Annex A (normative) Comparative weight loss procedure	28
Annex B (informative) Commonly used substrate steels	29
Annex C (informative) Pry bar	30
Annex D (informative) Substrate surface preparation	34
Annex E (informative) Bibliography	36

IEEE Standard for Pad-Mounted Equipment—Enclosure Integrity for Coastal Environments

1. Overview

1.1 Scope

This standard covers conformance tests and requirements for the enclosure integrity of above-grade pad-mounted electrical equipment intended for installation in coastal environments containing apparatus energized in excess of 600 V that may be exposed to the public including, but not limited to, the following types of equipment enclosures:

- Pad-mounted distribution transformers
- Pad-mounted capacitors or inductors
- Pad-mounted junction enclosures
- Pad-mounted metering equipment
- Pad-mounted voltage regulators

This standard does not cover installations that are under the exclusive control of electric utilities and that are located in such a manner that access to the equipment is controlled exclusively by the utility.

1.2 Purpose

The purpose of this standard is to describe the requirements for a comprehensive enclosure integrity system for pad-mounted equipment providing long service life with minimum maintenance and positive safety features.

1.3 Word usage

The word *shall* indicates mandatory requirements strictly to be followed in order to conform to the standard and from which no deviation is permitted (*shall equals is required to*).^{6,7}

⁶The use of the word *must* is deprecated and cannot be used when stating mandatory requirements; *must* is used only to describe unavoidable situations.

⁷The use of *will* is deprecated and cannot be used when stating mandatory requirements; *will* is only used in statements of fact.

The word *should* indicates that among several possibilities one is recommended as particularly suitable, without mentioning or excluding others; or that a certain course of action is preferred but not necessarily required (*should* equals *is recommended that*).

The word *may* is used to indicate a course of action permissible within the limits of the standard (*may* equals *is permitted to*).

The word *can* is used for statements of possibility and capability, whether material, physical, or causal (*can* equals *is able to*).

2. Normative references

The following referenced documents are indispensable for the application of this document (i.e., they must be understood and used, so each referenced document is cited in text and its relationship to this document is explained). For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments or corrigenda) applies.

ASTM B117, Standard Practice for Operating Salt Spray (Fog) Apparatus.⁸

ASTM D523, Standard Test Method for Specular Gloss.

ASTM D610, Standard Practice for Evaluating Degree of Rusting on Painted Steel Surfaces.

ASTM D660, Standard Test Method for Evaluating Degree of Checking of Exterior Paints.

ASTM D661, Standard Test Method for Evaluating Degree of Cracking of Exterior Paints.

ASTM D714, Standard Test Method for Evaluating Degree of Blistering of Paints.

ASTM D1654-05, Standard Test Method for Evaluation of Painted or Coated Specimens Subjected to Corrosive Environments.

ASTM D3170, Standard Test Method for Chipping Resistance of Coatings.

ASTM D3359, Standard Test Methods for Rating Adhesion by Tape Test.

ASTM D3363, Standard Test Method for Film Hardness by Pencil Test.

ASTM D4060, Standard Test Method for Abrasion Resistance of Organic Coatings by the Taber Abraser.

ASTM D4585, Standard Practice for Testing Water Resistance of Coatings Using Controlled Condensation.

ASTM D4587, Standard Practice for Fluorescent UV-Condensation Exposures of Paint and Related Coatings.

UL 94, Standard for Tests for Flammability of Plastic Materials for Parts in Devices and Appliances.⁹

UL 746C, Polymeric Materials – Use in Electrical Equipment Evaluations.

⁸ASTM publications are available from the American Society for Testing and Materials (<https://www.astm.org/>).

⁹UL publications are available from Underwriters Laboratories (<https://www.ul.com/>).

3. Definitions, acronyms, and abbreviations

3.1 Definitions

For the purposes of this document, the following terms and definitions apply. The *IEEE Standards Dictionary Online* should be consulted for terms not defined in this clause.¹⁰

above grade: A term referring to an equipment use location above the high-water line not intended for partial or total submersion.

axial force: A force applied along the axis of the pry bar from its handle to its pry tip.

coastal environment: The land area within 760 m (2500 ft) of the mean high-water line, or as determined by users to be affected by the coastal effect of salt-spray, high wind, or other harsh environmental effects.

conformance tests: Certain performance tests are conducted to demonstrate compliance with the applicable standards. The test specimen is normally subjected to all planned routine tests prior to initiation of the conformance test program.

NOTE—The conformance tests may, or may not, be similar to certain design tests. Demonstration of margins (capabilities) beyond the standard requirements is unnecessary.¹¹

design tests: Tests made by the manufacturer to determine the adequacy of the design of a particular type, or model of equipment or its component parts to meet its assigned ratings and to operate satisfactorily under normal conditions and under special conditions if specified. These tests are used to demonstrate compliance with applicable standards of the industry.

NOTE—Design tests, sometimes called *type tests*, are made on representative apparatus or prototypes to verify the validity of design analysis and calculation methods and to substantiate the ratings assigned to all other apparatus of basically the same design. These tests may also be used to evaluate the modification of a previous design and to verify that performance has not been adversely affected. Test data from previous similar designs may be used for current designs, where appropriate. In theory, the tests need not be repeated unless the design is changed so as to modify performance. However, experience has demonstrated that unintended change creeps into manufacturing processes and thus design tests should be periodically repeated.

dry film thickness: Thickness of any applied coating(s) measured after curing.

pad-mounted enclosure: An enclosure containing electrical apparatus, typically located outdoors at ground level where the general public has direct contact with the exterior surfaces of the equipment.

padlock: A locking device specified and supplied by the user that will prevent the disengagement of the pentahead device (e.g., key or combination lock, one time or twist lock, single use lock or similar device).

prying leverage: A force at right angles to the handle times the distance from this force to the point of insertion of the pry tip into a joint, crevice, or similar opening in enclosure.

routine tests: Tests made for quality control by the manufacturer on every device or representative samples, or on parts or materials as required to verify during production that the product meets the design specifications and applicable standards.

¹⁰*IEEE Standards Dictionary Online* is available at: <http://dictionary.ieee.org>. An IEEE account is required for access to the dictionary, and one can be created at no charge on the dictionary sign-in page.

¹¹Notes in text, tables, and figures of a standard are given for information only and do not contain requirements needed to implement this standard.

NOTE 1—Certain quality assurance tests on identified critical parts of repetitive high-production devices may be tested on a planned statistical sampling basis.

NOTE 2—Routine tests are sometimes called production tests.

substrate: The uncoated material that provides structural integrity to the enclosure.

3.2 Acronyms and abbreviations

AWG American wire gauge

4. Enclosure design, access, and security

4.1 General

The objective of this clause is to describe design and performance requirements for pad-mounted enclosures situated in coastal or other severe environments.

4.2 Design requirements

In addition to passing the tests defined in this standard, the construction of pad-mounted enclosures shall comply with the requirements of 4.2.1 through 4.2.16.

4.2.1 Substrate

The substrate(s) used on the exterior of the enclosure shall be a material that, when coated or otherwise processed, will maintain the structural integrity of the enclosure over the life of the apparatus. The substrate shall exhibit a general corrosion rate not to exceed 0.03 mm (0.001 inch) per year and a maximum pit depth not to exceed 0.13 mm (0.005 inch) over the life of the apparatus, when exposed to natural coastal environments.

4.2.1.1 Substrate performance requirements


Five substrate test panels and five bare AISI 409 stainless steel¹² control test panels shall be evaluated for percent weight loss after exposure to 1500 h of salt spray in accordance with ASTM B117.¹³ The average weight loss of each set of test panels shall not exceed 2.5%. In addition, the ratio of the average percent weight loss between the substrate test panel set and the control test panel set shall not exceed 5 to 1.¹⁴

The AISI 409 stainless-steel control test panels shall be unwelded and fabricated in accordance with Figure 1 using standard production practices prior to testing. For metallic substrates, the substrate test panels shall be fabricated in accordance with Figure 2 using standard production, fabrication, welding, and cleaning practices. For non-metallic substrates, the substrate test panels shall be fabricated in accordance with Figure 1 using standard production, fabrication, and cleaning practices. In summary, five unwelded control 409 panels compared to either five welded metallic substrates or five unwelded non-metallic substrates.

¹²See Annex B.


¹³Information on normative references can be found in Clause 2.

¹⁴It is not uncommon for a welded test panel to exhibit greater weight loss due to the galvanic action between the weldment and the base metal.

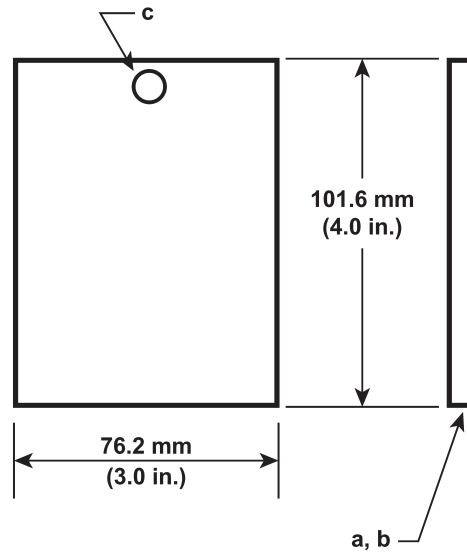

- a. Panel thickness to be of typical production stock used in the manufacture of devices for which the test is intended.
- b. Panel is to be cleaned and uncoated.
- c. Hole may be placed in panel if required for processing. Locate centered on short dimension and 3.2 mm (1/8 in.) to edge of hole on long dimension. Recommended maximum hole size is 14.3 mm (9/16 in.) in diameter.

Figure 1—Unwelded substrate test panel

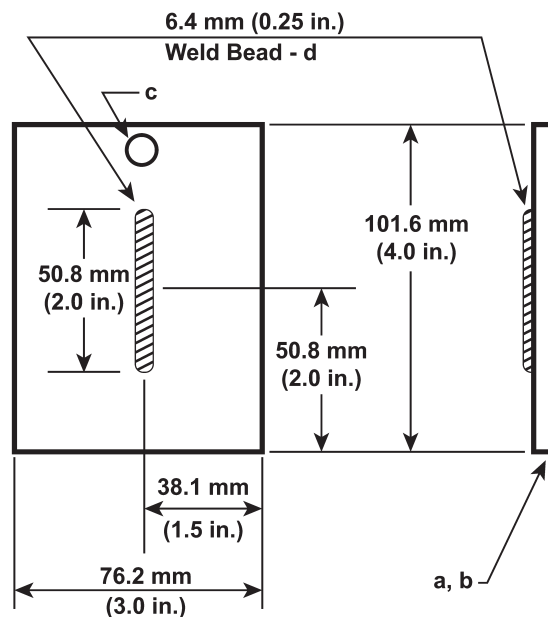

- a. Panel thickness to be of typical production stock used in the manufacture of devices for which the test is intended.
- b. Panel is to be cleaned and uncoated.
- c. Hole may be placed in panel if required for processing. Locate centered on short dimension and 3.2 mm (1/8 in.) to edge of hole on long dimension. Recommended maximum hole size is 14.3 mm (9/16 in.) in diameter.
- d. Weld bead to be the same type metal composition as the panel. Weld bead to be 6.4 mm (1/4 in.) wide and 3.2 mm (1/8 in.) high.

Figure 2—Welded substrate panel

The purpose of this test is to assure that the substrate (without coating) does not lose more weight than the 5 to 1 ratio compared to the bare unwelded AISI 409 stainless steel when exposed to salt spray.

Exceptions: Enclosures manufactured totally from AISI 409, 304L, 316, or 316L stainless steel, and welded in accordance with American Welding Society Standard Weld Procedure Specifications are exempt from this subclause.

See [Annex A](#) for the procedure for comparative weight loss analysis of the test panels.

4.2.2 Welds

All welds shall be treated to prepare the weld area and the heat affected zones for coating. Weld spatter shall be removed. All welds shall be made in accordance with appropriate industrial welding standards.

4.2.3 Exterior surface

The enclosure shall be designed such that all exterior surfaces are accessible for proper surface preparation and the application of a uniform amount of coating materials. Additionally, all exterior surfaces shall be accessible for the purposes of inspection and maintenance of the enclosure over the life of the equipment.

WARNING

Users should take care when deploying pad-mounted equipment in publicly accessible locations as operational and environmental factors may cause the equipment's exterior metal surfaces to reach temperatures which could result in burns to an individual who comes in contact with their surfaces.

4.2.4 Other exposed surfaces

Any surface, other than coated substrate, in the assembled equipment that is left exposed to the external environment (i.e., seals, gaskets, cables, etc.) must survive the same environment as the coated substrate.

4.2.5 Enclosure mounting

The bottom edge of the enclosure shall provide for flush mounting on a flat, rigid mounting surface.¹⁵

4.2.6 Contaminant accumulation

The enclosure shall be designed to shed water and minimize areas where corrosive elements can accumulate.

4.2.7 Water resistance

The enclosure shall restrict the entry of water (other than floodwater) into the enclosure so as not to impair the operation of the apparatus inside.

4.2.8 Sharp corners

External sharp corners and projections shall be minimized.

4.2.9 Panel assembly

Panels shall be fastened or hinged to resist disassembly, breaking, or prying open from the outside with the doors in the closed and locked position. Normal entry shall be possible only with the use of proper access tools. There shall be no exposed screws, bolts, or other fastening devices that are externally removable (with

¹⁵The security of the interface between the mounting surface and the equipment is the responsibility of the installer/user.

the exception of pentahead bolts provided for extra security) that would provide access to energized parts in the enclosure.¹⁶

4.2.10 Door hardware

Locking bolts and associated threaded receptacles, hinges, and hinge pins shall be AISI type 304 stainless steel or material of equivalent corrosion resistance.

4.2.11 Handhole covers

If handholes are publicly accessible, a guard shall be applied over the handhole that is secured from inside the locked air compartment enclosure.

4.2.12 Locking/latching devices

The latching device(s) shall be designed and constructed of such a material so as to resist breaking or bending. The provision for locking device(s) on the enclosure door(s) shall be designed and located as to comply with the defined tests.

4.2.13 Attachments

Any attachments to the assembled equipment (e.g., sight glass, viewing window, gauge) that are exposed to the external environment must retain their intended functionality.

4.2.14 Galling

Steps must be taken in the design and manufacture of the enclosures to prevent galling. Galling is known to occur with threaded fasteners where the mating surfaces are both made of the same stainless-steel alloy, aluminum alloy, or titanium alloy. Two commonly used methods to mitigate galling are listed below but are not specifically required separately or in combination. Alternative methods may be used if proven to be equally effective:

- Use anti-seize compounds or materials in the threaded joints
- Use dissimilar materials in threaded joints (i.e., silicon-bronze with stainless steel, brass with stainless steel, etc.)

NOTE—Manufacturers and users should be aware that the use of dissimilar metals may lead to galvanic corrosion in some service environments. The use of dielectric unions or physical isolation of the materials is known to mitigate corrosion potential.

4.2.15 Fire resistance

The enclosure shall be constructed of fire-resistant material. Non-metallic enclosures shall be made from material having a “5V” classification per UL 94, or the enclosure shall comply with the 127 mm (5 inch) flame test specified in UL 746C.


4.2.16 Enclosure access

All access doors shall be fastened with a device that uses a pentahead tool to permit unlatching the door only after the padlock has been removed. This pentahead device or bolt shall be coordinated such that the padlock cannot be inserted into the hasp until the access door is fully latched and the pentahead device is securely engaged.

¹⁶4.2.16 describes the design requirements for pentahead bolts.

Enclosures without latches shall have padlock and pentahead bolt provisions and shall be coordinated to prevent insertion of a padlock until the access door is fully closed and the pentahead device or bolt is securely engaged. It shall not be possible to disengage the pentahead bolt until the padlock is removed.

A minimum of one pentahead device or bolt and padlocking means shall be provided. The pentahead device or bolt shall be surrounded by a non-rotating guard or shall be recessed such that the pentahead device or bolt can be engaged only by the proper tool. The dimensions of the pentahead bolt and non-rotating recess shall comply with Figure 3. More than one door may be fastened with a single padlock and pentahead device or bolt. In the event that the pentahead bolt is missing, the design shall be such that the cabinet shall remain inaccessible through the bolt hole. The bolt hole shall be blocked from the back and all sides to prevent wire probe entry.

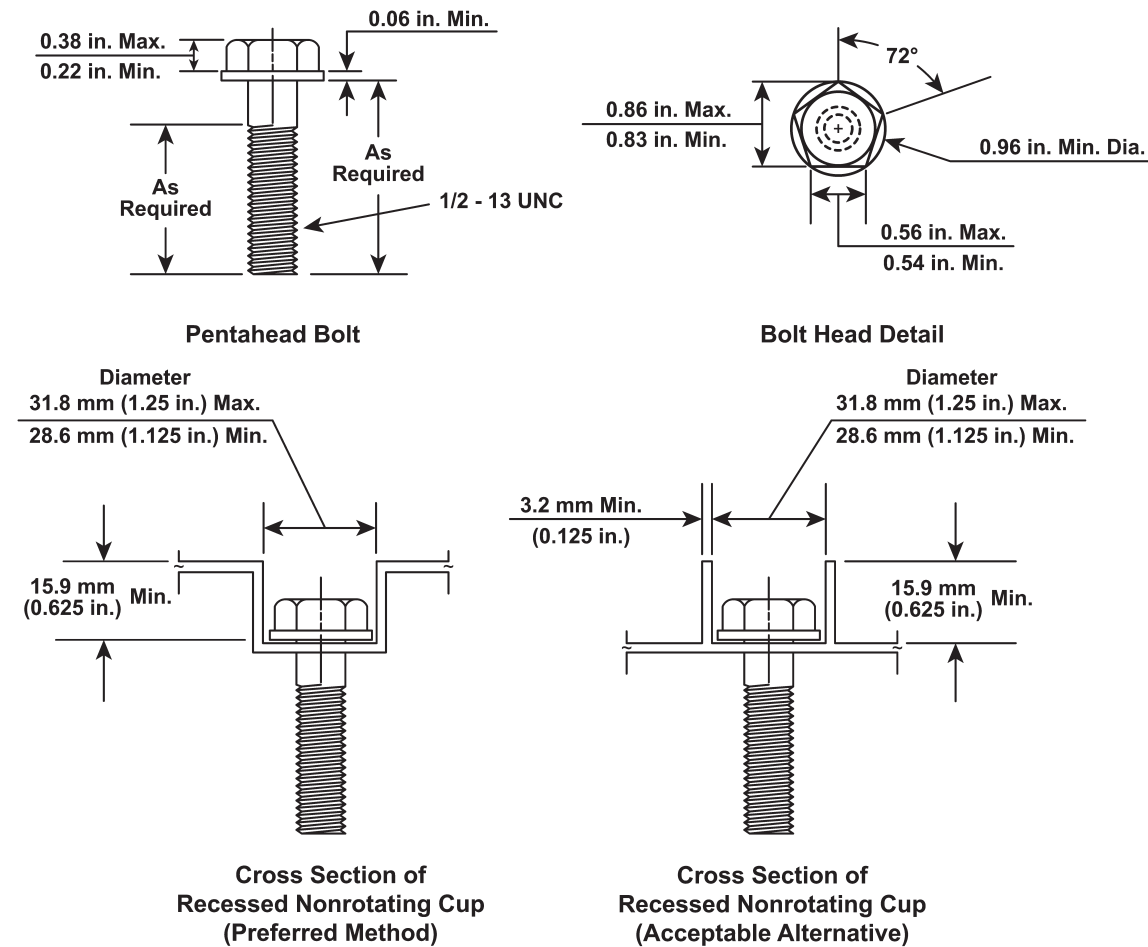

NOTE—The captive method is not shown.

Figure 3—Captive and recessed pentahead bolts

4.3 Security requirements

4.3.1 Test equipment

The tests for enclosure security shall be conducted with the following equipment or equivalent.

4.3.1.1 Pry bar

The pry bar shall be constructed with the pry tip shown in [Figure 4](#). The pry bar shall be capable of accurately indicating the axial force and prying leverage specified in [Table 1](#).

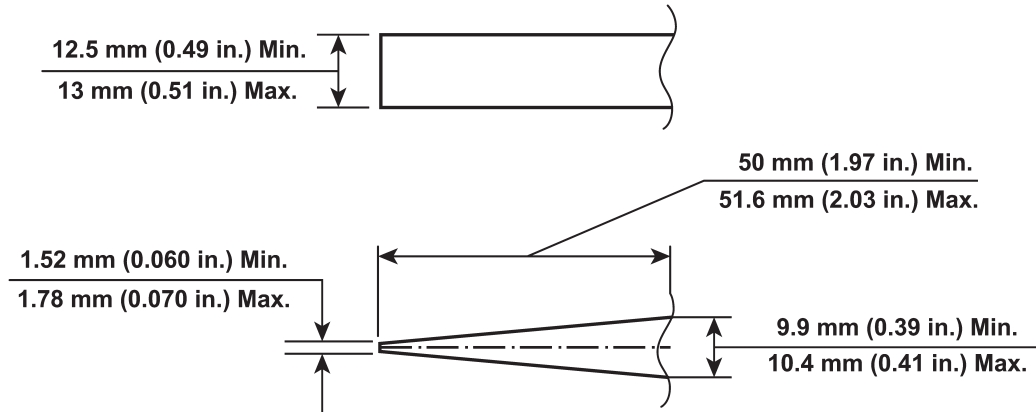


Figure 4—Pry bar tip

Table 1—Test values

Test	Value	Used in clause
Inward axial force	222 N (50 lbf)	4.3.2.2
Prying leverage tests	102 N·m (900 lbf-inch)	4.3.2.2
Pull test	667 N (150 lbf)	4.3.2.3
Deflection test	445 N (100 lbf)	4.3.2.5

4.3.1.2 Tool

The axial force and prying leverage indication may be obtained from a variety of readily available or custom-made tools. [Annex C](#) includes a complete set of detail drawings for one set of such tools. Other pry bar designs complying with [4.3.1.1](#) are acceptable.

4.3.1.3 Measurement

The prying leverage applied can be measured indirectly by measuring the deflection of the pry bar. The indicator is mounted on the pry bar and set to measure the deflection of a certain length of the bar. A calibration can be made which will result in a table or curve showing prying leverage versus reading of the indicator.

4.3.1.4 Pull tool

The device shown in Figure 5 shall be used in the pull tests.¹⁷

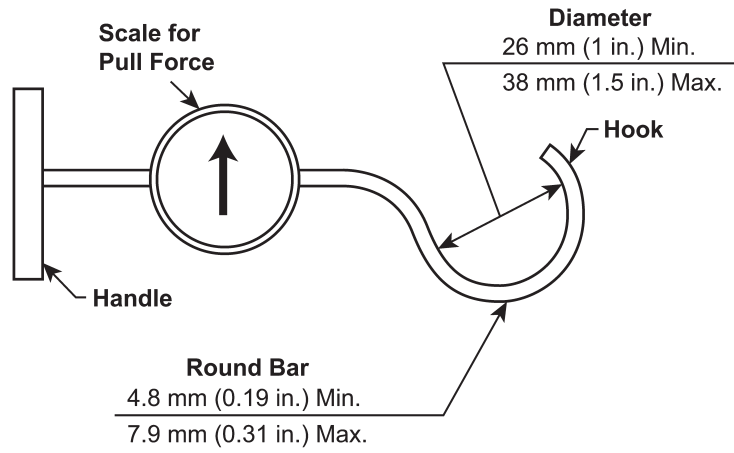


Figure 5—Pull hook

4.3.1.5 Push tool

A device that has a 12.7 mm × 12.7 mm (0.5 inch × 0.5 inch) square face as shown in Figure 6 with associated indicator to measure axial force shall be used to perform the deflection test (see Footnote 17).

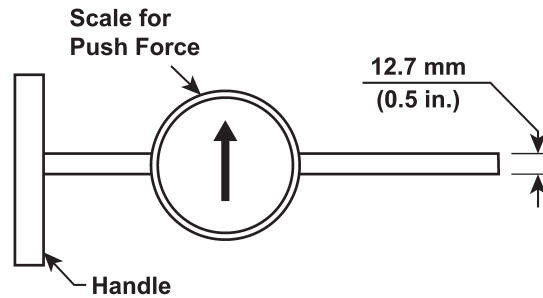


Figure 6—Push tool

4.3.1.6 Probe wire

The probing wire shall be bare number 14 AWG soft-drawn solid copper wire that is 3 m (10 ft) long.

4.3.2 Test methods

The following tests are to be performed on the enclosure. The enclosure shall resist the entry of foreign objects such as sticks, rods, or wires.

¹⁷Generic analog or digital scales can be configured to measure the push and pull forces for the tools in Figure 5 and Figure 6.

4.3.2.1 General

The pad-mounted enclosure shall be mounted on a flat surface according to the manufacturer's specification. With the access door(s) closed and locked using a padlock with an 8 mm (5/16 inch) diameter shackle, the following sequence of tests shall be performed:

- a) Pry tests
- b) Wire probe tests
- c) Pull tests
- d) Repeat wire probe tests
- e) Deflection tests
- f) Operation test

4.3.2.2 Pry tests

The pry bar shall be used on all joints, crevices, hinges, locking means and other objects that exist between the enclosure components, including the enclosure/pad interface. The pry bar shall be permitted to be placed at any angle to the enclosure surface. The tip of the bar shall first be inserted in the opening being tested using the value of axial force specified in [Table 1](#). Then, with that axial force being maintained, the prying force specified in [Table 1](#) applied alternatively first in one direction and then in the opposite direction (i.e., once in each direction). Application of either or both axial and prying force shall be maintained so long as relaxation is occurring. When relaxation ceases, or if no relaxation occurs, the pry bar shall be removed, and the pry test reapplied at the same location. When relaxation ceases or no relaxation occurs after the second test, the pry bar shall be removed and applied at an untested location.

4.3.2.3 Pull tests

A pulling force shall be applied to the critical points of all enclosure parts that can be engaged by the pulling hook. A pulling force indicated in [Table 1](#) shall be exerted at any angle to the enclosure surface. This force is to be maintained during any relaxation. When relaxation ceases, or if no relaxation occurs, the pull test shall be terminated. The hook shall then be inserted into any other part in which it can engage, and the test shall be repeated at the new location. All parts that can be engaged by the pull hook shall be tested once.

4.3.2.4 Wire probe tests

Following the pry tests and pull tests described in [4.3.2.2](#) and [4.3.2.3](#), an attempt to penetrate the enclosure with the probe wire shall be made. This penetration shall be attempted at all crevices and joints. The wire shall be straight with no pre-bends and shall be gripped by the tester with his or her bare hands. If the wire enters the joint, the wire shall be continually pushed and bent until either it can no longer be pushed, or it has entered the enclosure completely. This test is passed if no portion of the probing wire has entered the enclosure, or the probing wire is restricted by a barrier from intrusion into the enclosure to a point that does not reduce the clearance to energized parts of the equipment.

4.3.2.5 Deflection tests

The deflection test shall be applied to all sides and walls of the enclosure. This test is passed if the specific force (see [Table 1](#)) applied perpendicularly to the surface of the enclosure does not impair the dielectric, mechanical or corrosion performance of the equipment.

4.3.2.6 Operation test

Following all of the above tests, the unit shall be lifted at least 1 m in accordance with manufacturer's standard lift instructions and then set again on the flat surface. The doors shall be easily opened, closed, latched and locked without requiring adjustments to the cabinet, latch mechanism and/or enclosure door(s). All of the door latch points must fully engage when the door is closed.

4.3.2.7 Test repetition

These design tests shall be repeated whenever the enclosure design is changed so as to modify performance, or at least every five years, whichever occurs first.

4.3.3 Test values

The minimum test values for which entry shall be prevented are provided in [Table 1](#).

5. Applied coating system requirements

5.1 General

All coated surfaces on the exterior or interior of the enclosure that may be exposed to the atmosphere shall be capable of meeting the performance tests required by this standard. Each different combination of substrate(s) and coating(s) shall meet these design tests. If more than one substrate/coating system combination is used for different areas of the enclosure, the areas in which each is used shall be identified. The laboratory test performance data of each substrate/coating system shall be submitted for approval upon request.

5.2 Test repetition

Test data shall be resubmitted whenever there are changes in the production method and/or materials, or at least every five years, whichever occurs first.

5.3 Enclosure color

Unless otherwise specified, the topcoat color shall be Munsell Number 7GY 3.29/1.5 high gloss or 7GY 3.29/1.5 SG semi-gloss pad-mount green. The color variation of the coated product shall not exceed the Munsell Color Standard by more than a ΔE^* (CIELAB) value of two.¹⁸


NOTE—CIELAB uses ΔE^* to distinguish CIE 1976 $L^*a^*b^*$ scale in 1976 (Supplement No. 2 to CIE Publication No. 15, Colorimetry) from previous versions. CIELAB is more commonly used rather than Hunter.

5.4 Test specimens

Test specimens shall consist of panels of the same material composition used in production. Test specimens shall be fabricated in accordance with [Figure 7](#), [Figure 8](#), [Figure 9](#), and [Figure 10](#) as to size and design. Quantity and type of panels in each test are identified under the specific test. If more than one substrate and coating combination is used on an enclosure, all variations shall be tested in accordance with [5.5](#). All panels shall be prepared using the production coating system.¹⁹ Coated test panels shall be conditioned at room temperature and humidity for a minimum of 7 days prior to any testing.


¹⁸Munsell Color Standards, X-Rite, Inc. 4300 44th Street S.E. Grand Rapids, Michigan 49512 (<https://munsell.com/>).

¹⁹See [Annex D](#).

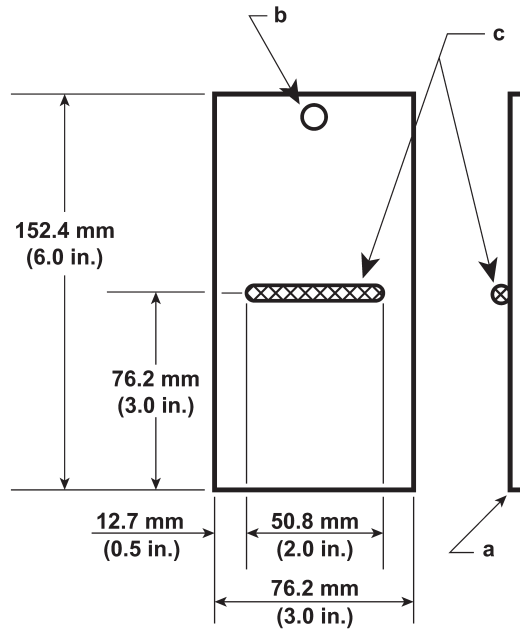


- a. Test panels shall be made from typical production stock of the same material type and thickness used in the construction of the device for which the specified test is intended.
- b. Hole may be placed in panel for hanging for coating operations if required. Locate centered on short dimension and 3.2 mm (1/8 inch) to edge of hole on long dimension. Recommended maximum hole size 14.3 mm (9/16 inch) in diameter.
- c. Weld bead shall be the same type of metal composition as the panel. Weld bead shall be 6.4 mm (1/4 inch) wide and 3.2 mm (1/8 in.) high.

Figure 7—Weld-bead coating test panel

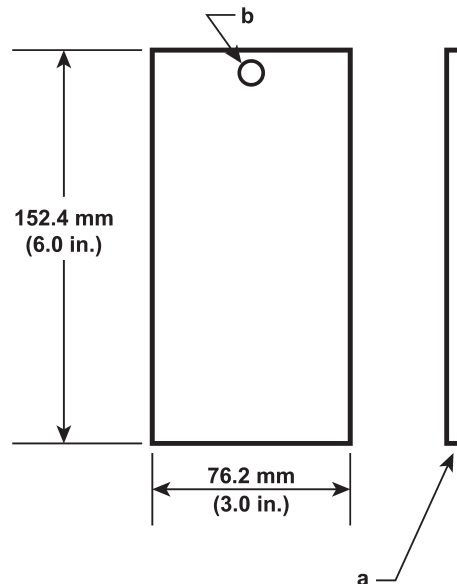


- a. Test panels shall be made from typical production stock of the same material type and thickness used in the construction of the device for which the specified test is intended.
- b. Hole may be placed in panel for hanging for coating operations if required. Locate centered on short dimension and 3.2 mm (1/8 inch) to edge of hole on long dimension. Recommended maximum hole size 14.3 mm (9/16 inch) in diameter.

Figure 8—Plain coating test panel

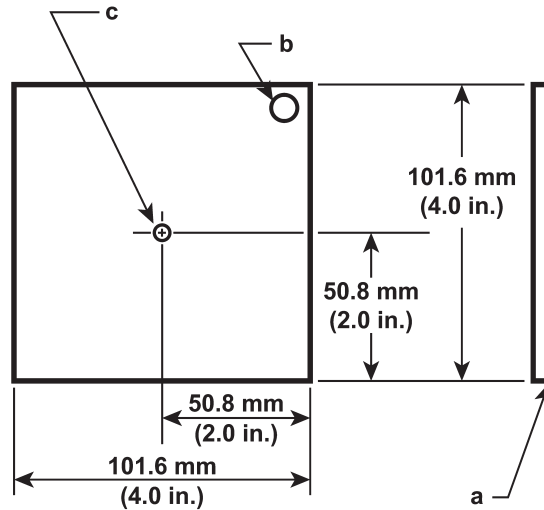

- a. Test panels shall be made from typical production stock of the same material type and thickness used in the construction of the device for which the specified test is intended.
- b. Hole may be placed in panel for hanging located in one corner. Recommended maximum hole size 14.3 mm (9/16 in.) in diameter.
- c. 7.9 mm (5/16 in.) diameter hole required to fit the ASTM D4060 test fixture post.

Figure 9—Abrasion coating test panel

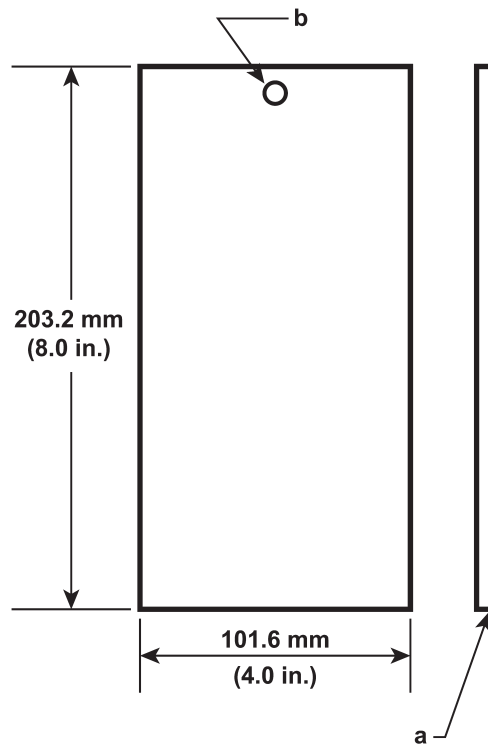

- a. Test panels shall be made from typical production stock of the same material type and thickness used in the construction of the device for which the specified test is intended.
- b. Hole may be placed in panel for hanging for coating operations if required. Locate centered on short dimension and 3.2 mm (1/8 in.) to edge of hole on long dimension. Recommended maximum hole size 14.3 mm (9/16 in.) in diameter.

Figure 10—Gravelometer coating test panel

5.5 Applied coating system performance requirements

5.5.1 Outdoor exposure test

This test demonstrates how the coating/substrate system may perform in coastal environments.

This test requirement shall apply only for coated surfaces on the exterior of the enclosure.

5.5.1.1 Exposure test site

A marine environment for natural accelerated testing, located on the ocean or Gulf of Mexico, with a view of the surf-line that is unrestricted by buildings. Corrosion rate for an ingot of iron of AISI 1008 carbon steel shall be greater than 254 μm (10 mil) per year as determined by annual evaluation. Monitoring for chloride deposition (monthly), iron ingot corrosion rate (annual), temperature, and rainfall shall be maintained, and historical data provided upon request.

5.5.1.2 Exposure test criteria

Three coated panels, shall be prepared in accordance with [Figure 7](#), scribed per ASTM D1654-05 to create an approximately 102 mm (4 inch) long scribe across the weld, and then tested for 12 weeks at a test site that meets the criteria in [5.5.1.1](#). The panels shall be exposed in a rack facing the ocean at a 30° angle from the horizontal and positioned so that moisture runs down the length of the scribe line during the exposure period.

5.5.1.3 Test evaluation

After the 12-week exposure, prepare the scribe for evaluation per ASTM D1654-05 Procedure A, Method 2 (scraping). The scribe shall be divided into 14 zones 6.4 mm (0.25 inch) in length and the worst spot in each zone will be evaluated [except the first 6.4 mm (0.25 inch) of the scribe at each end of the scribe line]. The average of the 14 readings shall be rated as given in Table 1 of ASTM D1654-05. Scribe creepage shall include discoloration and pitting caused from corrosion, as well as loss of coating adhesion, blistering, film undercutting, and removal of coating around the scribe line. After a rating has been set for each of the three panels, the average rating of the three panels shall not be less than nine. The area away from the scribe shall have no blisters per ASTM D714 and be free of any corrosion per ASTM D610. The 6.4 mm (0.25 inch) area around the perimeter of the panel and hanging hole shall not be included in the rating of the face of the panel.

5.5.2 Adhesion test

This test demonstrates proper adhesion of the coating system to the substrate.

This test requirement shall apply to all coating systems applied to the enclosure.

One coated test panel, per [Figure 8](#), shall be scribed to bare substrate in accordance with ASTM D3359. Method A shall be used for films thicker than 0.13 mm (5 mil or 0.005 inch). Method B shall be used for films less than or equal to 0.13 mm (5 mil or 0.005 inch). There shall be 100% adhesion to the substrate and between layers. A rating of 5A for Method A and 5B for Method B per ASTM D3359 is required.

5.5.3 Humidity test

This test evaluates the performance of the coating system under controlled condensation conditions. Condensation may cause deterioration of the coating system impacting the useful service life of the equipment.

This test requirement shall apply to all coating systems applied to the enclosure.

Two coated panels, per [Figure 7](#), shall be tested for 1000 h in accordance with ASTM D4585, except that the test shall be conducted at $45\text{ }^{\circ}\text{C} \pm 1\text{ }^{\circ}\text{C}$ ($113\text{ }^{\circ}\text{F} \pm 2\text{ }^{\circ}\text{F}$). Upon completion of the test, panels shall be evaluated for the following:

- Blistering: There shall be no blistering observed per ASTM D714 on the surface of the panels when inspected within 15 min after removal from the cabinet.
- Softening: After removal from the cabinet, allow the panels to air dry for $24\text{ h} \pm 1\text{ h}$. There shall be no more than one pencil hardness change when tested per ASTM D3363.
- Any color change shall be noted.

5.5.4 Insulating fluid resistance tests (for fluid-filled equipment only)

This test demonstrates proper adhesion of the coating to the substrate and chemical resistance to the insulating fluid whether gaseous or liquid.

This test requirement shall apply only for coated surfaces on the interior of the enclosure and that come into direct contact with insulating fluids.

Partially immerse one coated panel, per [Figure 8](#) in the insulating fluid for 72 h at the top fluid rise temperature plus $40\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ ($104\text{ }^{\circ}\text{F} \pm 4\text{ }^{\circ}\text{F}$). On the immersed portion of the panel, there shall be no loss of adhesion per ASTM D3359, no blisters per ASTM D714, no streaking, and no more than one pencil hardness change when tested in accordance with ASTM D3363, using either method. Any color change shall be noted.

Example: For $65\text{ }^{\circ}\text{C}$ ($149\text{ }^{\circ}\text{F}$) rise transformers the test temperature is $105\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ ($221\text{ }^{\circ}\text{F} \pm 4\text{ }^{\circ}\text{F}$), while for $75\text{ }^{\circ}\text{C}$ ($167\text{ }^{\circ}\text{F}$) rise transformers the test temperature is $115\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ ($239\text{ }^{\circ}\text{F} \pm 4\text{ }^{\circ}\text{F}$).

When multiple types of insulating fluid may be used in the equipment, a separate test is required for each type of insulating fluid.

5.5.5 Ultraviolet accelerated weathering test

This test demonstrates how the substrate plus the coating system survives exposure to ultraviolet (UV) light.

This test requirement shall apply only for coated surfaces on the exterior of the enclosure or that may routinely be exposed to sunlight.

Two panels prepared, per [Figure 8](#), shall be tested per ASTM D4587, cycle 2 (ultraviolet accelerated weathering) for 500 h utilizing either the FS-40 bulb, or using UVB-313EL lamps with an irradiance control system, with a cycle of 4 h of ultraviolet at $60\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ ($140\text{ }^{\circ}\text{F} \pm 4\text{ }^{\circ}\text{F}$), followed by 4 h of condensation at $50\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ ($122\text{ }^{\circ}\text{F} \pm 4\text{ }^{\circ}\text{F}$). For chambers utilizing an irradiance control system, the irradiance shall be set at 0.48 W/m^2 at 310 nm. Loss of gloss shall not exceed 50% of original gloss per ASTM D523. The coating shall not exhibit cracking per ASTM D661 or checking per ASTM D660 under unaided visual inspection.

5.5.6 Abrasion resistance

This test demonstrates how the substrate plus the coating system stands up to abrasion and handling.

This test requirement shall apply only for coated surfaces on the exterior of the enclosure.

One coated panel, per [Figure 9](#), having the minimum dry film thickness of the total coating system shall be tested using a CS-10 wheel and 1000 g weight, in accordance with ASTM D4060. A total of 3000 cycles shall be run with the wheels resurfaced before testing and after each 500-cycle run.

Upon completion of the test, no bare substrate shall be present.

5.5.7 Chipping resistance test

This test demonstrates how the substrate plus the coating system stands up to chipping commonly caused by shipping, storage, and installation.

This test requirement shall apply only for coated surfaces on the exterior of the enclosure.

Two coated panels per [Figure 10](#), are to be tested per ASTM D3170 at room temperature using 410 kPa (60 psig) gauge air pressure.

Evaluate the panels for chip size, including only chips that expose bare substrate. No chip shall be greater than 2.0 mm (0.08 inch) in diameter.

6. Labels

6.1 Purpose

Labeling can be an important aspect of pad-mounted enclosure integrity. Labeling can alert or inform an individual of potential hazard. Pad-mounted enclosures should be designed to achieve a high degree of integrity. When labels are attached to pad-mounted enclosures, they should be located as near the hazard as practicable. Labels should be concise and simple to understand and should accurately communicate the type and degree of hazard.

6.2 Application

The application of any labels, whether intended for interior or exterior use, shall be subject to an agreement between the purchaser and the manufacturer.

7. General

7.1 Shipment

The manufacturer shall provide a method of shipment that will allow the enclosure to be received by the purchaser such that it still meets the performance tests required by this standard.

7.2 Coating repair procedure

A coating system repair procedure shall be recommended by the manufacturer.

7.3 Coating touch-up prior to shipment

Touch-up, when required, shall be done at final inspection before any equipment is shipped. In areas where the integrity of the coating system is violated, the touch-up shall blend smoothly and meet all performance criteria of this standard.

Annex A

(normative)

Comparative weight loss procedure

The procedure is as follows:

- a) Inspect welded panels to assure that welds are smooth and will not collect salt in any area when exposed in accordance with ASTM B117 with the major axis of the weld upright.
- b) Make sure that all test panels are thoroughly dry. Record the weight of each panel to the nearest 0.0001 g.
- c) Expose all test panels to 1500 h salt spray in accordance with ASTM B117.
- d) After exposure, immediately remove the test specimens and immerse in warm water.
- e) Manually scour each panel while wet using a non-metallic, abrasive pad. Remove rust from pits with a sharp tool.
- f) After scouring all panels, rinse in clean warm water (never let the panels dry until rinsing is complete).
- g) Make sure that the test panels are thoroughly dry.
- h) Reweigh the panels to the nearest 0.0001 g and calculate the percent weight loss.

Annex B

(informative)

Commonly used substrate steels

carbon steel: Steel alloy with carbon (C), sulfur (S), and phosphorus (P) as the principal elements, restricted amounts of manganese (Mn) $< 1.65\%$, silicon (Si) $< 0.60\%$, and copper (Cu) $< 0.60\%$, and negligible amounts of other elements. Carbon steels can be categorized as low-carbon ($C \leq 0.30\%$), medium-carbon ($0.30\% < C \leq 0.60\%$), or high-carbon ($0.60\% < C \leq 1.00\%$).

copper bearing steel: (Also known as weathering steel) High-strength low-alloy steel with approximately 0.15% carbon, 0.05% maximum sulfur and a minimum of 0.2% copper content, exhibiting a minimum yield strength of 345 MPa and suitable for welding. ASTM A242 and ASTM A588 describe such steels in detail.

stainless steel: A steel alloy with chromium (Cr) as the main alloying element. Specific alloys have varying alloy compositions using carbon (C), nickel (Ni), manganese (Mn), phosphorus (P), sulfur (S), silicon (Si), nitrogen (N), and sometimes molybdenum (Mo) or titanium (Ti).

- **AISI 304** (UNS S30400): $18.0\% \leq Cr \leq 20.0\%$, $C \leq 0.08\%$, $8.0\% \leq Ni \leq 10.5\%$, $Mn \leq 2.00\%$, $P \leq 0.045\%$, $S \leq 0.03\%$, $Si \leq 1.00\%$, $N \leq 0.10\%$
- **AISI 304L** (UNS S30403): $18.0\% \leq Cr \leq 20.0\%$, $C \leq 0.03\%$, $8.0\% \leq Ni \leq 12.0\%$, $Mn \leq 2.00\%$, $P \leq 0.045\%$, $S \leq 0.03\%$, $Si \leq 1.00\%$, $N \leq 0.10\%$
- **AISI 316** (UNS S31600): $16.0\% \leq Cr \leq 18.0\%$, $C \leq 0.08\%$, $10.0\% \leq Ni \leq 14.0\%$, $Mn \leq 2.00\%$, $P \leq 0.045\%$, $S \leq 0.03\%$, $Si \leq 1.00\%$, $N \leq 0.10\%$, $2.0\% \leq Mo \leq 3.0\%$
- **AISI 316L** (UNS S31603): $16.0\% \leq Cr \leq 18.0\%$, $C \leq 0.03\%$, $10.0\% \leq Ni \leq 14.0\%$, $Mn \leq 2.00\%$, $P \leq 0.045\%$, $S \leq 0.03\%$, $Si \leq 1.00\%$, $N \leq 0.10\%$, $2.0\% \leq Mo \leq 3.0\%$
- **AISI 409** (UNS S40900): $10.50 \leq Cr \leq 11.75\%$, $C \leq 0.08\%$, $Ni \leq 0.50\%$, $Mn \leq 1.00\%$, $P \leq 0.045\%$, $S \leq 0.045\%$, $Si \leq 1.00\%$, $N \leq 0.03\%$, and minimum Ti of 6 times %C with a max of 0.75%

NOTE 1—AISI – American Iron and Steel Institute. AISI publications are available from the American Iron & Steel Institute, 25 Massachusetts Avenue, NW, Suite 800 Washington DC 20001.

NOTE 2—UNS – Unified numbering system.

NOTE 3—The “L” designation indicates a “low carbon” version – thus 304L is a low carbon version of 304.

NOTE 4—409 is a ferritic stainless steel and is magnetic, while 304, 304L, 316, and 316L are austenitic stainless steels and are not magnetic.

Annex C

(informative)

Pry bar

C.1 General

The pry bar, Figure C.1, depicted in this informative annex is just one design intended to meet the functional requirements of 4.3.1.1. Other pry bar designs complying with 4.3.1.1 are acceptable.

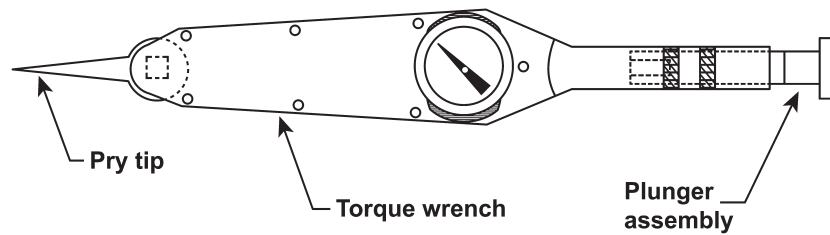


Figure C.1—Assembled pry bar

The pry bar consists of three parts: pry tip (Figure C.2), torque wrench, and axial force plunger (Figure C.3). The pry tip is designed for installation on a half-inch drive of a torque wrench. The plunger is designed to be inserted into the handle of a torque wrench with a hollow handle that has an interior stop for the plunger to fit into and press against.

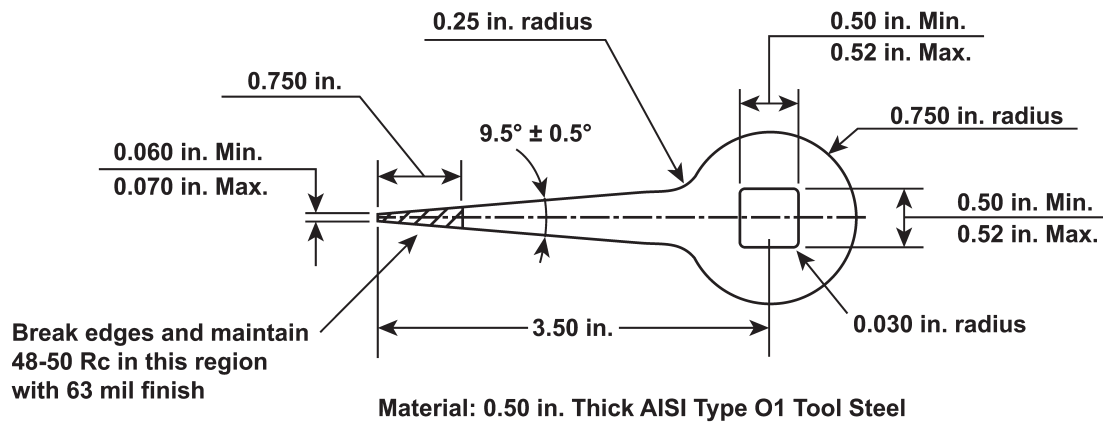


Figure C.2—Pry tip

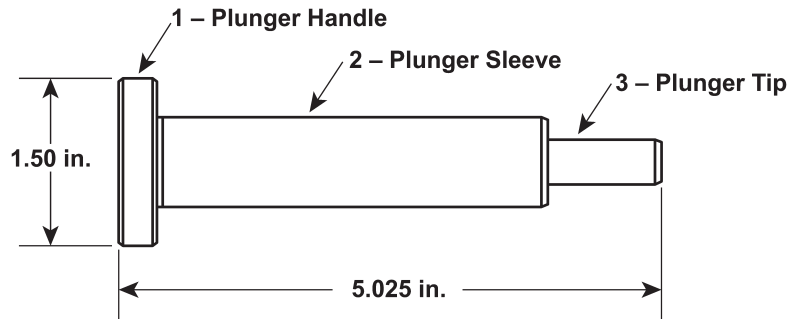


Figure C.3—Plunger assembly

C.1.1 Pry tip calibration

The addition of a pry tip to the torque wrench increases the moment arm of the tool. Consequently, the tool must be re-calibrated to account for the longer moment arm. Calibration is accomplished as follows:

- Clamp approximately 1 inch of the pry tip to a workbench or other rigid surface.
- Select a point on the torque tool handle to apply force.
- Measure the distance (in inches) from this point to the end of the pry tip.
- Divide 900 inch-lb by this distance to determine the force (in pounds) to be applied during calibration.
- Using a calibrated force measurement tool, apply the calculated force to the handle and record the torque indicated on the torque wrench dial.
- This value becomes the target prying leverage force to be used during the pry test.

C.1.2 Plunger calibration

The plunger is a simple spring force measurement tool made from machined steel parts. The plunger must be calibrated and marked to indicate when the desired force has been reached. The plunger fits into the hollow pipe handle of the torque wrench and must be installed into the torque wrench prior to calibration. Calibration is accomplished as follows:


- Apply force to the plunger using a calibrated force measurement tool.
- As force is applied, the plunger body moves into the torque wrench handle. When the desired force is obtained (50 lb) mark the plunger body at the torque wrench handle rim.
- During the pry test, depress the plunger until the mark aligns with the wrench handle rim.

C.2 Drawings

All dimensions are in inches. All tolerances are ± 0.03 unless otherwise stated.

C.3 Assembly instructions

- a) Insert plunger tip (Figure C.4) from threaded end of plunger sleeve (Figure C.5).

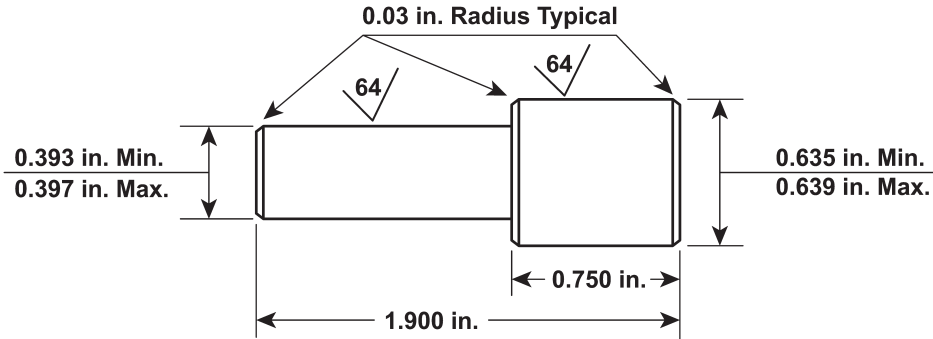

Material: 11/16 in. Dia. AISI 304 Stainless Steel Rod
Annealed and Ground – 1.900 in. long

Figure C.4—Plunger tip

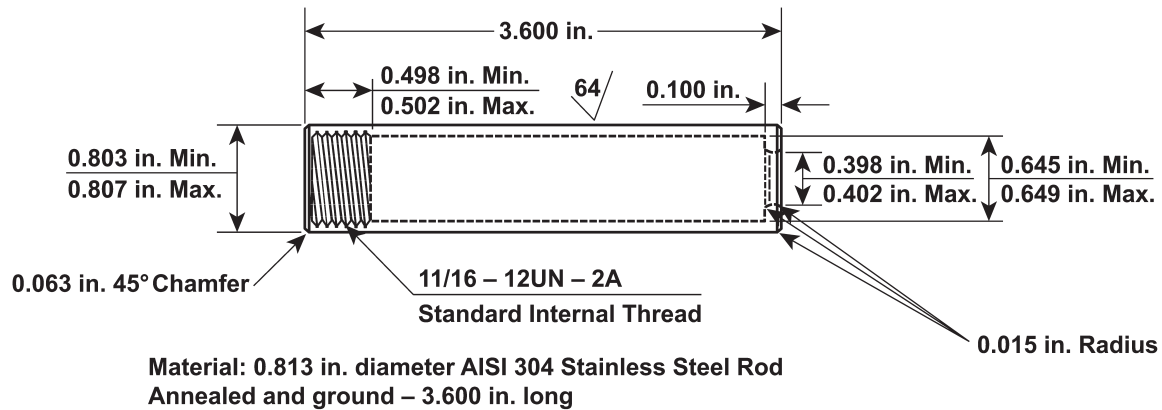


Figure C.5—Plunger sleeve

- b) Insert plunger spring (Figure C.6) from threaded end of plunger sleeve.


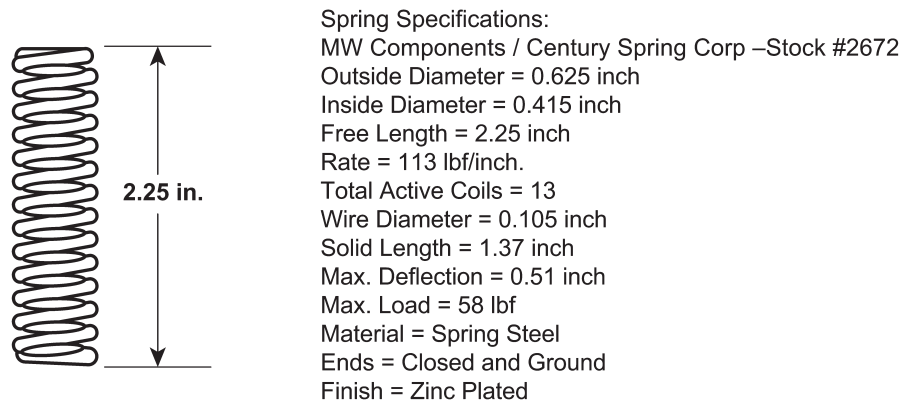


Figure C.6—Plunger spring

- c) Screw plunger handle (Figure C.7) into plunger sleeve.

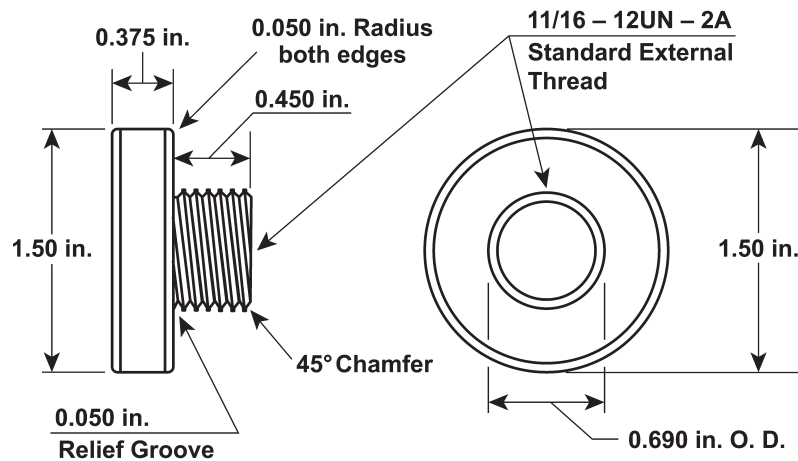

**Material: 1.50 in. Diameter AISI 304
 Stainless steel Rod, Annealed
 0.825 in. Long**

Figure C.7—Plunger handle

Annex D

(informative)

Substrate surface preparation

D.1 General

Coating adhesion to the substrate material is highly dependent on proper surface preparation and proper cleaning of the substrate material. The surface preparation methods listed below and the technical data sheets for the coating to be applied should be considered to ensure the appropriate surface profile prior to applying a protective coating. Proper cleaning is also essential in ensuring the best performance of the protective coating systems.

Listed below are SSPC (Society of Protective Coatings), NACE (National Association of Corrosion Engineers), BS (British Standards), ISO (International Standards Organization), and ASTM (American Society for Testing and Materials) standards associated with cleaning and surface preparation.

D.2 Iron and carbon steel and copper bearing steel substrates

- SSPC-SP1/ISO 8504 – Solvent Cleaning
- SSPC-SP2 – Hand Tool Cleaning
- SSPC-SP3 – Power Tool Cleaning
- SSPC-SP11 – Power Tool Cleaning to Bare Metal
- SSPC-SP7/NACE 4 – Brush-Off Blast Cleaning
- SSPC-SP14/NACE 8 – Industrial Blast Cleaning
- SSPC-SP6/NACE 3 – Commercial Blast Cleaning
- SSPC-SP10/NACE 2 – Near-White Blast Cleaning
- SSPC-SP5/NACE 1 – White Metal Blast Cleaning
- SSPC-VIS 1 – Pictorial Surface Standard Dry Blast Cleaning
- SSPC-SP12/NACE 5 – High- and Ultrahigh-Pressure Water Jetting Prior to Recoating
- ISO 8501 – Pictorial Appearance of Different Rust Grades at Various Levels of Cleanliness
- ASTM D4417–11 [B4]²⁰ – Standard Test Methods for Field Measurement of Surface Profile of Blast Cleaned Steel
- ASTM D2200–08/ASTM D2200–17 [B3] – Pictorial Surface Preparation Standards and Guides for Painting Steel Surfaces

²⁰The numbers in brackets correspond to those of the bibliography in [Annex E](#).

D.3 Stainless steel and non-ferrous substrates

- SSPC-SP1 – Solvent Cleaning
- SSPC-SP7/NACE 4 – Brush-Off Blast Cleaning
- SSPC-SP17 – Thorough Abrasive Blast Cleaning of Non-Ferrous Metals
- BS 7079 [B6] – Surface Roughness and Cleanliness Grade of Stainless Steel
- ASTM B254–92 [B2] – Standard Practice for Preparation of and Electroplating on Stainless Steel

Annex E

(informative)

Bibliography

Bibliographical references are resources that provide additional or helpful material but do not need to be understood or used to implement this standard. Reference to these resources is made for informational use only.

[B1] ANSI C2, Accredited Standards Committee C-2, National Electrical Safety Code® (NESC®).^{21,22}

[B2] ASTM B254–92, Standard Practice for Preparation of and Electroplating on Stainless Steel.²³

[B3] ASTM D2200–08/ASTM D2200–17, Standard Practice for Use of Pictorial Surface Preparation Standards and Guides for Painting Steel Surfaces.

[B4] ASTM D4417–11, Standard Test Methods for Field Measurement of Surface Profile of Blast Cleaned Steel.

[B5] Bringas, J. E. and M. L. Wyman, The Metals Black Book: Ferrous Metals, 3rd Ed. Edmonton, Alberta: CASTI Publishing Inc., 1998.

[B6] BS 7079, Surface Roughness and Cleanliness Grade of Stainless Steel.

[B7] IEEE Std C57.12.20™, IEEE Standard for Overhead-Type Distribution Transformers 500 kVA and Smaller; High Voltage, 34 500 V and Below; Low Voltage, 7970/13 800Y V and Below.^{24,25}

[B8] IEEE Std C57.12.23™, IEEE Standard for Submersible Single-Phase Transformers: 250 kVA and Smaller; High Voltage 34 500 GrdY/19 920 V and Below; Low Voltage 600 V and Below.

[B9] IEEE Std C57.12.24™, IEEE Standard for Submersible, Three-Phase Transformers, 3750 kVA and Smaller; High Voltage, 34 500 GrdY/19 920 V and Below; Low Voltage, 600 V and Below.

[B10] IEEE Std C57.12.28™, IEEE Standard for Pad-Mounted Equipment—Enclosure Integrity.

[B11] IEEE Std C57.12.30™, IEEE Standard for Pole-Mounted Equipment – Enclosure Integrity for Coastal Environments.

[B12] IEEE Std C57.12.31™, IEEE Standard for Pole-Mounted Equipment—Enclosure Integrity.

[B13] IEEE Std C57.12.32™, IEEE Standard for Submersible Equipment—Enclosure Integrity.

[B14] IEEE Std C57.12.34™, IEEE Standard Requirements for Pad-Mounted, Compartmental-Type, Self-Cooled, Three-Phase Distribution Transformers, 10 MVA and Smaller; High-Voltage, 34.5 kV Nominal System Voltage and Below; Low-Voltage, 15 kV Nominal System Voltage and Below.

²¹The NESC is available from the Institute of Electrical and Electronics Engineers (<https://standards.ieee.org/>).

²²ANSI publications are available from the American National Standards Institute (<https://www.ansi.org/>).

²³ASTM publications are available from the American Society for Testing and Materials (<https://www.astm.org/>).

²⁴The IEEE standards or products referred to in **Annex E** are trademarks owned by The Institute of Electrical and Electronics Engineers, Incorporated.

²⁵IEEE publications are available from The Institute of Electrical and Electronics Engineers (<https://standards.ieee.org/>).

[B15] IEEE Std C57.12.35™, IEEE Standard Bar Coding for Distribution Transformers and Step-Voltage Regulators.

[B16] IEEE Std C57.12.38™, IEEE Standard for Pad-Mounted-Type, Self-Cooled, Single-Phase Distribution Transformers 250 kVA and Smaller: High Voltage, 34 500 GrdY/19 920 V and Below; Low Voltage, 480/240 V and Below.

RAISING THE WORLD'S STANDARDS

Connect with us on:



Twitter: twitter.com/ieeesa



Facebook: facebook.com/ieeesa



LinkedIn: linkedin.com/groups/1791118



Beyond Standards blog: beyondstandards.ieee.org



YouTube: youtube.com/ieeesa

standards.ieee.org

Phone: +1 732 981 0060