
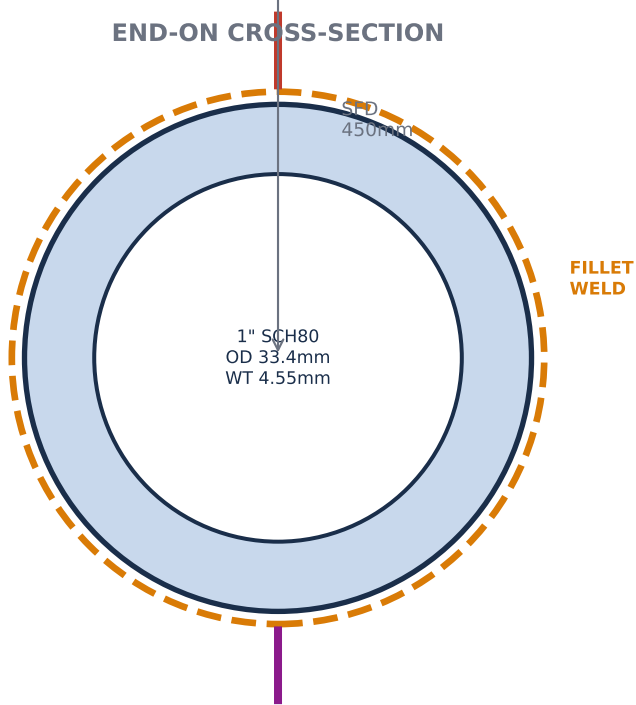


RADIOGRAPHIC TESTING PLAN — SOCKET WELD FITTING (1" NPS SCH 80 STAINLESS)

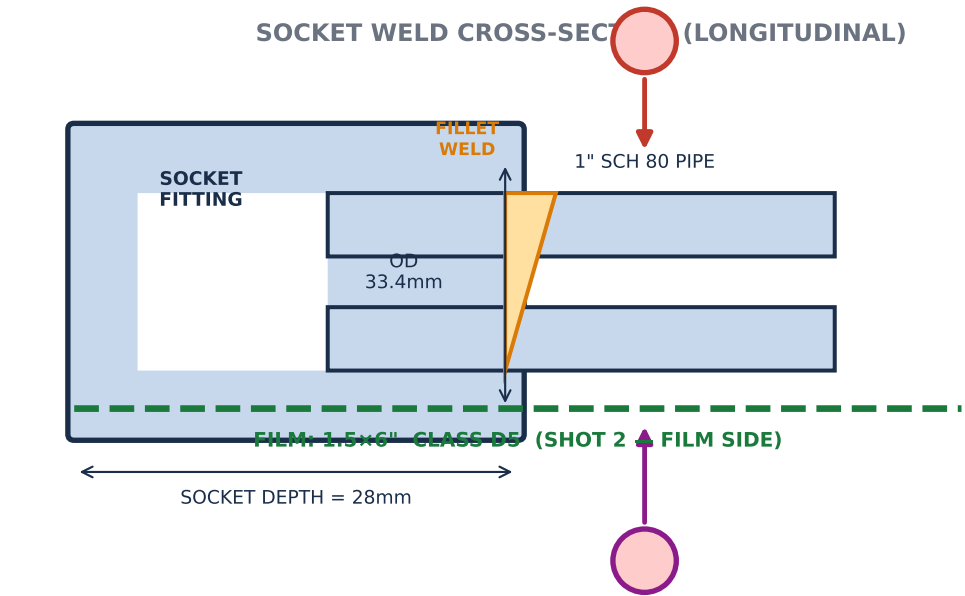

EXPOSURE SCHEDULE

SHOT	TECHNIQUE	kV	mA	S2 BOT SFD(mm)	FILM	COVERAGE	TIME(min)
1	SWSI — TOP	80	3.0	450	1.5×6 D5	180°	4

2	SWSI — BOT	80	3.0	450	1.5×6 D5	180°	4
---	------------	----	-----	-----	----------	------	---

NOTES:

- Per ASME B31.3 Process Piping — socket weld examination
- Material: ASTM A312 TP316L Stainless Steel pipe; A182 F316L fitting
- Film density: 2.0 – 3.5 per ASTM E94
- IQI: ASTM E747 wire set, 2T sensitivity required
- Single-wall single-image (SWSI) — 2 shots for 360° coverage
- Gap between pipe & socket shall be 1/16" min per B31.3

NDT INSPECTION SERVICES

1" NPS SCH 80 Socket Weld Fitting — 316L SS

Socket Fillet Weld RT Plan — 2-Shot SWSI

ACCEPTANCE STD: ASME B31.3

Date: 2025-03-15 Rev: A

DRAWING NUMBER

RT-TEST-SOCKET-WELD-001

MATERIAL: ASTM A312 TP316L / A182 F316L

SCALE: 1:5 SHEET: 1 of 1

NDT STANDARD

ASME Sec V Art. 2

ASTM E94

DISTRIBUTION: UNRESTRICTED