



RADIOGRAPHIC TESTING PLAN — STRUCTURAL T-JOINT FILLET WELD (PL 20mm × PL 16mm)

T-JOINT CROSS-SECTION (FILLET BOTH SIDES)

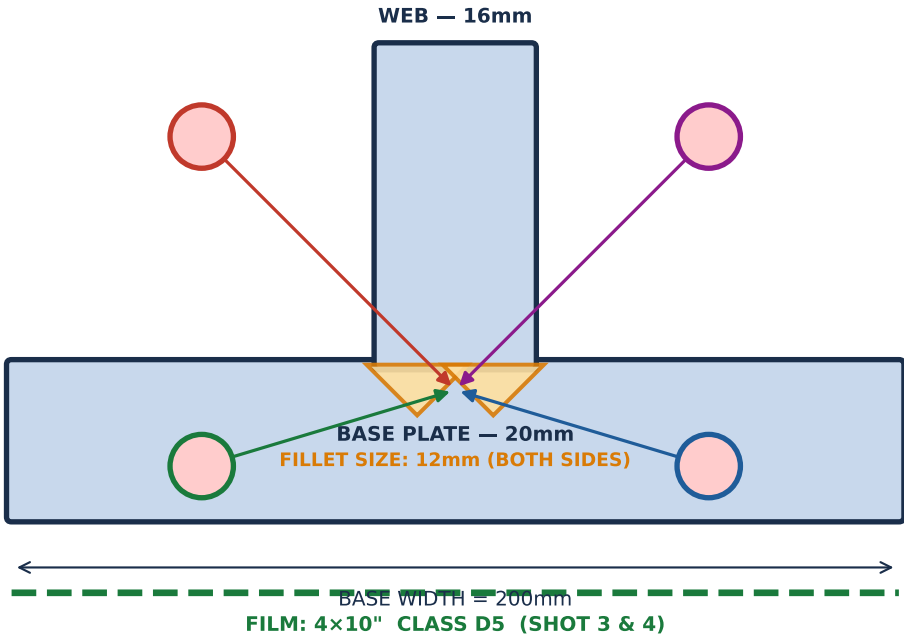

- NOTES:
- Per AWS D1.1 Structural Welding Code — Steel
 - Material: ASTM A36 Structural Steel plate
 - Film density: 2.0 – 3.5 (ASTM E94)
 - IQI: ASTM E747 wire penetrameter, 2T sensitivity
 - Fillet weld RT per AWS D1.1 Annex K procedure
 - Geometric Ug ≤ 0.51mm, focal spot 1.5mm

SIDE VIEW — SHOT LAYOUT

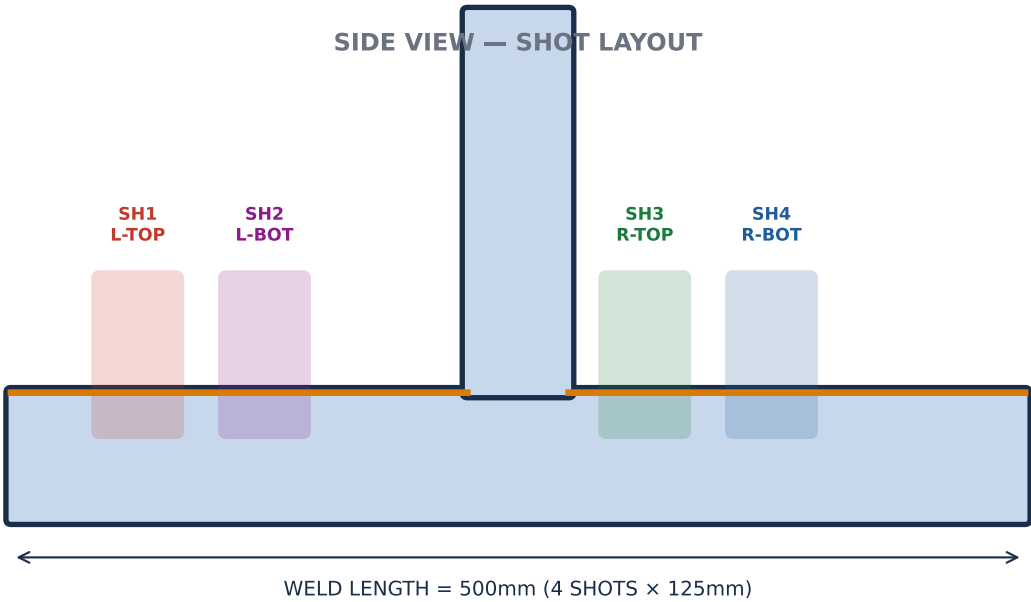

EXPOSURE SCHEDULE

SHOT	LOCATION	ANGLE	kV	mA	SFD(mm)	FILM	TIME(min)
1	TOP-LEFT	45°	100	3.5	600	4×10 D5	6
2	BOT-LEFT	45°	100	3.5	600	4×10 D5	6
3	TOP-RIGHT	45°	100	3.5	600	4×10 D5	6
4	BOT-RIGHT	45°	100	3.5	600	4×10 D5	6

NDT INSPECTION SERVICES

A36 Steel T-Joint — PL 20mm × PL 16mm

Fillet Weld RT Plan — 4-Shot

ACCEPTANCE STD: AWS D1.1

Date: 2025-03-15 Rev: A

DRAWING NUMBER

RT-TEST-TJOINT-001

MATERIAL: ASTM A36

SCALE: 1:5 SHEET: 1 of 1

NDT STANDARD

ASME Sec V Art. 2

ASTM E94

DISTRIBUTION: UNRESTRICTED