Zwick Roell

Print date: 02.02.21

Test report

Customer	:	-redacted-
Job no.	:	OPP.228903
Test standard	:	DIN EN ISO 6892-2 on 350°C
Material	:	Metallic arroy
Specimen type	:	M16 threaded head Ø 10mm
Tester	:	ct-Sam Liu
Machine data	:	Extensometer: LaserXtens (TZ) Ceramic clip-on

Test speeds	:	Method B		Speed, yield point	:	5	MPa/s
Pre-load	:	5	MPa	Test speed	:	0,09	1/min
Speed, Young's modulus	:	5	MPa/s				

Test results:

Legend	No.	m_E GPa	$R_{p0.2}$ MPa	R_m MPa	F_m kN	A_g %	A_{50mm} %	A_t %	d_0 mm	S_0 mm²	Temperature
	1	113	160	418	32,91	24,60	29,4	29,6	10,007	78,65	350°C
	2	140	158	301	23,65	5,47	-	-	10,005	78,62	350°C

Legend	No.	Extensometer
	1	LaserXtens (TZ)
	2	Ceramic clip-on

This is the way new reports look today.
Static and per test only.

Zwick Roell

Print date: 02.02.21

Series graph:

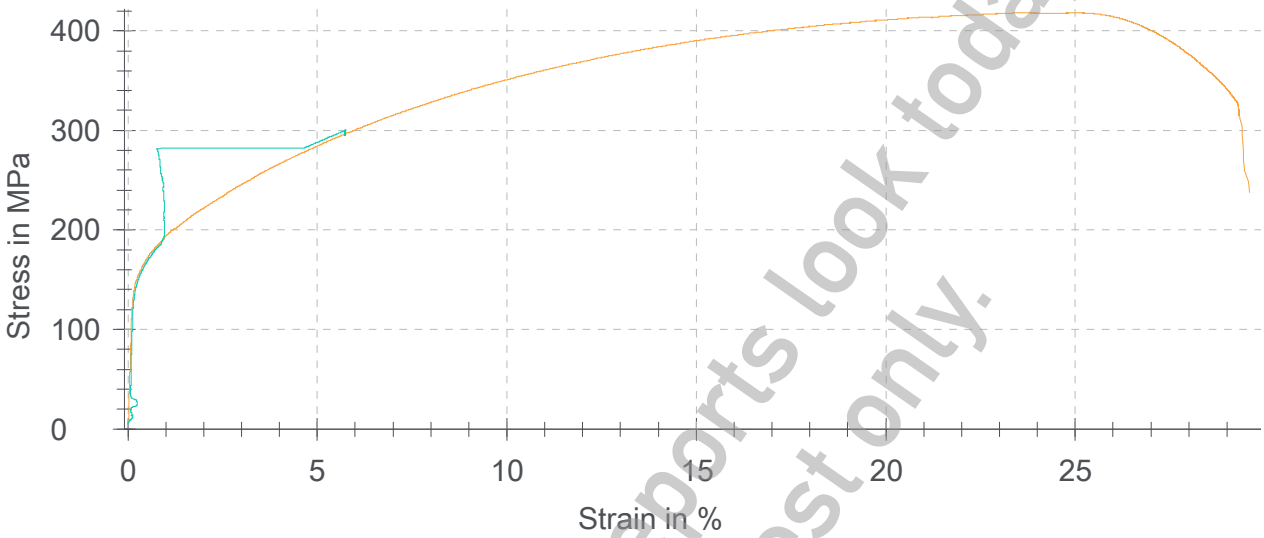

Statistics:

Series	m_E	$R_{p0.2}$	R_m	F_m	A_g	A_{50mm}	A_t	d_0	S_0
n = 2	GPa	MPa	MPa	kN	%	%	%	mm	mm²
$\bar{x}$	127	159	360	28,28	15,04	29,4	29,6	10,006	78,63
s	19	2	83	6,55	13,53	-	-	0,001	0,02
□ [%]	15,26	1,19	23,13	23,16	89,95	-	-	0,01	0,03

This is the way how reports look today.
Static and per test only.

Print date: 02.02.21

Speicme Graph :
Extensometer: LaserXtens (TZ)

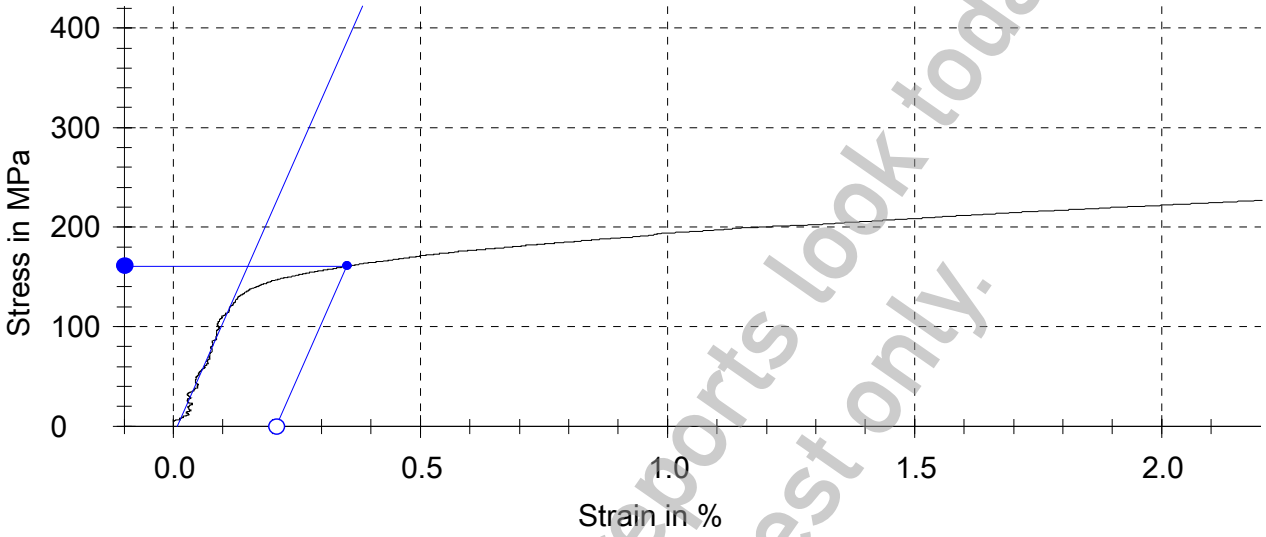

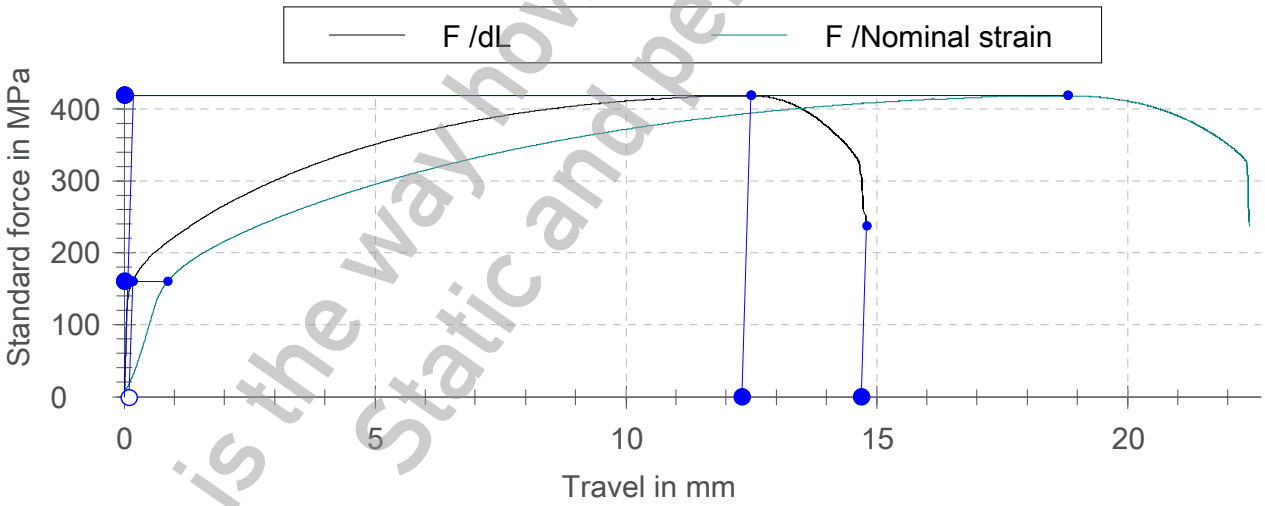

This is the way how reports look today.
Static and per test only.

Print date: 02.02.21

Extensometer: Ceramic clip-on

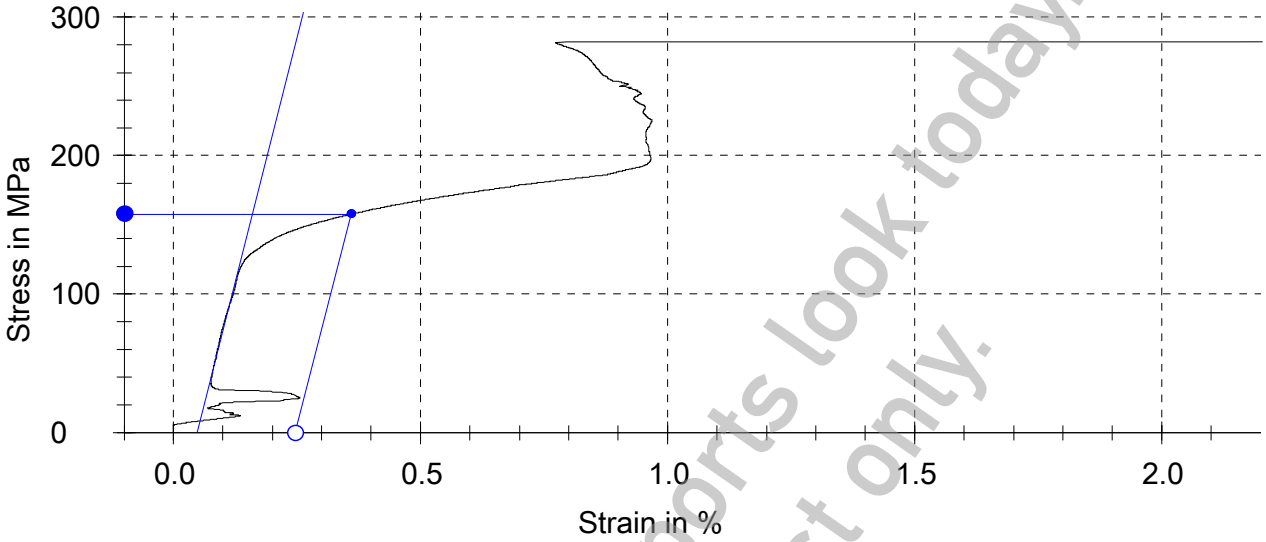

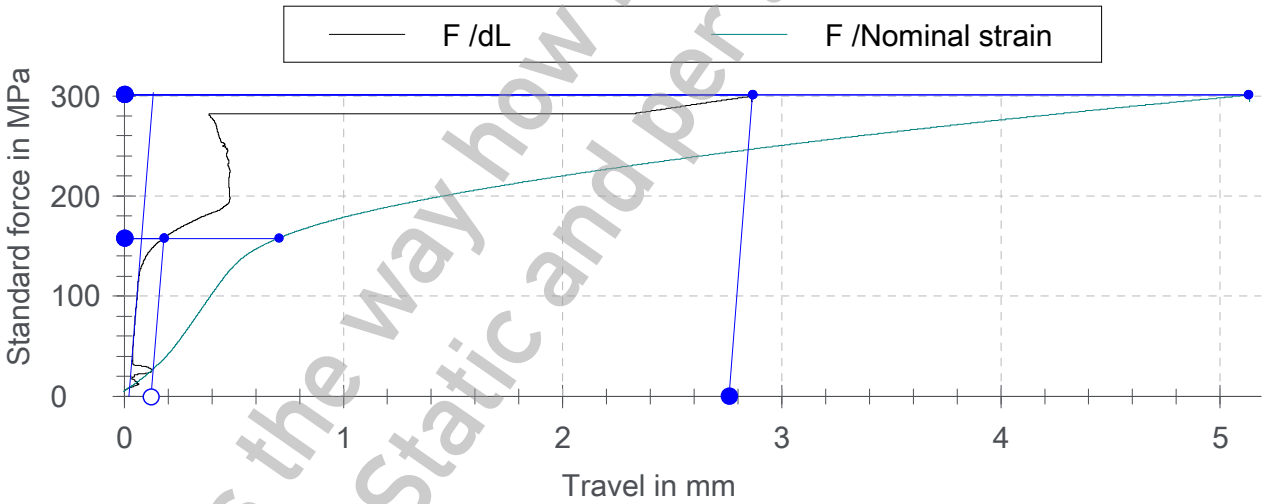

This is the way how reports look today.
Static and per test only.