

**AMENDMENT NO. 1 MARCH 2026**

**TO**

**IS 18809 : 2024 WEAR AND ABRASION RESISTANT STEEL  
SHEET AND PLATES — SPECIFICATION**

(Page 1, Clause 6.1, line 6) — Insert the following at the end:

‘Steel used for manufacturing the product shall conform to IS 14650.’

(Page 1, Clause 7.1, line 4) — Insert ‘or IS 8811’ after IS 228.

(Page 2, Table 2) — Insert the following notes:

‘NOTE — If agreed upon between the manufacturer and the purchaser, the content of Cr, Ni, and Mo may be increased beyond the specified limits, and other unspecified elements may be added to meet special application requirements such as high-temperature service (with or without corrosive conditions), high hardness, or other specific needs. In such cases, the hardness requirement shall also be mutually agreed upon, provided it exceeds the minimum specified hardness of the nearest applicable grade.’

(Page 3, Clause 8.1) — Substitute the following for the existing:

**‘8.1 Hardness Test**

Product shall conform to the hardness requirements specified in Table 5, when tested in accordance with IS 1500 (Part 1). Minimum core hardness shall be 90 percent of the guaranteed minimum surface hardness for plates with thickness greater than 20 mm. Core hardness for higher thickness may be determined as given in Annex B.

NOTE — IS 4258 shall be used for conversion of hardness values.

(Page 3, Clause 8.1.1) — Substitute the following for the existing:

**8.1.1 Sampling**

Hardness test to be conducted on sample drawn from the heat treated sheet/plate.

The test unit shall be 60 MT or part thereof. For plates from Plate Mill the test sample shall contain product from same form, grade, quality, heat treated condition and thickness. The thickness of the test sample shall not deviate more than 5 mm from the nominal thickness. The sample to be drawn from one end of the heat - treated plate at quarter width location of the plate. For sheets/plates produced from coil, three samples from each coil (head end, middle and tail end) shall be taken.’

(Page 4, Informal table, col (3), Heading) — Substitute the following for the existing:

‘Depth of Milling or Grinding, Min (mm)’

(Page 5, Clause 11.2) — Substitute the following for the existing:

‘11.2 Minor surface defects may be removed by the manufacturer by grinding. Maximum permissible depth of ground areas with a maximum of 2 percent of the inspected area as per Table 9 given below. The grinding shall be even and smooth and shall be widened enough to remove sharp ridges.

**Table 9 Maximum Permissible Depth Ground Areas with a  
Maximum of 2 Percent of the Inspected Area**

(Clause 11.2)

| SI No. | Nominal Thickness of the Product<br>t, mm | Permitted Grinding Depth,<br>mm |
|--------|-------------------------------------------|---------------------------------|
| (1)    | (2)                                       | (3)                             |
| i)     | $3 \leq t < 8$                            | 0.4                             |
| ii)    | $8 \leq t < 15$                           | 0.5                             |
| iii)   | $15 \leq t < 25$                          | 0.7                             |

**Amendment No. 1 to IS 18809 : 2024**

| SI No. | Nominal Thickness of the Product<br>t, mm | Permitted Grinding Depth,<br>mm |
|--------|-------------------------------------------|---------------------------------|
| (1)    | (2)                                       | (3)                             |
| iv)    | $25 \leq t < 40$                          | 0.9                             |
| v)     | $40 \leq t < 60$                          | 1.1                             |
| vi)    | $60 \leq t < 80$                          | 1.3                             |
| vii)   | $80 \leq t < 150$                         | 1.6                             |
| viii)  | $150 \leq t < 250$                        | 1.9                             |
| ix)    | $250 \leq t < 400$                        | 2.2                             |

(Page 5, Clause 12) — Insert the following new clause at the end:

**12.1 FLATNESS TOLERANCE**

If agreed at the time of enquiry and order, special flatness tolerances of Q&T plates may be given as per Table 10.

**Table 10 Special Tolerance on Flatness**

| SI No.                                                                         | Nominal Thickness<br>t, mm | Measuring Length <sup>a</sup> , mm |       |       |
|--------------------------------------------------------------------------------|----------------------------|------------------------------------|-------|-------|
|                                                                                |                            | 1 000                              | 2 000 | 4 000 |
| (1)                                                                            | (2)                        | (3)                                | (4)   | (5)   |
| i)                                                                             | $3 \leq t < 5$             | 7                                  | 14    | 28    |
| ii)                                                                            | $5 \leq t < 8$             | 7                                  | 13    | 26    |
| iii)                                                                           | $8 \leq t < 15$            | 7                                  | 12    | 24    |
| iv)                                                                            | $15 \leq t < 25$           | 7                                  | 11    | 22    |
| v)                                                                             | $25 \leq t < 40$           | 7                                  | 11    | 20    |
| vi)                                                                            | $40 \leq t < 250$          | 6                                  | 10    | 20    |
| vii)                                                                           | $250 \leq t \leq 400$      | 7                                  | 11    | 22    |
| <sup>a</sup> Use 1000 mm measuring length when wave pitch is $\leq 1\,000$ mm. |                            |                                    |       |       |

(Page 6, Annex A) — Insert the followings at an appropriate place:

‘IS 8811 : 1998 — Method for emission spectrometric analysis of plain carbon and low alloy steels point to plane technique (*first revision*)

IS 14650 : 2023 — Unalloyed and alloyed steel ingot and semi-finished products for re-rolling purposes — Specification (*first revision*)

IS 4258 : 2018/ISO 18265 : 2013 — Metallic materials — Conversion of hardness values (*third revision*)

IS 1501 (Part 1) : 2025/ISO 6507-1 : 2023 — Metallic materials — Vickers hardness test: Part 1 Test method (*sixth revision*)’

(Page 6) — Insert the following new annex:

**‘ANNEX B**

(Clause 8.1)

**DETERMINATION OF CORE HARDNESS**

The Core hardness is defined as the average through thickness hardness in the Plate in  $1/6^{\text{th}}$  the thickness on either side of the center point of plate thickness, that is  $1/3^{\text{rd}}$  the inner thickness of the plate. The hardness is measured by Vickers hardness testing (*see* IS 1501 (Part 1)) equipment at least 3 different spots – at  $1/3$ ,  $1/2$  and  $2/3$  thickness along the thickness of the plate, as per the figure given below:

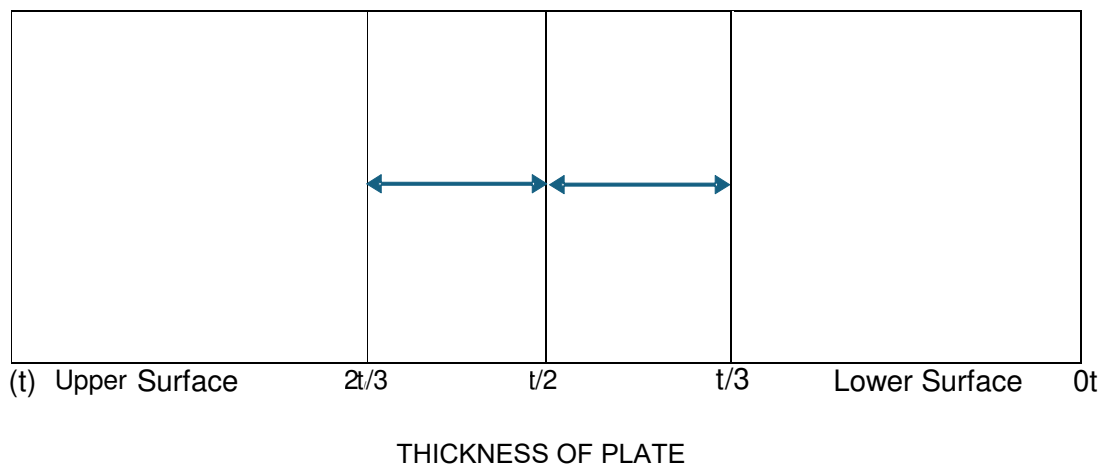


FIG 1. LOCATION FOR CORE HARDNESS MEASUREMENT

(Page 7, Annex B, title) — Substitute ‘Annex C’ for ‘Annex B’.

(Foreword) — Substitute ‘Annex C’ for ‘Annex B’.