

AMENDMENT NO. 1 MAY 2025

TO

IS 16058 : 2024 DUNNAGE PALLETS MADE FROM RECYCLED PACKAGING WASTES FOR WAREHOUSING APPLICATION — SPECIFICATION

(First Revision)


(Page 17, clause C-2) — Substitute the following for the existing:

‘C-2 PROCEDURE

The test specimen shall be clamped firmly between 2 frames made of 20 mm thick and 20 mm wide hardwood strips, by 8 bolts of 5 mm diameter placed at equal distances from the corner (*see* Fig. 12). This frame containing the specimen shall be held rigidly on 4 pillars at its corners. It may be noted that minimum internal length and width of the test specimen shall be 90 mm × 90 mm after clamping. A cylindrical block of mild steel of size 50 mm (Dia) having a mild steel hemispherical end with a radius of 25 mm shall be arranged to fall freely on the centre of the specimen by suitable means (*see* Fig. 13). The mass of the block together with any associated falling part shall be 4 kg. The height required for the block should be suitable to achieve a mass of 4 kg. The block shall be allowed to fall first from a height of 25 mm measured from the upper surface of the specimen and then from successive heights rising in increments of 25 mm until final failure of the specimen occurs. The failure of the specimen may take the form of a puncture or a visible fracture at the bottom of the specimen.’

(Page 18, Fig. 13) — Substitute the following for the existing:

DROP TEST EQUIPMENT

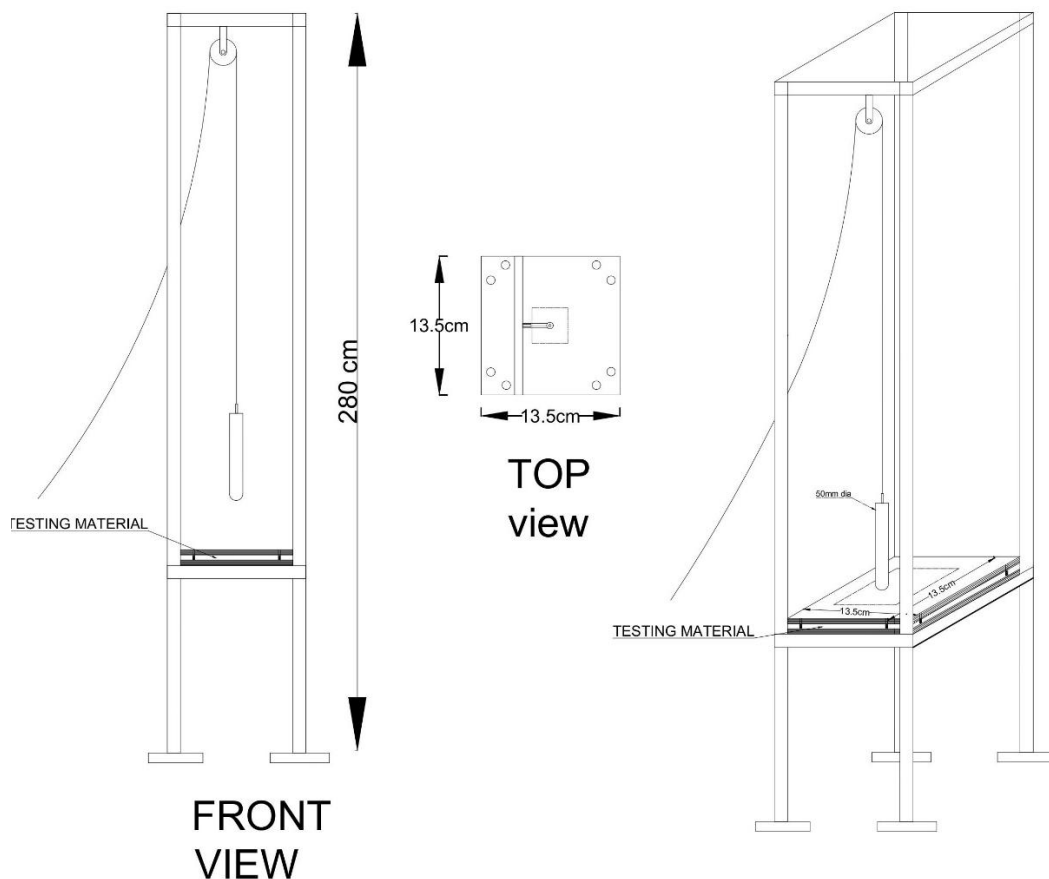

Amendment No. 1 to IS 16058 : 2024

[Page 12, clause **17.2**, Sl No. (i), (ii), (iii)] — Substitute the following for the existing:

<i>Sl No.</i>	<i>Tests</i>	<i>Test Method</i>	<i>Minimum Requirement</i>
(1)	(2)	(3)	(4)
i)	Tensile stress at proportional limits (kg/cm ²)	Annex B	75
ii)	Tensile stress at maximum load (kg/cm ²)	Annex B	80
iii)	Modulus of elasticity in tension parallel to grain (kg/cm ²)	Annex B	2 000