

AMENDMENT NO. 2 AUGUST 2001
TO
IS 3736 : 1995 CANVAS BOOTS, RUBBER SOLE —
SPECIFICATION
(Second Revision)

(Page 2, clause 4.1.7.1) — Delete the clause and renumber the subsequent clauses.

[Page 3, clause 4.1.7.3 (renumbered as 4.1.7.2)] — Substitute the following for the existing:

'4.1.7.2 The rubber components shall conform to Table 4 when tested.'

(Page 3, Table 4, Note 1) — Add the following after the existing text

'However in case it is not possible then 4.2.5.3 of IS 13695:1993 shall be followed.'

(Page 5, clause 4.7) — Substitute the following for the existing:

'4.7 Consolidation Test

From the quarter, cut a strip of 25.0 ± 0.5 mm width along the length of the boot and of sufficient length to permit separation over a length of 75 mm. Carry out the test on two test pieces (one from each odd) at the rate of traverse of 100 ± 10 mm per minute in accordance with IS 3400 (Part 5): 1986 or Static Dead Load Method as given in Annex C. The individual adhesion value for consolidation test shall not be less than 30 N (3.0 kgf) for each of the test pieces

NOTE — Manuel recording may also be done in absence of the machine with auto recording devicee.'

[Page 6, clause 4.8] — Substitute the following for the existing:

'4.8 Adhesion Test

From the upper foxing portion where it is adhered to the canvas cut a strip of 8.0 ± 0.5 mm width along with the length of the sole at the waist portion and of sufficient length to permit separation over a length of at least 75 mm. Carry out the test on two test pieces (one from each odd) at the rate of traverse of 100 ± 10 mm per minute in accordance with IS 3400 (Part 5):1986 or the Static Dead Load Method as given in Annex C.

The individual adhesion value noted/recorded shall not be less than 8 N (0.8 kgf) for each of the test pieces (see Note under 4.7).'

Amend No. 2 to IS 3736 : 1995

[Page 7, Annex B] — Insert the following new Annex C after Annex B and renumber Annex C as Annex D:

'ANNEX C
(Clauses 4.7 and 4.8)

C-1 STATIC DEAD LOAD METHOD

C-1.1 Apparatus

The apparatus required for the adhesion test by the static mass method consists of a supporting frame, testing clamps, mandrels, calibrated weights, and weight carriers. The supporting frame shall be of such design that clamps for strip specimens hang on it vertically and mandrels for rings specimens are supported on it horizontally. The frame shall have sufficient height to permit the weight carrier to be suspended from the test specimens by means of clamps and shall hang freely during the progress of the test, provision shall also be made to support the mandrels so that they revolve freely with minimum friction. Suitable apparatus is shown in Fig. 4.

C-1.2 Calibration of Apparatus

Calibrate the weights annually.

C-1.3 Cutting Tool

Maintain the cutting tool carefully so that the edge is sharp enough to avoid leaving ragged edges and pulling outside threads from the fabric.

C-2 PROCEDURE

C-2.1 Strip Test Piece (see Fig. 4)

Separate the parts of the strip to be tested by hand at one end of the strip specimen and at a sufficient distance to permit the jaws of the testing clamp to be attached. Suspend the strip on the spike of the vertical frame or board and attach the ply to be separated, to the grip. Attach the loaded scale pan to the grip through a light spring. The total mass of the grip, spring, loaded scale pan and attachments shall be taken as the applied load. Obtain either the load required to cause separation of 25 mm/min graphically by selecting various loads or for a known or specified load, determine the rate of separation. Repeat the procedure on the separate plies from the face ply to the centre ply. Test the second specimen commencing with the back ply and proceeding again to the centre ply.

Note — Precautions shall be taken during the test to prevent side threads from pulling out and interfering with the test result. Where this occurs excessively due to the threads not being parallel to the edge of the strip, the test pieces shall be discarded and a fresh one prepared.

Amend No. 2 to IS 3736 : 1995

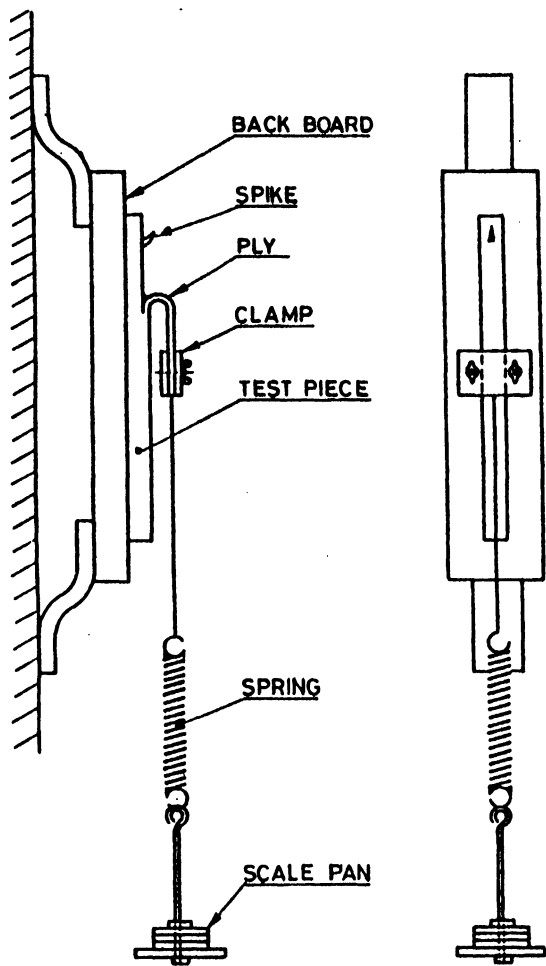


FIG. 4 APPARATUS FOR STATIC LOAD MEIHOD ON STRIP TEST PIECE

Amend No. 2 to IS 3736 : 1995

C-2.2 Expression of Results

Express the result as average force in kilo newtons per metre width required to cause a separation of the plies at 25 mm/min or obtain the rate of separation at a known or specified load.

C.3 REPORT

The report shall include the following:

- a) Adhesion value, that is median, range, statistical minimum, observed minimum, observed maximum;
- b) The type of specimen and thickness of specimen;
- c) All observations and recorded data on which the results are based;
- d) Date of manufacture or vulcanization of rubber; if known;
- e) Date of test;
- f) Statement of the method used (Dead load/ Static mass or dynamic on constant traverse); and
- g) Temperature of the test and its duration, and temperature and relative humidity of conditioning.'

(CHD 19)

Reprography Unit, BIS, New Delhi, India