

AMENDMENT NO. 1 DECEMBER 1976
TO
IS : 3523-1974 SPECIFICATION FOR METAL TRAVELLERS FOR
RING SPINNING FRAME
(Second Revision)

Alterations

(Page 1, clause 2.1) — Substitute the following for the existing clause:

‘2.1 Material — Suitable steel so as to obtain the hardness specified in 3.3.’

(Page 1, clause 3.1) — Substitute the following for the existing clause:

3.1 Weight — The weight of 1 000 travellers shall comply with the requirements of col 2 of Table 1 or as declared by the manufacturer. The number of travellers to be weighed shall be as follows:

<i>Conventional Number of Travellers</i>	<i>No. of Travellers to be Weighed</i>
1 to 30	10
1/0 to 30/0	100

(Page 1, clause 3.3) — Substitute the following for the existing clause:

‘3.3 Hardness — The travellers shall be hardened and tempered. Hardness of travellers when tested according to the method prescribed in IS : 1501 - 1968 ‘Method for Vickers hardness test for steel (first revision)’ under a load of 1, 2½ or 5 kg depending upon the size of travellers, shall be as under:

Heavier than Number 10	500 – 600 HV
Number 10 to Number 17/0	580 – 677 HV
Lighter than Number 17/0	580 – 701 HV

Note — The hardness of ring in conjunction with which the travellers are to be used should be within a range of 701 to 900 HV 30.’

(Page 1, clause 3.4, line 3) — Substitute ‘2.5 mm’ for ‘3 mm’.

(Pages 2 and 3, clauses 6.3 to 6.5) — Substitute the following for the existing clauses:

6.3 The number of travellers to be selected at random (see IS : 4905 - 1968 ‘Methods for random sampling’) for testing and the criteria for conformity for each of the characteristics shall be as follows:

<i>Characteristic</i>	<i>Number of Travellers to be Tested</i>	<i>Criteria for Conformity</i>
Workmanship and finish, and width of gap	See col 2 of Table 2	Non-conforming travellers not to exceed the corresponding acceptance number given in col 3 of Table 2
	See col 5 of Table 2	In case the number of non-conforming travellers is more than acceptance number but less than rejection number, draw second sample as under: Non-conforming travellers in both first and second samples not to exceed the corresponding acceptance number given in col 6 of Table 2
Hardness, shape and stretch test	See col 7 of Table 2	Each observed value shall satisfy the requirement
Weight	Two sets of specified number of travellers if the lot size is up to 10 000 and 5 sets of specified number if the lot size consists of more than 10 000 travellers.	Each observed value shall satisfy the requirement

TABLE 2 SAMPLE SIZE AND CRITERION FOR CONFORMITY

Lot Size	First Sample Size	(Clause 6.3) Acceptable Quality Level		Second Sample Size	Acceptance No.	Number of Travellers to be Tested for Hardness, Shape and Stretch Test
		Acceptance No.	Rejection No.			
(1)	(2)	(3)	(4)	(5)	(6)	(7)
Up to 3 000	20	1	4	20	4	5
3 001 to 10 000	32	2	5	32	6	8
10 001 to 35 000	50	3	7	50	8	13
35 001 and above	80	5	9	80	12	20

Addenda

(Page 1, clause 2.2.2) — Add the following new clause after 2.2.2:

‘ 2.3 Shape — Shape of traveller shall be checked on a profile projector and a variation up to ± 3 percent from manufacturer's standard drawing shall, however, be permissible.’

(Page 1, clause 3.4, line 3) — Add the following after ‘ 6 mm ’ :

(A typical stretch testing apparatus is illustrated in Fig. 2)

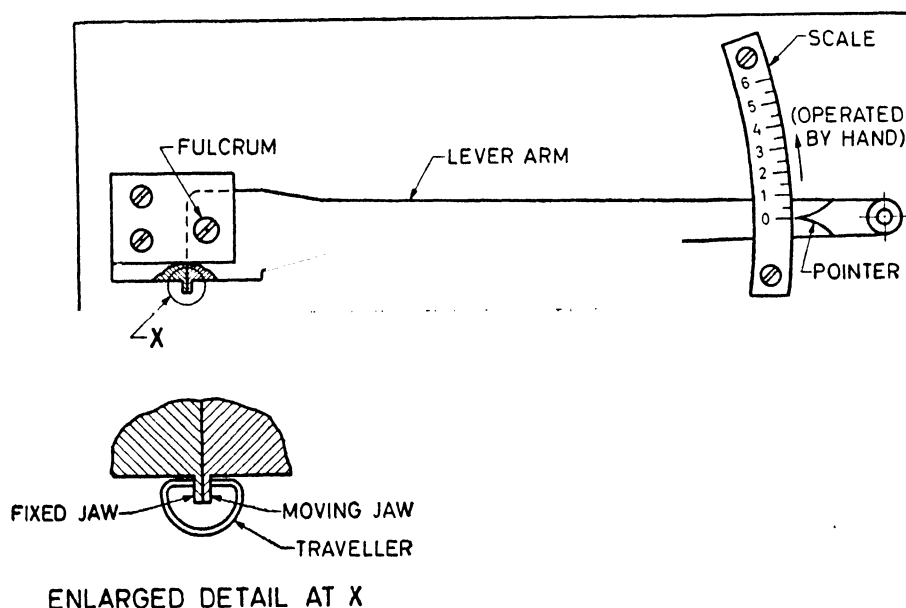


FIG. 2 A TYPICAL STRETCH TESTING APPARATUS FOR TRAVELLERS

(Page 3, Table 1) — Add the following Note after Note 1 and renumber the subsequent Notes accordingly:

‘ Note 2 — In case the weight of 1 000 travellers is different from those specified in col 2, the tolerance of ± 3 percent shall be applicable on the declared weight by the manufacturer.’