技术要求: Specifications:

1.天然胶,硬度:55±3 shore A,参照标准DBL 5558-45; Ⓒ
Nature rubber with 55±3 shore A,according to the spec.DBL 5558-45.

2.由索格菲完成粘接工序; The gluing is made by Sogefi.

3.粘接准备事项 Bush status before for gluing on stab bar:
3.1 内表面需保持清洁,索格菲粘接前无需处理措施
3.2 衬套出模后6个月可粘接;
3.3 采用脱模剂必须与索格菲粘接工艺兼容;
3.1 The internal surface of the bush must be clean and can receive the Sogefi glue without surface preparation.
3.2 The gluing operation can be made 6 months maximum after moulding.
3.3 The release agent used for bushes must be compatible with the Sogefi glue.

4.特殊特性参照标准 I-02-P-01-01:Special characteristics as I-02-P-01-01:
关键特性标识Critical:Ⓒ
重要特性标识Important:Ⓘ
橡胶尺寸公差参照 NF/T47-001 M3级执行; General tolerances on rubber M3 as norm NF/T47.001.


5.追溯性标识:字高2.5mm,字深0.2mm;
Traceability:characters height 2.5mm,characters deep 0.2mm.

6.刚度采用卡箍和夹具完成(见附表): Stiffness are checked with serial brackets and rigid blocks to meet the specification(see table).
6.1.z&x向静刚度:加载±1mm,速度:10mm/min,循环4次,计算±0.5mm时的刚度;
6.2.扭转刚度:加载±20°,速度:60°/min,循环4次,计算±5°时的刚度;
6.1.Radial static stiffness Kz&x:Load ±1mm for 4 cycles, speed:10mm/min, check at ±0.5mm.
6.2.Torsional stiffness Kty:Load ±20° for 4 cycles,speed:60°/min,check at ±5°.


7.索格菲试验项目(Sogefi test);
7.1 噪音实验:在80℃*4周和120℃*24h环境下对3根老化前后产品分别做噪音实验,测试角度:9.4°&±23.5°,5种温度(-30℃,-20℃,-10℃,0℃,+10℃,+20℃),5次循环,不可察觉的噪音为合格;
7.2 拔脱实验:80%的粘接效果为合格(新件);70%的粘接效果为合格(疲劳件);
7.3 环境试验:在110℃环境下,扭转9.4°,持续100小时,z&x向静刚度损失<10%,且粘接面积>70%为合格;
7.1 Noisy test:control before and after aging test on 3bars for 4 weeks at 80°c and 24h at 120°c,test angle(9.4°&±23.5°),5 temperatures(-30℃,-20℃,-10℃,0℃,+10℃,+20℃),evaluation on 5 cycles,not noticeable noise=OK;
7.2 Destructive tests:80% rubber adhesion for new bush; 70% rubber adhesion after fatigue;
7.3 Ambient test: Preload bars as 9.4° angle for 100h at 110℃,the test is ok if the stiffness loss in z&x < 10% between before and after and peeling ok > 70%.


8.◯为工序、出厂检验尺寸。
◯is marked for inspection dimensions.


标识内容:
零件号:19388-200
时间钟:24-25
材料标识:>NR+BR<
厂家代码:D200501
型腔号:01-32

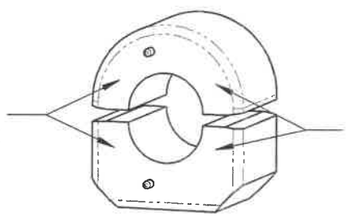


来历 From	客户版本号 Customer Version	变更标记 Marking	区域 Position	变更事项 Modification	中鼎版本号 ZD Version	日期 Date	责任人 Resp.
	19388-E			初始图纸Initial drawing	A	2025.07.04	马传德

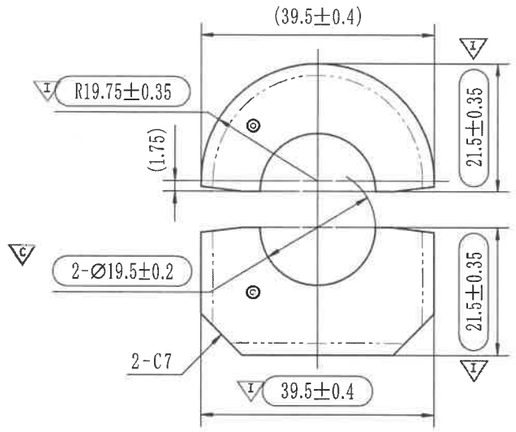

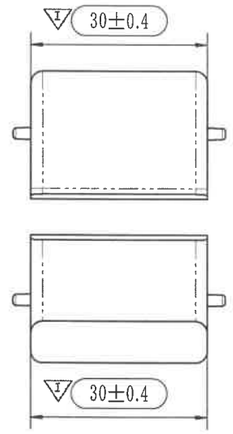

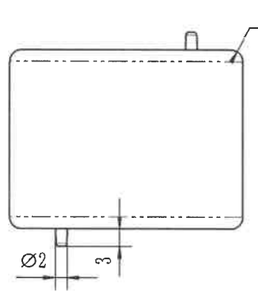

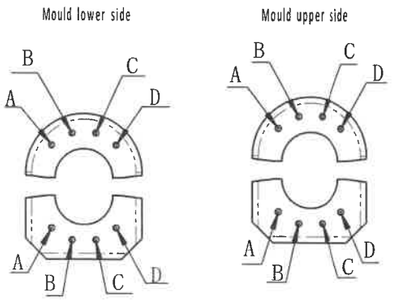

Upper bracket	19387			Stiffness requirement				
Lower bracket	19385							
Bar dia.	Bush dia	Identification	Colordot	Gauge	Ks-Z(N/mm)	Ks-X(N/mm)	Ks-Y(N/mm)	Ty(Nm/°)
Ø20.0	Ø19.5	A	White	Bracket	1500±15%	1250±15%	550±15%	2max
				Block (unbonded)				

NF/T 47-001 CLASS M3								
	≤6.3	≤10	≤16	≤25	≤40	≤63	≤100	≤160
F	±0.20	±0.20	±0.25	±0.35	±0.40	±0.50	±0.70	±0.80
C	±0.25	±0.35	±0.40	±0.50	±0.70	±0.80	±1.00	±1.30

投影法 Projection method	比例Scale	质量Weight(g)	材质Material	产品号ZD production code
第一画法First angle projection	1:1	38.3g	R6938-H55	C11423141-CPSJ

热处理·表面处理Heat Treatment·Surface Treatment

名称Part name: 后稳定杆衬套 (后稳定杆衬套)

批准 Approval	标准化 Standards	审批 Review	校对 Check	设计 Design	项目组 Team
				马传德 20250704	稳定杆系统 Stab Bar system

图号Drawing No: 19388-200 (JS873)

标记SIGN: S | 共 1 张 第 1 张 | 安徽中鼎密封件股份有限公司 | A3