



1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16
产品信息															
项目代码	支架零件号														
524B	19553-CN(Upper)														
	19554-CN(Lower)														

NO.	客户版本号 (CUSTOMER VERSION)	NO.	变更标记 (MARK CHANGE)	变更事项 (CHANGE CONTENT)	中鼎版本号 (ZD VERSION)	日期(DATE)	责任人 (RESPONSIBLE)
		1		Initial Release(同步开发初始版本)	A	2024.11.01	范康祺

技术要求:

Specifications:

- ▽1.天然胶NR,硬度: 60±3 shore A(后续会调整硬度以满足主要的径向刚度标准);
Nature rubber hardness : 60±3 shore A(To be adjusted to meet main Static Radial Rate),
- 2.所有的尺寸和特性由供应商设计以满足要求;
All dimensions and characteristics are designed by the supplier in order to meet the specifications.
- 3.粘接准备事项Bush status before for gluing on stab bar:
·出模后的清洗和激活工序来满足粘接;
·必须要在出模后4周内完成激活工序;
·激活4个月至出模6个月内需确保可粘接;
·脱模剂需满足激活并对索格菲粘接无影响;
· Operation of cleaning and activation after molding to guarantee the adhesion;
· Activation must be done within 4 weeks of molding;
· The gluing operation can be made 4 months maximum after activation and no more than 6 months after moulding;
· The un-mold agent used for bushes must be compatible with the activator and with no effect on the SOGEFI gluing;
- 4.粘接试验Bonding test: :
·骨架与橡胶粘接面积≥90%;
· The bonding area between insert and rubber is ≥90%;
- 5.特殊特性参照标准IGR-D-20/0:
Special characteristics as IGR-D-20/0:
关键特性标识Critical: ▽
重要特性标识Important: ▽
橡胶尺寸公差参照DIN ISO 3302-1 M3级执行;
General tolerances on rubber M3 as norm DIN ISO 3302-1.
- 6.刻字标识: 字高2.5mm, 字深0.2mm;
Traceability :characters height 2.5mm, characters deep 0.2mm.
标识内容: 中鼎徽,时间钟,厂家代码,材料标识,零件号,型腔号;
Logo: Country of production,Time of production,Manufacture code,Material,Part NO.,Cavity NO.
- 7.刚度实验分别采用刚性夹具和卡箍完成, 参照附表;
All measurement stiffness following the table are checked with rigid blocks and serial brackets.
- 8.通常飞边要求<0.5mm厚, <1mm长,
General Parting line max. 0.5mm thick and 1.0mm long permissible,
- 9.○为工序、出厂检验尺寸。
○ is marked for inspection dimensions.

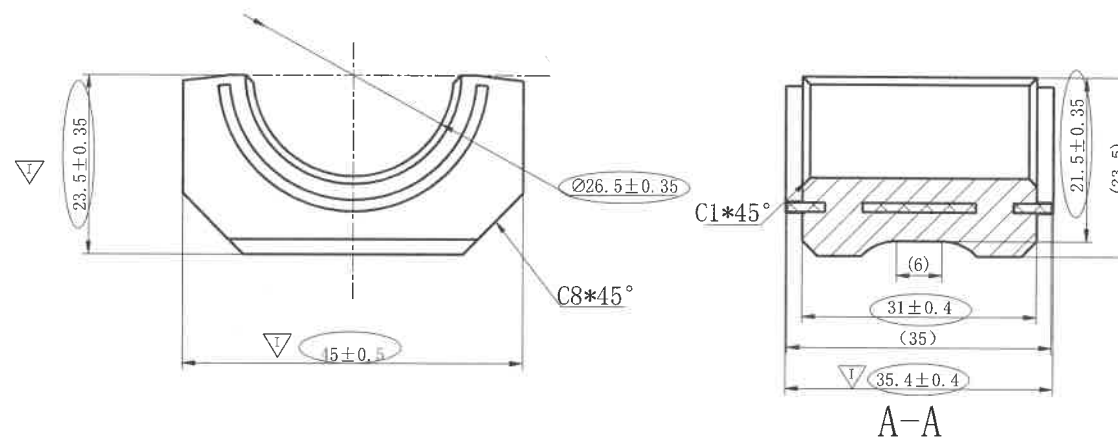

7.刚度实验Stiffness test				
No.	实验项目Test	试验方法Test procedure	检测器具Gauge	要求Request
1	Z向静刚度 Radial static stiffness	加载±5KN, 速度12mm/min, 循环4次, 计算±500N时的刚度Load ±5KN for 4 cycles,speed 12mm/min,check at±500N	Rigid block	/
2	Z向动刚度 Kdz-High	振幅±0.025mm频率10-600Hz,以10Hz为增量, Amplitude ±0.025mm,frequency:10-600Hz,By incremets 10Hz	Serial bracket	9500N/mm±15%
3	Z向动刚度 Kdz-Low	振幅±1mm, 频率0-50Hz,以5Hz为增量 Amplitude ±1mm,frequency:0-50Hz,By incremets 5Hz	Serial bracket	Result for reference
4	Y向静刚度Radial static stiffness	加载±500N, 速度12mm/min, 循环4次, 计算±500N时的刚度 Load ±500N for 4 cycles,speed 12mm/min,check at±500N	Rigid block	Result for reference
			Serial bracket	
5	X向静刚度Radial static stiffness	加载±5KN, 速度12mm/min, 循环4次, 计算±500N时的刚度Load ±5KN for 4 cycles,speed 12mm/min,check at±500N	Rigid block	Result for reference
			Serial bracket	
6	扭转刚度 Torsional stiffness	加载±25°, 速度100°/min, 循环4次, 计算±5°时的刚度 Load ±25° for 4 cycles,speed ±100°/min,check at ±5°	Rigid block	/
			Serial bracket	2 Max

DIN ISO 3302-1.CLASS M3									
	≤4	≤6.3	≤10	≤16	≤25	≤40	≤63	≤100	≤160
F	±0.25	±0.25	±0.30	±0.40	±0.50	±0.60	±0.80	±1.00	±1.30
C	±0.40	±0.40	±0.50	±0.60	±0.80	±1.00	±1.30	±1.60	±2.0

2	借用 Z6042541/01-01	Insert/骨架	1	DC01	15.5g	借用 C904881/01-01
1		Rubber/橡胶	1	NR(R7770-H60)	20.79g	
序号 (NO.)	图 号(PART NO.)	Composition/组成	Quantity/数量	Material/Size/材料	weight/重量	Note/备注
第一角画法(FIRST ANGLE PROJECTION) 		比例(SCALE) 1:1	质量(WEIGHT) 36.29g	材质(MATERIAL) 组件	产品号(PRODUCTION NO.) C114259-CPSJ	
热处理·表面处理(HEAT TREATMENT·SURFACE TREATMENT)				名称(NAME) 稳定杆衬套下衬套 (前稳定杆衬套)		
批 准 (APPROVAL)	标准化 (STD.)	审核 (AUDITOR)	校对 (CHECKER)	设计 (DESIGNER)	项目组 (PROJECT TEAM)	
李会			夏斌		范康祺	Stabilized bar system 稳定杆系统
图号(PART NO.)				Z6012542 (WYDL30)		
(SIGN) 标识	S	A	B	PAGES(共 1 张) OF(第 1 张)		安微中鼎密封件股份有限公司
						A3