
No.	客户版本号 (CUSTOMER VERSION)	No.	变更标记 (MARK CHANGE)	更改内容 (CHANGE CONTENT)	中鼎版本号 (ZD version)	日期 (DATE)	责任人 (RESPONSIBLE)
				Initial Release(初始版本)	A	20250120	马传德
SJ-254690			ⓐ/6	产品更新为下半个衬套，性能测试条件更新，更新产品名称，更新图号，增加刻字内容。	B	20250826	马传德

技术要求: Specifications:

1. 天然胶,硬度:60±5 shore A,参照标准RENAULT 30-00-118;
 Nature rubber with 60±5 shore A,according to the spec.RENAULT 30-00-118.
2. 由索格菲完成粘接工序; The gluing is made by Sogefi.
3. 粘接准备事项 Bush status before for gluing on stab bar:
 3.1 内表面需保持清洁,索格菲粘接前无需处理措施
 3.2 衬套出模后6个月可粘接;
 3.3 采用脱模剂必须与索格菲粘接工艺兼容;
 3.1 The internal surface of the bush must be clean and can receive the Sogefi glue without surface preparation.
 3.2 The gluing operation can be made 6 months maximum after moulding.
 3.3 The release agent used for bushes must be compatible with the Sogefi glue.
4. 特殊特性参照标准 I-02-P-01-01:Special characteristics as I-02-P-01-01:
 关键特性标识Critical:▽C
 重要特性标识Important:▽I
 橡胶尺寸公差参照 NF/T47-001 M3级执行; General tolerances on rubber M3 as norm NF/T47.001.
5. 追溯性标识:字高2.5mm,字深0.2mm;
 Traceability:characters height 2.5mm,characters deep 0.2mm.
6. 刚度采用卡箍和夹具完成（见附表）: Stiffness are checked with serial brackets and rigid blocks to meet the specification(see table).
7. 索格菲试验项目(Sogefi test);
 7.1 噪音实验:在80℃*4周和120℃*24h环境下对3根老化前后产品分别做噪音实验,测试角度:9.4° &18.8° ,5种温度(-30℃,-20℃,-10℃,0℃,+10℃,+20℃),5次循环,不可察觉的噪音为合格;
 7.2 拔脱实验:80%的粘接效果为合格(新件);70%的粘接效果为合格(疲劳件);
 7.3 环境试验:在110℃环境下,扭转9.4° ,持续100小时,z&x向静刚度损失＜10%,且粘接面积＞70%为合格;
 7.1 Noisy test:control before and after aging test on 3bars for 4 weeks at 80° c and 24h at 120° c,test angle(9.4° &18.8°),5 temperatures(-30℃,-20℃,-10℃,0℃,+10℃,+20℃),evaluation on 5 cycles,not noticeable noise=OK;
 7.2 Destructive tests:80% rubber adhesion for new bush; 70% rubber adhesion after fatigue;
 7.3 Ambient test: Preload bars as 9.4° angle for 100h at 110℃,the test is ok if the stiffness loss in z&x < 10% between before and after and peeling ok > 70%.
8. 为工序、出厂检验尺寸。
 is marked for inspection dimensions.

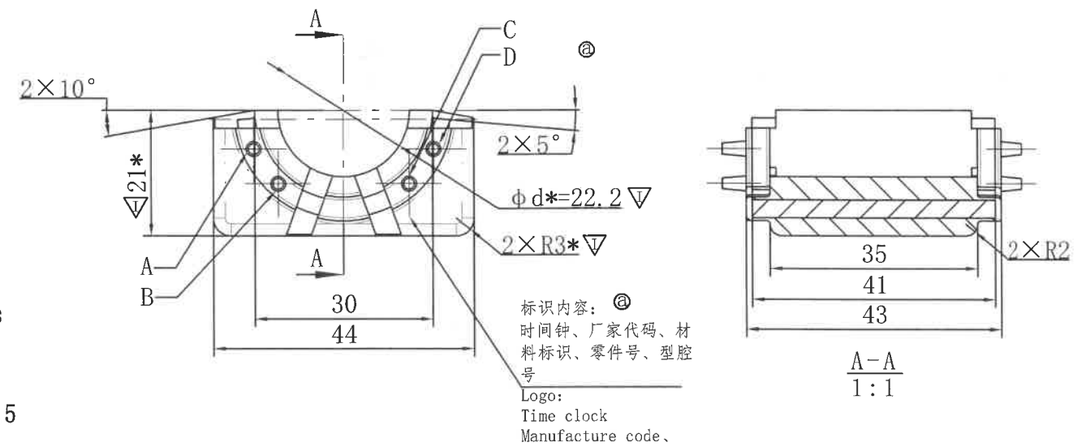

CHARACTERTISTICS TABLE					REQUEST	STATIC STIFFNESS ⓐ				DYNAMIC STIFFNESS
PART NUMBER	ARA REFERENCE	STAB BAR DIAMETER ∅D	INTERNAL BUSHING DIAMETER ∅d*	CODIFICATION	DIRECTION	▽RADIAL Z	▽TORSION Y	RADIAL X	AXIAL Y	RADIAL Z
					LOAD SPEED	10mm/min	60° /min	10mm/min	20mm/min	15 to 150Hz
					LOAD	±1mm	±16°	±1mm	±2mm	±0.01
					CHECK	±0.6mm	±9°	±0.6mm	±1.2mm	100Hz
		mm	mm		UNITS	N/mm	N.m/°	N/mm	N/mm	N/mm
TBD	18652-227	22.7	22.2	AB	ARA RIGID BLOCK	TBD	TBD	TBD	TBD	Kzdyn150/Kzstat<2
					SERIAL BRACKET	7000±15%	1.5±20%			
TBD	18652-235	23.5	23.0	AC	ARA RIGID BLOCK	TBD	TBD	TBD	TBD	Kzdyn150/Kzstat<2
					SERIAL BRACKET	7000±15%	1.5±20%			
TBD	18652-250	25.0	24.5	AD	ARA RIGID BLOCK	TBD	TBD	TBD	TBD	Kzdyn150/Kzstat<2
					SERIAL BRACKET	7000±15%	1.5±20%			

DIN ISO 3302-1 Class M3										
	≤4	≤6.3	≤10	≤16	≤25	≤40	≤63	≤100	≤160	>160
F	±0.25	±0.25	±0.30	±0.40	±0.50	±0.60	±0.80	±1.00	±1.30	±0.8%
C	±0.40	±0.40	±0.50	±0.60	±0.80	±1.00	±1.30	±1.60	±2.0	±1.3%

No.	PN/代号	Composition/组成	Quantity/数量	Material/材料	Note/备注
2	Z6012661/01-01 ⓐ	Plastic insert/塑料骨架	1	PA66+GF30	C114360/01-01
1		Rubber/橡胶		R5604-H60	

第一角画法 (FIRST ANGLE PROJECTION)	比例 (SCALE) 1:1	重量 (WEIGHT) TBDg	材料 (MATERIAL) NR+BR(R5604-H60)	产品号 (PRODUCT NO.) C114360-CPSJ
热处理·表面处理 (HEAT TREATMENT. SURFACE TREATMENT)			名称 (NAME) 前下稳定杆衬套 ⓐ (前稳定杆衬套)	

批准 (APPROVAL)	标准化 (STD.)	审核 (AUDITOR)	校对 (CHECKER)	设计 (DESIGNER)	项目组 PROJECT TEAM	图号 (PART NO.)
				马传德 2025.8.27	Stabilizer System 稳定杆系统	Z6012661 ⓐ (WYDL30)

SIGN(标记) S | PAGES(共 1 张) OF(第 1 张) | ZHONGDING SEALING PARTS CO.,LTD 中鼎密封件股份有限公司 | A3