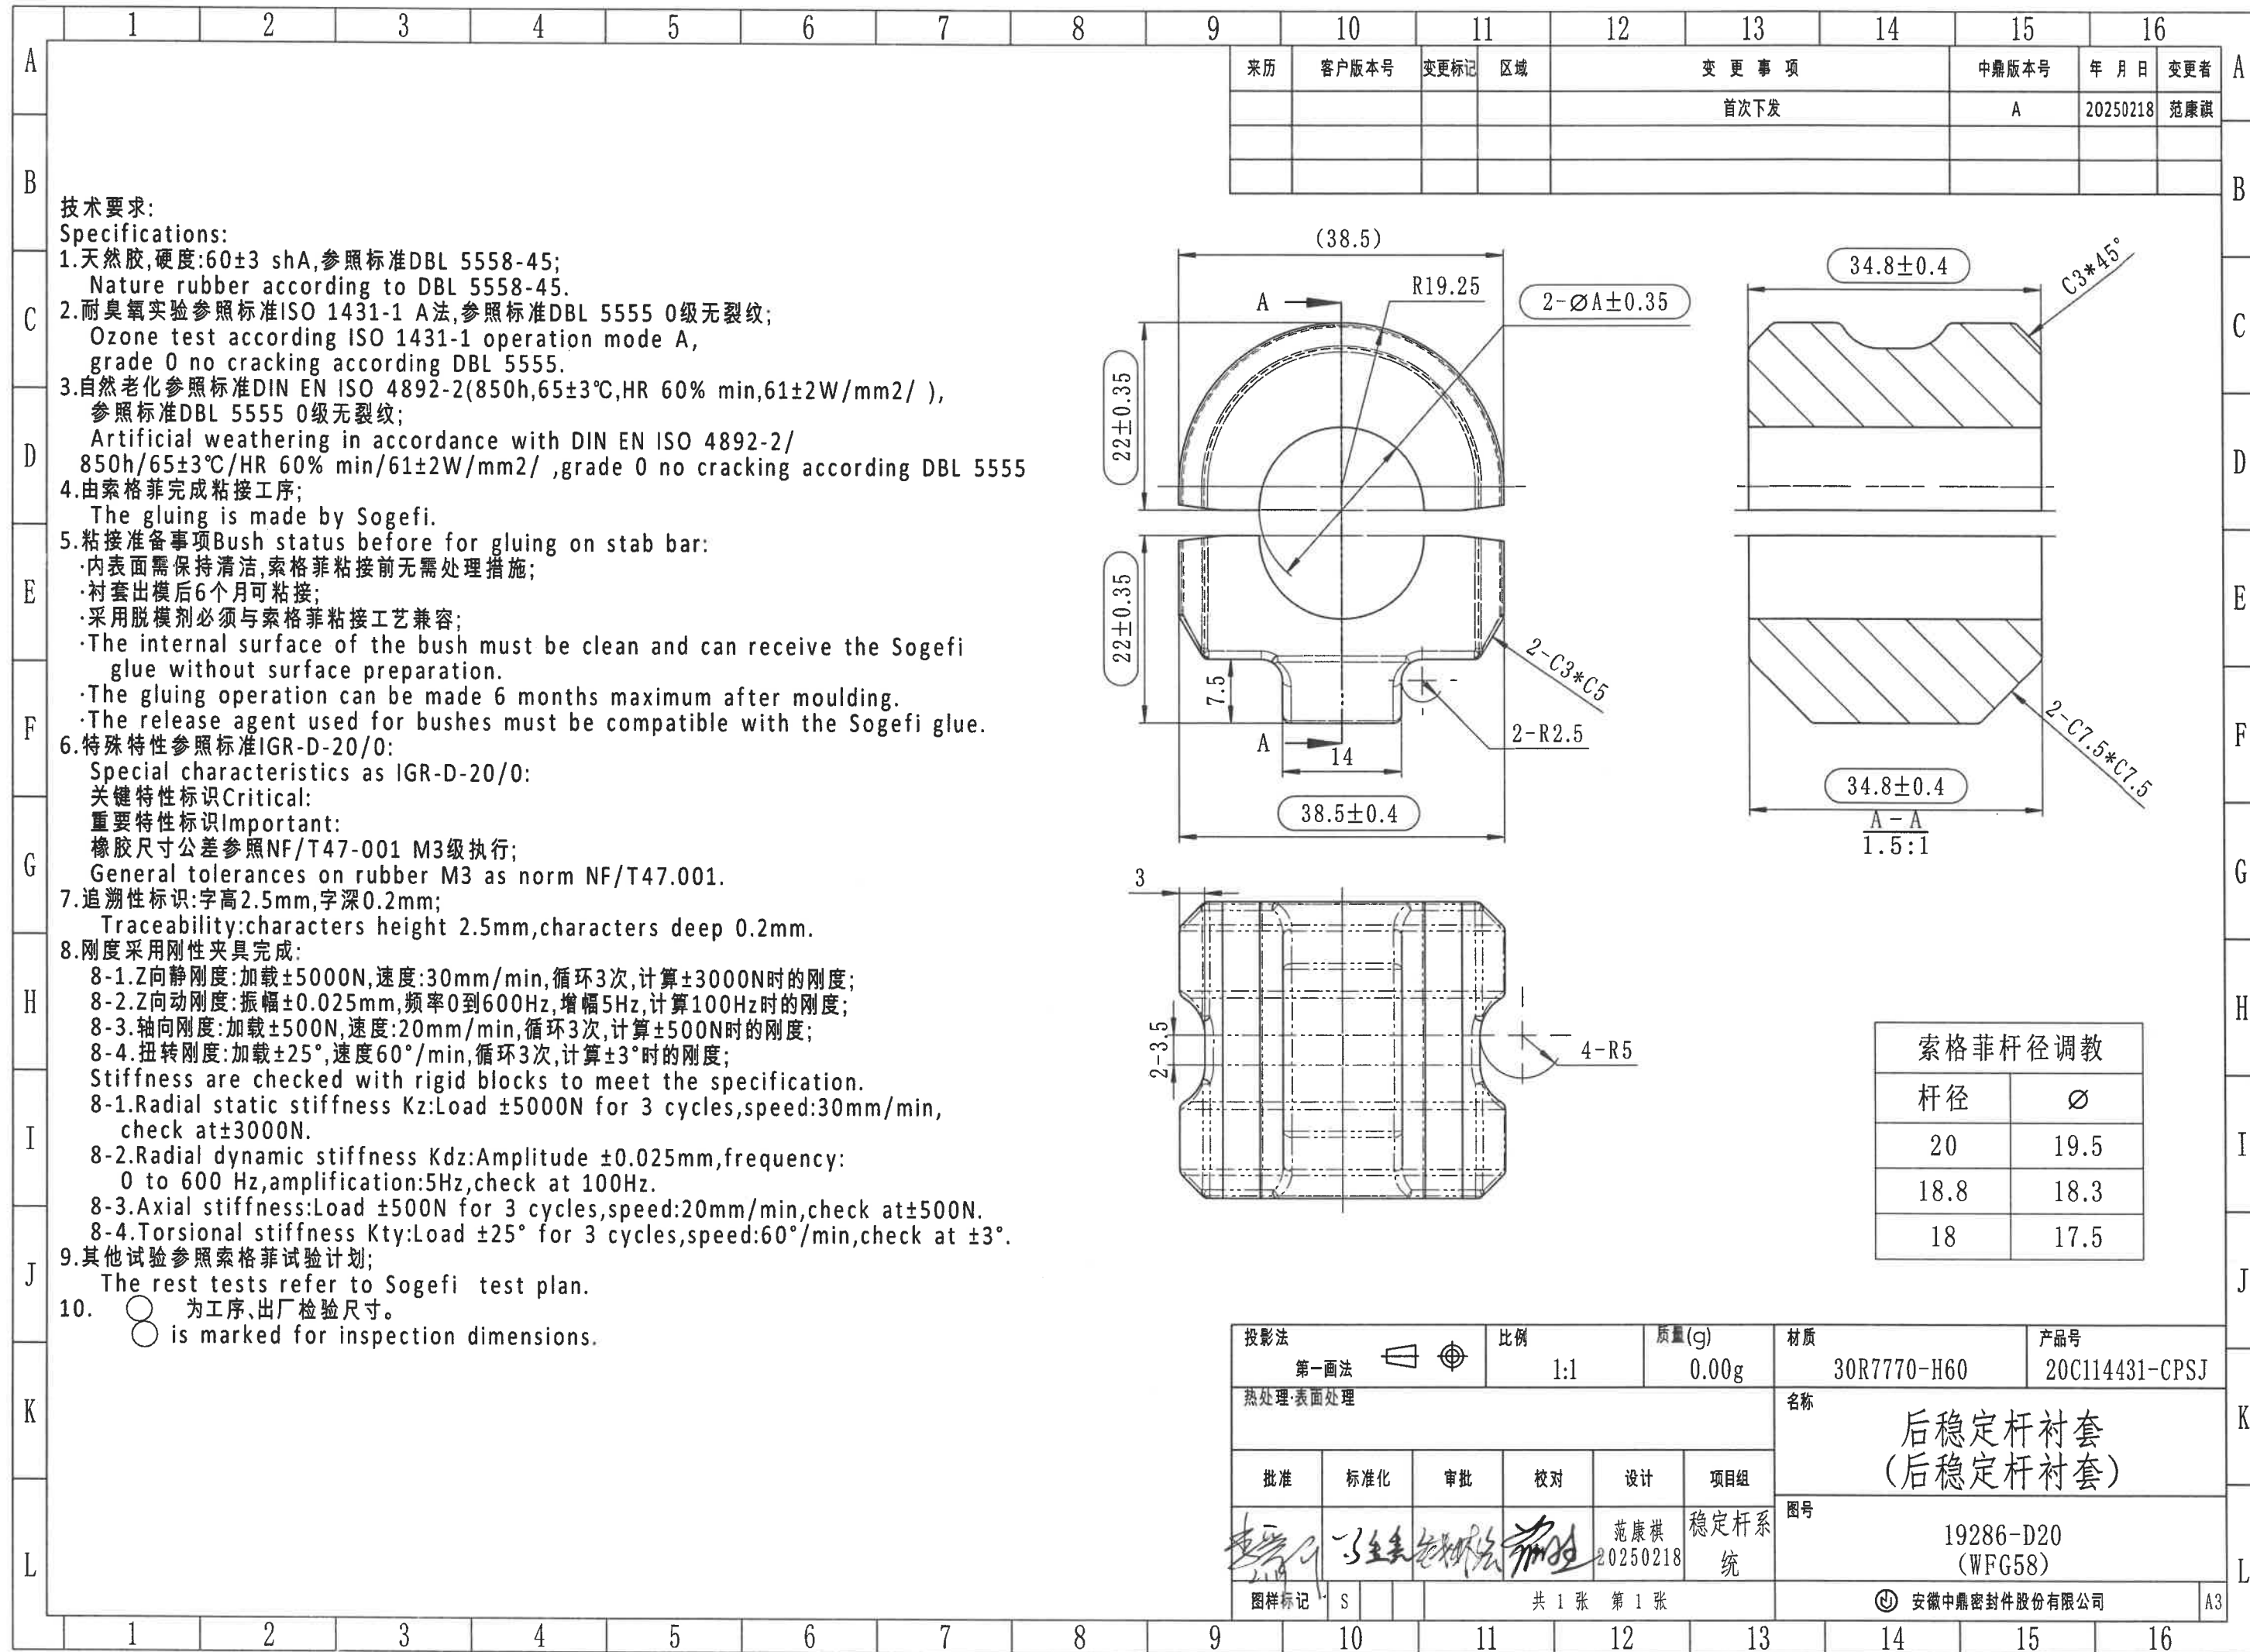






技术要求:

Specifications:

- 1.天然胶,硬度:60±3 shA,参照标准DBL 5558-45;
Nature rubber according to DBL 5558-45.
- 2.耐臭氧实验参照标准ISO 1431-1 A法,参照标准DBL 5555 0级无裂纹;
Ozone test according ISO 1431-1 operation mode A,
grade 0 no cracking according DBL 5555.
- 3.自然老化参照标准DIN EN ISO 4892-2(850h,65±3°C,HR 60% min,61±2W/mm2/),
参照标准DBL 5555 0级无裂纹;
Artificial weathering in accordance with DIN EN ISO 4892-2/
850h/65±3°C/HR 60% min/61±2W/mm2/ ,grade 0 no cracking according DBL 5555
- 4.由索格菲完成粘接工序;
The gluing is made by Sogefi.
- 5.粘接准备事项Bush status before for gluing on stab bar:
 - 内表面需保持清洁,索格菲粘接前无需处理措施;
 - 衬套出模后6个月可粘接;
 - 采用脱模剂必须与索格菲粘接工艺兼容;
 - The internal surface of the bush must be clean and can receive the Sogefi glue without surface preparation.
 - The gluing operation can be made 6 months maximum after moulding.
 - The release agent used for bushes must be compatible with the Sogefi glue.
- 6.特殊性参照标准IGR-D-20/0:
Special characteristics as IGR-D-20/0:
关键特性标识Critical:
重要特性标识Important:
橡胶尺寸公差参照NF/T47-001 M3级执行;
General tolerances on rubber M3 as norm NF/T47.001.
- 7.追溯性标识:字高2.5mm,字深0.2mm;
Traceability:characters height 2.5mm,characters deep 0.2mm.
- 8.刚度采用刚性夹具完成:
 - 8-1.Z向静刚度:加载±5000N,速度:30mm/min,循环3次,计算±3000N时的刚度;
 - 8-2.Z向动刚度:振幅±0.025mm,频率0到600Hz,增幅5Hz,计算100Hz时的刚度;
 - 8-3.轴向刚度:加载±500N,速度:20mm/min,循环3次,计算±500N时的刚度;
 - 8-4.扭转刚度:加载±25°,速度60°/min,循环3次,计算±3°时的刚度;
 - Stiffness are checked with rigid blocks to meet the specification.
 - 8-1.Radial static stiffness Kz:Load ±5000N for 3 cycles,speed:30mm/min,
check at±3000N.
 - 8-2.Radial dynamic stiffness Kdz:Amplitude ±0.025mm,frequency:
0 to 600 Hz,amplification:5Hz,check at 100Hz.
 - 8-3.Axial stiffness:Load ±500N for 3 cycles,speed:20mm/min,check at±500N.
 - 8-4.Torsional stiffness Kty:Load ±25° for 3 cycles,speed:60°/min,check at ±3°.
- 9.其他试验参照索格菲试验计划;
The rest tests refer to Sogefi test plan.
10. 为工序、出厂检验尺寸。
is marked for inspection dimensions.

索格菲杆径调教	
杆径	Ø
20	19.5
18.8	18.3
18	17.5

投影法 第一画法				比例 1:1	质量(g) 0.00g	材质 30R7770-H60	产品号 20C114431-CPSJ
热处理·表面处理						名称 后稳定杆衬套 (后稳定杆衬套)	
批准	标准化	审批	校对	设计	项目组		
				范康祺 20250218	稳定杆系 统	图号 19286-D20 (WFG58)	
图样标记		S	共 1 张 第 1 张				