来历	客户版本号	变更标记	区域	变 更 事 项	中鼎版本号	年 月 日	变更者
				初始图纸	A	20250512	马传德

技术要求:
Specification:
1.天然胶,硬度:60±4 shore A,参照标准RENAULT 30-00-118 --C § ANNEXE A.6.1;
Nature rubber with 60±4 shore A,according to the spec.
RENAULT 30-00-118 --C § ANNEXE A.6.1.
2.由索格菲完成粘接工序; The gluing is made by Sogefi.
3.衬套尺寸Bush sizes:所有尺寸和特性由供应商设计以满足要求:All the size with *are defined by provider respect the specifications.
4.粘接准备事项 Bush status before for gluing on stab bar:
4.1 衬套内表面需保持清洁并进行活化,索格菲粘接前无需额外的表面处理;
4.2 衬套出模后6个月可粘接;
4.3 采用脱模剂必须与索格菲粘接工艺兼容;
4.1 The internal surface of the bush must be clean and chemically activated,and can receive the Sogefi glue without additional surface preparation.
4.2 The gluing operation can be made 6 months maximum after moulding.
4.3 The release agent used for bushes must be compatible with the Sogefi glue.
5.特殊特性参照标准IGR-D-20/0:
Special characteristics as IGR-D-20/0:
关键特性标识Critical: C
重要特性标识Important: I
橡胶尺寸公差参照NF/T47-001 M3级执行;
General tolerances on rubber M3 as norm NF/T47.001.
6.追溯性标识:字高2.5mm,字深0.2mm;
Traceability:characters height 2.5mm,characters deep 0.2mm.
7.刚度实验分别采用刚性夹具和卡箍完成,参照附表;
All measurement stiffness following the table are checked with rigid blocks and serial brackets.
8.其他试验参照索格菲试验计划;
The rest tests refer to Sogefi test plan.
9. ◯ 为工序、出厂检验尺寸。
◯ is marked for inspection dimensions.

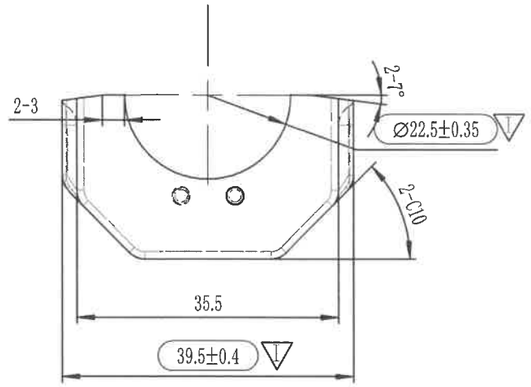

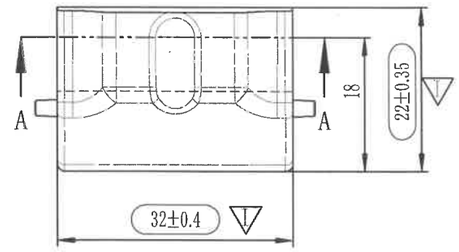



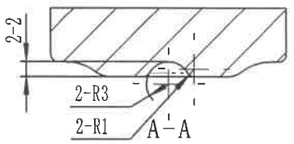

杆径 Bar	试验项目 ITEM	试验方法Test procedure	检测器具 Gauge	要求 © Request
Ø23	Z向静刚度 Kz	加载±5000N,速度30mm/min,循环3次,计算±3000N时的刚度Load ±5000N for 3 cycles,speed 30mm/min,check at±3000N	Serial bracket	2500±20%N/mm
			Rigid block	2650±20%N/mm
	X向静刚度 Kx	加载±5000N,速度30mm/min,循环3次,计算±300N时的刚度Load ±5000N for 3 cycles,speed 30mm/min,check at±300N	Serial bracket	1850±20%N/mm
			Rigid block	2500±20%N/mm
	Y向静刚度 Ky	加载±500N,速度20mm/min,循环3次,计算±500N时的刚度Load ±500N for 3 cycles,speed 20mm/min,check at±300N	Serial bracket	520±20%N/mm
			Rigid block	530±20%N/mm
	扭转刚度 Kty	加载±25°,速度120°/min,循环3次,计算第三次速度60°/min,取值范围±3° Load ±25° for 3 cycles,speed 120°/min for the first two cycles and 60°/min for the 3rd cycle ,check at ±3°	Serial bracket	≤2Nm/°
			Rigid block	≤2Nm/°
	Z向动刚度 Kdyn100	振幅±0.025mm,频率0-600HZ,以5HZ为增幅,计算范围±100HZ Amplitude ±0.025mm,frequency:0-600Hz,check speed by 5Hz,check at 100Hz	Serial bracket	Kzdyn100/Kzstat<2.5
			Rigid block	

NF/T 47001 CLASS M3								
	≤6.3	≤10	≤16	≤25	≤40	≤63	≤100	≤160
F	±0.20	±0.20	±0.20	±0.35	±0.40	±0.50	±0.70	±0.80
C	±0.25	±0.35	±0.40	±0.50	±0.70	±0.80	±1.00	±1.30

投影法	比例	质量(g)	材质	产品号
第一画法	1:1	20.8g	R5604-H60	C114578-CPSJ

热处理·表面处理

名称: 后稳定杆衬套下衬套 (后稳定杆衬套)

批准	标准化	审批	校对	设计	项目组
				马传德 20250512	稳定杆系统

图号: Z6012652 (WYDL30)

图样标记	S	A	B	共1张 第1张

安徽中鼎密封件股份有限公司 A3