

Manuscript Details

Manuscript number	SUBMIT2IJMS_2019_4099_R1
Title	Mechanical Behavior of Steel and Aluminum Foams at Elevated Temperatures. Local buckling based approach toward understanding of the material system behavior
Article type	Research Paper

Abstract

The objective of this study is to understand and quantify the thermo-mechanical behavior of hollow sphere (HS) steel and powder metallurgy (PM) aluminum foams over a broad range of elevated temperatures. The behavior of both the HS steel and PM aluminum foam is tested under compressive loading at ambient temperature (24C) and elevated temperatures of 100C, 150C, 200C, 300C, 400C, 550C and 700C, and results for the two foams are compared by their rates of degradation in mechanical properties. To link the cell geometry and base metal properties with the global mechanical performance, the experimental work is underpinned by a computational micro-model, consisting of an assembly of hollow spheres. The computational model shows that plastic buckling of cells with progressive plasticity of the contact area is the key local failure mechanism. As expected, due to the plastic buckling of the unit cells, thermal degradations of the tested metallic foams follow similar trends as does the yield stress of their bulk metals. The HS steel foam exhibits only minor elevated-temperature-induced degradation in stiffness and strength at or below 400C, while still maintaining 69% of its compressive strength at 550C. Comparatively, the PM aluminum foam begins degrading at an elevated temperature of only 150C. Interestingly, the HS steel foam oxidized between 300C and 400C, resulting in corresponding increases in the quasi-elastic modulus of elasticity. Future work might explore how to take advantage of oxidation reactions at the surfaces of the cells in the design of components using HS steel foams. Our computational study also revealed a possible new regime of cellular structures made up of ultra-thin-walled spherical cells that are predicted to fall within the elastic buckling regime at the local level. Thus, their deformations would be reversible even under high strains and their thermal behavior would be only controlled by thermal deterioration in the elastic constants, rather than plasticity parameters such as the yield stress.

Keywords	Metallic foam, Plastic buckling, Thermal analysis, Hollow-sphere steel foam, Thermo-mechanical analysis, Fire.
Manuscript category	SOLID MECHANICS
Corresponding Author	Stefan Szyniszewski
Order of Authors	Miguel Tavares, Jonathan Weigand, Luiz Vieira, Saulo Almeida, Stefan Szyniszewski

Submission Files Included in this PDF

File Name [File Type]
coverLetter.pdf [Cover Letter]
RESPONSES TO REVIEWERS.pdf [Response to Reviewers]
Highlights.docx [Highlights]
Graphical abstract.pdf [Graphical Abstract]
FirePaperRevised.pdf [Manuscript File]

Submission Files Not Included in this PDF

File Name [File Type]
CompetingInterests.txt [Conflict of Interest]
AuthorStatement.txt [Author Statement]
DataTables.xlsx [Supplementary Material]

To view all the submission files, including those not included in the PDF, click on the manuscript title on your EVISE Homepage, then click 'Download zip file'.



Durham University

Department of Engineering

<https://www.dur.ac.uk/engineering/>

May 1, 2020

Editorial Team
International Journal of Mechanical Sciences

Dear Editorial Team

Attached is a revised submission the article titled “Mechanical Behavior of Steel and Aluminum Foams at High Temperatures” co-authored with graduate student Miguel Tavares, Dr Jonathan Weigand, Prof. Luiz Vieira Jr, and Prof. Saulo Almeida.

We are grateful for helpful comments to the three reviewers. We have taken the feedback into account and improved figures and clarity of the article. The abstract and conclusions were shortened and the quality of the figures as well as depth and breadth of the citations expanded.

Generally speaking, our submission links the micro-mechanics of hollow sphere and powder metallurgy foams with their performance at elevated temperatures, for steel foams up to 700 C and for aluminum foams reaching 500 C. Our study combines micro-scale simulations and analytical study of unit cell buckling with experimental testing and validation. Our computational study revealed a possibility for a new range of ultra-thin-walled cellular structures, which are predicted to fall within the elastic buckling regime at the local level. Thus, their deformations will be reversible even under high strains and their thermal behavior controlled by the thermal deterioration of elastic constants, and not plasticity parameters such as yield stress.

Majority of currently produced cellular metals have relatively thick cell walls and consequently fail locally by plastic buckling. Thus, their thermo-mechanical behavior is controlled by the yield stress of the base metal as demonstrated computationally and experientially in the attached article. Our mechanistic insights are accompanied by an analytical formula producing stress-strain curves of steel and aluminum foams at elevated temperatures. Temperature dependent parameters for the tested steel and aluminum foams are tabulated in the appendix.

I appreciate your time in conducting a review of the revised paper and the opportunity to publish in the journal.

Sincerely,

Stefan Szyniszewski

Stefan Szyniszewski

Assistant Professor of Material and
Structures

Responses to reviewers:

-Reviewer 1

Summary: *The paper presents the thermo-mechanical behavior of a hollow sphere (HS) steel and powder metallurgy (PM) aluminum foams over a broad range of elevated temperatures. The experiment and simulation results show that ultra-thin walled presented reversible elastic buckling and large deformation capability. Moreover, oxidation reactions at the surfaces of the cells enhance their mechanical properties at High Temperatures. The paper has a clear goal, and the simulations, experiments and subsequent analysis support the final conclusions of the paper. I recommend this manuscript for publication after minor revision.*

Reviewer 1 recommendation: **Minor revision.**

Here are some specific comments that the authors should address:

Q1: *Page 12, Line 209, Page 19, Line 288 et al. Figure ??a and Figure ??b were presented in the manuscript. Please correct the format error and check the whole paper.*

Action: We have corrected all formatting errors and checked each figures and citation for accuracy.

Q2: *Page 9, Section Mechanical testing. Steel foam specimens were tested at 24 C (ambient temperature), 150 C, 200C, 300 C, 400 °C, 550 °C, and 700 °C, but aluminum foam specimens were tested at 24 °C, 150 °C, 200 °C, 300 °C, and 500 °C. Why not choose the same testing conditions for two metal foams.*

Response: Steel and aluminum have different melting points, and their mechanical properties degrade rapidly at different rates relative to increasing temperature. The mechanical properties of aluminum begin degrading at 100 °C, while those of steel don't appreciably degrade until 400 °C. For both metals, at least five test temperatures were chosen to span the most relevant temperature range (from 0 % to about 50 % of the melting point, where the most rapid degradation occurs). Table 1 lists the test temperatures, along with their corresponding percentages relative to the melting point temperatures of the aluminum and steel.

Table 1: Temperature and exposure time during compressive experiments

Temperature (°C)	Steel Foam		Aluminum Foam	
	Melting point (%)	Duration (min)	Melting point (%)	Duration (min)
24	2	∞	4	∞
150	10	15 & 30	23	15 & 30
200	13	15 & 30	30	15 & 30
300	20	15 & 30	45	15 & 30
400	27	15 & 30	-	-
500	-	-	76	15
550	37	15	-	-
700	47	15	-	-

Q3: Please added the nomenclature list of vocabulary of terms in the end of manuscript.
For instance, σ , σ_y , E_p , ϵ , wapex etc.

Action: A list of acronyms and a list of nomenclature has been added to the end of the article.

-Reviewer 2

Manuscript Number: SUBMIT2IJMS_2019_4099_Original_V1

Title: Mechanical Behavior of Steel and Aluminum Foams at High Temperatures

International Journal of Mechanical Sciences

The authors investigated the thermo-mechanical behavior of hollow sphere (HS) steel and powder metallurgy (PM) aluminum foams at high temperatures. The samples were subjected to the compressive loading at different temperatures and their mechanical properties were measured. Also, the achieved experimental results were compared with those given by a computational micro-model. Standard metrics for characterizing the temperature-dependent performance of the metallic foams were calculated based on ISO Standard 13314:2011, and the behavior was further parametrized by fitting a piecewise nine-parameter\Richard Equation" to the experimental stress-strain data of each specimen. The experimental results showed that the HS steel foam retained more than 89 % of its compressive strength, when measured by the plateau stress, up to 400 °C.

The manuscript is generally well written and organized. Also, the topic matches well with the major scope of International Journal of Mechanical Sciences. Nevertheless, before recommending for publication, the following revisions need to address carefully:

Q1: *The authors should clearly state in the introduction the novelty in this paper. What is new in this paper that has not been published before in the literature? Experimental tests and computational micro-model have been used already in the literature, so what is the exact contribution of this work?*

Response: This manuscript links the micro-mechanics of hollow steel spheres with the homogenized, global behavior of metal foams. This manuscript also examines the influence of elevated temperatures on the mechanical properties of metal foams. The simulations, corroborated with the experiments, allowed for the analytical synthesis based on the unit cell buckling stability, in the context of varying temperature.

The key novelty of this article is its use of micro-simulator, which uses random *packing* of the spheres, and was able to compute large scale deformations of the micro-model successfully. Results from the micro-simulator were in agreement with macroscopic test results, and also with previously published CT-scan based articles on the internal, local deformation mechanisms.

Equipped with validated, high-resolution results, we observed that local buckling stability controlled the global deformations of the cellular foams. This manuscript synthesized these findings using analytical, closed-form equations for the elasto-plastic stability of a spherical shell. The analysis revealed that the current manufacturing methods produce thick spheres, which are controlled by plastic buckling. However, if ultra-thin spheres were achievable, elastic buckling could produce globally elastic materials with highly-reversible, compressive behavior, akin to natural sponges.

We also used Richard's equation, fitted to the experimental data, to characterize systematic trends in the degradation of the foams' material properties at elevated temperatures, because characterization by the Richard equation provides a consistent basis for comparison of the results between temperatures. The experiments also revealed the formation of a blue-oxide film on steel foam cells, which increased its stiffness and strength in the temperature range from 200 °C to 400 °C. These findings underpin the assertion that analytical and computational work always needs to be

supported with macroscopic experiments due to the potential for surface changes/oxidations, which might noticeably influence the homogenized, global behavior.

Action: The introduction has been expanded to clearly state the points above.

Q2: What are the advantages of the experimental approach and computational micro-model used in this study? The authors should justify these issues. A comparison between the different experimental approaches to demonstrate their advantages and disadvantages is recommended.

Response: The Micro-model, validated against macroscopic experiments, yielded important insights into the internal mechanics of the metal foams, which could not have been easily measured, especially at elevated temperatures. The model also permitted investigation of local buckling behavior at the cell-level. The supplemental analytical buckling derivations re-confirmed the key findings and trends, and also revealed the potential benefits of ultra-thin-walled cellular metals, which might exhibit hyper-elastic properties. This manuscript's combination of the macroscopic experimental results and validated micro-model simulations yielded experimentally-validated, high-resolution information, including the locations of induced plastic strains and stresses, which allowed analytical conclusions and insights into the material behavior to be drawn.

Q3: Some advanced concepts should be referred to the adequate references leading the less experienced readers.

Action: The following references on cellular metals were added to the manuscript:

- Ashby, M., 2000. Metal foams : a design guide. Butterworth-Heinemann, Boston
- Gibson, L.J., Ashby, M.F., Ashby, M., 1999. Cellular Solids: Structure and Properties, 2nd ed. Cambridge University Press.

The following references with background information about the micro-simulator were also added to the manuscript:

- Smith, B.H., Szyniszewski, S., Hajjar, J.F., Schafer, B.W., Arwade, S.R., 2012. Characterization of Steel Foams for Structural Components. Metals 2, 399–410.

Q4: Some new physical insights should be added to the revised manuscript.

Response: Several key physical insights were derived from the simulations, analytical, consideration of elasto-plastic stability (of a spherical shell), and experimental results. Firstly, we showed that the macroscopic mechanical properties of the hollow sphere foam were linked with the buckling capacity of spherical shells, which can be identified within each hollow sphere. Thus, wall thickness-to-sphere radius ratio and base material properties are key parameters influencing the global response. We also showed that the load paths followed random trajectories, sensitively depending on the contact points and packing of the spheres. Finally, the stability analysis revealed the potential for achieving elastic buckling of the spheres through use of ultra-thin walls. Such a cellular structure would exhibit reversible, highly compressible behavior.

Our observations also revealed chemical oxidation of the steel foams, which manifested by forming a blue film layer on the surfaces of the cells. This stiffer blue oxide layer increased the macroscopic stiffness of the materials, due to large surface area of the hollow sphere steel foam.

Q5: Conclusion section should be shorten. The main new findings must be given in Conclusion.

Action: The conclusions section has been shortened.

Q6: For a special case, the obtained results need to check with those in open literature.

Response: The original submission compared our experimental data with previously published results for thermal degradation found in the literature below:

- European Committee for Standardization. Eurocode 3: Design of Steel Structures, Part 1-2: General Rules - Structural Fire Design – EN 1993-1-2:2005
- European Committee for Standardization. Eurocode 9: Design of Aluminum Structures, Part 1-2: Structural Fire Design – EN 1999-1-2:2007.
- M. Aly, Behavior of closed cell aluminium foams upon compressive testing at elevated temperatures: Experimental results, Materials Letters 61 (2007) 3138–3141.
- J. Kováčik, L. Orovčík, J. Jerz, High-temperature compression of closed cell aluminium foams, Kovové Materiály 54 (2016) 429–440.

- J. Liu, Q. Qu, Y. Liu, R. Li, B. Liu, Compressive properties of al-si-sic composite foams at elevated temperatures, *Journal of Alloys and Compounds* 676 (2016) 239–244.
- M. Taherishargh, E. Linul, S. Broxtermann, T. Fiedler, The mechanical properties of expanded perlite-aluminium syntactic foam at elevated temperatures, *Journal of Alloys and Compounds* 737 (2018) 590–596.

The comparison can be found in the Discussion, Section 6.

Q7: *In addition to those given in Fig. 10, is it possible to compare the parameters such as the primary resolved shear strain and fatigue life with those given in recently-published works?*

Response: The experimental setup, which used a Universal Testing Machine to apply the compressive loading, did not have the means to apply tension or cyclic loading inside the furnace to compute the fatigue life of the foams. Examining the resolved shear strains of metal foams would be an excellent subject for a future study.

Q8: *Figures should be modified. No data can be extracted from some figures. For example, see Figures 15 and 16.*

Action: The figures were modified so that the data can be extracted. An Excel spreadsheet with all of the measured data was also added as a supplement to the manuscript (in a Supplementary Information section). The parameters of the fitted Richard equation curves are also given in the Supplementary Information.

Q9: *References are old. Some new related works need to add the revised manuscript.*

Action: The introduction has been revised and expanded to include additional recent references across a variety of materials journals. In addition to the citations included in that section in the previous revision, citations to the following papers were added:

- D.P. Mondal, N. Jha, A. Badkul, S. Das, R. Khedle. “High temperature compressive deformation behaviour of aluminum syntactic foam.” *Materials Science and Engineering A*, 534 (2012), 521–529. doi:10.1016/j.msea.2011.16512.002.
- N. Bekoz, E. Oktay. “High temperature mechanical properties of low alloy steel foams produced by powder metallurgy.” *Materials and Design*, 53 (2014), 482–489. doi:10.1016/j.matdes.2013.07.050.
- N. Movahedi and E. Linul. “Quasi-static compressive behavior of the ex-situ aluminum-alloy foam-filled tubes under elevated temperatures.” *Materials Letters*, 206 (2017), 182–184. doi:10.1016/j.matlet.2017.07.018.

- E. Linul, N. Movahedi, L. Marsavina. “The temperature effect on the axial quasi-static compressive behavior of ex-situ aluminum foam-filled tubes.” *Composite Structures*, 180 (2017), 709–722. doi:10.1016/j.compstruct.2017.08.034.
- E. Linul, D. Lell, N. Movahedi, C. Codrean, T. Fiedler. “Compressive properties of zinc syntactic foams at elevated temperatures.” *Composites Part B*, 167 (2019) 122–134. doi:10.1016/j.compositesb.2018.12.019.

-Reviewer 3

This paper investigates the thermo-mechanical behavior of a hollow sphere steel and powder metallurgy aluminum foams over a broad range of elevated temperatures. The paper is well written; however, before publication, the following improvements are recommended:

Q1: *The “Abstract” and “Summary and Conclusions” sections must be written more concisely.*

Action: The Abstract and Summary and Conclusions sections have been revised to be more concise.

Q2: *Grammatical writing must be unified, whether the UK or the USA English must be used and not both.*

Action: The language and grammar have been unified to American English.

Q3. *Scale bars must be added to Figure 2.*

Action: Scale bars were added to Figure 2.

Q4: *Why only two specimens were tested under each temperature condition. According to the standard, at least 3 specimens should be used.*

Response: Our number of specimens was restricted by the limited volume of steel and aluminum foam we had available for testing (we sourced one block of each metal foam from Fraunhofer Institutes in Dresden and Chemnitz). The decision was made to have a higher number of points across the temperature range to better capture the material

degradation because the decreases in the strength and stiffness of steel and aluminum occur quite abruptly after exceeding their respective transition temperature. We acknowledge the trade-off between temperature-resolution and statistical rigor.

Generally speaking, the manuscript was equally focused on the simulations and analytical derivations as it was on the experiments. The experiments were primarily used to validate and confirm the insights gleaned from the computational simulations and analytical derivations. From this perspective, the tests can be viewed as blind tests or validation cases.

Q5: “Figure ??” must be named (see end of Section 3.2)

Action: The reference to the figure was corrected.

Q6: *The curves in Figure 8 must be plotted with lines not geometrical shapes (square, circles, etc.). These shapes being at a significant distance from each other fail to correctly reproduce the compression behavior.*

Action: Lines have been included in the plots, in addition to the geometrical shapes.

Q7. *Why are properties at 300C higher than RT or 100C, Figure 8b? In addition, those from 400C are higher than those from 200C. Why? Normally I should be like that.*


Response: A thin, blue oxide film coating was observed on all cells of the steel foam at temperatures exceeding 250 °C. This phenomenon is known as blue brittleness. The blue oxide layer is stiffer and stronger, but more brittle than the base steel alloy. Due to the large surface area of the hollow sphere steel foam, the formation of the stiffer film on the cells macroscopically increased the stiffness of the materials, as shown in Figure 8b. The effect was most apparent at temperatures in the 300 °C to 400 °C range. The stiffening of the steel foam due to the blue brittleness effect became negligible at higher temperatures as the base steel degraded, losing its stiffness and strength. The blue brittleness effect can also be observed in Figure 14 (a), where the retained plateau stress peaked at 300 °C. It is also reflected in the stress-strain curves in Figure 8b.




Action: Before introducing Figure 8b, the order of the curves and their underlying mechanisms were clarified. The text was added to the manuscript that explains the effect of the blue oxide film on the steel foam’s stiffness and strength in the range of 300 °C to




400 °C. The figure which shows the blue film on the tested sample was moved to a new location, immediately following the plotted of stress-strain curves in Figure 8b.




Q8: Error bars must be added to Figures 13, 14, 17-19, 21 and and 22.




Action: Error bars are shown below for the plots contained in Figures 13, 14, 17-19, 21, and 22. In these plots, the span of the error bars was determined by adding and subtracting one standard deviation from the average result, where the mean and standard deviation were calculated, assuming that the samples are drawn from a normal distribution.

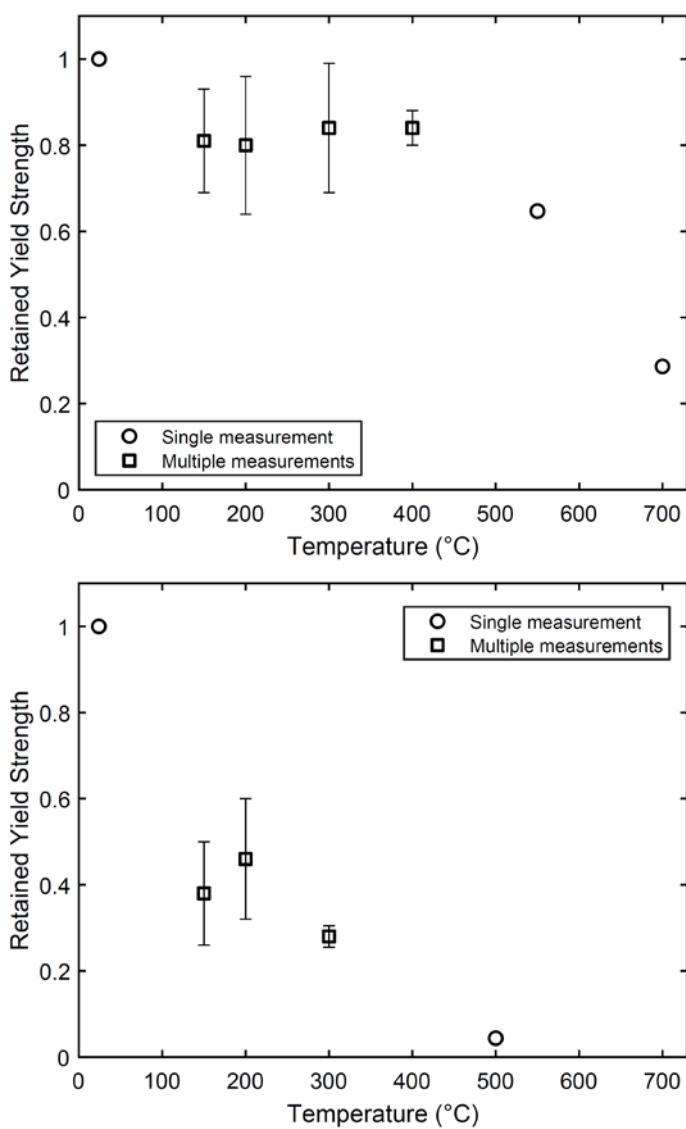

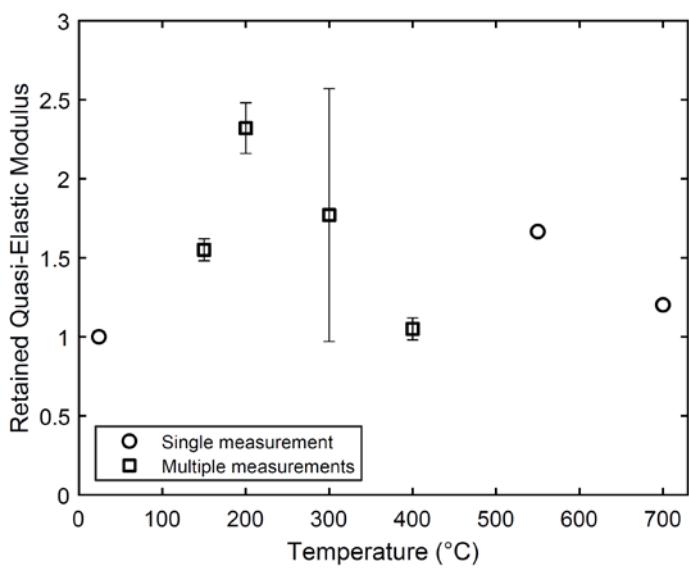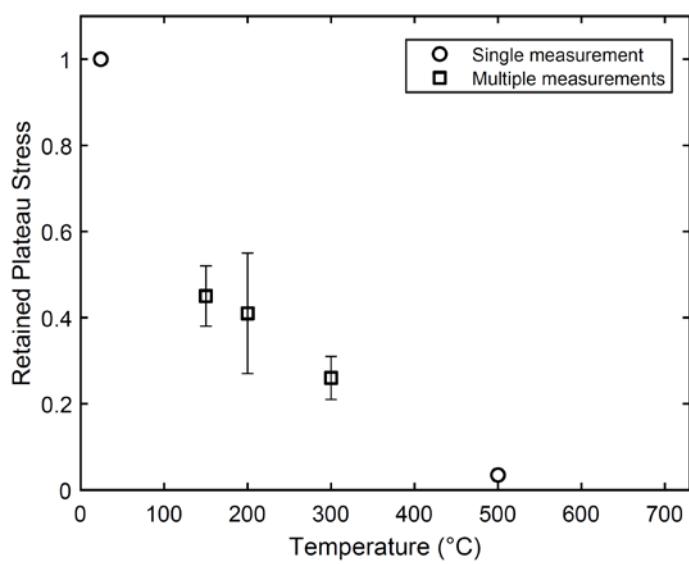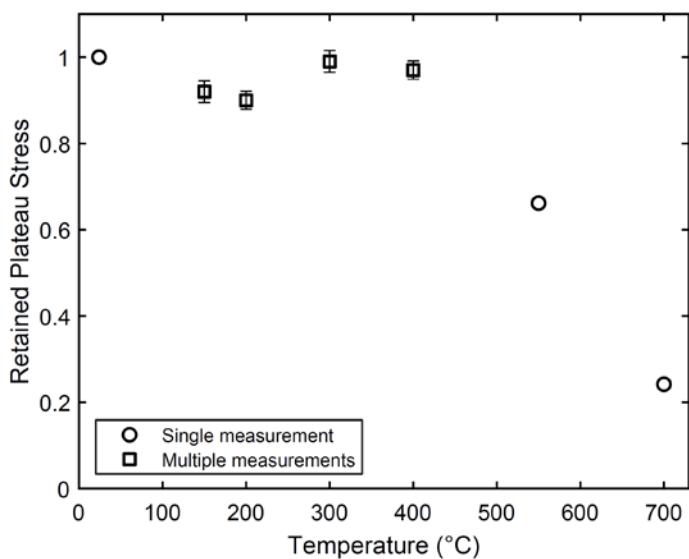

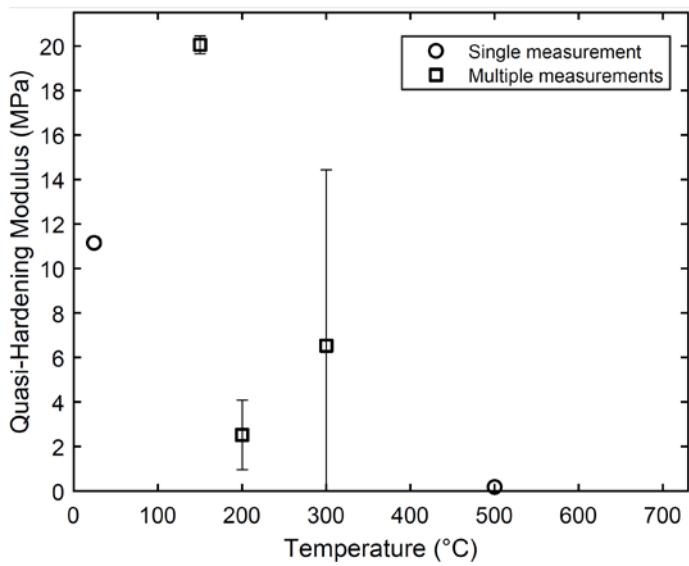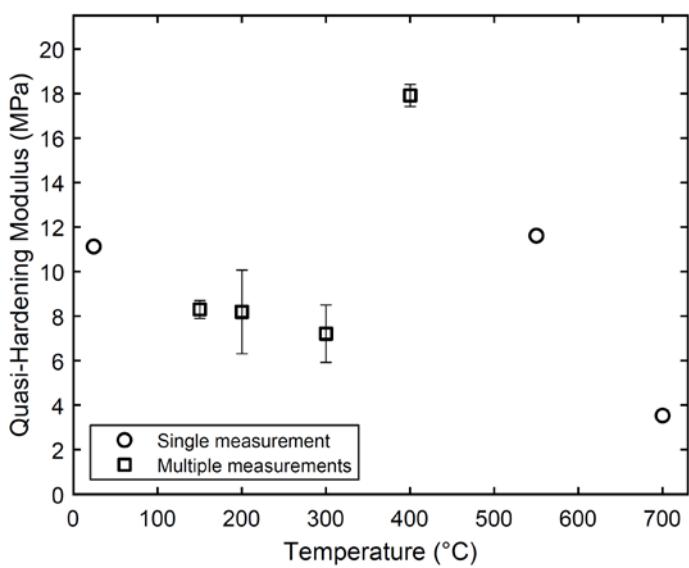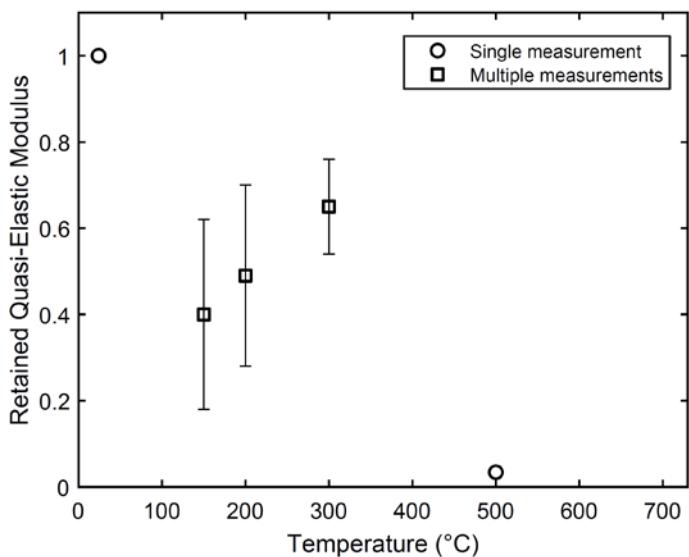

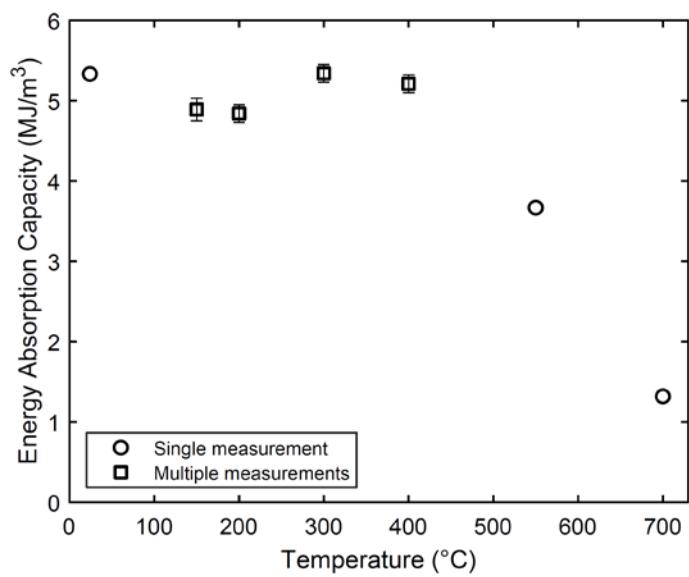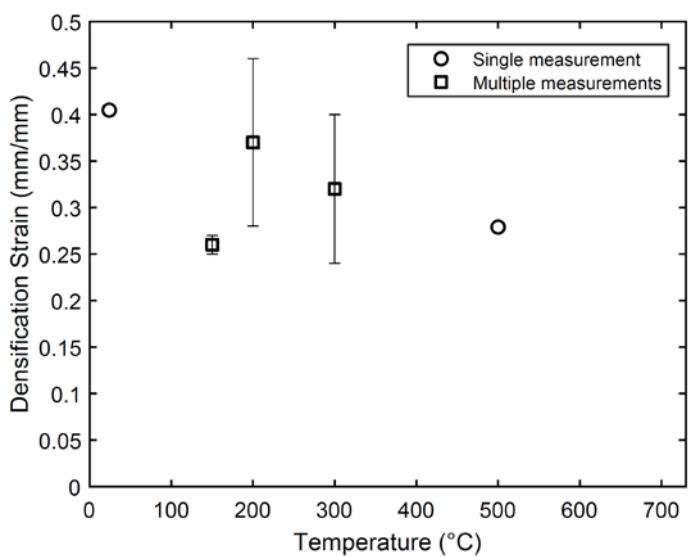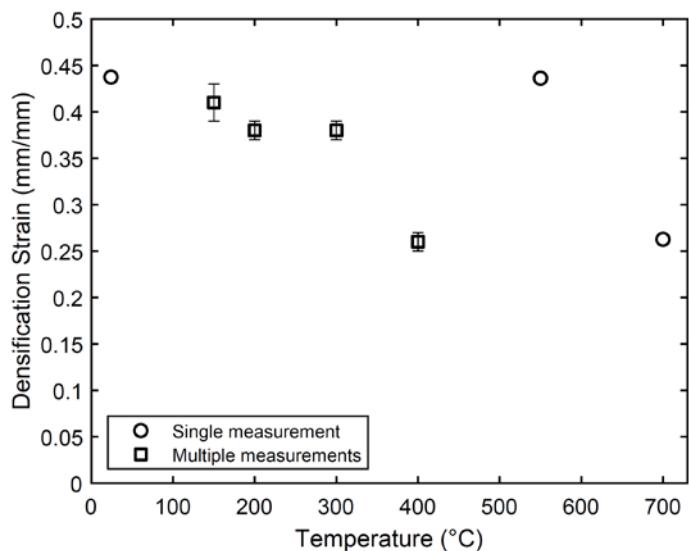

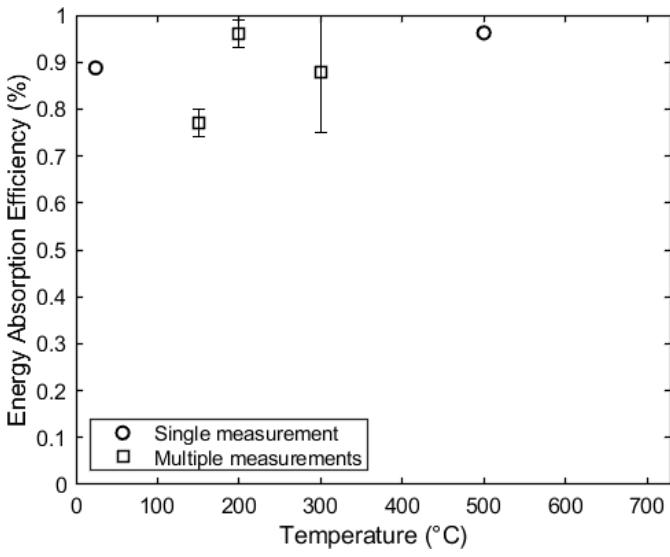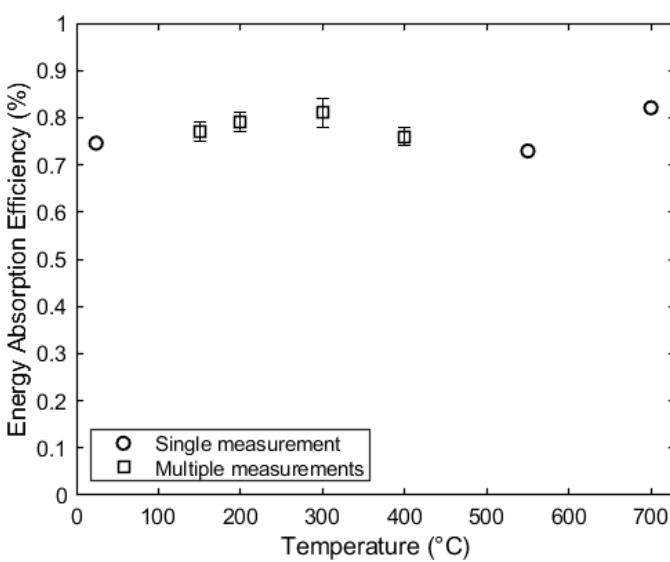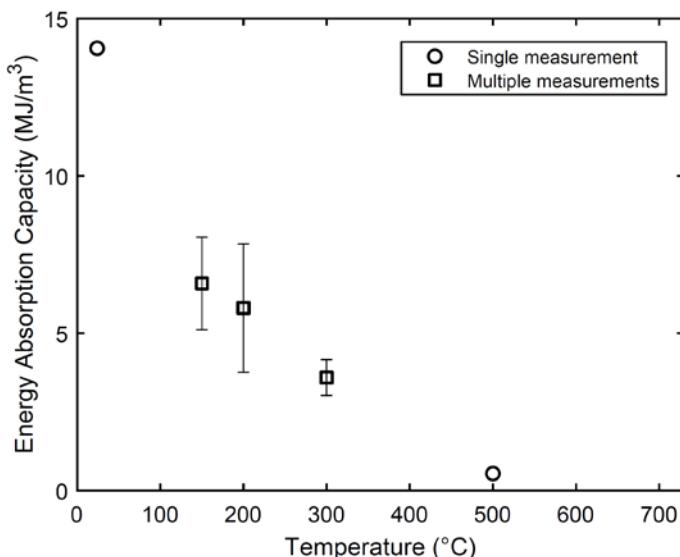

We, however, believe that these figures should not be included in the manuscript, since standard deviation is being calculated, in most cases, based on only four, three or two values. It is a questionable practice to convert three or two values into two other quantities (mean and standard deviation); as such, they mostly lose their meaning.

An alternative is to use the Student's t-distribution to determine, for example, a two-sided error bar with 95% confidence level, but the Student's t-distribution with $n-1$ degrees of freedom, where n is equal to 2 (number of data points in some cases), would result in a multiplicative factor of 12.71 – a very high factor – on the sample standard deviation, instead of the well-known 1.96 factor used for infinity many data points.

Since the authors used the experiments to validate and confirm simulations, an analytical derivations, plotting the actual data points reduces the risk of the reader's misunderstanding. It is important to note that we have not used experiments to derive empirical observations but to validate and cross-check our computational and analytical results.

Q9: *Figure 20 can be deleted because it is not representative.*

Action: We used representative test data of steel alloy at ambient temperature, instead of the previously used schematic. Thus the figure is now representative, and we would like to retain in the manuscript.

Q10: *Some tabular results of the compressive properties are encouraged to be presented.'*

Action: Tabulated test data are now included in the supplementary materials. A sample of these tabulated data are included in the screenshot shown below:

Specimen	Material	Temperature	Time of exposure	Retained yield strength	Mean	STD	COV
N°		(°C)	(min)				
1	Steel	150	15	0.73			
2	Steel	150	30	0.89	0.81	0.12	15%
3	Steel	200	15	0.69			
4	Steel	200	30	0.91	0.80	0.16	20%
5	Steel	300	15	0.72			
6	Steel	300	30	0.70			
7	Steel	300	15	0.94			
8	Steel	300	30	0.99	0.84	0.15	18%
9	Steel	400	15	0.87			
10	Steel	400	30	0.82	0.84	0.04	4%
11	Steel	550	15	0.65			
12	Steel	550	30	NA	---	---	---
13	Steel	700	15	0.29			
14	Steel	700	30	NA	---	---	---
15	Aluminum	150	15	0.30			
16	Aluminum	150	30	0.47	0.38	0.12	32%
17	Aluminum	200	15	0.35			
18	Aluminum	200	30	0.56	0.46	0.14	32%
19	Aluminum	300	15	0.27			
20	Aluminum	300	30	0.29	0.28	0.01	4%
21	Aluminum	500	15	0.04			
22	Aluminum	500	30	NA	---	---	---

Q11: The reference list must be standardized because abbreviations or complete Journal names are used.

Action: The reference list has been standardized to use only complete journal names.

Q12: The used Standards must be presented also in References list.

Action: All Standards used in the manuscript were added to the References.

Q13: The Introduction section must be improved. There are certain research groups (Movahedi et al., Linul et al., Marsavina et al., Fiedler et al., etc.) dealing with the compressive behavior of different metallic foams at room and low/high temperature testing conditions. Please refer to their works in the Introduction section.

Action: The introduction has been revised and expanded to include additional recent references across a variety of materials journals. In addition to the citations that were included in that section in the previous revision, citations to the following papers were added:

- D.P. Mondal, N. Jha, A. Badkul, S. Das, R. Khedle. "High temperature compressive deformation behaviour of aluminum syntactic foam." *Materials Science and Engineering A*, 534 (2012), 521–529. doi:10.1016/j.msea.2011.16512.002.
- N. Bekoz, E. Oktay. "High temperature mechanical properties of low alloy steel foams produced by powder metallurgy." *Materials and Design*, 53 (2014), 482–489. doi:10.1016/j.matdes.2013.07.050.
- N. Movahedi and E. Linul. "Quasi-static compressive behavior of the ex-situ aluminum-alloy foam-filled tubes under elevated temperatures." *Materials Letters*, 206 (2017), 182–184. doi:10.1016/j.matlet.2017.07.018.
- E. Linul, N. Movahedi, L. Marsavina. "The temperature effect on the axial quasi-static compressive behavior of ex-situ aluminum foam-filled tubes." *Composite Structures*, 180 (2017), 709–722. doi:10.1016/j.compstruct.2017.08.034.
- E. Linul, D. Lell, N. Movahedi, C. Codrean, T. Fiedler. "Compressive properties of zinc syntactic foams at elevated temperatures." *Composites Part B*, 167 (2019) 122–134. doi:10.1016/j.compositesb.2018.12.019.

Q14: Some recent developments published in the *International Journal of Mechanical Sciences* should be considered, showing continuity between the present work and those reported in the literature on similar topics.

Action: Citations to a number of recent articles were added from the *International Journal of Mechanical Sciences*, which address the effects of the elevated temperature on the mechanical properties of material systems. These include:




- Richeton, J., Ahzi, S., Vecchio, K.S., Jiang, F.C., Adharapurapu, R.R., 2006. Influence of temperature and strain rate on the mechanical behavior of three amorphous polymers: Characterization and modeling of the compressive yield stress. *International Journal of Solids and Structures* 43, 2318–2335.
- Thomas, J.D., Triantafyllidis, N., 2007. Theory of necking localization in unconstrained electromagnetic expansion of thin sheets. *International Journal of Solids and Structures* 44, 6744–6767.
- Zhang, Y., Liu, W., Yin, C., Ma, Y., Wang, L., 2020. Mode II interfacial fracture characterization of foam core sandwich materials at elevated temperatures: the effects of frictional stresses between the crack edges. *International Journal of Solids and Structures* 193–194, 28–38.

Q15: English is not the native language of this Reviewer; however, the manuscript requires some grammatical corrections.

Action: A comprehensive editorial review was conducted to improve the language and grammar of this manuscript.

Highlights

- Thermo-mechanical behaviour of cellular steel and aluminium foams,
- Plastic buckling of spherical cells links base material properties with global mechanical performance,
- Ultra-thin walled cellular structures are predicted to show reversible elastic buckling and large deformation capability,
- Oxidation reactions at the surfaces of the cells could increase their mechanical properties at high temperatures.

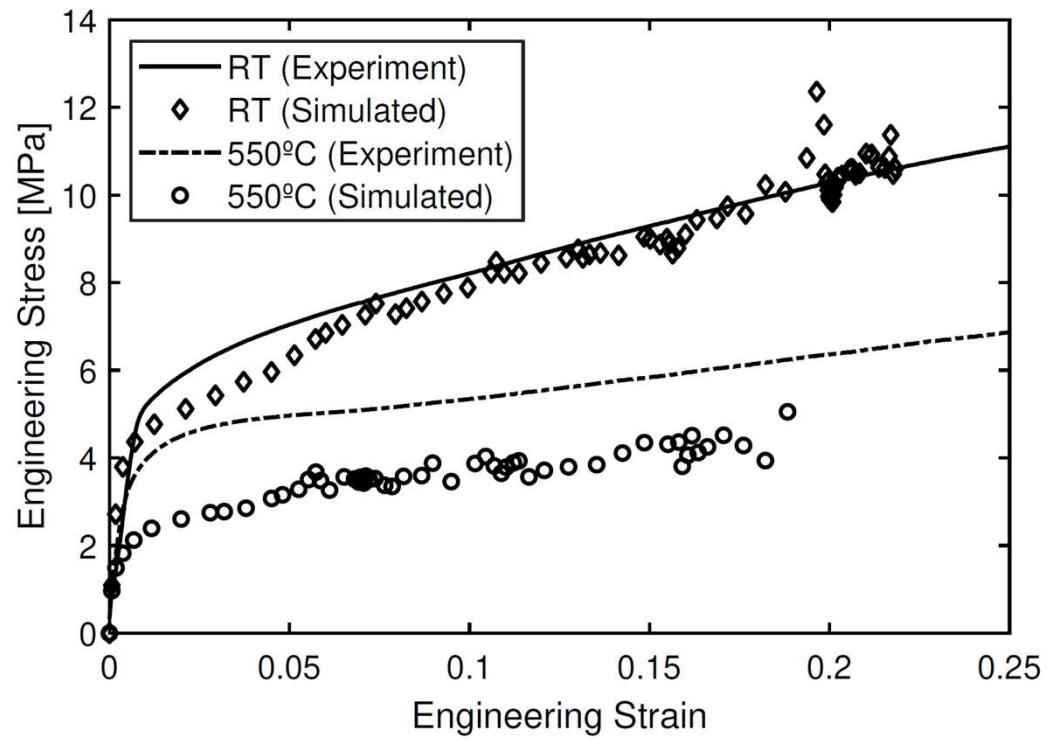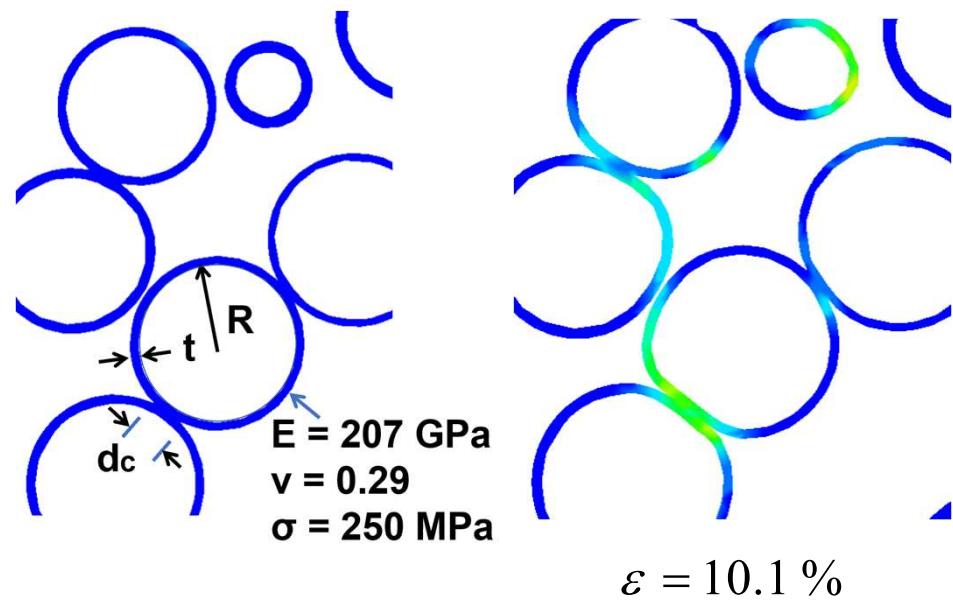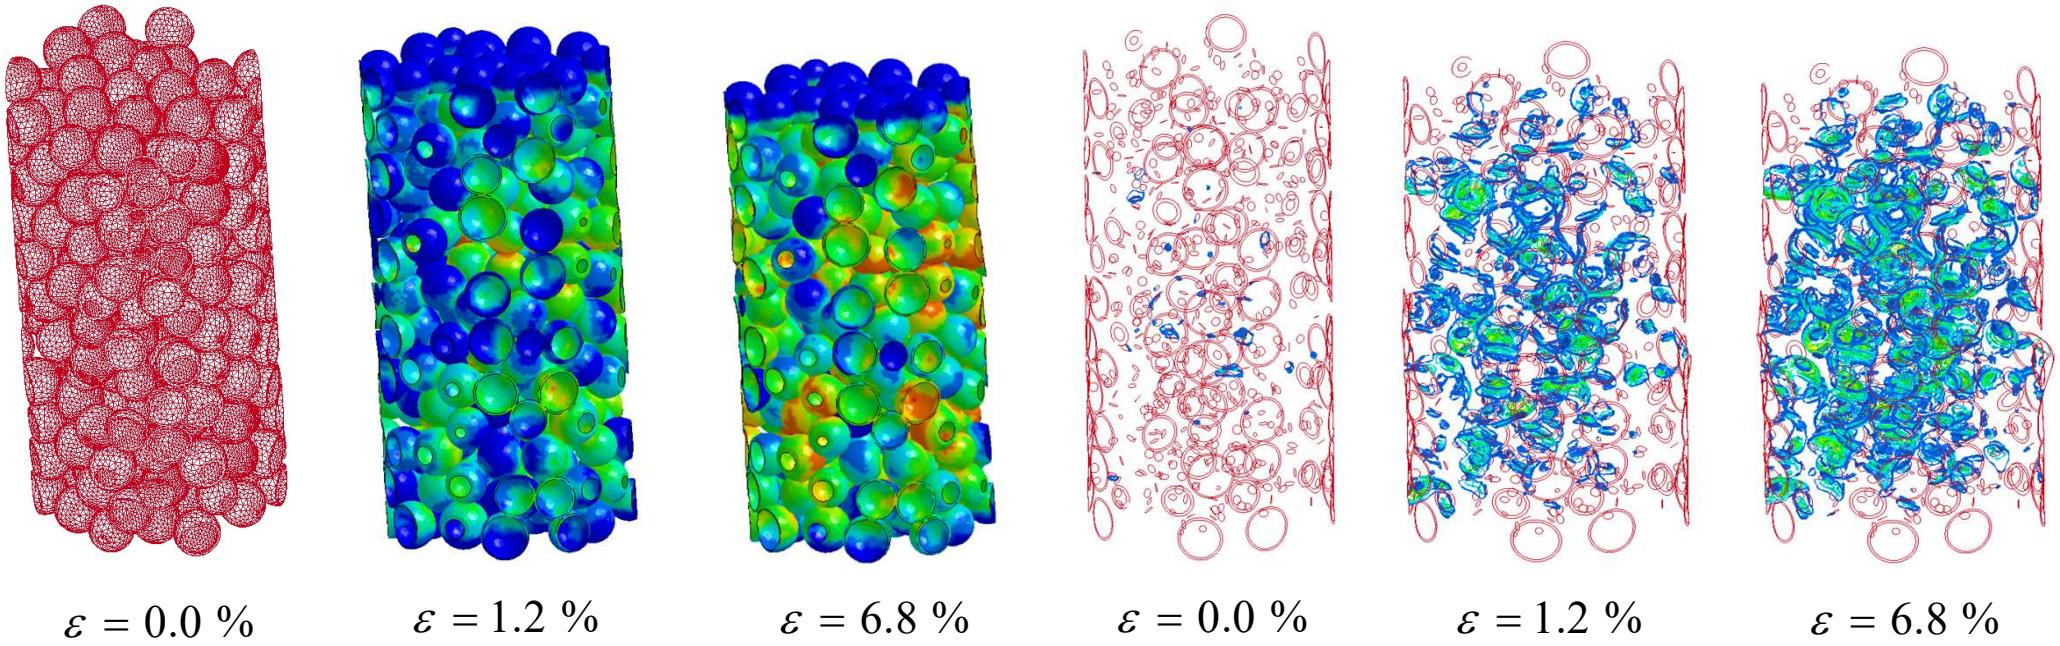

Mechanical Behavior of Steel and Aluminum Foams at Elevated Temperatures. Local buckling based approach toward understanding of the material system behavior

M. Tavares^a, J. M. Weigand^b, L. C. M. Vieira Jr.^a, S. J. C. Almeida^a, S. Szyniszewski^{c,*}

^a*Department of Structural Engineering, State University of Campinas, Campinas, Brazil*

^b*National Institute of Standards and Technology (NIST), Gaithersburg, Maryland, USA*

^c*Department of Engineering, Durham University, Durham, UK*

Abstract

The objective of this study is to understand and quantify the thermo-mechanical behavior of hollow sphere (HS) steel and powder metallurgy (PM) aluminum foams over a broad range of elevated temperatures. The behavior of both the HS steel and PM aluminum foam is tested under compressive loading at ambient temperature (24 °C) and elevated temperatures of 100 °C, 150 °C, 200 °C, 300 °C, 400 °C, 550 °C and 700 °C, and results for the two foams are compared by their rates of degradation in mechanical properties. To link the cell geometry and base metal properties with the global mechanical performance, the experimental work is underpinned by a computational micro-model, consisting of an assembly of hollow spheres. The computational model shows that plastic buckling of cells with progressive plasticity of the contact area is the key local failure mechanism. As expected, due to the plastic buckling of the unit cells, thermal degradations of the tested metallic foams follow similar trends as does the yield stress of their bulk metals. The HS steel foam exhibits only minor elevated-temperature-induced degradation in stiffness and strength at or below 400 °C, while still maintaining 69 % of its compressive strength at 550 °C. Comparatively, the PM aluminum foam begins degrading at an elevated temper-

*Corresponding author

Email address: s.szyniszewski@gmail.com (S. Szyniszewski)

ature of only 150 °C. Interestingly, the HS steel foam oxidized between 300 °C and 400 °C, resulting in corresponding increases in the quasi-elastic modulus of elasticity. Future work might explore how to take advantage of oxidation reactions at the surfaces of the cells in the design of components using HS steel foams. Our computational study also revealed a possible new regime of cellular structures made up of ultra-thin-walled spherical cells that are predicted to fall within the elastic buckling regime at the local level. Thus, their deformations would be reversible even under high strains and their thermal behavior would be only controlled by thermal deterioration in the elastic constants, rather than plasticity parameters such as the yield stress.

Keywords: Metallic foam, Plastic buckling, Thermal analysis, Hollow-sphere steel foam, Thermo-mechanical analysis, Fire.

1. Introduction

Cellular materials are commonly found in nature (for example, bird bones, cork) because they are lightweight, and tissue can grow into their open cells enhancing biological interfaces. Metallic foam is an intentionally porous metal substratum largely made up of voids varying in size from nanometers to millimeters. Because the physical parameters of a metal foam, such as its porosity, can be readily controlled during manufacture, the metallic foam's modulus of elasticity and yield stress can be tuned to satisfy an engineering project's specific needs, especially in the context of multi-functional and multi-physical engineering applications.¹⁰

Metallic foams have inherent fire retardancy, low thermal conductivity (relative to traditional metal structural components), and acoustic shielding. Open cell foams, albeit more expensive than conventional materials, also provide air, vapor, and fluid transport capabilities. Open cell foams act efficiently as heat exchangers due to the turbulent well-mixing flow that occurs within the foam's irregular micro-structural cavities, combined with the large surface area of their pores and high thermal conductivity of their base metals. The influences of

various micro-structural properties of metal foams, such as their porosity, pore and fiber diameters, tortuosity, pore density, and relative density on the heat
20 exchanger performance were discussed in [1]. Vadawala [2] showed that a new composite material combining copper foam with wax was efficient in increasing the thermal conductivity of thermal energy storage systems. Cellular metals are also used as catalyst support in fuel cells. Their large surface area and mixing potential increases the intensity of the interaction between the catalyst
25 and the fluid medium. Yuneta et al. [3] provides a review of the fabrication, characterization, and application of porous metal materials to fuel cells.

While existing applications for metallic foams reside largely in the mechanical, aerospace, and automotive domains [4], decreasing manufacturing costs and more widespread adoption of full-scale production techniques has ushered in the
30 potential for using metallic foams in civil infrastructure applications. Metallic foams exhibit excellent stiffness-to-weight ratios, in comparison to conventional building materials, under a variety of loading conditions. For example, Banhart and Seeliger [5] showed that foam panels have higher bending stiffness than solid steel sheets of the same weight. Metallic foams are also renowned for their compressibility because they can reliably sustain 90 % engineering strain prior to failure [6], lending them extraordinary energy dissipation capacity [7]. Energy dissipation via large compressive deformations at low-amplitude stress levels has been explored by the automotive industry as a potential crash protection technology [8].

40 The ambient-temperature mechanical properties of metallic foams, specifically steel and aluminum foams, are characteristically different from those of their solid base metals. Steel foam is highly-compressible after yielding, unlike solid steel [9], which exhibits only shear deformations and is incompressible in the plastic regime. Also, foams tend to fracture under tensile strains that are
45 noticeably lower than their crushing and compaction strains [10] thus warranting tailored respective failure criterions. Szymiszewski et al. [11] tested fifty hollow sphere (HS) steel foam bars to measure their compressive yield stress, densification strain, compressive plastic Poisson's ratio, compressive unloading

modulus, as well as axial and shear mechanical properties at ambient temperature. Szyniszewski et al. [11] noted the importance of correctly assessing Poisson's ratio due to its link to foam compressibility as shown by Deshpande and Fleck [9].

Research has shown that temperature influences the mechanical properties of engineering materials [12], and can reduce capacity of engineering systems such as sandwich panels [13]. Thermo-mechanical behavior is also important for manufacturing approaches employing electrical current or electromagnetic forming (EMF) [14]. Elevated temperatures have a significant influence on the compressive behavior of metallic foams. [15] conducted a series of compressive tests on ALPORAS, a commercially-available closed cell aluminum foam manufactured by the Shinko-wire Company, at temperatures ranging from 25 °C to 620 °C. They found that the foam's compressive strength decreased both with decreased density and increased temperature. [16] tested the mechanical properties of powder metallurgy steel foams at ambient and elevated temperatures, and reported an increase in compressive yield strength and stiffness for temperatures at or below 400 °C, and a decrease in compressive yield strength and stiffness above that temperature. [16] concluded that the aging effect (i.e., dynamic age-hardening) was responsible for the increase in mechanical properties up to 400 °C. [17] examined the high-temperature compressive behavior of powder metallurgy aluminum foams at temperatures ranging from 20 °C to 500 °C. They observed that increased temperatures resulted in decreased compressive strength and decreased energy absorption capacity, but increased densification strain (i.e., plateau length) at constant density. [17] also reported that exposure time (the amount of time which the specimen was held at a constant elevated temperature before compressing it) did not influence the foam's compressive behavior. As part of a broader study on the behavior of ex-situ aluminum-alloy filled tubes under elevated temperatures (see [18]), [19] performed one quasi-static compressive test of a closed-cell aluminum foam specimen at temperatures of 25 °C, 150 °C, 300 °C, and 450 °C. Their results found only minor degradation in yield stress at or below 300 °C, after which, because of passing

80 through its transition temperature, the degradation was more pronounced. [19] notes that, as the aluminum cell-walls began softening at higher temperatures, the morphology of the compressive stress-strain behavior became smoother, such that the aluminum foam behaved in a similar manner as a ductile metal.

Many additional studies have investigated the compressive behavior of composite or alloyed metallic foams at elevated temperatures. After testing the compressive behavior of cenosphere-filled aluminum syntactic foams at elevated temperatures of 100 °C and 200 °C, and strain rates ranging from $10^{-3}/\text{s}$ to $1/\text{s}$, [20] found that plateau stress decreased with temperature irrespective of strain-rate. [21] tested Distaloy (Cu-Ni-Mo) and Astaloy (Mo) foams having different degrees of porosity at elevated temperatures of 200 °C, 400 °C, and 600 °C. They found that the length of the yield plateau (in units of compressive strain) was appreciably affected by porosity but not temperature. They also observed that compressive yield strength increased up to a temperature of 400 °C, after which it sharply decreased at 600 °C. [22] investigated the compressive behavior of composite Al-Si-SiC foams at elevated temperatures, evaluating the influence of temperature on energy absorption and type of fracture. They reported a decrease in compressive strength with increasing temperature, as well as a decrease in absorbed energy when a ductile-type fracture mode occurred. [23] tested expanded perlite-aluminum syntactic foam cylinders in compression at elevated temperatures, comparing the foam's resulting temperature-degraded mechanical properties against those of the matrix materials, tested under the same conditions. Their results showed that the high-temperature behavior of the foams was controlled both by temperature-dependent softening of the matrix materials and a transition of the deformation behavior of the foam from brittle at low temperatures to ductile at high temperatures. [24] investigated the effect of temperature on the microstructure, failure mechanism, and compressive mechanical properties of commercially-available zinc-aluminum alloy syntactic foams with expanded perlite or expanded glass filler particles at four elevated temperatures of 100 °C, 200 °C, 300 °C, and 350 °C. The results showed that while the foam with expanded perlite was stronger than the foam with expanded

glass across all elevated temperatures, the relative reduction of plateau stress of the two foams was similar.

As a continuation of the work presented in [11], this study examines the thermo-mechanical behavior of HS steel foam samples removed from the same rectangular prism. Specifically, this paper characterizes and compares the mechanical properties of HS steel and powder-metallurgy (PM) aluminum foam specimens both exposed to a wide range of elevated temperatures, up to 700 °C and 500 °C, respectively, for durations of 15 min and 30 min. Consistent with ISO Standard 13314:2011, the yield strength and plateau stress are calculated for each specimen. To permit additional characteristics of their compressive stress-strain responses to be calculated, for example the strain at which densification begins, a nine-parameter phenomenological equation fitted to the compressive stress-strain response of each specimen. Finally, to examine the plasticity that localized at sphere interfaces due to contact forces, high-fidelity computational models of hollow-sphere foams were also conducted using LS-DYNA [25].

2. Experimental approach

Material samples

A HS steel foam rectangular prism, sourced from Fraunhofer Institute in Germany, with dimensions of 22 cm × 5.2 cm × 5.2 cm, was cut and machined into 10 cylindrical specimens following the specifications in the ISO Standard 13314:2011 [26]. The cylindrical specimens had a diameter of 25 mm and length of 50 mm (Figure 1).

According to ISO standard for testing, all spatial dimensions of the specimen shall be at least 10 times larger than the average pore size and no less than 10 mm, and the ratio of the length to the diameter shall be between 1.0 and 2.0. The measured average pore size was 2.27 mm, and the method for determining the average pore size is explained below. Between 12 and 14 spheres typically spanned across the 25 mm radius. The specimens had an average 85 % porosity, calculated based on the dimensions and volume of the specimens. The base

¹⁴⁰ metal was mild steel with 0.3 % to 0.5 % carbon content and 0.5 % phosphorous content. Based on that chemical composition, the base metal's bulk yield stress was estimated as 250 MPa, using the method outlined in [27]. [28] reported a yield stress of 260 MPa for the same material. The ultimate tensile capacity of the base metals was estimated as 500 MPa, based on tests performed by IFAM ¹⁴⁵ on tensile specimens produced by Spark Plasma Sintering and homogenization annealing. This estimate was consistent with data for alloys with similar carbon and phosphorous contents reported in the literature, see Worldwide Guide to Equivalent Irons and Steels table with Australian steel [27].

¹⁵⁰ The rectangular prism of PM aluminum foam had dimensions 14.8 cm × 6.0 cm × 6.0 cm, and was sourced from Fraunhofer Institute for Machine Tools and Forming Technology IWU in Chemnitz, Germany. Like for the HS steel specimens, the PM aluminum foam prism was machined into 8 cylindrical specimens, each with a diameter of 25 mm and length of 50 mm, in accordance with ISO 13314:2011. Due to the inherent heterogeneity of PM foams, the porosity varied between 71.4 % and 81.8 % for the 8 cylindrical specimens. The base metal consisted of a common aluminum alloy AW-6060 (AlMgSi0.5). ¹⁵⁵

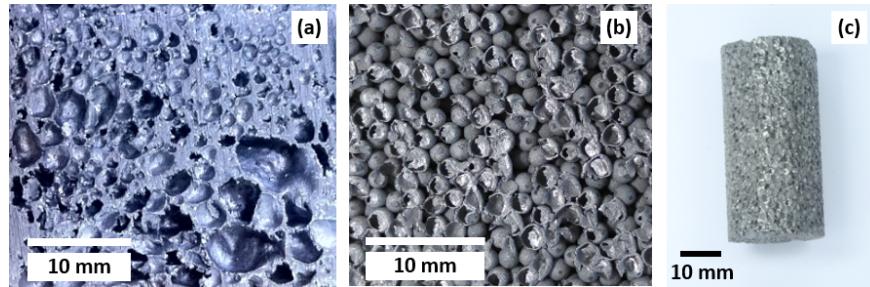


Figure 1: Metallic foam samples: (a) closeup view of PM aluminum foam, (b) closeup view of HS steel foam, and (c) HS steel foam cylinder specimen prior to compressive testing. The aluminum foam resembles a highly porous metallic medium while the steel foam resembles closely packed hollow spheres.

Pore Size Dimensions

The dimensions of the pores were determined to ensure that each cross-section contained a sufficient number of pores to achieve relatively homogeneous material properties. Based on a high-definition image of a transverse cut of the base samples, the largest dimension of 242 pores for HS steel foams and 237 pores for aluminum foam were measured. The 20 mm distance between the jaws of a Mitutoyo digital caliper was used as a reference length for the pixel distance measurement. 726.20 pixels = 20 mm in the HS steel foam, and 236.51 pixels = 10 mm in the PM aluminum foam (see Figure 2).

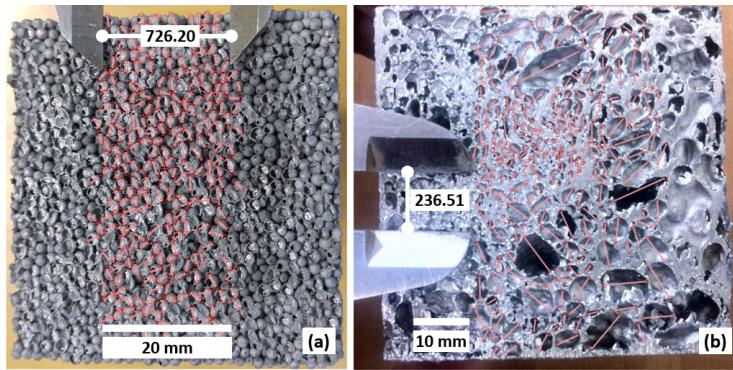


Figure 2: Method for measuring pore size for (a) HS steel foam specimens, and (b) PM aluminum foam specimens. Diameters of the spherical shells or pores are depicted using red lines.

A normal distribution with mean of 1.79 mm and variance of 0.19 mm² best described the pore sizes measured in the HS steel foam (Figure 3a). On the other hand, the aluminum foam's pore size was best captured by a lognormal distribution with mean of 2.13 mm and variance of 1.67 mm² (Figure 3b).

If the pore shape is spherical, the measurement of the pore size through a transverse cut will be smaller than the pore diameter, unless the cut passes exactly through the pore's center (Figure 4). Thus, an amplification factor was proposed to improve the estimate of the pore diameter from sectional pore measurements.

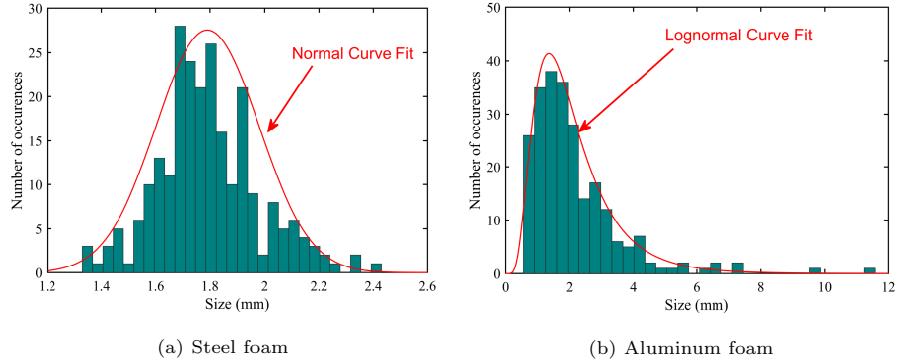


Figure 3: (a) Normal distribution of pore size of HS steel foam, (b) Lognormal distribution of pore size of PM aluminum foam. Independent of the distribution type, the HS steel foam had a lesser variability than did the PM aluminum foam, as characterized by a larger scatter in pore size.

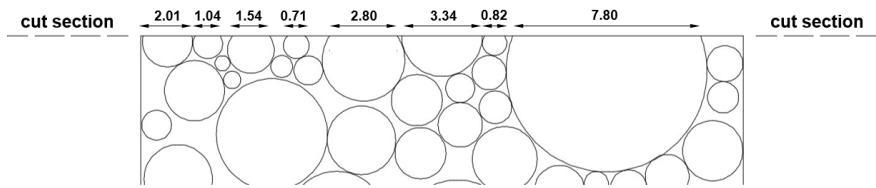


Figure 4: Schematic view of lateral cut plane through cylindrical sample. The cross-sectional diameters generally do not coincide with the true diameter of the sphere or cavity.

¹⁷⁵ Let us consider an unknown amplification factor as the ratio between the mean of the projected radius values and the true sphere's radius (Figure 5). If all pores are assumed as spherical, random cuts can be generated using a uniform random distribution of $h_{proj} \in \langle 0, r_{true} \rangle$ and for each cut a projected radius can be computed as:

$$r_{proj}^i = \sqrt{r_{true}^2 - h_{proj}^i} \quad (1)$$

¹⁸⁰

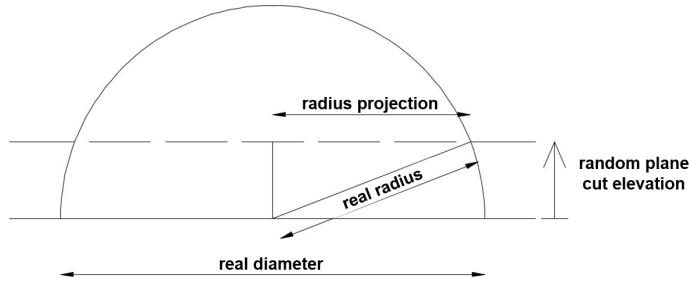


Figure 5: By cutting a sphere at a random elevation, the relationship between the expected mean radius in the cut plane and the real radius of the spherical cavity can be calculated.

Employing Monte-Carlo simulation, the average value of \hat{r}_{proj} was calculated; consequently, the correction factor was calculated as:

$$\alpha = \frac{r_{true}}{\hat{r}_{proj}} \quad (2)$$

¹⁸⁵ An amplification factor $\alpha = 1.27$ was obtained. This value resulted in corrected average pore diameters of $1.27 \times 1.79 \text{ mm} = 2.27 \text{ mm}$ in HS steel foam and $1.27 \times 2.13 \text{ mm} = 2.70 \text{ mm}$ for aluminum foam, which leads us to conclude that the specimens must have at least 22 mm and 27 mm of cross-sectional width respectively. Considering the size of aluminum and steel foam blocks, specimen diameters of 25 mm were chosen as a representative for both base materials.

¹⁹⁰ **3. Behavior of HS steel and PM aluminum metallic foams at elevated
temperatures**

Mechanical testing

Steel foam specimens were tested at 24 °C (ambient temperature), 150 °C, 200 °C, 300 °C, 400 °C, 550 °C, and 700 °C, while aluminum foam specimens
¹⁹⁵ were tested at 24 °C, 150 °C, 200 °C, 300 °C, and 500 °C (Table 1). For the most part, two specimens were tested at each temperature except ambient; one exposed to the elevated test temperature for 15 min, and the other exposed for 30 min. The exceptions were the 550 °C and 700 °C tests on the HS steel foam, and the 500 °C test on aluminum foam, which were all exposed for only
²⁰⁰ 15 min. For each test, the high-temperature furnace was heated to the test temperature without the specimen inside. Once the targeted elevated temperature was reached, the cylindrical metallic foam specimen was placed inside the furnace. The compressive test was not started until the specimen had reached and been held under a steady-state conditions at the target testing temperature
²⁰⁵ for the required exposure time. The testing temperature was regulated by a thermocouple installed on the side of each specimen. [29] reported that mild steel melts at a temperature of approximately 1536 °C, and [7] estimated the aluminum melting temperature at approximately 660 °C. The majority of the testing temperatures was conducted at elevated temperatures less than 400 °C
²¹⁰ because, based on both the available literature and EN 1993-1-2:2005 [30], the strength of steel is severely degraded at elevated temperatures exceeding 400 °C. The sensitivity of the mechanical properties to exposure time was evaluated by conducting the compressive testing following both 15 min and 30 min of steady-state pre-heating.

²¹⁵ **3.1. Testing approach**

The compressive testing was conducted using a servo-hydraulic Materials Testing Systems (MTS) Model 810 Universal Testing Machine (UTM), with a capacity of 100 kN in compression. A MTS Model 652.01 High-Temperature Electric Furnace applied the thermal loads (Figure 6).

Table 1: Temperature and exposure time during compressive experiments

Temperature (°C)	Steel Foam		Aluminum Foam	
	Melting point (%)	Duration (min)	Melting point (%)	Duration (min)
24	2	∞	4	∞
150	10	15 & 30	23	15 & 30
200	13	15 & 30	30	15 & 30
300	20	15 & 30	45	15 & 30
400	27	15 & 30	-	-
500	-	-	76	15
550	37	15	-	-
700	47	15	-	-

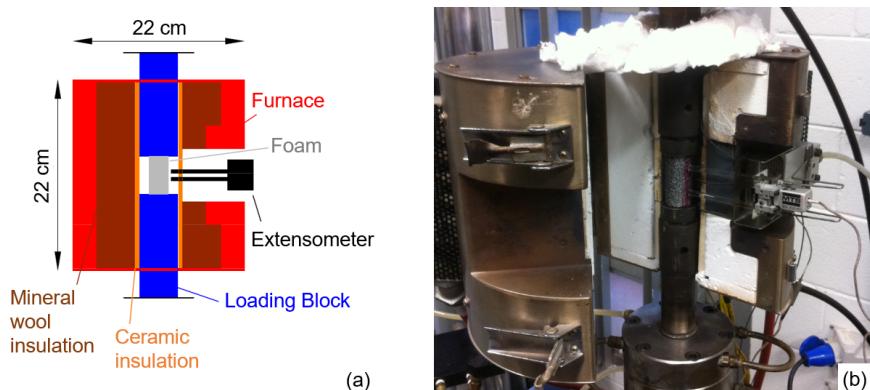


Figure 6: Experimental setup for thermal-mechanical compressive testing: (a) annotated schematic of high-temperature furnace, and (b) actual view of the opened furnace. Specimens were first heated and subsequently loaded in compression after internal temperature stabilized at target test temperature. Strains were measured using an extensometer placed inside the furnace.

²²⁰ Mechanical loads in the UTM were controlled using a MTS Flex Test 60 controller, and the furnace was controlled using a MTS Digital PID Temperature Controller. The high-temperature furnace allows pre-heating at temperatures up to 1000 °C, has multi-zone temperature control to compensate for vertical temperature gradients, and is accurate (at the constant steady-state temperature) to within ± 2 °C. After a preload of 0.10 kN was applied to remove any surface irregularities, axial loading was applied pseudo-statically using displacement control at a constant loading rate of 0.025 mm/s. The reported compressive stress, σ , was calculated as the ratio of the applied force F to the measured cross-sectional area before loading. Ideally, the reported compressive strain ϵ would be measured using the available MTS High-Temperature Axial Extensometer. However, for many specimens the tips of the extensometer leads slipped at relatively low compressive loads, and thus for consistency the compressive strain was calculated as the ratio of crosshead displacement to the measured length of each undeformed cylindrical specimen.

²³⁵ *3.2. Experimental stress-strain curves*

The compressive stress-strain behavior of metallic foams exhibited three distinct phases of behavior (Figure 7). Until yield, the behavior was elastic (Elastic Phase), and the stress was linearly related to the strain. After yield was a large plastic plateau (Plateau Phase). Within this region, an upper and lower yield point can be identified. The final phase (Densification Phase) is characterized by densification of the metallic foam, during which the stiffness of the compressive stress-strain curve rapidly increases. During densification, the cell walls of the metallic foam begin to buckle and contact one another as the voids close. The densification phase continues until the metallic foam reaches its compressibility limit. The slope of the stress-strain curve within the densification phase is defined as the densification modulus.

Results from the steel and aluminum foam specimens tested under uniaxial compression at elevated temperatures are shown in Figures 8a) and 8b), respectively. Similar trends were observed for both types of metallic foam, in that each

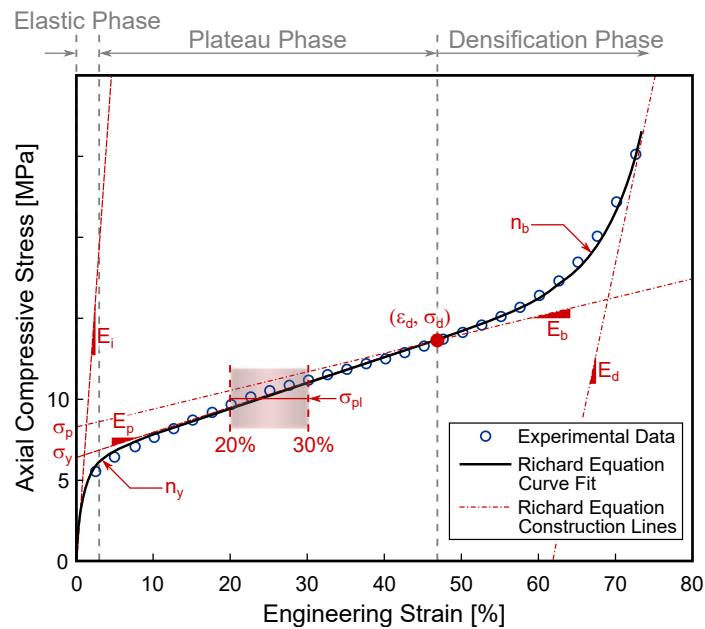


Figure 7: Three phases of compressive behavior of metal foams comprising an elastic phase, plateau phase, and densification phase. Plot annotations schematically depict the parametrization of the non-linear stress strain behavior of metallic foams, defined in Equation (11).

²⁵⁰ specimen exhibited, but to varying degrees, the three phases of behavior shown in Figure 7. The exposure (15 min or 30 min) did not appear to have had a systematic influence on the stress-strain behavior of the specimens. Kovacic et al [17] also reported that exposure time to elevated temperature did not influence the foam's compressive behavior.

²⁵⁵ An insightful reader might notice that properties at 300 °C are higher than room temperature or 100 °C. In addition, those from 400 °C are higher than those from 200 °C, which might initially seem puzzling. However, a thin blue oxide film was observed to form on all cells of the steel foam specimens at temperatures exceeding 250 °C (see Figure 9). The effect of steel oxidation at ²⁶⁰ around 300 °C, the so-called "blue brittleness effect", is a phenomenon that occurs in steel alloys with significant Carbon content upon heating, particularly within temperatures ranging from 180 °C to 370 °C ([31]). The blue oxide layer, which forms on the surface of the metal, is stiffer and stronger than the base steel alloy but more brittle. The addition of a stiffer film on the cells increased ²⁶⁵ the macroscopic stiffness of the foam due to the large surface area relatively to the volume of the base material. The effect of the distributed stiffening of the steel foam become negligible at higher temperatures when the base steel of the cells deteriorated past the transition temperature of 400 °C. The effect of a blue oxide film also affected parametric properties of the stress-strain curves, ²⁷⁰ such as plateau stress in the systematic analysis of the macroscopic steel foam properties at elevated temperatures described later in the paper.

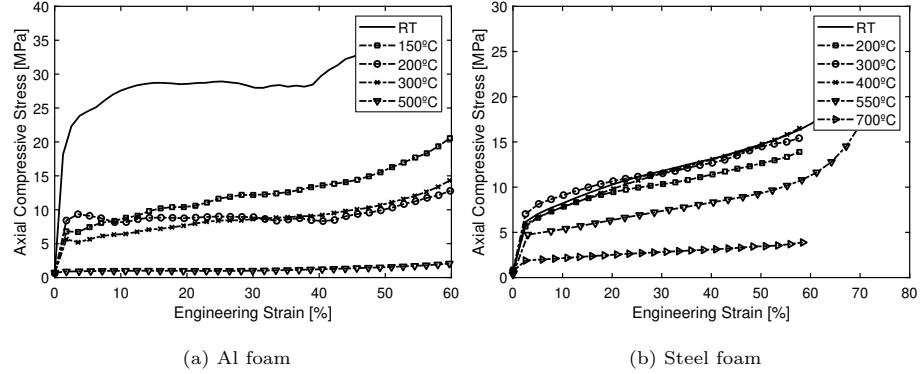


Figure 8: Stress-strain behavior of metallic foam specimens at ambient and elevated temperatures for (a) HS steel foam specimens, and (b) PM aluminum foam specimens.



Figure 9: (left) HS steel foam specimen before testing, and (right) HS steel foam specimen after testing at 300 °C following 30 min of exposure. Discoloration of the heated specimen indicated formation of a blue oxide film on the surfaces of the spherical shells.

4. Micro-mechanical simulations

The microstructure of a sintered HS foam consists of hollow spheres and welds between those spheres. The spheres have been shown to be in a random
275 close-packed (RCP) stacking configuration [32]. Wouterse and Philipse [33] tested five algorithms for generating random RCP sphere stacking and showed that two different variations of the “Mechanical Contraction Method” resulted in stackings that were most like an experimental stacking in their geometric properties. The algorithmically simpler of those two methods, the “Modified
280 Mechanical Contraction Method”, was chosen for the presented simulations, which involves the steps below. These steps are described in more detail in [34], [35].

1. Randomly place spheres of zero size throughout the domain.
2. Increase the size of all spheres by an equal magnitude.
- 285 3. Check for overlapping spheres and move both spheres in each overlap pair away from each other by an equal magnitude. Repeat this step until all but a minimum threshold of overlaps are eliminated.
4. Repeat Steps 2 and 3 until the final sphere size is reached.

After the spheres are successfully placed, welds are inserted to connect them.
290 The actual welds between the spheres are solid circular shapes with concave sides which curve until they reach a tangent with the sphere. However, due to the difficulty of modeling such a shape, these welds were approximated by a straight cylinder of a given diameter connecting any spheres within a specified threshold distance. The random variables in this geometry algorithm include sphere size,
295 wall thickness, and sphere location. The deterministic variables include the weld size, structure, and some of the input parameters for the Modified Mechanical Contraction Method such as the number of spheres to initially place and the number of overlaps threshold at which to increment the size of the spheres.

The core algorithms and functionality of the simulator was originally developed
300 by Smith and Arwade ([28, 36]. The algorithm produced geometries such

as that displayed in Figure 10a). The original implementation used the AD-INa solver, but in this study, the scripts were modified to generate meshes for LS-DYNA ([25]) due to its superior ability to handle multiple, concurrent contacts. The analyses used an implicit integration scheme for numerical efficiency and stability. The mechanical properties of the base steel at ambient temperature and 550 °C as shown in Table 2. The properties are based on mechanical testing of samples with similar chemical content, namely Fe-C(0.5)-P(0.5) by Fraunhofer Institute in Dresden and independent data from World Wide Guide of Equivalent Irons and Steels ([37]).

Table 2: Mechanical properties employed in the simulations.

Property	Value	
	Ambient	550 °C
Young modulus, GPa	200	91
Poisson ratio	0.29	0.29
Yield stress, MPa	250	67.5
Ultimate strain, mm/mm	0.18	0.21
Ultimate strength, MPa	600	192

The von Mises effective stress of the model under increasing compressive pressure (Figure 10b-c) indicated localized plasticity at the sphere interfaces, which led to sphere deformations. Simulated stress strain curve compared well with the experimental curve (see Figure 10d). The simulated curves became irregular at large strains because the implicit algorithm used in LS-DYNA struggled to converge because of the large number of contact surfaces. The simulated curve at 550 °C is noticeably higher than the experimental curve. This discrepancy is attributed to strengthening of the spherical shells due to oxidation of the steel foam at elevated temperatures (see Figure 9). This strengthening was not accounted for in the computational model.

The plastic strains localized in a few contact locations at 1.2 % global en-

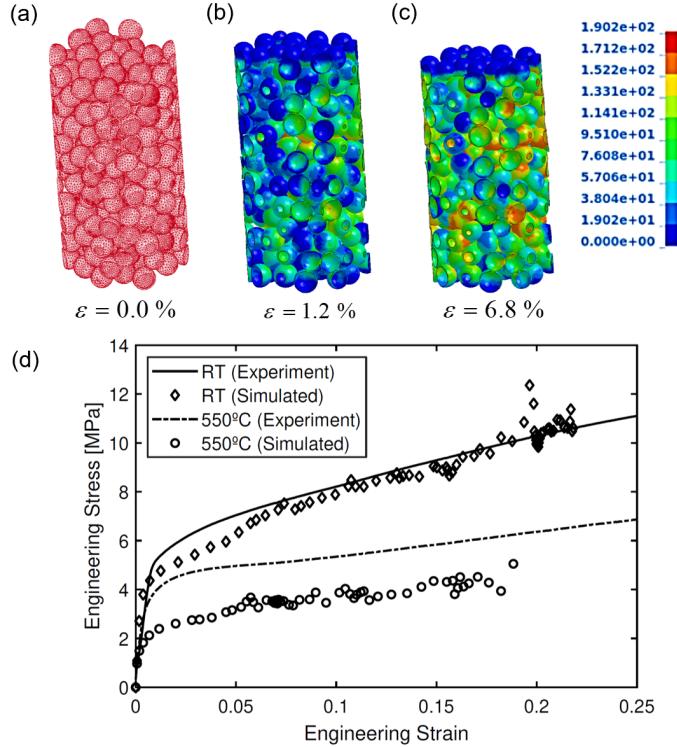


Figure 10: Comparison of computational (diamonds and circles) and experimental (continuous lines) strength predictions at room (RT) and high temperature (550°C). Von Mises stress (MPa) localized in the contact regions of the hollow steel spheres. Multiple and irregular load paths followed the random packing of the spheres, which resulted from the nature of the manufacturing process. Whereas simulated and experimental data showed good agreement, steel foam samples exhibited higher stiffness and strength at high temperatures when compared to the computational prediction.

gineering strain with progressively more localized plasticity regions with larger volume appearing at larger strains (Figure 11a-c). The randomness and tortuosity of the internal load paths is consistent with experimental study by Gründer et al. [38]. They tracked increasing contact areas between the spheres using CT images, while increasing the compressive loads. The location of the contact areas and direction of the local load paths changed from sphere to sphere in a random, chaotic manner. It is consistent with our simulated cross-sections in the micro-model. Figure 11d-f illustrate the typical deformation mechanism of the individual spheres. Even though only cross-sections are shown, these deformations are 3-dimensional and mostly axi-symmetric. The key parameters identified by [39], such as sphere radius R , thickness t , diameter of the contact area, and degraded mechanical properties of the base metal are all significant. The simulations showed that the diameter of the contact area was not constant; it gradually increased until the sphere collapsed at large strains. The simulations clearly indicated that plasticity dominated the local deformations of our HS steel foam samples.

4.1. Insights from the analytical expressions for buckling of a spherical shell

Pressure applied to a sphere, q_c needs to satisfy equilibrium with the membrane stress within the walls of the spherical shell [40]:

$$\sigma_{shell} 2\pi R t = q_c \pi \frac{d_c^2}{4} \quad (3)$$

340

Thus, the membrane stress resulting from the applied pressure can be approximated as:

$$\sigma_{shell} = q_c \frac{d_c^2}{8Rt} \quad (4)$$

When the critical limit of the membrane stress is exceeded, it may fail either due to material yielding at the elastic limit, σ_y , or due to the buckling arising

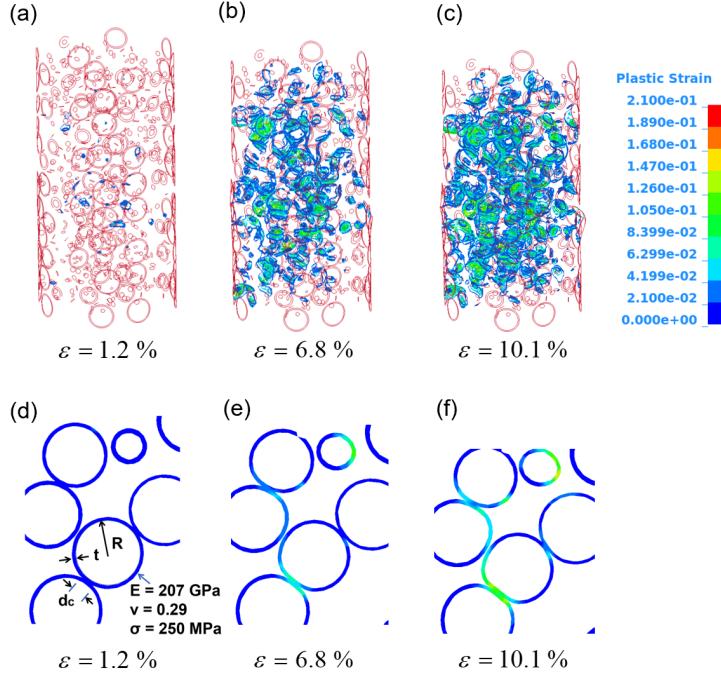


Figure 11: Plasticity localized at sphere interfaces experiencing plastic deformations arising from contact forces. As the load increased, the number of contact pairs and subsequently, plastic regions surged (b-c). Radius, R and thickness, t of the spherical shell, the diameter of the contact interface, d_c and material properties of the hollow spheres influence the local resistance mechanism (d). Following the initial yielding around the contact region, the plasticity spreads toward the equator of the sphere, accompanied by the gradually increasing diameter of the plastic hinge hoop moving outwards from the initial contact area (e-f). Due to the random packing, the number of contact regions and their directions vary from sphere to sphere, which is consistent with experimental study reported by Fallet et al. [39].

³⁴⁵ from its geometric imperfections. The shell's stress limit to avoid the elastic buckling is taken from [40] as:

$$\sigma_{cr} = \frac{Et}{R\sqrt{3(1-\nu^2)}} \quad (5)$$

³⁵⁰ Yielding typically leads to geometrical buckling anyway and the loss of the ideal spherical shape. Thus, the shell capacity of a hollow sphere can be expressed as:

$$\sigma_{failure} = \min(\sigma_y, \sigma_{cr}) \quad (6)$$

³⁵⁵ In the simulations, the steel base metal had a modulus of elasticity of $E = 200$ GPa, Poisson's ratio of $\nu = 0.29$, and yield stress of $\sigma_y = 250$ MPa. The average radius and thickness of the spheres were reported in a previous study [11] as $R = 1.86$ mm and $t = 0.02$ mm, respectively. The resulting geometrical slenderness, expressed as the ratio of the radius to the thickness, $R/t = 93$, is consistent with the plastic buckling region (Figure 12a). A more general measure of the slenderness is the ratio of the plastic yield stress to the elastic buckling stress because it includes the influence of the material properties on ³⁶⁰ the slenderness:


$$\lambda = \frac{\sigma_y}{\sigma_{cr}} \quad (7)$$

³⁶⁵ If slenderness $\lambda < 1$, then the structure is controlled by the material failure, namely plastic yielding. Alternatively, $\lambda > 1$ indicates high slenderness and propensity for elastic buckling (Figure 12b). Winter [41] developed an empirical curve for metallic plates, which showed that the transition between plastic and elastic buckling capacities is more gradual, and that there exists additional post-buckling reserve capacity in the elastic buckling regime. Even considering


Winter's curve, the HS steel foam, as well as other foams reported by [39], are still controlled by plastic buckling.

³⁷⁰ Coincidentally, the elastic buckling equations of a spherical shell also describes the elastic buckling capacity of a circular shell. Thus, the buckling curve in Figure 12b can also be used to analyzed hollow tubular lattice structures. Even considering the lightest metallic material achieved to-date by Schaedler et al. [42], only one of their configurations was in the elastic buckling region. Schaedler's experiments showed that the slender lattice exhibited large, reversible deformations, while the stub lattices experienced non-reversible deformations but higher absolute strength. These experimental observations are consistent with plastic and elastic buckling of the cylindrical shells at the junctions of the hollow tubular struts.

³⁸⁰ Based on a review of available data, conventionally produced HS foams exhibit local deformation mechanism controlled by the plastic buckling of the spherical shells. Thus, the thermal degradation of the global mechanical properties of our HS foam specimens is anticipated to be controlled by the influence of elevated temperatures on the base metal's yield stress.

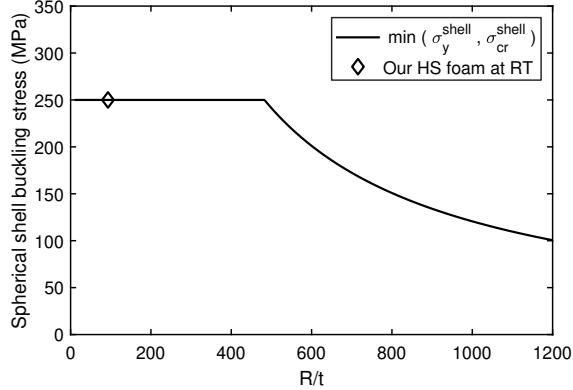

(a) The effect of geometric slenderness on the buckling capacity of a single sphere.

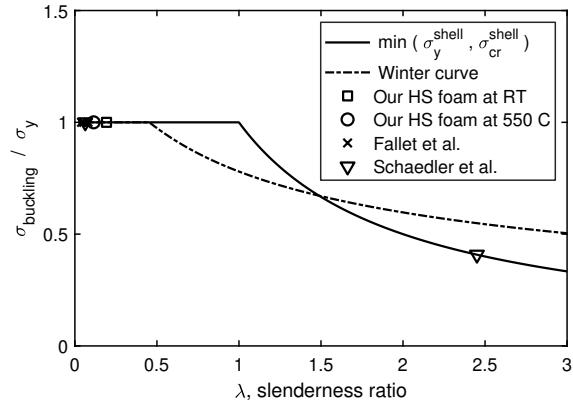

(b) The effect of slenderness ratio on the buckling strength of a hollow sphere.

Figure 12: Buckling capacity of a single spherical shell expressed in terms of its critical membrane stress. Geometric slenderness of our hollow sphere steel foam expressed as the ratio of radius to thickness, R/t is low and consistent with the plastic buckling mechanism. Normalized theoretical buckling stress as a function of the non-dimensional slenderness parameter, λ overlaid with a range of theoretical capacities of foams and tubular lattice structures. Apart from the ultra-light metallic lattice, most of the manufactured cellular structures have very low slenderness, which is consistent with the irreversible, plastic buckling.

³⁸⁵ Regarding the influence of the temperature on the stiffness of the foam, radial displacement of a spherical shell under uniform external pressure, q is a function of its geometry and elastic constants [40]:

$$w(\varphi) = \frac{q(1 + \nu)R^2}{Et} \left[k(\varphi) \cot \varphi + \cos \varphi - \frac{1}{1 + \cos \varphi} \right] \quad (8)$$

where $k(\varphi)$ is the auxiliary variable:

$$k(\varphi) = \left(1 - \frac{1}{1 + \cos \varphi} + \log(1 + \cos \varphi) \right) \sin \varphi \quad (9)$$

³⁹⁰ The deformation of the apex corresponds to $\varphi = \frac{\pi}{2}$, which gives:

$$w_{apex} = -\frac{q(1 + \nu)R^2}{Et} \quad (10)$$

³⁹⁵ Since the direct influences of temperature on the radius and thickness of the sphere, as well as Poisson's ratio, are expected to be minimal, the thermal degradation of the foam stiffness is anticipated to be controlled by the base metal's modulus of elasticity.

5. Standard Metrics Calculated based on ISO Standard 13314:2011

⁴⁰⁰ The following sections synthesize experimental observations to reveal the trends of the macroscopic material properties such as the plateau stress and ambient-temperature modulus of elasticity. Based on the computational and analytical considerations described in Section 3, it was anticipated that the phenomenological properties of the HS foam, with stub spherical shells, would primarily reflect the thermal degradation trends of their base metals' plastic properties.

5.1. Yield Strength

⁴⁰⁵ Porous metallic materials are known to exhibit substantial plastic yielding capacity following an initial elastic phase, but they do not typically ex-

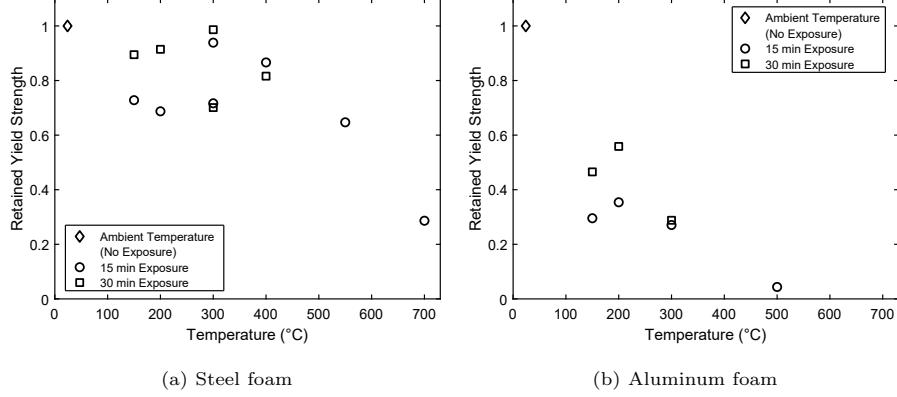


Figure 13: Retained yield strength $\sigma_y/\sigma_{y,\text{amb}}$, measured using the 0.2 % strain offset method, for: (a) HS steel foam, and (b) PM aluminum foam. In Equation (11), σ_y corresponds to the projection of the plastic modulus at zero strain.

hibit a “yield plateau”. Therefore, ISO Standard 13314:2011 recommends using the 0.2 % strain offset method to calculate the quasi-elastic compressive yield strength of porous metallic materials. Figure 13 show the retained yield strength of the HS steel and PM aluminum foams. At temperatures at or below 400 °C the HS steel foam retained an average of about 80 % of its ambient-temperature yield strength, but at temperatures exceeding 400 °C the yield strength was significantly degraded. The PM aluminum foam retained an average of less than 50 % of its ambient-temperature yield strength at or below 200 °C, and the retained yield strength was only 4.4 % at 500 °C.

5.2. Plateau Stress

The plateau stress, shown in Figure 14, was calculated following ISO Standard 13314:2011 as the average value of the stresses within the strain range spanning from 0.20 mm/mm and 0.30 mm/mm. There was little degradation in the measured plateau stress of the HS steel foam specimens at or below a 400 °C. However, the plateau stress of the PM aluminum foam specimens had significantly degraded by approximately 50 % at only 150 °C (i.e., at only 23 % of aluminum’s melting point).

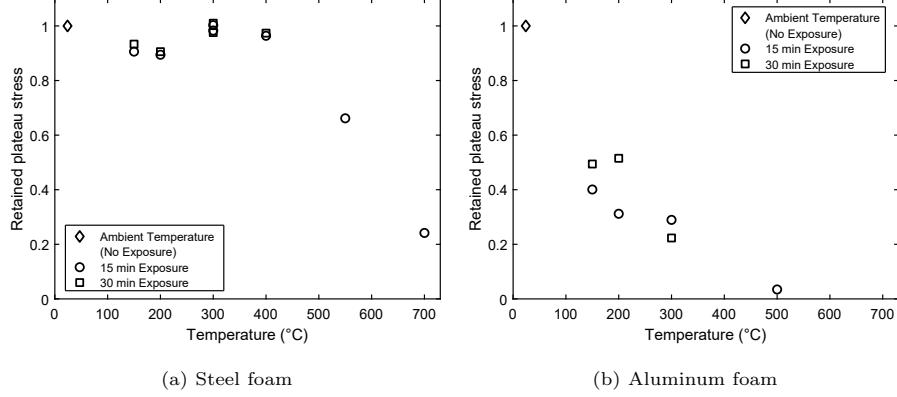


Figure 14: Retained plateau stress $\sigma_{\text{pl}}/\sigma_{\text{pl, amb}}$, where the plateau stress is depicted in Figure 7 as the average stress computed between 20 % and 30 % strain, for: (a) HS steel foam, and (b) PM aluminum foam.

The exposure (15 min or 30 min) had relatively little influence on the retained plateau stress for the HS steel foam; the retained plateau stress for the two exposures did not differ by more than 4.0 %. The retained plateau stress of the PM aluminum foam was more scattered, but no systematic influence of exposure on the energy absorption capacity was observed. It was noted that the porosity of the PM aluminum foam specimens ranged from 71.4 % to 81.8 %, which may have increased the variability in their calculated mechanical properties, relative to those for the HS steel foam specimens.

5.3. Additional Metrics Calculated based on Multi-Parameter Curve Fit

To further characterize the response of the HS steel and aluminum foams, the nine-parameter phenomenological equation

$$\sigma(\varepsilon, T) = \begin{cases} \frac{(E_i(T) - E_p(T)\varepsilon)}{\left(1 + \left|\frac{(E_i(T) - E_p(T)\varepsilon)}{\sigma_y(T)}\right|^{n_y(T)}\right)^{\left(\frac{1}{n_y(T)}\right)}} + E_p(T)\varepsilon, & \varepsilon \leq \varepsilon_d \\ \sigma_d + \frac{(E_b(T) - E_d(T))(\varepsilon - \varepsilon_d(T))}{\left(1 + \left|\frac{(E_b(T) - E_d(T))(\varepsilon - \varepsilon_d(T))}{\sigma_p(T)}\right|^{n_b(T)}\right)^{\left(\frac{1}{n_b(T)}\right)}} + E_d(T)(\varepsilon - \varepsilon_d(T)), & \varepsilon > \varepsilon_d \end{cases} \quad (11)$$

435

where

$$\sigma_d(T) = \frac{(E_i(T) - E_p(T))\varepsilon_d(T)}{\left(1 + \left|\frac{(E_i(T) - E_p(T))\varepsilon_d(T)}{\sigma_p(T)}\right|^{n_y(T)}\right)^{\left(\frac{1}{n_y(T)}\right)}} + E_p(T)\varepsilon_d(T), \quad (12)$$

was fitted to the compressive stress-strain response of each specimen by minimizing the square area between the fitted curve and the experimental data. Similar five-parameter models have been successfully used in previous research to characterize the thermal-structural performance of structural components, such as high-strength bolts (see [43]). Equation 11 is piecewise with the two curve segments joined at the densification point $(\varepsilon_d, \sigma_d)$, where ε_d is the densification strain and σ_d is the densification stress; each of the two segments is based on the nonlinear four-parameter “Richard Equation”, which was formulated in [44]. The coordinates $(\varepsilon_d, \sigma_d)$ also correspond to the inflection point defining the transition to stiffening (densification) behavior. In Equations 11 and 12, σ is the compressive stress, ε is the compressive strain, and E_i and E_p are initial elastic and plastic hardening modulus of the stress-strain response, respectively, σ_y is a reference load that corresponds to the projection of the plastic modulus at zero strain, and n_y is a shape parameter that controls the sharpness of the


⁴⁵⁰ transition from the elastic stiffness to the plastic stiffness. The densification takeoff modulus E_b permits a different takeoff slope for densification than the plastic hardening modulus, σ_p is the projection of the densification stress at zero strain, n_d is a shape parameter controlling the sharpness of the transition from the plastic stiffness to the densification stiffness E_d , and (T) denotes dependence ⁴⁵⁵ of the stiffness or capacity parameter on temperature.

The fitted values for the parameters in Equation 11 were determined using constrained gradient-based nonlinear multivariable optimization techniques available in MATLAB's Optimization Toolbox ([45]). Tables 3 and 4 (located in the appendix) presents a summary of the final fitted parameters for each ⁴⁶⁰ individual foam specimen, and quality of the analytical fits is also shown in Figure 15. Discussion on each of the calculated parameters is provided in the following sections.


5.3.1. Quasi-Elastic Modulus

⁴⁶⁵ The quasi-elastic modulus is the initial slope of the elastic phase of the compressive stress-strain curve. It should be noted that the definition of the quasi-elastic modulus differs slightly from that of the elastic gradient, which can be calculated only after the specimen has been loaded and subsequently unloaded. The quasi-elastic modulus was calculated by fitting Equation 11 within $[0, \varepsilon_y]$, where ε_y is the yield strain calculated using the 0.2 % offset method recommended by ISO Standard 13314:2011. Figures 16a and 16b show Equation 11, ⁴⁷⁰ with fitted parameters calculated using structural optimization techniques, relative to the stress-strain data in the elastic phase. Obviously, Equation 11 can provide a very close approximation to the actual experimental data. The fitted parameter values for each specimen are provided in the appendix.

⁴⁷⁵ Figure 17 show the resulting retained quasi-elastic modulus as a function of temperature. While values for the retained quasi-elastic modulus of the HS steel foam were widely scattered, the quasi-elastic modulus did not degrade noticeably with increasing temperature (i.e., the value of the retained quasi-elastic modulus was greater than 1.0 across the entire temperature range). The

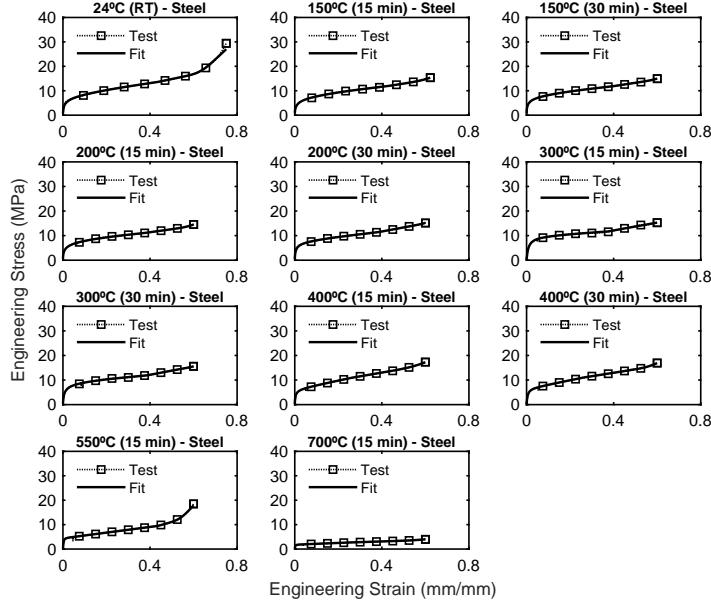


(a) Steel foam

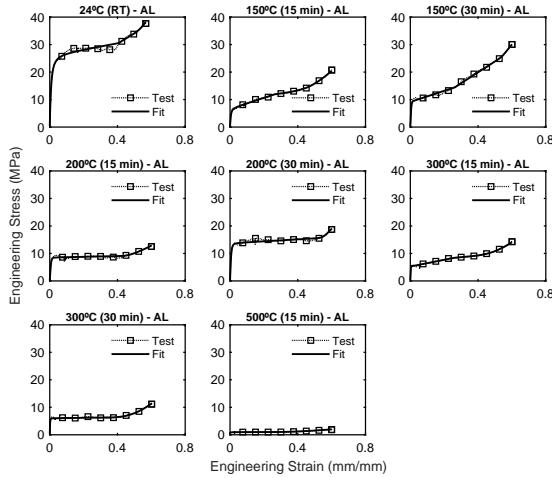


(b) Aluminum foam

Figure 15: Equation (9) fitted to the full stress-strain behavior of each specimen for: (a) HS steel foam specimens, and (b) PM aluminum foam specimens. Each plot is denoted by specimen name, using an annotation located in the upper-left-hand corner.

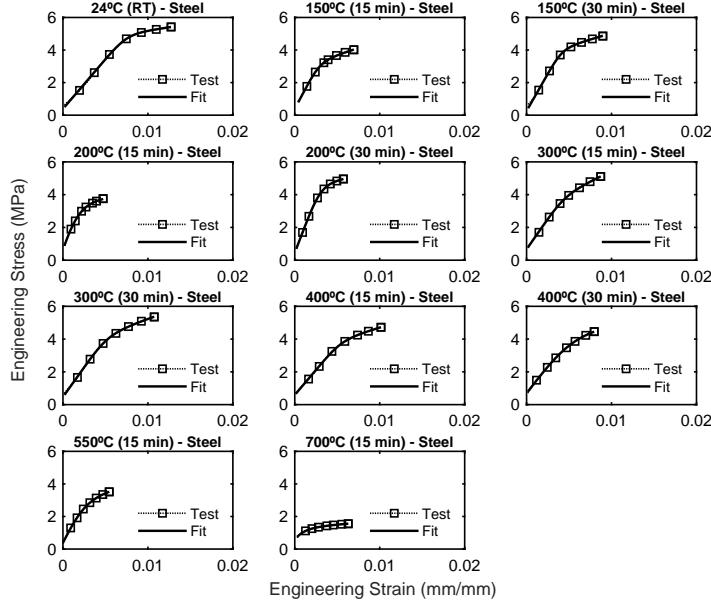

(a) Steel foam

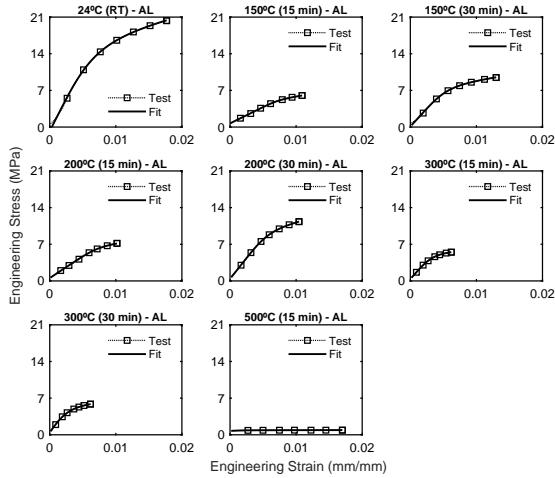

(b) Aluminum foam

Figure 16: Equation (9) fitted to the initial strain range of the stress strain curve for: (a) HS steel foam specimens, and (b) PM aluminum foam specimens. Each plot is denoted by specimen name, using an annotation located in the upper-left-hand corner.

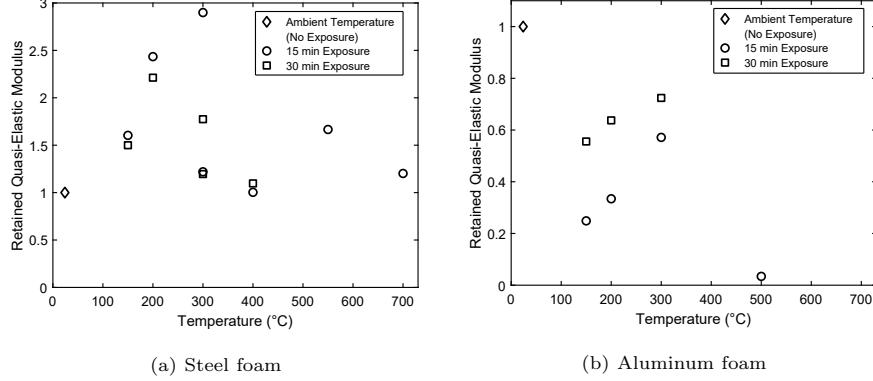


Figure 17: Retained quasi-elastic modulus $E_i/E_{i,amb}$, determined by fitting Equation (9) to the initial strain range of the stress strain curve for: (a) HS steel foam specimens, and (b) PM aluminum foam specimens.

480 largest increases in retained quasi-elastic modulus were at 200 °C and 300 °C. Conversely, quasi-elastic modulus of Aluminum foam deteriorated rapidly with the increase of the ambient temperature.

5.3.2. Quasi-Hardening Modulus

485 As described above, following yield closed-cell foams exhibit significant plastic hardening, which differs from the elastic-perfectly material behavior where the hardening modulus is assumed to be close to zero. To determine the quasi-hardening modulus, Equation 11 was fitted using global error minimization techniques to the entire experimental stress-strain curve for each specimen (shown in Figure 15).

490 The fitted parameters enable close approximation of the full stress-strain behavior of both HS steel and PM aluminum foams even throughout the densification phase. Table 4, located in the appendix, presents a summary of the fitted parameter values for each individual specimen. Figure 18 shows the resulting values of the quasi-hardening modulus as a function of temperature.

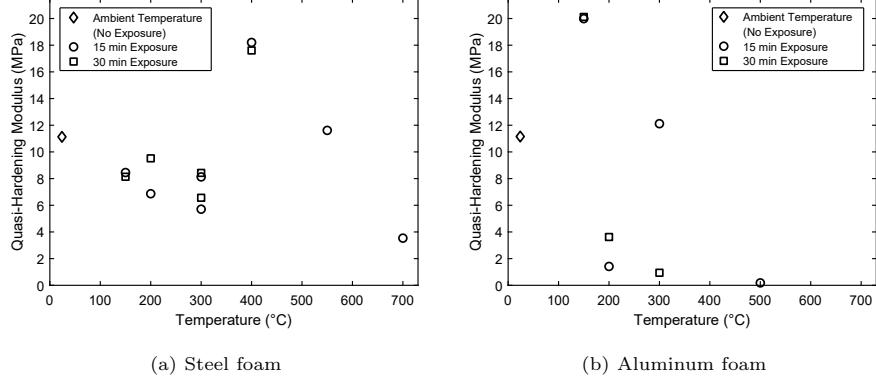


Figure 18: Quasi-hardening modulus, defined by plastic stiffness E_p , for: (a) HS steel foam, and (b) PM aluminum foam.

495 5.3.3. Densification Strain

The point of intersection of the two piecewise curves in Equation 11 identically defines the inflection point between those segments. The strain location of this inflection point is designated in this study as the densification strain, or the strain at which the tangent slope of the stress-strain curve begins to increase relative to the hardening modulus thereby indicating densification of the metallic foam. Figure 19 does not show a clear influence of either elevated temperatures nor exposure on the densification strain. Overall for both the HS steel and PM aluminum foams, the densification strain is scattered by approximately 0.08 mm/mm about a mean densification strain value of about 0.35 mm/mm.

505 5.3.4. Energy Absorption Efficiency

While ISO Standard 13314:2011 does specify a methodology for calculating the energy absorption efficiency, this methodology first requires characterization of the densification strain which could only be reliably determined using the multi-parameter optimization approach described above. The energy absorption efficiency is calculated per ISO Standard 13314:2011 as the ratio of energy absorption capacity to the product of the maximum compressive stress (within the strain range spanning from 0.00 mm/mm to the densification strain), and the value of the densification strain (see Figure 20). The energy absorption

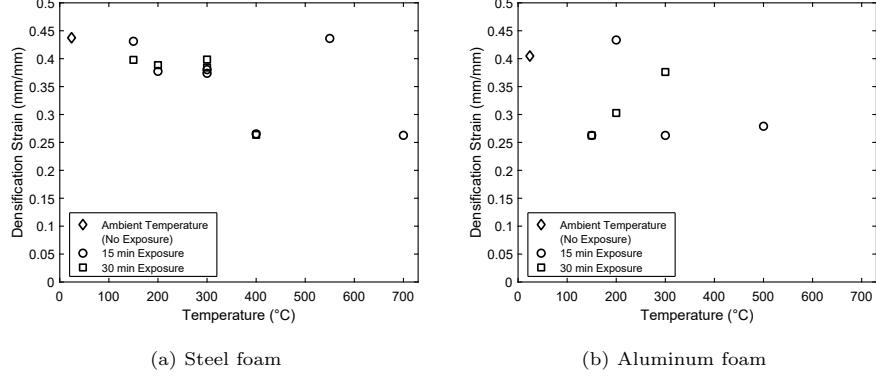


Figure 19: Densification strain, defined at the point of intersection of the two piecewise curves in Equation 11, which identically defines the inflection point between those segments, for: (a) HS steel foam, and (b) PM aluminum foam.

capacity is shown as the hatched area in Figure 20, and the product of the maximum compressive stress within the strain range and the densification strain is the area bounded by the blue rectangle.

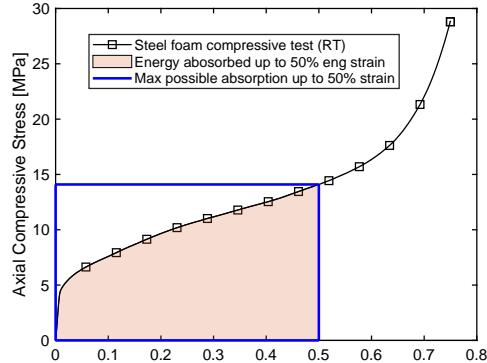


Figure 20: Schematic representation of methodology for calculating energy absorption efficiency.

The energy absorption capacity is calculated either by integrating the stress-strain curve between strains of 0.00 mm/mm and 0.50 mm/mm, or by multiplying the plateau stress by 1.3. The integration-based approach was used in this study. As expected, trends in the behavior of the energy absorption ca-

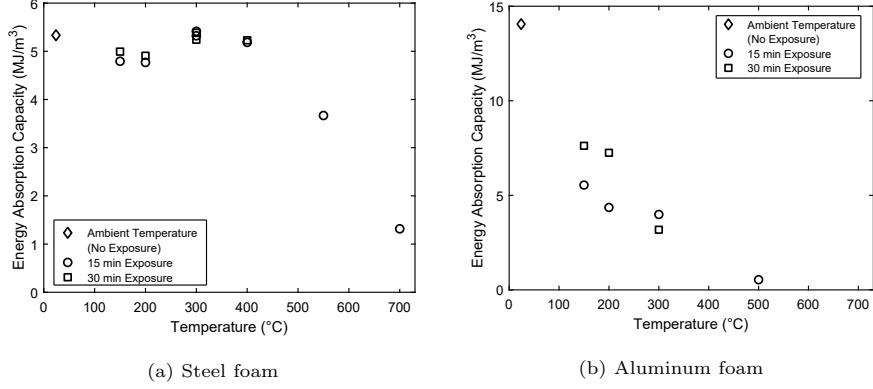


Figure 21: Energy absorption capacity, calculated by integrating the stress-strain curves of the steel foam specimens between strains of 0.00 and 0.50, for: (a) HS steel foam, and (b) PM aluminum foam.

525
pacity are similar to those of the plateau stress. Interesting, while the energy absorption capacity degrades more quickly with increasing temperature for the PM aluminum foam than for the HS steel foam, the energy absorption capacity of the two types of metallic foams is similar between temperatures of 150 °C and 300 °C (Figure 21). The exposure had relatively little influence on the energy absorption capacity for the HS steel foam; the energy absorption capacity for the two exposures did not differ by more than 4.0 %. The energy absorption capacity of the PM aluminum foam was more scattered, but no systematic influence of exposure on the energy absorption capacity was observed.

530
For the HS steel foam specimens, the energy absorption efficiency is nearly constant across all tested temperatures at a value of approximately 78 %, and irrespective of the exposure (Figure 22). This trend implies that the shapes of the stress-strain curves are self-similar (at least up to the densification strain) and could be reproduced, in an approximate sense, by scaling the ambient temperature stress-strain response by a temperature dependent scalar reduction factor.
535
Conversely, for the aluminum foam specimens, their small values of the hardening modulus at higher temperatures indicates that their behavior approaches an elastic perfectly plastic state, which contributed to their larger values of energy

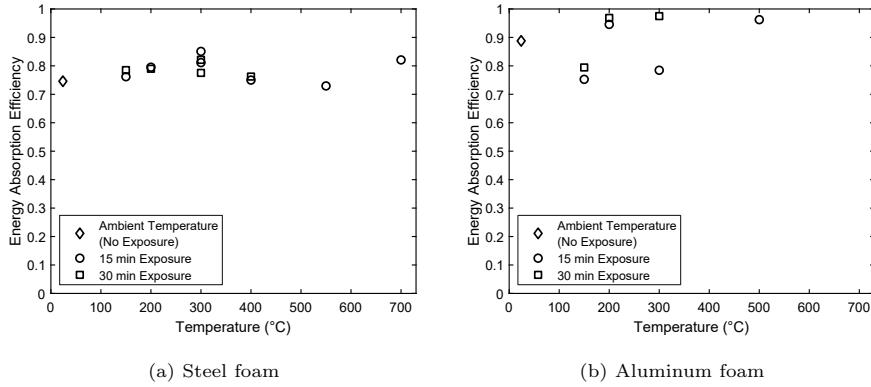


Figure 22: Energy absorption efficiency, calculated per ISO Standard 13314-2011 as the ratio of energy absorption capacity to the product of the maximum compressive stress (within the strain range spanning from 0.00 mm/mm to the densification strain).

absorption efficiency.

540 6. Discussion

The computational analyses revealed that the local capacity at the spherical shell length-scale, following initially elastic deformations, was controlled by the plastic buckling, mutual indentation, and bending of the spherical shells in contact. These contact regions are distributed randomly throughout the sample, resulting in localized plasticity. The deformation of the spheres is driven by bending of a spherical region, which increases radially as the material globally hardens. Random load paths complicate the development of closed-form multi-scale models linking local sphere geometry with the global macroscopic foam strength. Our computational observations compliment experimental studies by Gründer [38] and by Fallet et al. [39], which also used CT-images to investigate internal foam deformations. Fallet proposed using the Weibull distribution to estimate the expected number of contact regions as a function of the overall global strain. Further work is needed to enable analytical predictions of the macroscopic foam properties from the geometry of the hollow spheres and their base metal properties through the use of statistics and elasto-plastic analytical

modeling of the capacity of a spherical shell. Nevertheless, our simulations also indicated that the use of random variables for the sphere location and in the consideration of the packing pattern is necessary.

As expected from the fundamental buckling analysis of spherical shells, the thermal degradation of the metallic foams generally followed the temperature-induced reduction of yield stress of their respective base metals. Figure 23 compares the retention factors found in Eurocode ([30]) for the solid, bulk steel and aluminum to the thermal degradation rate of the metal foams. The data for the HS steel foam followed the trends of the base metal with reasonable consistency. Note that Eurocode does not specify a specific time of exposure, but only states that the heating rate stay between 2 °C/min to 50 °C/min. Thus, it refers to the continuous exposure to the given temperatures. The testing conducted in this study did not show a significant influence of thermal exposure time (15 min or 30 min) on the thermal-mechanical properties of either the HS steel or PM aluminum foams.

According to EN 1999-1-2 [46], the mechanical properties of solid aluminum degrade at much lower temperatures than those of solid steel. Taherishargh et al. [23] previously reported that the reduction in material properties of foams follow the trend of the solid material. The yield stress of solid aluminum decreases by about 20 % at 150 °C and about 90 % at 300 °C; the results for the PM aluminum foam followed a similar trend, but with even more significant reductions in strength (more than 50 % at 150 °C for some specimens, see Figure 23). The mechanical performance of the PM aluminum foam was essentially negligible at temperatures exceeding 300 °C. These findings about aluminum foam behavior at elevated temperatures (compressive strength, energy absorption capacity and elastic modulus) are consistent with previous studies of aluminum foams in the literature ([15], [17], [22]), and for the HS steel foams by [16].

Although manufacturing of steel foam is more expensive than aluminum foam due to increased energy costs deriving from the higher melting point of steel, the retained strength and stiffness of HS steel foam at a given elevated temperatures is clearly larger than that of the PM aluminum foam. The Iron (Fe)

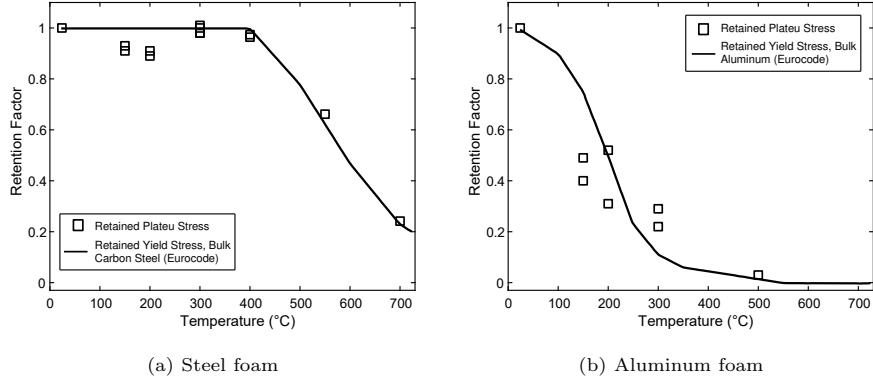


Figure 23: Comparison between retention factors for (a) HS steel foam with those for carbon steel in [30], and (b) PM aluminum foam with those for aluminum in [30].

based HS steel foam showed only minor degradation in mechanical performance at temperatures less than 400 °C, and retained 60 % of its compressive strength at 550 °C. Such resilience might allow steel foam components to perform their intended functions even under elevated temperatures, by largely retaining the safety factors embedded in typical designs.

The formation of a blue oxide surface skin during heating of HS steel foam specimens (see Figure 9) increased its stiffness within the temperature range of 200 °C and 300 °C. These findings are consistent with Bekoz et al. [16], who reported an increase in compressive yield strength and stiffness for PM steel foams for temperatures up to 400 °C, and a decrease above that temperature. Bekoz et al. [16] suggested an aging effect (dynamic age-hardening) as the reason for the increase in mechanical properties up to 400 °C but did not detect any enhancement in the compressive strength over the temperature range.

Considering the large surface areas of metallic foams, surface-oxidizing chemical reactions could have a significant positive influence on the thermal-mechanical performance of steel foams. For example, pre-oxidization of FeCrAl enhances its mechanical properties at temperatures up to 400 °C. The potential for such reactions to reliably increase thermo-mechanical performance should be also investigated for other base metals and alloys because these reactions could allow

metallic cellular structures to outperform their constituent base metals.

7. Summary and Conclusions

The compressive behavior of hollow sphere (HS) steel foam and powder metallurgy (PM) aluminum foams were studied at elevated temperatures to characterize their thermo-mechanical properties. The experimental results showed that the HS steel foam retained more than 89 % of its compressive strength, when measured by the plateau stress, up to 400 °C, and 69 % of its strength and energy absorption capacity at 550 °C. At 700 °C, much of the structural integrity of the HS steel foam was largely diminished, retaining only 24 % of its compressive strength and energy absorption capacity. Contrarily, the PM aluminum foam retained only about 45 % of its strength and energy absorption capacity at 150 °C, and had virtually no strength (only 3.5 %) remaining at 500 °C.

High-resolution computational models showed that, under increased deformation, plasticity spreads toward the equators of individual hollow spheres, gradually increasing the diameter of their plastic hinge hoops until buckling of the sphere-walls occurred. This observation was further supported by analytical consideration of buckling of a spherical shell. Thus, the local plasticity and plastic stress are critical for the thermal deterioration of metallic foams' mechanical capacities because they control local plastic buckling. As anticipated from the simulations, the retained plateau stress for both the HS steel and PM aluminum foams generally followed the elevated-temperature degradation of the yield stress of their respective base metals (available from Eurocode EN 1993-1-2:2005 and EN 1999-1-2:2007). However, based on the general buckling stability considerations, it might be possible to manufacture ultra-thin-walled foams, which should exhibit highly elastic, reversible deformations. Their thermal behavior would be expected to follow thermal deterioration of modulus of elasticity of the base material. This observation is consistent with previously reported hyper elastic behavior of ultra-thin-walled hollow lattice structures [42].

635 The experiments also revealed an interesting chemical phenomenon. A blue
oxide film formed on the surface of the steel foam. This film was likely responsible
for the moderate increases of quasi-elastic gradient between temperatures of
200 °C, 300 °C, higher stress-strain curves in the range of 300 °C to 400 °C then
100 °C as well as discrepancy between the simulated and experimental stress
640 strain curves of HS steel foam at higher temperatures. Chemical reactions that
occur at elevated temperatures will be considered in future studies because they
might allow metallic foams to exceed thermo-mechanical performance of their
base metals by taking advantage of the large surface area to volume ratio in
cellular structures.

645 The high thermal resilience of steel foams suggests that their potential range
of application might extend to temperatures traditionally precluded for poly-
meric or even aluminum foams. The energy absorption capacity of the HS steel
foam was nearly constant at the temperatures below 400 °C, and significant
residual energy absorption capacity (about 69 %) remained at 550 °C. In addition,
650 the energy absorption efficiency was essentially constant at about 80 % and
did not diminish at elevated temperatures. Thus, steel foams may be suitable for
dissipation of impacts, crashes or other extreme loads at elevated temperatures.
The crashworthiness could be combined with heat exchange functions in open
cell foams. This research is a part of broader effort to develop understanding of
655 cellular metallic materials with relevance to aerospace, automotive, energy and
infrastructure applications.

List of Acronyms

HS	Hollow Sphere
PM	Powder Metallurgy
ISO	International Organization for Standardization
IFAM	Fraunhofer Institute for Manufacturing Technology and Advanced Materials
MTS	Material Testing System
UTM	Universal Testing Machine
RCP	Random close-packed
RT	Room Temperature
SF	Steel Foam
AF	Aluminum Foam
METFOAM	International Conference on Porous Metals and Metallic Foams
EPSRC	Engineering and Physical Science Council

List of Symbols

α	Correction factor used for the measurement of the spherical pore size
λ	Slenderness
ν_{660}	Poisson ratio
ω_{apex}	Deformation of the sphere apex under uniform pressure
$\sigma_{failure}$	Failure stress
σ_{cr}	Critical limit of membrane stress
σ_{cr}^{shell}	Critical stress of the spherical shell
σ_d_{665}	Densification Stress that define the transition to stiffening behavior
σ_{pl}	Plateau Stress
$\sigma_p(T)$	Projection of densification stress at zero strain
σ_{shell}	Buckling Stress of Spherical Shell

	σ_y	Yield stress
670	σ_y^{shell}	Yield stress of the spherical shell
	ε	Compressive strain
	ε_d	Densification Strain that define the transition to stiffening behavior
	$\varepsilon_d(T)$	Densification stiffness
	ε_y	Yield strain calculated using the 0.2 % offset method
675	φ	Polar coordinate, where 0 corresponds to the equator and $\pi/2$ to the apex of the sphere
	d_c	Diameter of the contact area between the spheres
	E	Young Modulus
680	$E_b(T)$	Slope of the segment, which constraints Richard's equation fir at the densification point $(\varepsilon_d, \sigma_d)$, which is obtained by minimizing the square area between the fitted curve and the experimental data
	$E_d(T)$	Densification stiffness
	E_i	Initial elastic modulus
	$E_i(T)$	Initial elastic modulus at high temperature
685	E_p	Plastic hardening modulus
	$E_p(T)$	Plastic hardening modulus at high temperature
	f_y	Yield stress calculated using the 0.2 % offset strain method
	h_{proj}^i	Height of the random cut plane used for measurement of the spherical pore size
690	$n_b(T)$	Shape parameter that controls the sharpness of the transition from the plastic stiffness to the densification stiffness at high temperature, Figure 7

n_y	Shape parameter that controls the sharpness of the transition from the elastic stiffness to the plastic stiffness
695 $n_y(T)$	Shape parameter that controls the sharpness of the transition from the elastic stiffness to the plastic stiffness at high temperature
q_c	Pressure applied to a sphere
R	Sphere radius
r_{proj}^i	Projected Radius used for measuring the size of the spherical pore
700 r_{true}	True Radius of the spherical pore size
T	Temperature
t	Sphere Thickness
q	Applied pressure

Acknowledgments

705 The authors would like to express heartfelt gratitude to our academic colleagues for their feedback and fruitful discussions. We are grateful to Fraunhofer IWU in Chemnitz and Fraunhofer IFAM in Dresden for the ongoing collaboration, and for their help with supplying the metallic foam rectangular prisms for mechanical testing. We would like to thank Dr Rene Vogel, Dr Thomas Hipke, Dr Olaf Andersen, Dr Peter Quadbeck and Dr Christian Hannemann.

We also would like to express our gratitude to technicians who assisted us during the mechanical tests, namely Mr Peter Heynes and David Jesson. We are also indebted to LS-DYNA support and developers for their assistance with the implicit, large deformation and large-strain micro-model.

715 This study was funded by the Research Framework of the European Commission under METFOAM Career Integration Grant 631827 with support from program manager Dr. Ing. Antonio Cipollaro. The work was also supported

by the impact acceleration grant no EP/P511456/1, provided by the Engineering and Physical Science Council (EPSRC) in the UK. Support of Dr. Sue 720 Angulatta, a local program manager, is genuinely appreciated. Any opinions, findings, and conclusions expressed in this article are those of the author(s) and do not necessarily reflect the views of EPSRC or the European Commission.

Data availability

The data is available upon request from the corresponding author.

725 References

- [1] S. Mahjoob, V. Kambiz, A synthesis of fluid and thermal transport models for metal foam heat exchangers, International Journal of Heat and Mass Transfer 51 (2008) 3701–3711. doi:10.1016/j.ijheatmasstransfer. 2007.12.012.
- [2] P. Vadwala, Thermal energy storage in copper foams filled with paraffin wax. MSc Thesis, Mechanical and Industrial Engineering - University of Toronto, Toronto, Canada, 2011.
- [3] W. Yuan, Y. Tang, X. Yang, Z. Wan, Porous metal materials for polymer electrolyte membrane fuel cells - a review, Applied Energy 94 (2012) 309–329. doi:10.1016/j.apenergy.2012.01.073.
- [4] B. Smith, S. Szyniszewski, J. Hajjar, B. Schafer, S. Arwade, Steel foam for structures: a review of applications, manufacturing and material properties, Journal of Constructional Steel Research 71 (2012) 1–10. doi:10.1016/j.jcsr.2011.10.028.
- [5] J. Banhart, H. Seeliger, Aluminum foam sandwich panels: manufacture, metallurgy and applications, Advance Engineering Materials 10 (2008) 793–802. doi:10.1002/adem.200800091.

- [6] L. Gibson, M. Ashby, Cellular solids: structure and properties, 2nd Edition, Cambridge University Press, 1999.
- [7] M. Ashby, Metal foams: a design guide, 1st Edition, Butterworth Heinemann, 2000.
- [8] L. Lefebvre, J. Banhart, D. Dunand, Porous metals and metallic foams: current status and recent developments, *Advance Engineering Materials* 10 (2008) 775–787. doi:[10.1002/adem.200800241](https://doi.org/10.1002/adem.200800241).
- [9] V. Deshpande, N. Fleck, Isotropic constitutive models for metallic foams, *Journal of Mechanics and Physics of Solids* 48 (2000) 1253–1283. doi:[10.1016/S0022-5096\(99\)00082-4](https://doi.org/10.1016/S0022-5096(99)00082-4).
- [10] A. Reyes, O. Hopperstad, T. Berstad, A. Hanssen, M. Langseth, Constitutive modeling of aluminum foam including fracture and statistical variation of density, *European Journal of Mechanics - A/Solids* 22 (2003) 815–835. doi:[10.1016/j.euromechsol.2003.08.001](https://doi.org/10.1016/j.euromechsol.2003.08.001).
- [11] S. Szyniszewski, B. Smith, J. Hajjar, B. Schafer, S. Arwade, The mechanical properties and modeling of a sintered hollow sphere steel foam, *Materials and Design* 54 (2014) 1083–1094. doi:[10.1016/j.matdes.2013.08.045](https://doi.org/10.1016/j.matdes.2013.08.045).
- [12] J. Richeton, S. Ahzi, K. Vecchio, F. Jiang, R. Adharapurapu, Influence of temperature and strain rate on the mechanical behavior of three amorphous polymers: Characterization and modeling of the compressive yield stress, *International Journal of Solids and Structures* 43 (7-8) (2006) 2318–2335. doi:[10.1016/j.ijsolstr.2005.06.040](https://doi.org/10.1016/j.ijsolstr.2005.06.040).
- [13] Y. Zhang, W. Liu, C. Yin, Y. Ma, L. Wang, Mode II interfacial fracture characterization of foam core sandwich materials at elevated temperatures: the effects of frictional stresses between the crack edges, *International Journal of Solids and Structures* 193-194 (2020) 28–38. doi:[10.1016/j.ijsolstr.2020.02.001](https://doi.org/10.1016/j.ijsolstr.2020.02.001).

- 770 [14] J. Thomas, N. Triantafyllidis, Theory of necking localization in unconstrained electromagnetic expansion of thin sheets, International Journal of Solids and Structures 44 (21) (2007) 6744–6767. doi:10.1016/j.ijsolstr.2007.03.007.
- 775 [15] M. Aly, Behavior of closed cell aluminium foams upon compressive testing at elevated temperatures: Experimental results, Materials Letters 61 (2007) 3138–3141. doi:10.1016/j.matlet.2006.11.046.
- [16] N. Bekoz, E. Oktay, High temperature mechanical properties of low alloy steel foams produced by powder metallurgy, Materials and Design 53 (2014) 482–489. doi:10.1016/j.matdes.2013.07.050.
- 780 [17] J. Kováčik, L. Orovčík, J. Jerz, High-temperature compression of closed cell aluminium foams, Kovové Materiály 54 (2016) 429–440. doi:10.4149/km20166429.
- 785 [18] N. Movahedi, E. Linul, Quasi-static compressive behavior of the ex-situ aluminum-alloy foam-filled tubes under elevated temperatures, Materials Letters 206 (2017) 182–184. doi:10.1016/j.matlet.2017.07.018.
- [19] E. Linul, N. Movahedi, L. Marsavina, The temperature effect on the axial quasi-static compressive behavior of ex-situ aluminum foam-filled tubes, Composite Structures 180 (2017) 709–722. doi:10.1016/j.compstruct.2017.08.034.
- 790 [20] D. Mondal, N. Jha, A. Badkul, S. Das, R. Khedle, High temperature compressive deformation behaviour of aluminum syntactic foam, Materials Science and Engineering A 534 (2012) 521–529. doi:10.1016/j.msea.2011.12.002.
- 795 [21] N. Bekoz, E. Oktay, High temperature mechanical properties of low alloy steel foams produced by powder metallurgy, Materials and Design 53 (2014) 482–489. doi:10.1016/j.matdes.2013.07.050.

- [22] J. Liu, Q. Qu, Y. Liu, R. Li, B. Liu, Compressive properties of al-si-sic composite foams at elevated temperatures, *Journal of Alloys and Compounds* 676 (2016) 239–244. doi:10.1016/j.jallcom.2016.03.076.
- 800 [23] M. Taherishargh, E. Linul, S. Broxtermann, T. Fiedler, The mechanical properties of expanded perlite-aluminium syntactic foam at elevated temperatures, *Journal of Alloys and Compounds* 737 (2018) 590–596. doi:10.1016/j.jallcom.2017.12.083.
- 805 [24] E. Linul, D. Lell, N. Movahedi, C. Codrean, T. Fiedler, Compressive properties of zinc syntactic foams at elevated temperatures, *Composites Part B* 167 (2019) 122–134. doi:10.1016/j.compositesb.2018.12.019.
- [25] J. Hallquist, LS-DYNA theory manual, Lawrence Software Technology Corporation, Livermore, California, 2006.
- 810 [26] Technical Committee ISO/TC 164. Compression test for porous and cellular metals – ISO 13314:2011.
- [27] M. Cobb, World Wide Guide to Equivalent Irons and Steels, 2nd Edition, ASM International, 1987.
- 815 [28] B. Smith, Material characterization and computational simulation of steel foam for use in structural applications. MSc Thesis, University of Massachusetts Amherst, Amherst, Massachusetts, U.S.A., 2012.
- [29] A. Avallone, T. Baumeister, A. Sadegh, Mark's Standard Handbook for Mechanical Engineers, 11th Edition, McGraw-Hill, 2007.
- [30] European Committee for Standardization. Eurocode 3: Design of Steel Structures, Part 1-2: General Rules - Structural Fire Design – EN 1993-1-2:2005.
- 820 [31] M. Xiong, J. Liew, Mechanical properties of heat-treated high tensile structural steel at elevated temperatures, *Thin-Walled Structures* 98 (2016) 169–176. doi:10.1016/j.tws.2015.04.010.

- [32] Z. Gao, X. Yu, H. Zhao, Mechanical behavior of metallic hollow sphere materials: experimental study, *J. Aerospace Eng.* 21 (2008) 206–216. doi: 10.1016/(ASCE)0893-1321(2008)21:4(206).
- [33] A. Wouterse, A. Philipse, Geometrical cluster ensemble analysis of random sphere packings, *J. Chem. Phys.* 125 (2006) 194709–194719. doi:10.1063/1.2390700.
- [34] A. Kansal, S. Torquato, F. Stillinger, Computer generation of dense poly-disperse sphere packings, *J. Chem. Phys.* 117 (2002) 8212–8218. doi: 10.1063/1.1511510.
- [35] R. Williams, A. Philipse, Random packings of spheres and spherocylinders simulated by mechanical contraction, *Physical Review E* 67 (2003) 1–9. doi:10.1103/PhysRevE.67.051301.
- [36] B. H. Smith, S. Szyniszewski, J. F. Hajjar, B. W. Schafer, S. R. Arwade, Characterization of Steel Foams for Structural Components, *Metals* 2 (4) (2012) 399–410, number: 4 Publisher: Multidisciplinary Digital Publishing Institute. doi:10.3390/met2040399.
- [37] F. Cverna, Worldwide Guide to Equivalent Irons and Steels, ASM International, 2006, google-Books-ID: SpcF9IrYKR0C.
- [38] J. Gründer, G. Landgraf, O. Andersen, P. Löthman, Modeling and simulation of the meso- and macro-mechanical properties of hollow sphere structures, *Cellular Metals and Metal Foaming Technology* (ed. J. Banhart, M.F. Ashby, N.A. Fleck). Verlag MIT Publ., Bremen (2001) 6.
- [39] A. Fallet, P. Lhuissier, Y. Bréchet, Mechanical behaviour of metallic hollow spheres foam, *Advanced Engineering Materials* 10 (2008) 858–862. doi: 10.1002/adem.200800094.
- [40] S. Timoschenko, J. Gere, *Theory of Elastic Stability*, 2nd Edition, Dover Publications, Inc., 2009.

- 850 [41] G. Winter, Strength of thin steel compression flanges, Transactions of ASCE 2035 (1947).
- [42] T. Schaedler, A. Jacobsen, A. Torrents, A. Sorensen, J. Lian, J. Greer, L. Valdevit, W. Carter, Ultralight metallic microlattices, Science 334 (2011) 962–965. doi:10.1126/science.1211649.
- 855 [43] J. Weigand, R. Peixoto, L. Vieira, J. Main, M. Seif, An empirical component-based model for shear behavior of high-strength bolts at elevated temperatures, Journal of Constructional Steel Research 147 (2018) 87–102. doi:10.1016/j.jcsr.2018.03.034.
- 860 [44] M. Richard, J. Abbot, Versatile elastic-plastic stress-strain formulation, Journal of the Engineering Mechanics 101 (1975) 511–515.
- [45] MathWorks, MATLAB Global Optimization Toolbox User's Guide, Version 3.4.1 (R2016b), The MathWorks, Inc., Natick, Massachusetts, United States, 2016.
- 865 [46] European Committee for Standardization. Eurocode 9: Design of Aluminum Structures, Part 1-2: Structural Fire Design – EN 1999-1-2:2007.

Appendix

Fitted Richard Equation Parameters

The Richard Equation parameter values fitted only to elastic phase of each specimen's stress-strain response are presented in Table 3, and the Richard Equation parameter values fitted to each specimen's full stress-strain curve are presented in Table 4.

Table 3: Richard Equation Parameters fitted only to Elastic Phase of Specimen Stress-Strain Curve.

Spec.	$E_i(T)$	$E_p(T)$	$\sigma_y(T)$	$n_y(T)$	$E_b(T)$	$E_d(T)$	$\sigma_p(T)$	$n_d(T)$	$(\varepsilon_d, \sigma_d)$
SF_T24C	611	76.9	4.4	10.01	-	-	-	-	-
SF_T150C_15	979	166.8	2.8	5.59	-	-	-	-	-
SF_T150C_30	916	156.5	3.4	7.71	-	-	-	-	-
SF_T200C_15	1487	3.7	4	2.39	-	-	-	-	-
SF_T200C_30	1351	84.8	4.5	4.98	-	-	-	-	-
SF_T300C_15(1)	1770	381	2	2.79	-	-	-	-	-
SF_T300C_15(2)	745	246.1	2.8	5.9	-	-	-	-	-
SF_T300C_30(1)	1084	238	2.5	3	-	-	-	-	-
SF_T300C_30(2)	730	183.1	3.3	6.19	-	-	-	-	-
SF_T400C_15	613	157.4	3	7.6	-	-	-	-	-
SF_T400C_30	670	58.9	4.4	3.43	-	-	-	-	-
SF_T550C_15	1017	78.8	3.4	2.6	-	-	-	-	-
SF_T700C_15	734	35.9	1.3	2.3	-	-	-	-	-
AF_24C	2514	327.2	15.2	2.62	-	-	-	-	-
AF_T150C_15	625	205.9	3.6	9.12	-	-	-	-	-
AF_T150C_30	1397	204.1	6.9	3.88	-	-	-	-	-
AF_T200C_15	840	166.9	5.5	6.21	-	-	-	-	-
AF_T200C_30	1602	347.4	7.7	4.81	-	-	-	-	-
AF_T300C_15	1437	85.6	5.1	3.5	-	-	-	-	-
AF_T300C_30	1820	48	6.2	2.2	-	-	-	-	-
AF_T500C_15	86	2.2	0.8	9.54	-	-	-	-	-

Table 4: Richard Equation Parameters fitted to Specimen Full Stress-Strain Curve.

Spec.	$E_i(T)$	$E_p(T)$	$\sigma_y(T)$	$n_y(T)$	$E_b(T)$	$E_d(T)$	$\sigma_p(T)$	$n_d(T)$	$(\varepsilon_d, \sigma_d)$
SF_T24C	15697	11.1	11.8	0.35	0.44	18.7	84.6	13.1	9.36
SF_T150C_15	12219	8.5	11.5	0.35	0.43	13.7	54	9.3	3.98
SF_T150C_30	22337	8.1	11.2	0.35	0.4	13.6	50.9	8.2	8.32
SF_T200C_15	15550	6.9	11.8	0.34	0.38	12.3	44.1	6.8	9.14
SF_T200C_30	3841	9.5	8.4	0.6	0.39	16.5	64.8	10.8	15.15
SF_T300C_15(1)	3322	8.1	10.2	0.6	0.38	15.9	43.9	11.7	100.28
SF_T300C_15(2)	1146	5.7	9.8	0.99	0.37	15.9	66.8	12.1	107.82
SF_T300C_30(1)	14081	8.4	13.3	0.35	0.4	17.1	63.3	9.6	20.33
SF_T300C_30(2)	3798	6.6	10.5	0.56	0.38	16.7	66.4	10.9	38.01
SF_T400C_15	2554	18.2	6.3	0.84	0.27	15.1	51.8	12.3	6.61
SF_T400C_30	1252	17.6	6.5	1.17	0.26	14	45.5	9.7	12.37
SF_T550C_15	1191	11.6	4.4	1.83	0.44	25	101.9	8.5	5.5
SF_T700C_15	649	3.5	1.8	1.63	0.26	2.9	12.3	3.1	8.03
AF_24C	2565	11.2	26.1	1.44	0.4	37.2	199.6	29.6	5.77
AF_T150C_15	1195	20	6.7	1.58	0.26	9.2	62.7	13.6	3.81
AF_T150C_30	1393	20.1	9.2	3.65	0.26	39.8	75.8	10	39.83
AF_T200C_15	961	1.4	8.5	3.39	0.43	2.9	43.8	11.3	0.79
AF_T200C_30	1694	3.6	13.7	2.4	0.3	3.6	67.6	15.9	20.5
AF_T300C_15	1666	12.1	5.3	3.93	0.26	5.5	45.9	10.6	4.18
AF_T300C_30	2165	0.9	6	2.68	0.38	3.7	59.4	11.8	1.86
AF_T500C_15	3774	0.2	1	0.78	0.28	0.7	6.8	2.2	1.3