Supporting Information

Publication-Level Holdout Separates Fingerprint and Excited-State Descriptor Models of Measured TADF Gaps

Jean-Pierre Tchapet Njafa,[a]* Steve Cabrel Teguia Kouam,[b] Patrick Sorrel Mvoto Kongo,[a] Panebei Samafou,[c] and Serge Guy Nana Engo[a]

[a]Department of Physics, Faculty of Science, University of Yaoundé 1, Yaoundé 812, Cameroon.
[b]Department of Physics, Faculty of Science, University of Douala, Douala 24157, Cameroon.
[c]Department of Medical Imaging and Radiation Sciences, Faculty of Medicine and Health Sciences, Université de Sherbrooke, 3001, 12th Avenue Nord, Sherbrooke, QC J1H 5N4, Canada.

*E-mail: jean-pierre.tchapet@facsciences-uy1.cm; ORCID: https://orcid.org/0000-0002-1936-8353

S1. Computational details

S1.1 Semi-empirical calculations

Ground-state geometries were optimised with GFN2-xTB [1] (`xtb` 6.7.1, default convergence: $1 \times 10^{-6}\,E_\mathrm{h}$ SCF). Lowest singlet and triplet excitations were obtained with sTDA [2]. These semi-empirical excited states are used only to derive the natural transition orbital (NTO) descriptors of table S1; they are not used as a prediction target (the semi-empirical gap is circular with respect to such features; see main text).

S1.2 DFT reference calculations

Functional-dependence benchmarks (table S12) used B3LYP/6-31G(d) and CAM-B3LYP/def2-TZVP (ORCA 6.1.1 [3]), in gas phase and toluene (CPCM).

S2. Natural transition orbital descriptors

NTOs [4] were obtained by singular-value decomposition of the transition density matrix; the dominant hole–electron pair ($\lambda_\mathrm{NTO} > 0.9$) defines the spatial descriptors. The 35 NTO descriptors—which require the sTDA excited-state calculation but exclude the S_1/T_1 energy scalars—are enumerated in table S1. For each of the lowest singlet (S_1) and triplet (T_1) states we computed the hole–electron spatial overlap S_he, the charge-transfer number CT, the donor/acceptor NTO weights λ_D/λ_A, the hole–electron separation Δr, and the localisation indices (hole-on-acceptor, particle-on-donor). State differences ($\Delta X = X_{S_1} - X_{T_1}$) and their magnitudes $|\Delta X|$ were added because the S_1–T_1 exchange splitting depends on how the spatial distributions *change* between states. The oscillator strength f_{S_1} and the log-transformed absorption proxies are the only intensity-related quantities; no energy scalar enters the feature set.

Table S1: The 35 NTO spatial descriptors used as the structure-derived feature set. X_{S_1} and X_{T_1} denote the quantity evaluated in the singlet and triplet state; $\Delta X = X_{S_1} - X_{T_1}$. Energy scalars ($E_{S_1}$, E_{T_1}, and the gap) are deliberately excluded.

Family	Descriptors
Hole–electron overlap (5)	$S_\mathrm{he}(S_1)$, $S_\mathrm{he}(T_1)$, ΔS_he, $\lvert\Delta S_\mathrm{he}\rvert$, $\mathrm{Char}^2_\mathrm{diff}$
Charge-transfer number (4)	$\mathrm{CT}(S_1)$, $\mathrm{CT}(T_1)$, $\Delta\mathrm{CT}$, $\lvert\Delta\mathrm{CT}\rvert$
Donor weight (4)	$\lambda_D(S_1)$, $\lambda_D(T_1)$, $\Delta\lambda_D$, $\lvert\Delta\lambda_D\rvert$
Acceptor weight (4)	$\lambda_A(S_1)$, $\lambda_A(T_1)$, $\Delta\lambda_A$, $\lvert\Delta\lambda_A\rvert$
CT separation (4)	$\Delta r(S_1)$, $\Delta r(T_1)$, $\Delta(\Delta r)$, $\lvert\Delta(\Delta r)\rvert$
Localisation (4)	hole-on-A(S_1), particle-on-D(S_1), hole-on-A(T_1), particle-on-D(T_1)
NTO overlap composites (7)	$S^\mathrm{sum}_\mathrm{NTO}$, $S^\mathrm{prod}_\mathrm{NTO}$, $S^\mathrm{ratio}_\mathrm{NTO}$, ΔS_NTO, $\lvert\Delta S_\mathrm{NTO}\rvert$, NTO overlap($S_1$), NTO overlap($T_1$)
Intensity proxies (3)	f_{S_1}, $\log\lvert A_{S_1}\rvert$, $\log\lvert A_{T_1}\rvert$

S3. Machine learning details

S3.1 Target and dataset

The target is the experimental ΔE_ST, extracted from the literature and matched by compound name; multiple reports were reduced to the median. The benchmark contains 231 molecules spanning 212 Bemis–Murcko scaffolds [5]; 92.9 % of scaffolds are singletons, so a scaffold split is numerically close to a random split and the source-paper (DOI-grouped) split probes a different source-publication axis. It does not identify laboratories or control the measurement protocol.

The corpus was assembled by a name-based join, which is a fragile step; we therefore state the rule and its accounting in full (table S2). Starting from 1 520 extracted literature rows, we kept rows whose property specifier contained "EST" (1 490), parsed the reported value (all 1 490 parsed), and retained values in the physical range −0.3 eV to 1.5 eV (all 1 490). Each row's compound-name list was exploded and matched by exact string equality to the identifiers of molecules for which we had computed NTO descriptors, giving 363 name–value matches over 231 unique molecules.

Of these, 102 molecules carried more than one literature report; we collapsed each to its median. The inter-report spread (standard deviation across reports for a given molecule) had a median of 0 eV but reached 0.564 eV in the worst case. This is evidence of substantial inter-report variation for some molecules, not a global lower bound on MAE. Every matched molecule had an RDKit-parseable SMILES (zero dropped), yielding the final set of 231 molecules over 212 scaffolds. The script `code/si_supplementary_data.py` regenerates this table.

Table S2: Provenance of the experimental ΔE_{ST} corpus: rows retained or dropped at each stage of the name-based join.

Stage	Count
Extracted literature rows	1520
Specifier contains "EST"	1490
Value parsed and finite	1490
Value in physical range −0.3 eV to 1.5 eV	1490
Name–value matches to descriptor set	363
Unique molecules matched	231
of which with > 1 report	102
Dropped: no RDKit-parseable SMILES	0
Final benchmark molecules	**231**
Final Bemis–Murcko scaffolds	**212**

The corpus records no measurement medium: the solvent and atmosphere fields are empty for all 1 490 EST rows, so the target cannot be stratified by solvent. The label heterogeneity is instead quantified directly from the spread among independent reports of the same molecule—consistent with uncontrolled solvent, host and method effects on experimental ΔE_{ST} [6] (table S3); the corpus cannot separate conditions, protocol and transcription error. Across the 102 molecules with repeat reports, the inter-report range exceeds the model MAE (0.096 eV) for 19.6 % of molecules, and a single randomly chosen report sits 0.072 eV (RMS) from its molecule's median, while the median label of these 102 molecules carries an RMS standard error of 0.049 eV; counting the 129 single-report labels at single-report scatter, label noise over all 231 molecules is about 0.072 eV RMS. Label imprecision is thus a material term in the error budget without accounting for all of it; we do not claim it sets a floor the model has reached. Regenerated by `code/solvent_analysis.py`.

Table S3: Label heterogeneity of the experimental target, measured from within-molecule disagreement among independent literature reports (102 molecules with > 1 report). Range is max−min; SD is the standard deviation across a molecule's reports (the latter matches table S2).

Quantity (eV unless noted)	Value
Molecules with > 1 report	102
Inter-report range: mean / median	0.062 / 0.000
Inter-report range: 90th pct. / max	0.17 / 1.09
Fraction with range > model MAE	19.6 %
Inter-report SD: mean / max	0.036 / 0.564
Single report vs median (RMS)	0.072
Model MAE (reference)	0.096

S3.1b Feature–target leakage, quantified

Regressing the computed gap $E_{S_1} - E_{T_1}$ on features that contain its two constituents recovers arithmetic rather than structure–property information. We quantified this on the same Bemis–Murcko scaffold `GroupKFold`($k = 5$) used throughout: the target is the sTDA computed gap, and the features are the 35 NTO spatial descriptors with and without the S_1/T_1 energy scalars (table S4). A linear model supplied with the energies recovers the target to floating-point precision. How large the leak appears depends on whether the learner can express a difference of two continuous inputs: a random forest is axis-aligned and cannot, so it reports a far milder R^2 on identical leaked features. Regenerated by `code/a007_leakage_and_nested_cv.py` → `results/a007_leakage_nested_cv.json`. A feature that is an exact proxy for the target is a long-recognised cause of over-optimistic ML results [7, 8, 9]; table S4 is the controlled measurement for this case. Without the energies a linear model reaches $R^2 = 0.36$; with them it recovers the gap exactly. A random forest reaches only $R^2 = 0.59$ on the identical leaked features (a joint effect of its axis-aligned splits, tree depth and the 231-molecule sample). That score does not look anomalous, which is how a tree-based study can carry the defect through cross-validation unremarked. The main-text benchmark therefore uses the measured gap, and the NTO set excludes the two energy scalars. The risk is not particular to TADF: a target that is an algebraic combination of features already in the descriptor set is reproduced by arithmetic, and how visible the leak is under cross-validation depends on the learner. Where reported ML results target a computed gap, the check is to benchmark against the measured quantity with features that exclude the constituent energies.

Table S4: Cross-validated recovery of the computed gap $E_{S_1} - E_{T_1}$, with and without its constituent energies among the features ($n = 231$, scaffold `GroupKFold`, seed 0).

	with S_1/T_1 energies		energies excluded	
Learner	MAE (eV)	R^2	MAE (eV)	R^2
Linear regression	0.000	1.000	0.104	0.36
Ridge	0.018	0.981	0.102	0.38
Random forest	0.081	0.587	0.089	0.52
SVR	0.095	0.411	0.110	0.26

S3.2 Models and evaluation

Model. Random forests [10] (400 trees, scikit-learn [11]) were compared against ridge regression, support-vector regression, gradient boosting, a multilayer perceptron and a mean-value baseline; the random forest was best on every feature set. The forest used 400 estimators with no depth cap, all features considered at each split (scikit-learn default, `max_features` = 1.0), and a fixed seed. Leaving hyperparameters untuned does not by itself remove selection bias, because the *estimator* was chosen using the same folds on which performance is reported. We therefore repeated the comparison under nested cross-validation, selecting the learner inside each training fold and scoring it on the untouched outer fold: the random forest is selected in 5/5 outer folds and the nested MAE equals the reported value to five decimal places (0.09563 eV), so the selection optimism is 0 eV (`code/a007_leakage_and_nested_cv.py`).

Cross-validation. Performance is reported under Bemis–Murcko scaffold `GroupKFold` ($k = 5$): each fold holds out whole scaffolds, so no scaffold appears in both training and test, which removes the optimistic leakage of a random split on a set where 212 scaffolds cover 231 molecules.

Intervals and importance. 95 % confidence intervals come from 2 000 bootstrap resamples of the pooled out-of-fold predictions (table S5). Feature importance used exact TreeSHAP [12].

Paper-grouped ranking sensitivity. The original DOI-grouped `GroupKFold` produces Spearman $\rho = 0.155$ (Morgan) and 0.346 (NTO) over 231 molecules in 173 primary DOI groups. Paired resampling of molecules gives $\Delta\rho = 0.191$ with a 95 % interval 0.037 to 0.344. Paired resampling of whole DOI groups instead gives 0.014 to 0.366 (5 000 draws; out-of-fold predictions held fixed). Under 20 additional randomly partitioned paper-group holdouts with both forests retrained each time, NTO has higher test-set ρ in 19, with $\Delta\rho$ ranging from −0.014 to 0.404. These partitions overlap and do not establish transfer to an external laboratory. The fixed-split $\Delta\rho = 0.191$ is the value for one fold assignment; the median over 50 random assignments is 0.160 (table S7, main text Results, holdout-unit subsection). The machine-readable modelling inputs, source code and per-partition results accompany this SI as supplementary files.

Table S6 collects all accuracy and association metrics for the headline NTO model with their 95 % bootstrap confidence intervals, together with the power analysis for the rank-correlation test. Both Spearman ρ and Pearson r exclude zero, while the R^2 interval does not; the test for $\rho = 0.36$ is fully powered at $n = 231$ (only $n \approx 60$ is required for 80 % power), so the wide R^2 interval is a property of the variance-explained statistic under outlier influence rather than a sample-size limitation. Values regenerated by `code/r2_ci_power_analysis.py`.

A scaffold-CV learning curve (fig. S1) tests whether the 231-molecule set is simply too small. The cross-validated MAE shows no systematic decrease beyond $n \approx 90$: it varies by 5 % across $n = 46$–231, within the fold-to-fold standard deviation (≈ 0.013 eV), while the training MAE stays near 0.035 eV. The persistent train–CV gap that does *not* close with more data shows the model is not merely undersampled. The curve is not formally a plateau (`results/learning_curve.json` records `"plateau": false`) and the training sizes run only to $n = 184$; within this data regime, additional molecules of the same provenance did not lower the error. We do not read the gap as identifying an irreducible label-noise floor, since a train–CV gap is equally consistent with misspecification. Regenerated by `code/learning_curve_analysis.py`.

S3.3a Holdout-unit controls and the paper-multiplicity test

Table S7 gives the full holdout-unit comparison (50 random assignments of groups to five folds per unit, random forests with 400 trees). Ranges are the 2.5th to

Table S5: Prediction of experimental ΔE_{ST} (random forest, scaffold cross-validation, 231 molecules); R^2 with 95 % bootstrap CI. The 2D-structure-only sets (no quantum chemistry) match the NTO set (which needs an sTDA run); structure-only R^2 intervals include zero.

Feature set	MAE (eV)	R^2 (95 % CI)	ρ
Morgan FP (2D structure only)	0.091	0.27 (−0.19, 0.53)	0.31
RDKit desc. (2D structure only)	0.100	0.31 (−0.11, 0.51)	0.26
NTO spatial (needs sTDA)	0.096	0.25 (0.03, 0.45)	0.36
Energies + NTO (reference)	0.097	0.24	0.34
Mean-value baseline	0.107	0.00	—
Raw sTDA gap	0.251	−2.22	0.24

Table S6: Headline NTO random-forest model: accuracy and association metrics with 95 % percentile-bootstrap CIs (5 000 resamples of the out-of-fold predictions, 231 molecules), and a Fisher-z power analysis for the correlation test (two-sided, $\alpha = 0.05$).

Metric	Point estimate	95 % CI
MAE (eV)	0.096	(0.082, 0.109)
R^2	0.25	(0.03, 0.45)
Spearman ρ	0.36	(0.24, 0.47)
Pearson r	0.50	(0.26, 0.68)
Power analysis (correlation test, $\rho = 0.36$)		
Spearman ρ p-value	2.6×10^{-8}	
Achieved power at $n = 231$	≈ 1.0	
n for 80 % power	60	
n for 90 % power	79	

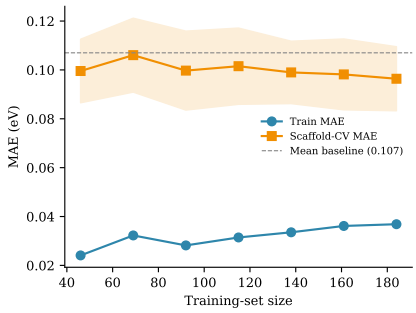


Figure S1: Scaffold cross-validation learning curve for the headline NTO random forest. Shaded band: ±1 fold standard deviation of the CV-MAE. The CV-MAE is flat beyond $n \approx 90$ and remains above the mean-value baseline gap, showing the error does not fall with more data of the same provenance.

97.5th percentiles over assignments and describe fold-assignment variability, not confidence intervals. On the fixed scaffold split, $\Delta\rho = 0.051$ with a scaffold-cluster 95 % interval of −0.099 to 0.202; 25.7 % of the 5 000 draws are ≤ 0, so the contrast under scaffold holdout is not resolved on that split. Table S8 gives the paper-multiplicity results (103 molecules from multi-molecule papers, 128 from single-molecule papers; same 50 assignments, molecule versus paper holdout). The reading is an association: structural near-duplication and laboratory protocol are both shared within a paper and are not separable here.

S3.3b Assumptions behind the noise ceiling

The ceiling $R^2_{max} = 1 - \overline{\sigma^2_{noise}}/\sigma^2_y$ ($\sigma_y = 0.1666$ eV from the labels) rests on five assumptions. (i) The noise is additive and independent of structure. (ii) Reports are independent; 57.8 % of multi-report molecules have zero spread, which may indicate re-citation, and that would make their standard error too small and R^2_{max} too high. (iii) The multi-report term uses SD/$\sqrt{n}$, the standard error of a mean; the standard error of the median is larger, so this term is a lower bound on the noise. (iv) The σ_y is computed from the labels, not from the prediction file; the difference is 0.0004 eV and does not change a reported digit. (v) The bootstrap interval resamples molecules and does not propagate uncertainty in the noise estimate itself. Under the three single-report noise choices the ceiling is 0.81 (pooled within-molecule SD 0.0856 eV, primary; 0.68 to 0.88), 0.80 (0.0905 eV; 0.65 to 0.87) and 0.86 (0.072 eV; 0.75 to 0.91), so the model ($R^2 \approx 0.26$) captures about 30 % to 32 % of it.

S3.3 Per-feature SHAP attributions

Table S9 lists the mean absolute TreeSHAP value of every NTO descriptor for the random forest trained on the 231-molecule set. Attribution concentrates on a

Table S7: Holdout-unit controls (medians over 50 assignments). ΔMAE is Morgan minus NTO. Ranges: 2.5th–97.5th percentile over assignments.

Holdout unit	$\Delta\rho$ (range)	$\Delta\rho > 0$	ρ Morgan	ρ NTO	ΔMAE, eV (range)	NTO higher /20
Source paper	0.160 (0.073, 0.246)	50/50	0.172	0.337	−0.0004 (−0.0061, 0.0068)	19
Scaffold	0.073 (0.007, 0.144)	49/50	0.269	0.351	−0.0045 (−0.0091, 0.0010)	11
Molecule	0.055 (−0.033, 0.126)	45/50	0.305	0.352	−0.0081 (−0.0157, −0.0002)	13

Table S8: Paper-multiplicity test (medians over 50 assignments). Sibling pull is the Spearman correlation between the out-of-fold prediction and the leave-self-out mean label of the same-paper molecules (103 molecules). Last columns: random minus paper holdout, median (2.5th–97.5th percentile).

Model	Quantity	Random	Paper	Random − paper	Range
Morgan	ρ, multi-paper (103)	0.538	0.264	0.269	0.174, 0.413
Morgan	ρ, single-paper (128)	0.097	0.099	−0.003	−0.121, 0.139
Morgan	sibling pull	0.676	0.255	0.415	0.276, 0.606
Morgan	MAE, multi-paper (eV)			−0.025	−0.034, −0.014
NTO	ρ, multi-paper (103)	0.483	0.446	0.040	−0.026, 0.111
NTO	ρ, single-paper (128)	0.243	0.245	−0.015	−0.101, 0.084
NTO	sibling pull	0.471	0.418	0.048	−0.014, 0.138
NTO	MAE, multi-paper (eV)			−0.007	−0.013, 0.001

handful of descriptors: the singlet hole–electron overlap $S_{\mathrm{he}}(S_1)$ alone accounts for 29 % of the total attribution, and the top five descriptors ($S_{\mathrm{he}}(S_1)$, $S_{\mathrm{NTO}}^{\mathrm{ratio}}$, f_{S_1}, $\Delta r(S_1)$, $S_{\mathrm{he}}(T_1)$) for 60 %. The 12 lowest-ranked descriptors together contribute under 3 %; the two raw NTO-overlap and the squared-character features are effectively unused. This is consistent with the main-text finding that the gap is governed by a small number of donor–acceptor overlap quantities rather than by the full 35-dimensional descriptor vector.

The interpretive value of the physics-informed descriptors is visible when their attribution is placed beside that of the equally accurate Morgan-fingerprint model (fig. S2). The ten highest-attribution NTO descriptors carry 79 % of the total and are all named physical quantities; the ten highest-attribution Morgan bits carry only 30 %, spread over 2 048 anonymous hashed substructure bits that resist mechanistic reading. Equal predictive accuracy thus buys interpretability only in the NTO representation. Regenerated by `code/shap_morgan_vs_nto.py`.

Table S9: Per-feature importance (mean |SHAP|, in meV) of the 35 NTO descriptors for the random forest on the 231-molecule experimental set, ranked high to low. Regenerated by `code/si_supplementary_data.py`.

Descriptor	meV	Descriptor	meV
$S_{\mathrm{he}}(S_1)$	36.9	|ΔCT|	1.6
$S_{\mathrm{NTO}}^{\mathrm{ratio}}$	14.5	hole-on-A(T_1)	1.5
f_{S_1}	11.5	$\Delta r(T_1)$	1.5
$\Delta r(S_1)$	7.9	CT(S_1)	1.4
$S_{\mathrm{he}}(T_1)$	6.9	$\lvert\Delta\lambda_A\rvert$	1.3
$\log\lvert A_{T_1}\rvert$	6.9	ΔCT	1.2
$\Delta(\Delta r)$	4.8	particle-on-D(S_1)	0.7
ΔS_{he}	4.3	$\lambda_D(S_1)$	0.7
$\lvert\Delta(\Delta r)\rvert$	4.1	particle-on-D(T_1)	0.6
$\lvert\Delta S_{\mathrm{he}}\rvert$	4.0	$\lambda_A(T_1)$	0.6
$\lvert\Delta\lambda_D\rvert$	3.1	$\lambda_A(S_1)$	0.5
$\log\lvert A_{S_1}\rvert$	3.0	hole-on-A(S_1)	0.5
$\Delta\lambda_D$	2.6	ΔS_{NTO}	0.1
$\Delta\lambda_A$	2.0	$S_{\mathrm{NTO}}^{\mathrm{sum}}$	0.1
$\lambda_D(T_1)$	2.0	NTO overlap(T_1)	0.1
CT(T_1)	1.7	NTO overlap(S_1)	0.0
		$\lvert\Delta S_{\mathrm{NTO}}\rvert$	0.0
		$S_{\mathrm{NTO}}^{\mathrm{prod}}$	0.0
		$\mathrm{Char}_{\mathrm{diff}}^2$	0.0

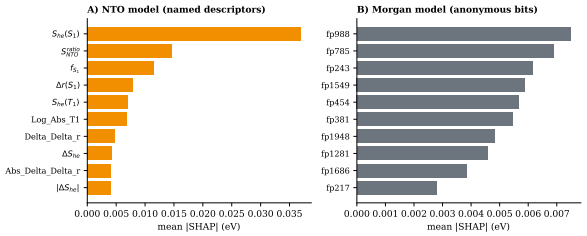


Figure S2: Top-ten SHAP attributions for the two equally accurate models. (A) NTO random forest: attribution concentrates on named donor–acceptor overlap and charge-transfer descriptors. (B) Morgan random forest: attribution is diffuse across anonymous fingerprint bits (`fp`*n*), which carry no direct chemical meaning.

To test whether this attribution pattern is a stable signal rather than an artefact of one particular fit, we refit the random forest on 200 bootstrap resamples of the 231-molecule set and recorded the top-five descriptors of each (table S10). The leading descriptor $S_{\mathrm{he}}(S_1)$ appears in the top five of 99.5 % of resamples; on average 3.7 of the five canonical descriptors recur per resample, and 64.5 % of resamples recover at least four of the five. The attribution is therefore reproducible at the top of the ranking, even though the model's ranking power on the gap itself is modest; we accordingly read these attributions as mechanistic hypotheses for experimental test, not validated causal claims. Regenerated by `code/shap_bootstrap_stability.py`.

Table S10: Bootstrap stability of the top-five SHAP descriptors: fraction of 200 resampled-and-refit models in which each canonical descriptor remains in the top five.

Descriptor	Top-5 frequency
$S_{\mathrm{he}}(S_1)$	99.5 %
$S_{\mathrm{NTO}}^{\mathrm{ratio}}$	74.0 %
f_{S_1}	72.0 %
$\Delta r(S_1)$	68.0 %
$S_{\mathrm{he}}(T_1)$	59.5 %
Mean top-5 overlap	3.7 / 5
Resamples recovering ≥ 4	64.5 %

S3.4 Scaffold-split characterisation

Because 212 Bemis–Murcko scaffolds cover 231 molecules, 92.9 % of scaffolds are singletons. Scaffold `GroupKFold` still differs from a random split in the way that matters for leakage: by construction no scaffold appears in both training and test (zero shared groups in every fold), whereas a random split of the same data leaks 3 to 8 scaffolds per fold across the train/test boundary (table S11). The numerical effect on difficulty is nonetheless small—the mean nearest-neighbour Tanimoto similarity between a test molecule and its closest training molecule falls only from 0.615 (random) to 0.592 (scaffold)—so we do not claim the split makes the task dramatically harder; we claim it removes a specific leakage channel.

That the model learns chemical signal rather than scaffold-group artefacts is established by a label-permutation test: the target was shuffled 1 000 times and the scaffold-CV MAE recomputed under each permutation. The true MAE (0.0956 eV) lies far in the left tail of the null distribution (mean 0.121 eV, SD 0.0043 eV, 95 % interval 0.112 to 0.129), giving $p = 0.001$. Regenerated by `code/scaffold_split_analysis.py`.

Table S11: Scaffold `GroupKFold` versus a random 5-fold split on the same 231 molecules. Scaffold splitting removes train/test scaffold overlap; the label-permutation test confirms the fitted model is far from the no-signal null.

Quantity	Scaffold split	Random split
Shared scaffolds per fold	0 (all folds)	3–8
Test–train NN Tanimoto (mean)	0.592	0.615
Label-permutation test (1000 shuffles, scaffold CV)		
True CV-MAE (eV)	0.0956	
Null CV-MAE: mean (95 % CI) (eV)	0.121 (0.112, 0.129)	
p-value (left tail)	0.001	

S3.5 Reproducibility

The scripts `code/finalize_model.py` and `code/rebuild_structural_model.py` regenerate table S5 and Fig. 1 of the main text from the benchmark data. The Zenodo concept DOI 10.5281/zenodo.17436069 (latest version) holds the archive; files are listed in S7.

S4. DFT level benchmark

Across 7 representative emitters in gas and toluene, B3LYP/6-31G(d) and CAM-B3LYP/def2-TZVP differ in ΔE_{ST} by a mean absolute 0.30 eV (up to 0.58 eV), with sign reversals of the relative ordering (e.g. DMAC-DPS). This functional dependence limits claims of agreement across *computed* reference gaps; it is not a physical error floor for a model trained on measured experimental gaps (table S12).

A higher-tier check confirms this functional dependence is not an artefact of the disparate B3LYP/CAM-B3LYP pair. Across six range-separated and hybrid functionals applied to 27 charge-transfer emitters [13], the singlet–triplet gap *estimate* ($E(\mathrm{S}_1^{\mathrm{ROKS}})$ –

Table S12: Functional dependence of ΔE_{ST} (eV): B3LYP/6-31G(d) vs CAM-B3LYP/def2-TZVP.

Molecule	Phase	B3LYP	CAM-B3LYP	Δ
4CzIPN	gas	0.192	0.361	+0.169
4CzIPN	toluene	0.206	0.335	+0.129
ACRFLCN	gas	0.007	0.590	+0.583
ACRFLCN	toluene	0.000	0.548	+0.548
ACRSA	gas	0.034	0.447	+0.413
ACRSA	toluene	0.000	0.372	+0.372
BACN	gas	0.524	0.991	+0.467
BACN	toluene	0.521	0.921	+0.400
DMAC-DPS	gas	0.489	0.188	−0.301
DMAC-DPS	toluene	0.444	0.207	−0.237
DMAC-TRZ	gas	0.098	0.261	+0.163
DMAC-TRZ	toluene	0.085	0.271	+0.186
PXZ-NAI	gas	0.245	0.355	+0.110
PXZ-NAI	toluene	0.289	0.360	+0.071

$E(S_1^{UKS}) \approx \Delta E_{ST}/2$) disagrees per molecule by a median of 0.049 eV (75th percentile 0.10 eV, one outlier excluded). Even among modern functionals the estimate varies at the 0.05 eV to 0.10 eV level; no absolute gap or experimental agreement is claimed from these data. Extracted by `code/parse_roks_benchmark.py` from `results/theoexp_roks_energies.csv`.

Three measured sources of variability pertain to different quantities (table S13); we do *not* combine them into one floor. Only the experimental label term applies directly to a model trained on the measured gap. The single-report scatter (A, 0.072 eV RMS) describes variation between published observations of the same molecule. For the 102 multi-report molecules the median label has an estimated RMS standard error of 0.049 eV; over all 231 molecules, with single-report labels counted at single-report scatter, label noise is about 0.072 eV RMS, against a random-forest MAE of 0.096 eV (95 % CI 0.082 to 0.109). This constrains interpretation of model error but does not show that the model has reached a noise floor. The vertical→adiabatic offset (B, 0.195 eV MAE) pertains to a computed approximation on 14 molecules and is absent from the 2D model. The functional dependence of a computed gap (C, mean 0.296 eV) affects comparisons among theoretical references; it does not set a lower bound on error against experiment. The capacity tests here did not close the remaining gap (table S20), but other models and representations remain untested. Component magnitudes are calculated in `code/ceiling_decomposition.py`.

S4.1 Vertical versus adiabatic gap

The NTO descriptors are evaluated at the ground-state (vertical) geometry. To bound the error this introduces relative to a relaxed (adiabatic) treatment, we recomputed ΔE_{ST} for 14 representative emitters in gas and toluene at CAM-B3LYP/def2-TZVP (D3BJ, RIJCOSX) with excited-state geometry optimisation in ORCA, and compared with the vertical sTDA-xTB values (table S14). Over the 27 converged points the vertical gap deviates from the adiabatic reference by a mean absolute 0.195 eV (RMSE 0.245 eV, worst case 0.548 eV for 2CzTPE). The deviation is dominated by an additive offset rather than by reordering: a linear fit of adiabatic on vertical gives slope 1.00 and intercept 0.07 eV ($R^2 = 0.70$), with rank correlation Spearman $\rho = 0.71$. The residual is not negligible (RMS 0.245 eV, signed deviations of both signs) and $n = 14$ cannot settle how much of it is systematic. Geometry relaxation therefore shifts the absolute scale while leaving the ordering—on which the triage use depends—largely intact. Regenerated by `code/adiabatic_validation_analysis.py` from `results/vertical_vs_adiabatic_comparison.csv`.

S4.2 Triplet manifold (T1–T2)

A small S_1–T_1 gap does not guarantee fast reverse intersystem crossing; the T_1–T_2 splitting and the wider triplet manifold matter too [14]. The same vertical CAM-B3LYP/def2-TZVP TD-DFT calculations that supplied the adiabatic benchmark also resolve ten triplet roots, so we report T_1 and T_2 directly (table S15). Across the 27 converged emitter–phase points the T_1–T_2 gap ranges from 0.018 eV (4CzIPN) to 1.50 eV (BBPA), mean 0.41 eV; 13 of 27 fall below 0.3 eV. The manifold therefore varies widely *among molecules with similar* ΔE_{ST} (e.g. DMAC-DPS and DMAC-TRZ have near-equal S_1–T_1 gaps but T_1–T_2 of 0.06 eV to 0.26 eV), which is exactly the information a scalar ΔE_{ST} triage cannot encode and a direction where the excited-state pipeline adds genuine value. Regenerated by `code/extract_triplet_manifold.py` from the `orca_package` outputs.

To read the manifold across the whole corpus rather than the 14-molecule ORCA subset, we extracted T_1 and T_2 for all 231 emitters from the cheaper sTDA-xTB pipeline (`code/extract_t1_t2_rerun.py`; 231/231 converged, `results/t1_t2_full.csv`). The full-corpus T_1–T_2 gap has median 0.14 eV (mean 0.24 eV), and 74 % of emitters fall below the 0.3 eV region where a near-degenerate second triplet can open competing non-radiative channels (fig. S3). Most low-gap candidates therefore remain exposed to inefficient reverse intersystem crossing—a hazard a scalar S_1–T_1 triage cannot see.

Table S13: Three measured sources of variability affecting different quantities. Only experimental report variability (A) contributes to imprecision of the measured target; the RMS standard error of the median label is 0.049 eV for the 102 multi-report molecules, and label noise over all 231 is about 0.072 eV RMS. B concerns the vertical-to-adiabatic computational approximation, and C concerns the choice of functional for a computed gap. They cannot be added into an experimental error floor.

	Source (what it bounds)	Magnitude (eV)
A	Single-report scatter about the median — applies to the experimental target (RMS)	0.072
B	Vertical→adiabatic descriptor offset — largely additive, ranking mostly preserved (n = 14); not a target floor (MAE)	0.195
C	Functional dependence of the computed reference — bounds computed-gap agreement only (mean)	0.296
	Observed random-forest MAE	0.096
	Mean-value baseline	0.107

Table S14: Vertical (sTDA-xTB, ground-state geometry) versus adiabatic (CAM-B3LYP/def2-TZVP, excited-state optimisation) ΔE_{ST} (eV) for 14 emitters. Δ = adiabatic − vertical. Summary: MAE 0.195 eV, slope 1.00, intercept 0.07 eV, $R^2 = 0.70$, $\rho = 0.71$.

Molecule	Phase	Vertical	Adiabatic	Δ
4CzIPN	gas	0.361	0.402	+0.041
4CzIPN	toluene	0.335	0.436	+0.101
DMAC-TRZ	gas	0.261	0.442	+0.181
DMAC-TRZ	toluene	0.271	0.638	+0.367
DMAC-DPS	gas	0.188	0.385	+0.197
DMAC-DPS	toluene	0.207	0.558	+0.351
PXZ-NAI	gas	0.355	0.243	−0.112
PXZ-NAI	toluene	0.360	0.491	+0.131
TPA-APy	gas	0.876	0.753	−0.123
TPA-APy	toluene	0.765	0.895	+0.130
BACN	gas	0.991	1.129	+0.138
BACN	toluene	0.921	1.063	+0.142
BMZ-TZ	gas	0.938	0.410	−0.528
BMZ-TZ	toluene	0.933	0.700	−0.233
2CzPN	gas	0.613	0.560	−0.053
2CzPN	toluene	0.621	0.652	+0.031
APPT-PXZ	gas	0.350	0.331	−0.019
2PXZP	gas	0.467	0.384	−0.083
2PXZP	toluene	0.485	0.639	+0.154
ACRSA	gas	0.447	0.204	−0.243
ACRSA	toluene	0.372	0.677	+0.305
ACRFLCN	gas	0.590	0.302	−0.288
ACRFLCN	toluene	0.548	0.576	+0.028
2CzTPE	gas	1.143	1.691	+0.548
2CzTPE	toluene	1.042	1.535	+0.493
BBPA	gas	1.521	1.641	+0.120
BBPA	toluene	1.433	1.562	+0.129

Table S15: Vertical CAM-B3LYP/def2-TZVP TDA energies (eV): S_1, T_1, T_2, the singlet–triplet gap $\Delta E_{ST} = S_1 - T_1$, and the triplet-manifold gap T_1–T_2, for 14 emitters in gas and toluene.

Molecule	Phase	S_1	T_1	T_2	ΔE_{ST}	T_1–T_2
2CzPN	gas	3.652	3.039	3.464	0.613	0.425
2CzPN	toluene	3.632	3.011	3.459	0.621	0.448
2CzTPE	gas	3.496	2.353	2.767	1.143	0.414
2CzTPE	toluene	3.411	2.369	2.788	1.042	0.419
2PXZP	gas	3.292	2.825	3.080	0.467	0.255
2PXZP	toluene	3.343	2.858	3.139	0.485	0.281
4CzIPN	gas	3.377	3.016	3.050	0.361	0.034
4CzIPN	toluene	3.343	3.008	3.026	0.335	0.018
ACRFLCN	gas	3.597	3.007	3.548	0.590	0.541
ACRFLCN	toluene	3.546	2.998	3.536	0.548	0.538
ACRSA	gas	3.769	3.322	3.513	0.447	0.191
ACRSA	toluene	3.746	3.374	3.500	0.372	0.126
APPT-PXZ	gas	2.701	2.351	2.734	0.350	0.383
BACN	gas	3.713	2.722	3.533	0.991	0.811
BACN	toluene	3.629	2.708	3.503	0.921	0.795
BBPA	gas	3.553	2.032	3.525	1.521	1.493
BBPA	toluene	3.458	2.025	3.526	1.433	1.501
BMZ-TZ	gas	3.730	2.792	3.180	0.938	0.388
BMZ-TZ	toluene	3.896	2.963	3.142	0.933	0.179
DMAC-DPS	gas	3.637	3.449	3.508	0.188	0.059
DMAC-DPS	toluene	3.678	3.471	3.538	0.207	0.067
DMAC-TRZ	gas	3.509	3.248	3.504	0.261	0.256
DMAC-TRZ	toluene	3.533	3.262	3.509	0.271	0.247
PXZ-NAI	gas	2.688	2.333	2.836	0.355	0.503
PXZ-NAI	toluene	2.650	2.290	2.829	0.360	0.539
TPA-APy	gas	3.555	2.679	2.823	0.876	0.144
TPA-APy	toluene	3.425	2.660	2.795	0.765	0.135

This full-corpus manifold must be read *qualitatively only*. Benchmarking the sTDA-xTB T_1–T_2 gap against the CAM-B3LYP reference on the six overlapping molecules gives a mean absolute deviation of 0.237 eV (Spearman $\rho = 0.43$, $p = 0.40$; table S16), so the two methods agree on neither magnitude nor rank at a useful level. Quantitative ranking on RISC propensity still requires the higher-level calculation; the sTDA manifold serves only to flag that the triplet-manifold hazard is widespread, not to order candidates by it.

Table S16: sTDA-xTB versus CAM-B3LYP T_1–T_2 gap (eV) for the six molecules present in both sets. Independent methods; the comparison is genuine (fresh GFN2 geometries). Summary: MAE 0.237 eV, Spearman $\rho = 0.43$ ($p = 0.40$, $n = 6$).

Molecule	sTDA-xTB	CAM-B3LYP
2CzPN	0.169	0.425
2PXZP	0.004	0.255
4CzIPN	0.073	0.034
ACRSA	0.006	0.191
DMAC-DPS	0.011	0.059
PXZ-NAI	1.146	0.503

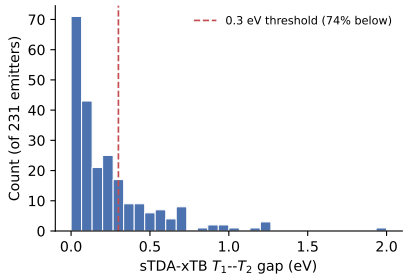


Figure S3: Distribution of the sTDA-xTB T_1–T_2 gap across all 231 emitters. 74 % fall below 0.3 eV (dashed line). Read qualitatively only (table S16).

S4.3 Range-separated TD-DFT reference gap

Referee comment on the original submission held that the semi-empirical sTDA gap understates what a proper range-separated TD-DFT calculation would achieve. We tested this directly. Vertical ΔE_{ST} was computed for all 231 benchmark molecules at wB97X-D4/def2-SVP with RIJCOSX and the Tamm–Dancoff approximation (ORCA 6 [3]; `nroots` 8, triplets included), at the GFN2-xTB ground-state geometry, with $\Delta E_{ST} = E(S_1) - E(T_1)$. All 231/231 jobs terminated normally with all states parsed and no inverted gaps; the run cost 609 core-hours (measured: 76.2 h elapsed on 8 processes; median 16.1 min per molecule, slowest 2.1 h; wall $\propto$ atoms$^{1.89}$). Per-molecule gaps and timings are in `results/tddft_reference_231.csv`; the head-to-head analysis is `results/ref1_tddft_gap.json`, produced by `code/ref1_tddft_gap.py` on the same experimental labels, SMILES, NTO features and scaffold `GroupKFold` folds as table S5.

The raw TD-DFT gap overestimates the measured gap by a systematic +0.654 eV (TD-DFT mean 0.803 eV, SD 0.248; experiment mean 0.149 eV, SD 0.167), more than triple the +0.221 eV sTDA offset. sTDA and TD-DFT gaps agree only moderately with each other ($r = 0.461$, $\rho = 0.402$, mean shift +0.433 eV). An in-fold degree-1 calibration ($a\,g + b$, fitted per training fold on $\approx$185 molecules, no test leak) removes the offset. table S17 lists every predictor on the common folds; table S18 the paired MAE differences (2000-resample bootstrap on identical folds plus Wilcoxon signed-rank on paired absolute errors).

Read raw, a higher level of theory is worse, not better: the range-separated TDA gap is the least accurate predictor in the study, driven by a large fixed exchange-splitting overestimate. It does track experiment better in rank (r 0.32 to 0.43 from sTDA to TD-DFT) and, once calibrated on experimental labels, in MAE (0.099 eV, below the mean baseline but not the structure-only forest). Added as one random-forest feature it gives the only physics contribution in this work that clears a paired test (M6 vs M1, M5 vs M2), a 4 % MAE reduction for 609 core-hours. Caveats: gas-phase vertical values only (no solvent, no excited-state relaxation); the +0.654 eV bias is specific to wB97X-D4/def2-SVP/TDA; def2-SVP is a small basis, though the systematic offset is expected to persist at a larger basis for a range-separated hybrid; TDA raises triplet energies relative to full TD-DFT, widening the gap, and was the deliberate stable choice; the M5/M6 gains ($\approx$0.003–0.004 eV) are real by the paired test but small against the 0.072 eV single-report label scatter.

S5. Substructure-filtered extended library

An extended set of 22 194 structures was obtained by screening the PubChem CID–SMILES collection for compounds carrying both a donor motif (carbazole, phenothiazine, phenoxazine, acridine, diphenylamine, triphenylamine or dimethylaniline) and an acceptor motif (triazine, benzonitrile, pyridine, pyrimidine, quinoxaline, benzothiadiazole, naphthoquinone or a cyano group), under the constraints MW $<$ 900 Da, $\geq$ 2 aromatic rings and $\geq$ 1 N/O/S heteroatom. The screen is in `code/build_shortlist.py` and the screening script in the deposit. It is a substructure filter over an existing

Table S17: TD-DFT reference gap versus semi-empirical gap and structure-only random forests, all on the same 231-molecule scaffold `GroupKFold`(k = 5) folds. B rows are single-quantity predictors; M rows are random forests (400 trees). "Calibrated" = in-fold linear fit requiring experimental training labels.

	Predictor	MAE (eV)	RMSE (eV)	R^2	r	ρ
B0	Mean baseline	0.107	0.167	−0.01	−0.11	−0.06
B1	Raw sTDA gap	0.251	0.299	−2.22	0.32	0.24
B3	Raw TD-DFT gap	0.654	0.694	−16.3	0.43	0.38
B2	Calibrated sTDA gap	0.104	0.160	0.08	0.29	0.23
B4	Calibrated TD-DFT gap	0.099	0.152	0.17	0.41	0.37
M1	RF Morgan (structure only)	0.091	0.142	0.27	0.55	0.31
M2	RF NTO (energy-free)	0.096	0.144	0.25	0.50	0.36
M5	RF NTO + TD-DFT gap	0.092	0.140	0.29	0.54	0.40
M6	RF Morgan + TD-DFT gap	0.087	0.138	0.31	0.58	0.37
M7	RF NTO + sTDA + TD-DFT	0.093	0.141	0.29	0.54	0.39

Table S18: Paired MAE difference on identical folds (positive = the TD-DFT gap helps). CI from 2 000 paired bootstrap resamples; p from the Wilcoxon signed-rank test on paired absolute errors.

Comparison	ΔMAE /eV	95 % CI /eV	Wilcoxon p
M6 vs M1 (Morgan + gap)	+0.0039	[+0.0004, +0.0071]	0.016
M5 vs M2 (NTO + gap)	+0.0032	[+0.0008, +0.0058]	0.013
B4 vs B0 (calib. gap vs mean)	+0.0085	[+0.0002, +0.0164]	0.006
B4 vs M1 (calib. gap vs RF)	−0.0075	[−0.0205, +0.0061]	0.28
B3 vs B1 (raw TD-DFT vs sTDA)	−0.403	[−0.431, −0.375]	1×10^{-37}

database, not a combinatorial enumeration of fragment pairs, and the distinction matters for how the set should be read: every member satisfies the donor–acceptor pattern test, but the matches are dominated by the weaker motifs (dimethylaniline in 85 % and pyridine in 59 % of the 100 lowest-predicted structures, against carbazole in 2 and triazine in 3). The set also inherits the composition of the source database rather than of a designed emitter series: 97 % of those structures carry a halogen and 53 % a stereocentre, and enantiomer pairs appear as separate entries with identical predicted gaps, which a 2D fingerprint cannot distinguish. Candidates were ranked by a rule-based TADF score

$$\begin{aligned}\text{TADF score} = {} & 0.35\, f_{\text{MW}} + 0.25\, f_{\text{LogP}} \\ & + 0.20\, f_{\text{rings}} + 0.20\, f_{\text{hetero}},\end{aligned} \tag{S1}$$

with each $f_i \in [0, 1]$ a normalised feature score based on established design heuristics [15, 16, 17]. The score is a coarse synthesis-planning filter, *not* a calibrated ΔE_{ST} predictor. The random-forest model trained on the labelled benchmark is applied to this set only to obtain split-conformal prediction intervals (S6.7); no candidate is put forward on the strength of its predicted gap. These are synthesis-planning leads only: they are not quantum-validated, and the heuristic score is not a calibrated ΔE_{ST} predictor. Property distributions of the filtered set versus the top-scoring subset are shown in fig. S4.

We additionally ranked the full library with the calibrated structure-only Morgan-FP model and attached a split-conformal 90 % prediction interval to every prediction (mean half-width 0.18 eV, empirical coverage 0.89). No ranked shortlist is deposited: for the leading candidates the predicted gap is 0.02 eV to 0.05 eV while the full interval width is about 7.6 times as large (half-width 3.8 times), and the lower bound of every one of the 100 lowest-predicted intervals falls below zero. At this accuracy the conformal procedure does not support selection at the single-molecule level, and no device-level quantity is predicted.

S6. Robustness analyses

S6.1 Cluster cross-validation

Because 92.9 % of scaffolds are singletons, we built non-singleton groups by Butina clustering (Morgan Tanimoto distance) and ran cluster-grouped CV across a cutoff scan (table S19). Even at the coarsest grouping (70 clusters, largest 38 molecules), the MAE (0.099 eV) sits between scaffold-CV (0.096 eV) and random-CV

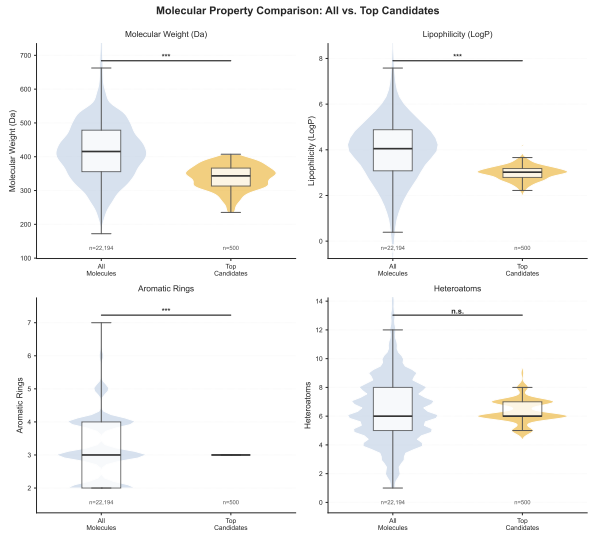


Figure S4: Property distributions of the filtered library (22 194 PubChem structures passing the donor–acceptor substructure screen, grey) versus the top 500 by heuristic TADF score (blue). Enrichment toward lower molecular weight reflects the scoring rule; these are unvalidated leads, not predicted emitters.

(0.106 eV), a spread of 0.010 eV. Performance is therefore *stable across validation schemes*: the headline number is not an artefact of singleton scaffolds. Regenerated by `code/cluster_cv_analysis.py`.

Table S19: Cluster-grouped CV of the headline NTO RF across Butina distance cutoffs, with scaffold and random CV for reference.

Grouping	#groups	largest	MAE (eV)	ρ
Butina 0.3	186	7	0.100	0.35
Butina 0.4	153	10	0.100	0.38
Butina 0.5	111	15	0.104	0.31
Butina 0.6	70	38	0.099	0.40
Scaffold (headline)	212	—	0.096	0.36
Random 5-fold	—	—	0.106	0.34

S6.2 Dimensionality and model capacity

Two checks address the charge that a 2 048-bit fingerprint over-parameterises a 231-molecule set. First, shrinking the fingerprint to 1 024 or 512 bits leaves the MAE and the (negative) lower R^2 confidence bound essentially unchanged (table S20, top), so the negative R^2 tail is intrinsic to the low variance-explained on this target, not a width artefact; the lowest-dimensional regularised model (NTO + ElasticNet) brings the lower bound closest to zero (−0.03) but does not lift it. Second, no higher- or different-capacity learner beats the random forest under the same scaffold CV (table S20, bottom): gradient boosting, an MLP and an SVR are all worse. Model capacity is not the limiting factor. Retraining on the 208 molecules whose inter-report standard deviation is $\leq$ 0.05 eV does not lower the MAE (0.106 eV). That subset is a weak test, because 129 of those 208 molecules have no replicate at all and enter with SD = 0 by construction, so only 23 molecules are actually excluded. Conditioning instead on molecules that carry replicates, and reading the error off the same out-of-fold predictions, the model achieves 0.074 eV on the 79 whose reports agree to $\leq$ 0.05 eV, 0.106 eV on the 23 whose reports disagree, and 0.107 eV on the 129 whose label precision cannot be measured. The constant predictor scores 0.074, 0.107 and 0.110 eV on the same strata, respectively, so the comparison carries no information about label quality. Regenerated by `code/dimensionality_check.py` and `code/capacity_and_noise_ceiling.py`.

Table S20: Top: fingerprint-width sweep (RF) — MAE and 95 % bootstrap R^2 CI. Bottom: alternative learners under the same scaffold CV. None beats the RF.

Setting	MAE (eV)	R^2 (95 % CI)
Morgan 512 (RF)	0.098	0.15 (−0.44, 0.46)
Morgan 1024 (RF)	0.096	0.24 (−0.25, 0.51)
Morgan 2048 (RF)	0.091	0.27 (−0.19, 0.53)
NTO + ElasticNet	0.102	0.10 (−0.03, 0.17)
RandomForest (headline)	0.096	—
HistGradientBoosting	0.105	—
MLP (100, 50)	0.169	—
SVR (RBF)	0.120	—
ElasticNet	0.102	—

S6.3 SHAP cross-check by permutation importance

An independent, model-agnostic permutation-importance analysis (held-out 30 %, 50 repeats) ranks the singlet hole–electron overlap $S_{\mathrm{he}}(S_1)$ *first*, in agreement with TreeSHAP; two of the SHAP top-five recur in the permutation top-five. The leading attribution is thus corroborated by two methods, while the lower-ranked tail is not — consistent with our restriction of mechanistic reading to the dominant descriptor. Regenerated by `code/permutation_importance_check.py`.

S6.4 Enrichment curve and calibrated operating points

The main-text enrichment curve reports precision (fraction of selected molecules with experimental gap $\leq$ 0.10 eV) against screening budget. Enrichment peaks at 1.37× over the 49 % base rate around the top 5 % to 20 % and does not improve at more aggressive cuts (the top 1 % is two molecules). A split-conformal calibration gives a 90 % interval half-width

of 0.178 eV (empirical coverage 0.892). These intervals convey uncertainty but are too wide to identify an individual low-gap emitter reliably. Regenerated by `code/enrichment_curve.py`.

S6.5 Multi-criteria triage

A small S_1–T_1 gap is necessary but not sufficient for efficient delayed fluorescence: the emitter must also be optically bright and free of a near-degenerate second triplet. We therefore composed the predicted gap with two auxiliary structure-level filters—oscillator strength $f_{S_1} \geq 0.01$ (209/231 pass; `code/oscillator_strength_model.py`) and sTDA T_1–$T_2 > 0.10$ eV (table S16)—leaving 131 molecules that clear all three (`code/multi_criteria_triage.py`). Ranking within this pool raises the top-5 % precision for low-gap emitters from 0.58 (gap alone) to 0.71, i.e. enrichment 1.18→1.45×; the two curves converge by the top 50 %. The gain is real but small and rests on only a handful of molecules at the sharpest cut, so we read the multi-criteria filter not as a precision gain but as a physically motivated way to discard the 43 % of low-gap candidates that are dark or manifold-unsafe—a decision a scalar-gap triage cannot make. The T_1–T_2 term inherits the qualitative-only caveat of table S16.

S6.6 Dataset expansion stress-test

To test whether the benchmark is limited by corpus size, we resolved and featurised 624 additional donor–acceptor emitters from the experimental literature (name-to-structure resolution followed by the identical GFN2-xTB/sTDA natural-transition-orbital pipeline; `code/expand_dataset.py`, `code/featurize_nto_local.py`). After discarding 127 structures already present in the training set, 497 genuinely new molecules extend the corpus to 728 (table S21). Enlarging the set does *not* improve structure-only prediction: under the same scaffold CV the MAE rises from 0.098 eV to 0.124 eV and R^2 falls to −0.01 (the curated-set MAE of 0.098 eV reproduces the headline 0.096 eV within single-seed variation). Restricting the new molecules to those with replicate measurements (234 with ≥ 2 independent reports) recovers part of the loss (MAE 0.110 eV, R^2 0.05), placing one component of the degradation in label noise from automated literature extraction. We do not decompose the degradation further: the added molecules are resolved through a different structure pipeline, so label quality and chemical diversity are confounded and this design cannot apportion the loss between them. What the expansion rules out is that the corpus is merely too small. Regenerated by `code/expansion_stress_test.py`.

Table S21: Scaffold-CV of the NTO random forest as the corpus is expanded and as new-label confidence is tightened. Expansion does not improve accuracy.

Corpus	n	MAE (eV)	R^2	ρ
Curated baseline	231	0.098	0.18	0.34
+ all new	728	0.124	−0.01	0.16
+ multi-report new (≥ 2)	465	0.110	0.05	0.24

S6.7 Candidate triage and the filtered library (moved from the main text)

Candidate prioritisation as a triage filter.. The model's practical value is as a coarse triage filter: it eliminates the bottom tier of candidates rather than ordering the viable subset. We quantify this directly. Taking emitters with experimental $\Delta E_{ST} \leq 0.10$ eV as the targets (49 % of the set), the structure-only model's top-ranked candidates are enriched in targets relative to random selection by 1.2 to 1.4× (precision rising from the 49 % base rate to 60 % at the top 10–20 and 68 % at the top 50); a bootstrap confidence interval on this cross-validation enrichment, given below, shows the smaller cutoffs are not statistically distinguishable from chance. Note that ΔE_{ST} is a necessary but not sufficient condition for TADF efficiency; emission wavelength matching is a subsequent, independent design step not addressed by this model. The filter therefore works, but weakly: it is a coarse first pass that modestly concentrates good emitters, not a selector. Part of that weakness is the threshold itself: 0.10 eV is only 0.03 eV above the 0.072 eV RMS inter-report scatter (the main-text ceiling subsection), so a molecule's true class membership near that line is itself uncertain at the level of label noise—tightening the triage threshold runs directly into the same ceiling that bounds the regression task. Among well-characterised emitters, DMAC-DPS (experimental $\Delta E_{ST} \approx 0.09$ eV) and PXZ-NAI are examples of low-gap emitters the filter retains. Application to a specific lighting niche—horticultural or human-centric—is a *separate, downstream* step: it requires matching the emission wavelength and oscillator strength, neither of which this scalar ΔE_{ST} model predicts. We therefore make no spectral-matching or device-level claim (reverse intersystem crossing rates and external quantum efficiencies depend on quantities this model does not resolve, and our earlier device estimates did not survive scrutiny (main-text limitations paragraph).

A substructure-filtered extended chemical space.. To indicate the chemical space such triage would operate over, we screened PubChem for structures carrying both a donor and an acceptor motif, retaining 22 194 (main-text Methods, library subsection; molecular weights 172 Da to 899 Da, 2 to 12 aromatic rings; property distributions in fig. S4). Every member passes the donor–acceptor pattern test, but the set carries the composition of the source database rather than of a designed emitter series, and its matches lean on the weaker motifs; it indicates scale, not a curated design space. We do not deposit a ranked candidate list. On the filtered set the split-conformal 90 % prediction interval spans 0.36 eV (mean half-width 0.18 eV), about 7.6 times the predicted gap, and for every one of the 100 lowest-predicted molecules the interval's lower bound falls below zero. At this accuracy conformal prediction refuses selection at the single-molecule level; the filtered set only indicates the scale of the space that the labelled-data triage would operate over. The heuristic score of the main-text TADF score equation remains a planning aid, not a calibrated predictor, and the retained molecules are not quantum-validated.

Quantifying triage utility.. On held-out labelled molecules the structure-only model enriches the low-gap class by 1.2 to 1.4× over random selection, but a 95 % bootstrap confidence interval (5 000 resamples over molecules, the ranking re-derived from the fixed cross-validation out-of-fold predictions within each resample) shows this holds only at the less aggressive cutoffs. Against the 49 % base rate ($\Delta E_{ST} \leq 0.10$ eV), top-ranked precision reaches 60 % at both the top 10 and top 20 candidates (enrichment 1.22×, 95 % CI 0.63 to 1.89 and 0.80 to 1.70: both intervals include no enrichment), and 68 % at the top 50 (1.38×, CI 1.10 to 1.60) or 67.4 % at the top 20 % of the benchmark (1.37×, CI 1.08 to 1.61: both intervals exclude no enrichment). The enrichment is therefore only statistically established at cutoffs of roughly 50 molecules or a fifth of the benchmark; at the ten-to-twenty candidate scale a laboratory would actually shortlist, it cannot be distinguished from chance at this sample size. The full enrichment curve (fig. S5) peaks near 1.37× at the top 5 % to 20 % and does not improve at more aggressive cuts; a split-conformal calibration lets a laboratory fix an operating point at a stated confidence. This is a statement about the labelled benchmark: the model supports *triage*, not selection, and the interval widths reported above rule out projecting a hit rate onto the unvalidated filtered library.

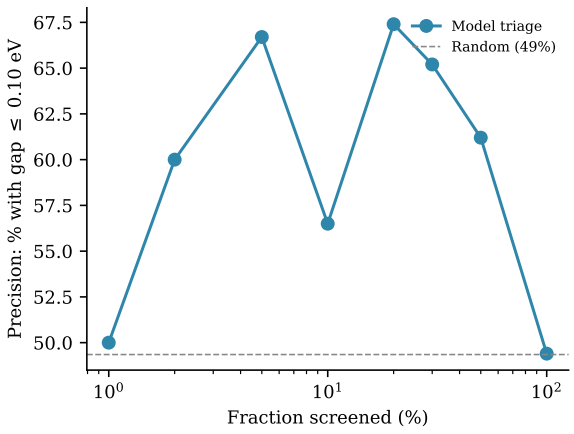


Figure S5: Triage precision versus fraction of the benchmark screened (log x). Dashed line: the 49 % random base rate. Enrichment is real but bounded at ≈ 1.3–1.4×; the top 1 % is two molecules.

S6.8 Detailed limitations (moved from the main text)

This study is bounded in several ways. (1) The experimental corpus is heterogeneous (mixed solvents and methods, 0.072 eV RMS inter-report scatter); a single-source, solvent-controlled dataset would help separate label variability from representation error. The estimated noise bound lies well above observed R^2, so a model improvement is not excluded by these data. (2) The model predicts a consensus gap, not solvatochromic or conformer-dependent values. (3) We make no quantitative device claims. Molecule-independent estimates for spin–orbit coupling, k_{RISC}, and external quantum efficiency, derived from literature medians, were deliberately excluded from this analysis. (4) Ranking power is moderate ($\rho = 0.36$), so the model supports triage, not final candidate selection. (5) The target is a single scalar, $\Delta E_{ST}(S_1–T_1)$. A small $S_1–T_1$ gap is necessary but not sufficient for efficient delayed fluorescence: the splitting of the triplet manifold ($T_1–T_2$) also governs reverse intersystem crossing.[14] To gauge this we extracted T_1 and T_2 from the CAM-B3LYP TD-DFT calculations for 14 emitters (table S15): the $T_1–T_2$ gap ranges 0.02 eV to 1.50 eV and varies widely *among molecules with near-equal* ΔE_{ST}, so a scalar-gap triage cannot rank them on RISC propensity. The semi-empirical step adds no error reduction for the $S_1–T_1$ gap (main-text NTO subsection) and does at least yield a triplet-manifold quantity that 2D structure does not, but we cannot show that quantity is reliable. Extending the sTDA extraction to all 231 emitters, 74 % carry a $T_1–T_2$ gap below 0.3 eV; that classification should be treated as indicative only, since the deviation of the sTDA man-

ifold from the CAM-B3LYP reference (0.24 eV, below) is comparable to the 0.3 eV threshold being applied. We read this full-corpus manifold only qualitatively: benchmarked against the 14-molecule CAM-B3LYP reference (six molecules overlapping), the sTDA T_1–T_2 gap carries a mean absolute deviation of 0.24 eV and a rank correlation that is not resolved at this sample size (Spearman $\rho = 0.43$, $p = 0.40$, $n = 6$): the two methods agree on neither magnitude nor rank at a useful level, so quantitative ranking on RISC propensity requires the higher-level calculation (table S15). Emitters with an *inverted* gap ($\Delta E_{ST} < 0$), which violate Hund's rule through double-excitation character,[18] are out of scope, and the model fails on them exactly as its construction requires. A literature screen flags 5 corpus compounds for which at least one report gives an inverted gap; for two of these the consensus median we train on is itself negative (HAP-3MF, −0.22 eV; TPA-NZP, −0.038 eV), and these are the only 2 negative labels among the 231. The random forest—built on GFN2-xTB features that enforce Aufbau ordering—returns a positive gap for all five, so it carries the wrong sign for both molecules whose own training label is negative. The failure is representational rather than incidental. A regression forest can in principle return a negative value, since its output is an average over training labels and two of ours are negative; what it lacks is any feature that separates an inverted-gap molecule from a conventional one, because the sTDA descriptors are computed under Aufbau ordering and the structure-only descriptors carry no excited-state information at all. Predicting this class would require descriptors that encode double-excitation character, not more data (fig. S6). Screening this class would require ROKS- or EOM-CCSD-level descriptors.[19] (6) The semi-empirical descriptors are computed at ground-state vertical geometries and therefore carry no information about excited-state structural relaxation, and none about spin–orbit coupling. Both matter physically for delayed fluorescence, and the omission is a plausible part of why the NTO features do not outperform 2D fingerprints: a vertical descriptor cannot represent the charge-transfer relaxation that separates two molecules with similar ground-state topology. Our 14-molecule adiabatic comparison bounds the size of the vertical approximation (mean absolute deviation 0.195 eV, RMS 0.245 eV) but cannot remove it, and excited-state optimisation for the full corpus was outside the compute budget. Descriptors built on relaxed excited-state geometries are a natural next test of whether the similar errors observed here persist under a richer excited-state representation. On the model side, the comparison covers tabular learners and one frozen pretrained molecular-transformer embedding (the main-text ceiling subsection); an end-to-end message-passing network or an encoder fine-tuned on a larger labelled set was not attempted, and either would need a benchmark larger than 231 molecules to be informative.

(7) Under a source-paper (DOI-grouped) split the model's advantage over a mean-value predictor is not statistically resolved (main-text benchmark subsection); demonstrated transfer is to new scaffolds measured under represented protocols, not to new measurement laboratories. Future work targets a curated experimental benchmark and uncertainty-aware models that report calibrated confidence alongside each prediction.

S6.9 Naive baselines and prior ML on computed gaps (moved from the main text)

We contextualise the absolute errors against three baselines computed on the out-of-fold scaffold-CV predictions (table S22; 95 % bootstrap CIs, 2 000 resamples): the mean-value predictor (predicting $\bar{y}$ for every molecule, MAE = 0.107 eV), the median-value predictor (MAE = 0.098 eV), and a random-permutation null (mean MAE over 1 000 label shuffles, 0.120 eV, 95 % interval 0.113 to 0.127). The median is a tougher baseline than the mean because the experimental gap distribution is right-skewed toward low-gap emitters; the permutation null is clearly worse than either constant predictor, confirming that the trained model exploits a real feature–label association rather than a fold artefact. Our best model (RF–Morgan, MAE = 0.091 eV) improves on the mean baseline by 15 %; the headline NTO model (MAE = 0.096 eV) improves by 10.6 % (0.011 eV, 95 % CI on the paired difference 0.003 to 0.022, excluding zero). The model edges even the skewed-median baseline (0.098 eV). This gain is modest and should be read against label noise: across the 102 multi-report molecules a single report deviates from the median by 0.072 eV on average (RMS), the worst molecule reaching a standard deviation of 0.56 eV; the median label for those molecules has an RMS standard error of 0.049 eV, and the estimated label noise over all 231 molecules is about 0.072 eV RMS. Label quality is a material term in the error budget, but the model does not sit at a floor (main-text ceiling subsection). As shown in the main text, the excited-state NTO descriptors offer no accuracy advantage over the purely structural sets.

Prior ML for TADF gaps is best read by the *reference* it predicts, not by the headline error alone (table S23). The low MAEs in the literature are all against *computed* targets: Gómez-Bombarelli et al. [20] trained a neural network to reproduce a TD-DFT gap inside

Table S22: Naive baselines versus the structure-based model on the same 231-molecule out-of-fold scaffold-CV predictions. MAE in eV with 95 % percentile-bootstrap CI (2 000 resamples); the permutation row is the mean and central 95 % of 1 000 label shuffles. The median outperforms the mean (right-skewed target); the permutation null is worse than both, so the model captures real signal. Values from `code/compute_baselines.py`.

Predictor	MAE (eV)	95 % CI
Mean predictor	0.107	(0.092, 0.124)
Median predictor	0.098	(0.081, 0.118)
Random-permutation null	0.120	(0.113, 0.127)
NTO-RF (this work)	**0.096**	(0.082, 0.109)

a $>10^6$-molecule screen, Thapa et al. [21] screened a large virtual library against semi-empirically computed gaps, Barneschi et al. [22] reach 0.02 eV with a 3D message-passing network—but against ADC(2) values, and for inverted-gap molecules rather than donor–acceptor TADF—and Li and Li [23] reach 0.06 eV on 233 INVEST and TADF molecules with a quasiparticle-corrected Kohn–Sham protocol. Whether such physics-based estimators retain that accuracy against measured gaps, where the label itself carries about 0.072 eV RMS of noise, remains to be tested. Predicting the *experimental* gap is the task this paper addresses. Nigam et al. [24] describe an early attempt at regressing gaps with neural networks and then used a good/bad classifier; their labels are gaps simulated at the ωB2PLYP′ level, not measured gaps, so that result does not bear on measured gaps. Our 0.096 eV, under scaffold cross-validation and with label and reference noise accounted for, shows that cheap structural features nonetheless track the experimental gap to within $\approx$ 0.1 eV. The result is a measured comparison of the semi-empirical NTO and 2D representations: little difference in scaffold-CV error, and a corpus-conditional rank-order contrast on source-paper-grouped tests. Its paper-cluster interval barely excludes zero and its repeated partitions overlap; independent, protocol-controlled evidence is needed before it can guide selection at a new laboratory (main-text benchmark and holdout-unit subsections).

S7. Data and code availability

The measured labels come from the Huang–Cole TADF database [26]. The concept DOI 10.5281/zenodo.17436069, which resolves to the latest version, holds the data, code and full analysis ledger for the three related articles, mirrored at `https://github.com/TchapetNjafa/Data_Articles_TADF`. The scripts and outputs of analyses A-016 to A-020 are in that archive (`ML_reproducibility/code` and `ML_reproducibility/data`) and are also provided as Supplementary Data (`supplementary_data/` and `JMGM_group_ranking_supplement.zip`). The files are, code: `jmgm_doi_group_ranking_check.py`, `_dataset.py`, `a017_split_unit_controls.py`, `a018_noise_ceiling_heterogeneous.py`, `a019_series_shortcut_test.py`, `a020_controls.py`, `fig_holdout_unit_ranking.py`; data: `a016_jmgm_doi_group_input.csv`, `a016_jmgm_doi_group_ranking.json`, `a017_split_unit_controls.json`, `a018_noise_ceiling_heterogeneous.json`, `a019_series_shortcut_test.json`, `a020_controls.json` and `a006_equivalence_ceiling.json`. The primary 231-molecule benchmark descriptors were generated with `xtb` 6.7.1 (S1.1); the 497-molecule expansion stress test (S6.6) was re-featurised with `xtb` 6.7.1. Other software: `xtb4stda` with `stda` 1.6.3, Multiwfn 3.8, ORCA 6.1.1, Python 3.12, scikit-learn 1.8.0, RDKit 2026.03.2, and SHAP 0.50. Random forests used `random_state` = 0; fold-assignment and bootstrap seeds are listed in table S24.

S8. Inverted singlet–triplet emitters (out of scope)

The pipeline targets conventional TADF emitters with positive gaps; it nonetheless includes two negative consensus labels in the 231-molecule corpus, so the fitted model's failure on inverted cases remains visible. The inverted singlet–triplet (INVEST) class [18] lies outside the present pipeline: GFN2-xTB and sTDA-xTB enforce Aufbau ordering, so the random forest cannot predict a negative gap from the current feature set. A screen of the 25 482-record literature database (`code/ist_screening.py`) returns 66 reports of an inverted gap across 61 compound names (deposited, `results/ist_candidates.csv`); five of those compounds also appear in our 231-molecule corpus. For two of them the consensus median label is itself negative (HAP-3MF, −0.22 eV; TPA-NZP, −0.038 eV) and these are the only two negative labels in the corpus; the remaining three (DPXZ-DPPM, 2CzPN, UGH3) carry positive medians despite an inverted report existing. The random forest predicts a positive gap for all five, so it assigns the wrong sign to both molecules whose own training label is negative. The limitation is representational rather than statistical. A regression forest can in principle return a negative value, since its prediction is

Table S23: Machine-learning prediction of TADF singlet–triplet gaps, ordered by reference type. Low MAEs are obtained only against *computed* gaps; against the *experimental* gap, errors are substantially larger. Only values reported in the cited sources are tabulated; n.r., not reported here.

Study	Model (features)	Set (N)	Reference	MAE (eV)
Gómez-Bombarelli 2016 [20]	NN surrogate	$>10^6$ screened	TD-DFT (computed)	reproduces TD-DFT[a]
Barneschi 2024 [22]	3D message-passing GNN	INVEST set	ADC(2) (computed)	0.02[b]
Nigam 2024 [24]	DNN classifier (Morgan FP)	GA-evolved	ωB2PLYP′ (computed)	regression poor[c]
He 2026 [25]	ML (fingerprints among inputs)	1 321 records	experimental	n.r.
This work	RF (NTO, structure)	231	experimental	**0.096**

[a] Predicts the TD-DFT gap; no experimental-reference regression MAE reported. [b] Inverted-gap (Hund's-rule-violating) molecules, not donor–acceptor TADF. [c] An early regression attempt on computed gaps was abandoned for a good/bad classifier.

Table S24: Reporting summary for the machine-learning models (main text, Methods). Seed ranges describe fold-assignment variability, not confidence intervals.

Item	Entry
Data source	Huang–Cole TADF database [26]; 231 donor–acceptor emitters, 173 primary source papers, 212 Bemis–Murcko scaffolds; target: experimental ΔE_{ST}(eV)
Splits	Error metrics: scaffold `GroupKFold` (k = 5). Holdout-unit comparison: five-fold holdout by molecule, scaffold and source paper, 50 random fold assignments per unit (NumPy seeds 0–49). 20 source-paper `GroupShuffleSplit` partitions (20 % of groups held out, seed 17)
Features	Morgan fingerprints (radius 2, 2 048 bits, `GetMorganFingerprintAsBitVect` defaults: no chirality, no feature invariants); 217 RDKit 2D descriptors; 35 GFN2-xTB/sTDA NTO descriptors (S_1/T_1 energy scalars excluded)
Model	Random-forest regressor, scikit-learn 1.8.0; RDKit 2026.03.2
Hyperparameters	400 trees, `random_state` = 0, other scikit-learn defaults
Metrics with uncertainty	Scaffold-CV MAE 0.091 eV (Morgan) and 0.096 eV (NTO), paired difference 95 % CI −0.017 to 0.009 eV; paper-holdout median Spearman ρ 0.34 (NTO) and 0.17 (Morgan), $\Delta\rho$ = 0.16 (range 0.07 to 0.25 over 50 assignments); fixed DOI split $\Delta\rho$ = 0.191, paper-cluster bootstrap 95 % interval 0.014 to 0.366 (5 000 draws, seed 54 321)
Code and data	Supplementary Data (`supplementary_data/`, `JMGM_group_ranking_supplement.zip`); archive: Zenodo concept DOI 10.5281/zenodo.17436069; file list in S7

an average over training labels and two of ours are negative; what the feature sets lack is any variable that distinguishes an inverted-gap molecule, because the semi-empirical descriptors are computed under Aufbau ordering and the structure-only descriptors carry no excited-state information. More data of the same kind would not change this. INVEST screening needs ROKS- or EOM-CCSD-level descriptors [19] and is out of scope here.

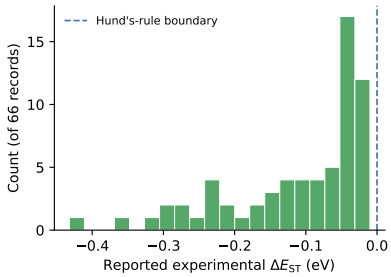


Figure S6: Reported experimental ΔE_{ST} for the 66 inverted-gap records identified in the literature database. All lie below the Hund's-rule boundary (dashed line). Structures were not resolved for these records (`n_with_smiles` = 0), so no model prediction is made for them; they are shown to indicate the reported range of the class, not as a test set.

References

[1] C. Bannwarth, S. Ehlert, S. Grimme, GFN2-xTB—an accurate and broadly parametrized self-consistent tight-binding quantum chemical method with multipole electrostatics and density-dependent dispersion contributions, Journal of Chemical Theory and Computation 15 (3) (2019) 1652–1671. doi:10.1021/acs.jctc.8b01176.

[2] S. Grimme, C. Bannwarth, Ultra-fast computation of electronic spectra for large systems by tight-binding based simplified Tamm-Dancoff approximation (sTDA-xTB), The Journal of Chemical Physics 145 (7) (2017) 074108. doi:10.1063/1.4991798.

[3] F. Neese, F. Wennmohs, U. Becker, C. Riplinger, The ORCA quantum chemistry program package, The Journal of Chemical Physics 152 (22) (2020) 224108. doi:10.1063/5.0004608.

[4] R. L. Martin, Natural transition orbitals, The Journal of Chemical Physics 118 (11) (2003) 4775–4777. doi:10.1063/1.1558471.

[5] G. W. Bemis, M. A. Murcko, The properties of known drugs. 1. molecular frameworks, Journal of Medicinal Chemistry 39 (15) (1996) 2887–2893. doi:10.1021/jm9602928.

[6] Y. Olivier, J.-C. Sancho-García, L. Muccioli, G. D'Avino, D. Beljonne, Computational design of thermally activated delayed fluorescence materials: The challenges ahead, The Journal of Physical Chemistry Letters 9 (20) (2018) 6149–6163. doi:10.1021/acs.jpclett.8b02327.

[7] S. Kaufman, S. Rosset, C. Perlich, O. Stitelman, Leakage in data mining: Formulation, detection, and avoidance, ACM Trans. Knowl. Discov. Data 6 (4) (2012) 1–21. doi:10.1145/2382577.2382579.

[8] S. Kapoor, A. Narayanan, Leakage and the reproducibility crisis in machine-learning-based science, Patterns 4 (9) (2023) 100804. doi:10.1016/j.patter.2023.100804.

[9] N. Artrith, K. T. Butler, F.-X. Coudert, S. Han, O. Isayev, A. Jain, A. Walsh, Best practices in machine learning for chemistry, Nature Chemistry 13 (6) (2021) 505–508. doi:10.1038/s41557-021-00716-z.

[10] L. Breiman, Random forests, Machine Learning 45 (1) (2001) 5–32. doi:10.1023/A:1010933404324.

[11] F. Pedregosa, G. Varoquaux, A. Gramfort, V. Michel, B. Thirion, O. Grisel, M. Blondel, P. Prettenhofer, R. Weiss, V. Dubourg, J. Vanderplas, A. Passos, D. Cournapeau, M. Brucher, M. Perrot, E. Duchesnay, Scikit-learn: Machine learning in Python, Journal of Machine Learning Research 12 (2011) 2825–2830.

[12] S. M. Lundberg, S.-I. Lee, A unified approach to interpreting model predictions, Advances in Neural Information Processing Systems 30 (2017) 4765–4774.

[13] T. Froitzheim, L. Kunze, S. Grimme, J. M. Herbert, J.-M. Mewes, Benchmarking charge-transfer excited states in TADF emitters: ΔDFT outperforms TD-DFT for emission energies, J. Phys. Chem. A 128 (30) (2024) 6324–6335. doi:10.1021/acs.jpca.4c03273.

[14] R. Keruckiene, A. A. Vaitusionak, M. I. Hulnik, I. A. Berezianko, D. Gudeika, S. Macionis, M. Mahmoudi, D. Volyniuk, D. Valverde, Y. Olivier, K. L. Woon, S. V. Kostjuk, S. Reineke, J. V. Grazulevicius, G. Sini, Is a small singlet–triplet energy gap a guarantee of tadf performance in mr-tadf compounds? impact of the triplet manifold energy splitting, Journal of Materials Chemistry C 12 (10) (2024) 3450–3464. doi:10.1039/d3tc04397e.

[15] Y. Liu, M. Nishiura, Y. Wang, Z. Hou, π-conjugated aromatic enynes as a single-emitting component for white electroluminescence, Journal of the American Chemical Society 134 (2012) 5592–5593. doi:10.1021/ja3073925.

[16] H. Uoyama, K. Goushi, K. Shizu, H. Nomura, C. Adachi, Highly efficient organic light-emitting diodes from delayed fluorescence, Nature 492 (7428) (2012) 234–238. doi:10.1038/nature11687.

[17] M. Y. Wong, E. Zysman-Colman, Purely organic thermally activated delayed fluorescence materials for organic light-emitting diodes, Advanced Materials 29 (2017) 1703554. doi:10.1002/adma.201701354.

[18] S. Veglianti, A. Michieletti, D. Padula, Toward circularly polarized luminescence from inherently chiral inverted singlet–triplet chromophores, ACS Materials Letters 7 (10) (2025) 3220–3226. doi:10.1021/acsmaterialslett.5c00872.

[19] E. Salvi, G. Agostini, S. Veglianti, G. J. Costa, L. De Vico, D. Padula, C. A. Guido, On the role of electronic correlation and state-specific environment polarization in singlet–triplet gap inversion, J. Comput. Chem. 46 (30) (2025) e70267. doi:10.1002/jcc.70267.

[20] R. Gómez-Bombarelli, J. Aguilera-Iparraguirre, T. D. Hirzel, D. Duvenaud, D. Maclaurin, M. A. Blood-Forsythe, H. S. Chae, M. Einzinger, D.-G. Ha, T. Wu, G. Markopoulos, S. Jeon, H. Kang, H. Miyazaki, M. Numata, S. Kim, W. Huang, S. I. Hong, M. Baldo, R. P. Adams, A. Aspuru-Guzik, Design of efficient molecular organic light-emitting diodes by a high-throughput virtual screening and experimental approach, Nature Materials 15 (2016) 1120–1127. doi:10.1038/nmat4717.

[21] K. Thapa, J. I. Jones, L. E. Ratcliff, A high throughput virtual screening approach for identifying new thermally activated delayed fluorescence-based emitters, J. Mater. Chem. C 13 (37) (2025) 19212–19225. doi:10.1039/d5tc01938a.

[22] L. Barneschi, L. Rotondi, D. Padula, Molecular geometry impact on deep learning predictions of inverted singlet–triplet gaps, J. Phys. Chem. A 128 (12) (2024) 2417–2426. doi:10.1021/acs.jpca.4c00172.

[23] Y. Li, C. Li, Efficient prediction of singlet–triplet gaps in delayed fluorescence emitters using Kohn–Sham orbital energies, J. Phys. Chem. Lett. 17 (1) (2026) 141–148. doi:10.1021/acs.jpclett.5c03449.

[24] A. Nigam, R. Pollice, P. Friederich, A. Aspuru-Guzik, Artificial design of organic emitters via a genetic algorithm enhanced by a deep neural network, Chem. Sci. 15 (7) (2024) 2618–2639. doi:10.1039/d3sc05306g.

[25] Z. He, H. Zhang, Y. Wang, W. Yang, J. Chen, H. Bi, Multiagent data mining for enhanced machine learning prediction of delayed fluorescence materials, ACS Omega 11 (31) (2026) 46279–46289. doi:10.1021/acsomega.6c03486.
URL http://dx.doi.org/10.1021/acsomega.6c03486

[26] D. Huang, J. M. Cole, A database of thermally activated delayed fluorescent molecules auto-generated from scientific literature with ChemDataExtractor, Scientific Data 11 (1) (Jan. 2024). doi:10.1038/s41597-023-02897-3.
URL http://dx.doi.org/10.1038/s41597-023-02897-3