


University of Lagos
Metallurgical & Materials Engineering Laboratory

Tensile Test Report

Customer Name : Operator : Pogoson Test Period 6/30/2026 20:11
Material Name : PETG CF YZ Test Standard : ASTM D638 Specifications
Test Speed 5.000mm/min Gauge Length : 25.000mm

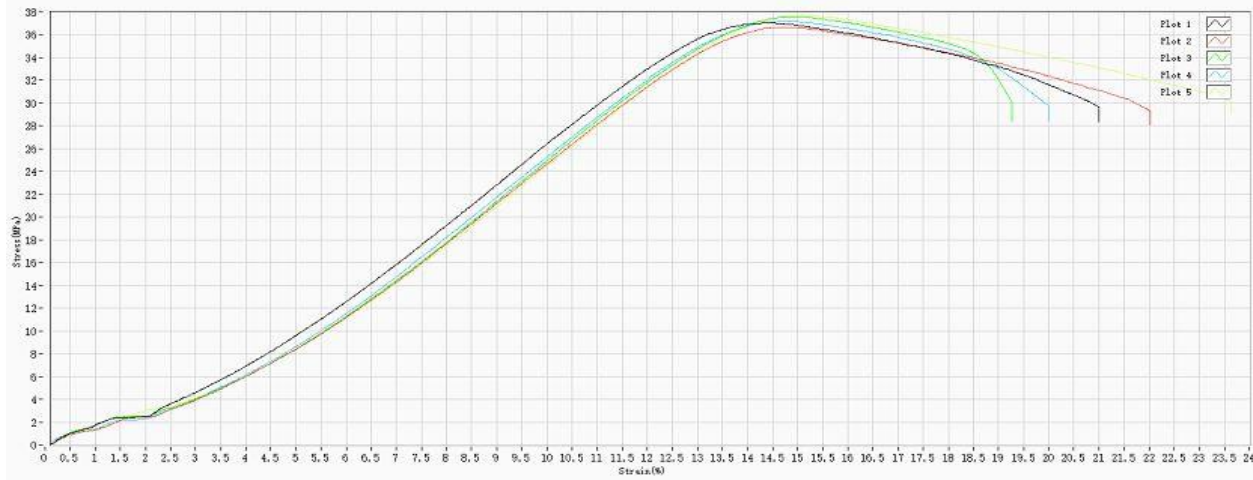

No.	OutDia.(mm)	Thickness(mm)	Width(mm)	Force @ Peak(N)	Tensile Stress(MPa)	elongation percentage @ break(%)	Elong. @ Peak(mm)	ElasticityCoe.(N/mm)	Yong's Modules(MPa)	Strength @ upper yield point(MPa)	
1	0	3.73	6.2	856.121	37.02	21.005	3.573	269.113	290.92	36.977	
2	0	3.77	6.25	862.986	36.626	22.019	3.613	266.559	282.827	16.482	
3	0	3.75	6.2	873.773	37.582	19.275	3.762	267.427	287.556	37.539	
4	0	3.75	6.15	857.102	37.165	19.998	3.648	268.332	290.881	16.712	
5	0	3.73	6.25	878.676	37.692	23.65	3.734	261.428	280.358	16.953	
Mean	-	-	-	865.732	37.217	21.189	3.666	266.572	286.508	24.933	