


PREFIXED OBJECTIVES OF SAND 260821 :

Fineness Modul (2,85).....(2,7 a 3).....real.....3,07
Fines 1 (5%).....(2 a 5 %).....real.....1,97%
Sand Equivalent (2,85).....(80 al 85 %).....real.....85,3 %

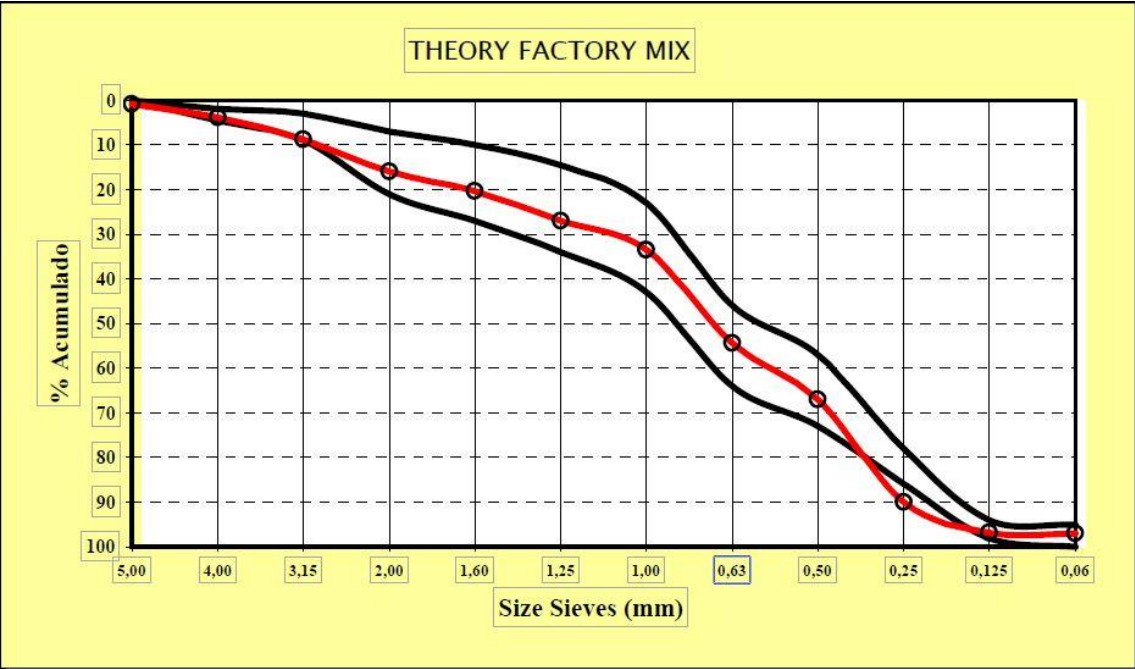

GRANULOMETRY.

The optimum sand for the production should be of the following granulometry.

nº Sieve.	Size in mm.	%	% of the total
4	4,76	0	0
8	2,38	10	10
12	1,7	17	7
116	1,19	27	10
30	0,59	57	30
50	0,297	78	21
100	0,149	94	16
200	0,074	97	3
Powder	0,05		3
			100

GRANULOMETRY.

PREFIXED OBJECTIVES :

Fineness Modul (2,85).....(2,7 a 3).....real.....**3,07**
Fines 1 (5%).....(2 a 5 %).....real.....**1,97%**
Sand Equivalent (2,85).....(80 al 85 %).....real.....**85,3 %**

FINENESS MODUL

The calculation is made by adding the retained percentages of the sieves.

4+2+1+0,5+0,25+0,125 and dividing them by 100.



FINES 1

It is the loss of fines that passes through the sieve of 0.0623 mm with the help of water (it is called fine washing)

The percentage of fines lost due to this washing is valued as a percentage



GRANULOMETRY.

SAND EQUIVALENT.

The sand equivalent test indicates the ratio between the granular and clay elements of an aggregate (sand).

Sand Equivalent (EA) = (Sand measuring / Clay measuring) x 100

There is very little difference between the values sand and the upper part of the clay.



Arganda del Rey 260821